

Thermally Drawn Polycaprolactone Fibres with Customised Cross Sections

Syamak Farajikhah^{a*}, Ivan D. Rukhlenko^a, Alessio Stefani^{a,b}, Maryanne Large^a,
Wojciech Chrzanowski^{c,d}, and Simon Fleming^{a,d}

^aInstitute of Photonics and Optical Sciences (IPOS), School of Physics, The University of Sydney, 2006, NSW, Australia; ^bDTU Fotonik, Department of Photonics Engineering, Technical University of Denmark, DK-2800 Kgs. Lyngby, Denmark; ^cSchool of Pharmacy, The University of Sydney, 2006, NSW, Australia; ^dSydney Nano Institute, The University of Sydney, 2006, NSW, Australia

ABSTRACT

There is growing demand for biodegradable polymer fibres in tissue engineering and nerve regeneration. We demonstrate a scalable and inexpensive fabrication technique to produce polycaprolactone (PCL) fibres using fibre-drawing technique. Here we report on the first successful drawing of hollow-core and solid-core PCL fibres of different cross sections. The demonstrated capacity to tailor the surface morphology of PCL fibres, together with their biodegradability and tissue compatibility, makes them a unique material base for tissue engineering and nerve regeneration applications.

Keywords: biodegradable fibres, thermally drawn fibres, polymer fibres, polycaprolactone

1. INTRODUCTION

Over the last decades, natural and synthetic polymer scaffolds have emerged as an alternative to biological grafts in tissue engineering¹. There have also been an increasing interest in using fibrous structures for biomedical applications². Biodegradable polymers such as polycaprolactone (PCL) have attracted a particular attention as compared to other polymeric materials for applications such as tissue engineering³ and optical neural interfaces⁴. Polymeric materials as substrates for cell growth are crucial for the production of platforms for cell culture and tissue engineering. Their high biocompatibility, tissue-like mechanical properties, and appropriate surface morphology are essential for biomedical applications⁵.

Surface features such as grooves in polymer and fibre scaffolds have already been demonstrated to have a strong influence on nerve cell regeneration⁶. Following our previous works on drawing soft polymer fibre materials⁷, here we report on the first time (to the best of our knowledge) successful drawing of solid-core and hollow-core PCL fibres with tailored cross sections using the well-established fibre drawing technique, used for making optical fibre, involving drawing in a furnace from a macroscale preform. Our fibres benefit from high flexibility (relatively low Young's modulus), biodegradability, tuneability of surface morphology, and ease of handling, which make them an ideal material base for tissue engineering, nerve regeneration, and implantable biomedical devices.

2. RESULTS AND DISCUSSION

The melting point and decomposition temperature of PCL (Polysciences, Inc., MW 80000) are the key parameters for drawing a polymer fibre. They were measured using differential scanning calorimetry (DSC) and thermal gravimetric analysis (TGA). According to Figure 1a and Figure 1b, the melting point of PCL is about 55°C while the decomposition of PCL starts at 350°C. These give us a relatively broad temperature range to work over.

Three preforms schematised in Figure 1c to Figure 1e were prepared to explore the possibility of drawing submillimetre PCL fibres with different internal and external features. The preforms were fabricated by melting PCL pellets inside polypropylene or Teflon moulds (with an outer diameter of 15 mm) at 80°C for 17 hours. The PCL fibres were then successfully drawn and collected on spools using a fibre drawing tower. The drop-off temperature was set to 90°C while the subsequent drawing was performed at 85°C. The preform was fed downwards into a furnace at a constant rate of 2 mm/min, and the fibres were drawn with a capstan wheel at rates of 0.5 to 1.5 m/min.

*syamak.farajikhah@sydney.edu.au; phone +61 2 86277994

Figure 1f to Figure 1h show the optical micrographs of the PCL fibres drawn from the preforms in Figure 1c to Figure 1e. The original external and internal features of the preforms were successfully preserved in submillimetre PCL fibres without pressurising the preforms over the draw process or without using a cladding material.

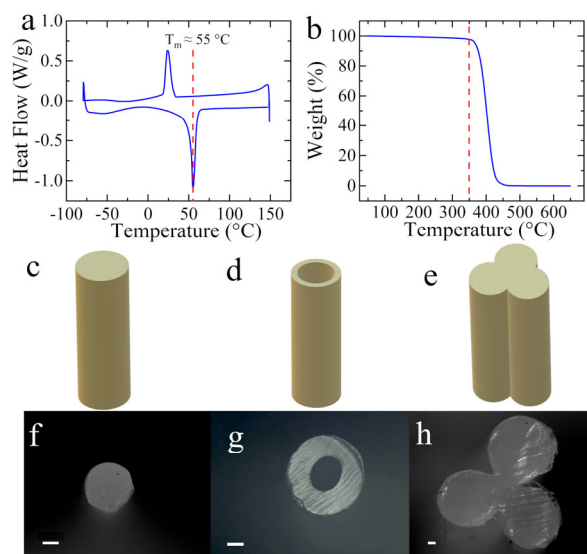


Figure 1. (a) DSC and (b) TGA spectra of PCL showing its melting point and decomposition temperature respectively, (c)-(e) preforms for making solid-core, hollow-core, and grooved PCL fibres, and (f)-(h) optical micrographs of the respective PCL fibres (all the scale bars are 100 μm) demonstrating the preservation of the shape of the preforms' cross section.

To summarise, we have successfully drawn submillimetre PCL polymer fibres with internal and external features using a well-established melt-drawing technique without pressurising the preforms or using an etchable cladding. The produced fibres are highly flexible, biocompatible, biodegradable, and easy to handle. These characteristics make them a promising material for various biomedical applications, including tissue engineering, nerve regrowth and implantable biomedical devices.

3. ACKNOWLEDGEMENTS

We gratefully acknowledge the Australian Research Council Discovery Project DP170103537, the Marie Skłodowska-Curie grant of the European Union's Horizon 2020 research and innovation programme (708860), and the technical assistance of Peter Henry and facilities of the Research & Prototype Foundry Core Research Facility at the University of Sydney, part of the Australian National Fabrication Facility

REFERENCES

- [1] Diaz-Gomez, L., García-González, C. A., Wang, J., Yang, F., Aznar-Cervantes, S., Cenis, J. L., Reyes, R., Delgado, A., Évora, C., Concheiro, A. and Alvarez-Lorenzo, C., "Biodegradable PCL/fibroin/hydroxyapatite porous scaffolds prepared by supercritical foaming for bone regeneration," *Int. J. Pharm.* **527**(1–2), 115–125 (2017).
- [2] Farajikhah, S., Cabot, J. M., Innis, P. C., Paull, B. and Wallace, G., "Life-Saving Threads: Advances in Textile-Based Analytical Devices," *ACS Comb. Sci.* **21**(4), 229–240 (2019).
- [3] Mo, X., Weber, H. J. and Ramakrishna, S., "PCL-PGLA composite tubular scaffold preparation and biocompatibility investigation," *Int. J. Artif. Organs* **29**(8), 790–799 (2006).
- [4] Park, S., Loke, G., Fink, Y. and Anikeeva, P., "Flexible fiber-based optoelectronics for neural interfaces," *Chem. Soc. Rev.* **48**(6), 1826–1852 (2019).
- [5] Abdal-hay, A., Abdelrazek Khalil, K., Al-Jassir, F. F. and Gamal-Eldeen, A. M., "Biocompatibility properties of polyamide 6/PCL blends composite textile scaffold using EA.hy926 human endothelial cells," *Biomed. Mater.* **12**(3), 035002 (2017).
- [6] Koppes, R. A., Park, S., Hood, T., Jia, X., Abdolrahim Poorheravi, N., Achyuta, A. H., Fink, Y. and Anikeeva, P., "Thermally drawn fibers as nerve guidance scaffolds," *Biomaterials* **81**, 27–35 (2016).
- [7] Kaysir, M. R., Stefani, A., Lwin, R. and Fleming, S., "Flexible optical fiber sensor based on polyurethane," 2017 Conf. Lasers Electro-Optics Pacific Rim **170103537**(708860), 1–2 (2017).