

**Point defect induced incommensurate dipole moments in the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  Dion-Jacobson layered perovskite**

KONG, J., NAYAK, S.K., CO, K., NAYAK, S., WU, J., FETEIRA, Antonio <<http://orcid.org/0000-0001-8151-7009>>, BEYER, K.A., ALPAY, S.P. and PRAMANICK, A.

Available from Sheffield Hallam University Research Archive (SHURA) at:  
<http://shura.shu.ac.uk/29822/>

---

This document is the author deposited version. You are advised to consult the publisher's version if you wish to cite from it.

**Published version**

KONG, J., NAYAK, S.K., CO, K., NAYAK, S., WU, J., FETEIRA, Antonio, BEYER, K.A., ALPAY, S.P. and PRAMANICK, A. (2021). Point defect induced incommensurate dipole moments in the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  Dion-Jacobson layered perovskite. *Physical Review B*, 104 (22).

---

**Copyright and re-use policy**

See <http://shura.shu.ac.uk/information.html>

# **Point defect induced incommensurate dipole moments in $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ Dion-Jacobson layered perovskite**

J. Kong,<sup>1</sup> S. K. Nayak,<sup>2</sup> K. Co,<sup>2</sup> S. Nayak,<sup>1,\$</sup> J. Wu,<sup>1</sup> A. Feteira,<sup>3</sup> K. A. Beyer,<sup>4</sup> S. P. Alpay,<sup>2,5</sup>  
and

A. Pramanick<sup>1,\*</sup>

<sup>1</sup>*Department of Materials Science and Engineering, City University of Hong Kong, Hong Kong SAR, China*

<sup>2</sup>*Department of Materials Science and Engineering, University of Connecticut, Storrs 06269-CT, USA*

<sup>3</sup>*Materials and Engineering Research Institute, Sheffield Hallam University, Sheffield, S1 1WB, UK.*

<sup>4</sup>*Advanced Photon Source, Argonne National Laboratory, Lemont 60439-IL, USA*

<sup>5</sup>*Department of Physics, University of Connecticut, Storrs 06269-CT, USA*

\*Corresponding author: [apramani@cityu.edu.hk](mailto:apramani@cityu.edu.hk); \$present address: Indian Institute of Technology, Madras

---

## Abstract

Local structural distortions due to isolated atomic defects and defect complexes strongly affect the macroscopic properties of oxide ceramics. While the characterization of local defect structures is more common in simple  $ABO_3$  perovskites, unambiguous determination of the same in layered perovskites is more difficult due to their complex crystal structures. Here, we combined x-ray pair distribution function and density functional theory calculations to characterize the structure of cation-oxygen divacancy pairs in a Dion-Jacobson (D-J) layered perovskite. Our study indicates that local incommensurate dipole moments with polarization density in the range of  $\sim 0.1\text{-}17 \mu\text{C}/\text{cm}^2$  are created due to divacancy-induced structural distortions in the D-J phase  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ . This is comparable to defect dipole moments observed in well-known perovskite ferroelectrics. The current results imply that controlling the atomic defects can potentially lead to significant control of dielectric properties in D-J layered perovskites.

## Introduction

Interest in layered perovskites has grown in recent years due to their novel functionalities such as high- $k$  dielectrics, high  $T_C$  superconductors, catalysis, and quantum magnetism.[1–5] The unique properties of layered perovskites can be attributed to their 2-dimensional slab structure, whereby discrete  $ABO_3$  perovskite-like layers are separated by interlayer structural motifs such as alkali metal ions or  $Bi_2O_2$  fluorite units. Dion-Jacobson (D-J) phases are one such class of layered perovskites with the general formula of  $A'[A_{m-1}B_mO_{3m+1}]$ , where  $A'$  is an alkali metal and  $m$  represents the number of octahedral layers within each perovskite slab.[6,7,8] In recent years, D-J phase oxides have gained attention due to their numerous existing and potential applications, such as tunable and high-temperature dielectrics, photocatalysis, photovoltaic electrode materials, and a new generation of high-temperature superconductors.[9–14] Furthermore, ferroelectric instability in some D-J phase oxides and D-J phase oxide-derived nanosheets has broadened the application range of these materials.[15,16] Despite several experimental studies on the crystal structure of D-J phases, the exact determination of their atomic structure can be difficult due to complex local structural distortions.[17–21] In this regard, a critical source of local structural distortions is point defects such as cation or oxygen vacancies, which result as an unintended consequence of high-temperature processing and may have a significant impact on material properties. Indeed, earlier studies indicated that local electrical dipoles and structural distortions arising from point defects significantly influence functional properties in  $ABO_3$  perovskites, such as electrical polarization and dielectric relaxation.[22,23] It is also acknowledged that cation and oxygen vacancies may influence functional properties of D-J phases, such as electrical conductivity, dielectric permittivity, and photocatalytic activity.[24–27] In order to better understand the effect of atomic-scale defects on

macroscopic properties, it is essential to characterize the local structure of the defect centers. However, detailed characterization of local defect structures in D-J phase compounds is currently lacking.

Characterization of local structural distortions due to atomic defects has remained a challenging task. In the past, local defect structures in  $ABO_3$  perovskite ferroelectrics were characterized using techniques such as electron paramagnetic resonance (EPR) or positron annihilation spectroscopy [28–34] which nevertheless have their own limitations. EPR can be used only for paramagnetic ions. Positron annihilation spectroscopy can infer characteristic defect types, but their structure is difficult to decipher. Furthermore, microscopic techniques such as high-resolution transmission electron microscopy (HRTEM) suffer from surface-related effects and artifacts related to sample preparation. In recent years, efforts have been made to characterize local structure around defects using the pair distribution function (PDF), derived from total x-ray or neutron scattering experiments.[35,36] However, unambiguous determination of defect structure using the PDF alone can be challenging. Notably, for layered perovskite D-J phases, the presence of four or more elemental components and a sandwich of multiple structural forms open a multitude of possibilities for defects, which complicates the determination of exact local structural distortions introduced by defects. In this regard, density functional theory (DFT) can narrow the possible space of defect complexes based on energy considerations as well as taking into account local atomic chemistry and charge balance requirements.[37–44] Thus, pairing x-ray scattering data with *ab initio* computations holds significant potential advantages.

Here, we demonstrate the characterization of local defect-induced structural distortions in the prototypical D-J layered perovskite,  $KCa_2Nb_3O_{10}$ , using combined x-ray total scattering

experiments and DFT calculations. Our study indicates the presence of large local dipole moments density due to Ca-O vacancy pairs (or divacancies) in  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ , akin to other well-known perovskites such as  $\text{PbTiO}_3$ . The defect-induced local dipoles are likely a contributing factor to the dielectric relaxation and nonlinearity measured for this material. The current result implies that local defect dipoles should be an important factor in discussing the functional properties of D-J phase compounds.

## Experiment

$\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics were prepared by a conventional solid-state synthesis method. Stoichiometric amounts of  $\text{K}_2\text{CO}_3$  (Sigma Aldrich, 99.7 %),  $\text{CaCO}_3$  (Sigma Aldrich, nominal purity 100.0 %),  $\text{Na}_2\text{CO}_3$  (Sigma Aldrich, nominal purity 100.0 %), and  $\text{Nb}_2\text{O}_5$  (Sigma Aldrich, 99.9 %) were ball-milled in ethanol for 24 h. The powder samples were dried in the oven at 100 °C for 2 hours before weighing to remove adsorbed moisture. The mixed powder slurry was dried and then calcined in the temperature range of 1200°C for 12 h. The calcined powders were ground, mixed with polyvinyl alcohol (PVA), and sieved through 100  $\mu\text{m}$  mesh. The granulated powders were pressed into pellets of diameter 10 mm and thickness 1 mm with a pressure  $\sim 34.5$  MPa. The pellets were placed in an alumina crucible and sintered in air at 1325 °C for 4 hours. During sintering, the green pellets were covered with powders of the same composition of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  to limit volatilization of certain elements, such as K, Ca, and Nb. The x-ray diffraction pattern of synthesized  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  could be indexed with a Dion-Jacobson phase structure, indicating that we have successfully synthesized the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  compound with no evident secondary phases. (see details in Supplemental Material Section A) [45].

The frequency-dependent ( $100 \text{ Hz} \leq f \leq 1 \text{ MHz}$ ) dielectric properties of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  at low electric fields (0.1 V ac) were measured using an LCR meter (Agilent-4284A, Technologies).

The high-field electrical polarization of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  was characterized from polarization-electric field (P-E) hysteresis loops, using a Radiant Precision LC-II Ferroelectric Test System (2835 Pan American Fwy).

High-energy synchrotron x-ray total scattering data at room temperature were collected at the beamline 11-ID-B of the Advanced Photon Source, Argonne National Laboratory, using a wavelength of  $\lambda = 0.2113 \text{ \AA}$ . The samples were loaded in  $\text{\AA}1\text{mm}$  quartz capillaries. The scattered intensity was recorded at a sample to detector distance of 170 mm with Debye-Scherrer geometry in transmission mode on a large amorphous-Si TFT panel detector. The local structure was characterized by the atomic pair distribution function  $G(r)$ , obtained from the x-ray total scattering intensity pattern. The high-energy x-ray scattering results were corrected for the sample absorption, background, Compton scattering, and incident flux. The normalized intensities were reduced to the structure factor  $S(Q)$ , which was then Fourier transformed using the function:

$$G(r) = \frac{2}{\pi} \int_{Q_{\min}}^{Q_{\max}} Q [S(Q) - 1] \sin(Qr) dQ \quad (1)$$

to achieve the corresponding PDFs, where  $Q$  is the momentum transfer and is defined as  $Q = 4\pi \sin(\theta) / \lambda$ . The PDF conversion was executed in the software PDFgetX2 [46], and the  $Q_{\max}$  used was  $19 \text{ \AA}^{-1}$  (see details in Supplemental Material Section B) [45]. The pair distribution function was analyzed using the software PDFGui.[47] The synchrotron x-ray diffraction pattern was analyzed by Rietveld refinement using *FullProf* software.[48]

Raman measurements were carried out in a backscattering geometry using a Thermo Scientific DXR<sup>TM</sup>2 Raman microscope equipped with a laser of 532 nm with a maximum power of 10 mW.

## Results and Discussion

### Electrical Properties

Fig.1(a) shows the low-field dielectric constant ( $\epsilon'$ ) and dielectric loss ( $\tan \delta$ ) of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics at room temperature as a function of frequency. The dielectric constant is higher for lower frequencies due to contributions from dipolar and interfacial polarization but stabilizes for frequencies higher than  $10^4$  Hz. Fig.1 (b) shows the temperature-dependent dielectric constant and dielectric loss, exhibiting large dielectric relaxation at high temperatures for  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics. Notably, the dielectric loss for this material in this study is observed to be lower ( $\sim 0.11$  at 100 Hz ) as compared to previous studies [9,49]. The high-field dielectric permittivity was characterized from the P-E hysteresis loops of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics, which were measured with an applied ac electric field of amplitude  $E \leq 210$  kV/cm and frequency  $f = 10$  Hz as shown in Fig.1(c). Details for calculation of the high-field permittivity from the P-E loops are provided in Section C of the Supplemental Material [45] (see also references [50,51] therein). The dielectric permittivity as a function of electric field amplitude is shown in Figure 1(d). A nonlinear increase in  $\epsilon'$  can be observed for electric field amplitudes greater than 180 kV/cm. Such unusual properties, that is, a large dispersion of  $\epsilon'$  with frequency and nonlinear increase in  $\epsilon'$  with electric field amplitude, can potentially arise in centrosymmetric ionic compounds as a result of relaxation or reorientation of local dipoles created due to point defects.[39,52,53] Compositional analysis of the synthesized  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  powders indicated a significant presence of ionic vacancies (See details in Section D of the Supplemental Material) [45]. In order to better understand the vacancies induced local dipoles for the layered perovskite  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ , we undertook a detailed structural characterization of this material.



## Description of Rietveld and PDF refinements

The Rietveld refinement of the x-ray diffraction data is shown in Fig. 2(a), which indicates that the long-range crystal structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  is orthorhombic with the  $Cmcm$  space group, and the lattice parameters:  $a = 3.8787(2) \text{ \AA}$ ,  $b = 29.5385(15) \text{ \AA}$ , and  $c = 7.7219(4) \text{ \AA}$ . For the current refinement, the average crystal structure of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  phase determined by Fukuoka et al. [54] was used as a starting point (see details in Section E.1. of Supplemental Material) [45]. The atomic positions in the long-range average structure are listed in Table 1. The corresponding unit cell structure is shown in Fig.2(b), composed of two perovskite slabs of  $\text{Ca}_2\text{Nb}_3\text{O}_{10}$  and K ions sandwiched between the perovskite blocks. Both the terminal (next to K ions) and inner (central) layer octahedra exhibit tilting around the a and b axes at room temperature. The complex crystal structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  has three different cations that are significantly different in terms of their ionic radii and nature of cation-oxygen bonding, which makes local deviations from long-range average structure likely; such as consider that such local deviations also exist in simple perovskite  $\text{BaTiO}_3$  with ionic Ba-O and covalent Ti-O bond[55]. The presence of ionic vacancies is also expected to cause local structural distortions [35]. Therefore, we examined the short-range local atomic structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  from analysis of its x-ray pair distribution function or  $G(r)$ . The structure parameters obtained from Rietveld refinement were used as a starting point for fitting the x-ray  $G(r)$ . Fig. 2(c) compares the model  $G(r)$  based on the average long-range structure and the experimentally observed x-ray PDF. In Fig. 2(c), the model  $G(r)$  is calculated by refining only the lattice parameters and the atom displacement parameter (ADPs) to best fit the observed  $G(r)$ , while keeping the atomic coordinates the same as that obtained from fitting of the Bragg peaks. The experimentally observed  $G(r)$  and the calculated  $G(r)$  based on the average structure are close to each other for  $r$

$> 6 \text{ \AA}$ , which indicates that they approximately converge for  $r > 6 \text{ \AA}$ . However, there are notable differences between the experimental and the calculated  $G(r)$  for the average structure for  $r < 6 \text{ \AA}$ , most prominently in the region marked by a green oval in Fig. 2(c), which has the most contribution from the nearest and the next-nearest neighbor Nb-O, Ca-O and O-O interatomic correlations (see Fig.S5 in Supplemental Material [45]). It is known that nearest-neighbor correlated atomic motions can influence the peak intensity for pair-wise atomic correlations in the short range.[56,57] Therefore, we accounted for the effect of correlated atomic motions by refining the displacement correlation parameter  $\delta_2$  at low temperatures.[58] In this case, we fitted the experimental  $G(r)$  by refining  $\delta_2$ , in addition to lattice parameters and the ADPs. As shown in Fig. 2(d), including  $\delta_2$  in the refinement could reproduce the peak intensity of the nearest neighbor Nb-O correlations ( $\delta_2 = 3.23 (4.7e^{-5})$ ), which means that atomic motions of Nb and O can be highly correlated. However, the next two peaks Ca-O/O-O in the  $G(r)$ , cannot be fit well even while refining  $\delta_2$ , particularly for the shorter Ca-O/O-O distances at  $r \sim 2.4 \text{ \AA}$ . This can be explained due to the predominantly covalent character of the Nb-O bonds, in contrast to the predominantly ionic Ca-O bonds [57]. Thus, it is difficult to describe the experimentally observed difference between the average and local structures of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  as a result of correlated dynamic atomic motions alone. Effort to fit the experimental  $G(r)$  by undertaking a full refinement of the structure, including lattice parameters, atomic positional coordinates, and APDs, provided a reasonable fit for  $r > 6 \text{ \AA}$ , but also did not provide a good fit in the low- $r$  range covering nearest-neighbor distances (i.e.  $r < 6 \text{ \AA}$ ) (details are provided in section E.3. of the Supplemental Material [45]).

It is known that D-J phase compounds are highly amenable to non-stoichiometry.[24-27] X-ray photoelectron spectroscopy (XPS) indicated that Ca and K vacancies are the major defect

species in the synthesized powders (see Table S1 [45]). However, the fundamental charge neutrality condition dictates that the cation vacancies should be ideally compensated by anion vacancies, in this case, oxygen vacancies, in the form of cation-oxygen divacancy pairs. This is also supported by the exhibition of good insulating properties of the synthesized ceramics, with a very low dielectric loss at room temperature as shown in Fig. 1(a), which otherwise may show enhanced electron (hole) conductivity due to excitation of low-lying defects states into the conduction (valence) band. Moreover, due to the complex crystal structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ , various types of divacancy configurations are also possible. Therefore, to investigate the most likely isolated vacancy and divacancy complexes, we undertook a detailed characterization of the vacancy and divacancy formation energies for  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  using DFT.

### **DFT computation of defect formation energies**

First-principles calculations are performed with DFT using the plane-wave pseudopotential method.[59,60] Non-spin-polarized calculations are performed with generalized gradient approximation (GGA) with Perdew-Burke-Ernzerhof parametrization as the exchange-correlation functional.[61] The core and valence electrons are treated with the projector augmented wave method.[62] The kinetic energy cutoff for the plane waves is set to 500 eV. For the defect models, the basis vectors of the unit cell have been expanded to  $2 \times 1 \times 2$  supercells containing 256 atoms. Fig. 3(a) shows the [100] projection of the supercell with all inequivalent atom types indicated by differentiating colors. The atomic positions of defect models were thoroughly optimized to minimize the residual interatomic forces. The integrations in the Brillouin zone are performed in a discretized Monkhorst-Pack [63]  $k$ -points mesh of  $2 \times 2 \times 2$  for the geometrical optimization. Geometrical optimization for the models is carried out with the tolerance for total energy convergence set to  $1.0 \times 10^{-7}$  eV. The calculations are performed

with the Vienna Ab Initio Simulation Package (VASP).[64,65] The volume relaxed lattice parameters were found to be  $a = 3.95 \text{ \AA}$ ,  $b = 29.98 \text{ \AA}$ ,  $c = 7.83 \text{ \AA}$ , which match with those obtained from our Rietveld refinement of the x-ray diffraction pattern, and also consistent with earlier studies.[54]

The centrosymmetric crystal structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  has one type of K atom site, two symmetry inequivalent Ca (Ca1 and Ca2) atom sites, two symmetry inequivalent Nb (Nb1 and Nb2) atom sites, and seven symmetry inequivalent O (O1,..., O7) atom sites, see Fig.3(a). The defect models were created to span all possible isolated vacancies ( $V_{\text{K}}$ ,  $V_{\text{Ca1}}$ ,  $V_{\text{Ca2}}$ ,  $V_{\text{Nb1}}$ ,  $V_{\text{Nb2}}$ ,  $V_{\text{O1}}$ ,...,  $V_{\text{O7}}$ ), constituting a total of 12 configurations (see the label of Fig. 3(b)), as well as divacancy cases forming nearest-neighbor cation-oxygen vacancy pairs, constituting a total of 18 configurations (see the label of Fig.3(c)).

The formation energy ( $E_{\text{F}}$ ) of defects is calculated from the total energy of defect supercell ( $E_{\text{Defect Supercell}}$ ), and the total energy of stoichiometric host ( $E_{\text{Host}}$ ) as: [66,67]

$$E_{\text{F}} = E_{\text{Defect Supercell}} - E_{\text{Host}} + \sum_i p_i n_i \mu_i \quad (2)$$

where  $\mu_i$  is the chemical potential of species  $i$ , their number  $n_i$ , and the factor  $p_i$  equals to  $-1$  ( $+1$ ) for atoms added to (removed from) the host to construct the defect supercell. The  $\mu$  for K, Ca, Nb, and O is derived from the total energies of standard oxides  $\text{K}_2\text{O}$ ,  $\text{CaO}$ ,  $\text{Nb}_2\text{O}_5$ , and  $\text{O}_2$  molecule, respectively. The formation energies of all the different ionic defects are provided in table S2 in the Supplemental Material section F.1 [45].

The average  $E_{\text{F}}$  of isolated vacancies,  $V_{\text{K}}$ ,  $V_{\text{Ca}}$ ,  $V_{\text{Nb}}$ , and  $V_{\text{O}}$  are 1.68 eV, 0.96 eV, 3.27 eV, and 1.77 eV, respectively (see Table S2 [45]). Among these, the most notable is the  $V_{\text{O3}}$

vacancy, which is energetically most favorable with  $E_F = 0.06$  eV. Therefore, although XPS data did not reveal O deficiency, which is likely due to lower sensitivity and surface adsorbed O, it is expected that O vacancies will form in this material. The DFT results also imply that the oxygen vacancy is more likely to appear between the perovskite sublayers, that is  $V_{O3}$ , than the interfacial region between the perovskite slab and K atoms. Moreover, analysis of the formation energies of cation vacancy-oxygen vacancy pairs shows that  $V_{Ca}-V_{O3}$  (Ca includes Ca1 and Ca2) are more probable vacancy complexes than  $V_{Ca}-V_O$  (O includes O1, O2, O4, and O5),  $V_K-V_O$ , or  $V_{Nb}-V_O$ . Importantly, the negative formation energies for  $V_{Ca}-V_{O3}$  indicates the likely existence of  $V_{Ca}-V_{O3}$  in  $KCa_2Nb_3O_{10}$ .

In well-known perovskite ferroelectrics, it is traditionally understood that electrical polarization originates from the off-centered displacement of cations from their high-symmetry positions in the crystal lattice.[68] Therefore, a natural question arises on whether local atomic reconstruction around the  $V_{Ca}-V_O$  complex gives rise to local dipole moments? To get a better insight into this area, we re-analyzed the x-ray  $G(r)$  with input from DFT.

### **PDF analysis with input from DFT**

The short-range atomic correlations for the structures with cation-oxygen defect complexes are next compared against the experimental  $G(r)$ . To calculate  $G(r)$  from the DFT model structures, the lattice parameters and ADPs were refined to best reproduce the experimental  $G(r)$ , since the structure calculated from DFT is for 0 K (see details in Supplemental Material Section F.2.[45]). For fitting of  $G(r)$  with the inclusion of defect complexes, the displacement correlation parameter  $\delta_2$  was not refined, since their inclusion only provided marginal improvement in the fit (see Supplemental Material Section F.3.[45]) Fig. 4 (a-d) compares the experimental  $G(r)$  with the calculated  $G(r)$  based on DFT structures with (a) no vacancy, (b) Ca1 vacancy ( $V_{Ca1}$ ), (c) O3

( $V_{O3}$ ) vacancy, and (d) the  $V_{Ca1}$ - $V_{O3}$  divacancy pair. In Fig.4 (a), the calculated  $G(r)$  with no vacancies reproduce the experimentally measured  $G(r)$  except for the first three peaks, which correspond to the nearest-neighbor Nb-O, and Ca-O/O-O interatomic correlations. The supercells with  $V_{Ca1}$ (Fig.4 (b)) or  $V_{O3}$  (Fig.4 (c)) isolated vacancies can better reproduce the experimentally measured  $G(r)$ , as compared to the supercell with no vacancy, which is reflected from lower values of the weighted residuals  $R_w$  for these structures, and additionally, better reproduction of the first three peaks. However, considering electronic charge compensation in cation vacancy-anion vacancy pairs and the fact that the samples are highly insulating, the divacancy complex is more likely to form rather than isolated vacancies. Additionally, as can be seen from Figure 3(c), the divacancy pair of  $V_{Ca1(2)}$ - $V_{O3}$  has the lowest formation energy (see Table S2 in Supplemental Material [45]). Moreover, it can be observed from Fig. 4(d) and Figs. S7-S8 that  $R_w$  for the supercell structures with or  $V_{Ca1}$ - $V_{O3}$  are lower as compared to those of structures with  $V_{Ca1}$  or  $V_{Ca2}$ . Moreover,  $R_w$  for the supercell structures with  $V_{Ca1(2)}$ - $V_{O3}$  are among the lowest for all the structures, including other isolated vacancy modes as shown in Fig.S7 and divacancy modes as shown in Fig.S8 [45]. Therefore, taking into account both the defect formation energies and reproducibility of the  $G(r)$  based on the DFT calculated supercell structure, we can conclude that the  $V_{Ca1(2)}$ - $V_{O3}$  divacancies are the predominant defect complex present in the material. In the Kroger-Vink notation, the divacancy pair is represented as  $V_{Ca}'' - V_O^{**}$ , however, here, we will use the  $V_{Ca1(2)}$ - $V_{O3}$  notation without implying their possible ionization states. Similar results about tightly bound cation-oxygen divacancy pairs were obtained earlier for perovskite ferroelectrics in Ref. [69]. However, it is essential to note that the  $V_{Ca1(2)}$ - $V_{O3}$  divacancy pairs in  $KCa_2Nb_3O_{10}$  are oriented nearly orthogonal to the longer  $b$  axis. This can be compared with  $PbTiO_3$ -based perovskite ferroelectrics, where  $V_{Pb}$ - $V_O$  are oriented

along the longer  $c$ -axis.[37] Note that for the fits shown in Fig. 4, the displacement correlation factor  $\delta_2$  was not considered. As shown in Fig.S9 (of the Supplemental Material Section F.3. [45]), incorporation of  $\delta_2$  while refining the defect structures from DFT yielded only marginal improvements in the fits to the experimental  $G(r)$ . This suggests that the local structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  is more strongly affected by the ionic defect complexes, as considered here, than due to locally correlated atomic motions.

### Calculation of vacancy induced local dipole moment

Figure 5(a) shows the perovskite layers of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  supercell with the  $\text{V}_{\text{Ca}1}\text{-V}_{\text{O}3}$  divacancy oriented nearly parallel to the oxygen octahedral layers. The position of the oxygen octahedra and the Nb-O-Nb angle within the different perovskite layers are labeled using  $D_i^x$  and  $\beta_i^x$ , where the subscript  $i$  refers to their position along the  $c$ -axis and  $x$  denotes their position along the  $b$ -axis. The distortion parameters ( $D$ ) for the different O octahedra are represented in Fig.5 (b-d) by solid symbols for the supercell with no vacancy and by open symbols for the supercell with  $\text{V}_{\text{Ca}1}\text{-V}_{\text{O}3}$  divacancy. The distortion parameter ( $D$ ) is calculated using the following equation [70]:

$$D = \frac{1}{n} \left[ \sum_i^n \left( \frac{d_i - d}{d} \right)^2 \right] \quad (3)$$

where  $n$  is the coordination number (in this case,  $n=6$ ), and  $d_i$  and  $d$  are the individual and average values of the Nb-O bond lengths, respectively. For  $D_3^A$  and  $D_3^B$  (in Fig.5),  $n = 5$ , due to one missing oxygen.

For the structure with no vacancy, the O octahedra in the terminal layers ( $D_i^A$  and  $D_i^C$  are more distorted ( $D \sim 0.81\%$ ) as compared to the O octahedra in the inner layer ( $D_i^B$ ) with  $D \sim 0.01\%$ . With the introduction of the  $V_{Ca1}$ - $V_{O3}$  divacancy, all three layers exhibit additional distortion. However, the maximum change in  $D$  is observed for  $D_3^A$  (see Fig. 5(b) inset), which is closest to the  $V_{O3}$  site. Overall, while the  $V_{O3}$  is placed in between the inner and terminal octahedra, the inner layer exhibits a larger change in  $D$  as compared to the terminal layers.

Support for local structural distortions around the defect centers is further obtained from Raman scattering data. Figure 6 shows the Raman spectrum for the synthesized ceramics in the range of wavenumbers 400-1000  $\text{cm}^{-1}$ . The sharp peak at  $\sim 935 \text{ cm}^{-1}$  is due to the terminal short Nb-O bond ( $\sim 1.7 \text{ \AA}$ ) in the highly distorted octahedra of the terminal layers. In comparison, the peaks at  $\sim 580 \text{ cm}^{-1}$  and  $\sim 760 \text{ cm}^{-1}$  are due to the Nb-O bonds in the slightly distorted octahedra of the inner layer. The relative number of short Nb-O bonds in the terminal octahedra can be characterized from the intensity ratio,  $I(\sim 935 \text{ cm}^{-1})/I(\sim 580 \text{ cm}^{-1})$ , where  $I$  indicates the integrated area under the corresponding peak.[71] Theoretically, for  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ ,  $I(\sim 935 \text{ cm}^{-1})/I(\sim 580 \text{ cm}^{-1})$  should be  $\sim 2$ , which reflects the ratio of the terminal octahedra to the inner octahedra [71]. Based on the data shown in Fig.6,  $I(\sim 935 \text{ cm}^{-1})/I(\sim 580 \text{ cm}^{-1}) \sim 1.25$ , which indicates a significant depletion of the terminal short Nb-O bonds. The Raman data is consistent with a sharp decrease in  $D$  for the terminal octahedron near the  $V_{Ca}$ - $V_O$  defect pair, as shown in Figure 5 (b), which is mainly due to the absence of a short Nb-O bond. In addition, the Raman peak at  $\sim 580 \text{ cm}^{-1}$  is asymmetric, which indicates inhomogeneous structural distortions for the middle layer octahedra and is likely a result of higher  $D$  around defect centers for the structure containing divacancy pairs, as depicted in Figure 5(c).



The Nb-O-Nb bond angle ( $\beta$ ) for the different perovskite layers are shown in Figure 5(e-g), using the same notation style as  $D$ . The solid symbols represent  $\beta$  for the supercell with no vacancy, and the open symbols represent  $\beta$  for the supercell with  $V_{Ca1}-V_{O3}$  divacancy. With the introduction of  $V_{Ca1}-V_{O3}$ , the maximum changes in  $\beta$  are observed for the terminal octahedral layer nearest to the  $V_{Ca1}-V_{O3}$  in the A layer, that is,  $\beta_2^A$ . Within the terminal layer of the structure with no vacancy, the tilting angle around the a-axis ( $\beta$ ) for the neighboring octahedra alternates between  $180^\circ$  and  $140^\circ$ . With the introduction of  $V_{Ca1}-V_{O3}$ , the structure relaxes to minimize the difference between  $\beta$  of the neighboring octahedra within the terminal layer. Furthermore, for the inner octahedral layer,  $\beta$  stays close to uniform across the neighboring octahedra, even with the introduction of vacancies. In contrast,  $D_{1-4}^B$  are all similarly affected by the introduction of the  $V_{Ca1}-V_{O3}$ . This indicates that the additional strain introduced by vacancies is relieved within the inner layer through octahedral distortions, rather than by disturbing the octahedral tilting pattern.

Importantly, these results show that introduction of the  $V_{Ca1}-V_{O3}$  divacancy modifies the octahedral distortions and tilting by disturbing the complex interplay between the layer-wise strain energies and atomic bonding energies, the details for which will require further investigation. Consequently, although the maximum changes in the octahedral distortions and Nb-O-Nb bond angles are close to  $V_{O3}$ , that is  $D_3^A$  and  $\beta_2^A$ , the neighboring positions are also significantly affected. In other words, the modulation of the atomic structure due to the additional strain field from the divacancy pair is longer-range (not only limited to nearest neighbors) and therefore not commensurate with the unit cell of the lattice.

The above analysis shows that structural distortions introduced as a result of cation-oxygen divacancies could lead to the formation of local anisotropic electrical dipoles. In other words, while the long-range structure is centrosymmetric, the presence of cooperative point vacancies can cause the structure to deviate locally from bulk symmetry and result in uncompensated electrical dipoles. In this regard, we estimated the strength of local polarization of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  lattice upon inclusion of  $\text{V}_{\text{Ca}}\text{-V}_{\text{O}}$  divacancy pairs from the DFT-relaxed supercell models.

To calculate dipole density, the atomic Born effective charge (BEC)  $Z_i^*$  ( $i$  = atomic index of the supercell models), was computed using the density functional perturbation theory, BEC is a tensorial quantity; however, the orthorhombic symmetry of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  lattice ensures primary contribution from the  $Z_{xx}^*$ ,  $Z_{yy}^*$ , and  $Z_{zz}^*$  components. The Cartesian component of the atomic displacement ( $d_{x/y/z,i}$ ) was computed as the difference between the atomic positions in the relaxed defect supercell model and the non-defect supercell model. The magnitudes of polarization density components ( $P_x$ ,  $P_y$ , and  $P_z$ ) and the effective polarization ( $P$ ) is then obtained via:

$$P_x = \frac{1}{\Omega} \sum_i Z_{xx,i}^* d_{x,i}, P_y = \frac{1}{\Omega} \sum_i Z_{yy,i}^* d_{y,i}, P_z = \frac{1}{\Omega} \sum_i Z_{zz,i}^* d_{z,i}, \quad (4a)$$

$$|P| = \sqrt{P_x^2 + P_y^2 + P_z^2} \quad (4b)$$

Here,  $\Omega$  is the volume of the supercell model. Since the lattice vectors are orthogonal, the Cartesian polarization components  $P_x$ ,  $P_y$ , and  $P_z$  match to  $P_a$ ,  $P_b$ , and  $P_c$ , respectively. The magnitude of the polarization components are in the order of milli- $\text{e}/\text{\AA}$ .

The data for polarization density of  $\text{V}_{\text{Ca}}\text{-V}_{\text{O}}$  divacancy pairs are tabulated in Table 2. Note that the atoms corresponding to the vacancies are not included in the computation of

polarization  $P$  as the BEC of vacancies are essentially zero. Further, the polarization values represent the integrated dipole moments arising from an incommensurate structure due to defect-induced atomic rearrangement. Although we use polarization to describe it, it should not be confused with the conventional polarization definition that is associated with a global structural change or the "ferroelectric phase." Nevertheless, the local polarization plays a vital role in determining the material properties, which is important to characterize. Due to the limited size of our supercell models, the values in Table 2 can be treated as the theoretical upper bound of polarization for  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  that are obtainable with defect dipoles. These values are dependent on the particular defects under consideration, and are significant numerically given that the bulk crystal structure is centrosymmetric. For example, the calculated local polarization of the  $\text{V}_{\text{Ca}2}\text{-V}_{\text{O}3}$  defect dipole, which has the lowest formation energy and hence is the most probable defect type, is  $\sim 14 \mu\text{C}/\text{cm}^2$ . From the set of  $\text{V}_{\text{Ca}2}\text{-V}_{\text{O}}$  pairs, the polarization of  $\text{V}_{\text{Ca}1}\text{-V}_{\text{O}5}$  defect has a still larger polarization value,  $\sim 17 \mu\text{C}/\text{cm}^2$ , although its formation energy is larger than the other types of defect dipole configuration. These values are not unexpected. For example, consider that the dipole moment of the Pb-O divacancy pair in well-known ferroelectric  $\text{PbTiO}_3$  is  $0.1 \text{ e}/\text{\AA}^2$  or  $\sim 160 \mu\text{C}/\text{cm}^2$ . [37]. In comparison, the polarization value of perovskite ferroelectric compounds  $\text{BaTiO}_3$  and  $\text{PbTiO}_3$  are 28.4 and  $66 \mu\text{C}/\text{cm}^2$ , respectively, and that of Aurivillius  $\text{Bi}_4\text{Ti}_3\text{O}_{12}$  is  $50 \mu\text{C}/\text{cm}^2$ . [40,72–74]

The synthesized  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics show large dielectric relaxation at high temperatures, as well as dielectric nonlinearity at high electric fields (see Fig.1), which can be partially attributed to the large local fields from the divacancy pairs. Additional contributions could include space charges at grain boundaries or stacking faults, which are not considered here. The second important observation from the DFT studies is that  $\text{V}_{\text{Ca}}\text{-V}_{\text{O}}$  defect dipoles of more


than one orientations have similarly negative formation energies, which when integrated within the thermodynamics limits may present no definite directionality, but would modulate the magnitude of the macroscopic polarization of bulk  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics. Recently, Osada et al. proposed that deficiency at the A-site in nanosheets derived from D-J phases may lead to ferroelectric instability through octahedral distortion and octahedral tilting.[5,10] Our structural and theoretical analysis provides ample evidence in support of this hypothesis and brings out the role of  $V_{\text{Ca}}\text{-}V_{\text{O}}$  divacancies more distinctly.

## **Conclusions**


In summary, we obtained the structure of cation-oxygen divacancy pairs in D-J phase layered perovskite  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  by combining x-ray pair distribution function and first-principles computation. Our results indicate that calcium-oxygen divacancy pairs are most likely to form in between the octahedral layers, which gives rise to local structural distortions leading to large dipole moment density that are oriented within the 2-dimensional perovskite blocks. Most importantly, the current results demonstrate a strong polar nature of defect-induced local structural distortions in D-J phase compounds, which should motivate a broader investigation of defect dipoles in layered perovskites and their implication on polar interphases or other related macroscopic properties.

## **Acknowledgments**

Funding support from CityU (Projects No. 7005276 and 6000688) are gratefully acknowledged. The work described in this paper was partially supported by a grant from the Research Grants Council of the Hong Kong Special Administrative Region, China (Project No. eg CityU 11306720). This research used resources of the Advanced Photon Source, a US Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under contract no. DE- AC02- 06CH11357. DFT computations were carried out using the resources provided by the High Performance Computing (HPC) facility of CityU Burgundy.

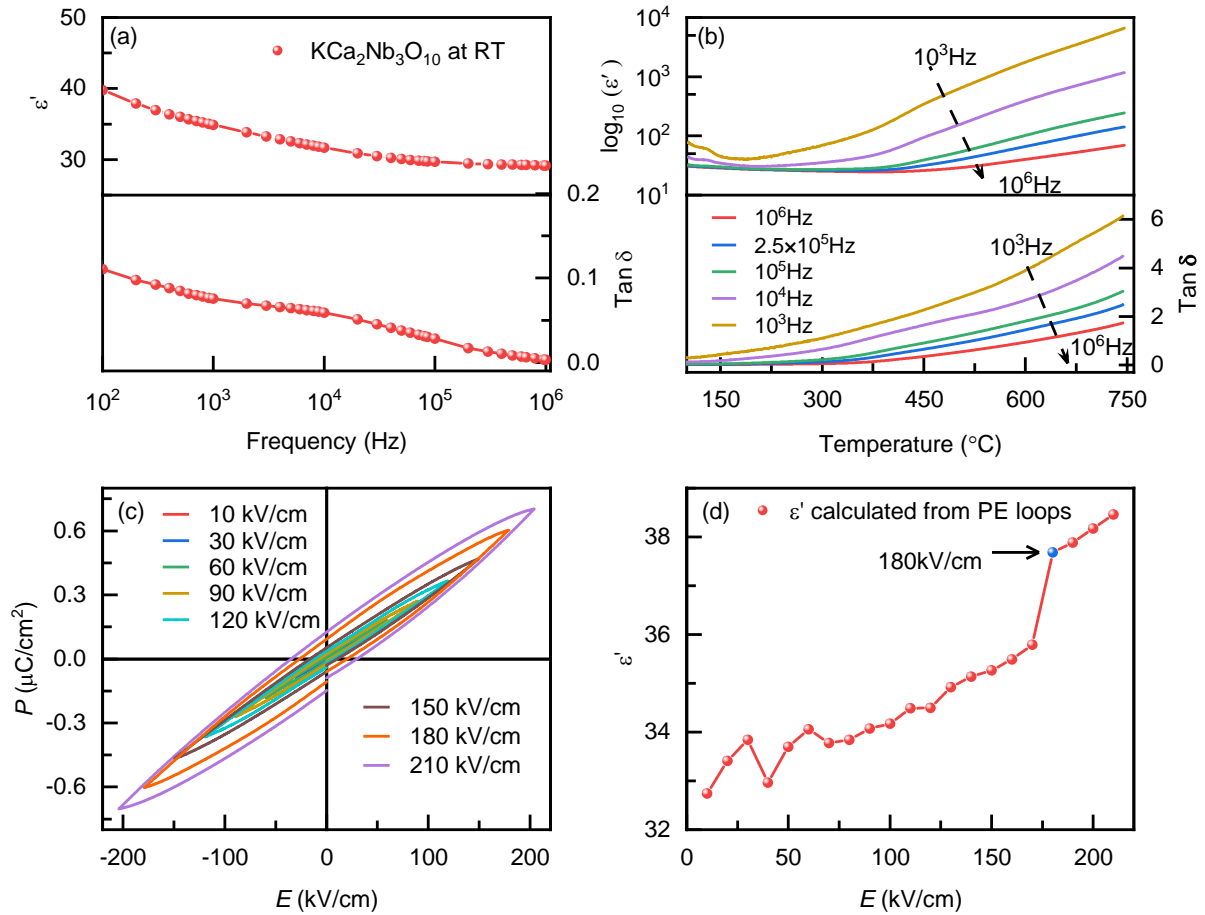

**Figure 1.** (a) Frequency-dependent dielectric constant ( $\epsilon'$ ) and loss-tangent ( $\text{Tan}\delta$ ) of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  ceramics at various frequencies;  $100 \text{ Hz} \leq f \leq 1 \text{ MHz}$  at room temperature. (b) Dielectric constant ( $\epsilon'$ ) and loss-tangent ( $\text{Tan}\delta$ ) of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  at higher temperature (100-750 °C). (c) Hysteresis loops ( $P$  versus  $E$ ) of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  measured at  $E \leq 210$  kV/cm and  $f = 10$  Hz. (d) High electrical field permittivity (calculated from PE loops) as a function of an electrical field.

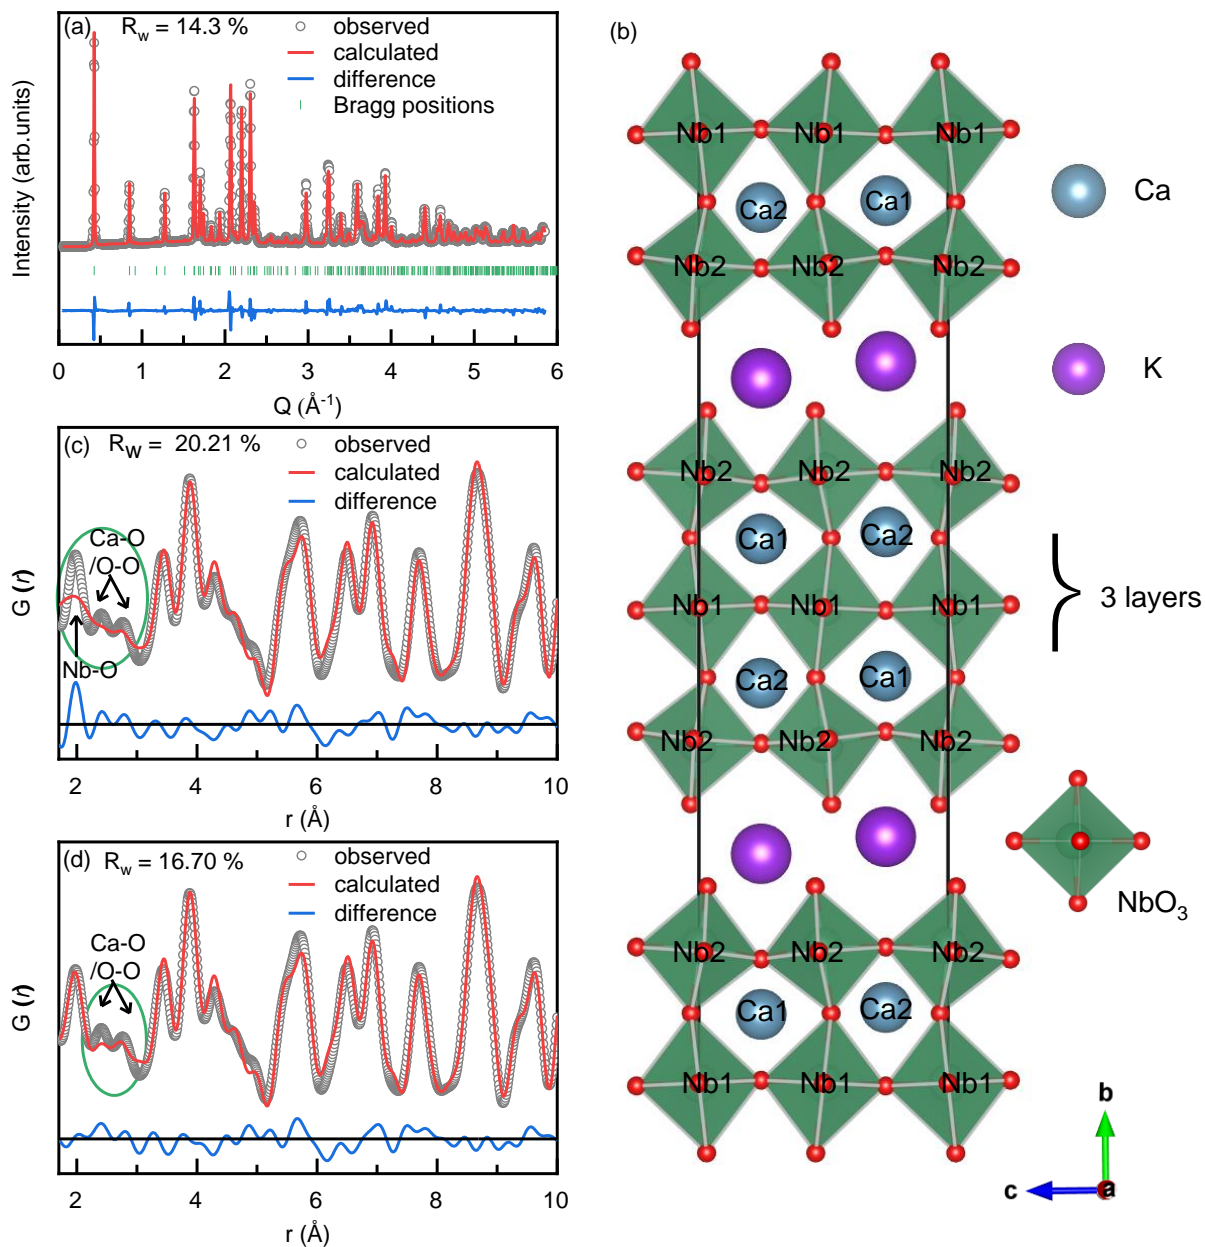


**Figure 2.** (a) Synchrotron X-ray diffraction pattern along with the Rietveld refinement of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ . (b) The crystal structure of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$ . (c) Observed and calculated  $G(r)$  profiles of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  for interatomic distance  $r \leq 10 \text{ \AA}$ , while refining only lattice parameter and ADPs of the average structure. (d) Observed and calculated  $G(r)$  profiles of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  for interatomic distance  $r \leq 10 \text{ \AA}$ , while refining displacement correlation parameter  $\delta_2$ , in addition to lattice parameter and ADPs.

**Table 1.** Structural parameters, fractional atomic coordinates, and atomic displacement parameters ( $U_{\text{iso}}$  in  $\text{\AA}^2$ ) from the Rietveld refinement.


Formular $\text{KC}_2\text{Nb}_3\text{O}_{10}$					
Crystal system: orthorhombic phase					
Space group: $Cmcm$					
Atoms	site	X	Y	Z	$U_{\text{iso}}$
K1	4c	0	0.2589(2)	0.25	0.0056(18)
Ca1	4c	0.5	0.0722(3)	0.75	0.014(2)
Ca2	4c	0.5	0.0795(3)	0.25	0.025(3)
Nb1	4a	0	0	0.5	0.0013(7)
Nb2	8f	0	0.1441(5)	0.5034(3)	0.0012(4)
O1	4c	0	0.003(3)	0.75	0.198(12)
O2	4b	0.5	0	0.5	0.181(10)
O3	8f	0	0.0734(7)	0.469(4)	0.096(5)
O4	8f	0.5	0.1383(6)	0.520(4)	0.022(3)
O5	4c	0	0.1304(12)	0.75	0.004(6)
O6	4c	0	0.1430(12)	0.25	0.006(6)
O7	8f	0	0.2064(5)	0.533(3)	0.000(3)
Lattice parameter ( $\text{\AA}$ )					
a=3.8787(2)		b=29.5385(15)			
c=7.7219(4)		$\alpha=\beta=\gamma=90^\circ$			
$R_w=14.3\%$					

<sup>a</sup> Note that O1 and O2 are disordered atoms [54]




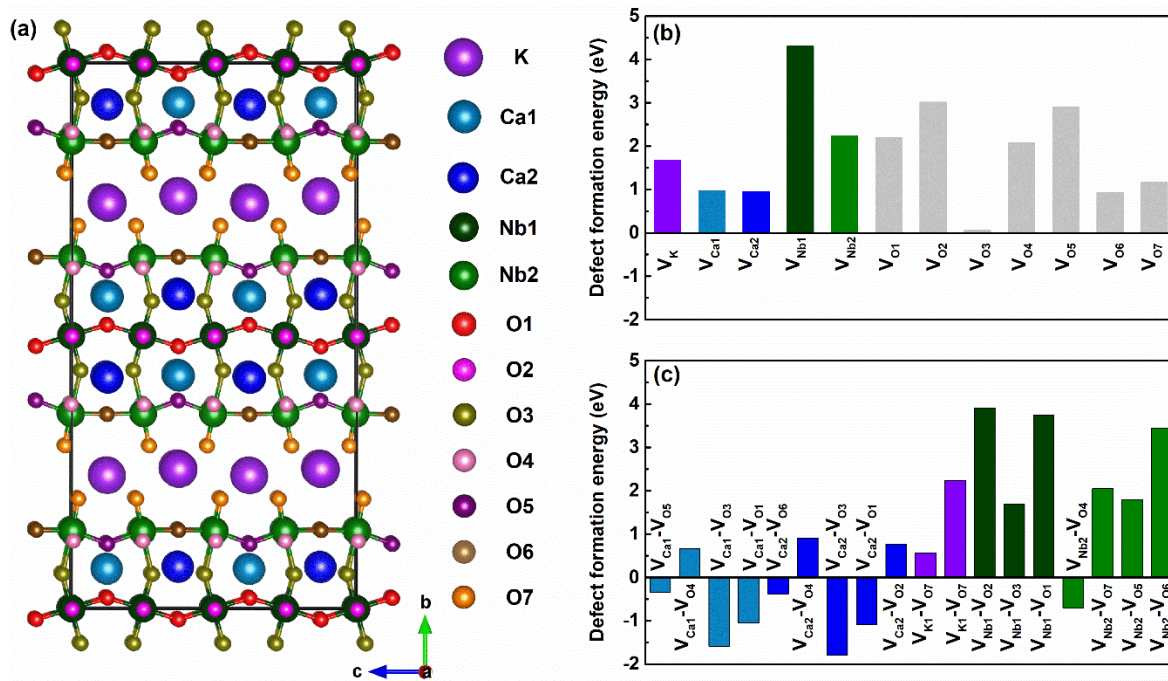


**Figure 3.** (a) Schematic structure of the  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  supercell projected along the  $[1\ 0\ 0]$  direction. The structure is in the orthorhombic  $Cmcm$  space group, and all atoms are colored according to Wyckoff position. (b) Calculated formation energies of isolated vacancies in  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  and (c) nearest-neighbor cation vacancy-oxygen vacancy pairs.

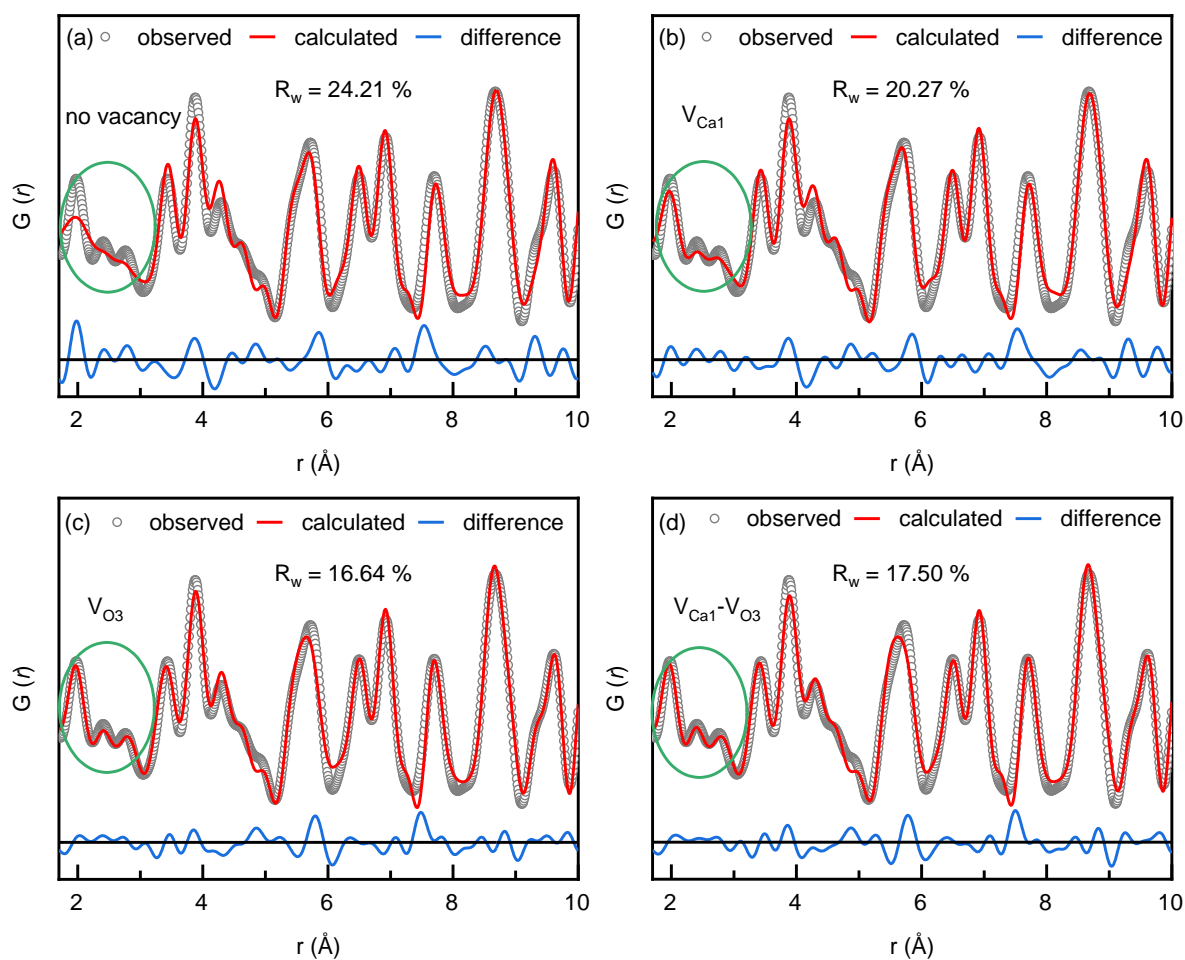

**Figure 4.** Observed and calculated  $G(r)$  profiles of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  for interatomic distance  $r \leq 10 \text{ \AA}$ . Note that the calculated structure model is from the DFT supercell. (a) supercell with no vacancy; (b) supercell with  $V_{\text{Ca}1}$ ; (c) supercell with  $V_{\text{O}3}$ ; (d) supercell with  $V_{\text{Ca}1}\text{-}V_{\text{O}3}$  divacancy pairs.

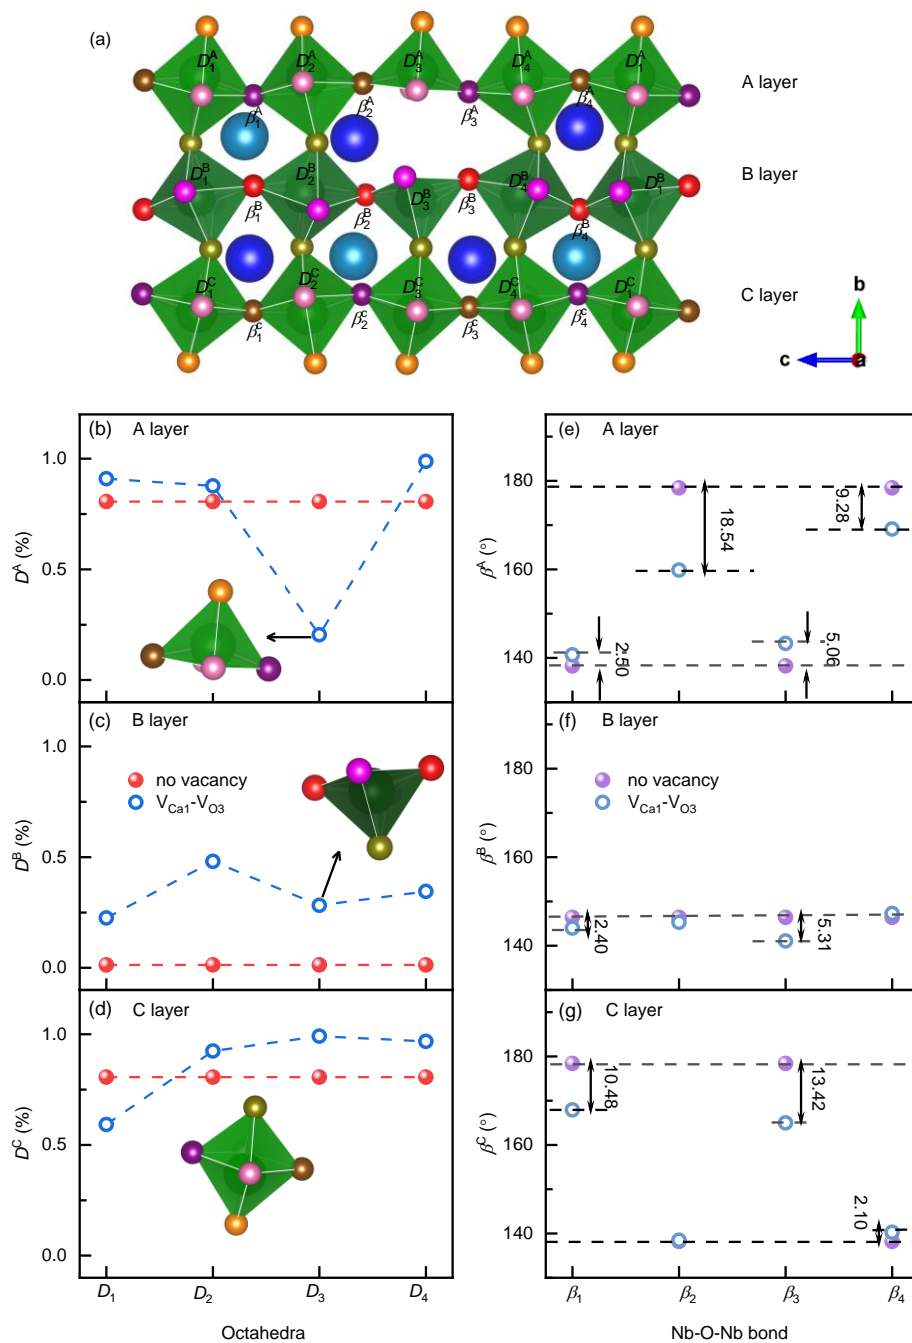

**Figure 5.** (a) The triple perovskite slabs of  $\text{KCa}_2\text{Nb}_3\text{O}_{10}$  supercell with  $V_{\text{Ca1}}-V_{\text{O3}}$  vacancies. (b-d) Distortion parameter evolution in A, B, and C layer, respectively. (e-g) Nb-O-Nb angle in  $a$ - $c$  plane (angle  $\beta$ ) evolution in different perovskite layers A, B, and C, respectively.

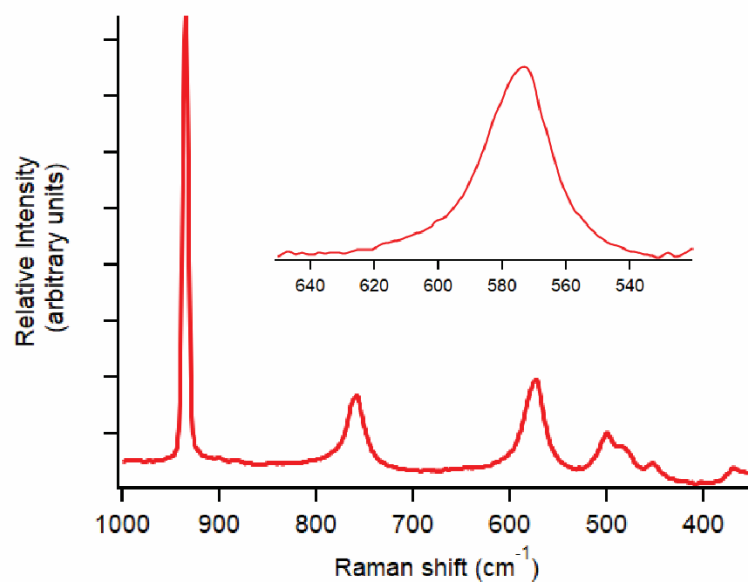

**Figure 6.** Raman spectrum of KCa<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub> showing significant depletion of terminal short Nb-O bonds (refer text).

**Table 2.** Dipole density obtained from DFT computation using Eq. (4) for relaxed defect supercells with  $V_{Ca}$ - $V_O$  nearest neighbor divacancies.

Sl. No.	Vacancy complex	Dipole density				
		$P_a$ ( $me/\text{\AA}^2$ )	$P_b$ ( $me/\text{\AA}^2$ )	$P_c$ ( $me/\text{\AA}^2$ )	$ P $ ( $me/\text{\AA}^2$ )	$P$ ( $\mu\text{C}/\text{cm}^2$ )
1	$V_{Ca1}$ - $V_{O5}$	6.270	6.274	6.305	10.883	17.436
2	$V_{Ca1}$ - $V_{O4}$	0.0	-0.059	-0.033	0.068	0.109
3	$V_{Ca1}$ - $V_{O3}$	1.614	1.594	1.608	2.780	4.454
4	$V_{Ca1}$ - $V_{O1}$	2.636	2.675	2.609	4.573	7.327
5	$V_{Ca2}$ - $V_{O6}$	-0.341	-0.362	-0.314	0.588	0.943
6	$V_{Ca2}$ - $V_{O4}$	0.0	-0.041	-0.014	0.043	0.069
7	$V_{Ca2}$ - $V_{O3}$	-5.169	-5.196	-5.186	8.978	14.385
8	$V_{Ca2}$ - $V_{O1}$	-1.081	-1.107	-1.102	1.899	3.043
9	$V_{Ca2}$ - $V_{O2}$	-0.001	-0.060	-0.012	0.062	0.099

## References:

- [1] C. A.-P. de Araujo, J. D. Cuchiaro, L. D. McMillan, M. C. Scott, and J. F. Scott, *Fatigue-Free Ferroelectric Capacitors with Platinum Electrodes*, *Nature*, **374**, 627-629 (1995).
- [2] D. G. Schlom, L.-Q. Chen, X. Pan, A. Schmehl, and M. A. Zurbuchen, *A Thin Film Approach to Engineering Functionality into Oxides*, *J. Am. Ceram. Soc.* **91**, 2429 (2008).
- [3] C.-H. Lee, N. D. Orloff, T. Birol, Y. Zhu, V. Goian, E. Rocas, R. Haislmaier, E. Vlahos, J. A. Mundy, L. F. Kourkoutis, Y. Nie, M. D. Biegalski, J. Zhang, M. Bernhagen, N. A. Benedek, Y. Kim, J. D. Brock, R. Uecker, X. X. Xi, V. Gopalan, D. Nuzhnyy, S. Kamba, D. A. Muller, I. Takeuchi, J. C. Booth, C. J. Fennie, and D. G. Schlom, *Exploiting Dimensionality and Defect Mitigation to Create Tunable Microwave Dielectrics*, *Nature* **502**, 532 (2013).
- [4] N. A. Benedek, J. M. Rondinelli, H. Djani, P. Ghosez, and P. Lightfoot, *Understanding Ferroelectricity in Layered Perovskites: New Ideas and Insights from Theory and Experiments*, *Dalton Transactions* **44**, 10527-10890 (2015).
- [5] M. Osada and T. Sasaki, *Nanoarchitectonics in Dielectric/Ferroelectric Layered Perovskites: From Bulk 3D Systems to 2D Nanosheets*, *Dalt. Trans.* **47**, 2841 (2018).
- [6] M. Dion, M. Ganne, and M. Tournoux, *Nouvelles Familles de Phases MIMII2Nb<sub>3</sub>O<sub>10</sub> a Feuilletés "Perovskites," Mater. Res. Bull.* **16**, 1429 (1981).
- [7] A. J. Jacobson, J. W. Johnson, and J. T. Lewandowski, *Interlayer Chemistry between Thick Transition-Metal Oxide Layers: Synthesis and Intercalation Reactions of K[Ca<sub>2</sub>Na<sub>n-3</sub>Nb<sub>n</sub>O<sub>3n+1</sub>] (3 ≤ n ≤ 7)*, *Inorg. Chem.* **24**, 3727 (1985).
- [8] A. J. Jacobson, J. T. Lewandowski, and J. W. Johnson, *Ion exchange of the layered perovskite KCa<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub> by protons*, *Journal of the Less Common Metals* **116**, 137-146 (1986).
- [9] B.-W. Li, M. Osada, Y. Ebina, T. C. Ozawa, R. Ma, and T. Sasaki, *Impact of Perovskite Layer Stacking on Dielectric Responses in KCa<sub>2</sub>Na<sub>n-3</sub>Nb<sub>n</sub>O<sub>3n+1</sub> (n=3-6) Dion-Jacobson Homologous Series*, *Appl. Phys. Lett.* **96**, 182903 (2010).
- [10] B.-W. Li, M. Osada, Y.-H. Kim, Y. Ebina, K. Akatsuka, and T. Sasaki, *Atomic Layer Engineering of High-κ Ferroelectricity in 2D Perovskites*, *J. Am. Chem. Soc.* **139**, 10868 (2017).
- [11] K. Maeda and T. E. Mallouk, *Comparison of Two- and Three-Layer Restacked Dion-Jacobson Phase Niobate Nanosheets as Catalysts for Photochemical Hydrogen Evolution*, *J. Mater. Chem.* **19**, 4813 (2009).
- [12] N. Kulischow, C. Ladasiu, and R. Marschall, *Layered Dion-Jacobson Type Niobium Oxides for Photocatalytic Hydrogen Production Prepared via Molten Salt Synthesis*, *Catal. Today* **287**, 65 (2017).
- [13] M. R. Aziza, C.-W. Chang, A. Mohapatra, C.-W. Chu, C.-C. Kaun, and Y.-H. Su, *Dion-Jacobson Phase Perovskite Ca<sub>2</sub>Na<sub>n-3</sub>Nb<sub>n</sub>O<sub>3n+1</sub> (n = 4-6) Nanosheets as High-κ Photovoltaic Electrode Materials in a Solar Water-Splitting Cell*, *ACS Appl. Nano Mater.* **3**, 6367 (2020).
- [14] M. Kato, Y. Imai, T. Kajita, Y. Takarabe, T. Minakawa, K. Nemoto, H. Tezuka, T. Noji, and Y. Koike, *Synthesis of Oxide Superconductors by Soft-Chemical Techniques*, *Mater. Sci. Eng. B* **148**, 53 (2008).

- [15] C. J. Fennie and K. M. Rabe, *Ferroelectricity in the Dion-Jacobson CsBiNb<sub>2</sub>O<sub>7</sub> from First Principles*, Appl. Phys. Lett. **88**, 262902 (2006).
- [16] C. Chen, H. Ning, S. Lepadatu, M. Cain, H. Yan, and M. J. Reece, *Ferroelectricity in Dion–Jacobson A<sub>2</sub>BiNb<sub>2</sub>O<sub>7</sub> (A = Rb, Cs) Compounds*, J. Mater. Chem. C **3**, 19 (2015).
- [17] T. Tokumitsu, K. Toda, T. Aoyagi, D. Sakuraba, K. Uematsu, and M. Sato, *Powder neutron diffraction study of layered perovskite KCa<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub>*, J. Cer. Soc. Jap. **114**, 795-797 (2006)
- [18] N. A. Benedek, *Origin of Ferroelectricity in a Family of Polar Oxides: The Dion-Jacobson Phases*, Inorg. Chem. **53**, 3769 (2014).
- [19] T. Zhu, T. Cohen, A. S. Gibbs, W. Zhang, P. S. Halasyamani, M. A. Hayward, and N. A. Benedek, *Theory and Neutrons Combine To Reveal a Family of Layered Perovskites without Inversion Symmetry*, Chem. Mater. **29**, 9489 (2017).
- [20] E. E. McCabe, E. Bousquet, C. P. J. Stockdale, C. A. Deacon, T. T. Tran, P. S. Halasyamani, M. C. Stennett, and N. C. Hyatt, *Proper Ferroelectricity in the Dion–Jacobson Material CsBi<sub>2</sub>Ti<sub>2</sub>NbO<sub>10</sub>: Experiment and Theory*, Chem. Mater. **27**, 8298 (2015).
- [21] T. Zhu, A. S. Gibbs, N. A. Benedek, and M. A. Hayward, *Complex Structural Phase Transitions of the Hybrid Improper Polar Dion–Jacobson Oxides RbNdM<sub>2</sub>O<sub>7</sub> and CsNdM<sub>2</sub>O<sub>7</sub> (M = Nb, Ta)*, Chem. Mater. **32**, 4340 (2020).
- [22] A. Pramanick, A. D. Prewitt, J. S. Forrester, and J. L. Jones, *Domains, Domain Walls and Defects in Perovskite Ferroelectric Oxides: A Review of Present Understanding and Recent Contributions*. Critical Reviews in Solid State and Materials Sciences **37**(4): p. 243-275 (2012).
- [23] Y. Feng, J. Wu, Q. Chi, W. Li, Y. Yu, and W. Fei, *Defects and Aliovalent Doping Engineering in Electroceramics*. Chem Rev **120**(3): p. 1710-1787 (2020).
- [24] V. Thangadurai and W. Weppner, *Electrical Properties of A'Ca<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub> (A'=K, Rb, Cs) Layered Perovskite Ceramics*, Ionics (Kiel). **7**, 22 (2001).
- [25] R. J. Goff, D. Keeble, P. A. Thomas, C. Ritter, F. D. Morrison, and P. Lightfoot, *Leakage and Proton Conductivity in the Predicted Ferroelectric CsBiNb<sub>2</sub>O<sub>7</sub>*, Chem. Mater. **21**, 1296 (2009).
- [26] T. Wang, C.-L. Chiang, P.-C. Li, Y.-K. Hsieh, and C.-F. Wang, *Effect of B-Site Vacancy on Surface Chemistry and Catalytic Performance of Dion–Jacobson Phase Layered Perovskite KCa<sub>2</sub>Nb<sub>3</sub>O<sub>10</sub>*, Chem. Eng. J. **244**, 243 (2014).
- [27] W. Zhang, K. Fujii, E. Niwa, M. Hagihala, T. Kamiyama, and M. Yashima, *Oxide-Ion Conduction in the Dion–Jacobson Phase CsBi<sub>2</sub>Ti<sub>2</sub>NbO<sub>10-δ</sub>*, Nat. Commun. **11**, 1224 (2020).
- [28] E. Siegel and K. A. Müller, *Structure of Transition-Metal---Oxygen-Vacancy Pair Centers*, Phys. Rev. B **19**, 109 (1979).
- [29] E. Siegel and K. A. Müller, *Local Position of Fe<sup>3+</sup> in ferroelectric BaTiO<sub>3</sub>*, Phys. Rev. B **20**, 3587 (1979).
- [30] W. L. Warren, D. Dimos, G. E. Pike, K. Vanheusden, and R. Ramesh, *Alignment of Defect Dipoles in Polycrystalline Ferroelectrics*, Appl. Phys. Lett. **67**, 1689 (1995).
- [31] W. L. Warren, G. E. Pike, K. Vanheusden, D. Dimos, B. A. Tuttle, and J. Robertson,

- Defect- dipole Alignment and Tetragonal Strain in Ferroelectrics*, J. Appl. Phys. **79**, 9250 (1996).
- [32] D. J. Keeble, B. Nielsen, A. Krishnan, K. G. Lynn, S. Madhukar, R. Ramesh, and C. F. Young, *Vacancy Defects in (Pb, La)(Zr, Ti)O<sub>3</sub> Capacitors Observed by Positron Annihilation*, Appl. Phys. Lett. **73**, 318 (1998).
- [33] S. Gottschalk, H. Hahn, A. G. Balogh, W. Puff, H. Kungl, and M. J. Hoffmann, *A Positron Lifetime Study of Lanthanum and Niobium Doped Pb(Zr<sub>0.6</sub>Ti<sub>0.4</sub>)O<sub>3</sub>*, J. Appl. Phys. **96**, 7464 (2004).
- [34] D. J. Keeble, S. Singh, R. A. Mackie, M. Morozov, S. McGuire, and D. Damjanovic, *Cation Vacancies in Ferroelectric PbTiO<sub>3</sub> and Pb(Zr,Ti)O<sub>3</sub>: A Positron Annihilation Lifetime Spectroscopy Study*, Phys. Rev. B **76**, 144109 (2007).
- [35] Y. Ma, P. Garcia, J. Lechelle, A. Miard, L. Desgranges, G. Baldinozzi, D. Simeone, and H. E. Fischer, *Characterization of Oxygen Defect Clusters in UO<sub>2+x</sub> Using Neutron Scattering and PDF Analysis*, Inorg. Chem. **57**, 7064 (2018).
- [36] A. E. Maughan, A. M. Ganose, A. M. Candia, J. T. Granger, D. O. Scanlon, and J. R. Neilson, *Anharmonicity and Octahedral Tilting in Hybrid Vacancy-Ordered Double Perovskites*, Chem. Mater. **30**, 472 (2018).
- [37] C. H. Park and D. J. Chadi, *Microscopic Study of Oxygen-Vacancy Defects in Ferroelectric Perovskites*, Phys. Rev. B **57**, R13961 (1998).
- [38] S. Pöykkö and D. J. Chadi, *Ab Initio Study of Dipolar Defects and 180° Domain Walls in PbTiO<sub>3</sub>*, J. Phys. Chem. Solids **61**, 291 (2000).
- [39] E. Cockayne and B. P. Burton, *Dipole Moment of a Pb-O Vacancy Pair in PbTiO<sub>3</sub>*, Phys. Rev. B **69**, 144116 (2004).
- [40] K. Co, F.-C. Sun, S. P. Alpay, and S. K. Nayak, *Polarization Rotation in Bi<sub>4</sub>Ti<sub>3</sub>O<sub>12</sub> by Isovalent Doping at the Fluorite Sublattice*, Phys. Rev. B **99**, (2019).
- [41] B. Jiang and S. M. Selbach, *Local and Average Structure of Mn- and La-Substituted BiFeO<sub>3</sub>*, J. Solid State Chem. **250**, 75 (2017).
- [42] N. Kitamura, N. Hamao, S. C. Vogel, and Y. Idemoto, *Oxide-Ion Conduction, Average and Local Structures of LaSrGa<sub>1-x</sub>Mg<sub>x</sub>O<sub>4-δ</sub> with Layered Perovskite Structure*, Electrochemistry **81**, 448-453 (2013).
- [43] S. K. Nayak, H. T. Langhammer, W. A. Adeagbo, W. Hergert, T. Muller, and R. Buttcher, *Chromium Point Defects in Hexagonal BaTiO<sub>3</sub>: A Comparative Study of First-Principles Calculations and Experiments*, Phys. Rev. B - Condens. Matter Mater. Phys. **91**, 155105 (2015).
- [44] W. A. Adeagbo, H. Ben Hamed, S. K. Nayak, R. Böttcher, H. T. Langhammer, and W. Hergert, *Theoretical Investigation of Iron Incorporation in Hexagonal Barium Titanate*, Phys. Rev. B **100**, 184108 (2019).
- [45] see Supplemental Material for additional details on sample preparation, sample composition, measurement and analysis of x-ray scattering data, electrical properties measurements and DFT calculations.
- [46] P. Juhas, T. Davis, C. L. Farrow, and S. J. L. Billinge, *PDFgetX3: a rapid and highly automatable program for processing powder diffraction data into total scattering pair distribution functions*, J. Applied Crystallography. **46**, 560-566 (2013)



- [47] C. L. Farrow, P. Juhas, J. W. Liu, D. Bryndin, E. S. Bozin, J. Bloch, T. Proffen, S. J. L. Billinge, *PDFfit2 and PDFgui: Computer programs for studying nanostructure in crystals*. *J. Phys. Condens. Matter*, **19**, 335219 (2007).
- [48] J. Rodríguez-Carvajal, *Recent advances in magnetic structure determination by neutron powder diffraction*. *Physica B Condens Matter*. **92**, 55–69 (1993)
- [49] S.-H. Kweon, M. Im, G. Han, J.-S. Kim, S. Nahm, J.-W. Choi, and S.-J. Hwang, *Sintering behavior and dielectric properties of  $KCa_2Nb_3O_{10}$  ceramics*, *Journal of the European Ceramic Society* **33**, 907 (2013).
- [50] R. E. Eitel, T. R. Shrout, and C. A. Randall, *Nonlinear contributions to the dielectric permittivity and converse piezoelectric coefficient in piezoelectric ceramics*, *Journal of Applied Physics* **99**, 124110 (2006).
- [51] A. Pramanick, D. Damjanovic, J. C. Nino, and J. L. Jones, *Subcoercive cyclic electrical loading of lead zirconate titanate ceramics I: nonlinearities and losses in the converse piezoelectric effect*, *Journal of the American Ceramic Society* **92**, 2291-2299 (2009).
- [52] A. A. Bokov and Z.-G. Ye, *Recent Progress in Relaxor Ferroelectrics with Perovskite Structure*, *J. Mater. Sci.* **41**, 31 (2006).
- [53] J. E. García, R. Pérez, D. A. Ochoa, A. Albareda, M. H. Lente, and J. A. Eiras, *Evaluation of Domain Wall Motion in Lead Zirconate Titanate Ceramics by Nonlinear Response Measurements*, *J. Appl. Phys.* **103**, 54108 (2008).
- [54] H. Fukuoka, T. Isami, and S. Yamanaka, *Crystal Structure of a Layered Perovskite Niobate  $KCa_2Nb_3O_{10}$* , *J. Solid State Chem.* **151**, 40 (2000)
- [55] M. S. Seen, D. A. Keen, T. C. A. Lucas, J. A. Hriljac, A. L. Goodwin, *Emergence of long-range order in  $BaTiO_3$  from local symmetry-breaking distortion*, *Phys. Rev. Lett.* **116**, 207602 (2016)
- [56] I.-K. Jeong, T. Proffen, F. Mohiuddin-Jacobs, and S. J. L. Billinge, *Measuring correlated atomic motion using X-ray diffraction*, *J. Phys. Chem. A*, **103**, 921-924 (1999).
- [57] I.-K. Jeong, R. H. Heffner, M. J. Graf, S. J. L. Billinge, *Lattice dynamics and correlated atomic motion from the atomic pair distribution function*, *Phys. Rev. B*, **67**, 104301 (2003).
- [58] C. L. Farrow, P. Juhas, J. W. Liu, D. Bryndin, E. S. Bozin, J. Bloch, Th. Proffen, and S. J. L. Billinge, *PDFgui user guide. Diffpy*, 2016
- [59] R. O. Jones and O. Gunnarsson, *The Density Functional Formalism, Its Applications and Prospects*, *Rev. Mod. Phys.* **61**, 689 (1989).
- [60] M. C. Payne, M. P. Teter, D. C. Allan, T. A. Arias, and J. D. Joannopoulos, *Iterative Minimization Techniques for Ab Initio Total-Energy Calculations: Molecular Dynamics and Conjugate Gradients*, *Rev. Mod. Phys.* **64**, 1045 (1992).
- [61] J. P. Perdew, K. Burke, and M. Ernzerhof, *Generalized Gradient Approximation Made Simple*, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [62] P. E. Blöchl, *Projector Augmented-Wave Method*, *Phys. Rev. B* **50**, 17953 (1994).
- [63] H. J. Monkhorst and J. D. Pack, *Special Points for Brillouin-Zon Integrations*, *Phys. Rev. B* **13**, 5188 (1976).
- [64] G. Kresse and J. Furthmüller, *Efficiency of Ab-Initio Total Energy Calculations for Metals*

- and Semiconductors Using a Plane-Wave Basis Set*, Comput. Mater. Sci. **6**, 15 (1996).
- [65] G. Kresse and J. Furthmüller, *Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set*, Phys. Rev. B **54**, 11169 (1996).
- [66] S. K. Nayak, H. T. Langhammer, W. A. Adeagbo, W. Hergert, T. Müller, and R. Böttcher, *Chromium Point Defects in Hexagonal BaTiO<sub>3</sub>: A Comparative Study of First-Principles Calculations and Experiments*, Phys. Rev. B - Condens. Matter Mater. Phys. **91**, (2015).
- [67] S. K. Nayak, C. J. Hung, V. Sharma, S. P. Alpay, A. M. Dongare, W. J. Brindley, and R. J. Hebert, *Insight into Point Defects and Impurities in Titanium from First Principles*, Npj Comput. Mater. **4**, 11 (2018).
- [68] M. E. Lines and A. M. Glass, *Principles and Applications of Ferroelectrics and Related Materials* ( Oxford University Press, 1977)
- [69] H. Mestric, R.-A. Eichel, T. Kloss, K.-P. Dinse, S. Laubach, S. Laubach, P. C. Schmidt, K. A. Schönau, M. Knapp, and H. Ehrenberg, *Iron-Oxygen Vacancy Defect Centers in PbTiO<sub>3</sub>: Newman Superposition Model Analysis and Density Functional Calculations*, Phys. Rev. B **71**, 134109 (2005).
- [70] L. Veselinović, M. Mitrić, M. Avdeev, S. Marković, D. Uskoković, *New insights into BaTi<sub>1-x</sub>Sn<sub>x</sub>O<sub>3</sub> (0 ≤ x ≤ 0.20) phase diagram from neutron diffraction data*. J. Appl. Cryst. **49**, 1726 (2016).
- [71] J. M. Jehng and I. E. Wachs, *Structural Chemistry and Raman Spectra of Niobium Oxides*, Chem. Mater. **3**, 100 (1991).
- [72] H. H. Wieder, *Electrical Behavior of Barium Titanate Single Crystals at Low Temperatures*, Phys. Rev. **99**, 1161 (1955).
- [73] V. G. Bhide, M. S. Hegde, and K. G. Deshmukh, *Ferroelectric Properties of Lead Titanate*, J. Am. Ceram. Soc. **51**, 565-568 (1968).
- [74] D. Maurya, A. Charkhesht, S. K. Nayak, F.-C. Sun, D. George, A. Pramanick, M.-G. Kang, H.-C. Song, M. M. Alexander, D. Lou, G. A. Khodaparast, S. P. Alpay, N. Q. Vinh, and S. Priya, *Soft Phonon Mode Dynamics in Aurivillius-Type Structures*, Phys. Rev. B **96**, 134114 (2017).