

6-1-2010

# On the Bandstructure Velocity and Ballistic Current of Ultra-Narrow Silicon Nanowire Transistors as a Function of Cross Section Size, Orientation, and Bias

Neophytos Neophytou  
*Technical University of Vienna, Austria*

Sung-Geun Kim  
*Network for Computational Nanotechnology, Purdue University*

Gerhard Klimeck  
*Network for Computational Nanotechnology, Purdue University, gekco@purdue.edu*

Hans Kosina  
*Vienna Univ Technol*

Follow this and additional works at: <http://docs.lib.purdue.edu/nanopub>

 Part of the [Nanoscience and Nanotechnology Commons](#)

Neophytou, Neophytos; Kim, Sung-Geun; Klimeck, Gerhard; and Kosina, Hans, "On the Bandstructure Velocity and Ballistic Current of Ultra-Narrow Silicon Nanowire Transistors as a Function of Cross Section Size, Orientation, and Bias" (2010). *Birck and NCN Publications*. Paper 513.  
<http://docs.lib.purdue.edu/nanopub/513>

This document has been made available through Purdue e-Pubs, a service of the Purdue University Libraries. Please contact [epubs@purdue.edu](mailto:epubs@purdue.edu) for additional information.

# On the bandstructure velocity and ballistic current of ultra-narrow silicon nanowire transistors as a function of cross section size, orientation, and bias

Neophytos Neophytou,<sup>1,a)</sup> Sung Geun Kim,<sup>2</sup> Gerhard Klimeck,<sup>2</sup> and Hans Kosina<sup>1</sup>

<sup>1</sup>Technical University of Vienna, TU Wien, Vienna 1040, Austria

<sup>2</sup>Network for Computational Nanotechnology, Birk Nanotechnology Center, Purdue University, West Lafayette, Indiana 47907-1285, USA

(Received 27 December 2009; accepted 26 February 2010; published online 1 June 2010)

A 20 band  $sp^3d^5s^*$  spin-orbit-coupled, semiempirical, atomistic tight-binding model is used with a semiclassical, ballistic field-effect-transistor model, to theoretically examine the bandstructure carrier velocity and ballistic current in silicon nanowire (NW) transistors. Infinitely long, uniform, cylindrical, and rectangular NWs, of cross sectional diameters/sides ranging from 3–12 nm are considered. For a comprehensive analysis, n-type and p-type metal-oxide semiconductor (NMOS and PMOS) NWs in [100], [110], and [111] transport orientations are examined. In general, physical cross section reduction increases velocities, either by lifting the heavy mass valleys or significantly changing the curvature of the bands. The carrier velocities of PMOS [110] and [111] NWs are a strong function of diameter, with the narrower  $D=3$  nm wires having twice the velocities of the  $D=12$  nm NWs. The velocity in the rest of the NW categories shows only minor diameter dependence. This behavior is explained through features in the electronic structure of the silicon host material. The ballistic current, on the other hand, shows the least sensitivity with cross section in the cases where the velocity has large variations. Since the carrier velocity is a measure of the effective mass and reflects on the channel mobility, these results can provide insight into the design of NW devices with enhanced performance and performance tolerant to structure geometry variations. In the case of ballistic transport in high performance devices, the [110] NWs are the ones with both high NMOS and PMOS performance as well as low on-current variations with cross section geometry variations. © 2010 American Institute of Physics. [doi:10.1063/1.3372764]

## I. INTRODUCTION

*Motivation:* The recent advancements in process and manufacturing of nanoelectronic devices have allowed the manufacturability of nanowire (NW) devices, which are considered as possible candidates for a variety of applications. For field-effect-transistor applications, NWs have recently attracted large attention because of the possibility of enhanced electrostatic control and the possibility of close to ballistic transport.<sup>1</sup> Ultrascaled NW transistors of diameters down to  $D=3$  nm and gate lengths down to  $L_G=15$  nm, have already been demonstrated by various experimental groups.<sup>2–7</sup> Beyond the use in ultrascaled high performance logic and memory transistors, NWs have also attracted large attention as biological sensors,<sup>8</sup> optoelectronic,<sup>9,10</sup> and thermoelectric devices.<sup>11,12</sup> NW properties can be engineered and optimized through size, crystal orientation, and strain.<sup>13,14</sup> The carrier mobility and electrical conductivity that determine to a large degree the on-current and performance of devices, are quantities closely related to the bandstructure velocity of the channel. A thorough understanding of the bandstructure velocity and the parameters that control it, will aid the optimization and design of devices for a variety of electronic transport applications ranging from the diffusive to the ballistic limits. The bandstructure velocity and ballistic

on-current in NWs as a function of the cross sectional size, transport orientation, carrier type, and gate bias is the focus of this work.

The properties of one-dimensional silicon NWs<sup>13–18</sup> and two-dimensional (2D) thin-body devices<sup>19–21</sup> in the high symmetry orientations [100], [110], and [111], have been addressed in a variety of theoretical studies. The challenges in simulating ultra-thin-body (UTB) and NW devices in which the atoms are countable in their cross section, call for sophisticated models beyond the effective mass approximation, especially in describing the valence band. The tight-binding<sup>13,14,16,17</sup> and the  $k \cdot p$ <sup>20,22</sup> methods were used to calculate the electronic properties of these nanostructures, both with unstrained and strained lattice and scattering considerations.<sup>23–26</sup> The performance in terms of on-current is associated with the carrier velocities, which are linked to the effective mass and the carrier mobility. Strain engineering, in that respect, is introduced in devices as a way to increase the carrier velocities and improve performance.<sup>27,28</sup>

These theoretical studies, however, have been performed for specific NW cross sections or thin-body widths. A comprehensive study that addresses the carrier velocities and ballistic on-current in NWs as a function of, (i) channel cross sectional size, (ii) carrier type [n-type or p-type metal-oxide semiconductor (NMOS or PMOS)], (iii) transport orientation ([100], [110], and [111]), (iv) gate bias, and (v) cross sectional shape (cylindrical/rectangular), has not yet been re-

<sup>a)</sup>Author to whom correspondence should be addressed. Electronic mail: neophytou@iue.tuwien.ac.at.

ported. Such a comprehensive device exploration will provide useful insight into optimization strategies of NW device performance for a variety of applications. The analysis presented in this paper addresses all these design factors. The nearest-neighbor atomistic tight binding (TB) model ( $sp^3d^5s^*$ -SO) (Refs. 29–32) is used for the NWs' electronic structure calculation, coupled to a 2D Poisson solver for the electrostatic potential. To evaluate transport characteristics, a simple semiclassical ballistic model<sup>13,14,33,34</sup> is used. Cylindrical NWs of diameters from  $D=3$  nm to  $D=12$  nm and rectangular NWs from 3 nm to 12 nm wide/tall (all combinations of aspect ratios) in three different transport orientations are considered. The design space could be further expanded by the use of strain as partly shown in Ref. 15, but this is beyond the scope of this paper.

We find that cross section reduction introduces changes in the bandstructure features that in general increase the carrier velocities. The increase can vary from  $\sim 0$  to  $\sim 100\%$  depending on the NW category. High inversion conditions (large gate biases) also increase the carrier velocities by  $\sim 50\%$  as higher energy states are occupied. Device designs are identified for optimized performance as well as performance variation tolerance to cross section variations. We note here that the ballistic model used in this study provides the upper limit for the performance of the devices. In reality, even devices with ultrashort channel lengths are not 100% ballistic. The carrier velocity trends, however, reflect on the effective mass and carrier mobility and point to the direction of enhanced performance. In addition, imperfections and nonidealities will also affect the performance. In the Sec. VI of the paper, therefore, the results for one particular geometry are quantified in the presence of surface roughness scattering (SRS) using a quantum ballistic, full band, atomistic tight-binding simulator,<sup>17,35,36</sup> and the magnitude of this additional variation is estimated.

This paper is organized as follows: In part II, we describe the approach followed. In part III, we present the results for the velocity and on-current as function of diameter in cylindrical NWs. In part IV, we discuss and provide explanations for the results. In part V, we extend our analysis to rectangular NW devices. In part VI, we provide design considerations for optimized performance. Finally, part VII summarizes and concludes the work.

## II. APPROACH

*Atomistic modeling:* To obtain the bandstructure of the NWs both for electrons and holes for which spin-orbit coupling is important, a well calibrated atomistic model is used. The nearest neighbor TB  $sp^3d^5s^*$ -SO model captures all the necessary band features, and in addition, is robust enough to computationally handle larger NW cross sections as compared to *ab initio* methods. As an indication, the unit cells of the NWs considered in this study contain from  $\sim 150$  to  $\sim 6500$  atoms and the computation time needed varies from a few hours to few days for each bias point on a single CPU. The model itself and the parameterization used,<sup>29</sup> have been extensively calibrated to various experimental data of various natures with excellent agreement.<sup>37–40</sup> In particular, we

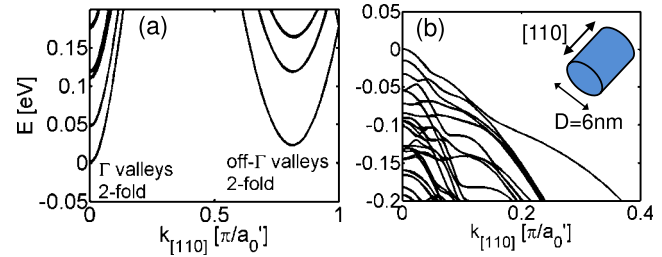


FIG. 1. (Color online) Equilibrium dispersion relations for the  $D=6$  nm  $[110]$  NW (positive  $k$ -states). (a) Electrons. (b) Holes. The edges of the first band are shifted to  $E=0$  eV.  $a_0'$  is the unit cell length.

highlight the match to experimental data considering the valley splitting in slanted strained Si UTB devices on disordered SiGe,<sup>39</sup> and single impurities in Si<sup>40</sup> without any material parameter adjustments. The model provides a simple but effective way for treatment of the surface truncation by hydrogen passivation of the dangling bonds on the surface of the NW.<sup>41</sup> What is important for this work, the Hamiltonian is built on the diamond lattice of silicon and the effect of different orientations and cross sectional shapes is automatically included, all of which impact the interaction and mixing of various bulk bands.

*The simulation approach:* The devices simulated are cylindrical and rectangular NWs in the  $[100]$ ,  $[110]$ , and  $[111]$  transport orientations, surrounded by  $\text{SiO}_2$ . In the case of the cylindrical devices, the oxide thickness is set to 8 nm. These are typical NW device sizes that have been reported in experimental studies.<sup>3,4</sup> In the rectangular cases, the oxide used is 1.1 nm, which is a more realistic thickness for ultimately desired high performance devices. The simulation procedure consists of three steps as described in detail in Ref. 13 and is summarized here.

- (1) The bandstructure of the wire is calculated using the  $sp^3d^5s^*$ -SO model. As an example, Figs. 1(a) and 1(b) show the conduction and valence bands of the  $D=6$  nm cylindrical NW in the  $[110]$  direction (positive  $k$ -parts of the dispersions). The different valleys, with different effective masses as well as band interactions, nonparabolicities and anisotropies of the Si bulk bandstructure, especially for the valence band, are all captured by the model and appear in the NW dispersions.
- (2) A semiclassical top-of-the-barrier ballistic model is used to fill the electronic states and compute the transport characteristics.<sup>13,14,33,34</sup> The range of validity of this model is explored in detail in Ref. 42 with a much more computationally demanding three-dimensional (3D) full non-equilibrium Green's function (NEGF) model. There it was shown that the approach is valid when the wire's length/width ratio exceeds  $L/W > 5$  in which case source-drain tunneling is suppressed.
- (3) The 2D Poisson equation is solved in the cross section of the wire to obtain the electrostatic potential. It is added to the diagonal on-site elements of the atomistic Hamiltonian as an effective potential for recalculating the bandstructure until self consistency is achieved.

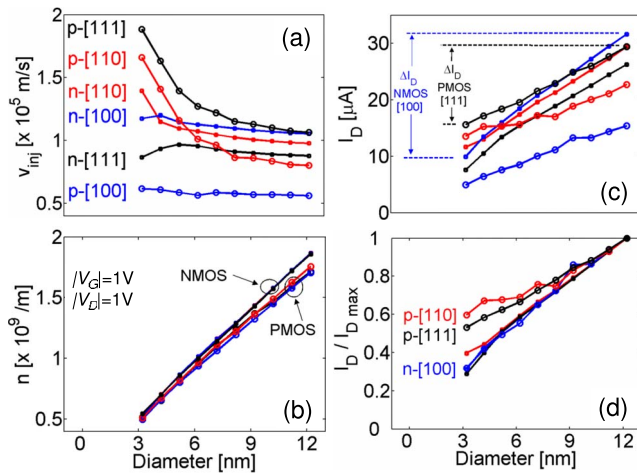


FIG. 2. (Color online) Results for cylindrical NMOS and PMOS NWs at  $|V_G|=1$  V and  $|V_D|=1$  V vs diameter. (a) Carrier injection velocity. (b) Charge density. (c) On-current. (d) On-current normalized to its maximum value (the  $D=12$  nm value).

Although the transport model used is a simple ballistic model, it allows for examining how the bandstructure alone will affect the channel properties and transport characteristics and thus, it provides essential physical insight. It is the simplicity of the transport model, which allows to shed light on the importance of the dispersion details and their effect on transport.

### III. RESULTS

The average carrier velocity (or injection velocity  $v_{inj}$ ) of the wires, defined as  $I_D/qn$ , where  $I_D$  is the ballistic drain on-current and  $n$  is the carrier density in the NW cross section, depends strongly on carrier type, cross section diameter, and orientation. Figure 2 presents these results, while Fig. 3 extends the analysis by including the dependence on gate bias as well. Figure 2(a) shows the carrier velocity for the cylindrical NMOS (dotted lines) and PMOS (circled lines) NWs in the [100] (blue), [110] (red), and [111] (black) transport orientations at on-state ( $|V_G|=|V_D|=1$  V) as a function of the wire's diameter. Large differences in the carrier velocities of the different NW orientation and carrier type are observed. Within the same NW category, large variations are also observed as the diameter reduces. The changes are more prominent in the PMOS [111], PMOS [110], and NMOS [110] cases. There, the velocity increases by up to a factor of  $2\times$  as the diameter reduces. The other three cases show minor velocity variations. As it will be explained in the Sec. IV, this behavior originates purely from bandstructure changes.

Figure 2(b) shows the charge density as a function of the diameter. The charge increases almost linearly with cross section for devices at these diameter scales, following the increase in the cylindrical oxide capacitance  $C_{OX} = 2\pi\kappa\epsilon_0/\ln(1+(t_{OX}/a))$  with the radius  $a$ . The charge, however, is of similar magnitude in all cases, irrespective of orientation, NMOS, or PMOS because the gate oxide dominates the overall capacitance in Si NWs. (The NMOS NWs have only slightly higher charge than the PMOS ones). The total gate capacitance  $C_G$  in our simulations is degraded from  $C_{OX}$

by  $\sim 20\%$ – $30\%$  as also shown in Ref. 13. This degradation is the same irrespective of NW type. NWs of different orientations or carrier type, have small differences in their quantum capacitance  $C_Q$  of the order of  $<10\%$  in most cases, but these cause only small differences in the total gate capacitance  $C_G$ .<sup>13–15</sup> At  $V_G=V_D=1$  V,  $C_Q$  varies from  $C_Q \sim 1.5$  to  $C_Q \sim 9$  nF/m as the diameter increases from  $D=3$  to  $D=12$  nm. (It increases with gate bias because  $C_Q$  a measure of the density of states at the Fermi level, and more and more subbands are occupied as the bias increases). The values are very similar in magnitude for all NW types. The oxide capacitance, on the other hand, increases from  $C_{OX}=0.124$  to  $C_{OX}=0.26$  nF/m in the same diameter range, values  $12\times$  and  $34\times$  smaller than  $C_Q$ , respectively. This indicates that  $C_{OX}$  still dominates the electrostatics (more for the larger diameters than the smaller ones). Of course the effect of  $C_Q$  is more prominent for smaller oxide thicknesses. Still, its importance is reduced, and at a specific diameter, the already small variations between the different NW types do not cause any variations in the charge density.

When considering ultrascaled transistors, transport can be close to the ballistic limit.<sup>4</sup> In this case the current through a device is simply given by the product of charge times velocity,  $I_D=qn \times v_{inj}$ . The on-current versus diameter is shown in Fig. 2(c). It increases with diameter but its magnitude, as well as its rate of increase, is different for each NW case. The NWs with the larger velocity variations have the smaller variations in  $I_{ON}$  as the diameter changes, as indicated by the PMOS [111]  $\Delta I_D$  range versus the NMOS [100]  $\Delta I_D$  range in Fig. 2(c). When the carrier velocity does not vary significantly with diameter, the change in  $I_D$  follows the change in the charge density with diameter. This is the case for all NMOS NWs and the PMOS [100] NWs. In the PMOS [110] and [111] cases where the carrier velocity increases as the diameter decreases, the counter-acting effect of velocity increase and capacitance decrease makes the ballistic current more tolerant to diameter variations. This behavior is better illustrated in Fig. 2(d), which shows the on-current of each NW category normalized to its higher value (the value of the  $D=12$  nm NW). The PMOS [110] and PMOS [111] NWs have the least on-current reduction as the diameter decreases. As the diameter is scaled by four times (from  $D=12$  to  $D=3$  nm),  $I_D$  reduces by  $\sim 2$  in the PMOS [110] and PMOS [111] cases, whereas it reduces by  $\sim 3$  times in the rest of the NW categories. This behavior can potentially provide a mechanism for device designs with ballistic performance more tolerant to structural variations, especially considering the difficulties in controlling the line etch roughness in nanofabrication processes.

From Figs. 2(a) and 2(c), it is evident that the designs are diameter dependent since at a certain NW diameter different NWs perform differently. For the NMOS cases, at larger diameters, the [100] NWs (dotted-blue) perform better, closely followed by the [110] NWs (dotted-red). At smaller diameters this order is reversed. For the PMOS cases, at larger diameters the performance of the [110] NW (circled-red) suffers compared to the [111] NWs (circled-black). At smaller diameters, however, the [110] NWs suffer a smaller performance reduction, and their performance becomes simi-



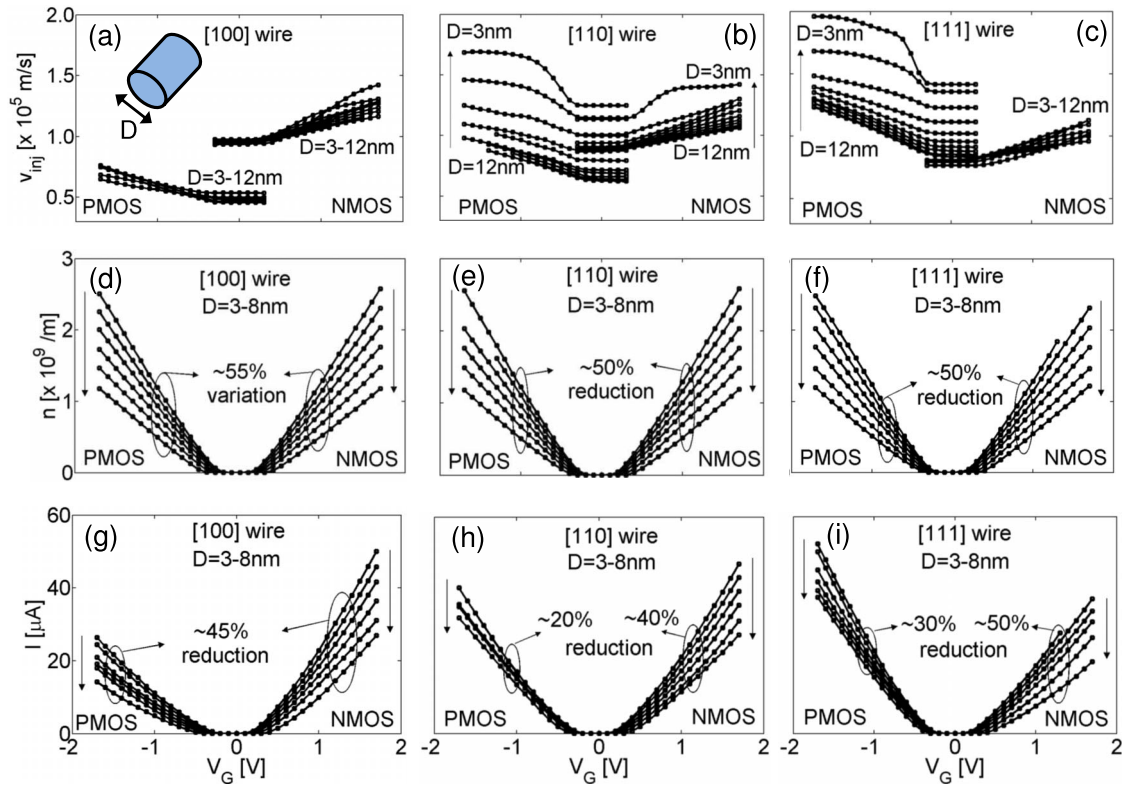


FIG. 3. (Color online) Results for cylindrical NWs of diameters varying from  $D=12$  nm down to 3 nm, PMOS and NMOS vs  $V_G$  for  $|V_D|=1$  V. PMOS NW results are shown for negative  $V_G$ , NMOS results for positive  $V_G$ . The arrows indicate the direction of diameter decrease in the cases for which a unidirectional trend is observed. [(a)–(c)] Carrier velocities. [(d)–(f)] Charge density (for  $D=8$  nm down to  $D=3$  nm). [(g)–(i)] Ballistic current (for  $D=8$  nm down to  $D=3$  nm). Left column—[100] oriented wires. Middle column—[110] oriented wires. Right column—[111] oriented wires. Inset of (a): the cylindrical NW cross section.

lar to the [111] NWs' performance. The fact that the NMOS [111], and especially the PMOS [100] NWs always lack on performance, leaves the [110] direction the one with high performance for both carrier types in the entire diameter range. This is enhanced by the fact that [110] NWs suffer less performance loss as the diameter reduces, for both carrier types. In complementary metal-oxide semiconductor (CMOS) applications, for which both NMOS and PMOS need to be utilized, [110] seems to be the optimal case.

The results of Fig. 2 are drawn at on-state at a fixed  $|V_G|=|V_D|=1$  V. Figure 3 generalizes these results by showing the variation in the velocity, charge, and current as a function of diameter, orientation, and additionally gate bias. Row-wise, results for *carrier velocity* (first row), *charge* (second row), and *current* (third row) versus  $V_G$  are shown. Columnwise, results for the different transport orientations are shown, [100]—first column, [110]—second column, and [111]—third column. The left/right panels of each figure (negative/positive  $V_G$ ), show results for PMOS/NMOS NWs, respectively. The NWs considered are cylindrical in cross section [as shown in the inset of Fig. 3(a)] with diameters varying from  $D=12$  nm down to  $D=3$  nm in decrements of 1 nm. The arrows in each subfigure indicate the direction of diameter reduction.

The carrier velocities of the NWs versus  $V_G$  are shown in Figs. 3(a)–3(c). In all cases, the carrier velocities increase with increasing  $V_G$  (positive for the NMOS and negative for the PMOS cases). At higher inversion conditions, higher en-

ergy states are occupied with higher carrier velocity ( $v_{inj} \sim dE/dk$ ). The increase in the carrier velocity with gate bias increase is as high as  $\sim 50\%$  and appears in all NW cases.

The strong diameter dependence in the cases of PMOS [110] and [111] NWs [Figs. 3(b) and 3(c), left panels] is also observed through all biases. As the diameter scales from  $D=12$  to  $D=3$  nm, the velocity doubles from  $v_{inj} \sim 0.7 \times 10^5$  to  $v_{inj} \sim 1.4 \times 10^5$  m/s (values around  $V_G=0$  V), independent of gate bias. A similar variation trend, but at a smaller scale is observed for the NMOS [110] NWs [Fig. 3(b), right panel], for which the velocity increases from  $v_{inj} \sim 0.9 \times 10^5$  to  $v_{inj} \sim 1.2 \times 10^5$  m/s as the diameter is reduced (values around  $V_G=0$  V). On the other hand, in the cases of PMOS [100] [Fig. 3(a), left panel], NMOS [100] [Fig. 3(a), right panel], and NMOS [111] [Fig. 3(c), right panel], the carrier velocity has only a small diameter dependence. In these cases, the variation trends intermix at different gate biases and cannot be identified as monotonically increasing or decreasing with diameter. Explanations for all these trends are provided below in the Sec. IV.

Comparing the magnitude of the velocities in each NW category, NMOS NWs in the [100] and [110] directions have similar performance, with their velocities at low gate bias being about  $v_{inj} \sim 1 \times 10^5$  m/s. In the NMOS [110] case, the  $D=3$  nm NW has a slight advantage with the velocity raising to  $v_{inj} \sim 1.15 \times 10^5$  m/s. The NMOS [111] NW velocities are  $\sim 20\%$  lower at  $v_{inj} \sim 0.8 \times 10^5$  m/s. In the PMOS

NW cases, at a specific diameter size, the [111] NWs perform better, followed by the [110] NW and finally by the [100] oriented NWs. The PMOS [100] NWs can only deliver  $v_{inj} \sim 0.5 \times 10^5$  m/s (low gate bias value), which makes them the NWs with the lowest carrier velocities of all categories examined for all diameter sizes. This behavior holds for all gate bias conditions.

In Figs. 3(d)–3(f) (second row) and Figs. 3(g)–3(i) (third row), we show the charge and ballistic current, respectively, of the NWs with diameters from  $D=8$  nm down to  $D=3$  nm for which a large velocity variation is observed. As also shown in Fig. 2(b), at the same gate overdrive the charge in the NWs of the same diameter is of similar magnitude, changing linearly with the oxide capacitance, irrespective of orientation, NMOS or PMOS.

The ballistic  $I_D$  versus  $V_G$  characteristics in Figs. 3(g)–3(i) are given by the product of the charge times velocity  $I_D = qn \times v_{inj}$ . In the NMOS NW cases (all right panels), where the carrier velocity does not vary significantly with diameter, the change in  $I_D$  follows the change in the charge density with diameter. Same happens to the PMOS [100] NWs [Fig. 3(g), left panel]. At a given  $V_G$  value, as the diameter decreases from  $D=8$  to  $D=3$  nm, the  $I_D$  is almost halved. In the PMOS [110] and [111] cases Figs. 3(h) and 3(i) (left panels) where the carrier velocity increases as the diameter decreases, the ballistic current is tolerant to diameter variations and reduces only by  $\sim 20\%$  and  $30\%$ , respectively. This is a general behavior at all gate biases.

## IV. DISCUSSION

The velocity variation trends with diameter and orientation are explained in Fig. 4 for NMOS and Fig. 5 for PMOS NWs. These figures show the first occupied subband (subband envelopes) of the NWs of each diameter at off-state conditions. Figures 4(a)–4(c) show results for NMOS NWs in [100], [110], and [111] orientations, respectively. For example, Fig. 4(a) shows the first occupied subband of the  $D=12$  nm (blue-square) down to the  $D=3$  nm (red-dot) NMOS [100] NW. The subband edges of each NW are shifted to the same reference  $E=0$  eV for comparison purposes. The arrows show the direction of diameter decrease. There are two counteracting mechanisms that affect the carrier velocity in these NWs as the diameter decreases, (i) the  $\Gamma$  mass increases, a result of nonparabolicity in the dispersion of the Si bulk bandstructure. From the bulk value of  $m^* = 0.19m_0$ , it increases to  $0.27m_0$  at  $D=3$  nm.<sup>13</sup> (ii) The off- $\Gamma$  valleys with heavier transport mass ( $m^* = 0.89m_0$ ), but light quantization mass, shift higher in energy. The second mechanism is slightly stronger and the combined effect is that the velocities are slightly higher for NWs of smaller diameters. As the gate bias increases, however, electrostatic confinement also increases the valley separation of the larger diameter NWs. No clear trend in the velocities at all biases can, therefore, be identified as earlier described in Fig. 3(a) (right panel).

Figure 4(b) shows the first occupied subband of the [110] NWs of all diameters. As the diameter reduces (i) the  $\Gamma$  mass slightly reduces (a result of the anisotropic dispersion

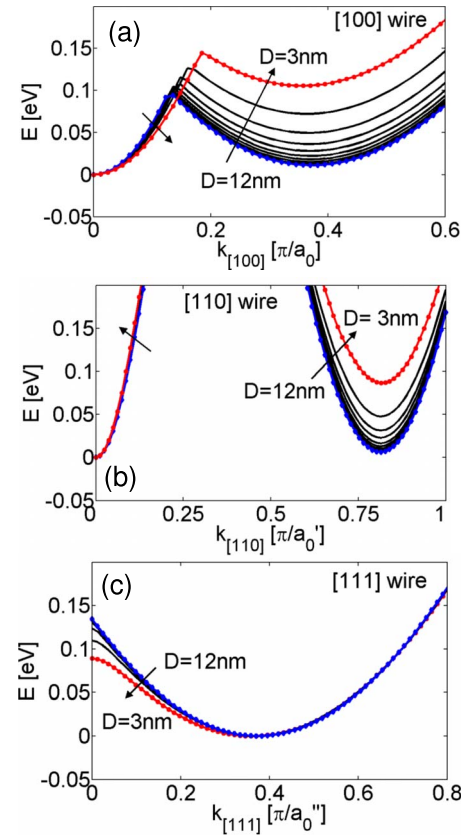


FIG. 4. (Color online) The first subband (subband envelope) of NMOS NWs as the diameter scales from  $D=12$  to  $3$  nm. The arrows indicate the direction of diameter decrease. (a) [100] oriented wires. (b) [110] oriented wires. (c) [111] oriented wires. The minima of all bands are shifted to  $E=0$  eV.

of the Si bulk bandstructure [Ref. 13]), and (ii) the heavier transport mass off- $\Gamma$  valleys shift higher in energy. Both effects tend to increase the carrier velocities. A clear trend in velocity reduction as the diameter reduces is therefore observed, as shown in Fig. 3(b) (right panel).

In the case of the [111] NMOS NWs in Fig. 4(c), the mass of the first conduction subband slightly increases as the diameter reduces (the curvature reduces). This increase is only marginal and does not lead to any observable variations in the carrier velocities as shown in Fig. 3(c) (right panel).

Figure 5 shows the same quantities as in Fig. 4, but for the PMOS NWs. Figure 5(a) shows the first *two* occupied subbands for the [100] PMOS NWs as the diameter reduces from  $D=12$  nm (blue-square) to  $D=3$  nm (red-dot). The subbands indicate no clear trend in their curvature as a function of diameter. Instead, an oscillatory behavior is observed,<sup>14</sup> with several band-crossings between bands from wires of different diameters. (Showing the higher *two* bands in this case indicates the oscillations more clearly). This reflects in the velocities of Fig. 3(a) (left panel), for which no significant variation exists, and as the gate bias increases, the magnitude of the velocities of wires with different diameters is also observed to interchange. The oscillatory behavior of the subbands keeps the carrier velocities low. The low bias velocity of [100] PMOS NWs is  $v_{inj} \sim 0.5 \times 10^5$  m/s, whereas in all other NW categories the velocities are almost  $2 \times$  higher.

The variation pattern in the subband envelopes of the

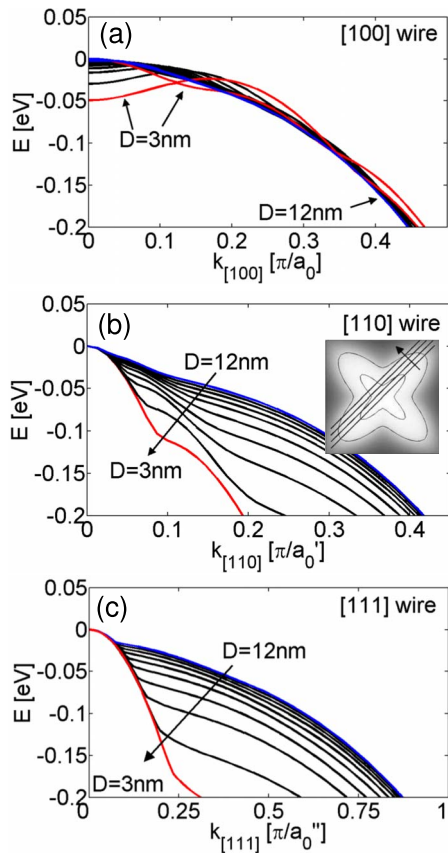


FIG. 5. (Color online) The first subband (subband envelope) of PMOS NWs as the diameter scales from  $D=12$  to  $3$  nm. The arrows indicate the direction of diameter decrease. (a)  $[100]$  oriented wires (the first two subbands are shown). (b)  $[110]$  oriented wires. (c)  $[111]$  oriented wires. The minima of all bands are shifted to  $E=0$  eV. Inset of (b): the heavy-hole subband of the valence band with  $(1\bar{1}0)$  surface quantization subbands indicated.

$[110]$  and  $[111]$  PMOS NWs in Figs. 5(b) and 5(c) is clearer. Here the subbands undergo a large transformation as the diameter decreases, acquiring a larger curvature and lighter effective masses, and thus significantly higher carrier velocities. This explains the velocity trend in Figs. 3(b) and 3(c) (left panels). The subband shape behavior, and its large change under cross section reduction is described in detail in Ref. 14, and is a result of the anisotropy of the heavy-hole subband of the valence band shown in the inset of Fig. 5(b). There, the  $45^\circ$  lines drawn show the relevant energy lines that form the subbands for NWs with the  $(1\bar{1}0)$  surface quantized, as is the case for the  $[110]$  (and  $[111]$ ) oriented NWs. As the diameter reduces, subbands further away from the center of the Brillouin zone are utilized, which have large curvatures and lower effective masses. The arrow along the  $45^\circ$  lines shows the direction of decreased wire cross section, corresponding to larger  $k$ -value quantization. The subband trend in Fig. 5(b) has its origin in this anisotropic energy surface. Of course, real NW quantization involves many more interactions, but the basic trend of the heavy-hole band is transferred to the NW subbands. A similar effect is responsible for the subband trend of the  $[111]$  NWs shown in Fig. 5(c).

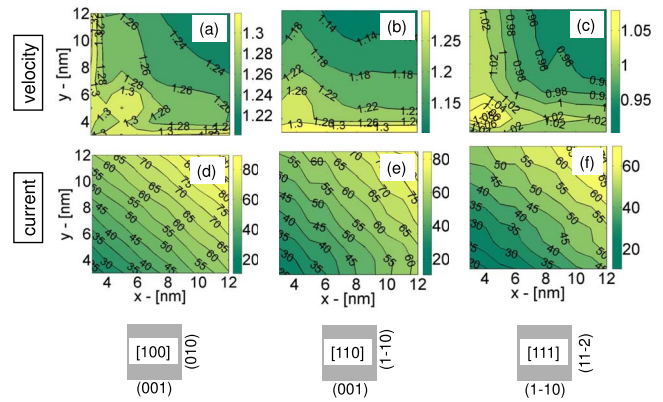


FIG. 6. (Color online) 2D surfaces of transport quantities for rectangular NMOS NWs as the width ( $W$ )/height ( $H$ ) directions vary from  $W=3$  to  $W=12$  nm and  $H=3$  to  $H=12$  nm. [(a)–(c)] The average carrier velocity in  $10^5$  m/s for  $[100]$ ,  $[110]$ , and  $[111]$  directed wires, respectively. [(d)–(f)] The current density in  $\mu\text{A}$  for  $[100]$ ,  $[110]$ , and  $[111]$  directed wires, respectively. The lower row indicates the NW directions and surface orientations.

## V. RESULTS FOR RECTANGULAR NWS

After investigating the carrier velocity and current variations of cylindrical NWs, we extend our analysis to rectangular NWs with widths/heights varying from  $3$  to  $12$  nm (all aspect ratios), for the three orientations under consideration. Figures 6 and 7 show the results for NMOS and PMOS NWs, respectively. Due to the large volume of the data for NWs with various aspect ratios and gate biases, only the velocity (first row) and current (second row) results at on-state ( $V_G=V_D=1$  V for NMOS and  $V_G=V_D=-1$  V for PMOS) are presented. The lower left corners of the subfigures in Figs. 6 and 7 show the velocity/current of the  $3 \times 3$  nm<sup>2</sup> NWs, whereas the upper right corners show the velocity/current of the  $12 \times 12$  nm<sup>2</sup> wires. Other than the width/height of the NWs no other parameter is changed in the simulations.

Figures 6(a)–6(c) (first row of Fig. 6) present the velocity results for the  $[100]$ ,  $[110]$ , and  $[111]$  oriented NMOS NWs, respectively. In all cases, cross section reduction results in higher velocities (higher velocities in the lower/left

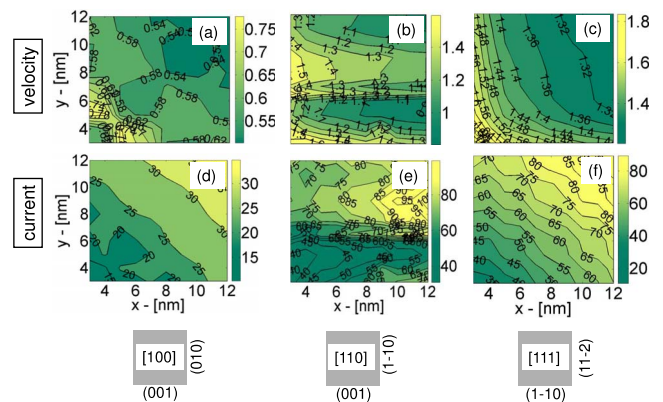


FIG. 7. (Color online) 2D surfaces of transport quantities for rectangular PMOS NWs as the width ( $W$ )/height ( $H$ ) directions vary from  $W=3$  to  $W=12$  nm and  $H=3$  to  $H=12$  nm. [(a)–(c)] The average carrier velocity in  $10^5$  m/s for  $[100]$ ,  $[110]$ , and  $[111]$  directed wires respectively. [(d)–(f)] The current density in  $\mu\text{A}$  for  $[100]$ ,  $[110]$ , and  $[111]$  directed wires, respectively. The lower row indicates the NW directions and surface orientations.



than the upper/right part of the figures). In the [100] NW case in Fig. 6(a), following the cylindrical case arguments, the off- $\Gamma$  valley is pushed higher in energy and the overall velocity is higher. The velocity variation in the entire figure is of the order of  $\sim 8\%$ , ranging from  $1.2 \times 10^5$ – $1.3 \times 10^5$  m/s.

In the case of the [110] NMOS NWs in Fig. 6(b), the width and the height surfaces are in the  $[1\bar{1}0]$  and  $[001]$  directions, respectively, as shown in the third row of Fig. 6. The nature of valley quantization is different for each surface. In the height in the  $[001]$  quantization direction, the  $\Gamma$  valleys have *light transport* mass, but *heavy quantization* mass. The off- $\Gamma$  valleys have the reverse, *heavy transport* mass, but *light quantization* mass. Reducing the height lifts the lightly quantized off- $\Gamma$  valleys, just as in the [100] NW cases above, and increases the velocities [i.e., the velocities increase as one moves from top to bottom in Fig. 6(b)]. On the other hand, in the  $[1\bar{1}0]$  width direction, the off- $\Gamma$  valleys are more heavily quantized than the  $\Gamma$  valleys. Variations in the width do not shift their energy minima strongly, and the carrier velocities are therefore almost constant along that direction.

An extrapolation of our results, indicates that NMOS (001)/[110] channels (extension beyond the lower-right corner of Fig. 6(b)), have higher velocities than NMOS ( $1\bar{1}0$ )/[110] channels (extension beyond the upper-left corner of Fig. 6(b)). Experimental data on the channel mobility versus transport and quantization orientation in Si metal-oxide-semiconductor field-effect transistor (MOSFET) channels<sup>21,43</sup> show that the mobility is also higher for NMOS (001)/[110] rather than ( $1\bar{1}0$ )/[110] channels. Although the mobility depends also on the scattering process and not only on bandstructure, the velocity results point toward a possible explanation of the experimental behavior. Furthermore, for long channel NWs devices with finite width, the fact that the velocity is not sensitive to variations in the  $[1\bar{1}0]$  direction, points toward utilizing this direction as the one for which the line etch control is minimal in the fabrication process, so that the performance variation due to size variations is reduced.

Comparing the magnitude of the carrier velocities, it is very similar in the [100] and [110] oriented NWs in Figs. 6(a) and 6(b) since in both cases it is mostly determined by the  $\Gamma$  valleys. It ranges from  $1.1 \times 10^5$ – $1.3 \times 10^5$  m/s. On the other hand, the velocities of the [111] oriented NWs in Fig. 6(c), are determined by tilted Si conduction band ellipsoids of higher effective mass ( $m^* \sim 0.43m_0$  in bulk).<sup>13</sup> They are therefore  $\sim 30\%$  lower, ranging only from  $0.9 \times 10^5$ – $1.1 \times 10^5$  m/s. Still, however, the same pattern is followed, where size reduction increases carrier velocities.

Figures 6(d)–6(f) present the ballistic on-current results for the NWs in the three orientations. Since the charge increases linearly with the cross section [by almost four times in Fig. 2(b)], and the velocity decreases by only  $\sim 30\%$ , the on-current increases monotonically following the increase in the cross section. As in the cylindrical NW cases earlier, the on-current is higher for the [100] NWs, closely followed by the [110] NWs, whereas the [111] NWs have  $\sim 25\%$  lower on-current. The contour lines in the subfigures, all tilted at

$\sim 45^\circ$ , indicate the linear increase in  $I_D$  with cross section increase, as well as the symmetry between width/height surfaces, even in the velocity asymmetric case of the [110] NWs.

Figures 7(a)–7(c) present the carrier velocities for the rectangular PMOS NWs. The velocities of the [110] and [111] NWs in Figs. 7(b) and 7(c) range from  $v_{inj} \sim 1 \times 10^5$ – $1.5 \times 10^5$  m/s, and  $v_{inj} \sim 1.2 \times 10^5$ – $1.8 \times 10^5$  m/s, respectively, a variation of  $\sim 50\%$ . For the [100] NWs in Fig. 7(a), the velocities range from  $v_{inj} \sim 0.5 \times 10^5$ – $0.8 \times 10^5$  m/s and are much lower compared to all other NW cases of either carrier type. Similar to the NMOS case, in general, cross section size reduction increases the carrier velocities. This is more evident in the [100] and [111] NW orientation cases of Figs. 7(a) and 7(c), respectively. Figure 7(b), on the other hand, shows a strong surface anisotropic behavior for the [110] PMOS NWs. Scaling of either NW side (width in  $[1\bar{1}0]$  or height in  $[001]$ ), increases carrier velocities. In the case of scaling the height, however, at  $\sim 6$  nm the velocity gets a downward jump before it starts to increase again. This is attributed to the anisotropic quantization mass in the two surfaces and detailed explanations are provided in Ref. 15.

It is also worth mentioning here that in the case of the PMOS [110] channels, experimental data<sup>21,43</sup> show that long channel ( $1\bar{1}0$ )/[110] MOSFET channels have higher mobility than the (001)/[110] ones, the opposite of what is observed in the NMOS [110] channels. The different carrier velocities in the two PMOS channels could point to the reasons that might be responsible for this. Scaling of the  $[1\bar{1}0]$  width quantizes the k-space along the light branch of the anisotropic heavy-hole valley [inset of Fig. 5(b)]. Scaling the  $[001]$  height does not provide this advantage. Although this surface difference is only weakly reflected in the velocities of the narrow NWs of Fig. 7(b) (left versus lower parts), simulations using real 2D bandstructures could potentially demonstrate the difference in velocities between the two surfaces. In general, however, physical scaling of the channel in directions that utilize the larger curvature regions of the bulk bandstructure is beneficial to the carrier velocity and device performance (as the scaling of the  $[1\bar{1}0]$  width in the PMOS ( $1\bar{1}0$ )/[110] case).

Figures 7(d)–7(f) show the PMOS NWs ballistic on-current results for the three orientations. In the [100] case in Fig. 7(d) and [111] case in Fig. 7(f), the on-current increases monotonically as the cross section increases, similar to the NMOS cases. In the case of the [110] NWs in Fig. 7(e), the on-current has a more complex behavior, following the complex behavior of the velocity in Fig. 7(b). Here, the regions of 3–5 nm and 7–12 nm of height, and for any width are design regions for low on-current variations to large cross section variations. Around a height of  $\sim 6$  nm, however, large variations are observed and device designs with such height should be avoided. Comparing the magnitude of the on-current in the PMOS NW cases, it is in general higher for the [111] NWs, closely followed by the [110] NWs, whereas the performance of the [100] NWs is almost half compared to the other NWs.



TABLE I. Relative performance comparison for the NWs of the different orientations and diameters: (a) NMOS. (b) PMOS.

NMOS performance	[100]	[110]	[111]
Small $D$ (3 nm)	High (2)	High (1)	Low (3)
Large $D$ (12 nm)	High (1)	High (2)	Fair (3)
PMOS performance	[100]	[110]	[111]
Small $D$ (3 nm)	Low (3)	High (2)	High (1)
Large $D$ (12 nm)	Low (3)	Fair (2)	High (1)

## VI. DESIGN CONSIDERATIONS

Table I summarizes the performance comparisons between the NWs of the different orientations for the small ( $D=3$  nm) and the larger ( $D=12$  nm) diameters. The indications “High,” “Fair,” and “Low”, refer to the relative performance of the NWs of each row (orientation comparison) and not necessarily on an absolute scale. The numbers within brackets correspond to the performance order (both carrier velocity and current have the same order) of the different orientated NWs within each row. Although this table is constructed according to the cylindrical NW results, the same conclusions follow in the cases of the rectangular devices.

In the case of NMOS NWs, in Table I, both the [100] and [110] orientations have high performance, with the [100] orientation having an advantage at larger diameters and the [110] at smaller diameters. The [111] NWs have lower performance at smaller diameters and fair at larger diameters compared to the two other orientations. The PMOS performance comparison is also shown in Table I. In this case, the [111] orientation is the most advantageous in all diameter ranges, closely followed by the [110] orientation, whereas the [100] orientation performs purely for all NW diameters. PMOS [111] NWs perform higher than all other NWs (PMOS or NMOS), and are the optimal solution for applications that require high performance individual NWs. Since the NMOS [111] and especially the PMOS [100] NWs perform purely, for CMOS applications that both NMOS and PMOS high performance is required, the [110] orientation seems to be the optimal solution.

Upto this point our analysis considered infinitely long, undistorted NWs with perfect surfaces, assuming perfect manufacturability. In reality, structure imperfections exist in devices and affect the performance.<sup>44–48</sup> Controlling the line edge roughness in nanofabrication processes imposes challenges, and the lack of it leads to device-to-device performance variations. The width is usually less well controlled since it is formed by etching, whereas the height is controlled by growth and can be more precise. For the high performance rectangular PMOS [110] NWs build on (001) substrates, the on-current is not significantly sensitive to the width [Fig. 7(e)]. It is also not significantly sensitive to the height, except at around 6 nm of height, a design region that should be avoided. In the NMOS [110] case the (001)/[110] configuration is also beneficial since the velocity is almost constant in the  $[1\bar{1}0]$  width direction. Although the ballistic on-current in Fig. 6(e) is symmetric with respect to the

width/height, devices are not 100% ballistic, and therefore it is still beneficial to have the direction of least control aligned with the direction of velocity invariance.

As a design strategy, therefore, our results demonstrate that out of all NWs examined, the [110] oriented NWs are advantageous for CMOS technology applications in either design case, (i) if the design goal is driven by the highest performance assuming perfect manufacturing abilities or (ii) if the design is driven by low device-to-device performance fluctuations. Design regions with velocity and on-current insensitivity to geometry can provide low device-to-device variations strategies for both, long channel devices, and short channel close-to-ballistic devices. In the cases of the [110] channel orientations built on (001) substrates, design regions can be identified for either case, while still keeping the performance high.

An important source of performance variation and degradation is surface roughness scattering (SRS). To quantify the previous results, we examine the effect of SRS on the velocity and current variations for the case of the NMOS [110]  $D=3$  nm cylindrical NW. For this purpose, real-space 3D, full-band, quantum ballistic simulations are performed using the OMEN code,<sup>17,35,36</sup> in which the roughness is treated in a realistic way by adding/subtracting atoms on the surface of the NW.<sup>44</sup> A  $\sim 15\%$  degradation, as well as an additional  $\sim 30\%$  variation in the velocities is computed by using a sample size of 50 rough NWs. A 10% variation in the on-current is also observed, in agreement with other works.<sup>45,47,48</sup> This is an indication of an additional variation, on top of the variation expected due to bandstructure as a result of diameter change. A proper and more elaborate investigation the effect of SRS which targets all orientations and a large range of diameter sizes will be presented elsewhere. These numbers, however, further stress the need of device and circuit designs tolerant to performance variations originating from structure variations and nonidealities. Bandstructure features can provide a mechanism to partially help on this.

## VII. CONCLUSION

An atomistic tight-binding approach and a semiclassical ballistic model are used to calculate the bandstructure velocity and ballistic current of NW devices, self-consistently with the electrostatic potential. NMOS and PMOS NWs of diameters from  $D=12$  nm down to  $D=3$  nm in [100], [110], and [111] orientations, of cylindrical and rectangular cross sectional shapes are considered. The carrier velocities are strong function of orientation, band type, diameter, and bias. Cross section scaling, in general increases the carrier velocities either by raising the energy minima of the heavier transport mass valleys or by significantly changing the subbands' curvature. PMOS [110] and [111] NWs have the largest velocity sensitivity to diameter, in which cases the velocity doubles as the diameter scales from  $D=12$  to  $D=3$  nm. The carrier velocity of NMOS [110] NWs is also sensitive to the diameter but at a smaller degree. On the other hand, the velocities of NMOS [100] and [111], and PMOS [100] NWs are insensitive to the diameter. Gate bias also tends to increase carrier

velocities by  $\sim 50\%$ , as higher energy states are occupied at inversion conditions. Trends in carrier velocity with diameter do not completely reflect to the terminal current characteristics because the carrier density is also subject to the change of the cross section geometry. The ballistic on-current shows less sensitivity with cross section fluctuations in the cases of [110] PMOS and [111] PMOS NWs, whereas in the rest of the cases it varies linearly with cross section. The PMOS [111] NWs are the ones with the highest performance from all NW categories, whereas the PMOS [100] the ones with the lowest performance. The [110] oriented NWs, on the other hand, are the ones with both, high NMOS and PMOS carrier velocities and on-current, and therefore more suitable for CMOS applications. In either case, if the design goal is driven by the highest performance assuming perfect manufacturability or if the design is driven by low device-to-device performance fluctuations, this study suggests the (001)/[110] oriented NWs for both NMOS and PMOS NW devices for either long channel or short channel ballistic devices.

## ACKNOWLEDGMENTS

This work has been partially supported by funds from the Austrian Science Fund, FWF, Contract No. I79-N16. S.G. Kim was supported by Materials Structures and Devices Focus Center MSD/MARCO. Dr. Mathieu Luisier is acknowledged for providing the quantum transport code for the surface roughness calculations and for various discussions. Computational resources of the Network for Computational Nanotechnology (NCN) operated by nanoHUB.org are acknowledged. The simulations in this work can be duplicated with Bandstructure Lab on nanoHUB.org (Ref. 49).

<sup>1</sup>ITRS Public Home Page, <http://www.itrs.net/reports.html>.

<sup>2</sup>N. Singh, F. Y. Lim, W. W. Fang, S. C. Rustagi, L. K. Bera, A. Agarwal, C. H. Tung, K. M. Hoe, S. R. Omampuliyur, D. Tripathi, A. O. Adeyeye, G. Q. Lo, N. Balasubramanian, and D. L. Kwong, *Tech. Dig. - Int. Electron Devices Meet.* **2006**, 548.

<sup>3</sup>K. H. Cho, Y. C. Jung, B. H. Hong, S. W. Hwang, J. H. Oh, D. Ahn, S. D. Suk, K. H. Yeo, D.-W. Kim, D. Park, and W.-S. Lee, *Tech. Dig. - Int. Electron Devices Meet.* **2006**, 1-4.

<sup>4</sup>K. H. Cho, K. H. Yeo, Y. Y. Yeoh, S. D. Suk, M. Li, J. M. Lee, M.-S. Kim, D.-W. Kim, D. Park, B. H. Hong, Y. C. Jung, and S. W. Hwang, *Appl. Phys. Lett.* **92**, 052102 (2008).

<sup>5</sup>M. Kobayashi and T. Hiramoto, *J. Appl. Phys.* **103**, 053709 (2008).

<sup>6</sup>J. Xiang, W. Lu, Y. Hu, Y. Wu, H. Yan, and C. M. Lieber, *Nature (London)* **441**, 489 (2006).

<sup>7</sup>K. H. Yeo, S. D. Suk, M. Li, Y.-Y. Yeoh, K. H. Cho, K.-H. Hong, S. K. Yun, M. S. Lee, N. Cho, K. Lee, D. Hwang, B. Park, D.-W. Kim, D. Park, and B.-I. Ryu, *Tech. Dig. - Int. Electron Devices Meet.* **2006**, 717.

<sup>8</sup>S. Huang and Y. Chen, *Nano Lett.* **8**, 2829 (2008).

<sup>9</sup>C. B. Winkelmann, I. Ionica, X. Chevalier, G. Royal, C. Bucher, and V. Bouchiat, *Nano Lett.* **7**, 1454 (2007).

<sup>10</sup>M. Law, L. E. Greene, J. C. Johnson, R. Saykally, and P. Yang, *Nature Mater.* **4**, 455 (2005).

<sup>11</sup>A. I. Boukai, Y. Bunimovich, J. Tahir-Kheli, J.-K. Yu, W. A. Goddard III, and J. R. Heath, *Nature (London)* **451**, 168 (2008).

<sup>12</sup>A. I. Hochbaum, R. Chen, R. D. Delgado, W. Liang, E. C. Garnett, M. Najarian, A. Majumdar, and P. Yang, *Nature (London)* **451**, 163 (2008).

<sup>13</sup>N. Neophytou, A. Paul, M. Lundstrom, and G. Klimeck, *IEEE Trans. Electron Devices* **55**, 1286 (2008).

<sup>14</sup>N. Neophytou, A. Paul, and G. Klimeck, *IEEE Trans. NanoTechnol.* **7**, 710 (2008).

<sup>15</sup>N. Neophytou and G. Klimeck, *Nano Lett.* **9**, 623 (2009).

<sup>16</sup>M. Luisier, A. Schenk, and W. Fichtner, *Proceedings of the 12th International Conference on Simulation of Semiconductor Processes and Devices (SISPAD 2007)* (Springer, Wien, New York, 2007), pp. 221–224.

<sup>17</sup>M. Luisier and G. Klimeck, *Proceedings of the 13th International Conference on Simulation of Semiconductor Processes and Devices (SISPAD 2008)*, 9–11 September 2008 (IEEE, Piscataway, NJ, 2008), pp. 17–20.

<sup>18</sup>G. C. Liang, J. Xiang, N. Kharche, G. Klimeck, C. M. Lieber, and M. Lundstrom, *Nano Lett.* **7**, 642 (2007).

<sup>19</sup>Y. Liu, N. Neophytou, T. Low, G. Klimeck, and M. S. Lundstrom, *IEEE Trans. Electron Devices* **55**, 866 (2008).

<sup>20</sup>M. V. Fischetti, Z. Ren, P. M. Solomon, M. Yang, and K. Rim, *J. Appl. Phys.* **94**, 1079 (2003).

<sup>21</sup>M. Yang, V. W. C. Chan, K. K. Chan, L. Shi, D. M. Fried, J. H. Stathis, A. I. Chou, E. Gusev, J. A. Ott, L. E. Burns, M. V. Fischetti, and M. Jeong, *IEEE Trans. Electron Devices* **53**, 965 (2006).

<sup>22</sup>E. X. Wang, P. Matagne, L. Shifren, B. Obradovic, R. Kotlyar, S. Cea, and M. Stettler, *IEEE Trans. Electron Devices* **53**, 8 (2006).

<sup>23</sup>E. Gnani, A. Gnudi, S. Reggiani, and G. Baccarani, *IEEE Trans. Electron Devices* **57**, 336 (2010).

<sup>24</sup>S. Jin, M. V. Fischetti, and T.-W. Tang, *J. Appl. Phys.* **102**, 083715 (2007).

<sup>25</sup>R. Kotlyar, B. Obradovic, P. Matagne, M. Stettler, and M. D. Giles, *Appl. Phys. Lett.* **84**, 5270 (2004).

<sup>26</sup>R. Kim and M. Lundstrom, *IEEE Trans. Electron Devices* **56**, 132 (2009).

<sup>27</sup>S. E. Thompson, M. Armstrong, C. Auth, M. Alavi, M. Buehler, R. Chau, S. Cea, T. Ghani, G. Glass, T. Hoffman, C.-H. Jan, C. Kenyon, J. Klaus, R. Kuhn, M. Zhiyong, B. McIntyre, K. Mistry, A. Murthy, B. Obradovic, R. Nagisetty, N. Phi, S. Sivakumar, R. Shaheed, L. Shifren, B. Tufts, S. Tyagi, M. Bohr, and Y. El-Mansy, *IEEE Trans. Electron Devices* **51**, 1790 (2004).

<sup>28</sup>M. Saitoh, S. Kobayashi, and K. Uchida, *Tech. Dig. - Int. Electron Devices Meet.* **2007**, 711.

<sup>29</sup>T. B. Boykin, G. Klimeck, and F. Oyafuso, *Phys. Rev. B* **69**, 115201 (2004).

<sup>30</sup>G. Klimeck, F. Oyafuso, T. B. Boykin, R. C. Bowen, and P. von Allmen, *Comput. Model. Eng. Sci.* **3**, 601 (2002).

<sup>31</sup>G. Klimeck, S. Ahmed, H. Bae, N. Kharche, S. Clark, B. Haley, S. Lee, M. Naumov, H. Ryu, F. Saied, M. Prada, M. Korkusinski, and T. B. Boykin, *IEEE Trans. Electron Devices* **54**, 2079 (2007).

<sup>32</sup>J. C. Slater and G. F. Koster, *Phys. Rev.* **94**, 1498 (1954).

<sup>33</sup>M. S. Lundstrom and J. Guo, *Nanoscale transistors: Device Physics, Modeling and Simulation* (Springer, New York, 2006).

<sup>34</sup>A. Rahman, J. Guo, S. Datta, and M. Lundstrom, *IEEE Trans. Electron Devices* **50**, 1853 (2003).

<sup>35</sup>M. Luisier and G. Klimeck, *Proceedings of the 8th IEEE Conference on Nanotechnology*, 18–21 August 2008 (IEEE, Piscataway, NJ, 2008), pp. 18–21.

<sup>36</sup>M. Luisier, N. Neophytou, N. Kharche, and G. Klimeck *Tech. Dig. - Int. Electron Devices Meet.* **2008**, 887–891.

<sup>37</sup>R. C. Bowen, G. Klimeck, R. Lake, W. R. Frensley, and T. Moise, *J. Appl. Phys.* **81**, 3207 (1997).

<sup>38</sup>J. Wang, Ph.D. thesis, Purdue University, 2005.

<sup>39</sup>N. Kharche, M. Prada, T. B. Boykin, and G. Klimeck, *Appl. Phys. Lett.* **90**, 092109 (2007).

<sup>40</sup>R. Rahman, C. J. Wellard, F. R. Bradbury, M. Prada, J. H. Cole, G. Klimeck, and L. C. L. Hollenberg, *Phys. Rev. Lett.* **99**, 036403 (2007).

<sup>41</sup>S. Lee, F. Oyafuso, P. Von Allmen, and G. Klimeck, *Phys. Rev. B* **69**, 045316 (2004).

<sup>42</sup>A. Paul, S. Mehrotra, G. Klimeck, and M. Luisier, *Proceedings of International Workshop on Computer Electronics (IWCE)*, Beijing China, May 2009, (IEEE, Piscataway, NJ, 2009), pp. 177–180.

<sup>43</sup>L. Chang, M. Jeong, and M. Yang, *IEEE Trans. Electron Devices* **51**, 1621 (2004).

<sup>44</sup>M. Luisier, A. Schenk, and W. Fichtner, *Appl. Phys. Lett.* **90**, 102103, 2007.

<sup>45</sup>J. Wang, E. Polizzi, A. Ghosh, S. Datta, and M. Lundstrom, *Appl. Phys. Lett.* **87**, 043101 (2005).

<sup>46</sup>N. Seoane, A. Martinez, A. R. Brown, J. R. Barker, and A. Asenov, *IEEE Trans. Electron Devices* **56**, 1388 (2009).

<sup>47</sup>M. Lenzi, A. Gnudi, S. Reggiani, E. Gnani, M. Rudan, and G. Baccarani, *J. Comput. Electron.* **7**, 355 (2008).

<sup>48</sup>S. Poli, M. G. Pala, T. Poiroux, S. Deleonibus, and G. Baccarani, *IEEE Trans. Electron Devices* **55**, 11 (2008).

<sup>49</sup>nanoHub Bandstructure lab on nanoHUB.org (<https://www.nanohub.org/tools/bandstrlab/>).