

**PERMEABILITY AND ABSORPTIVITY
OF
INDIANA LIMESTONE
COARSE AGGREGATES**

**MARCH, 1956
No. 9**

by

W. L. Dolch

**Joint
Highway
Research
Project**

**PURDUE UNIVERSITY
LAFAYETTE INDIANA**

PERMEABILITY AND ABSORPTIVITY
OF
INDIANA LIMESTONE COARSE AGGREGATES

TO: K. B. Woods, Director
Joint Highway Research Project

March 13, 1956

FROM: Harold L. Michael, Assistant Director

File: 5-7-7
C-36-47F

Attached is a copy of a report, "Permeability and Absorptivity of Indiana Limestone Coarse Aggregates," by W. L. Dolch of our staff. The report covers work done in the chemistry laboratory of the Joint Highway Research Project on the pore structure of certain coarse aggregates and its relation to their durability histories in concrete.

Respectfully submitted,


HL Michael /wld

Harold L. Michael, Assistant Director
Joint Highway Research Project

HEM/WLD:cjg

Attachment

cc: J. R. Cooper	R. E. Mills
J. T. Hallett	B. H. Petty
F. F. Havey	Lloyd Poindexter
G. A. Hawkins	C. E. Vogelgesang
G. A. Leonards	J. L. Waling
B. B. Lewis	



Digitized by the Internet Archive
in 2011 with funding from
LYRASIS members and Sloan Foundation; Indiana Department of Transportation

PERMEABILITY AND ABSORPTIVITY
OF
INDIANA LIMESTONE COARSE AGGREGATES

by

W. L. Dolch, Research Assistant
Joint Highway Research Project

File: 5-7-7

C-36-47F

Purdue University
Lafayette, Indiana

March 13, 1956

ACKNOWLEDGMENTS

The friendly advice and counsel of Prof. K.B. Woods, Head of the School of Civil Engineering, Purdue University, are acknowledged with many thanks. The encouragement and academic sponsorship of Dr. M.G. Mellon, Professor of Chemistry, Purdue University, have been greatly appreciated.

Dr. G.A. Leonards, Professor of Soil Mechanics, Purdue University, has been generously helpful in every way. His technical advice and assistance and his review of the manuscript are gratefully acknowledged.

Mr. L.S. Gifford, Jr. finished most of the sample prisms and built the air bath and Mr. B. Bradley traced the data curves.

This work was financed by the State Highway Commission of Indiana through the Advisory Board of the Joint Highway Research Project. This support is gratefully acknowledged.

CONTENTS

	Page
LIST OF TABLES	v
LIST OF FIGURES	vi
ABSTRACT	vii
INTRODUCTION	1
Statement of the Problem	1
Statement of Purpose	2
Literature Review	3
Approach Used in this Work	15
EXPERIMENTAL WORK.	16
Materials.	16
Sample Preparation	19
Apparatus and Procedure.	21
Absorption	21
Densities	22
Porosity	26
Specific Surface	30
Tortuosity	35
Permeability	38
Absorptivity	46
Calculations	48
Data	49
Density, Porosity, Absorption, and Saturation.	49
Tortuosity	49
Specific Surface	52
Permeability	52
Absorptivity	63
DISCUSSION	72
Theoretical Background	72
Permeability and Pore Structure.	72
Absorptivity and Pore Structure.	78
Results	81
Discussion of Data and Results	83
Densities and Porosity	85
Tortuosity	87
Sorption Measurements.	88
Permeability	90
Absorptivity	92
Saturation	95
Absorptivity-Permeability Relationship	97
Radii	101
Specific Surfaces.	102

Interpretation of Data and Results	106
SUMMARY OF RESULTS	125
CONCLUSIONS	128
RECOMMENDATIONS	130
BIBLIOGRAPHY	132
APPENDIX A. INFLUENCE OF n ON TORTUOSITY	139
APPENDIX B. DERIVATION OF PERMEAMETER EQUATION	141
APPENDIX C. DERIVATION OF PERMEABILITY RELATIONSHIPS	145
APPENDIX D. DERIVATION OF SLIP FACTOR RELATIONSHIP	148
APPENDIX E. DERIVATION OF ABSORPTIVITY RELATIONSHIPS	151
APPENDIX F. REEF ROCK DATA	155
VITA	158

LIST OF TABLES

	Page
1. General Description of Test Materials	17
2. Chemical and Mineralogical Composition of Test Materials	18
3. Densities, Porosity, Absorption, and Saturation . . .	50
4. Tortuosities and Associated Factors	51
5. Specific Surfaces	54
6. Permeability and Slip Factor	62
7. Absorptivity Results	63
8. Calculated Average Pore Radii of the Rocks	82
9. Calculated Specific Surfaces of the Rocks	84
10. Unit Saturations	121
11. Absorptivity-Permeability Ratios	122

LIST OF FIGURES

	Page
1. Volumenometer	25
2. Porosimeter	28
3. Sorption Apparatus	33
4. Permeameter	43
5. Sorption Isotherms	53
6. Permeability of 1-LS-P-37	55
7. Permeability of 3-LS-H-P-30p	56
8. Permeability of 9-LS-P-73	57
9. Permeability of 9-LS-P-54p	58
10. Permeability of 9-LS-P-73, Low Pressure Runs	59
11. Permeability of 47-2S-P-98	60
12. Permeability of 67-2S-P-45	61
13. Absorptivity of 1-LS	64
14. Absorptivity of 3-LS-H-P-30p	65
15. Absorptivity of 9-LS-p	66
16. Absorptivity of 9-LS, Effect of Flow Direction	67
17. Absorptivity of 9-LS-P-199, Effect of Various Exposures	68
18. Absorptivity of 47-2S	69
19. Absorptivity of 67-2S	70
20. pK_a vs. pK_1	100
21. Absorptivity of Reef Rock	156

ABSTRACT

Many studies have shown the importance of the coarse aggregate component in the determination of the resistance to freezing and thawing as a durability factor in the performance of pavement concrete. Field and laboratory studies have been used in Indiana to identify certain limestone coarse aggregates as outstandingly good or poor with respect to the resistance to frost action of the concrete made with them. Data from standard tests of aggregates are only partially successful in the prediction of the field performance of pavements. Information is inadequate concerning the mechanisms by which these materials exert such great influence.

Since the presence of water is fundamental to frost damage, the details of the acquisition and retention of water by these materials and of its movement therein become important. The pore structure has been shown to be one of the most important properties of coarse aggregates when they are used in portland-cement concrete. The nature of this structure is not completely evaluated by tests now being performed on these materials. More information is needed concerning this property.

This study was designed to investigate the usefulness of simple fluid-flow measurements and of the data derived therefrom with respect to the elucidation of the pore structure of limestone coarse aggregates and to a possible correlation with the durability histories of pavements made with limestone aggregates.

Five limestones with well-established durability histories were chosen. The quarries were sampled. Small prisms were cut from the larger samples and were finished by hand grinding. Their dimensions were measured. The specific surfaces were determined on pulverized samples by the use of water-vapor sorption with a gravimetric technique and the Brunauer, Emmett, Teller theory. Values of the absorption for both the immersed and the vacuum-saturated conditions were determined by conventional methods on the prisms. Porosities and true and bulk densities were determined using a gas-compression volumometer and a McLeod gage porosimeter. Permeabilities were determined at various mean pressures with a pressure-decay permeameter and an equation derived for this apparatus. The Klinkenberg slip factors and the pressure-independent permeabilities were determined from the plots of the permeability data. Tortuosities of the rocks were measured by the electrical-analog resistivity method. Absorptivities were determined with a simple gravimetric technique.

The specific surfaces and average pore radii were calculated from these data on the basis of a tortuous capillary-tube model. These calculations were made using the Kozeny equation for the permeabilities, a modified Klinkenberg equation for the slip factors, and a derived equation for the absorptivities.

The absorptivity method was found to be superior to the permeability or slip methods as an interpreter of specific surface. An empirical relation was shown by means of which a fairly-good value of the permeability could be derived from the easily-measured absorptivity value.

The tortuosities, slip factors, and average pore radii had no relation to the durability histories of the materials. The poor-quality materials had higher porosities, permeabilities, specific surfaces, and absorptivities than did the good-quality materials. The differences were especially noticeable in the case of the absorptivity values. The materials could also be separated according to their durability histories on a basis of the rate of capillary saturation which was calculated from the absorptivities and the porosities and on a basis of the ratio of absorptivity to permeability; the poor-quality materials in every case had higher rates of saturation and higher absorptivity to permeability ratios.

The usefulness of the methods and principles involved and the desirability of their further application to evaluating the quality of coarse aggregates for use in portland-cement concrete are indicated.

INTRODUCTION

Statement of the Problem

During 1943-4 a comprehensive performance survey was made of Indiana's rigid pavements. The results were reported by Woods, Sweet, and Shelburne (95) and constituted the starting point for subsequent work on Indiana's coarse aggregate materials. Deterioration of concrete pavements, especially the frequency of blowups and map cracking, was studied in its relation to influential factors. The significant results of the study, as stated in the synopsis, were:

- (1) An outstanding correlation existed between certain coarse aggregates used in the concrete mix and the blowup performance of the pavements.
- (2) No correlation existed between the cement, fine aggregate, traffic, or subgrade soils used and blowup performance.
- (3) Extensive laboratory research is indicated as necessary to determine the basic reason for the variation in performance....and to develop new and better methods of tests....

These data [i.e., results] were considered important, since it was observed generally that map cracking, serious disintegration, and a relatively short pavement life accompanied the blowup failures.

A research program was therefore started at the Joint Highway Research Project. This program is a part of the general research studies on the durability of concrete. Significant results have come from these studies. Non-durable materials have been identified. Tests for performance prediction have been set up and improved. Accurate information on the properties of some of the components of concrete has been obtained. Hypotheses concerning the influences of

various agents on concrete have been derived and, in some cases, verified. Considerable insight into the nature of concrete durability has been obtained, but the picture is far from complete. In the studies at the Joint Highway Research Project principle emphasis has been placed on the influence exerted over the durability of concrete by the coarse aggregate component. This component seems to be determinative in Indiana experience. The study reported here is part of that continuing program and was designed to give information on what are considered to be important properties of aggregates.

Statement of Purpose

The pore structure of coarse aggregates has been shown to have an important influence on the durability of concrete. This structure is of particular importance in freezing-and-thawing durability and probably exerts considerable influence on blowup frequency, cement-aggregate reaction, and bond of aggregate with the paste. Past investigations of porosity have been limited to determinations of the total porosity and of the degree of microporosity of the aggregate. Additional information is needed on the pore structures of these materials.

The purpose of this study was to investigate the pore structure of certain Indiana limestone coarse aggregate materials by means of fluid-flow experiments and to relate the data obtained to properties of the material, to field performance, and to hypotheses concerning the movement and freezing of water in concrete.

Literature Review

In this review the problem of the durability of concrete is outlined. Special attention is placed on the influence of the coarse aggregate under freezing and thawing conditions. Hypotheses of frost action are summarized and the importance of the pore structure is emphasized. Work which has been done to elucidate the pore structure of aggregates and concrete is outlined.

The problem of the durability of concrete is complex. Concrete is a heterogeneous material and this, in itself, introduces complications. There are several choices of aggregate materials and gradations. Cements differ in chemical and physical properties. The possibility of a number of additives exists. Mix designs differ as do methods of handling, placement, and curing. Environmental conditions for the finished concrete are widely variable. All these factors can influence durability, by which is meant permanence when overloading, in the structural sense, is not primarily involved.

The general problem of the durability of concrete has been reviewed recently by Scholer (75) and by Jones (36). These reviewers stressed the complex nature of the problem and cited the large number of possible influences and interactions. They give the impression that in hardly any of its aspects can the question of concrete durability be considered satisfactorily solved.

Two methods of approach are possible. One is to study the properties of the mixture and the other is to study the properties of the individual components. From such individual properties deductions are

then made concerning the behavior and properties of the combined material. This is a valid approach if it is realized that the interactions may modify the behavior of the components once they are combined.

The properties of cement paste have been investigated with great thoroughness. Illustrative of this work is the series of papers by Powers and Brownyard (60). Experience in Indiana is, however, that the component exerting the greatest influence on pavement durability is the coarse aggregate. Most of what follows will, therefore, be confined to the influence of the coarse aggregate while realizing that it can be considered separately only to a degree.

Lack of durability due to coarse aggregate can take a variety of forms. First in importance, for the purposes here, is failure due to instability in freezing and thawing. The aggregate may be responsible for frequent blowups of the pavement concrete. The thermal properties of coefficient of expansion and diffusivity of the aggregate may be so incompatible with those of the paste that failure is caused by heating and cooling. The aggregate may contain material which undergoes chemical reactions with the paste. This can, in turn, result in excessive expansion of the concrete. The best-known of such reactions is the alkali-aggregate reaction in which certain silicious materials in the aggregate react with alkalis from the cement. There may be, however, other harmful reactions. The aggregate may contain substances, such as certain clays, that swell and contract to a large extent on wetting and drying and thereby contribute to expansion of the concrete mass. The differential swelling and contracting between the aggregate itself and

the paste as the degree of saturation changes can also cause stress. All these influences can cause distress of the concrete.

The properties of aggregate materials and their influence on concrete are discussed in the above-mentioned reviews by Scholer (75) and by Jones (36). The reviews by Blanks (11) and by Rhoades and Mielenz (66, 67) deal specifically with aggregates. Sweet (82) gave a review of the influence of aggregates on pavement durability. He also reviewed methods of testing aggregates and the meaning of the results of such tests (80). Aggregates were discussed, with specific reference to the influence and measurement of porosity, by Lewis, Dolch, and Woods (45). Powers (59) recently reviewed the properties of paste and aggregates, alone and in combination, from the point of view of the relationship between physical structure and the movement of water on freezing and thawing.

The early conclusions of Woods, Sweet, and Shelburne (95) were expanded as a result of a subsequent paper by Sweet and Woods (83) which showed the importance of the subgrade soil and its moisture-retention properties. Lack of durability was most prevalent and deterioration most rapid on poorly-drained soils. Chert was identified as a particularly deleterious constituent of Indiana aggregates (79). Then in 1948 Sweet (81) reported a comprehensive study of Indiana aggregates with well- or partly-established performance records. His tests included unconfined freezing and thawing, freezing and thawing of concrete, microscopic determination of micropores, and sodium-sulfate soundness, as well as the more ordinary determinations such as absorption and specific gravity. He found the same aggregates which had been

identified by Woods, Sweet, and Shelburne as causing severe blowup distress and cracking to be non-durable in freezing and thawing. Unconfined freezing and thawing and sodium-sulfate soundness results did not confirm field experience of durability. Absorption and degree of saturation of the aggregates were fairly good indexes of freezing and thawing performance but a range was found which was intermediate between the clearly good and the clearly poor materials. One of the most interesting findings was that all the harmful materials had voids ratios greater than 0.1 for voids smaller in diameter than five microns (micropores) while the good materials had corresponding ratios of less than 0.06. Fears (28) confirmed this finding in his investigation of the microscopic method of determining microporosity.

Chemical tests of most of the state's stones and some of its gravels were reported by Slate (77) and showed no consistent relationship between chemical composition and field performance. More of the poor-performing stones were dolomites than limestones and this trend was attributed to porosity characteristics. These materials were also tested for alkali reactivity and only one material, a chert, was found to have borderline reactivity. Blackburn (9) has since reported positive results for the "quick chemical test" for alkali reactivity of several Indiana gravels but the stones seem to be immune.

Sweet (81) mentioned the possibility of thermal incompatibility being a factor in the deterioration he observed. A limited amount of work on the thermal properties of the state's stones was done by Lu (49), who measured the expansion coefficient, and by Fox and Dolch (30) who determined the thermal diffusivity. The latter study showed the

poor performing stones to have slightly higher diffusivities than the good. Both kinds had values considerably higher than that of cement paste. The presence of small amounts of water changed the measured diffusivities considerably. Lu's tests showed a reversal of the expected trend. One of the best materials in the state had a lower coefficient of thermal expansion than did one of the poorest, and this latter almost matched the accepted coefficient for paste. These tests seem to show that thermal incompatibility, if present as a harmful influence, is only of minor importance for Indiana materials.

Work has been done by Bugg (16) and by Blackburn (8) on the performance, in freezing and thawing tests, of concrete containing these same Indiana aggregates and various amounts of entrained air. Their results showed that just enough air to protect the paste did not benefit a bad aggregate but that benefit was obtained as the air content was increased to higher values. The benefit was considerably greater for stones than for gravels. This difference is thought to be due to the localized nature, e.g., chert pebbles, of the harmful elements in gravels. Recent work on gravels by Lewis and Venters (46) showed the deleterious constituents to be highly absorptive particles of low specific gravity. Much of the foregoing work has been summarized by Lewis and Woods (47).

Some of the work at the Joint Highway Research Project has paralleled and complimented work of a similar nature in other organizations. Problems of aggregate durability in freezing and thawing are widespread. (In a paper by Walker and Bloem (85) is a good list of refer-

ences on the general subject.) The Indiana studies have been reviewed in detail because the materials were the same as those used in this work.

The results of the studies point to field performance, with respect to a widespread type of distress (characterized by D-line cracking, followed by slab failure), being reasonably reproducible in laboratory freezing and thawing tests. Assuming favorable conditions with respect to the paste component, the deterioration of the concrete seems traceable to the aggregate component and, in Indiana at least, to the coarse aggregate component.

The research work on the freezing and thawing durability of concrete has had two aspects. By far the greater amount of work has been done on test methods in an effort to reproduce field performance and to predict such performance for new materials. Several variations of test methods have been devised. A trend toward automation and acceleration of testing has taken place. The other aspect of the work has been the attempts toward an understanding of the phenomena involved, i.e., toward the postulation of a mechanism and toward its verification. A full understanding of the problem waits on such results, however perfect the diagnostic tests may become.

The work on test methods has also given useful fundamental information. An example is the work of Sweet (81) which showed the importance of absorption, saturation, and microporosity.

Much fundamental information on these matters has come from workers in the fields of brick, building stone, ceramics, soils, and cement paste.

An early paper on bricks was written by Jones (37) in 1907 in which he discussed the freezing of water in a porous system and pointed out the importance of the permeability of the material. His discussion was a forerunner of the modern hydraulic pressure theory.

In the early 1920's Washburn and his co-workers presented a series of papers (87, 89, 90, 91, 92) on the pore structure, absorption, capillarity, and saturation of ceramics that included an analysis of methods for measuring these properties.

Work on building stone has been of particular importance. With the modification of inclusion of the cement paste component, the freezing problems for building stone are analagous to those of aggregate materials and much of the results has bearing on the aggregate problem.

Howe (34) in 1910 noted the importance of the type of porosity and the degree of saturation. Seipp (76) stated the critical degree of saturation to be about 0.91 for freedom from frost action but Kreuger (41) found lower critical degrees of saturation--of the order of 0.85--and postulated inhomogeneous water distribution.

Comprehensive reports on building stones are those by Schaffer (71) and by Thomas (84). Schaffer was concerned with all aspects of building stone durability. His report seems to be the first to announce a pore diameter of five microns as critical, with respect to freezing durability. This value was obtained from microscopic measurements. It was substantiated for aggregates by Sweet (81) and by Fears (28) who used the microscopic method and by Blanks (11) who used capillary pressure measurements.

Thomas (84) dealt specifically with the mechanism of freezing in building stones. He showed the importance of the degree of saturation, freezing temperature, freezing rate, and specimen size. He also presented a few curves on rate of saturation by simple immersion.

Madgwick measured porosity and permeability (to air) of building stones (50, 51). He derived theoretical relationships for capillary movement of water and for its transmission in terms of the experimental variables and various constants (52). These constants were evaluated in a fourth paper (53) for stones, brick, and plaster but were not related to the structure of the materials.

The work by Powers and his associates on the nature of cement paste has a two-fold bearing on the question at hand--both from the point of view of a freezing mechanism and of the fact that pastes are a constituent of concrete. What happens to the concrete and to the aggregate is influenced by what happens to the paste. Powers and Brownyard (60) reported investigations of the physical nature of cement paste and its water component. Briefly stated, the paste was found to consist of small spheres of hydrated cement gel about 100 Angstrom units in diameter and separated by gel pores with a hydraulic radius of about 10 Angstrom units. At a water-cement ratio of around 0.4 the paste is made up entirely of such a gel structure. At larger water-cement ratios another kind of pore space is present. These are called capillary pores. They are usually considerably larger than the gel pores. Powers (58) presented evidence leading to the conclusion that "throughout the practical range of water-cement ratios the capillary

pores are discrete pockets..." and that at higher ratios they gradually become an interconnected network.

Four mechanisms have been postulated to be operative when the water in the capillary pores freezes. (The water in the gel pores does not freeze at any temperatures normally found in the field.) The most obvious point is that if the saturation is greater than about 0.9 and no escape from the body is possible, then the increase in volume of the water on freezing must cause dilation and stress which will rupture the body unless its strength is sufficient to withstand the action. This might be termed the hydrostatic or degree-of-saturation mechanism. Powers (57) originated a second postulate which has become known as the hydraulic pressure hypothesis. In this mechanism escape is possible for the water and the growing ice volume forces it through the porous medium. Such escape can be to an outside surface or to voids in the interior of the body which are not saturated. But this movement must take place through a comparatively impermeable porous solid and, therefore, hydraulic pressure will be generated which, depending on the magnitude of such variables as freezing rate, length of flow path, permeability, and strength, may rupture the body. A principle function of entrained air is to limit the distance such water must traverse and so keep the pressures within safe limits. The third mechanism was presented by Powers and Helmut (62) and involves the surface diffusion of the (unfrozen) gel water to ice in the capillary pores along a free energy gradient created by the temperature decline below 0 C. This process causes swelling pressure in the capillaries and consequent dilation of the specimen. The action is comparatively slow and depends

upon the temperature being maintained for an appreciable time. Entrained air also helps minimize this difficulty by enabling gel water to diffuse to air voids rather than to capillary pores. The fourth mechanism involves osmotic pressure between the gel water and the water, in a capillary, whose salt concentration has been increased by partial freezing of the solvent water. Powers (59) discussed these matters in a recent review.

He also used the results on paste and those of others on aggregates and building stone to postulate mechanisms for the action under freezing of the aggregate component and of the concrete as a whole.

The argument goes as follows. In concrete the aggregate piece is sealed in a paste of low permeability whose pore system is generally smaller than that of the aggregate. When freezing begins, if the paste contains air bubbles of the proper number and spacing it should be immune to distress from the hydrostatic, hydraulic, and to a certain extent, the capillary accretion sources of stress. The osmotic pressure source is thought to be of comparatively minor importance. So entrained air should protect the paste under all ordinary conditions.

Water in the aggregate pieces should start freezing sooner and at a higher temperature than that in paste capillaries because the aggregate water is in larger pores and has a lower salt concentration. (Also, the aggregate piece ought to change temperature more rapidly than the paste because of its higher thermal diffusivity.) If the piece of rock has an overall saturation higher than about 0.9 some water must be expelled into the paste. The paste is comparatively impermeable and this process will result in dilation. But saturations

less than 0.9 do not necessarily render immunity. If, due to inhomogeneous distribution of the water, any part of the aggregate is unable to accommodate the volume increase on freezing, the water must travel to less-saturated places in the rock or to the surrounding paste. In either case excessive pressures can develop.

The pore system of the aggregate is generally larger than that of the paste so, for conditions of partial saturation, the water will migrate to the paste by virtue of the higher capillary pressure and lower vapor pressure in the more finely-porous system. For the aggregate to reach a high degree of saturation by capillarity the paste must first have its capillary system virtually saturated. Water preceding by capillarity in concrete will prefer to stay in the paste, so to speak, rather than enter an aggregate particle.

This, of course, assumes simplifying ideal conditions. In a practical concrete there are pores other than the aggregate pores and the various void spaces of a perfect paste. Bleeding channels, imperfect-consolidation spaces, shrinkage cracks, and settlement spaces under aggregate particles exist. Jones (36) states "This [ideal system] will hardly be true in some actual mortars and concretes because of imperfect packing of aggregate particles combined with lack of sufficient cement to fill all interstices, because of porosity arising by imperfect adhesion between aggregate and paste surfaces, and because of porosity of the aggregate itself."

Some of these spaces might provide entrance channels for capillary or percolating water.

The above points to the importance of the presence or absence of water in the aggregate in situations where the aggregate is one of the harmful components of the concrete. The acquisition of water by capillarity and its movements within the piece are involved in the properties of absorptivity and permeability. Jones (36) stated with respect to aggregates "It is necessary to study chiefly porosity, absorption and permeability; surface texture; and shape," and "Only if full data are available can a proper assessment be made of relative importance of various factors as regards durability." Blanks (11) and Rhoades and Mielenz (66) gave first importance to the pore structure of the aggregate and its relationship to water.

Little work has been done on the pore structure of aggregates or on the movement of water through this structure. Most correlations with durability have been made with the absorption, total porosity, specific gravity, or various absorption ratios. Much of this work was reviewed by Lewis and Dolch (44). The measurements on microporosity by Sweet (81), Blanks (11), Fears (28) and Schaffer (71) have given further insight into the structures of these materials. In their paper on the permeability of pastes (61) Powers et al. gave some data on the permeability of various rocks as a comparison to show the average pore size of the rocks to be larger than that of the paste. Wray and Lichtfeld (96) measured the rate of saturation of gravels and found that the stream-wet condition was difficult to reproduce by simple immersion. Vacuum saturation was considerably more effective than immersion and the material that saturated most readily was the poorest in freezing and thawing. Blaine, Hunt, and Tomes (10) measured the

specific surfaces of various materials by sorption techniques and found comparatively high specific surfaces for materials poor in freezing and thawing and for limestone aggregates with bad service records in concrete.

There has been a large amount of work on the permeability of concrete. Slate's bibliography (78) gives a list of references up to 1947. The subject is of practical importance where concrete is used as a barrier to liquid. Most of the studies have been made to determine the transmission properties of the material under various heads, and have not been concerned with pore structure. One of the most comprehensive of these studies was that of Ruettggers, Vidal, and Wing (70). Their paper and the more recent one by Cook (21) show the apparatus and conditions for the test with water.

Approach Used in This Work

Aggregates with both good and poor field performance were chosen. The quarries were sampled. Small rectangular prisms were shaped from the rock and their dimensions were measured. True density, porosity, and bulk density were determined. Permeability to air was measured in a pressure-decay apparatus at various pressures and the slip correction was determined. The absorptivity coefficient was measured by capillary absorption on a free-water surface. Tortuosity was determined by the electrical analog method. Specific surface was determined by the sorption method using water vapor. These data were then used to calculate characteristics of the pore system on the basis of a simple model.

EXPERIMENTAL WORK

Materials

The materials studied in this work were five limestones or dolomitic limestones which are being, or have been, used as concrete coarse aggregates in Indiana rigid pavement construction. These materials have well-established field-performance records. They have been studied repeatedly.

The geologic origin, appearance, and field performance of the materials are listed in Table 1. The chemical compositions and calculated mineralogical compositions, both for major constituents only, are listed in Table 2.

The quarries from which these samples were obtained were described by Sweet (82). Care was taken to secure material from the appropriate ledge in those cases in which different materials are present in the same quarry. The samples taken were reasonably homogeneous, i.e., inclusions, seams, fractures, and weathered surfaces were avoided. No effort was made to assure representative sampling on a statistical basis. The samples were merely selected at random and with an eye towards similarity to the general mass. For an exploratory study such as the one reported here, this sampling procedure was considered adequate.

A corollary of this sampling technique is the assumption that the material obtained is reasonably representative of that used in the pavements for which the field performance ratings were obtained. Explicitly, it is assumed that if material exactly like these samples

Table 1
General Description of Test Materials (81)

Source No. *	Geologic Origin	Description	Field Performance
1-15	Liston Creek, Silurian	Brown, medium-grained, dolomitic limestone	Good
3-15-H	Jeffersonville, Devonian	White, fine-grained, laminated, dolomitic limestone	Bad
9-13	Kokomo, Silurian	Buff, fine-grained, laminated, dolomitic limestone	Bad
47-25	St. Louis, Mississippian	Brown, medium-grained limestone	Bad
67-25	St. Genevieve, Mississippian	Light gray, medium-grained limestone	Good

* The meaning of these designations is on file at the Joint Highway Research Project.

Table 2

Chemical and Mineralogical Composition of Test Materials (23)*

Source	1-LS	3-LS-H	9-LS	47-2S	67-2S
CaO	30.08	32.1	29.9	42.3	54.64
MgO	20.24	18.07	19.4	3.78	0.34
CO ₂	44.61	46.10	44.53	38.9	41.53
SiO ₂	1.95	0.56	3.00	3.95	1.12
Al ₂ O ₃	2.72	2.90	1.3	4.14	1.80
Calcite	3	12	5	77	97
Dolomite	93	83	89	17	2

* All values are percentages of oven-dry sample.

had been made into pavements, those pavements would have durability histories similar to those of the pavements that were actually made with material from the corresponding sources.

One exception to the above may exist. This is the material labeled 3-1S-H. The samples from this source, although thought to be taken from the proper ledge, exhibited absorptions and saturations that are lower than those of samples taken some years ago. This material therefore may not be truly representative of that used in the pavements. In fact, all tests imply that if pavements had been made from this sample they would not have particularly bad durability ratings. This source was not included in the first plans and was tested when an additional source was thought desirable. Only small pieces were available; hence only small prisms (about 3 cm. long) could be made. This material seems on appearance the least homogeneous of the rocks tested and the samples may be less representative than those from the other sources.

Sample Preparation

Most of the runs were made on small rectangular prisms of rock. It was necessary to have regular geometrical shapes and prisms seemed the simplest to prepare.

Slabs about one inch in thickness were cut from the large pieces using a "Clipper" masonry saw* with a diamond blade. From these slabs rough blanks for the prisms were then cut. The final finishing was done by hand grinding on a glass plate using (generally) 100 mesh

* Clipper Manufacturing Co., Kansas City, Mo.

alundum or corundum powder. The grinding was done wet so that powder would not be carried into the pores by capillary water. Rectangularity of the cross section was checked with a small square. The finished prisms were scrubbed under the faucet with a test-tube brush. They were then rinsed, dried over-night in a 105 C oven and stored over anhydrous magnesium perchlorate in a dessicator. Considerable attention was paid to the selection of homogeneous material, free from defects, for the final prisms.

The individual prisms were given a designation that showed the source and the weight to the next lowest decigram and so permitted identification without marking in any way, e.g., 47-2S-P-116. The 47-2S is the source designation. P means shaped prism (some of the early work was done with small chips). 116 means a weight of 11.6 g. All weights throughout this work were measured on an analytical chainomatic balance and were read to the nearest 0.0001 g. All units are c.g.s. unless stated to be otherwise.

The dimensions of each prism were measured with a Brown and Sharpe precision caliper. Measurements were made to the nearest 0.002 cm. In those instances where the prisms were several centimeters long a width measurement was made about every centimeter along the length and the average was taken as the dimension in question.

The assumption is made that prisms, from the same source, cut from adjacent material, and selected to appear homogeneous are alike in their physical properties. This assumption is necessitated by the use of properties that were measured on one particular prism for calculations involving another and is obviously not strictly true but

is probably true enough for the purposes involved here. A variety of duplicated measurements have led to no serious discrepancies in this respect. The prisms are further assumed to be representative of the samples taken and therefore, on the basis previously discussed, of the source.

One series of experiments, the sorption runs, was done on granular material. The rock was processed by crushing some of the rough prisms and sieving the material to obtain the fraction passing the No. 10 (Tyler) and retained on the No. 30 (U.S. Standard). The sieving was done dry and the material was then washed with distilled water on the No. 30 sieve, dried in an oven, and resieved.

Apparatus and Procedure

Absorption

Absorption is defined as the amount of water (or other liquid) contained in a porous substance under specified conditions and is expressed here as a fraction of the oven-dry weight of the sample. Many workers have investigated this property, trying various liquids and methods for saturating the sample. Usually the attempt has been to obtain higher, preferably complete, saturation. Typical of these experiments is the work of Washburn and Footitt (92). Types of immersion have been simple immersion, evacuation and immersion, boiling in the fluid, and evacuation, immersion, and application of pressure. Various ratios of the absorption under different conditions have been advocated as characteristic of the material (66). Frequently, the assumption is made that liquids completely saturate a porous material

but repeated demonstrations are to the contrary.

In this work the absorptions were measured after 24 hr. immersion and after evacuation for 1 hr. followed by 23 hr. immersion.

The apparatus used for the vacuum absorption runs was a one-liter filtration flask. The prisms were placed therein, a stopper carrying a separatory funnel was placed in the neck, and the funnel was filled with water. An aspirator was attached to the side arm and the flask and its contents were evacuated. Sweet (82) has shown that there is no point in using a vacuum pump for this operation and that an aspirator is sufficient. After one hour of evacuation, the water in the funnel was admitted to cover the samples, atmospheric pressure was restored to the system, and the samples were allowed to remain immersed for 23 hr. At the end of this time they were removed, blotted surface-dry on a damp cloth, and weighed rapidly. The balance was pre-set to approximately the correct weight and was magnetically damped. The weighings, therefore, took only about 20 sec. and evaporation was minimized. For the 24 hr. immersion runs the samples were simply immersed in distilled water for the requisite time and then treated similarly. This technique for surface drying gave reproducible results for successive trials. With these polished surfaces it was possible to see free moisture as a reflecting glisten. The surface dry point was a uniform dullness.

Densities

True density is defined as

$$\rho_T = \frac{W_s}{V_s} \quad (1)$$

where ρ_T = true density

W_s = mass of solids

V_s = volume of solids.

Bulk density is defined as

$$\rho_B = \frac{W_s}{V_B} \quad (2)$$

where ρ_B = bulk density

V_B = bulk volume, i.e., volume of solids and voids.

Methods for determining the density of solids are given in standard texts on experimental methods (65, 93). The methods used on porous solids in general and concrete aggregates in particular were reviewed by Lewis, Dolch, and Woods (45).

The true density of a porous solid is determined by displacement methods using either a liquid or a gas. If a liquid is used the solid should be powdered so that as complete a penetration of the pores as possible is obtained (4). Since it was desired to have a non-destructive test, a gas-displacement method was chosen for this study. The apparatus was essentially that proposed by Washburn and Bunting (90). In any such test the question of which gas to use arises. Frequently helium is chosen because it is so little adsorbed and errors due to this factor are thereby avoided. These rocks, however, have comparatively low specific surfaces and sorption should not be a problem in the density measurements. Air was therefore chosen as the gas because of obvious simplicity.

The apparatus is shown in Fig. 1. All glassware used in apparatus in this work was Pyrex. All stopcocks and ground joints were hand-finished with No. 220 alundum powder.

The use of the apparatus depends on compressing the system by a certain known volume. This volume was that of the bulb in the center of the figure. Scratch marks for calibration were made on the tubes leading to the bulb. The volume between these marks was determined by affixing a stopcock onto the bottom end and drawing mercury into this assembly to the upper scratch mark. The mercury was then run into a tared weighing bottle until the bottom mark was reached. The weight of this mercury then permitted calculation of the corresponding volume.

In operation the mercury level was raised exactly to the bottom mark with the leveling bulb and a screw adjustment (not shown). At this time the stopcock at the left was closed, thus closing the system above the mercury in the left leg. The mercury level was then raised exactly to the upper scratch mark by means of the leveling bulb. This process compressed the air in the system by the known volume. The corresponding pressure was read on the meter-stick-manometer assembly. The barometer was read and room temperature was determined. The barometric reading and the manometer reading were both fully corrected.

These data then permitted calculation of the volume of the system, assuming Boyle's law to hold. The final equation, resulting from simple algebra is

$$V_2 = \frac{P_a \Delta V}{\Delta P} \quad (3)$$

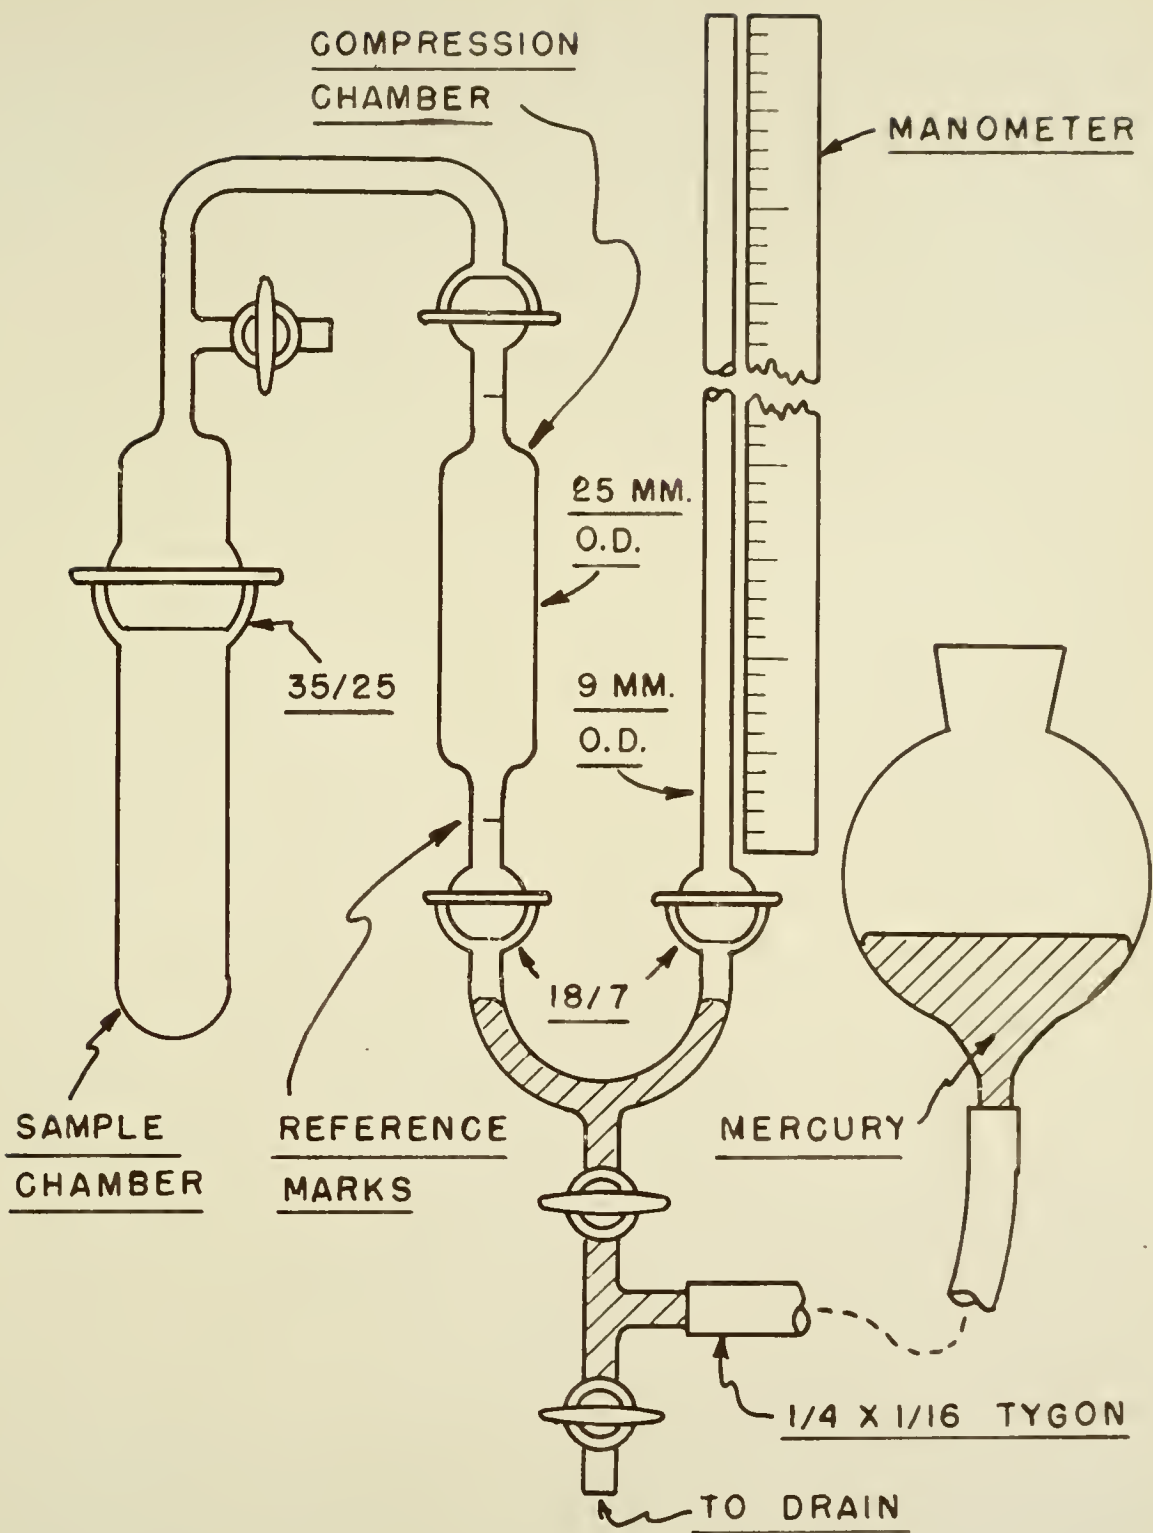


FIG. 1 VOLUMENOMETER

where V_2 = volume of sample chamber to upper scratch mark
of compression bulb

P_a = atmospheric pressure

ΔV = volume of compression bulb

ΔP = pressure change on compression.

Constant temperature during the run was assumed. Since the runs took only a few minutes this assumption seemed justified. If the measurement is done on the empty chamber and repeated with a sample in the chamber the difference in volume gives the volume of the solids of the sample. From this value and the sample weight the true density was calculated. The assumption is that the gas in the pores attains the equilibrium pressure rapidly. This was checked by the fact that no pressure change with time was observed after the compression.

When the densities of known substances (mercury and calcite) were measured there were persistent small errors in the final values which were attributed to gas law deviations and unknown sources. To correct for these errors a run was made on a known volume of mercury and the empty volume of the sample chamber was determined empirically. Subsequent checks on calcite gave good results (2.72 compared with 2.71 (88 p. 143)). This empirically-determined value for the volume of the sample chamber was used in all later runs.

Porosity

Two ratios that express the volume of pore space in a porous material are in common use. One is called the porosity, and the other the voids ratio. Porosity is defined as

$$\epsilon = \frac{V_V}{V_B} \quad (4)$$

and the voids ratio is defined as

$$R_V = \frac{V_V}{V_S} \quad (5).$$

These are related by

$$\epsilon = \frac{R_V}{1 + R_V} \quad (6).$$

Methods of measuring porosity were reviewed by Lewis, Dolch, and Woods (45) and by Fancher, Lewis, and Barnes (26). Two frequently-used methods are by calculation from the true and bulk densities according to

$$\epsilon = 1 - \frac{\rho_B}{\rho_T} \quad (7)$$

or by saturation with a liquid and weighing. The objection to the latter method is the assumption of complete saturation.

Since a direct measurement was preferred, an adaptation of the McLeod gauge porosimeter of Washburn and Bunting (91) was used. The apparatus is shown in Figure 2. The upper section was a 5 ml. microburet graduated in 0.02 ml.

The operation of the apparatus follows. The sample was placed in the container and the apparatus was assembled. The ball and socket joint was carefully greased and clamped with a No. 35 clamp. The mercury level was then raised by means of the levelling bulb. The sample floated and soon contacted the small intrusions in the glass just above the ground joint. As the levelling bulb continued to be raised the

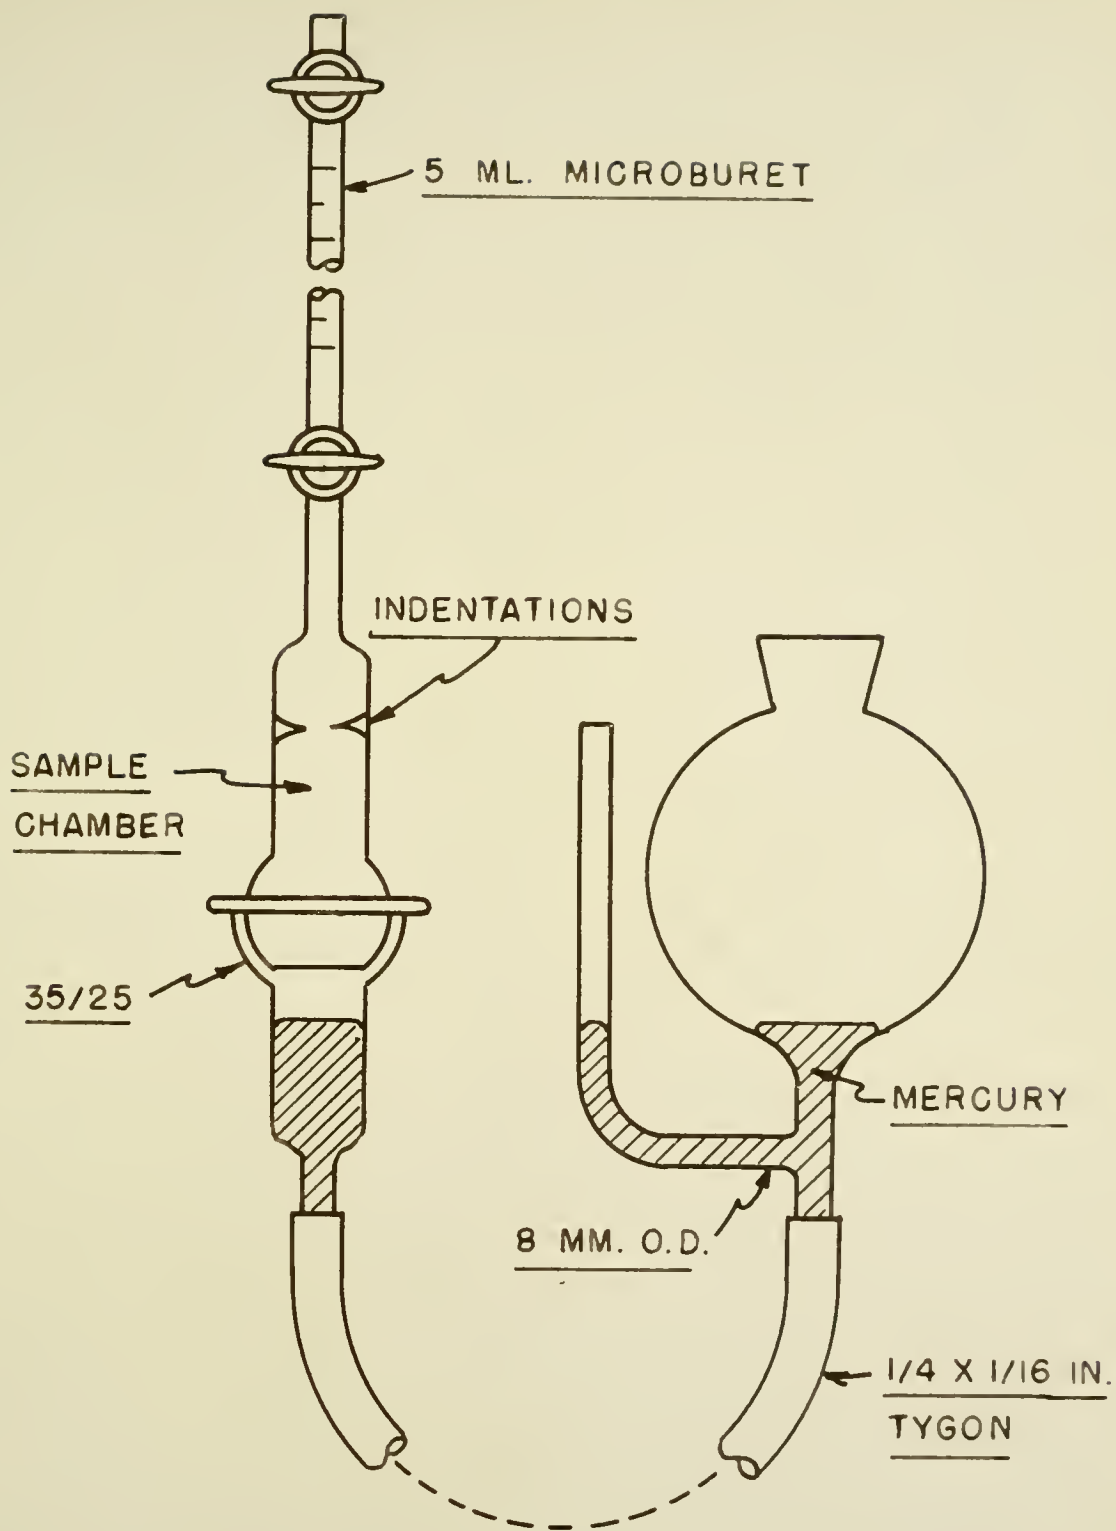


FIG. 2 POROSIMETER

mercury covered the sample and trapped the air in the voids at atmospheric pressure. The level was raised to the top mark of the buret and both stopcocks were closed. The levelling bulb was then lowered. As the pressure on the sample fell the air in the voids expanded and bubbled up through the mercury. This lowering was continued until the sample was entirely exposed. The level was then raised again and the air which had been emitted from the voids was trapped above the mercury at the lower stopcock. This stopcock was then opened and the air was allowed to rise into the buret. Since the rising mercury had trapped a certain amount of air in the voids at the comparatively low "evacuation" pressure, the lower stopcock was then closed and the procedure was repeated. The increments of air from the pores were combined in the buret. Finally the levelling bulb was raised and adjusted to the level in the buret and the volume of air in the pores, i.e., the pore volume, was read directly from the buret. The number of evacuations needed before no significant change was noticed in the cumulative volume was around four.

The question was raised concerning the length of time the sample needed to be exposed to the low pressure on the evacuation. Considerable time might be necessary for the air to come out of impermeable rocks. Accordingly, arrangements were made to have the level remain lowered for about fifteen minutes rather than for the customary one minute or so. When exposed for the longer time no noticeable difference was observed in results on the same sample. It is probable that at the low pressures involved the permeability becomes high due to slip flow.

The above procedure gave the volume of voids. The previously-described procedure gave the volume of solids. Their ratio is the voids ratio. Porosity was calculated by means of equation (6) and the bulk density by means of equation (7). An alternative to this procedure is to calculate ρ_B directly from the weight and the measured dimensions according to equation (2) and ϵ directly from V_v and the measured dimensions according to equation (4). This method of determining bulk volume is, however, influenced by errors in the measurements of the sample dimensions and was used, except as a check, only for 3-LS-H for which only small prisms were available. On these small prisms the error in the determination of the volume of solids in the volumenometer would have been large.

Specific Surface

The specific surface of a porous material is the surface area, including that of the pores, per unit of material. Two expressions of that area have been used in this work. These are the surface area per unit bulk volume, S , and the area per unit weight, S_g . These are related by

$$S = S_g \rho_B \quad (8).$$

A number of methods exist for measuring this property of a porous material. Many were listed by Ergun (25) and were discussed more completely by Brunauer (14).

Two independent methods have been used in this work. These are the fluid flow method, in connection with the major purpose of this study, and the gaseous sorption method. Investigators have found dis-

crepancies between the results of these two methods (13) and have attributed the differences to different areas being contacted by the sorbed vapor and by the flowing fluid. In an effort to investigate this discrepancy for these rocks, the sorption test was performed.

The sorption method involves the calculation, from the data of the low-pressure part of the isotherm, of the amount of gas required to form a sorbed layer one molecule in thickness on the solid. This value, combined with a knowledge of the surface area occupied by one molecule, permits calculation of the total surface area.

The equation most widely used for this calculation is probably that derived by Brunauer, Emmett, and Teller (BET) (14, 15) to represent their multimolecular condensation theory of the sorption process.

The BET equation can be written

$$\frac{1}{w} \left(\frac{x}{1-x} \right) = \frac{1}{V_m C} + \frac{C-1}{V_m C} x \quad (9)$$

where w = weight of sorbate per unit weight of sorbent'

V_m = weight of sorbate in a monolayer per unit weight of sorbent

C = a constant related to heat effects

x = relative pressure of sorbate.

This is the equation of a straight line in $(1/w)(x/1-x)$ and x with an intercept of $1/V_m C$ and a slope of $(C-1)/V_m C$. The value of V_m can therefore be obtained and from this value the total surface area is calculated. Katz (39) and Gleysteen and Kalousek (31) simplified equation (9) by noting that C is frequently large compared to unity and that $1/V_m C$ is then a small number. These authors, therefore, assumed that a plot of the isotherm using only the origin and one

point constituted a close approximation to the curve obtained by taking several data points. Some early runs were made using this simplified procedure. The results of these experiments were checked by repeating the determination using several data points. The results showed the value of C to be so small for these systems (rock and water vapor) that the assumptions of the simplified theory were unwarranted. Accordingly, all runs were made using several data points and the original BET equation.

The apparatus used to obtain the data of the amount of vapor sorbed on the solid as a function of the sorbate pressure was a modification of that used by Gleysteen and Kalousek (31) and is shown in Figure 3. The sample-flask assemblies were connected to the manifold by short lengths of Tygon tubing. The tubing was merely slipped on with the aid of a little moisture and was found to hold well, with no leaks at all. The dibutyl phthalate manometer was used to measure the lower vapor pressures involved and the mercury manometer was used for higher pressures. The apparatus was housed in an air bath made from 3/4 in. plywood. The bath was cooled by tap water running through a coil of copper tubing and was heated by a light bulb which was controlled with a Thermocap* relay activated by a thermometer graduated in 0.2 Centigrade degrees. The temperature maintained in this bath and used for all the sorption runs was 25.0 ± 0.1 C.

* Niagara Electron Laboratories, Andover, N. Y.

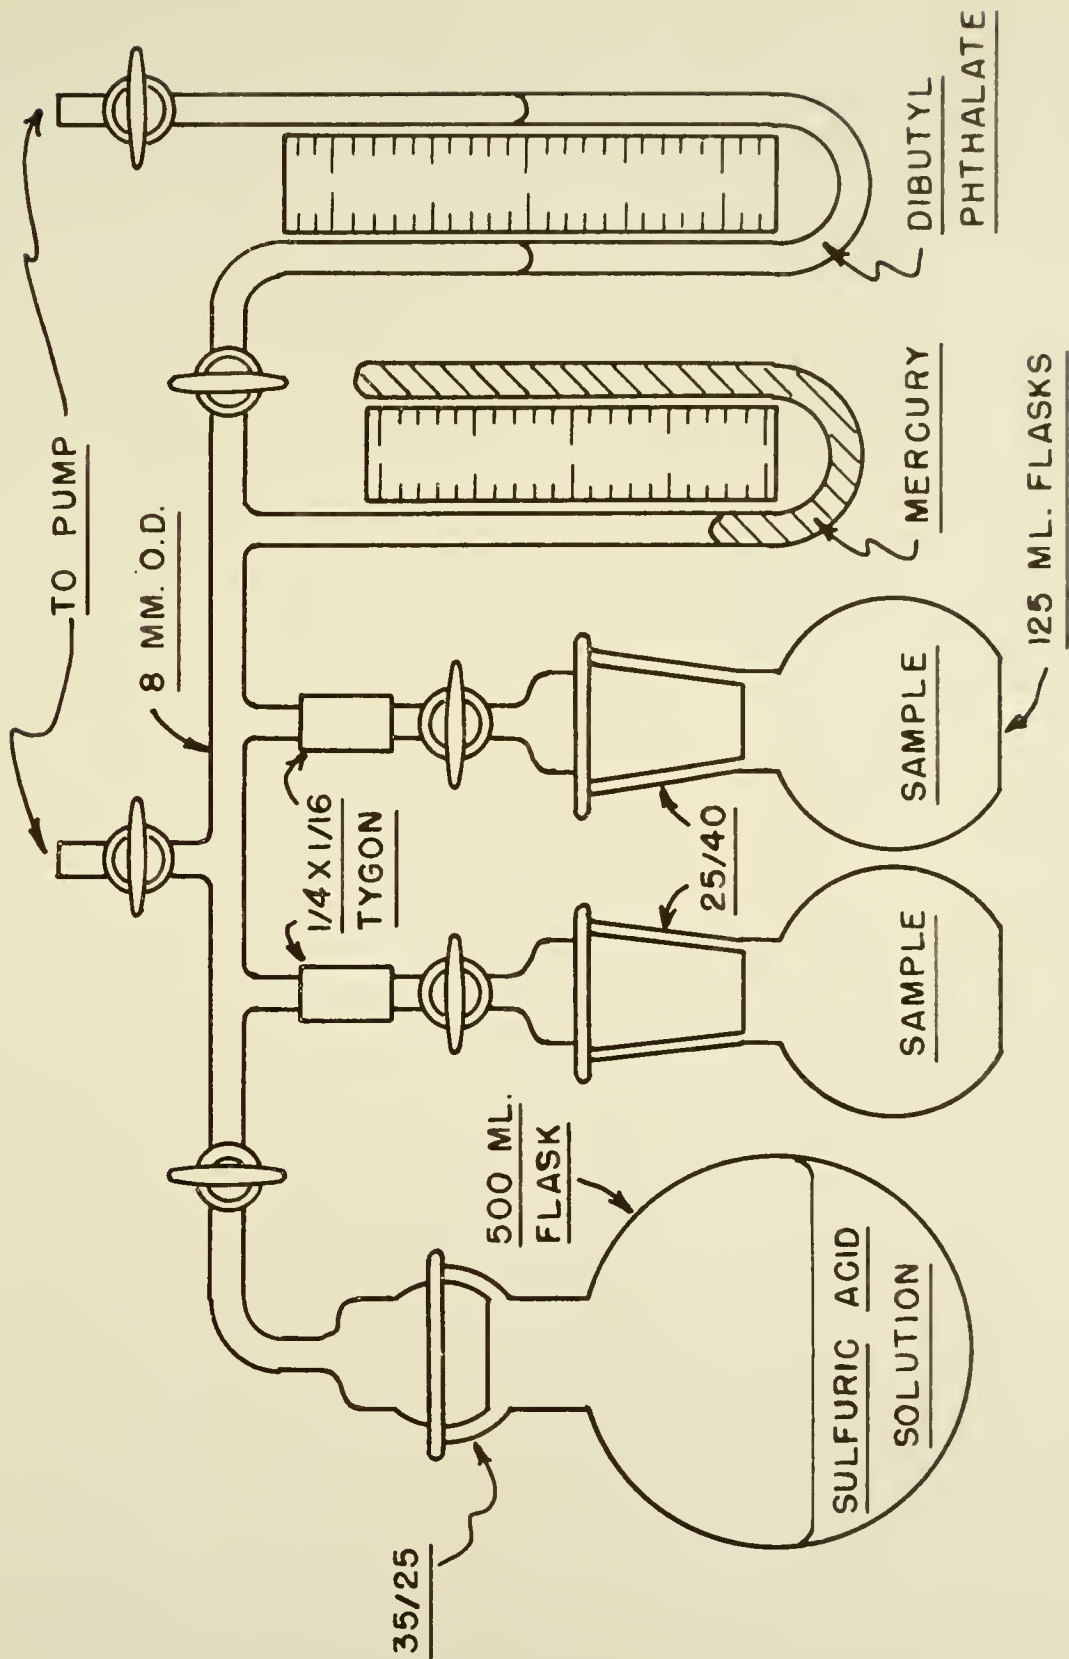


FIG. 3 SORPTION APPARATUS

Sulfuric acid solutions were used in the large flasks as sources of water vapor, which was the sorbate. The solutions were made up to approximately the correct strength, as stated in handbook tables (33 p. 1926), and the actual pressures involved in the determinations were measured with the appropriate manometer.

The procedure for the measurement was as follows. The oven-dry rock, No. 10 (Tyler) to No. 30 (U.S. Std.), was weighed into the 125 ml. flasks by difference. Charges of around 60-70 g. were used. The apparatus was then assembled and, with all stopcocks open except that leading to the larger flask, the system was evacuated on the Megavac. The samples were warmed slightly to assist outgassing and the pumping was continued for 1 hr. This evacuation was needed not only to outgas the rocks but also to remove possible volatile matter from the dibutyl phthalate. The stopcocks to the sample flasks and to the oil manometer were then closed. The Tygon connections were cut off and the sample-flask assemblies were weighed. The apparatus was reassembled and the manifold and the solution flask were pumped out. When the solution began to boil the stopcock leading from the manifold to the pump was closed and the water vapor was admitted to the samples. From time to time the amount of sorbed vapor was determined by removing the flasks and weighing. Sorption was continued until constant weight was obtained. About one hour was sufficient time. At this point the vapor pressure of the water in the evacuated system was measured with the dibutyl phthalate manometer. The data for other points on the curve were obtained by repeating the above procedures using other con-

centrations of sulfuric acid solution. The weight-of-sorbate values obtained by this method were corrected for the weight of unsorted water vapor in the sample-flask assemblies.

Tortuosity

The tortuosity of a pore system is defined as the square of the ratio of the average actual length of flow path to the exterior length of the flow path, i.e.,

$$k_t \text{ [or } \tau] = \left(\frac{L_t}{L} \right)^2 \quad (10)$$

where k_t [or τ] = tortuosity

L_t = average tortuous length of flow path

L = macro length of flow path.

The tortuosity of the pore system of a consolidated porous medium is presently measured in one of two general ways. One method involves the determination of the curve of capillary pressure as a function of saturation, and the other is an electrical analog method. The electrical analog method, as discussed in papers by Wyllie and Rose (98) and Wyllie and Spangler (99), was used in this work because of its simplicity and proved applicability.

The method is based on the premise that electric current flowing through a conducting liquid in the pores of a porous body will follow the same path as will a fluid flowing through these pores in a fluid-flow experiment. The ratio of the resistance of the porous medium containing the conducting liquid to the resistance of an amount of the liquid alone equal in size to the bulk dimensions of the sample is called the formation factor, F . F can be related to the structural

properties of the material. A difference of opinion exists as to the form this relation should take. Wyllie and Rose (98) and Wyllie and Spangler (99) considered that the effective cross-sectional area of current flow is ϵA where A is the macro cross section. Accordingly

$$k_t = F^2 \epsilon^2 \quad (11).$$

Cornell and Katz (22), on the other hand, assumed an effective cross-sectional area of $\epsilon A/k_t^{1/2}$. In this case

$$\tau = F \epsilon \quad (12).$$

Wyllie and Gregory (97), who investigated this discrepancy for unconsolidated aggregates, stated "Arguments in favor of both approaches may be adduced." The details of these arguments, however, seem to be lacking in the aforementioned papers. It may be mentioned that empirical relations between the variables involved have been advanced (27, 94) which are different from those of either of the above two equations. The matter is referred to again in the Discussion section.

Assuming the correctness of equation (11), if the solid is incompletely saturated with the conducting fluid the formation factor, F_e , will be larger than F and given by

$$F_e = \frac{k_{te}^{1/2}}{\epsilon S_w} \quad (13)$$

where k_{te} = tortuosity of conducting phase

S_w = fractional saturation

by analogy with equation (11). The ratio of these formation factors is called the resistivity index I ,

$$I = \frac{F_e}{F} \quad (14).$$

The resistivity index has been experimentally determined to be a simple function of the degree of saturation,

$$I = S_w^{-n} \quad (15).$$

The exponent n seems to be independent of the value of saturation for values high enough so that the conducting phase is reasonably continuous (99), and has a magnitude which varies for different rock textures but is approximately 2. This is the value used here. By the use of these equations the tortuosity of a porous medium at any saturation can be calculated if the formation factor at a known saturation is measured and the porosity is known.

The determination of the formation factor was as follows. The ends of the prisms were painted (two coats) with a colloidal silver, conducting paint used in the electronic industry for printed circuits. When the paint was dry the prisms were vacuum saturated with an exactly five percent sodium chloride solution (i.e., 50 g. per liter). The apparatus used was that described under the section on the determination of absorption. The samples were allowed to stay immersed for only about an hour, however, rather than for the 23 hr. used in the regular vacuum saturation procedure. Each prism was then removed from the solution, was blotted dry on a cloth moist with the solution, and its resistance was measured rapidly. After the resistance was measured the sample was weighed rapidly on a preset balance. The instrument used for the resistance measurements was a Bouyoucos portable bridge* operating at 2000 cycles with an auditory indication of the balance point.

* Wood and Metal Products Co., Bloomfield Hills, Michigan.

The resistance of an equal-sized volume of the pure solution was calculated from the measured dimensions and the specific conductance at the appropriate temperature which was obtained from tables (33 p. 1967).

The ratio of these resistances was the formation factor at the measured saturation. Using an exponent of 2 in equation (15) the resistivity index was calculated and the formation factor for complete saturation was obtained using equation (14). The tortuosity was then calculated from equations (11) or (12). A reversal of these calculations gives the tortuosity applicable at any other saturation.

The errors most likely to be influential in affecting this determination (assuming the equality of flow path with current path) are involved in the choice of the value for the exponent n . An analysis of the error involved in this choice is given in Appendix A.

Permeability

Permeability refers to the ability of a solid to permit passage of a fluid.

By far the greatest amount of work on the methods of measurement of permeability, its theoretical interpretation, and its use has been done in the two fields of soil mechanics and petroleum technology. For rocks, the publications in the latter field are especially valuable and were the starting point for the present work on the question.

The quantitative relationship between the factors involved in permeation under viscous flow conditions is known as Darcy's law, and was found empirically to be

$$u_a = K_i i \quad (16)$$

where u_a = approach (or discharge) velocity
 K_i = permeability or transmission coefficient
 i = hydraulic gradient.

The approach velocity is the ratio of the volume rate of flow to the total approach area and the hydraulic gradient is the loss in total head per unit macro length of flow path. K_i in this expression depends on the properties of both the solid and the fluid. An alternate and more frequently-used expression defines a quantity called the specific permeability, but herein called simply the permeability, which is independent of the properties of the fluid. This alternate form of Darcy's law is

$$u_a = \frac{K \nabla P}{\eta} \quad (17)$$

where K = specific permeability
 ∇P = hydraulic gradient in pressure units
 η = viscosity of fluid.

Darcy's law is discussed in detail in Muskat's book (55).

Various units are possible for the permeability and transmission coefficient. K_i in equation (16) has the dimensions of a velocity and the units in most common use are cm./sec. and ft./sec. K in equation (17) has, if c.g.s. units are used, the dimensions of an area, and the square centimeter is the unit of specific permeability. It is, however, such a large unit that a smaller one is frequently used. This is the millidarcy (md.) which is one thousandth of a darcy which is, in turn, the unit for K if the pressure gradient is expressed in

atmospheres/cm., the viscosity in centipoises, and the velocity in cm./sec. Most soil permeability work has been done in terms of cm./sec., most on concrete in ft./sec., and most on petroleum-bearing rocks in terms of md. If one assumes water at 25 C to be the permeating fluid (viscosity = 0.894 cp.) then the various units have the following relationship:

$$1 \text{ cm}^2 = (1.013)(10^{11}) \text{ md.} = (1.097)(10^5) \text{ cm./sec.} = (3.60)(10^3) \text{ ft./sec.}$$

The determination of permeability involves a knowledge of the various quantities in equation (17), i.e., the flow rate, the dimensions of the sample, the viscosity of the fluid, and the pressure differential causing the flow. The measurement of permeability is discussed in Muskat's book (55) and apparatus that has been used on concrete is shown in papers by Ruetters, Vidal, and Wing (70) and by Cook (21), that used on cement paste by Powers et al. (61), and on soil by Lambe (42).

With cement paste, concrete, and soil it is necessary to use water as the permeant because for the use of gases the solid must be dry and such a drying operation would so seriously change the properties of the materials that the permeability value obtained would be meaningless. For material not harmed by drying, however, the use of gases is to be preferred for permeability measurements on dense samples because of the shorter time and the lower pressure gradients involved in the test. In such experiments the volume flow rate of the gas for use in equation (17) must be that at the mean pressure across the sample (55 p. 77).

On samples of comparatively high permeability (e.g., open sandstones) the results from gas and liquid measurements are in close agreement. With samples of lower permeability, however, the values obtained with gases are generally higher than those obtained using liquids (26). The reason for this discrepancy was first given by Klinkenberg (40). The permeability coefficient in equation (17) is constant only if one assumes viscous flow of the gas. When the mean free path of the gas becomes appreciable with respect to the size of the channels through which it is flowing the viscous-flow assumption of zero gas velocity at the tube wall no longer holds and the gas begins to "slip" past the tube walls. This has been known for some time and is discussed in texts on the kinetic theory of gases (48). The slip contributes an additional component to the velocity beyond that of viscous flow and this component becomes appreciable at low pressures and/or when the channels are extremely small. The result of this slip component is a higher value for permeability which is no longer pressure independent. Based on the laws of slip flow, Klinkenberg derived the equation

$$K = K_1 \left(1 + \frac{b}{P_m} \right) \quad (18)$$

where K_1 = a constant

K = measured permeability

P_m = mean pressure across sample

b = slip factor.

This is the equation of a straight line of K as a function of $\frac{1}{P_m}$ whose slope is $K_1 b$ and whose intercept is K_1 . Klinkenberg showed that b is

related to the properties of the solid and the fluid and that, theoretically, K_1 should be the permeability value that would be obtained if slip were not present, i.e., the permeability to liquids. His experiments confirmed this hypothesis and it will be assumed henceforth here that K_1 is the pressure-independent, liquid permeability of the solid. The liquid permeability reported for the rocks in this study was determined by measuring the apparent permeability, K , as a function of the reciprocal mean pressure and determining the intercept of the plot.

In making gas permeability measurements the flow rate can be measured by collecting the outlet gas, by using a capillary-tube or orifice flowmeter, or, for lower flow rates, some device such as the soap-bubble flowmeter described by Bonillas (12), all of which leave something to be desired for dense samples.

The apparatus used in making the permeability measurements in this work is shown in Figure 4. It is an adaptation of that of Arnell (3). Rigden (69) and Kamack (38) also used the same principle for their experiments. The principle of the apparatus is that the flow rate is measured by following the decay of a pressure differential imposed across the sample. A knowledge of this decay rate, the sample dimensions, and certain apparatus constants permits the calculation of the permeability.

The operation of the apparatus was as follows. The oven-dry prism of rock was first coated on its sides (speaking in terms of the flow experiment) with a hard asphalt cement (penetration of about 10). The asphalt was melted and then buttered on the sides of the prism with a small spatula. A thin, even, coat was applied and smoothed with

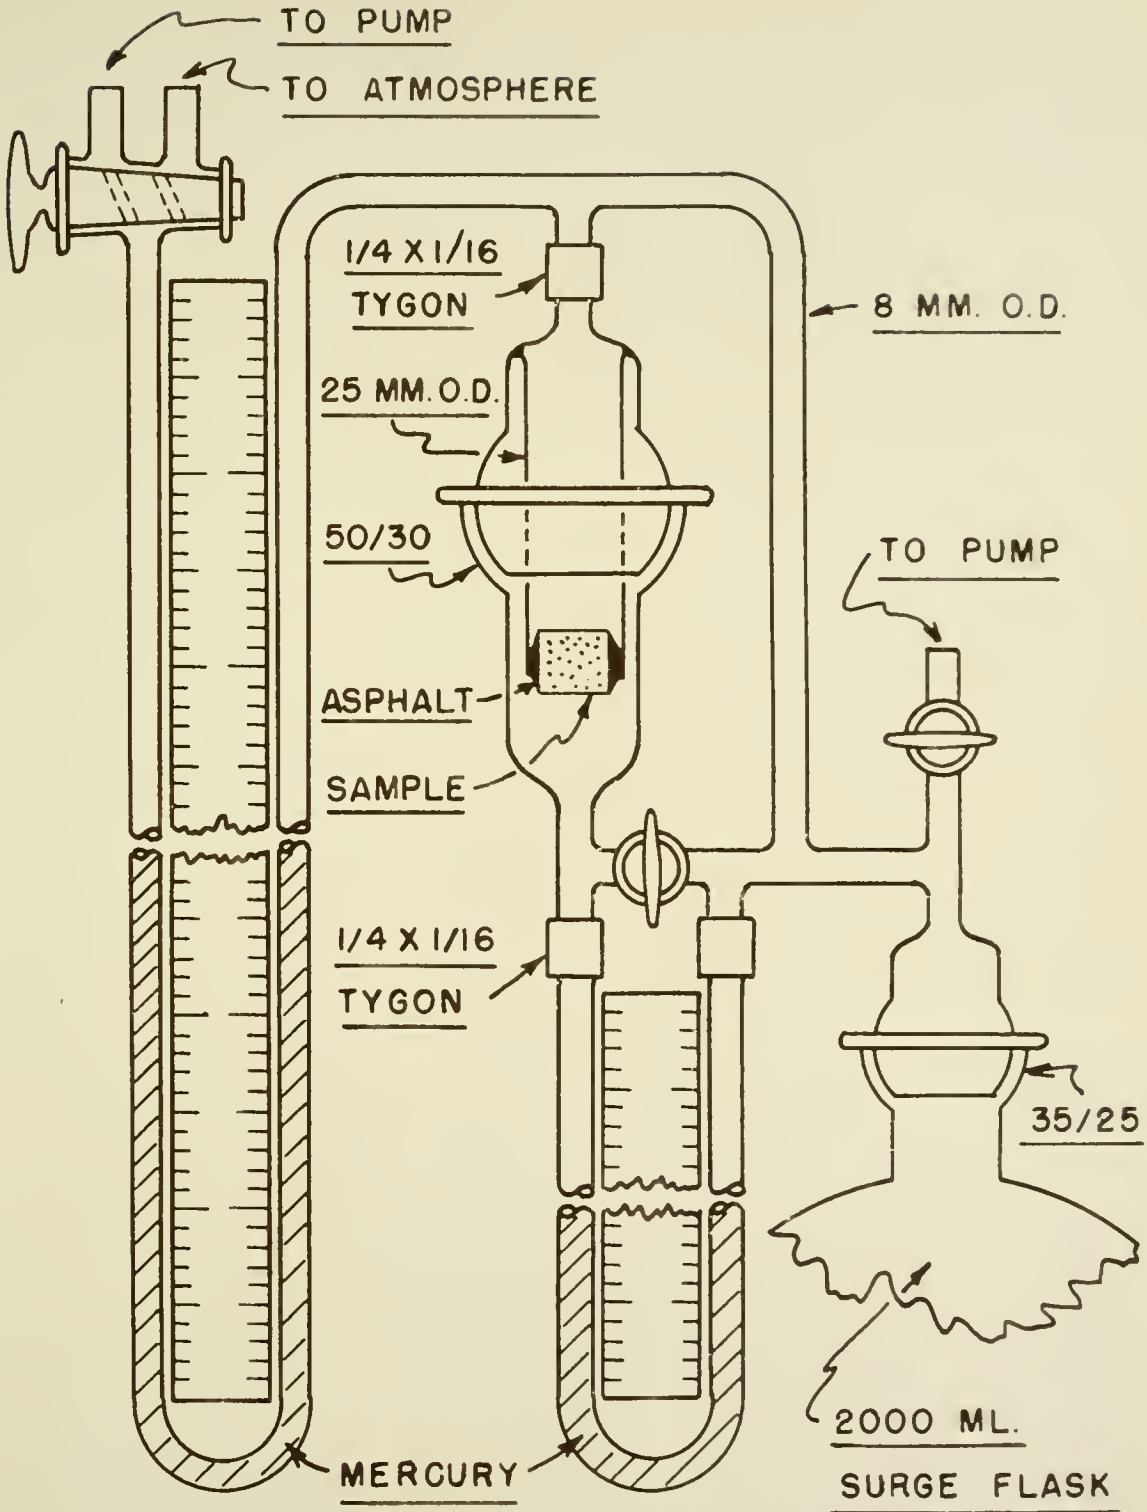


FIG. 4 PERMEAMETER

the hot spatula. Final smoothing was done by brushing with a burner flame. The sample was then placed in position in the holder and sealed in place with a ring of the same asphalt cement. The ring was made as thick as possible to achieve considerable strength. Final smoothing of the outside (the part protruding from the tube) of the ring was done by brushing with a flame. The asphalt was allowed to harden for several hours. The sample holder was then placed in position, the 50/30 ball and socket joint was clamped, and the unit was connected by means of the Tygon joint. The left leg of the large manometer was evacuated to give a direct reading of the pressure. With the bypass stopcock open, the stopcock at the surge tank was opened to pump and the system was pumped down to the high pressure desired. This pressure was, obviously, atmospheric or anything less. At this point the bypass stopcock was closed and the pumping was continued until the desired pressure differential was attained as shown by the differential manometer across the sample. The stopcock at the surge flask was then closed and the pressure differential was allowed to decay as the air flowed through the sample. The differential manometer was read with a magnifier and the rate of decay was followed with the aid of an electric stopwatch reading in hundredths of a minute. The time for the run varied approximately from one minute to half an hour depending on the permeability. Measurement of the pressure on the low-pressure side of the sample was made by reading the long manometer, and measurement of the temperature of the system with an adjacent thermometer completed the data needed. The decay curve is not, of course, a straight line but it was possible to take readings over an interval of

head loss of about one centimeter of Hg and thus to avoid drawing the curve for each run. The curve, in other words, was considered to be straight between points whose difference in magnitude was of the given order.

The equation used to calculate the permeability was

$$K = \frac{\eta L (1.013)(10^{11})}{\Delta P A P_m (1.333)(10^4)(60)} \left(\frac{dh}{dt} \right) \left(V_h + \frac{A_t h}{2} + \frac{A_t P_h}{2} \right) \quad (19)$$

where K = permeability, md.

η = viscosity of gas, poise

L = specimen length, cm.

A = specimen approach area, cm.²

A_t = area of differential manometer tube, cm.²

V_h = volume of the high pressure side of the system down to the equilibrium position in the differential manometer, cm.³

and, with respect to a certain small (in terms of head change) interval in the decay process and to the midpoint of this interval,

P_h = high pressure on sample, cm. Hg

P_m = mean pressure on sample, cm. Hg

h = height difference on differential manometer, cm.

ΔP = pressure differential across sample, cm. Hg

dh/dt = time rate of change of h , cm./min.

ΔP and h are numerically equal if mercury is used and the rate of change of head can be taken, as mentioned above, to be the head loss divided by the time interval, i.e., $dh/dt = \Delta h/\Delta t$.

The derivation of equation (19) and an explanation of the determination of the values of V_h and A_t are given in Appendix B.

Absorptivity

A special type of permeation is that in which the driving pressure is the capillary pressure at the meniscus as the liquid proceeds through the solid. Capillary pressure exists by virtue of the curvature of the meniscus and the presence of surface free energy and is inversely proportional to the size of the channel in question.

Much work has been done on the question of capillary absorption with reference to soils because of the connection of these matters with agriculture and with soil mechanics. Comparatively little has been done on the capillary dynamics of stone in general and aggregates in particular.

The coefficient of absorptivity, or the absorptivity for short, is defined here after Powers and Brownyard (60 p. 865) by

$$\frac{V^2}{A^2} = K_a t \quad (20)$$

where V = volume of liquid absorbed

A = macro or approach area

t = time elapsed from start of absorption

K_a = absorptivity coefficient.

The absorptivity of the samples was measured in the following way. The prism was taped on the sides with "Scotch" brand* plastic electrical tape. This operation was done carefully. The tape was placed so that the sides were completely covered and the covering was pressed firmly into place to form the best-possible seal. Special care was

* Minnesota Mining and Manufacturing Co., Saint Paul, Minn.

taken to seal the places where the tape overlapped. Several layers of filter paper were then placed on the desk top and wetted thoroughly with distilled water. A water supply was arranged through a cloth wick into an adjacent beaker filled with water. The surface of the paper under these circumstances was quite wet but not sloppy and, it is assumed, was essentially a free-water surface. The taped prism was then placed firmly on this wet surface and an electric stopwatch was started simultaneously. At certain arbitrary time intervals the stopwatch was interrupted and the prism was removed from the filter paper, blotted surface-dry on a damp cloth, and weighed. The balance was pre-set and magnetically damped so the weighing took only around twenty seconds. The sample was then replaced on the wet filter paper and the stopwatch started again. The first weighing was usually made two minutes after the start of the run and subsequent ones were made every few minutes up to around twenty minutes. After this the intervals became progressively longer as the rate of absorption decreased. The test was continued until capillary absorption had sensibly stopped. Some small weight gain continued, even at this point, to be recorded but it is assumed that this gain was due to diffusion and not to capillarity.

The data were plotted on log-log paper, V/A as ordinate against t as abscissa. From this plot the absorptivity and capillary saturation were determined.

This technique for the determination of absorptivity is extremely simple. There are, however, possible objections. First of these is the surface-drying method. This is discussed in the section on absorp-

tion. Secondly, there is the possibility of moisture movement during the weighing operation. Moisture will be drawn to the more finely-porous part of a body both by capillarity because of the larger capillary pressure in the smaller pores and by vapor diffusion due to the lower vapor pressure in the smaller pores. The latter process is slow at the small vapor pressure differentials (a few mm. of Hg) involved. The capillary redistribution is also thought to be slow under the small capillary pressure differentials involved when no free water source is present. At any rate, no discontinuities were observed in the curves at the data points. The third possible source of error involves temperature control. Both the surface tension and the viscosity of the liquid enter into the calculations. These properties are functions of temperature and even though the ratio of the two is used in the calculations the coefficients are not compensating and the ratio is also a function of temperature. Thermostating seemed to promise small help because the free-water surface was cooled by evaporation. The resultant compromise was that the measurements were made when the room temperature was such as to make the water temperature on the free surface about 25 C and this value was assumed for all runs.

Calculations

All calculations in this work were performed on a slide rule with the exception of those for which it was necessary to have more than three significant figures. The latter were performed on a calculator.

Data

Density, Porosity, Absorption, and Saturation

In Table 3 are presented the results of the calculations for true and bulk density, porosity, absorption, and the corresponding saturations. The porosity was calculated from the voids ratio by means of equation (6). The voids ratio was calculated using equation (5), the value of V_v obtained with the McLeod gauge porosimeter, and the value of V_s obtained with the volumenometer. The bulk densities were calculated by means of equation (7). In other words, the values for bulk and true density, porosity, and voids ratio all were derived basically from values for solid and void volumes. The one exception to the above are the values for the source 3-1S-H. As mentioned previously, only small prisms of this rock were available so the bulk volume was calculated from the dimensions, the void volume was obtained from the porosimeter experiment, and the porosity was calculated from equation (4) and the true density from equation (7).

Tortuosity

In Table 4 are given the measured and calculated formation factors and tortuosities. F_e is the formation factor obtained from the resistance data and S_{we} is the corresponding saturation. F is the formation factor calculated therefrom. The tortuosities marked k_t and $k_{t\alpha}$ are the calculated tortuosities, according to Wyllie and Rose (i.e., $F^2\epsilon^2$), at complete saturation and at the saturation obtained in the absorptivity experiments respectively. Those marked τ and τ_α are the

Table 3
Densities, Porosity, Absorption, and Saturation

Source No.	$\rho_T, \text{g./cm.}^3$	$\rho_B, \text{g./cm.}^3$	ϵ	Absorption		S_w	
				Immersed	Evacuated	Immersed	Evacuated
1-LS	2.82	2.75	0.0256	0.0046	0.0085	0.494	0.911
3-LS-H	2.89	2.60	0.1003	0.0174	0.0278	0.451	0.708
9-LS	2.84	2.16	0.242	0.0813	0.1048	0.723	0.940
47-2S	2.77	2.47	0.1064	0.0259	0.0384	0.603	0.893
67-2S	2.70	2.64	0.0232	0.0052	0.0061	0.591	0.587

corresponding Cornell and Katz tortuosities (i.e., F_e). The equations used in calculating the formation factors and tortuosities at other than the measured saturations are equations (11) through (15) with the exponent n taken to equal 2.

Table 4
Tortuosities and Associated Factors

Source No.	F_e	S_{we}	F	k_t	$k_{t\alpha}$	τ	τ_α
1-LS	7070.	0.329	765.	384.	2245.	19.6	47.3
3-LS-H-p	158.	0.708	79.1	63.1	174.	7.95	13.2
9-LS	15.8	0.910	13.1	10.0	18.7	3.16	4.32
9-LS-p	16.6	0.945	14.8	11.3	28.4	3.36	5.33
47-2S	107.	0.841	76.0	65.5	176.	8.09	13.3
67-2S	1704.	0.427	317.	54.1	176.	7.35	13.3

The notation "p" after a source number indicates that the direction of the flow (of electricity or fluid) was parallel to the laminations of the specimen. The laminated rocks were 3-LS-H and 9-LS. The former was tested only in the parallel direction and the latter was tested both parallel and perpendicular to the laminations in order to indicate the effects of this variable.

The values for the source 1-LS should be regarded as the most uncertain in the group. Difficulty was experienced in measuring the resistance values of this sample. The other rocks had resistances which checked well in repeated measurements. But the resistance values

on the 1-1S sample had a large scatter (extremes of 80-120% of the average). This performance was puzzling in view of the close checks with the other rocks and the only explanation that can be offered is that, with this very high tortuosity, any slight reorientation of the conducting fluid from run to run would have a large effect on the measured resistance.

Specific Surface

Figure 5 shows the data obtained in the sorption tests in the form of conventional isotherms. These data were then plotted linearly, according to equation (9). The equation was solved graphically for V_m and C and the V_m values were converted to specific surface by means of

$$S_g = \frac{a_1 V_m N}{M} \quad (21)$$

where a_1 = area of surface occupied by one molecule of sorbate

N = Avogadro's number

M = molecular weight of sorbate.

The value used for a_1 was $(10.6)(10^{-16})$ cm.² (60 p. 489). The values so obtained for the specific surfaces of the various rocks are given in Table 5. The values for the individual runs are given together with their average. Although the information does not apply directly to this study, it may be noted that the values for C ranged about from four to eight.

Permeability

The permeability was calculated from the decay flow data by means of equation (19). The values obtained for the rocks are plotted against

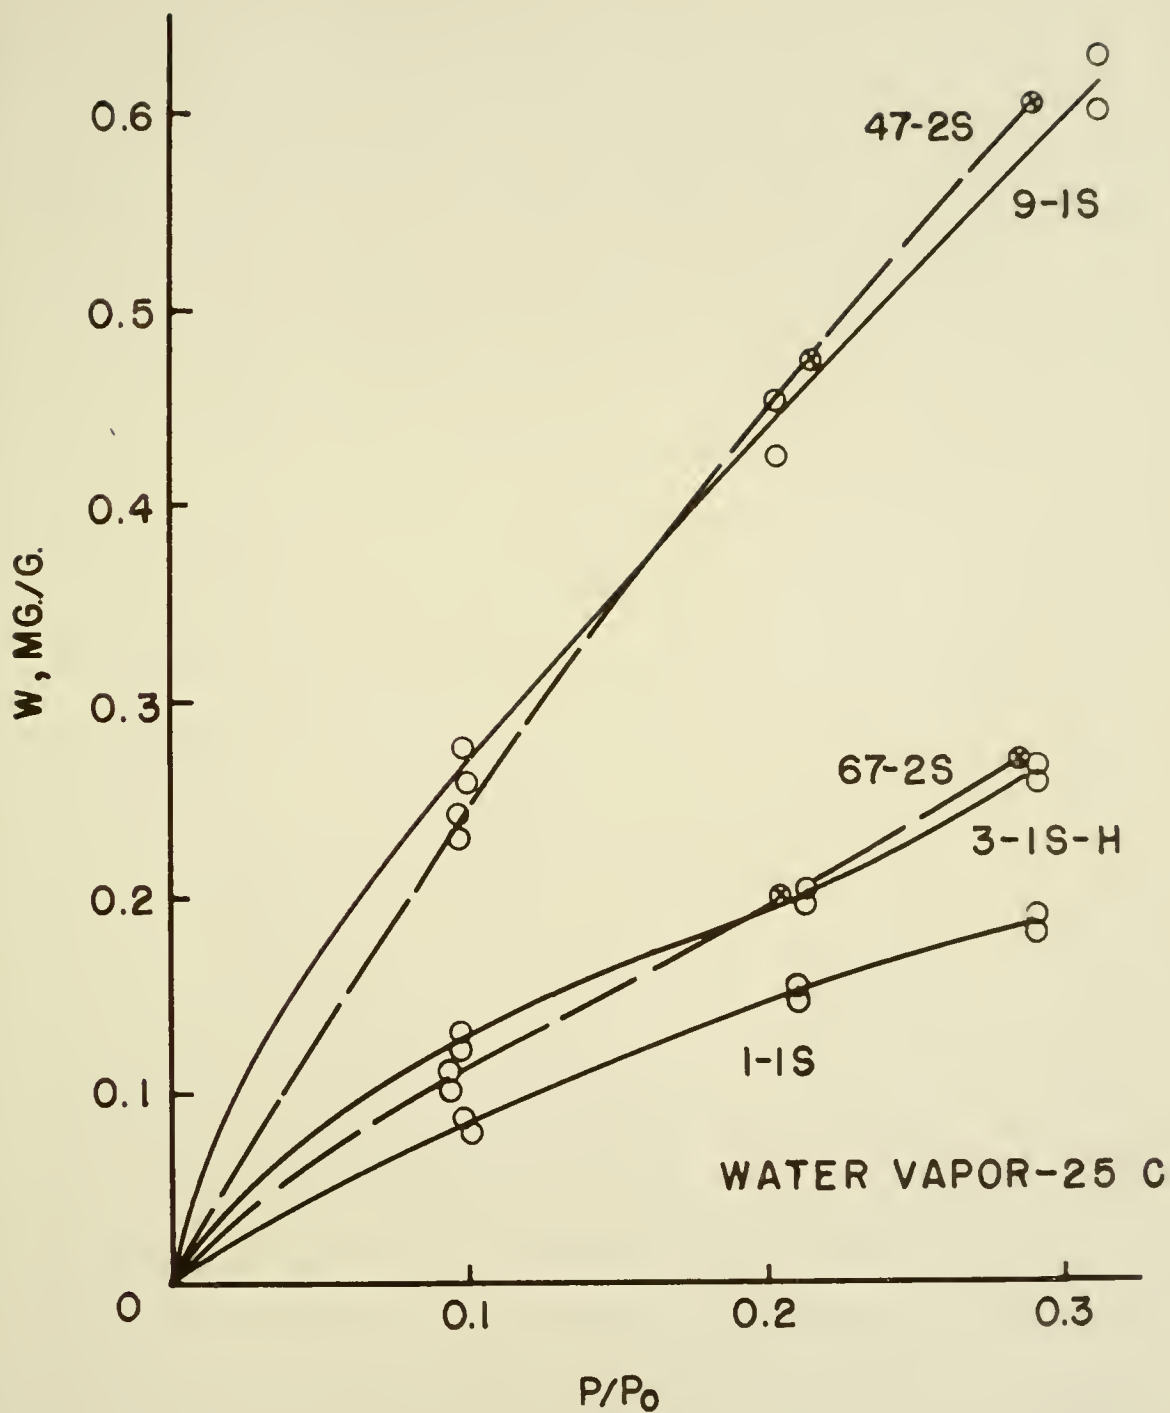


FIG. 5

SORPTION ISOTHERMS

the reciprocal mean pressures in Figures 6 - 12.

Table 5
Specific Surfaces

Source No.	$S_g, m.^2/g.$	Avg.
1-1S	0.68, 0.66	0.67
3-1S-H	0.88, 0.86	0.87
9-1S	2.02, 2.06	2.04
47-2S	2.44, 2.65	2.54
67-2S	1.06, 1.11	1.09

Straight lines were drawn through the data. This was done by least squares in the case of 1-1S but for all others the lines were drawn by eye. The latter procedure was used because the data, with the exception noted, fit a straight line very closely.

The slopes and intercepts were then obtained from the curves and put in the form of a Klinkenberg equation (equation 18). The intercept permeability to liquid, K_1 , and the b factor of the Klinkenberg equation are tabulated in Table 6. Also given is a value labelled pK_1 which is the logarithm of the reciprocal of the permeability expressed in $cm.^2$. This notation is introduced as a convenient way to indicate permeability when wide variations are encountered and it will be used later when comparisons are made.

It will be noted that Figures 6 and 12 show one data point each which is farther from the curve than is accountable to experimental

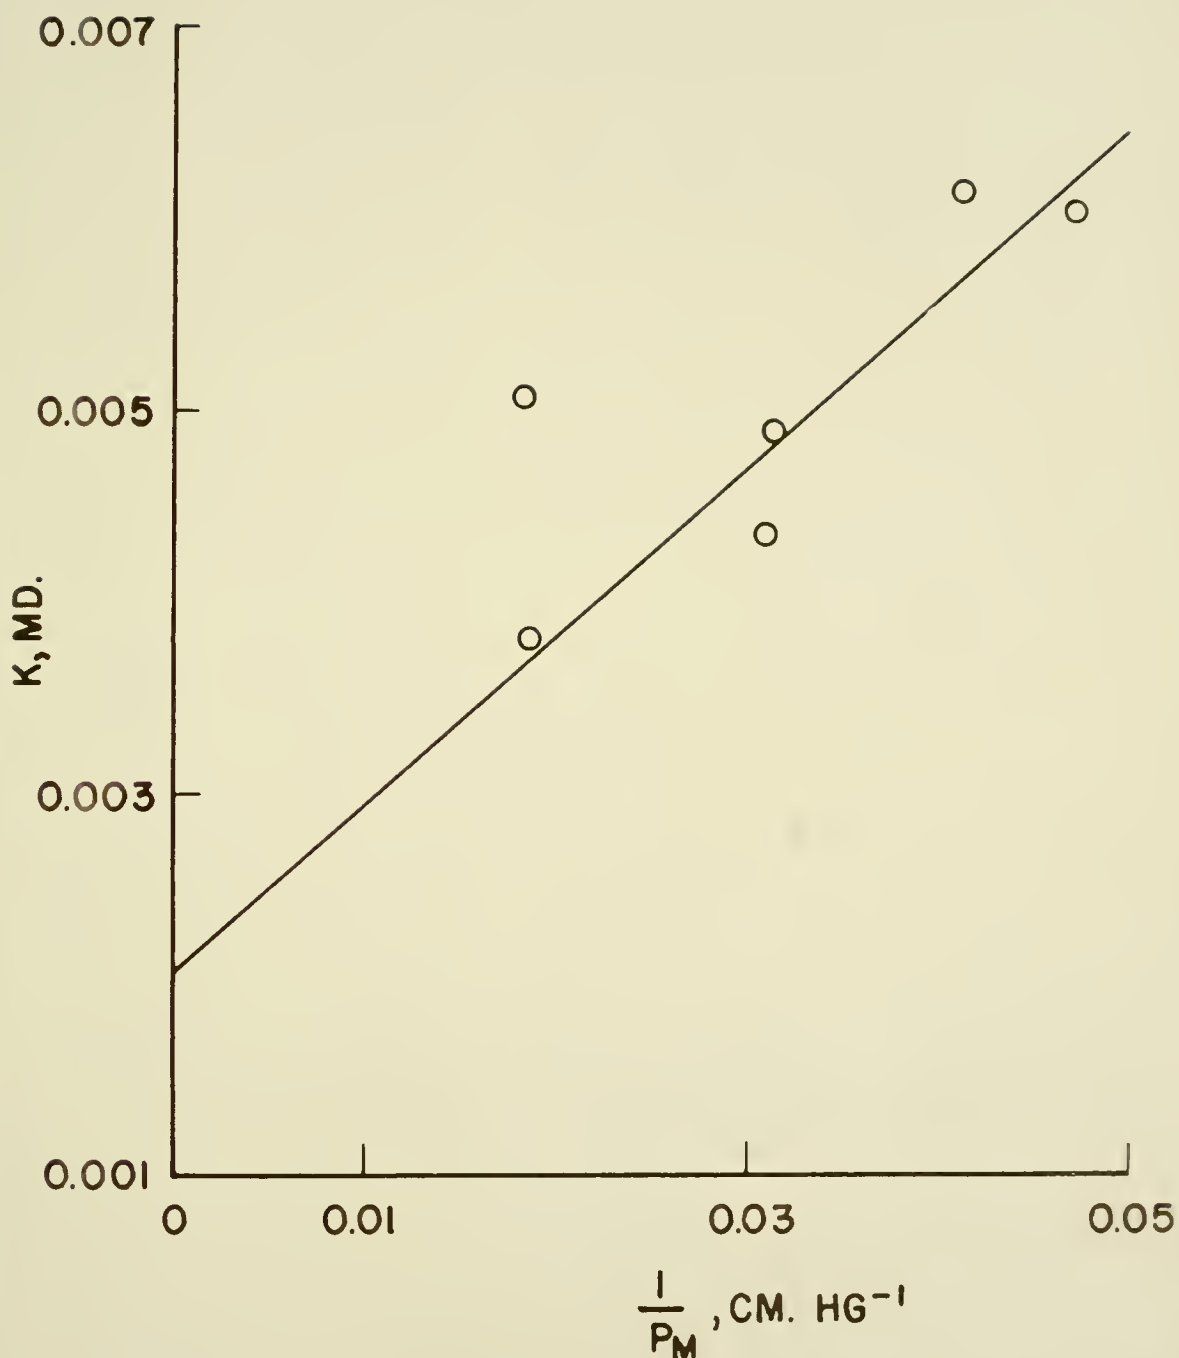


FIG. 6 PERMEABILITY OF I-IS-P-37

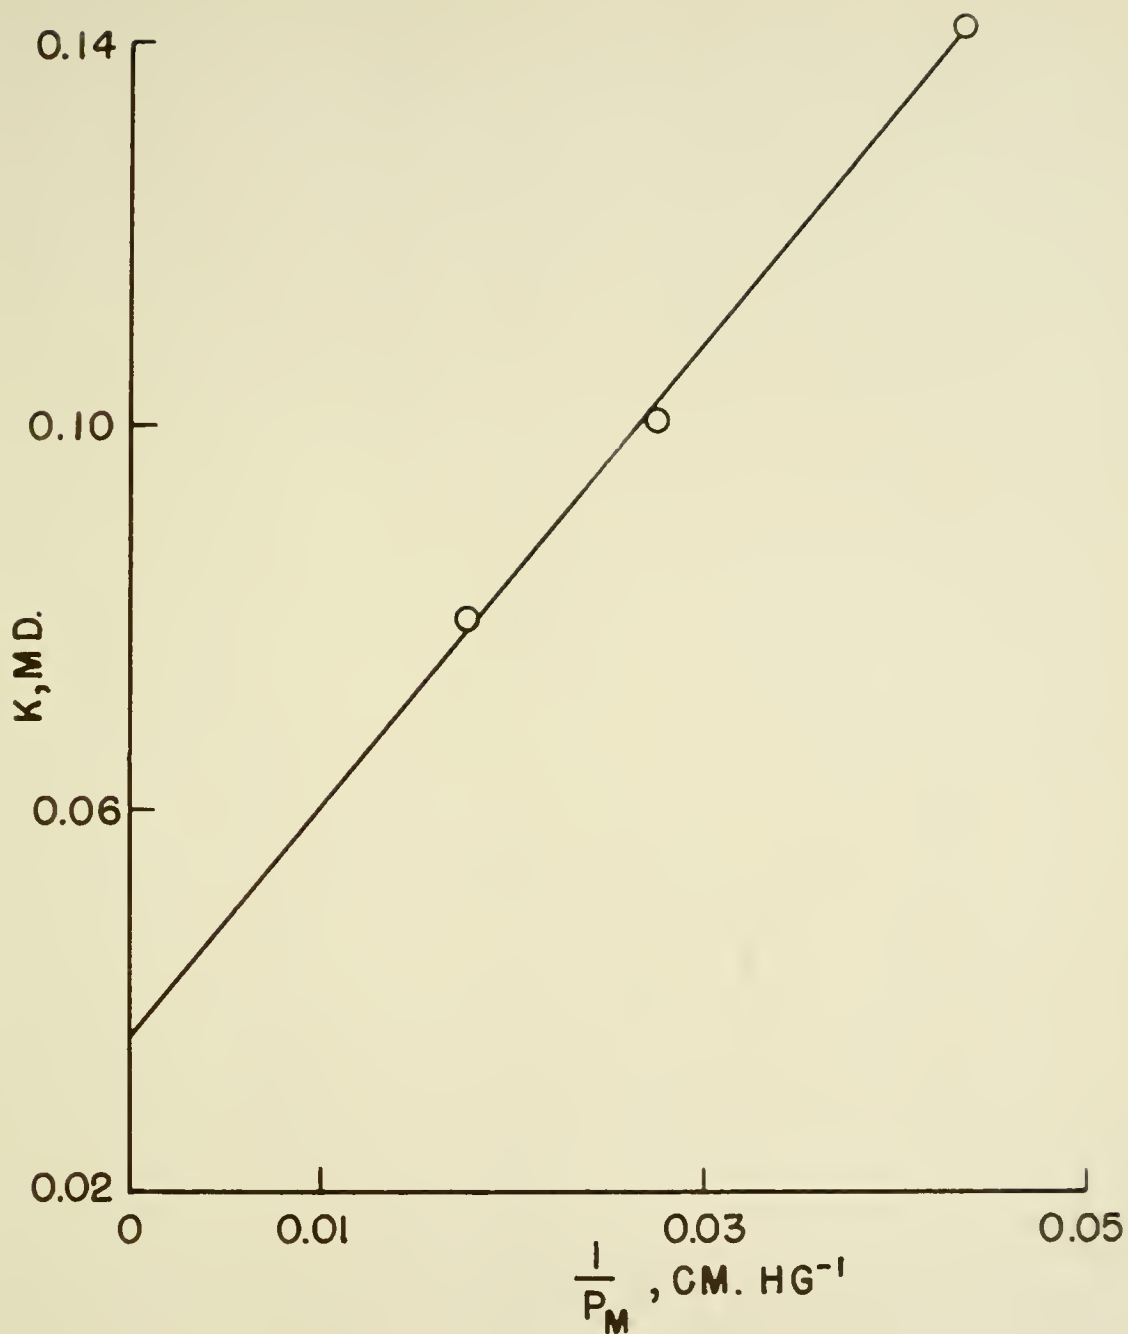


FIG. 7 PERMEABILITY OF 3-IS-H-P-80_p

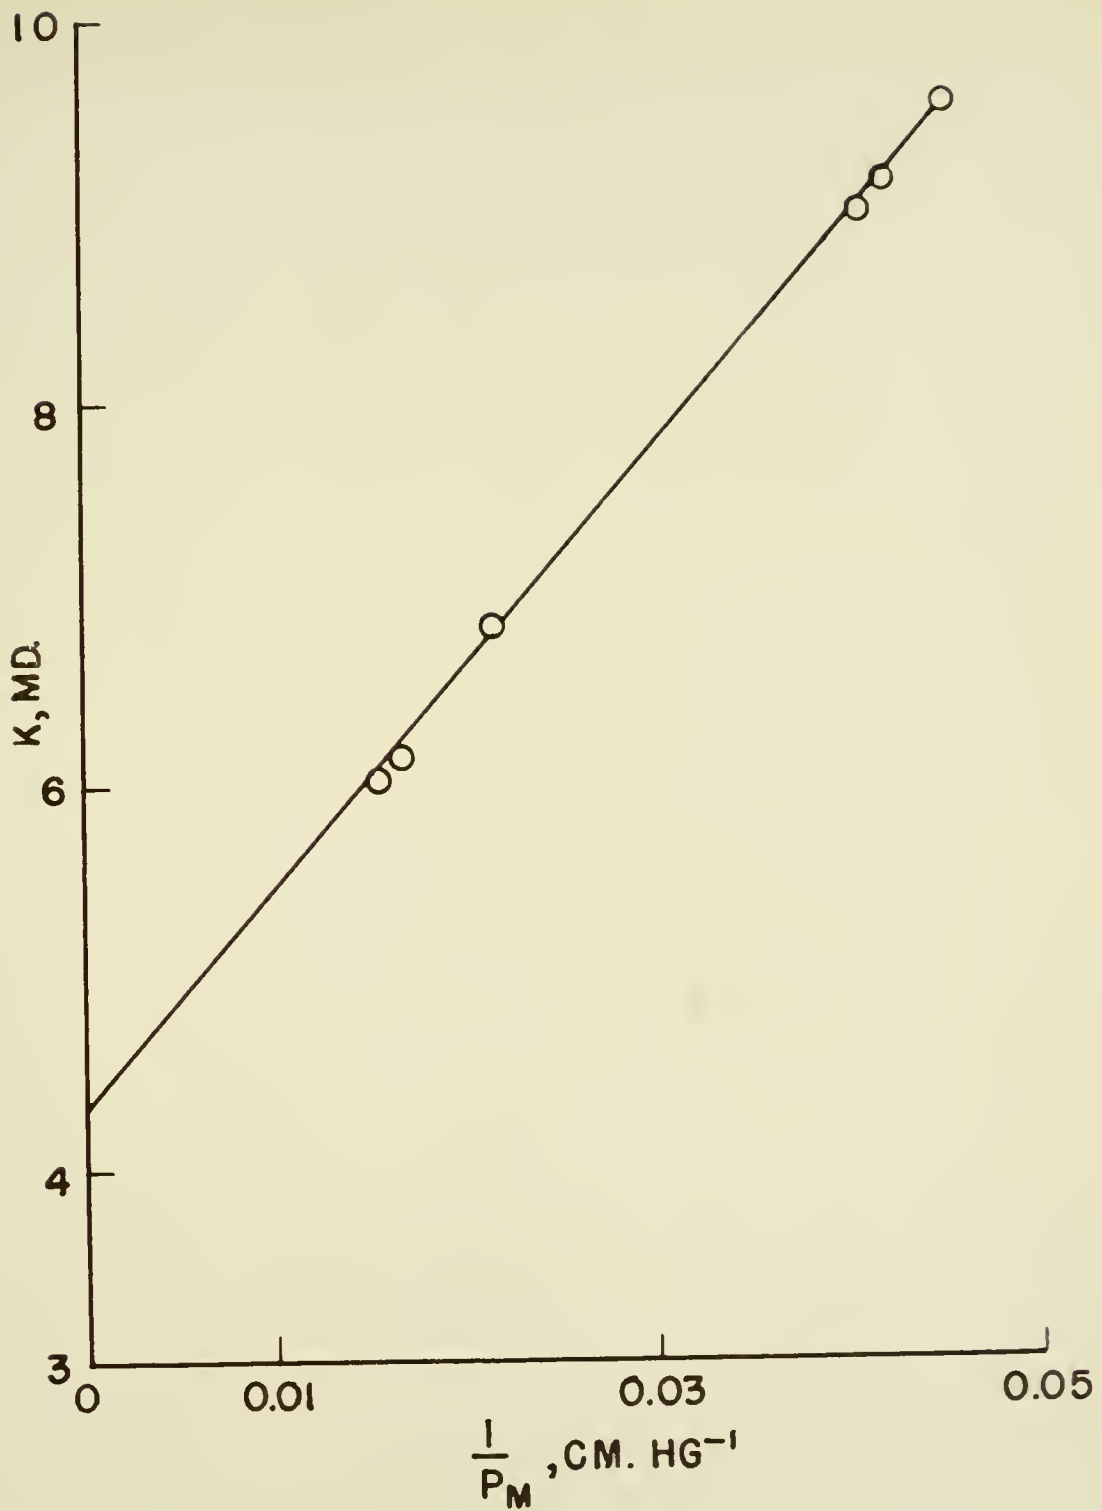


FIG. 8 PERMABILITY OF 9-IS-P-78

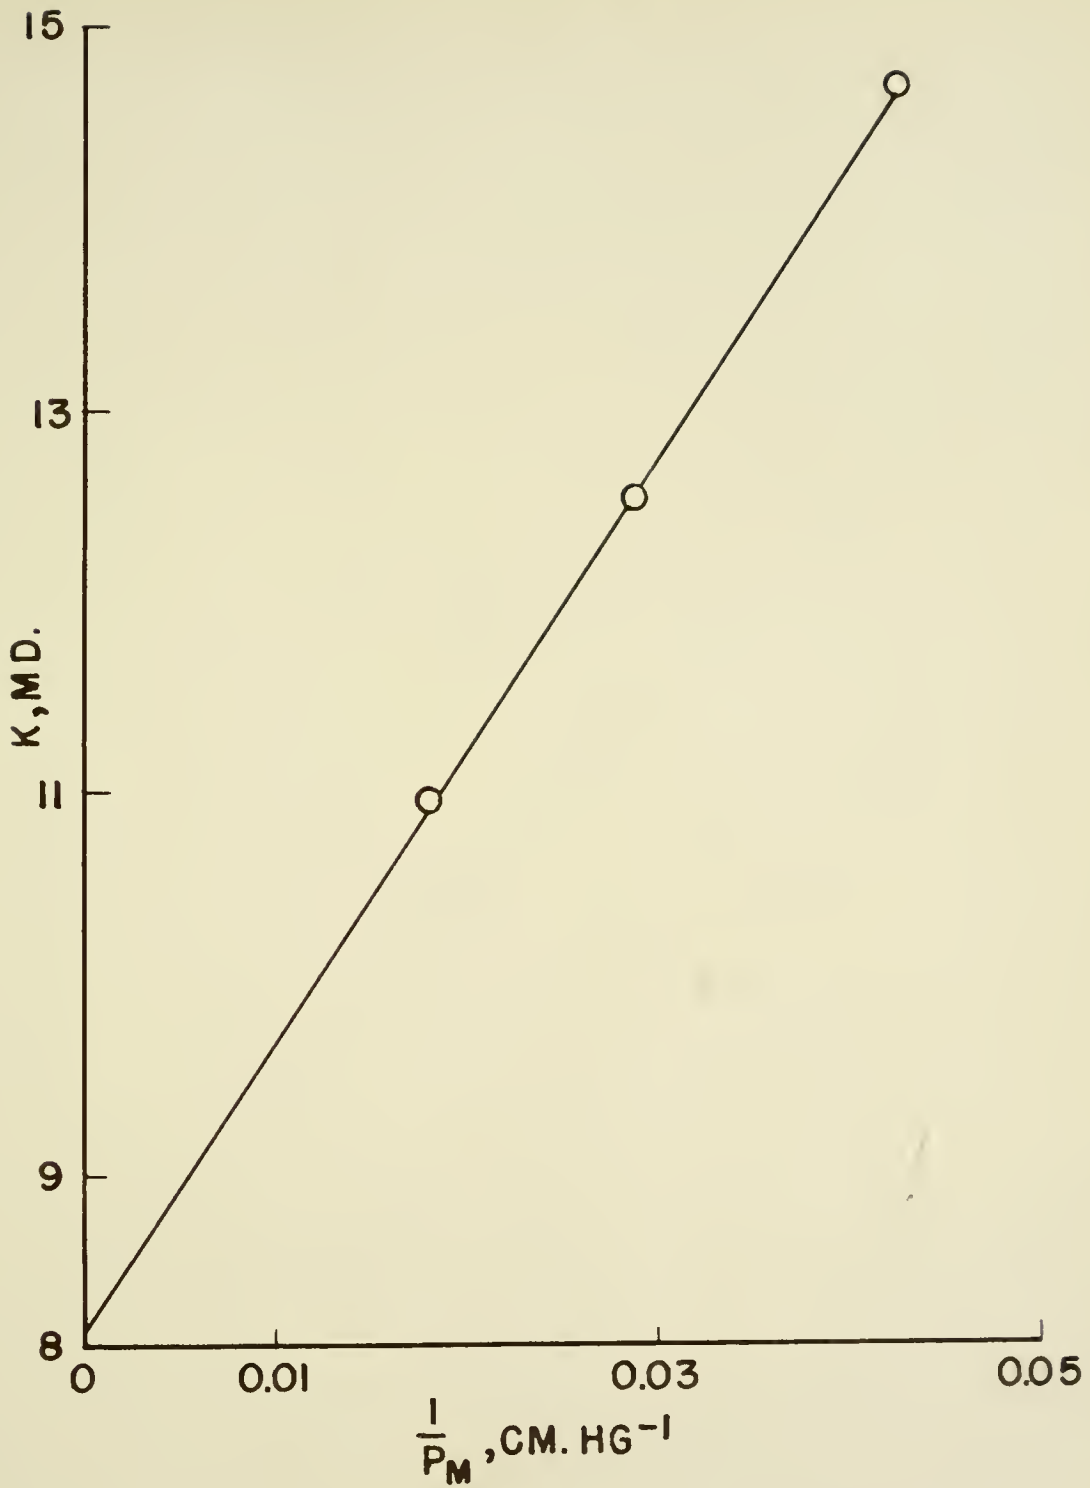


FIG. 9 PERMEABILITY OF 9-IS-P-54_p

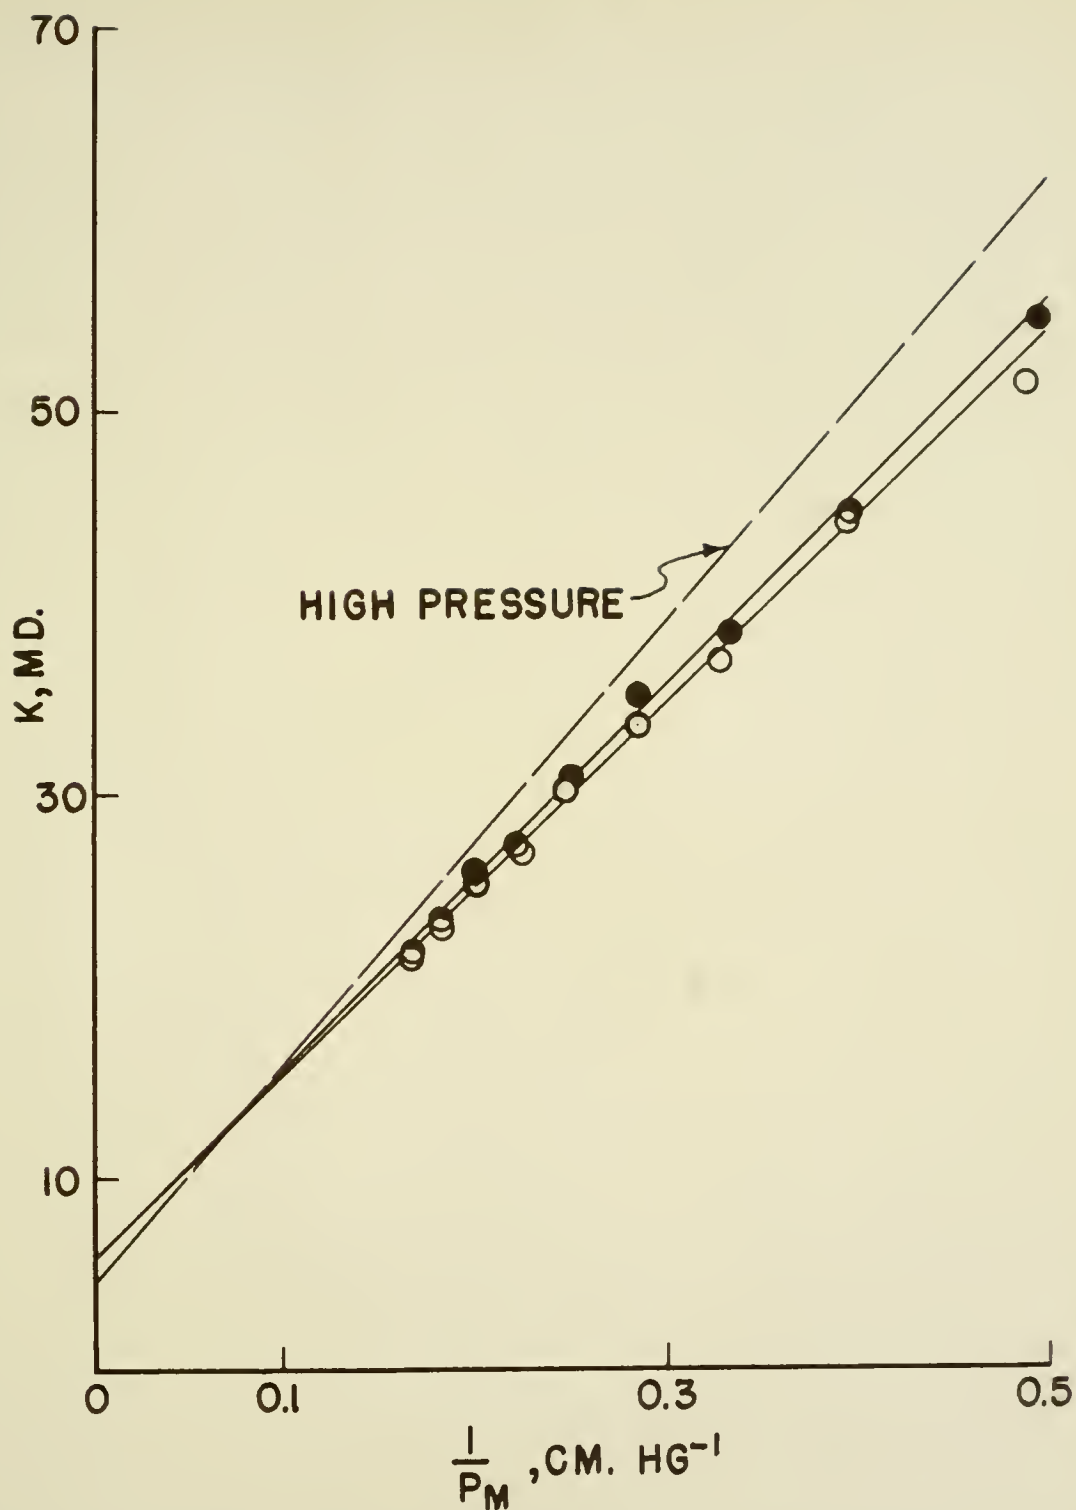


FIG. 10 PERMEABILITY OF 9-IS-P-78
LOW PRESSURE RUNS

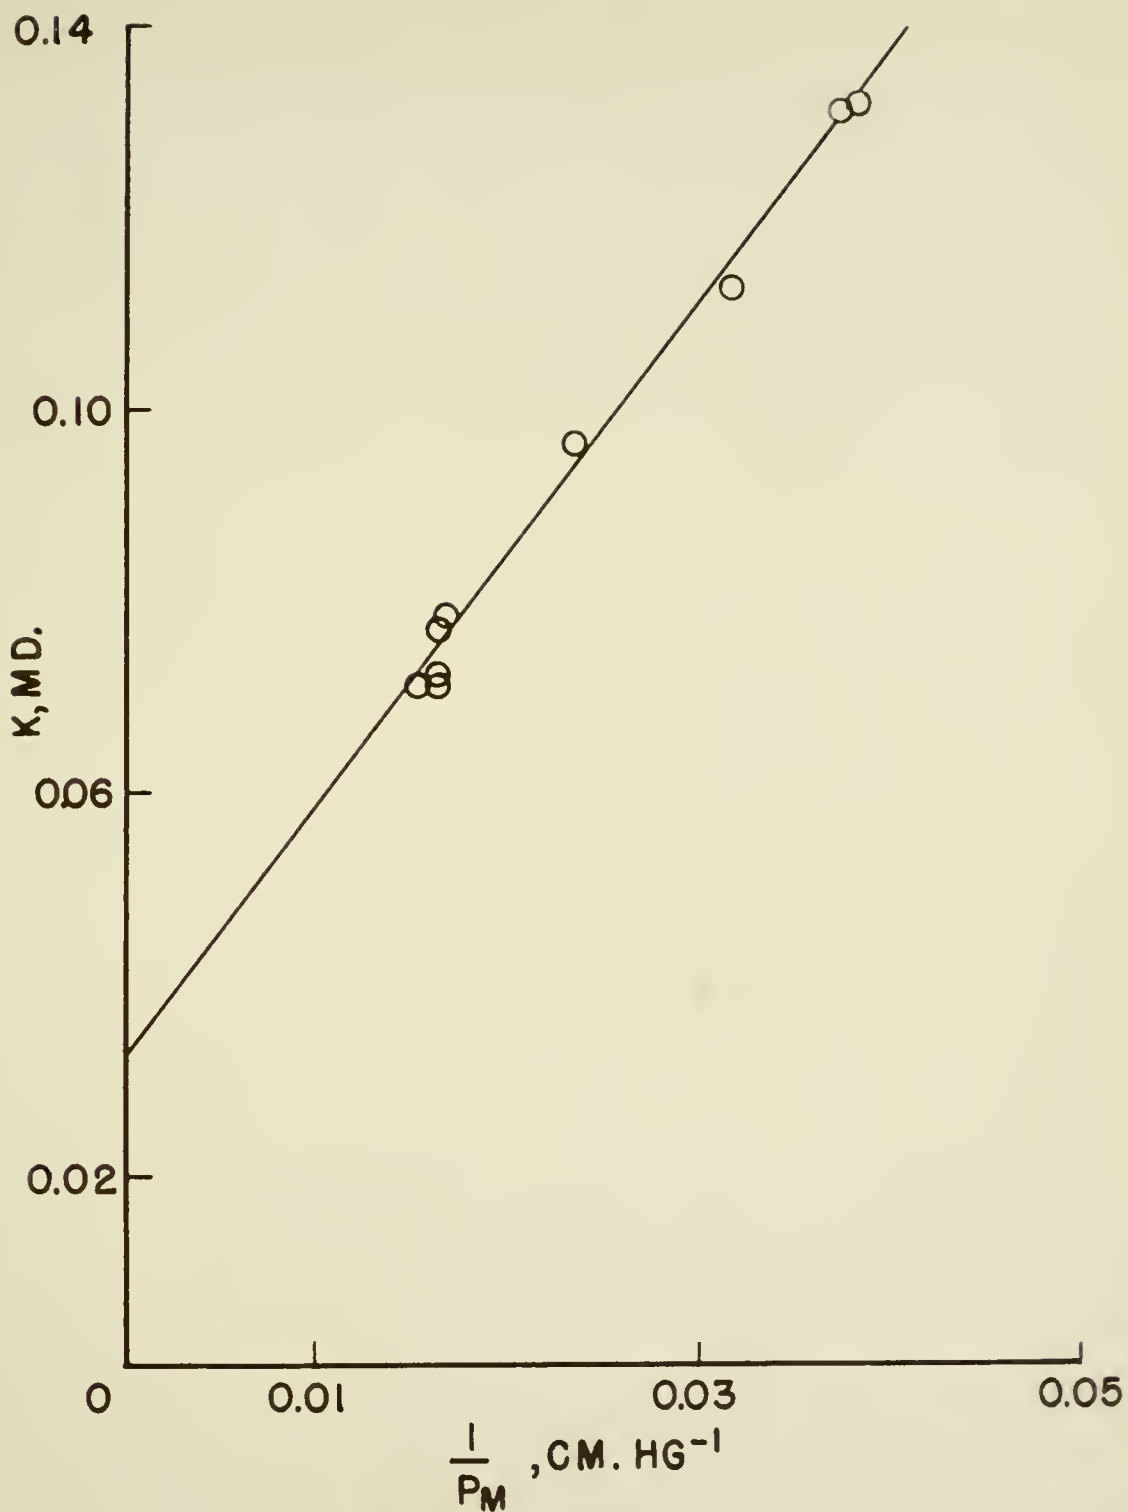


FIG. II PERMEABILITY OF 47-2S-P-98

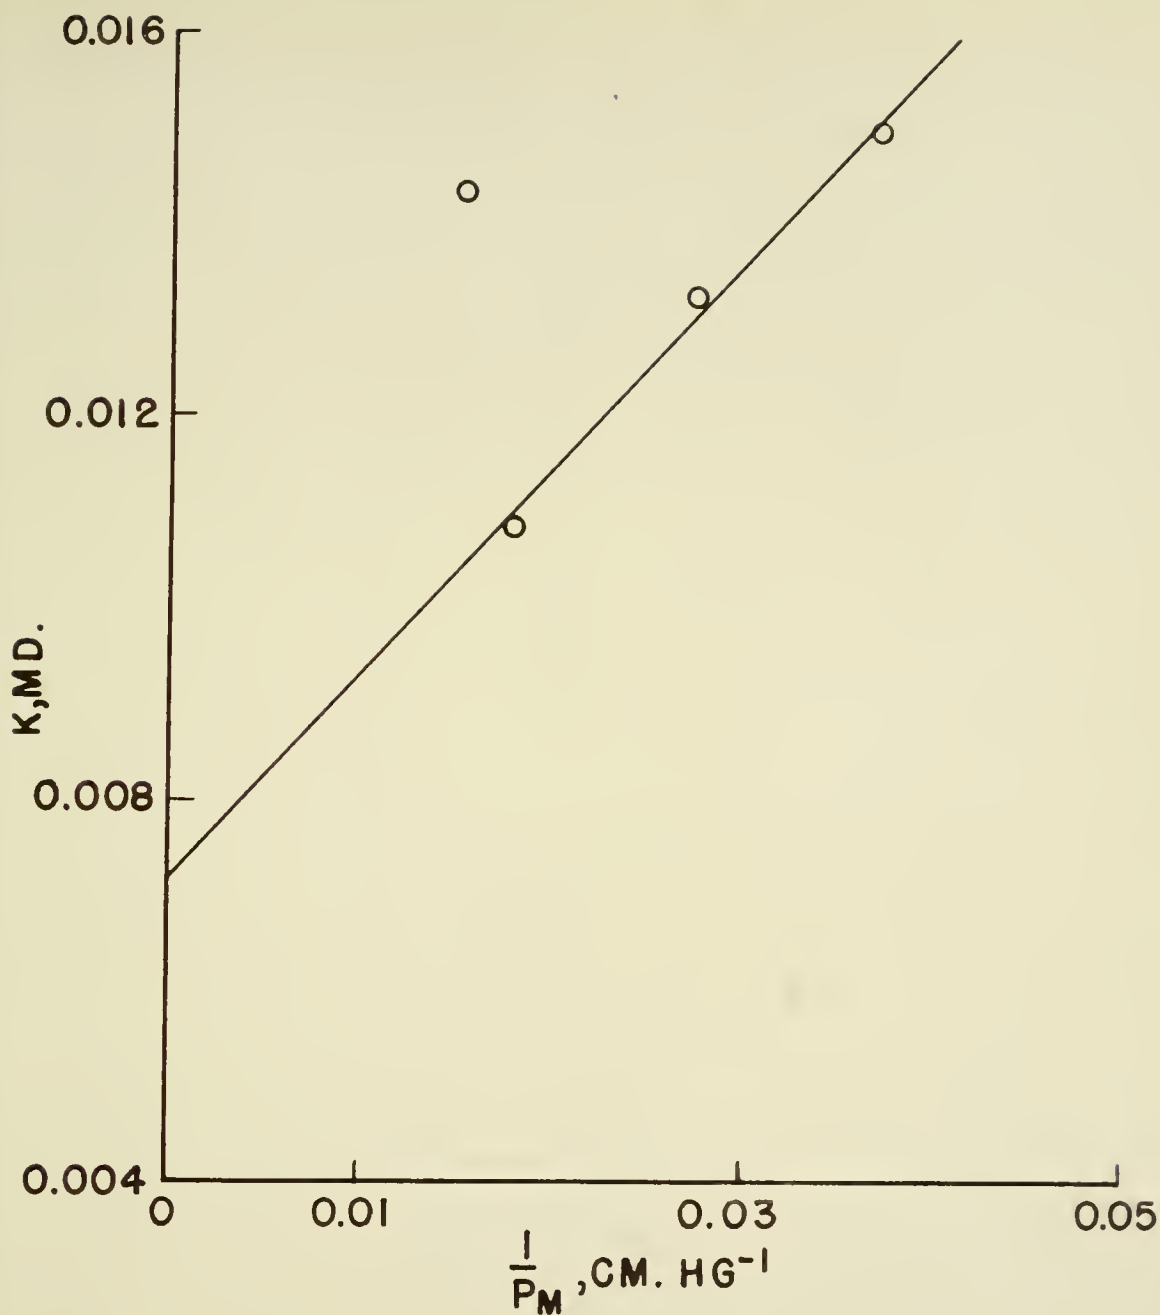


FIG. 12 PERMEABILITY OF 67-2S-P-45

error. In each instance these are the first runs made on the sample and the only explanation that can be offered is that of "starting up" errors.

Table 6
Permeability and Slip Factor

Source No.	K_1 , md.	pK_1	b, cm. μ g
1-1S	0.00205	13.694	43.2
3-1S-H-p	0.036	12.449	66.9
9-1S	4.30	10.372	26.9
9-1S-p	8.16	10.094	18.6
47-2S	0.032	12.500	82.5
67-2S	0.0072	13.148	29.7

Figure 10 shows the results of two low-pressure runs. The crosses are taken from adjacent intervals of one decay curve and the circles from another. At higher pressures this same calculation can also be made but the resultant points are relatively close together and cannot be used to define the line. It was thought that, by this means, perhaps only one run would suffice to define the entire line. The higher pressure curve shown is that of Figure 8 for the same sample. The agreement is fair but a discrepancy exists, especially for the slope, and the idea was abandoned for this study.

Absorptivity

The log-log plots of V/A vs. t for the capillary absorption runs are given in Figures 13 - 19. The data were such that straight lines could be drawn satisfactorily by eye in all cases except that of 1-15 (Figure 13). This one was done by least squares. The values obtained from the curves are given in Table 7. A comparison of the curves with equation (20) shows that the square of the intercept at $t = 1$ min. is the absorptivity coefficient in cm^2/min . Division by 60 gave the value in cm^2/sec ., which is the unit for the K_a values in Table 7. The logarithm of the reciprocal of this value, pK_a , is also given.

Table 7
Absorptivity Results

Source No.	K_a , cm^2/sec .	pK_a	α	$S_{w\alpha}$
1-15	3.74×10^{-9}	8.427	0.0106	0.413
3-15-H-p	1.22×10^{-7}	6.913	0.0604	0.602
9-15	1.82×10^{-5}	4.739	0.1770	0.731
9-15'-p	6.00×10^{-5}	4.221	0.1629	0.673
47-2S	6.62×10^{-7}	6.179	0.0650	0.610
67-2S	9.89×10^{-9}	8.004	0.0129	0.554

The values marked α are considered to be the effective porosities applicable to the capillary process, i.e., the volume of capillary permeant per unit bulk volume of material when capillary equilibrium was reached. The values marked $S_{w\alpha}$ are the corresponding saturations.

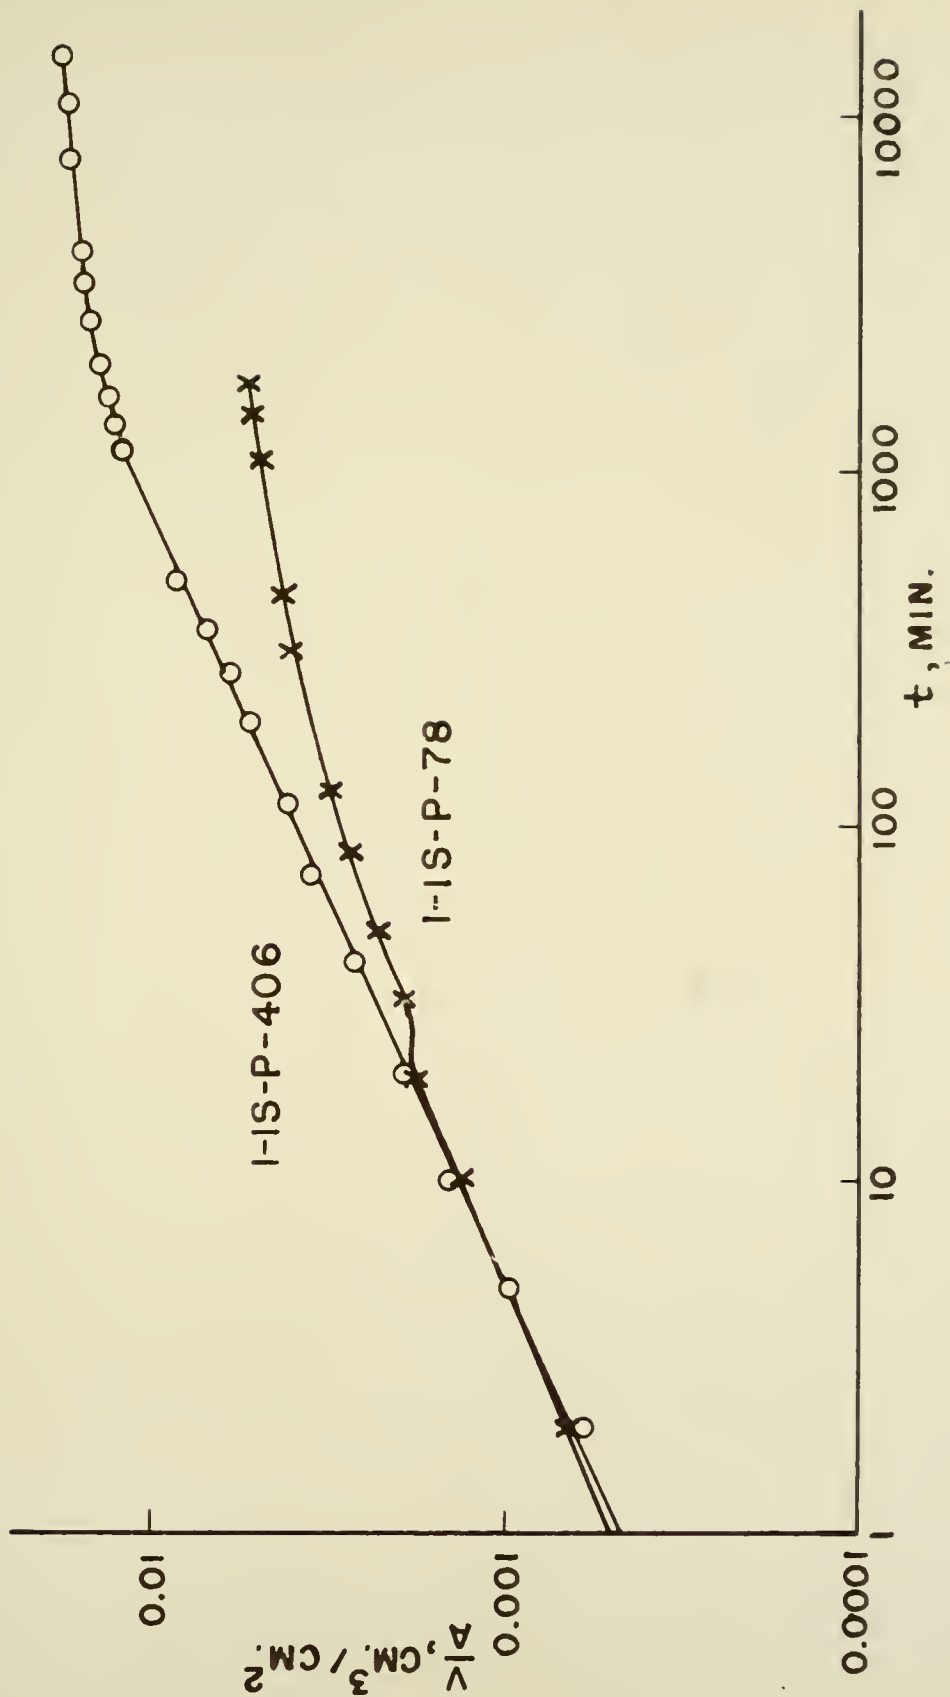


FIG. 13 ABSORPTIVITY OF I-IS

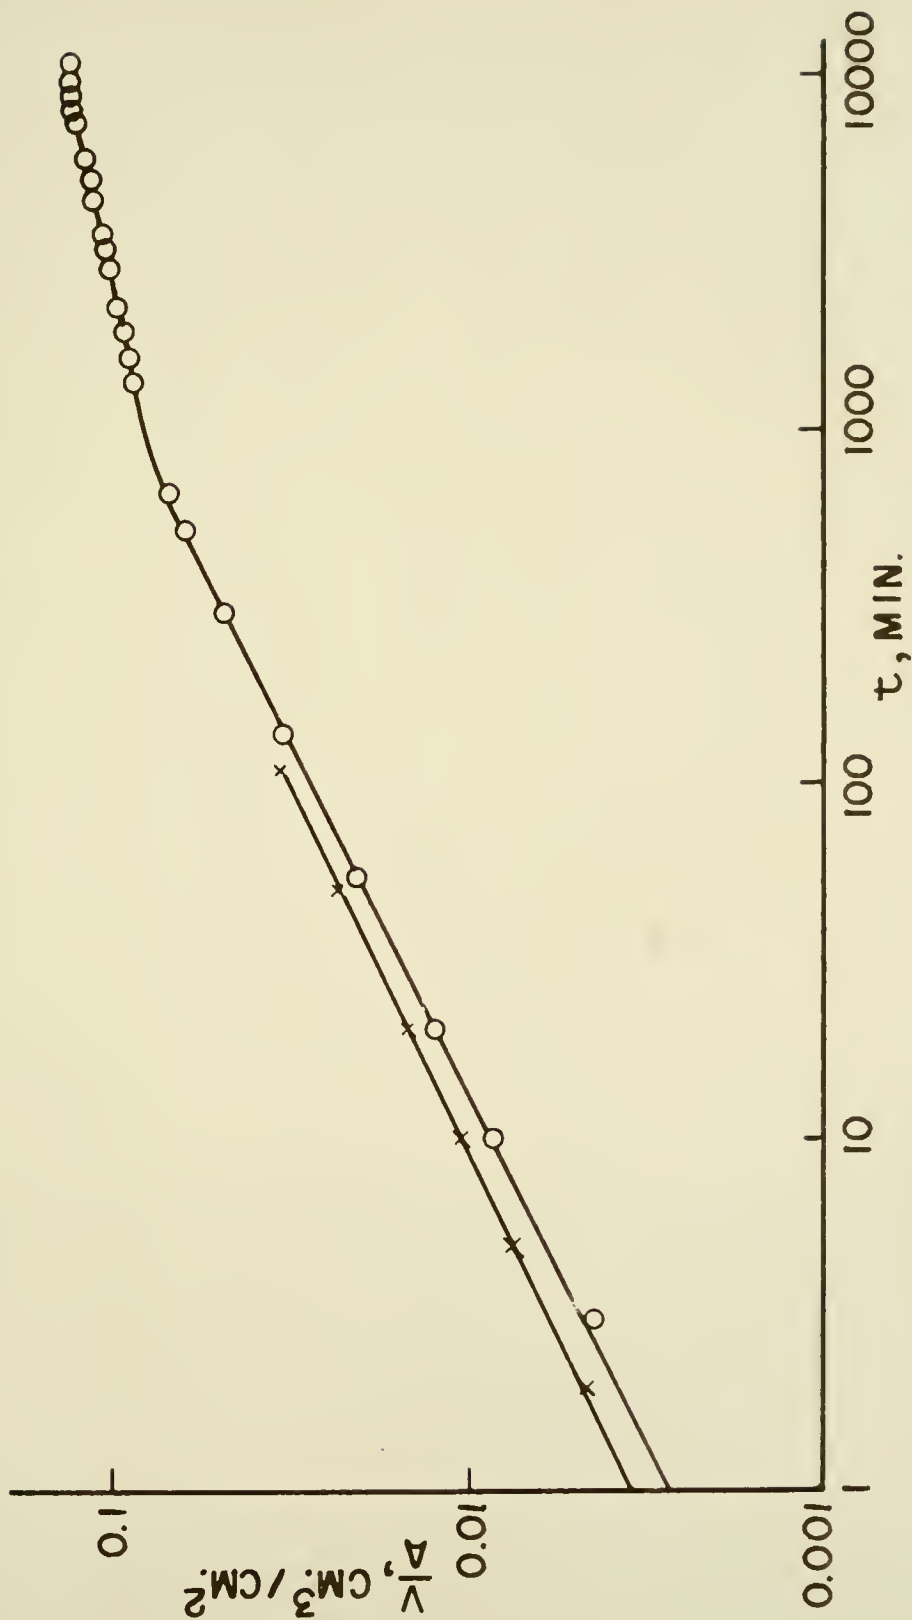


FIG. 14 ABSORPTIVITY OF 3-IS-H-P-80P

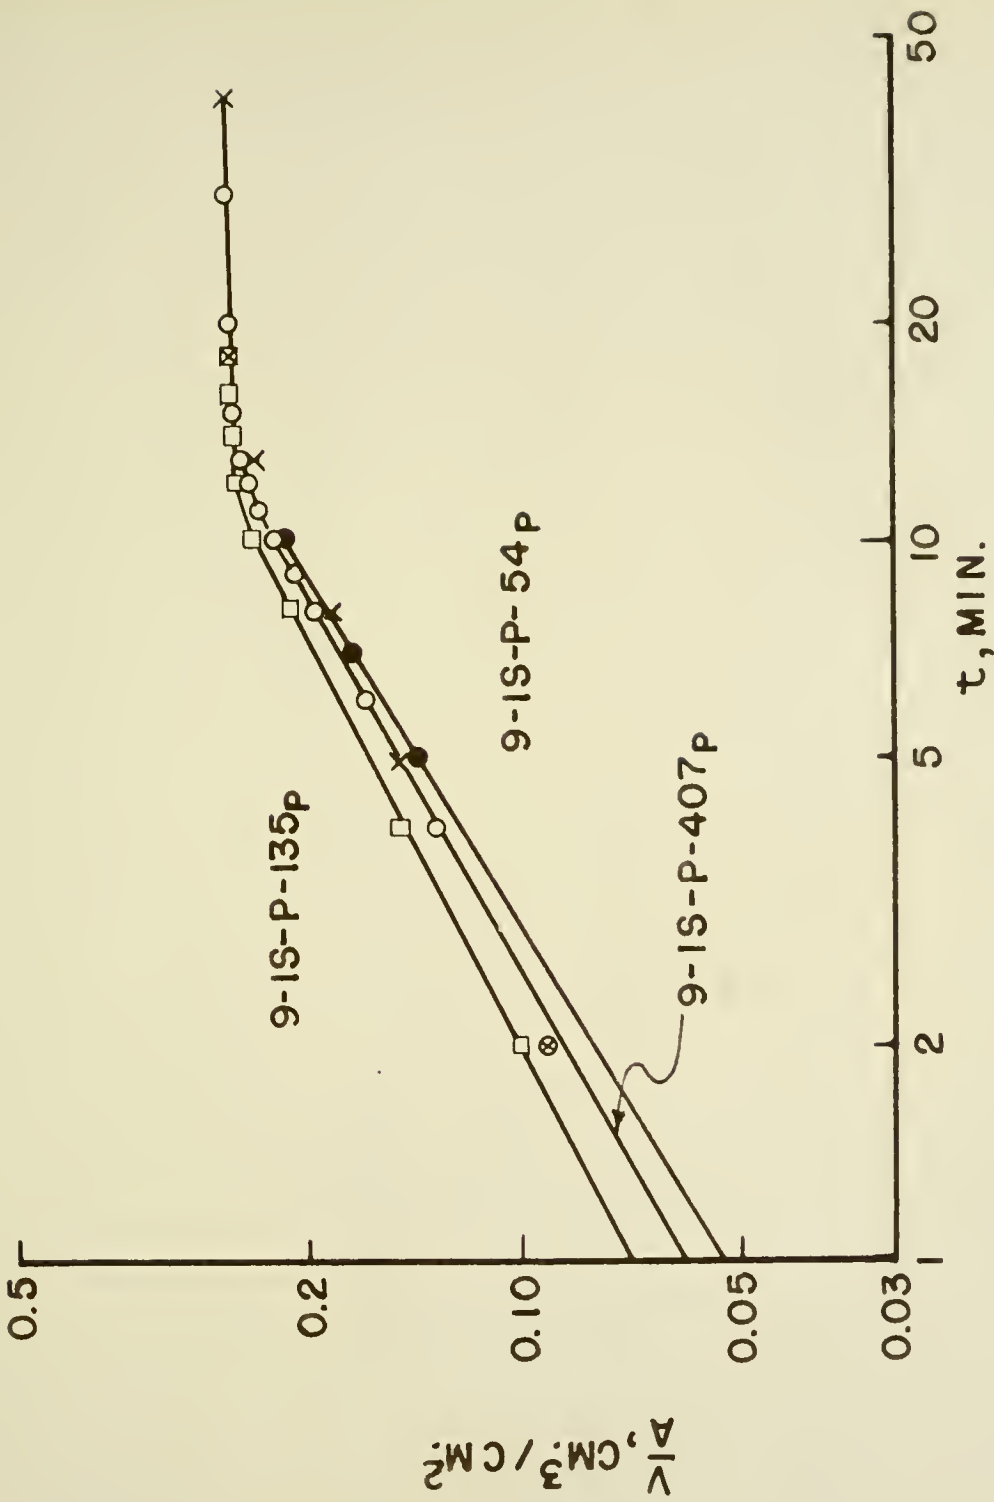


FIG. 15 ABSORPTIVITY OF 9-IS-P

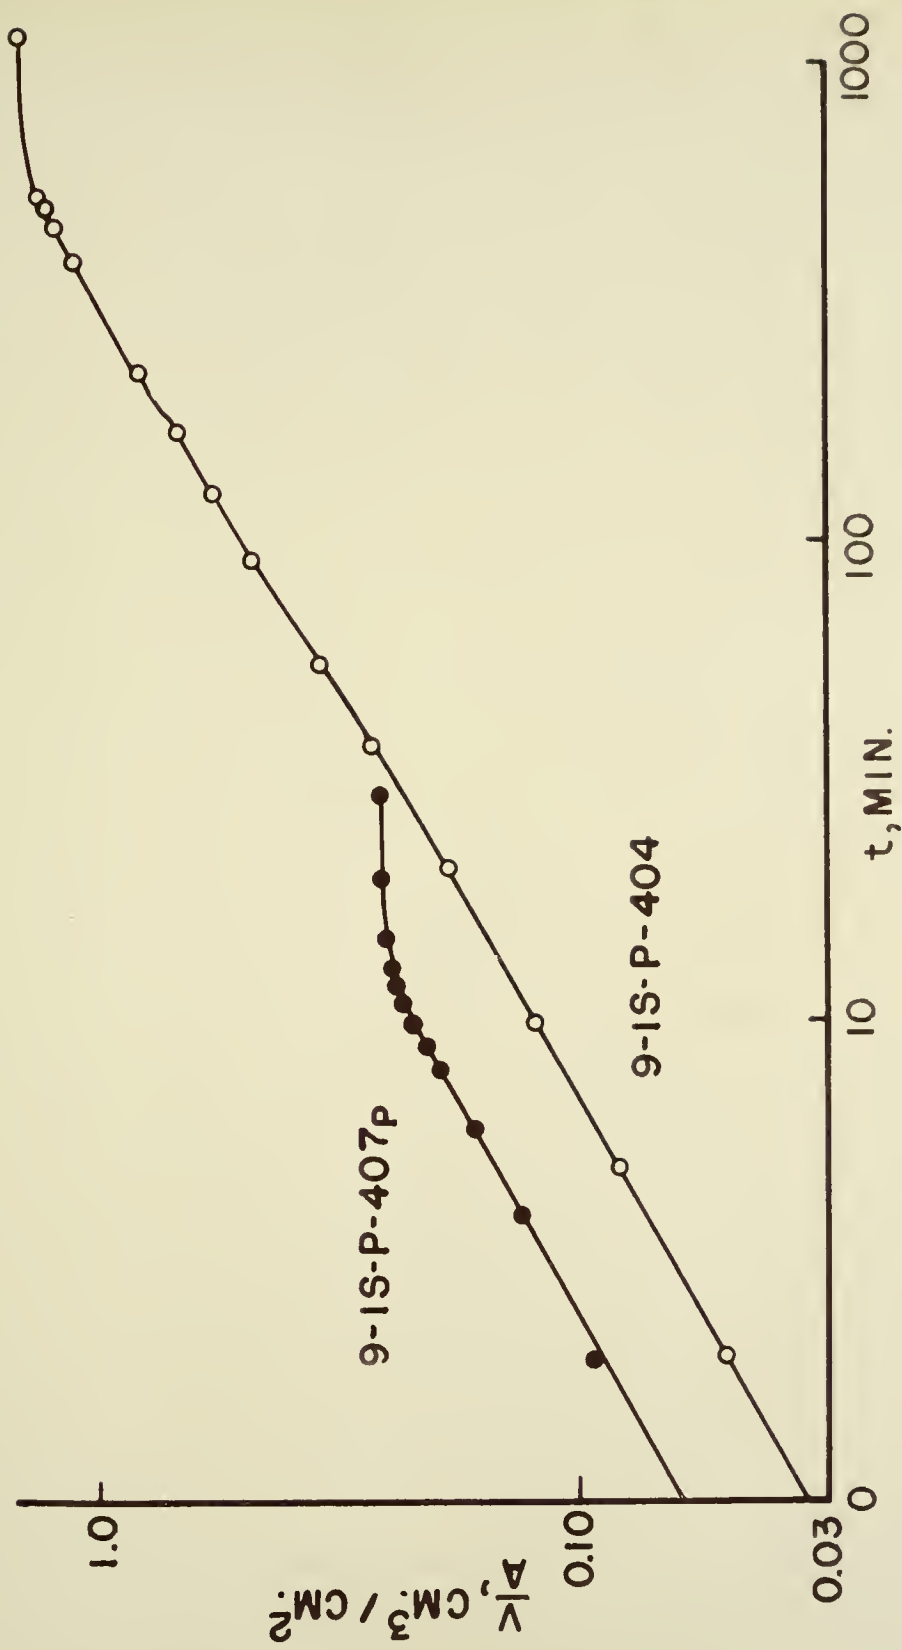


FIG. 16 ABSORPTIVITY OF 9-IS
EFFECT OF FLOW DIRECTION

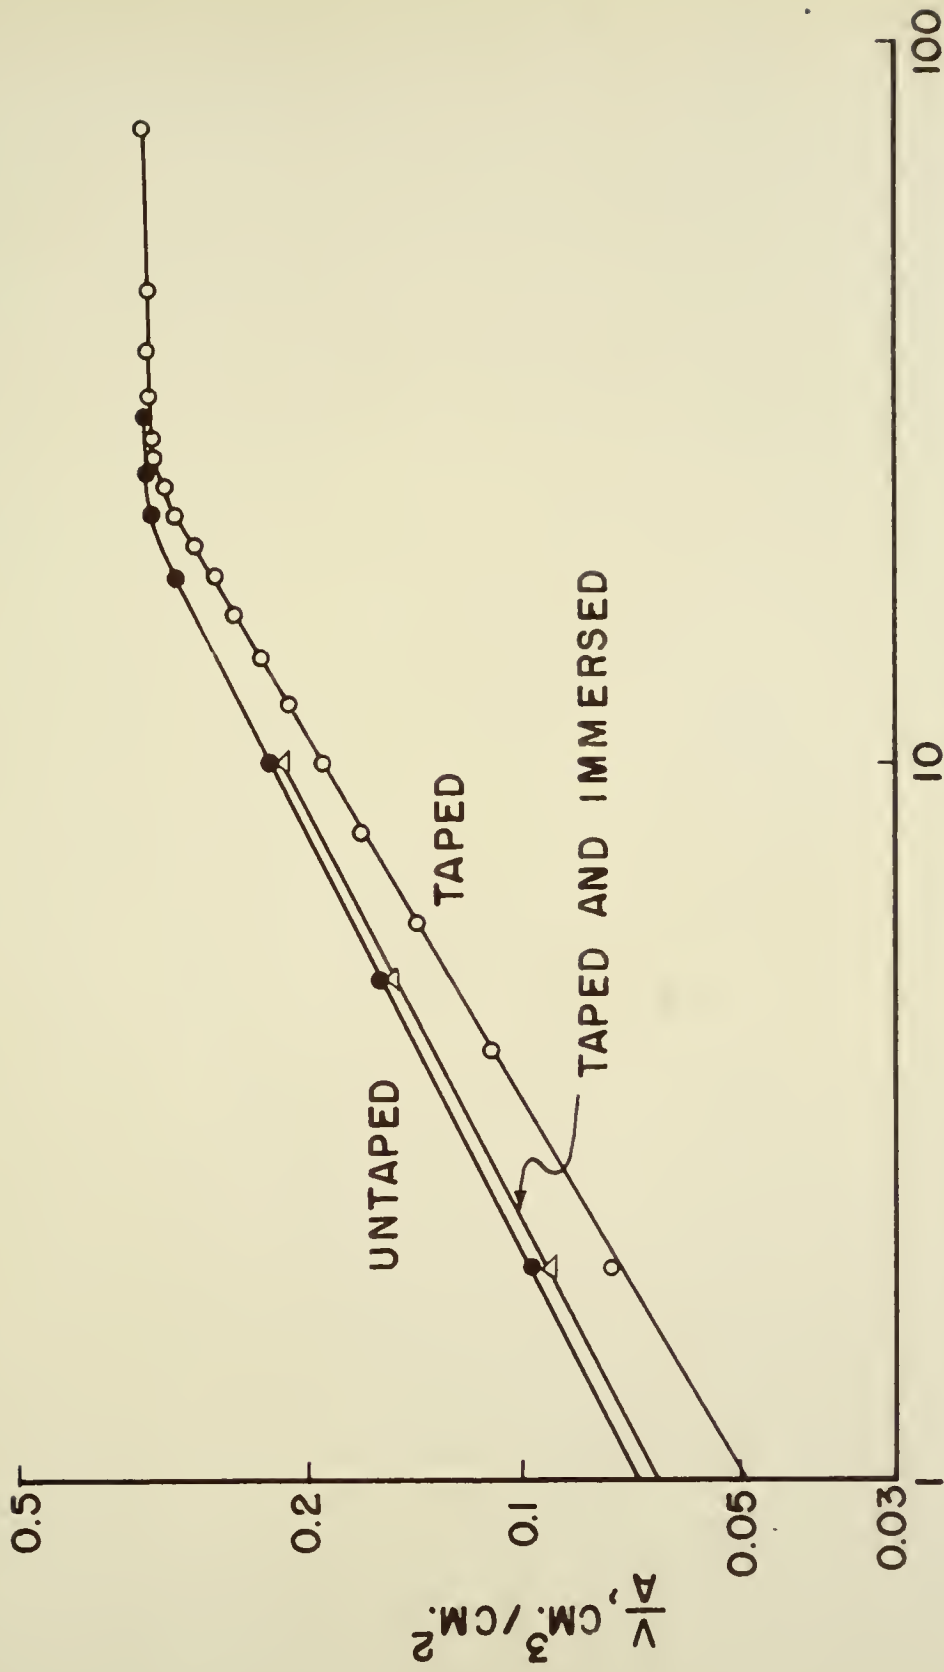


FIG. 17 ABSORPTIVITY OF 9-IS-P-199
EFFECT OF VARIOUS EXPOSURES

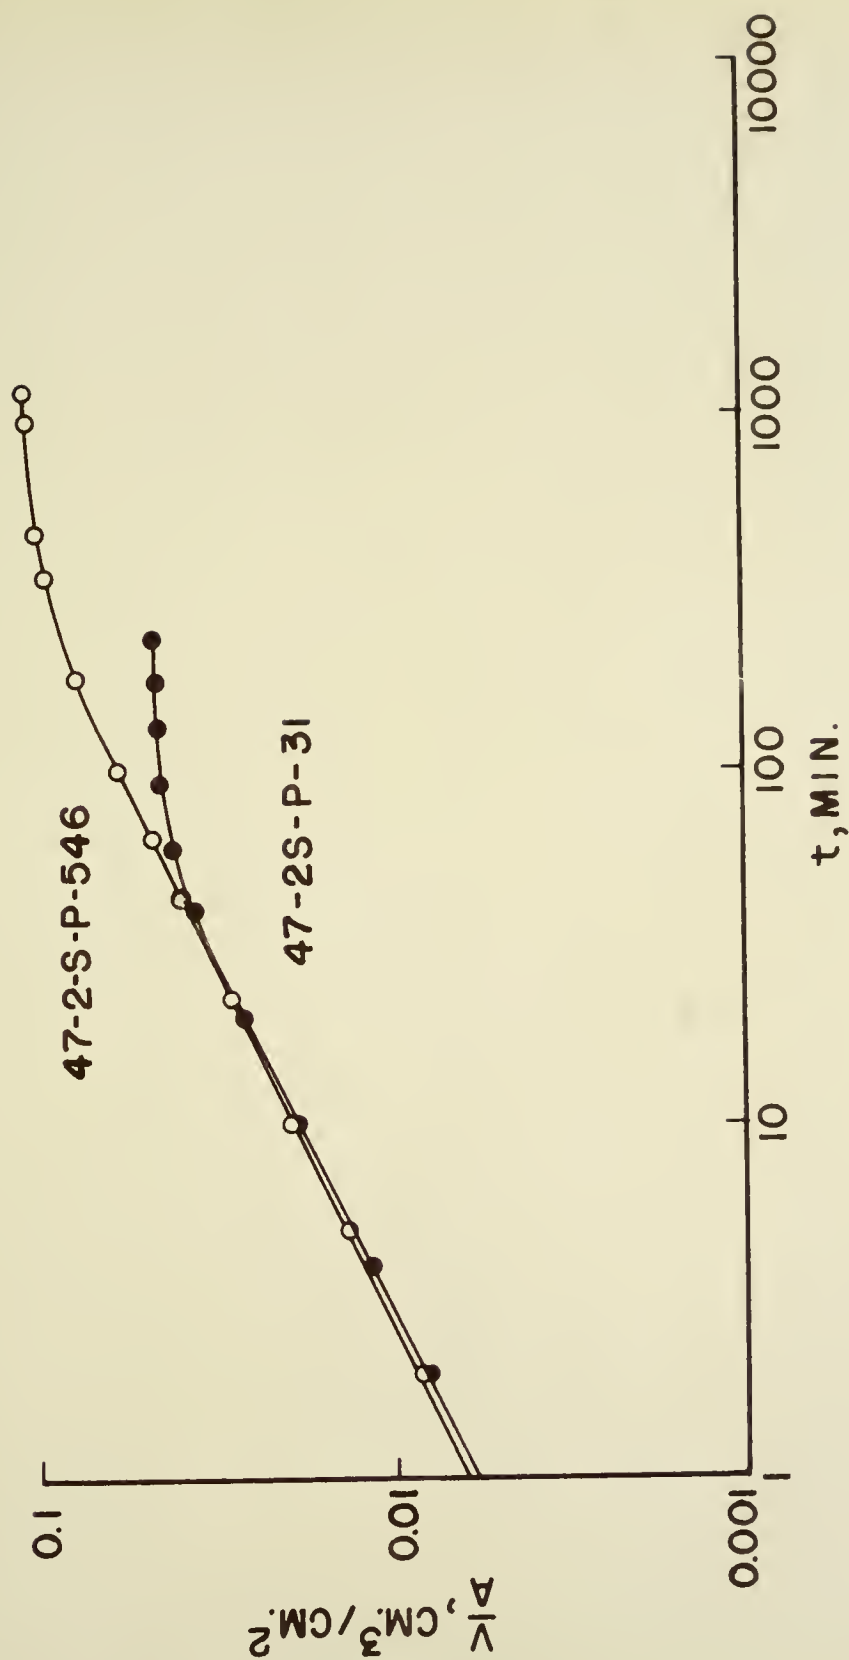


FIG. 18 ABSORPTIVITY OF 47-2S

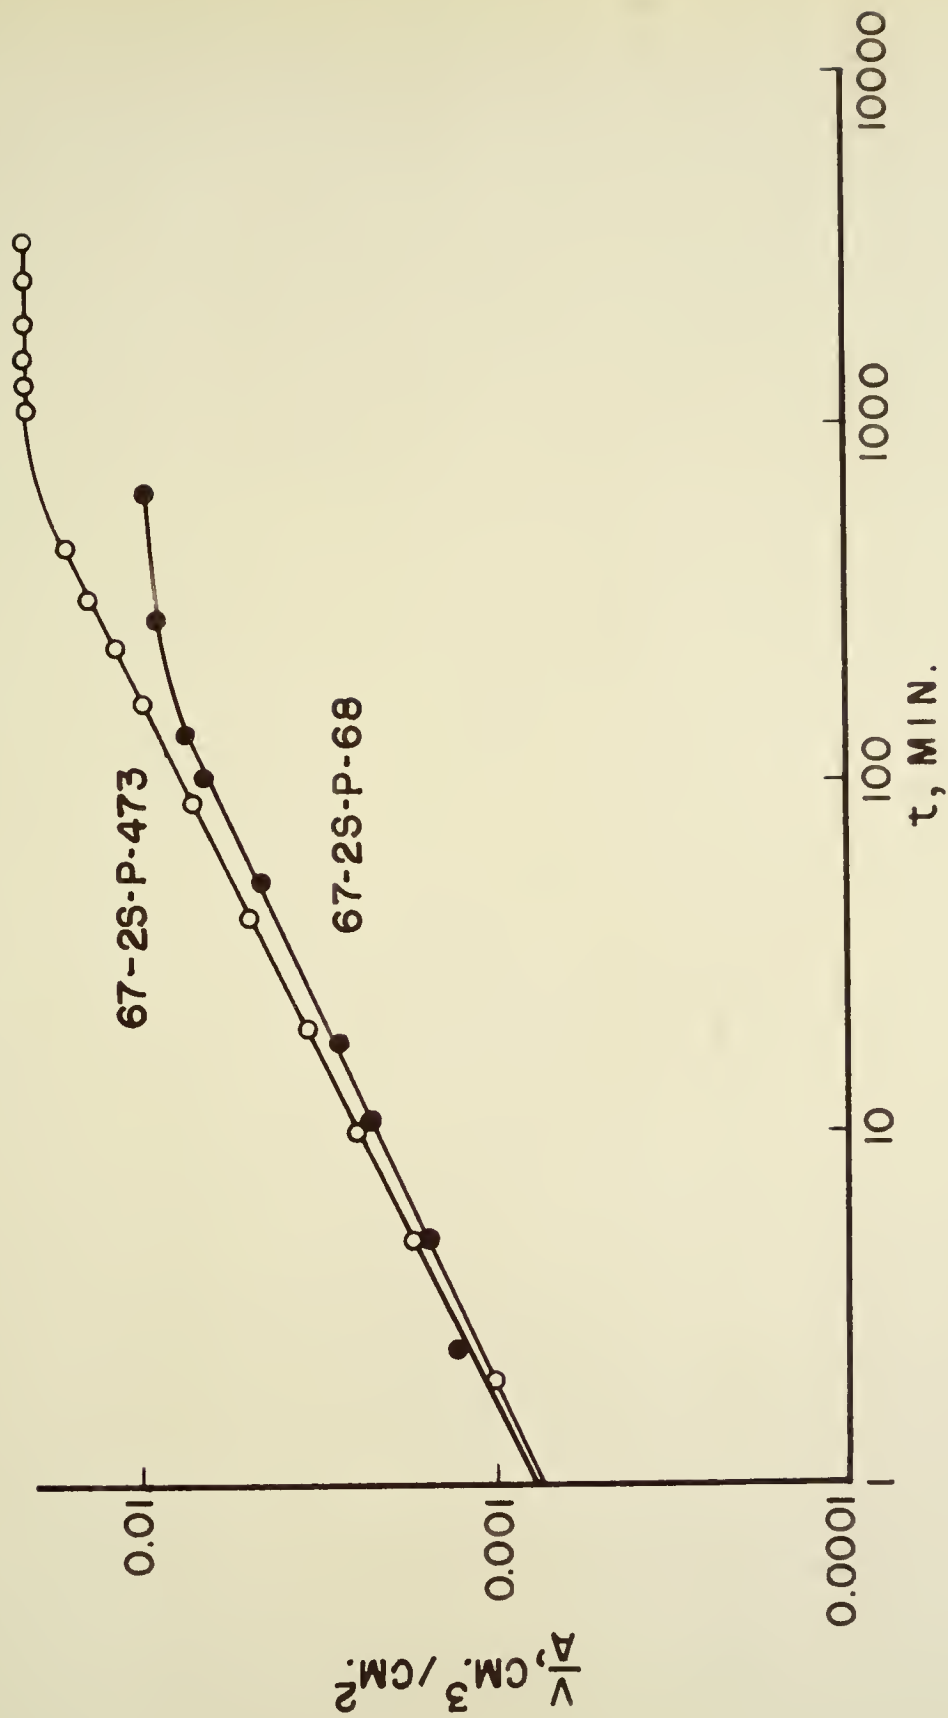


FIG. 19 ABSORPTIVITY OF 67-2S

A problem was encountered in connection with the evaluation of α . It was desired to know the amount of liquid that had entered by capillarity alone. Diffusion starts as soon as water enters but its contribution is probably small at any comparatively short interval of time. For those curves, therefore, that ascended and then broke reasonably sharply into the region of little gain in weight the problem was simple. It grew more complicated for those curves (1-LS, 3-LS-H) which had a considerable curved portion, i.e., a section not on the theoretical capillary absorption line but still not so flat as to indicate negligible weight gain. It was finally decided to use as the capillary water value that corresponding to the intersection of the original straight line and the straight line drawn through the points in the substantially flat region of negligible weight gain. The matter is referred to again in the Discussion section.

Most of the curves show measurements on two different prisms. The general agreement in intercept is taken as an indication of capillary similarity in the different prisms from the same source. Figures 14 and 15 show duplicate measurements on the same sample and given an indication of the reproducibility of this measurement. Figure 16 shows curves for flow both parallel and perpendicular to laminations in the same prism. Figure 17 shows the effects of varying the condition of the sample. One curve was obtained in the regular way. One is for the same prism untaped, and one is for the same prism taped and immersed to about 1 cm. depth in the water (contained in a beaker).

DISCUSSION

Theoretical Background

Permeability and Pore Structure

The basis for the use of fluid-flow measurements for the investigation of the internal structure of porous solids is the fact that the viscous flow rate is controlled by the interaction between the solid surface and the fluid. The extent of the surface and, therefore, the size of the flow channels are theoretically determinable by the use of such measurements.

The calculation of the values of these characteristics depends on a preconceived notion about the general nature of the porous structure, i.e., it involves the choice of a model. The use of a model is necessitated by the complex nature of the interior of porous materials. Most porous substances have a structure which is continuously variable and which cannot, by the nature of things, be described in detail. Even if the point-to-point details could be described the resulting equations for the description of fluid flow through the medium would be so complicated as to defy solution (55 p. 144, 74). The net result is that, for practical purposes, the use of a model, the details of which can be described mathematically, is necessary. Such a model is postulated to have the same values for its experimental properties as the actual sample, i.e., the same macro dimensions, porosity, densities, permeability, and absorptivity. The model can be simple such as one of straight, equal-sized, cylindrical pores, or it can be complicated such as the

random statistical model described by Scheidegger (73), who also discussed the details of some simpler models (72). The use of a model is a recognized compromise for which there seems to be no alternative.

The model used in the calculations to follow is a common one which recognizes and accounts for two important properties of actual porous media. These are 1) that the actual flow channels are of some irregular cross-sectional shape, and 2) that the actual flow path traversed by a "particle" of fluid is tortuous rather than straight.

The model used here is of the sort described by Carman (19). The approach area is A and the macro length is L . The porosity is ϵ . The pore space is completely interconnected and, from the point of view of fluid flow, can be thought of as a "pipe" of very complex but constant cross-section. The length of this "pipe" is L_t , which is greater than L . The hydraulic radius of this "pipe" is m .

Given this model, the next step is to derive an expression describing viscous flow of a fluid through the model. Such an expression, with the flow rate given in terms of permeability, is usually called a Kozeny equation after its originator. One of the chief advocates of the use of this equation has been Carman, and a derivation of the Kozeny equation for substantially the same model used here is given in papers by him (19, 20). In the latter paper he also discussed the assumptions involved in the equation and the consequent restrictions on its use. The derivation of the Kozeny equation for the model used herein, which follows substantially Carman's method, is given in Appendix C. The result is

$$K_1 = \frac{\epsilon m^2}{k_o k_t} \quad (22)$$

where the symbols are as previously defined. The hydraulic radius, m , of the cross-section of the pore system is, by definition, the ratio of the area of fluid to the wetted perimeter. For the condition of a saturated pore system and complete contact of the solid by the flowing liquid, the hydraulic radius becomes the ratio of the porosity to the specific surface (bulk volume basis),

$$m = \frac{\epsilon}{S} = \frac{\epsilon}{S_g \rho_B} \quad (23).$$

The insertion of this expression into equation (22) gives the Kozeny equation in terms of the specific surface,

$$K_1 = \frac{\epsilon^3}{k_o k_t S_g^2 \rho_B^2} \quad (24).$$

Since the Kozeny-Carman equation is based on a generalized analogy with Poiseuille's law, the condition of viscous flow is an important assumption. This condition was checked by the use of the Reynold's number formula given by Johansen et al. (35) and was found to be fulfilled. For the conditions of this study, therefore, only viscous flow need be considered.

The Kozeny equation has been used extensively. The constants have been evaluated for unconsolidated porous media by means of an independent determination of the surface area of the materials and are fairly well-established.

The shape factor, k_o , was given by Carman (19) as 2.5 for bead packs (i.e., spherical particles) and this figure has recently been confirmed by Wyllie and Gregory (97) for packs of vari-shaped particles. This factor is expected, on theoretical grounds, to be fairly constant. Carman (19) listed the shape factors applicable to widely differing

cross-sectional shapes. The factor for circular cross section is 2.0 and the whole range of values is only from 1.2 to 3.0. Rocks are, of course, consolidated porous media but the shape factors applicable should be of the same order as those discussed above. Wyllie and Spangler (99) considered this question and their conclusion was that, for the rocks they tested, the shape factors were approximately constant with the best value being about 2.7. This is the value that has been used here.

The tortuosity, k_t , of a porous medium can, on the other hand, have widely varying values. The value for spherical bead packs was found by Carman (18) to be around 2. The product of k_o and k_t is the parameter appearing in the Kozeny equation and, using Carman's values, this product is equal to 5. This is the value which has been widely accepted and used with a variety of porous materials. This was the best that could be done as long as independent methods of measuring tortuosity or specific surface for consolidated media were lacking.

These limitations have been lessened with the development of (at least) two independent methods of measuring tortuosity.

The first of these involves a combination of static and dynamic effects in an effort to relate the capillary properties of a fluid in the porous medium to its permeability. Equations have been derived by Purcell (63), Wyllie and Spangler (99), and Burdine, Gournay, and Reichertz (17). They differ in method but the idea is the same. Involved or implicit in these equations is the concept of tortuosity.

The other method, which was used here, is the electrical analog method. This method is discussed briefly and the pertinent equations

are given in the Experimental section. Further discussion is perhaps needed concerning the different concepts of the relation between tortuosity, formation factor, and porosity. As noted previously, Wyllie and co-authors (98, 99) considered tortuosity to equal $(F\epsilon)^2$ while Cornell and Katz (22) preferred $F\epsilon$. The distinction between the two concepts depends upon what is considered to be the effective cross-sectional area of the conductor in the resistivity experiments. None of the above authors spelled out in detail the reasons for their preferences. Wyllie and co-authors apparently think of a conductor of area ϵA since any plane through a homogeneous porous medium will, by definition, intersect an area of free space proportional to the porosity. On the other hand, if one considers a sort of "slanted tube" model in which the "tube" of complex shape has a cross-sectional area normal to the longitudinal axis (and, therefore, normal to the direction of current and fluid flow) of a , and a length L_t in a matrix length of L , then the volume of voids will be aL_t and the bulk volume will be AL , where A is the approach area. Porosity, ϵ , will, by definition, be aL_t/AL and the area of conductor in a resistivity experiment, a , will be $\epsilon AL/L_t$ or $\epsilon A/k_t$. This agrees with the proposition as stated by Cornell and Katz. Wyllie and Gregory (97) compared the two concepts for unconsolidated media composed of particles of various shapes and concluded that the $(F\epsilon)^2$ tortuosity was preferable to the $(F\epsilon)$ tortuosity. Slightly different relationships from either of the aforementioned have been obtained, empirically, by other investigators. Winsauer et al. (94) found a tortuosity of $(F\epsilon)^{1.2}$ and Faris et al. (27) found $0.671 (F\epsilon)^{1.95}$.

For the low values of tortuosity associated with bead packs and other unconsolidated media the differences between the numerical values of these varying formulations are comparatively small but for the higher tortuosities of consolidated media the differences are large. On the evidence of the Wyllie and Gregory paper (97) the concept of $(F\epsilon)^2$ for tortuosity has been provisionally accepted as the best founded for the calculations that follow here. But the Cornell and Katz formulation of $(F\epsilon)$ has also been used to illustrate the differences.

Direct measurement of tortuosities has shown that the value can be much higher than had been assumed previously. Wyllie and Spangler (99) found good agreement between surface areas of petroleum sands measured by permeability determinations and using independently-measured tortuosity values and those obtained by a "pin-dropping" statistical technique. Brooks and Purcell (13) used the Wyllie-Spangler capillary-pressure method for the measurement of tortuosity and found good agreement between Kozeny and geometrical areas for bead packs. But when the Kozeny areas for sandstones were compared with nitrogen sorption areas a large discrepancy was found with the sorption areas always being considerably the larger. Two reasons were given for the differences. One was that sorbed molecules contact all of the surface while flowing fluid contacts only parts of the surface and the rest (e.g., cracks in pore walls, dead-end pores) bounds stagnant fluid and does not contribute to retardation of flow. The other was that an essential assumption of the Kozeny equation is a more or less constant pore size and this condition is not usually met in consolidated media.

The basis of this difficulty is the fact that a large pore will contribute to the permeability entirely out of proportion to its surface area.

The other approach to pore-size determination via permeability measurements is through the dependence of permeability on pressure if the experiment is conducted with a gas. The concepts of slip-flow have been used to modify the Kozeny equation for the measurement of surface areas of powders (2). The Klinkenberg equation and its background have been described in the Experimental section. The slip component to permeability, as specified by the slip factor, b , of the Klinkenberg equation, is related to the size of the flow channel and the properties of the gas. One derivation was given by Klinkenberg (40) and a slightly different one, used here, is given in Appendix D. The derivation is for round tubes but the result probably holds fairly well for irregular shapes. For an actual porous media with a variety of sizes of channels through which the gas is flowing, two conflicting effects are probably operative in determining the slip contribution. These are 1) that the smaller the channel the greater the degree of slip but 2) the smaller the channel, the less the flow through it. The net result is probably that the slip factor reflects the size of the larger channels. Heid et al. (32) evaluated the slip factor for oil-bearing rocks and calculated the pore size therefrom using Klinkenberg's original formula.

Absorptivity and Pore Structure

The theory of the penetration of capillary tubes by liquids by

capillary pressure has been in existence for many years. The general matter is called here "absorptivity", which should be distinguished from "absorption."

Equations for the rate of capillary advance in a single tube were given by Washburn (86). The basic problem was the inclusion of the capillary pressure, i.e., the pressure difference across a meniscus, in the Poiseuille expression for viscous flow. Washburn's equations subsequently were refined by Rideal (68). Barrer (6) has given a similar equation in a review of fluid flow. Eley and Pepper (24) derived an equation which includes the concept of tortuosity. Razouk (64) discussed these matters briefly.

The equations for penetration into single capillaries have been extended to the more complicated problem of absorptivity in porous media. Bangham and Razouk (5) measured the absorptivity of charcoal blocks for methanol by a weighing technique. Their method, incidentally, involved periodic interruption of the capillary process just as did the one used on the rocks in this study. Madgwick (53) measured the absorptivity of building stone for water but did not relate the "penetration constant" so obtained to the pore structure of the material. Heid et al. (32) used the method on petroleum sands. They measured the time for the penetrant to traverse the sample from bottom to top and used the integrated form of the equation for straight tubes to calculate an average pore size. Powers and Brownyard (60 p. 865), who seem to have coined the term "absorptivity," measured this property for blocks of hardened neat-cement paste by immersion in water and continuous weighing.

Powers and Brownyard derived an equation which relates the absorptivity and the permeability of the sample to the specific surface of the conducting channels. This equation assumes that the two flow processes involve the same channels. The equation is, in the symbolism used in this work,

$$\eta_a^{K_a} = 2 K_{lc} \gamma S_{gc} \rho_B \quad (25)$$

where K_{lc} = liquid permeability, assuming all flow takes place through the "capillary" channels

S_{gc} = specific surface (weight basis) of the "capillary" channels.

Appendix E contains the derivation of the equations relating the absorptivity coefficient to the properties of the pore system of the model. Equation (E1) is similar to that of Barrer (6) except that the restrictions of steady-state conditions and circular cross-section are not applied here. The statement is made in the derivation that the equation can be simplified by ignoring the presence of the gas, the weight of the liquid, and the deceleration force term. This simplification has been assumed by most of the workers cited previously. A sample calculation shows that the only term which is arguable with respect to its being ignored is the one for the viscous retardation force in the gas. At the start of the run the capillaries are filled with air. The ratio of the viscous retardation force for the air to that for the water is (see equation E1).

$$\frac{\eta_g}{\eta} \left(\frac{L_t}{x} - 1 \right).$$

Since the ratio of the viscosities is about 0.02, the gas viscous-force term may be consequential when L_t/x is large, i.e., at the start

of the run. It is thought, however, that little difficulty has been encountered from this source. With all terms ignored except the capillary and viscous terms for the liquid the result of the derivation is an equation of the form

$$\left(\frac{V}{A}\right)^2 = C_1 t \quad (26).$$

On a log-log plot this equation is linear with a slope of 1/2. If the gas viscosity term is included the result is an equation of the form

$$\left(\frac{V}{A}\right)^2 + C_1 \left(\frac{V}{A}\right) = C_2 t \quad (27).$$

The data for these rocks do plot as straight lines on log-log paper with a slope of 1/2, within experimental error. It is possible that if data points had been taken very early in the run some deviations would have been observed. As matters stand, however, the conclusion is that the dropping of the gas viscosity term is justified. The net result of the derivation in Appendix E is

$$K_a = \frac{2 \gamma m \alpha^2}{k_o k_{ta} \eta} \quad (28).$$

Results

In this section are given the results of the calculations concerning pore structure, based on the theories of permeability and absorptivity just discussed, and using the measured values listed in the Data section.

In Table 8 are presented the calculated values for effective or average radii of the pores if the model chosen is that of equal-sized, round, tortuous tubes.

Table 8
Calculated Average Pore Radii of the Rocks.

Source No.	Radius, μ			
	Slip	Permeability	Absorptivity	Sorption
1-1S	0.460	0.493	0.187	0.110
3-1S-H-p	0.296	0.422	0.0144	0.101
9-1S	0.737	1.18	0.0269	0.131
9-1S-p	1.07	1.73	0.159	0.131
47-2S	0.240	0.394	0.0684	0.0372
67-2S	0.668	0.364	0.0261	0.0208

The slip radii were calculated by means of equation (D8). The permeability radii were calculated using equation (C7) which is the Kozeny equation for round tubes. The shape factor, k_0 , is 2.0 in this equation and the tortuosities used were the Wyllie-Rose tortuosities for complete saturation. The absorptivity radii were calculated from equation (E11) using the Wyllie-Rose tortuosities, $K_{t\alpha}$, for the capillary saturation. This equation also implies a shape factor of 2. The sorption radii were calculated from the BET specific surfaces by means of the relationship $m = \epsilon/S_g \rho_B$ and assuming round pores, for which $r = 2m$.

The use of the round-tube model is an approximation which may be acceptable for comparative purposes. The differences between the round-tube radii and the hydraulic radii are only the difference between the shape factors, 2.0 and 2.7 respectively.

In Table 9 are presented the calculated values for the specific surfaces of the rocks along with the measured BET sorption values.

The "slip" areas were computed using the "slip" radii, i.e., they are the areas of arrays of round tubes with radii equal to the calculated "slip" radii.

The "permeability" areas were computed from equation (24). Two expressions for the tortuosity factor appearing in this equation have been used. The column marked k_t contains values computed using the Wyllie-Rose tortuosity, i.e., $(F\tau)^2$. The column marked τ contains values computed using the Cornell-Katz tortuosities, i.e., $F\tau$.

The absorptivity areas were calculated according to equations (E13) or (E14) depending upon the interpretation placed on m . This choice is discussed in more detail in the following section. The tortuosities used for computing the values on the $m = \epsilon/S$ basis were the Wyllie-Rose values computed for the capillary saturations. Both tortuosity concepts have been used for the values computed on the $m = \alpha/S_\alpha$ basis. The column marked $k_{t\alpha}$ contains values computed using the tortuosities just described. The column marked τ_α contains values computed using the corresponding Cornell-Katz tortuosities.

The column headed S_{gc} contains values for the "capillary specific surface" computed using equation (25) which was derived by Powers and Brownyard. It should be noted that the units of the values in this column are $\text{cm.}^2/\text{g}$ while those in the rest of the table are in $\text{m.}^2/\text{g}$.

Discussion of Data and Results

In this section the data and results are discussed from the point of view of the tests per se, the agreement, or lack thereof, among

Table 9

Calculated Specific Surfaces of the Rocks

Source No.	Sorption	Slip	Specific Surface, $m.^2/g.$			Absorptivity	S_{gc} (cm. ² /g.)	
			Permeability	$m = \epsilon/S$	$m = \alpha/S_\alpha$			
			k_t	τ	$k_{t\alpha}$	$k_{t\alpha}$	τ_α	
1-1S	0.67	0.0428	0.0326	0.144	0.0756	0.0312	1.48	4.16
3-1S-H-p	0.87	0.261	0.157	0.442	3.96	2.38	31.4	8.16
9-1S	2.04	0.298	0.163	0.290	6.23	4.55	19.6	12.4
9-1S-p	2.04	0.206	0.111	0.204	1.04	0.700	3.73	21.5
47-2S	2.54	0.350	0.188	0.536	0.930	0.568	7.55	52.3
67-2S	1.09	0.0238	0.0416	0.113	0.499	0.276	3.67	3.26

various values, and the concepts of pore structure which can be inferred from the results. Most of the operational questions have previously been discussed in the Experimental section. The interpretation of the results in terms of the quality of the rocks as concrete aggregates is taken up in the next section.

Densities and Porosity

The true densities (Table 3) are derived from the values for the volume of solids obtained with the volumenometer. The advantages of this method are that the test is non-destructive, rapid, and that questions of degree of saturation, encountered when using liquids, are not a factor. An inherent disadvantage, on the other hand, is that totally-enclosed voids will appear as a volume of solids rather than of voids. Any real porous body will have some such voids and their destruction is an advantage to the techniques in which the sample is powdered. All that can be said here is that the values obtained in this study agree fairly well with those obtained by others who used the powdering method on materials from the same sources. They also agree within a few percent with values obtained by calculation from the chemical composition and the appropriate values for the pure mineral species. The bulk densities calculated from the true densities and voids ratios agree to approximately a half percent, with those, for the same samples, obtained by the direct measurement of the dimensions.

If regular shapes are obtainable, dimensional measurement is probably the best way of determining bulk volume. Slight irregularities in the shapes of prisms could, however, result in considerable

error. The values reported here for the bulk density are, therefore, those obtained using the volumenometer and the calculation from the true density.

The "McLeod gage" porosimeter method for the determination of porosity has the same virtues of non-destruction, speed, and simplicity which were listed for the volumenometer. A disadvantage, especially for large samples, is the difficulty in constructing a leak-free joint for closure. Even with the small apparatus used here the ball and socket joint gave trouble and it had always to be greased carefully to keep grease out of the system. Even so, frequent cleanings were necessary.

The results shown in Table 3 for the porosity and for the absorption and consequent degree of saturation are all of the correct general magnitude, with one exception, when compared with previous results on the same materials (8, 16, 28, 81). The exception is for source 3-LS-H. The values obtained for the absorption and, especially, for the saturation are considerably different from any published for this source. The matter already has been mentioned with respect to the small pieces that were available and the low degree of homogeneity of the rock. This lack of agreement may not, however, be as serious as it seems. Recent tests (54) on the same batch from which the pieces used here were obtained show approximate agreement with the values given here. The conclusion, therefore, is that the values are not erroneous for these specific pieces. The inferences with respect to the quality of the stone will be given later.

Tortuosity

The method of measuring the tortuosities was straightforward and simple. The measurements were precise in every case except that already noted, 1-LS. A possible reason for this has been mentioned, i.e., differences in orientation of the conducting saturant from run to run. The final result, a tortuosity of 384, is certainly high. It is not, to be sure, impossible but it is unusual. The values for the other rocks are all of a reasonable magnitude.

The basic validity of the electrical analog method is dependent on an assumed equality between the overall magnitude, if not the small details, of the electrical and fluid flow paths. This assumption seems justified for completely saturated conditions but it may not be for partial saturation. Wyllie and Spangler (99) discussed this point and described the electrical tortuosity at incomplete saturation as lower than the hydraulic tortuosity because an almost empty pore space will not support fluid flow but will pass an electric current by means of a "skin effect" in the liquid wetting the pore walls.

The use of the value 2.0 for the resistivity index exponent, n , has already been discussed (and see Appendix A). Rather than assuming an arbitrary value, it would have been better to measure n directly by making a number of resistance measurements at various saturations. Such experiments, on the same piece of rock, have been difficult because of the necessity to get different saturations without changing the composition of the saturant. Birks (7) introduced a method for this determination in which he used a saturated solution of calcium

sulfate and evaporated some of the water for each successive test. He obtained somewhat different values for the formation factors of dense limestones when using calcium sulfate than when using sodium chloride so the choice of electrolyte may be important. For any choice, the specific conductance of the solution used should probably be measured directly rather than dependence being placed on handbook values. If n is measured directly the experiment should be the last of the series because the presence of the salt in the rock pores would alter subsequent measurements and its removal is difficult.

The tortuosity measurements, particularly for the denser rocks, are probably the least accurate of the measurements reported here.

Sorption Measurements

The experimental technique for the sorption runs was simpler than the more common volumetric or gravimetric techniques. It is faster than the humid-air-train apparatus of Powers and Brownyard (60 p. 249). Where room temperature and run temperature are almost equal there is no objection to removing the sample from the constant-temperature bath for weighing. The successful use of the Tygon joints rather than the more cumbersome standard-taper joints is worth mentioning.

The surface area values obtained using water vapor have been found (10, 31) to be different from those obtained with nitrogen, a more conventional sorbate for this experiment. The matter is somewhat arbitrary and the simplicity possible for the apparatus and the precedent with concrete materials (31, 60 p. 249) dictated the choice of water vapor at room temperature.

The Brunauer-Emmett-Teller theory was used because of its successful history. Its basic assumption that the net heat of adsorption in every layer after the first is zero has been questioned (29). The necessity to assume a constant area for a sorbed molecule in the first layer is also a disadvantage. But, regardless of its possible shortcomings, the theory has given reliable results for surface area determinations and has been used probably more than any other for this purpose.

The particular data obtained here could have been improved by using more experimental points to define the isotherm. The data, however, fit well when plotted according to the linear form of the BET equation. The concurrent measurements were fairly precise, as is shown by the individual values in Table 5, especially considering the comparatively low specific surfaces involved. The values of the heat constant, C , in the BET equation were so low (about 4 to 8) that the use of the single point approximation method gave, as stated previously, large errors in the final area value.

No previous measurements of surface area of these Indiana aggregates have been made. These values are, in fact, the standards to which other methods for area measurement are later compared. They are, however, of the same order of magnitude as the results of the measurements on "limestones" made by Blaine, Hunt, and Tomes (10) and by Brooks and Purcell (13).

Permeability

The pressure-decay permeameter is preferable to the conventional apparatus for a substance of low permeability (less than about one millidarcy). The conventional type of apparatus necessitates a measurement of the flow rate either by collecting the permeant or by the use of a flowmeter. For substances of high permeability either operation is feasible but the elimination of the direct measurement is better for dense materials.

A disadvantage to this particular apparatus was the method of holding the sample. The hard asphalt cement was difficult to remove completely from the sample and the test is destructive to this extent.

Considerable differences exist between the times for a run on a dense and on a fairly permeable sample. With the impermeable samples the rate of travel of the meniscus of the differential manometer was so slow that there was some question as to the time at which the meniscus was opposite the appropriate mark on the scale. On the other hand, the overall time for the pressure to decay was proportionately longer than for the more permeable samples and the relative accuracy was probably about the same in all cases.

The data presented in Figure 10 show an interesting possibility which has already been mentioned—that of defining the whole curve with one run at low pressure rather than with several at higher pressures. For a low-pressure run the small absolute changes in mean pressure during the decay represent comparatively large numbers when the reciprocals are taken and so show up on the plot at a distance apart suf-

ficient to define the line. The large increase in permeability at low pressures is evident from the figure and may be the reason for the shortness of the time needed for the run with the McLeod gage porosimeter. The low-pressure technique is reasonably precise as is shown by the good agreement between the two runs on the same sample that are shown in the figure. The intercept that was obtained is slightly higher than that obtained for the same sample with the higher-pressure technique--5.8 as contrasted with 4.3 millidarcys. A more serious difference is in the slopes. The extrapolated line for the high pressure data is shown also on the figure and the corresponding b values are about seventeen and twenty-seven.

The fairly good agreement in intercept indicates possibilities for using the low-pressure method for the determination of K_1 . The higher permeabilities at the lower pressures mean that the time for the run is shorter and this is an attractive feature. There were, however, enough uncertainties present so that the higher pressure method was used here.

The curves show good linearity of the data with the exception of some of the points for 1-LS (Figure 6). This agreement is taken to mean that no gross errors were made in the experiments. A further argument in favor of the data is the record of a few runs made on 9-LS and 47-2S with a conventional train apparatus and collecting the permeant over water. The values obtained by the two methods agree well.

Absorptivity

The method used here for the measurement of absorptivity is, as far as the writer knows, novel. The main question that can be brought against it is that of possible moisture movement during the weighing and this matter has already been discussed in the Experimental section and the reasons given for thinking that such movement is slight. Assuming no trouble from this source, the method has to recommend it its simplicity and directness. A disadvantage to the technique is the amount of time necessary for the reaching of capillary equilibrium with samples of the nature and thickness of those used here. If only the value of the absorptivity coefficient is desired it can be obtained in a few minutes by taking the first data points on the curve. But if the properties of the pore system are to be calculated from K_a , the capillary porosity, α , must be known. With the present experimental technique the only way to determine α is to wait for equilibrium. With these samples (roughly 2 cm. thick) the time needed was from extremes of approximately ten minutes to a week. The obvious way to lessen such a long time is to use thinner samples. Examples of the changes that can be expected are shown in Figures 18 and 19 in which samples of different thicknesses have been used with a great reduction in the time for the thinner pieces to reach equilibrium.

The question of taping the sides is somewhat arbitrary. Figure 17 shows three runs on the same sample under different conditions. The lowest curve is a record of a run done in the ordinary way. The longer upper one is for the same sample untaped. The shorter upper

one is for the sample taped and immersed to about 1 cm. in the water. The reasons that suggest themselves for the differences are that, for the untaped sample, the displaced air can escape to the sides instead of being trapped by the advancing menisci or forced to traverse the longer route to the top. The amount imbibed in a certain time would, therefore, be greater than for the same sample in the taped condition. The immersed sample had a hydrostatic head applied and again, the net result should be a higher apparent absorptivity such as was actually observed. For adherence to the principle of the capillary tube model, however, the sides should be taped and the absorption should be by capillarity from a free-water surface.

The values of K_a reported in Table 7 are those for the large prisms on which the density and porosity measurements were made. Generally curves for another sample of the same rock are given to indicate the variation from piece to piece. For 1-LS, 47-2S, and 67-2S the agreement between the two is good. The agreement is poorer for the 9-LS samples. This rock is laminated with alternating bands of fine and coarse material and it is understandable that companion pieces might exhibit differences in individual behavior. Two curves from runs on the same sample are shown for 3-LS-H-p and for 9-LS-p. The precision is good for the 9-LS-p and fair for the 3-LS-H-p.

Since such a comparatively large volume is absorbed in the early part of the test, care should be taken with the initial manipulation. With attention to details the method is capable of good precision.

The sample of 9-LS was tested by exposure both perpendicular and parallel to the laminations. The two curves of the data are shown in

Figure 16. The perpendicular exposure had the lower absorptivity. This difference is in line with the expectations from the permeability which exhibits the same differences (Table 6). The curve for the perpendicular exposure was the only one where non-linearity was observed. Two discontinuities can be seen. It is thought that these were caused by the water front reaching a layer of material whose capillary potential was particularly high. This behavior is one reason for preferring the parallel exposure technique for these layered materials.

The theoretical slope of the log-log curves of the data should be 0.5. The slopes of all the curves except those for 9-1S are in agreement with this figure within the limits of experimental error (± 0.03 or so). The slopes of the curves for 9-1S are uniformly high. The average for the six runs (taped samples) shown is 0.57 with a range of 0.52 to 0.60. What this difference means, if indeed a valid difference is present, is unknown.

The capillary porosity, α , is the fraction of the bulk volume occupied by the capillary permeant under the conditions of the absorptivity experiment. Mention has already been made in the Data section about the determination of this value from the experimental curves. For only two of the rocks (1-1S and 3-1S-H) was a problem encountered. These two rocks have data curves which have a comparatively long intermediate section that is neither on the straight-line, slope-of-one-half, capillary-absorption curve nor on the almost flat portion which indicates negligible capillary absorption. These two rocks are the least homogeneous of the group. They both have comparatively large amounts of material which appears different from the majority of the

mass and which may be assumed to have different capillary properties from this majority. In the runs on both materials there was observed an uneven wetting of the top surface. It is a logical assumption that the first break in the curves represents the point at which the permeant first broke through to the top. This was observed to be approximately true.

From this point on, the sample size was changed, i.e., the V/A ratios were calculated using a macro area larger than that applicable to the capillary process which was still active. The situation just outlined can account for the shape of the curves in question. It is not until the flat region is reached that the capillary pore space is filled. This point should, therefore, be the one at which the weight of water in the sample represents the capillary porosity. The nearly flat portion of the curve was extrapolated to the original line (to remove small deviations from ideality) and the intersection so obtained was taken to represent the capillary-held water.

Saturation

This is perhaps the place to discuss one further aspect of the degree-of-saturation. The problem is the reason for incomplete saturation—during capillary absorption and particularly when the sample has been evacuated and immersed.

A possible mechanism to account for incomplete saturation is that of entrapment of gas in the pores. The commonly-used examples are a blind-end pore or an "H" structure in which gas is trapped in the connecting passageway between two pores. If the air trapped in the pore

is at atmospheric pressure the advancing water will not enter unless the capillary pressure across the meniscus is greater than atmospheric. If the capillary pressure is greater than atmospheric the water will enter the pore and compress the gas until equilibrium is established. Any higher saturation can be accomplished only by dissolution of the trapped gas and its diffusion from the region.

When a piece of stone is immersed in water as is done in the ordinary 24-hr. immersion test, the water starts to enter from all sides more or less at once. The situation is presumably ideal for entrapment of air. In the capillary absorptivity test the air can escape from the top surface but still there are many possibilities for entrapment. An inspection of Tables 3 and 7 will show that the saturations by the two methods were roughly equal except for the case of 3-1S.

Air-entrapment processes should, however, not apply to the method of vacuum saturation. If all the air is removed from the pores, it is difficult to see how it can block anything. Only molecules of water vapor are in the pores under these conditions. No blockage is possible and complete saturation should be achieved. But the fact is that, except perhaps for very open materials, complete saturation is not obtained and in some cases as much as a third or more of the pore space remains unfilled under these conditions.

The argument that the evacuation is not complete if it is done with an aspirator is poor in view of Sweet's (82) tests which showed that no improvement was obtained by substituting a good vacuum pump for the aspirator.

Some mechanism other than simple blocking must be operative to account for the facts observed in vacuum saturation experiments. Such a mechanism would presumably also be operative for absorption under conditions of simple immersion but would then be augmented by entrapment processes.

Another possible mechanism is that of the capillary pressure being lowered or reversed. Powers (59) refers to the reluctance of water to enter a large void from a small space. If water progressing by capillary action comes to a bulge the capillary pressure will decrease. The viscous drag retarding the flow will, however, remain almost the same. But there is a further aspect to the problem. A change in the contact angle can take place if a change in the angle of the pore walls occurs. The action has been called the "overturning" of the meniscus and was discussed by Adam (1). Unless perfect wetting takes place--and it probably seldom does for the advancing angle--a change in the angle of the pore walls can result in the contact angle becoming large, even greater than 90° . The capillary pressure therefore becomes small or reverses and the driving force causing penetration is removed or counterbalanced. Adam's (1) Figure 1 illustrates the point. The extent to which a pore space remains unfilled under vacuum saturation conditions is, according to these ideas, a measure of the extent to which these capillary pressure diminishing or reversing operations take place.

Absorptivity-Permeability Relationship

A final aspect of the absorptivity part of these experiments which remains to be discussed is the relation between the absorptivity

and the permeability. If one assumes that in both processes the flow takes place through the same pore space and is affected in the same quantitative manner by this space, the equations for the absorptivity and the permeability coefficients can be related through common factors. This was done by Powers and Brownyard (60 p. 865) in their derivation, the result of which was given as equation (25). For these rocks, the measured absorptivities and permeabilities were inserted in this equation and the resultant area was computed. The results are given in the last column of Table 9, in $\text{cm.}^2/\text{g}$. These specific surfaces are so small that they negate the equation and the assumptions it involves for these rocks. It is inconceivable that the areas of the pore walls supporting the flow are so small compared to the total area as determined by the sorption measurements.

On the other hand, if the sorption areas and the absorptivities are introduced into the equations relating K_a and K_l and these are solved for the permeability the results are much lower than the measured permeabilities. Even if account is taken of the principles of relative permeability and the results of the above calculations are called effective rather than total permeabilities, the results are still powers of ten away from the theoretical relative permeabilities.


The reason for this great disparity may be that the widenings in the pores are spaces which, according to the previously-discussed saturation mechanisms, stop or retard the capillary flow. But these spaces are, on the other hand, just those which permit the maximum of the saturated flow which takes place in a permeability experiment. These spaces, in other words, tend to give a comparatively high per-

meability and low absorptivity.

For rocks of the same general texture (and specifically for the rocks studied here) there should be a rough correspondence between the absorptivity and the permeability. Permeability measurements are difficult. They require comparatively complicated equipment. The measurement of absorptivity, on the other hand, requires (at least with the technique used here) only a few minutes and hardly any special equipment at all. For many situations, therefore, the ability to get even a rough value of the permeability from the absorptivity coefficient would be of value. The extent to which this can be done with these rocks is shown in Figure 20. The values plotted here are the so-called "p" values, i.e., the negative logarithms of the values. A tentative line has been drawn through the points in Figure 20. With the exception of the value for 47-2S the points are within a reasonable distance of this line; certainly they are close enough so that permeability values obtained in this way would be acceptable for general use.

The disparity in the case of 47-2S may be due to actual structural differences from the rest of the rocks. It should be noted that, except for the 3-1S-H-p and 47-2S samples, the absorptivity and permeability determinations were not run on the same individual pieces of rock. Any differences from piece to piece would add to the uncertainty of these points.

An illustration of the extent to which structure alters the position of points on this diagram and of the danger of generalizations is given by the point plotted for a fairly-mature cement paste of a

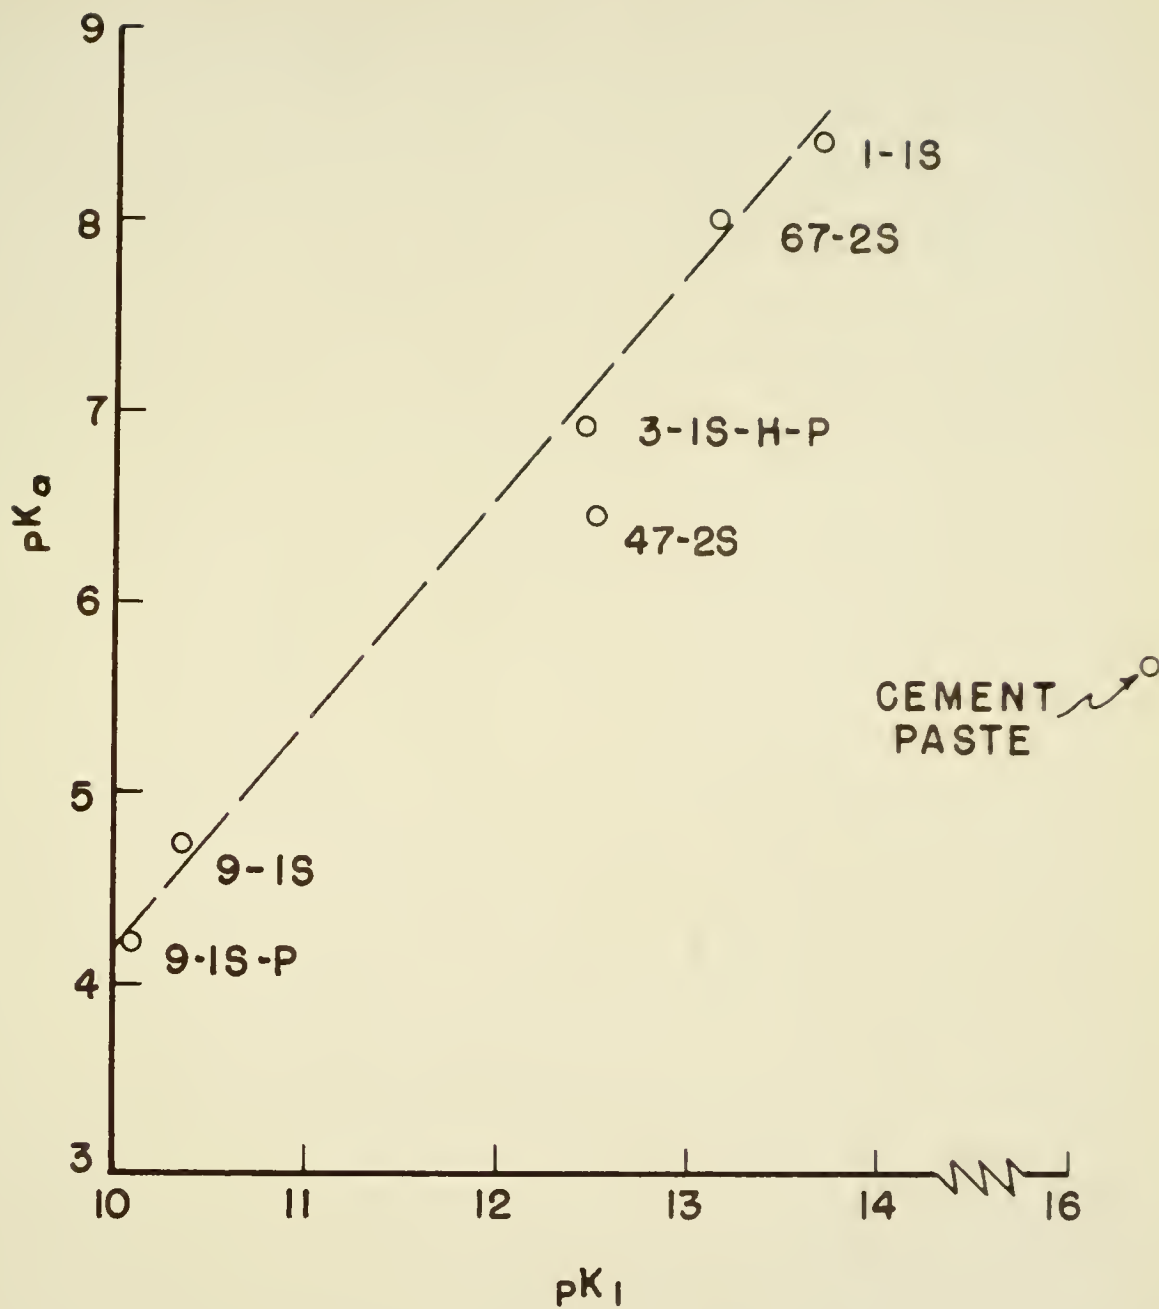FIG. 20 pK_a VS. pK_1

water-cement ratio of about 0.46 after bleeding. The absorptivity value was taken from Powers and Brownyard (60 p. 865) and the permeability from Figure 6A of Powers et al. (61). The large difference between the paste and the rocks is obvious. The permeability is only about 10^{-5} of that which a rock of this type and having the same absorptivity as the paste would have.

No advocacy for the general use of this curve is being given but it is suggested that the relation shown for these rocks is valid and perhaps a similar one exists for other types of structures. If this surmise is true, the practical advantages of the relationship are obvious.

Radii

The radii values given in Table 8 have little meaning in themselves. Their relation to durability will be taken up in the following section. They are only reflections of the porosities and specific surfaces and the comments in the following paragraphs on results of the surface area calculations apply, in a sense, to the radii also.

The fact that there are no large differences between any of these listed values should be noted. The values for 9-1S for flow parallel to the bedding planes are larger than are those for the flow perpendicular to the planes. The situation may be thought of approximately as tubes of different sizes in parallel or in series for the flow parallel and perpendicular to the laminations respectively.

The values for the slip and the permeability radii are in rough agreement as are those for the absorptivity and the sorption radii. Furthermore, the values for the slip and permeability radii are uni-

formly and, in most instances, considerably higher than are those calculated by the other two methods. This result is expectable from a consideration of the processes involved in the two pairs of cases. The slip and permeability values reflect a higher pore size because the flow of air is through a saturated medium in which the larger spaces permit the major part of the flow. The absorptivity, on the other hand, may be expected to reflect a smaller pore size since the larger spaces, by the mechanism previously discussed, deny capillary absorption of the liquid. The flow, therefore, preferentially takes place in the smaller spaces.

Specific Surfaces

With respect to the results of the specific surface calculations given in Table 9, the sorption values should be the largest, i.e., no value for surface area can, theoretically, be larger than the sorption value and be valid. The sorbate presumably contacts the entire surface of the material. Inspection of the table will show that most of the values, there being several exceptions, are smaller than the sorption values for the same rocks. In comparing the values for any one source it should be remembered that the sorption, permeability, and absorptivity runs were usually done on different individual samples. They were, to be sure, taken from adjacent pieces of the same mass but they may, nevertheless, reflect inherent, short-range variations of the material.

The values calculated from slip and permeability data show fair agreement with each other, as did the corresponding values for the radii. The essential agreement between the slip and permeability

values is interesting in view of the sensitivity of the b value (see Figure 10, for example) to changes in experimental conditions. Probably more reliance should be placed on the permeability values than on the slip values for this reason. The use of the Cornell-Katz tortuosity, τ , rather than the Wyllie-Rose k_t results in only a slight change in area values even for these rocks which have comparatively high tortuosities. No choice between the two concepts can be made on the basis of this comparison.

The slip and permeability area values are, in every case, considerably lower than the sorption values. This finding corroborates that of Brooks and Purcell (13) who obtained similar differences for sandstones.

The values for specific surface calculated from the absorptivity data and theory are larger than the values calculated from the permeabilities and they more nearly approximate the sorption areas. The absorptivity values are divided into two groups depending on the interpretation placed on the hydraulic radius. By definition, the hydraulic radius is the ratio of the capillary porosity to the area of the capillary walls, i.e., $m = \alpha/S_\alpha$. If the assumption is made that the unfilled part of the pore space has the same volume to wall-area ratio--has, that is, the same structure as the capillary-filled space--then the extrapolation can be made that $m = \epsilon/S$. The implication of such an assumption is that the barrier to capillary flow is a meniscus overturning due to angular changes in the capillary walls and not due to the occurrence of bulges or other large spaces which the liquid cannot enter by capillarity.

The data show that, saving two exceptions to be noted below, the absorptivity specific surfaces are uniformly lower than the sorption surfaces if the Wyllie-Rose tortuosities are used in the computation. No distinction as to structure can, however, be made because the data are few and there are exceptions. Other mechanisms may be operative to account for the absorptivity surfaces being smaller than the sorption surfaces. Also, since the absorptivity surfaces are inversely proportional to the absorptivity coefficients, the measurements of this property are probably not accurate enough to place great reliance on the specific surface values in the table.

They are, on the other hand, accurate enough so that it becomes necessary to account for the absorptivity surfaces being less than the sorption surfaces.

The reason probably lies in the presence of comparatively large pores which cause a higher absorptivity than is accountable to surface area. A bulge or large section in a pore will cause a retardation in the flow due to a reduction of the capillary pressure but a pore that is uniformly large will have a higher absorptivity than will a smaller one because the viscous drag is proportional to the square of the size while the capillary pressure is proportional only to the first power of the size. Until now the implication has been that the pores are approximately the same size with possible bulges here and there. But certainly some pores are larger than others throughout all their length. There are probably continuous passageways through this interconnected pore system which are larger than other possible passageways, whether or not they contain bulges. The presence of such larger

passageways negates the model to a corresponding extent and gives rise to higher absorptivities and, consequently, to lower specific surfaces when the calculation is made on the basis of the model.

The exceptions to the generalizations made concerning the various values for specific surface are the samples 3-LS-H-p and 9-LS (flow perpendicular to the laminations). All absorptivity surface area values of these two groups of data are higher than the sorption values. For the case of 9-LS (perpendicular) the reason may be that the strata composed of fine pores cut down the absorptivity so much that the resultant area value is too high. In view of this result and of the other reasons mentioned earlier, it seems preferable to run these tests with the flow parallel to any laminations.

The reasons for the results for 3-LS-H-p are not apparent. This material may be so inhomogeneous that the pieces on which the sorption values were run were greatly different from those on which the absorptivity was determined. An attempt was made to run the sorption test on the absorptivity piece but the weight of the sample was so low that a reliable sorption test could not be performed. No other statements can be made concerning the matter. Further work on this rock would be necessary to determine whether or not a real difference between it and the others exists in this respect.

The general statement can be made that, except for the case of 3-LS-H, the absorptivity method is superior to the permeability method as an interpretor of specific surface. The statement applies best to the values calculated on the $m = \epsilon/S$ basis. For three cases--9-LS-p, 47-2S, and 67-2S--there is roughly a two to one relationship between

the sorption and the absorptivity specific surfaces. The 1-LS sample is a poorer agreement. And the 3-LS-H-p sample fails.

Absorptivity methods have received little attention for the determination of the specific surface of porous solids; permeability has received a great deal. If these data are valid, however, the former holds, for consolidated media, more promise than the latter.

It was stated in connection with the values for the permeability specific surfaces that no distinction could be made between the Wyllie-Rose and the Cornell-Katz tortuosities. A distinction can, however, be made by means of the values for the absorptivity areas. The area values computed according to the Cornell-Katz tortuosity concept are listed under the symbol τ_{α} and are, in every case, higher than the sorption areas. Assuming the reasonable correctness of the model and the data, such a result tends to substantiate the Wyllie-Rose rather than the Cornell-Katz concept. The data are, of course, too few to be firm about the point.

Interpretation of Data and Results

In this section, the information presented in the Data and the Results sections are examined from the point of view of possible correlation between laboratory data and field durability of the pavement concrete that has been made with aggregate from the rock sources studied.

The standard for comparison is the field histories of the materials in Indiana experience. This is a rather general yardstick and the comparisons are correspondingly qualitative. It is true that more quantitative data are available. The original blowup survey of Woods, Sweet and Shelburne (95) contains data on blowup frequency for three of the

rocks (1-LS, 9-LS, 67-2S). Sweet's (81) tests included all of the sources used here and durability factors can be calculated from his curves. Bugg (16) and Blackburn (8) used some of these same materials and durability factors can also be calculated from their curves. But the mix designs in these three studies varied, particularly with respect to the air contents of the concrete. The durability factors show considerable variation in some cases (e.g., up to 100% differences, even for the same aggregate, same air content, and same type of saturation prior to mixing).

It was decided, therefore, for the comparisons to be made here, not to attempt to use a numerical measure of durability but merely to use the field classification in a general sense. On such a basis the pavement history of these rocks is, in order of decreasing durability, 67-2S, 1-LS, 47-2S, 3-LS-H, and 9-LS. Stones 67-2S and 1-LS are about equally good. Neither has given trouble. Source 47-2S does not seem to be as bad an offender as are materials 3-LS-H and 9-LS and its situation may be complicated by factors other than lack of resistance to simple freezing and thawing. The field cracking pattern is not the typical D-line cracking of frost damage but seems frequently to be a more general map-cracking such as is often found in connection with chemically reactive aggregates. The ASTM "quick chemical test" for alkali reactivity does not, however, show it to be reactive. The broken concrete has, nevertheless, darkened rims inside the aggregate particles and these have been diagnosed as being due to alkali-aggregate reaction (43). In spite of this, stone 47-2S has a poor rating in laboratory freezing and thawing tests when incorporated in the con-

crete with a saturation approximating the quarry-wet condition (31) and, therefore, has been rated here as poor in frost durability. Stones 3-1S-H and 9-1S have the poorest histories of all.

This study was chiefly exploratory in nature. The principle test methods used have rarely, if ever, been used on concrete aggregates. They have never been used in the Indiana studies on these materials. This work was done to investigate their promise as test methods in themselves, as tests for interpreting pore characteristics, and as tests for predicting aggregate durability with respect to frost action. The assumptions involved in the selection of samples is related to these purposes. These assumptions are stated in detail in the Experimental section. The small pieces used in these tests cannot, obviously, be statistically representative of the sources. The essence of the point is that the samples are assumed to be representative of "good" and "bad" aggregate materials even though they may differ somewhat from other material in the quarries.

This last assumption seems justified in all cases except that already noted, 3-1S-H. All the tests indicate that, contrary to field performance, these samples from source 3-1S-H are not those of a particularly poor aggregate. The tests indicate a material intermediate in performance and much better than the field history of the source. The sampling from which these pieces were taken probably was of a different material than that which was made into the pavements with the poor service record. Current tests tend to confirm this conclusion (54). They show absorptions for this batch that are much lower than those obtained on former samples from the source and that approximate

that obtained in this work. Freezing and thawing tests on concrete made with this material also show it to have superior frost resistance to that tested by former investigators. This disparity is unfortunate. The results of the tests on this rock should be interpreted in the light of the above remarks and its "bad" rating should probably be held in question here.

The various ways in which coarse aggregate can affect concrete deleteriously have been mentioned in the Review section. The field history of the source does not discriminate between these actions and the confusion this may lead to may be illustrated by the case of 47-2S, previously discussed. Nevertheless, since the laboratory freezing and thawing tests have reproduced reasonably the field histories of these materials, it will be assumed that a poor history reflects frost instability of the material in pavement concrete. Such instability often means a high blowup frequency as well, since it is thought that blowup occurrence is preceded by cracking due to some other cause.

The standard test methods applied to concrete aggregates frequently are poor as predictors of performance with respect to freezing and thawing stability. Many studies have shown that such tests as absorption, unconfined freezing and thawing, sulfate soundness, and degree of saturation do not always give the correct prediction. Enough exceptions are encountered in their interpretation so that the results of these tests cannot be used unreservedly. Extremes, of course, can usually be recognized. A limestone with half a percent absorption, 50 percent vacuum saturation, and practically no loss in the soundness tests would probably be acceptable and, conversely, rocks having the

other extremes in results would be rejected. But in the large middle ground, the line is difficult to draw. Highway specification writers, being unwilling to discriminate against possibly good material on the basis of quasi-proven tests, frequently do not use to advantage even the tests that exist.

The necessity of the aggregate piece to acquire considerable water before it can cause frost damage has been repeatedly emphasized: "The effect of an aggregate particle upon freezing and thawing durability of concrete depends largely upon the ability of the particle to attain a high degree of saturation while it is enclosed by cement (66)." "The durability of solid materials during freezing and thawing is controlled by the freedom with which they are permeated by water (11)." "Materials that contain no water are not likely to be harmed by freezing (45)." The point is obvious. Agreement is universal. But how this water gets into the piece and what happens to it, with and without freezing, is not well-understood and is the question upon which research is focused.

Perhaps a brief discussion of the history of a limestone aggregate is appropriate in order to examine the ways in which it can get, and keep, the water which is so potentially destructive.

At the time the rock is formed in the sedimentary process, a certain amount of water, the so-called connate water, is included therein. The subsequent history of the formation in general and of the small part of it which later becomes the quarry in question determines what subsequent changes in the water content will take place. The position in relation to the water table is important. The rock has,

for geologic ages, opportunity to acquire water if it is below the water table or to lose water if it is above the table. Any changes that occur in the formation which change the permeability and porosity of the mass will be important. Dolomitization, faulting, cracking, and secondary deposition in cracks, are factors which can alter these properties and can influence the water content.

When the rock is quarried it will have a certain "quarry-wet" degree of saturation which is determined by the above-mentioned factors. The rock is then crushed. Whether or not it is stockpiled prior to its use in the concrete is an important question. If it has an opportunity to dry out at this point the frost durability of the concrete made with it can be materially improved. Conversely, if it is unprotected from the rain it can become even wetter.

The aggregate is then mixed with the other components of the concrete and, restricting the discussion to pavement concrete, the slab is laid. One of these components of concrete is, of course, water. While the mixture is plastic an opportunity exists for the aggregate to pick up water. Once the initial set has taken place, the aggregate must compete with the surrounding paste for any water it gets. The matter becomes more complicated. During the period when the cement is hydrating comparatively rapidly a self-dessication of the paste occurs. Water in what are to become the capillary pores is withdrawn into the gel to continue the hydration process. Even effective curing methods apparently cannot prevent this self-dessication of the paste and it is reasonable to suppose that water can be withdrawn from the aggregate as well at this time.

If, at this stage of the process, the stone is saturated to a dangerous extent and freezing occurs, disruption can start at once. A much more common situation, however, is for the pavement to give service for a number of years and for the damage to become apparent only after some time. After symptoms begin to appear the condition of the pavement becomes progressively worse until it is unserviceable. Mechanisms for the acquisition of water must, therefore, take this time element into account.

If the surrounding paste forms a perfect seal, the aggregate piece can obtain water only by capillary attraction from the paste. Various reviewers have discussed this aspect of the matter (11, 59, 66). The basic consideration is the relative size of the pores in the paste and in the rock. If the capillary potential in the rock is higher than that of the paste at the degree of saturation in question, the rock will extract water from the paste and vice versa. Powers (59) stated that the pores in most rocks were larger than those in the paste and that, therefore, the rock could acquire water by capillarity only if the paste were saturated. He apparently based his statement on permeability measurements of pastes and various rocks (61). Blanks (11) reported measurements on rocks and on concrete using an apparatus which measured the capillary pressure of the smallest section of the largest continuous pore through the sample. The capillary pressures were then converted to the equivalent radii of round pores. His results showed certain argillaceous limestones to have a "pore size" smaller than those of the concrete specimens tested. He concluded that water could, therefore, move by capillarity from the paste into

the aggregate particles.

The situation has other aspects. Powers' (58) extensive studies on hardened cement paste have shown that the capillary pores in a paste are, for normal water-cement ratios, discrete void spaces and that only at comparatively high water-cement ratios do they link up to form a connecting network. Paving mixes are stiff enough to fall into the category of "normal water-cement ratios." If this picture is accurate, an aggregate particle enclosed in a perfect paste would be surrounded by a gel structure which would contain isolated "capillary" pore spaces whose size would be a function of the water-cement ratio but which would be, very roughly, about the same as that of the pores in most dense rocks. These capillary pores would presumably be at least partly filled with water. So would the pores in the rock. But the two kinds of pores would be separated by a gel whose characteristic pores are only a few times the size of a water molecule and whose permeability is exceedingly small. The permeability of a paste which has no capillary pores (w/c about 0.35), i.e., the permeability of the gel alone, has been determined (61) to be in the neighborhood of 10^{-6} md. This is the material that water would have to traverse in moving between rock pores and paste capillaries. If the paste capillaries were not saturated the driving force for water movement would be the difference in capillary pressure between the capillaries and the rock pores. Under these conditions, the two kinds of pores being even approximately equal in size, the flow of water would be vanishingly small. The maximum flow would take place when the paste capillaries were saturated and could remain so by acquisition of water

from an outside source. Even in this circumstance, the flow would still be small. For a slab, however, that is situated on a poorly-drained subgrade and whose underside is continually wet, saturation of the aggregate particles by this mechanism would be possible. It would take a long time. Whether or not this mechanism is principally responsible for the long-time aspects of frost damage is a question that cannot be answered now; but it is a possibility.

The "perfect paste" that has just been discussed is hardly ever a reality. A number of things can and do happen which destroy its ability to seal the aggregate effectively. The webs of gel which separate the paste capillary pores from each other and, presumably, also the aggregate from the capillaries, may be broken by drying shrinkage. Powers et al. (61) found large increases in the permeability of a paste upon drying it to equilibrium with about eighty percent humidity. He postulated cracking of these webs to account for his results. Such cracking would tend materially to decrease the barrier to the flow of water between the aggregate pores and the paste capillaries. During the early stages of hydration, bleeding channels are formed throughout the mass. Spaces appear under aggregate particles due to settling of the materials, particularly for the case of flat particles. Spaces may occur at the surfaces of aggregate particles due to poor adhesion, and imperfect consolidation of the concrete can leave a variety of spaces in its interior. Many of these spaces would act as macropores which would be difficult to fill by capillarity. But others, particularly the micro gel cracks and any channels leading from an outside surface into the interior of the slab might facilitate the entrance of water

into the mass and thereby, into the aggregate particles.

Another process, which may be important in admitting water to the interior of the concrete, is paste failure due either to frost action or to wetting and drying. If the paste capillaries become saturated, and particularly if properly-spaced entrained-air bubbles are absent, the paste can dilate and crack upon freezing. The mechanisms of this action have been listed in the Review section. Since the gel swells and shrinks on wetting and drying, it is reasonable to assume that cracking can result from this action as well. Either kind of damage would open the concrete and aggregate to easier invasion by water.

These mechanisms could also be augmented by failure of the aggregate pieces and the surrounding mortar due to chemical or thermal instability of the rock. Cracking due to overloading is not considered as a lack of durability but could, of course, augment the destructive processes that have been outlined.

All these actions tend to open the concrete to penetration by water and to make the acquisition of this water by the aggregate easier. Many of these processes are long-time in their nature and may help to account for the interval that frequently takes place before overt frost damage appears.

Once the aggregate became saturated to a critical degree and began to cause freezing-and-thawing dilation and failure, the situation would become progressively worse. Damage would cause more damage until the slab could no longer perform its structural job.

Entrained air helps the situation in, presumably, two ways. One way, probably the more important, is to protect the paste from frost

damage and so to permit it to seal the aggregate more effectively. The other is to provide, in the form of air voids adjacent to the aggregate, a certain amount of space into which water forced out of a saturated piece by progressive freezing could move. Whatever the mechanism, studies have shown that the use of air-entraining cement helps the frost durability of these materials.

However the water may enter the mass, whether by any or all of the mechanisms outlined, its acquisition and retention by the aggregate is probably fundamental to any freezing-and-thawing instability of the concrete which is caused by the aggregate. Emphasis should, and will, be given this aspect of the problem. Powers (59) stated the proposition clearly - - ". . . a principal difference among different kinds of rock particles is the rate at which they become saturated when given free access to water."

Still another possible mechanism for disintegration is fatigue cracking from repeated freezing. Although any one stress application would not cause rupture, the fatigue effect might eventually cause a crack. This process would also take a long time but might not necessitate such high aggregate saturations.

The data reported here on porosity, absorption, and saturation can add little to previous work on these properties of these materials. Sweet (81) found the materials with good durability to be characterized by a voids ratio for voids smaller than 5μ in diameter of less than 0.06. This value corresponds to a porosity of about 0.057 so by this criterion any rock whose total porosity was less than this amount would, perforce, be a durable one. Other things being equal, the

higher the porosity the poorer the freezing and thawing prospects for the material, but the danger of such generalizations is shown by the example cited by Rhoades and Mielenz (66) of a volcanic material with an absorption of almost 25 percent which had, in concrete, a comparatively good freezing and thawing record.

There is an absolute lower limit to the conceivably harmful porosity below which, even if saturated, the rock can elastically accommodate any volume increase on freezing. Most sedimentary rocks probably have porosities higher than this minimum value.

The only serious departures of the data from previous values are for the case of the sample of 3-1S-H stone. The values (Table 3) of around 45 and 71 percent saturation for the immersed and evacuated conditions respectively are much lower than, for instance, Sweet's (81) values of about 80 and 90 percent. This is a clear indication of the statement made at the beginning of this section that the material used in this work from this source does not represent a bad aggregate.

Although the absolute critical saturation value for aggregate particles is about 91 percent, the practical value, for reasons mentioned in the Review section, is probably somewhat lower—around 85 percent perhaps. But this saturation is that of the particle in the concrete and the problem is to determine which, if any, of the methods of test on the aggregate alone gives an accurate indication of this value. The tendency has been to emphasize the vacuum saturation values (47) possibly on the pragmatic grounds that this is almost invariably the only method by means of which saturations in the high and critical region are obtained. An inspection of the appropriate tables (3 and 7)

will show that in no case was the 24-hr. immersion or the absorptivity saturation value high enough to be critical. The quarry-wet saturation can, however, be much higher than these capillary absorption values, since geologic time has been available for the entrance of water.

An interesting observation, which has a bearing on the question of the rate at which these materials absorb water, can be made by comparing the values for the saturations obtained in the resistivity experiments, S_{we} (Table 4), with those for the immersed and evacuated conditions (Table 3). The resistivity saturations, as previously described, were run by vacuum saturating the material but letting it soak for only an hour or so rather than the 23-hr. period of the usual vacuum technique. (3-1S-H is an exception. It was allowed to go the full 24-hr. period because both values were being obtained simultaneously.) The good materials (1-1S, 67-2S) had not attained, in spite of the evacuation, even their 24-hr. immersion values while the poor materials (9-1S, 47-2S) had attained saturations approximately equal to those of the usual vacuum method. The marked reluctance, evacuation notwithstanding, of the good materials to pick up the liquid is obvious.

Tortuosity apparently has nothing to do, per se, with the question of the durability of the materials. Even if the very high value for 1-1S is disregarded the others show no recognizable relation to the quality of the stones.

The results of the sorption specific surface determinations confirm the findings of Blaine, Hunt and Tomes (10) that the materials

with poor durability have higher specific surfaces than do those with good durability. This finding is, of course, partly misleading since a comparatively high porosity will give rise to a comparatively high surface area even if the pore structure is not different in the two cases being compared.

The low result in the case of material from source 3-LS-H has already been discussed.

It should be noted that the sorption surfaces reflect durability in a qualitative sense only, e.g., the specific surface of stone 9-LS is about twice that of stone 67-2S but the durability ratio of the two materials is enormously greater.

The results of the radii calculations (Table 8) show the inadequacy of an average value of pore size (determined, at least, by any of the four methods used here) for the purpose of distinguishing between good and poor-performing aggregate materials. The table shows no discernible relation between the two properties. The inadequacy of the simple model and the complex nature of the actual pore characteristics and of their relationship to durability are particularly evident here. It seems to the writer that the capillary pressure apparatus of Blanks (11) would suffer from similar shortcomings. The value for pore size obtained with this apparatus is that of a round tube which has a capillary pressure equal to that at the smallest opening in the largest continuous passageway through the material. Such a value is rather arbitrary but Blanks nevertheless obtained pore size values which were not only reflections of durability but conformed, more or less, to the 5μ diameter dividing line which has become semi-conventional.

Probably experiments, such as those with the mercury porosimeter, which give data showing the distribution of pore volume according to size would be more valuable than average-value techniques. Expense and complexity are disadvantages to the mercury porosimeter but its use with concrete aggregate materials is clearly desirable.

The values for the absorptivity and permeability coefficients show promise with respect to correlation with durability. An examination of Tables 6 and 7 will show that for both these coefficients the good aggregates (1-LS, 67-2S) have the smallest values, the bad-but-intermediate ones (3-LS-H, 47-2S) have intermediate values, and the worst material (9-LS) has the largest value. These three groups are, furthermore, distinct from each other, the values, for the most part, being separated by powers of ten. A comparatively high absorptivity means a comparatively high rate of water absorption for the material in question and this, in turn, should mean a correspondingly low durability. But beyond a certain minimum absorption, the degree of saturation may be more important than the overall absorption. For instance, a material could have a high absorption but if this amount of water filled only half the pore space the material would probably be durable in freezing-and-thawing action. The rate at which the saturation changes might, therefore, give insight concerning the comparative durability of the materials. This matter was evaluated by dividing the square root of the absorptivity coefficient by the appropriate porosity (ϵ or α). The square root of the absorptivity is the volume (cm.³) of water that would enter a cube 1 cm. on a side in 1 sec. The bulk volume of this cube would be 1 cm.³ and the pore volume would

therefore be ϵ or α cm.³, depending on whether the total or "capillary" porosity was being used. The ratio of $K_a^{\frac{1}{2}}$ to the porosity is therefore the degree of saturation at 1 sec. for this unit cube. The values so computed are listed in Table 10 and are called the "unit saturations."

Table 10
Unit Saturations

Source No.	$K_a^{\frac{1}{2}}/\epsilon$	$K_a^{\frac{1}{2}}/\alpha$
1-1S	0.00248	0.00576
3-1S-H-p	0.00348	0.00578
9-1S	0.0176	0.0241
9-1S-p	0.0320	0.0475
47-2S	0.00764	0.0125
67-2S	0.00429	0.00775

The values have no meaning in themselves. On a comparative basis, they reflect the respective durability histories rather well with the high values indicating low durability and vice versa. Again the exception is 3-1S-H; it has dropped down to a position near the good aggregates which may well be where it belongs as far as these samples are concerned. Preference between the use of ϵ or α in this connection is a moot point.

A high absorptivity is, by the nature of things, associated with a high permeability. Figure 20 shows this general relationship. However, within the framework of the absorptivity and capillary properties

of the material, a high permeability is preferable. An indication of the magnitude of a relationship of this sort is given by the ratios of K_a to K_1 which are tabulated in Table 11.

Table 11
Absorptivity-Permeability Ratios

Source No.	$(10^{-5})K_a/K_1$
1-1S	1.85
3-1S-H-p	3.44
9-1S	4.30
9-1S-p	7.45
47-2S	10.2
67-2S	1.39

The values used in computing these ratios are the ones which were plotted on Figure 20. The statement made earlier that, while a general relationship between K_a and K_1 might exist for these materials, the small differences therein might be important, begins to have meaning. With these ratios a distinction is possible on the basis of the durability histories with the poor materials having higher values for the ratio than do the more durable materials. (In Tables 10 and 11 the values for 9-1S perpendicular (i.e., no "p" after the source number) have been included for the sake of completeness but have been ignored in the assessments because of the previously-stated preference for data from parallel flow experiments.) The value for 47-2S is too high when it is compared with that for 9-1S in the light of their relative

durabilities. The approximate reflection by these K_a/K_1 ratios of the relative durability of the materials is in conformity with general theoretical expectations. The higher the absorptivity and the lower the permeability, i.e., the larger their ratio, the less durable would a rock be expected to be in concrete because it would tend to gain water relatively rapidly but would present a comparatively high obstruction to its movement on freezing. The case for the more durable materials would be the converse.

Whether these ratios have any usefulness in describing the pore structure of these materials is an interesting possibility. If the material had bulges in the pore system and these bulges were responsible for the limitation of capillary absorption, the material would tend to have a comparatively high permeability for its absorptivity, i.e., a low value of the K_a/K_1 ratio. It would also have a comparatively low capillary saturation. The data on the rocks 1-1S and 67-2S fit this picture. 1-1S has some voids which are large enough to be visible to the naked eye and might, therefore, tend to fit such a "bulge" theory. But 67-2S is a dense, fine-grained stone with no apparent macropores. The fact that they cannot be seen does not, of course, prove them to be absent.

If the material did not have bulges it would have a relatively lower permeability and, therefore, a higher ratio of K_a to K_1 . Mercury porosimeter hysteresis data would be necessary to prove the point.

Whether or not the values in Tables 10 and 11 have any real relation to durability or structure, the measured values that were used in their calculation are felt to be accurate enough so that the differ-

ences between the values for the various rocks (with respect to the durability interpretation) are real rather than apparent.

SUMMARY OF RESULTS

The following is a recapitulation of the major findings of this study:

1. The use of the volumenometer and McLeod gage porosimeter techniques gave values for the true and bulk densities which were precise and were consistent. In the case of the bulk densities, the computed values compared favorably with those obtained by measurement of the sample dimensions.
2. The electrical analog values for the tortuosity of the rocks ranged from 10 to 384. This latter value is unusually high and its measurement was difficult. The next highest value was 65. No apparent relation was found between the durability histories of the materials and their tortuosities.
3. The specific surfaces of the rocks, as determined by the sorption method and the BET theory, ranged approximately from 0.7 to 2.5 m.²/g. The poor materials had the higher specific surfaces but the differences were only qualitative. The sorption data followed the BET theory at the low humidities used. The C values of the BET equation were too low to permit the use of one-point approximation methods.
4. The values for the permeability of the rocks ranged approximately from 0.002 to 8 md. A fair distinction could be made between the rocks with good, poor, and bad durability records on the basis of their permeability values. The permeability data corresponded to the Klinkenberg slip theory in all cases but the slip (b) factors bore no relation to the durability histories. A few tests at low mean pressures

advanced the possibility of simplifying the test procedure considerably with relatively little sacrifice in precision. In the case of one of the laminated rocks the permeability parallel to the laminations was roughly twice that perpendicular to them.

5. The absorptivity test method was found to be simple and reliable. An equation was developed which relates the absorptivity coefficient to the pore characteristics of a model. The data show agreement with theoretical expectations. The absorptivity values for the rocks ranged from 4×10^{-9} to 6×10^{-5} cm.²/sec. The values for the good, poor, and bad materials were separated by order of magnitude differences, the good materials having the lower absorptivities. The saturations obtained in the absorptivity runs were in rough agreement with the 24-hr. immersion values.

6. The pore radii of the rocks calculated from the slip and permeability theories were in rough agreement with each other and were larger than those calculated from the absorptivity theory. The latter values approximated those calculated from the sorption specific surfaces and the porosities. The values from the saturated flow experiments ranged from 0.2 to 1.7 μ and those from the absorptivity experiments from 0.01 to 0.2 μ . There was no relationship between the durability histories of the rocks and their average pore radii calculated by any of the four methods.

7. The specific surfaces calculated from the slip and the permeability theories were much lower than the sorption surfaces. The absorptivity surfaces were lower than the sorption surfaces also but the agreement was considerably better than was that for the saturated

flow methods. For the cases of materials 3-LS-H and 9-LS (perpendicular flow) the absorptivity surfaces were higher than the sorption surfaces. The absorptivity surfaces, calculated for just the capillary-penetrated portion of the structure, were higher than the sorption surfaces in every case when the Cornell-Katz tortuosity was used rather than the Wyllie-Rose tortuosity. The specific surfaces calculated from the Powers and Brownyard equation relating absorptivity and permeability were extremely low, about a thousandth of the sorption surface values.

8. A fairly-good empirical relationship was found between the absorptivity and permeability of the rocks when plotted as the negative logarithms of the values and to a linear scale. The values for the rocks on this basis were many orders of magnitude different from a value for hardened cement paste which was obtained from the literature.

9. The ratios of the absorptivity to the permeability ranged from about 10^5 to 10^6 and permitted a good distinction between the materials with good and bad service records. The ratio was higher for the poor materials if allowance is made for the probable differences between this 3-LS-H sample and the durability history of the source.

10. The unit saturations by absorptivity, i.e., the saturations a 1 cm. cube would have after 1 sec. of exposure, ranged from about 0.002 to 0.03 and showed a clear relation to the durability histories, being higher for the poor materials (with the same qualification concerning 3-LS-H).

11. When the absorptivity test was performed on a reef rock with a very open structure, the results failed to follow the theoretical expectations.

CONCLUSIONS

Based on the results of this study, the following conclusions seem reasonable. The parts of them which apply to the materials tested can logically be expected to apply only to other materials of the same type. The results on the reef rock (Appendix F) illustrate this restriction.

1. The rate of saturation of the material, as measured by the "unit saturation," is a comparative index of the frost durability of pavement concrete made with the aggregate. The less durable materials have comparatively high "unit saturations."

2. Although more porous materials naturally have higher absorptivities and permeabilities than do less porous materials, the ratio of the absorptivity to the permeability is an index of the frost durability of pavement concrete made with the aggregate. The less durable materials have a comparatively high ratio.

3. Specific surface is a fair indication of frost durability. The less durable materials have a comparatively high specific surface.

4. The method used to determine the absorptivity coefficient is simple and reliable. For rocks of this type a general relationship exists between the absorptivity and the permeability coefficients. This relationship is sufficiently exact to justify the process of the rough determination of permeability by making absorptivity measurements, especially considering the experimental ease of the latter method compared with the difficulty of the former.

5. Absorptivity methods are considerably better than permeability methods for the determination of the specific surface of sedimentary rocks. Nevertheless, the use of the absorptivity method may be expected to give values which are lower than the total internal surface.

6. The use of the gas-compression volumenometer and of the McLeod gage porosimeter have attractive features which recommend their further applications to aggregate materials for the purpose of determining densities and porosity.

7. The use of one-point approximation methods in the sorption determination (with water vapor) of specific surface is inaccurate for this kind of substance.

8. The tortuosity of a rock has no direct relation to the durability of the rock as a concrete aggregate.

9. No distinction can be made between stones with good and poor durability characteristics on the basis of average pore radii, when a comparatively simple capillary model is used to interpret the results of fluid flow experiments.

RECOMMENDATIONS

The following are general proposals which seem desirable to amplify and extend this study.

An obvious extension, which is the result of a defect in this study, is the procurement and testing of better samples of 3-LS-H. Samples should be obtained from the more absorptive ledges to see if their properties fit the proper place in the general correlations with durability.

The stone from source 47-23 should be further investigated with respect to its chemical reactivity. This subject was mentioned in the Discussion. Particularly, the acid-insoluble residue of this rock should be examined for the presence of expansive clay minerals. The nature of the darkened rims inside the aggregate pieces should be investigated to determine what possible harmful reactions are taking place.

The feasibility of determining the permeability-slip curve by a single low-pressure run should be determined. The present results are inconclusive and such a procedure would represent a considerable saving in time.

More materials should be studied to amplify the results obtained here. Sampling should be more representative and concurrently-gathered material should be made into concrete whose durability should be determined by standard procedures. The comparison of results could then be made in terms of durability factor or some other quantitative measure of performance.

Rates of absorption and saturation should be studied by means of the standard tests for these properties. These methods have the advantage of using a large sample which does not require shaping. Valuable information might be easily obtained from such a program.

The question of the degree of saturation and the failure to obtain complete saturation should be studied. Two possible approaches are 1) using large pressures to overcome any capillary pressure reversals (some work along these lines has already been done) and 2) evacuating the sample on a pump, saturating it with ammonia, and admitting water to see what degree of saturation would result.

Mercury porosimeter data should be obtained for aggregates in order to relate pore-size distribution and other structural factors to frost susceptibility. Such an investigation offers great promise. Work should be done, if possible, to devise a simpler method for the determination of pore-size distribution. All current methods have disadvantages.

BIBLIOGRAPHY

1. Adam, N. K., "Principles of Penetration of Liquids Into Solids," Discussions Faraday Soc. No. 3, 5 (1948).
2. Arnell, J. C., "Permeability Studies. I. Surface Area Measurements Using a Modified Kozeny Equation," Can. J. Research A 24, 103 (1946).
3. Arnell, J. C., "Permeability Studies. II. Surface Area Measurements of Inorganic Pigment Powders," Can. J. Research A 25, 191 (1947).
4. A.S.T.M., "Standard Method of Test for Specific Gravity of Soils, D854-52," Am. Soc. Testing Materials, Standards 1952, P. III, 1447.
5. Bangham, D. H. and Razouk, R. I., "The Wetting of Charcoal and the Nature of the Adsorbed Phase Formed from Saturated Vapors," Trans. Faraday Soc. 33, 1463 (1937).
6. Barrer, R. M., "Fluid Flow in Porous Media," Discussions Faraday Soc. No. 3, 61 (1948).
7. Birks, J., "An Evaporation Method for Measuring the Resistivity-Water Saturation Characteristics of Cores," J. Inst. Petroleum 40, 14 (1954).
8. Blackburn, J. B., "Freeze and Thaw Durability of Air-Entrained Concrete Using Indiana Aggregates," Highway Research Board, Proc. 28, 171 (1948).
9. Blackburn, J. B., "A Study of Variability in Concrete Freeze-Thaw Test Data," Thesis, Purdue University, 1955.
10. Blaine, R. L., Hunt, C. E., and Tomes, L. A., "Use of Internal Surface Area Measurements in Research on Freezing and Thawing of Materials," Highway Research Board, Proc. 32, 293 (1953).
11. Blanks, R. F., "Modern Concepts Applied to Concrete Aggregates," Proc. Am. Soc. Civil Engrs. 75, 441 (1949).
12. Bonillas, W. K., "Evaluating Low-Permeability Cores," Petroleum Engr. 26, No. 7, B65 (1954).
13. Brooks, C. S., and Purcell, W. R., "Surface Area Measurements on Sedimentary Rocks," J. Petroleum Technol. 4, 289 (1952).
14. Brunauer, S., "The Adsorption of Gases and Vapors. Vol. I. Physical Adsorption," Princeton University Press, Princeton, N.J., 1943.

15. Brunauer, S., Emmett, P. H., and Teller, E., "Adsorption of Gases in Multimolecular Layers," J. Am. Chem. Soc. 60, 309 (1938).
16. Bugg, S. L., "Effect of Air Entrainment on the Durability Characteristics of Concrete Aggregates," Highway Research Board, Proc. 27, 156 (1947).
17. Burdine, N. T., Gournay, L. S., and Reichertz, P. P., "Pore Size Distribution of Petroleum Reservoir Rocks," J. Petroleum Technol. 2, 195 (1950).
18. Carman, P. C., Trans. Inst. Chem. Engrs. (London) 15, 150 (1937).
19. Carman, P. C., "Permeability of Saturated Sands, Soils, and Clays," J. Agr. Sci. 29, 262 (1939).
20. Carman, P. C., "Some Physical Aspects of Water Flow in Porous Media," Discussions Faraday Soc. No. 3, 72 (1948).
21. Cook, H. K., "Permeability Tests of Lean Mass Concrete," Am. Soc. Testing Materials, Proc. 51, 1156 (1951).
22. Cornell, D. and Katz, D. L., "Flow of Gases Through Consolidated Porous Media," Ind. Eng. Chem. 45, 2145 (1953).
23. Dolch, W. L., "Solubility Studies of Indiana Limestone," Thesis, Purdue University, 1949.
24. Eley, D. D. and Pepper, D. C., "A Dynamical Determination of Adhesion Tension," Trans. Faraday Soc. 42, 697 (1946).
25. Ergun, S., "Determination of Geometric Surface Area of Crushed Porous Solids," Anal. Chem. 24, 388 (1952).
26. Fancher, G. H., Lewis, J. A., and Barnes, K. B., "Some Physical Characteristics of Oil Sands," Penn. State Coll. Mineral Ind. Exp. Sta., Bull. No. 12, 65 (1933).
27. Faris, S. R., Gournay, L. S., Lipsom, L. B., and Webb, T. S., "Verification of Tortuosity Equations," Bull. Am. Assoc. Petroleum Geol. 38, 2226 (1954).
28. Fears, F. K., "Determination of the Pore Size of Four Indiana Limestones," Thesis, Purdue University, 1950.
29. Foster, A. G., "Pore Size and Pore Distribution," Discussions Faraday Soc. No. 3, 41 (1948).
30. Fox, R. G. Jr. and Dolch, W. L., "A Technique for the Determination of a Thermal Characteristic of Stone," Highway Research Board, Proc. 30, 180 (1950).

31. Gleysteen, L. F. and Kalousek, G. L., "Simplified Method for the Determination of Apparent Surface Area of Concrete Products," Proc. Am. Concrete Inst. 51, 437 (1955).
32. Heid, J. G., McMahon, J. J., Nielsen, R. F., and Yuster, S. T., "Study of the Permeability of Rocks to Homogeneous Fluids," Am. Petroleum Inst., Drilling and Production Practice, (1950).
33. Hodgman, C. D., ed., "Handbook of Chemistry and Physics," 30th. ed., Chemical Rubber Publishing Co., Cleveland, Ohio, 1947.
34. Howe, J. A., "The Geology of Building Stones," Edward Arnold, London, 1910.
35. Johansen, R. T., Lorenz, P. B., Dodd, C. G., Pidgeon, F. D., and Davis, J. W., "The Permeation of Water and Isooctane Through Plugs of Microscopic Particles of Crushed Quartz," J. Phys. Chem. 57, 40 (1953).
36. Jones, F. E., "The Physical Structure of Cement Products and Its Effect on Durability," Proc. 3rd. Intern. Symposium on the Chem. of Cement (London), 368 (1952).
37. Jones, J. C., "The Relation of Hardness of Brick to Their Resistance to Frost," Trans. Am. Ceram. Soc. 9, 528 (1907).
38. Kamack, H. J., "Simple Air-Permeability Method for Measuring Surface Areas of Fine Powders," Anal. Chem. 26, 1623 (1954).
39. Katz, M. J., "An Explicit Function for Specific Surface Area," Anal. Chem. 26, 734 (1954).
40. Klinkenberg, L. J., "The Permeability of Porous Media to Liquids and Gases," Am. Petroleum Inst., Drilling and Production Practice, 200 (1941).
41. Kreuger, H., "Investigations of Climatic Action on the Exteriors of Buildings," Trans. Roy. Swedish Inst. Sci. Ind. Research, No. 24 (1923).
42. Lambe, T. W., "Soil Testing for Engineers," John Wiley and Sons, New York, 1951.
43. Lewis, D. W., personal communication.
44. Lewis, D. W. and Dolch, W. L., "Porosity and Absorption," Am. Soc. Testing Materials, Special Tech. Pub. No. 169, 1955.
45. Lewis, D. W., Dolch, W. L., and Woods, K. B., "Porosity Determinations and the Significance of Pore Characteristics of Aggregates," Am. Soc. Testing Materials, Proc. 53, 949 (1953).

46. Lewis, D. W. and Venters, E., "Deleterious Constituents of Indiana Gravels," Highway Research Board, Bull. 94, 1954.
47. Lewis, D. W. and Woods, K. B., "Research as Related to the Development of Aggregate Specifications," Purdue University, Engrng. Expt. Sta., Reprint No. 51 (1950).
48. Loeb, L. B., "The Kinetic Theory of Gases," 2nd. ed., Chap VII, McGraw-Hill Book Co., New York, 1934.
49. Lu, N. Y., "Comparison of the Thermal and Moisture Expansion of Concrete and Stone," Thesis, Purdue University, 1947.
50. Madgwick, E., "Some Properties of Porous Building Materials. I. The Absolute Porosity and Saturation Coefficient," Phil. Mag. 12, 1155 (1931).
51. Madgwick, E., "II. The Flow of Air Through Porous Bodies," Phil. Mag. 12, 1160 (1931).
52. Madgwick, E., "III. A Theory of the Absorption and Transmission of Water by Porous Bodies," Phil. Mag. 13, 632 (1932).
53. Madgwick, E., "IV. The Determination of the Absorption Constants of a Homogeneous Specimen," Phil. Mag. 13, 641 (1932).
54. McLaughlin, J. F., personal communication.
55. Muskat, M., "The Flow of Homogeneous Fluids Through Porous Media," J. W. Edwards, Inc., Ann Arbor, Mich., 1946.
56. Perry, J. H., ed., "Chemical Engineers' Handbook," 2nd. ed., McGraw-Hill Book Co., New York, 1941.
57. Powers, T. C., "A Working Hypothesis for Further Studies of Frost Resistance of Concrete," Proc. Am. Concrete Inst. 41, 249 (1945).
58. Powers, T. C., Discussion, Proc. 3rd. Intern. Symposium on the Chem. of Cement (London), 425 (1952).
59. Powers, T. C., "Basic Considerations Pertaining to Freezing-and-Thawing Tests," To be published by Am. Soc. Testing Materials.
60. Powers, T. C. and Brownyard, T. L., "Studies of the Physical Properties of Hardened Portland Cement Paste," Proc. Am. Concrete Inst. 43, 101, 249, 469, 549, 669, 845, 865, 933, 971 (1947).
61. Powers, T. C., Copeland, L. E., Hayes, J. C., and Mann, H. M., "The Permeability of Portland Cement Paste," J. Am. Concrete Inst. 26, 285 (1954).

62. Powers, T. C. and Helmut, R. A., "Theory of Volume Changes in Hardened Portland Cement Paste During Freezing," Highway Research Board, Proc. 32, 285 (1953).
63. Purcell, W. R., "Capillary Pressures--Their Measurement Using Mercury and the Calculation of Permeability Therefrom," J. Petroleum Technol. 1, 39 (1949).
64. Razouk, R. I., General Discussion, Discussions Faraday Soc., No. 3, 119 (1948).
65. Reilly, J. and Rae, W. R., "Physico-Chemical Methods," Vol. I., 5th. ed., Chap. XII (Section 2), D. Van. Nostrand Co., New York, 1953.
66. Rhoades, R. and Mielenz, R. C. "Petrography of Concrete Aggregate," Proc. Am. Concrete Inst. 42, 581 (1946).
67. Rhoades, R. and Mielenz, R. C., "Petrographic and Mineralogic Characteristics of Aggregates," Am. Soc. Testing Materials, Special Techn. Pub. No. 83, 20 (1948).
68. Rideal, E. K., "On the Flow of Liquids Under Capillary Pressure," Phil. Mag. 44, 1152 (1922).
69. Rigden, P. J., "The Rheology of Non-Aqueous Suspensions," Dept. Sci. Ind. Research, Road Research Paper No. 28, H.M.S.O., London, 1954.
70. Ruettgers, A., Vidal, E. N., and Wing, S. P., "An Investigation of the Permeability of Mass Concrete with Particular Reference to Boulder Dam," Proc. Am. Concrete Inst. 31, 382 (1935).
71. Schaffer, R. J., "The Weathering of Natural Building Stones," Dept. Sci. Ind. Research, Building Research Special Dept. No. 18, H.M.S.O., 1932.
72. Scheidegger, A. E., "Theoretical Models of Porous Matter," Producers Monthly 17, No. 10, 17 (1953).
73. Scheidegger, A. E., "Statistical Hydrodynamics in Porous Media," J. Appl. Phys. 25, 994 (1954).
74. Scheidegger, A. E., "General Statistical Hydrodynamics in Porous Media," Geofis. pur. e appl. 30, 17 (1955).
75. Scholer, C. H., "Significant Factors Affecting Concrete Durability," Am. Soc. Testing Materials, Proc. 52, 1145 (1952).
76. Seipp, H., "On the Theory of the Action of Frost on Natural Building Stones," Proc. 5th. Intern. Congr. Testing Materials, 1909.

77. Slate, F. O., "Chemical Reactions of Indiana Aggregate in Disintegration of Concrete," Am. Soc. Testing Materials, Proc. 49, 954 (1949).
78. Slate, F. O., "Comprehensive Bibliography of Cement and Concrete, 1925-1947," Joint Highway Research Project, Engrng. Expt. Sta., Purdue Univ., Lafayette, Indiana, 1949.
79. Sweet, H. S., "Chert as a Deleterious Constituent in Indiana Aggregates," Highway Research Board, Proc. 20, 599 (1940).
80. Sweet, H. S., "Physical and Chemical Tests of Mineral Aggregates and Their Significance," Am. Soc. Testing Materials, Special Tech. Pub. No. 83, 49 (1948).
81. Sweet, H. S., "Research on Concrete Durability as Affected by Coarse Aggregates," Am. Soc. Testing Materials, Proc. 48, 988 (1948).
82. Sweet, H. S., "Concrete Durability as Affected by Coarse Aggregates," Thesis, Purdue University, 1948.
83. Sweet, H. S. and Woods, K. B., "Mapcracking in Concrete Pavements as Influenced by Soil Textures," Highway Research Board, Proc. 26, 286 (1946).
84. Thomas, W. N., "Experiments on the Freezing of Certain Building Materials," Dept. Sci. Ind. Res., Building Research Tech. Paper No. 17, H.M.S.O., London, 1938.
85. Walker, S. and Bloem, D. L., "Performance of Automatic Freezing and Thawing Apparatus for Testing Concrete," Am. Soc. Testing Materials, Proc. 51, 1120 (1951).
86. Washburn, E. W., "The Dynamics of Capillary Flow," Phys. Rev. 17, 273 (1921).
87. Washburn, E. W., "Porosity. I. Purpose of the Investigation. II. Porosity and the Mechanism of Absorption," J. Am. Ceram. Soc. 4, 916 (1921).
88. Washburn, E. W., ed., "International Critical Tables," Vol. I, McGraw-Hill Book Co., New York, 1926.
89. Washburn, E. W. and Bunting, E. N., "Porosity. IV. The Use of Petroleum Products as Absorption Liquids," J. Am. Ceram. Soc. 4, 983 (1921).
90. Washburn, E. W. and Bunting, E. N., "Porosity. VI. Determination of Porosity by the Method of Gas Expansion," J. Am. Ceram. Soc. 5, 112 (1922).

91. Washburn, E. W. and Bunting, E. N., "Porosity. VII. The Determination of the Porosity of Highly Vitrified Bodies," J. Am. Ceram. Soc. 5, 527 (1922).
92. Washburn, E. W. and Footitt, F. F., "Porosity. III. Water as an Absorption Liquid," J. Am. Ceram. Soc. 4, 961 (1921).
93. Weissberger, A., "Physical Methods of Organic Chemistry," 2nd. ed., Part I, Vol. I, Chap. VI, Interscience Publishers, New York, 1949.
94. Winsauer, W. O., Shearin, H. M., Masson, P. H., and Williams, M., "Resistivity of Brine-Saturated Sands in Relation to Pore Geometry," Bull. Am. Assoc. Petroleum Geol. 36, 253 (1952).
95. Woods, K. B., Sweet, H. S., and Shelburne, T. E., "Pavement Blowups Correlated with Source of Coarse Aggregate," Highway Research Board, Proc. 25, 147 (1946).
96. Wray, F. N. and Lichtefeld, H. J., "The Influence of Test Methods on Moisture Absorption and Resistance of Coarse Aggregate to Freezing and Thawing," Am. Soc. Testing Materials, Proc. 40, 1007 (1940).
97. Wyllie, M. R. J. and Gregory, A. R., "Fluid Flow Through Unconsolidated Porous Aggregates. Effect of Porosity and Particle Shape on Kozeny-Carman Constants," Ind. Eng. Chem. 47, 1379 (1955).
98. Wyllie, M. R. J. and Rose, W. D., "Some Theoretical Considerations Related to the Quantitative Evaluation of the Physical Characteristics of Reservoir Rock from Electrical Log Data," J. Petroleum Technol. 2, 105 (1950).
99. Wyllie, M. R. J. and Spangler, M. B., "Application of Electrical Resistivity Measurements to Problems of Fluid Flow in Porous Media," Bull. Am. Assoc. Petroleum Geol. 36, 359 (1952).

APPENDIX A

INFLUENCE OF n ON TORTUOSITY

The purpose of this section is to show the variation in the computed value of the tortuosity due to variation in the choice of the exponent n in equation (15).

Rewriting the pertinent equations and assuming the correctness of the Wyllie-Rose expression for tortuosity,

$$F = \frac{k_t^{1/2}}{\epsilon} \quad (A1)$$

where F = formation factor for the completely saturated state

k_t = tortuosity

ϵ = porosity

and

$$I = \frac{F_e}{F} = S_w^{-n} \quad (A2)$$

where I = resistivity index

F_e = formation factor for partially saturated state

S_w = saturation

n = a constant assumed to be independent of saturation.

Eliminating I and F from these equations and solving for k_t , the result is

$$k_t = F_e^2 \epsilon^2 S_w^{2n} \quad (A3)$$

Taking the total differential of k_t with respect to n and dividing by the value for k_t , the result is

$$\frac{dk_t}{k_t} = 2(\ln S_w) dn \quad (A4)$$

which for small values of the increment becomes

$$\frac{\Delta k_t}{k_t} = 2 (\ln S_w) \Delta n \tag{A5}.$$

This is the expression for the relative variation of k_t in terms of change in n .

As an illustration, if n is assumed equal to 2 and this value is 5 percent in error, $\Delta n = 0.1$. At a saturation of 0.5 the error in k_t would then, by equation (A5), be about 14 percent. At larger saturations the error is much less, e.g., for the above conditions but $S_w = 0.8$, the error in k_t is about 4 percent. A comparatively high saturation in the resistance runs is, therefore, desirable. Reference to Table 4 shows that in two cases, 1-1S and 67-2S, the saturation was rather low. The tortuosity values for these two rocks may, therefore, be less accurate than are those for the others.

APPENDIX B

DERIVATION OF PERMEATEMETER EQUATION

The purpose of this section is the derivation of equation (19) by means of which the permeability of the samples was calculated from the measured quantities.

Keeping in mind the nature of the apparatus as shown in Figure 4, the mass of gas m on the high-pressure side of the sample at any time during the decay process is

$$m = P_h \left(V_h + \frac{h A_t}{2} \right) \rho_1 \quad (B1)$$

where P_h = pressure on the high-pressure side of the sample

V_h = volume of the apparatus on the high-pressure side of the sample when the differential manometer is at equilibrium

h = height difference on the differential manometer

A_t = internal cross-sectional area of the differential manometer tube

ρ_1 = density of the gas at unit pressure, i.e., $\rho_1 = M/RT$

where M = molecular weight

R = gas constant

T = absolute temperature.

The time rate of change of m is the mass flow rate assuming steady-state conditions. These are not, of course, steady-state conditions. Kamack (38), however, stated for a similar set of circumstances "...a negligible error is involved in assuming that the air instantly adjusts itself to the equilibrium flow rate corresponding to the pressure drop. This situation is usually referred to as a quasi-stationary state." If, then, steady-state conditions are assumed

and equation (B1) is differentiated with respect to t the result is

$$\frac{dm}{dt} = V_h \rho_l \left(\frac{dP_h}{dt} \right) + \frac{A_t \rho_l}{2} \left(\frac{h dP_h}{dt} + \frac{P_h dh}{dt} \right) \quad (B2).$$

The approach velocity at mean pressure, u_a , is given by

$$u_a = \frac{l}{A \rho_l P_m} \left(\frac{dm}{dt} \right) \quad (B3)$$

where A = approach area of the sample

P_m = mean pressure across the sample.

Substituting the value for dm/dt from equation (B3) in equation (B2) and solving for u_a , the result is

$$u_a = \frac{l}{A P_m} \left(V_h + \frac{h A_t}{2} \right) \left(\frac{dP_h}{dt} \right) + \frac{A_t P_h}{2 A P_m} \left(\frac{dh}{dt} \right) \quad (B4).$$

Specific permeability, K , for the case of gaseous flow, is defined by Muskat (55), via Darcy's law, as

$$u_a = \frac{K \Delta P}{\eta L} \quad (B5)$$

where ΔP = head loss across sample, in pressure units

η = viscosity of the gas

L = macro length of sample.

Eliminating u_a from equations (B4) and (B5) and solving for K , the result is

$$K = \frac{\eta L}{\Delta P A P_m} \left[\left(V_h + \frac{A_t h}{2} \right) \frac{dP_h}{dt} + \left(\frac{A_t P_h}{2} \right) \frac{dh}{dt} \right] \quad (B6).$$

Practically speaking, the manometric fluid is mercury so, if pressures are in cm. Hg and h is in cm., then

$$\frac{dP_h}{dt} = \frac{dh}{dt} \quad (B7)$$

if the low pressure, P_1 , is kept constant by means of the surge flask. Introducing equation (B7) and using the conversions 60 sec. = 1 min., $1 \text{ cm.}^2 = (1.013)(10^{11}) \text{ md.}$, and $(1.333)(10^4) \text{ dynes/cm.}^2 = 1 \text{ cm. Hg}$, the final result is the working formula

$$K = \frac{\eta L (1.013)(10^{11})}{\Delta P A P_m (1.333)(10^4)(60)} \left(\frac{dh}{dt} \right) \left(V_h + \frac{A_t h}{2} + \frac{A_t P_h}{2} \right) \quad (\text{B8})$$

where K is in md. and dh/dt is in cm./min.

To use this equation A_t and V_h must be determined. A_t was found by measurement with divider and scale and appropriate calculation. The determination of V_h was made by expanding the gas in the volume V_h by a known amount and measuring its pressure before and after the expansion. Assuming the gas law holds, V_h can be calculated from such data. The measurement was performed in two different ways. In the first method the sample was replaced by a rubber stopper of the same approximate dimensions. The differential manometer was removed and replaced by plugs of sealed tubing, the one for the high-pressure side being cut to the proper length so that V_h would be unchanged. The volume of the low-pressure side was then determined by measuring the linear dimensions of the various tubes involved, calculating the corresponding volumes, and adding the sum of these to that of the surge flask. Admittedly, this is an inaccurate method of obtaining this volume but the relative error in the result was probably small due to the large surge volume. Air at atmospheric pressure (measured with a room barometer) was then admitted to V_h and the bypass stopcock was closed. The low-pressure side was pumped completely out and the stopcock to pump at the surge flask was closed. The

bypass stopcock was then opened and the air in V_h expanded into the total volume. The final pressure was measured on the large manometer and the value for V_h was calculated.

The second method for determining V_h was as follows. The sample was replaced with a stopper as before. The differential manometer was left attached. With air at atmospheric pressure in V_h , and with the bypass stopcock closed, the low-pressure side of the apparatus was pumped down until a comparatively large differential was on the bypass manometer. The pumping was then stopped. The air in V_h had expanded by the small, but accurately measurable, volume $hA_t/2$. The new pressure in V_h was measured by combining the readings of the large and the differential manometers. The value of V_h was then calculated from these data. The values obtained by the two methods were 64 cm.^3 and 66 cm.^3 and their average was used as V_h .

APPENDIX C

DERIVATION OF PERMEABILITY RELATIONSHIPS

The purpose of this section is the derivation of the equations which relate the properties of the chosen model to the liquid permeability of the samples, K_1 . The result is a Kozeny-Carman equation. The method of derivation here is similar to that of Carman (19,20). The model is that previously described.

The generalized Poiseuille law for viscous flow of a fluid through a pore of complex cross section is

$$u_t = \frac{V}{t a} = \frac{m^2 \Delta P}{k_o \eta L_t} \quad (C1)$$

where u_t = true velocity in the pipe

V/t = volume flow rate in the pipe

a = area of the pipe normal to the tortuous flow direction

m = hydraulic radius of the pipe

ΔP = total head loss, in pressure units

k_o = a cross-sectional shape factor

η = viscosity of the fluid

L_t = tortuous length of the tube.

This true velocity will have a direction at some angle ϕ to the macro flow direction because the flow is tortuous. The component of the true velocity in the macro flow direction is called the streaming velocity, u_s , and is given by

$$u_s = u_t \cos\phi \quad (C2)$$

but $\cos \phi = L/L_t = l/k_t^{1/2}$ so

$$u_s = \frac{u_t}{k_t^{1/2}} \tag{C3}$$

where L = macro flow path length

k_t = tortuosity.

The flow actually takes place only through the pore space of the medium so the relation between the streaming velocity and the approach velocity, u_a , is

$$u_a = u_s \epsilon \tag{C4}$$

where ϵ = porosity.

Darcy's law, by means of which the permeability is defined, is

$$u_a = \frac{K_1 \Delta P}{\eta L} \tag{C5}$$

A combination of equations (C2), (C3), (C4), and (C5) to eliminate the velocity terms gives

$$K_1 = \frac{\epsilon m^2 L}{k_o k_t^{1/2} L_t} = \frac{\epsilon m^2}{k_o k_t} \tag{C6}$$

This is the Kozeny equation with the product $k_o k_t$ being the conventional Kozeny constant.

By a strictly analogous procedure a model of tubes with circular cross section of radius r can be analyzed. The result for such a case is

$$K_1 = \frac{\epsilon r^2}{8 k_t} \tag{C7}$$

By the use of the relationship

$$m = \frac{\epsilon}{S} = \frac{\epsilon}{S_g \rho_B} \quad (C8)$$

equation (C6) can be transformed into

$$K_1 = \frac{\epsilon^3}{k_o k_t S_g^2 \rho_B^2} \quad (C9).$$

APPENDIX D

DERIVATION OF SLIP FACTOR RELATIONSHIP

This purpose of this section is the derivation of the relationship between the Klinkenberg slip factor, b , and the pore size of a round-tube model.

Klinkenberg (40) showed that the b factor could be expressed as

$$b = \frac{4 c \ell P_m}{r} \quad (D1)$$

where ℓ = mean free path of gas at P_m

P_m = mean pressure

r = pore radius

c = a constant.

The only difficulty with the use of this formula is the interpretation of the value of c . Analysis shows it to be approximately unity but the exact value depends on an arbitrary choice of several factors.

In Klinkenberg's paper c is defined by

$$u_o = c \ell \left(\frac{du}{dr} \right) \quad (D2)$$

where u_o = slip velocity at the tube wall

du/dr = velocity gradient in the vicinity of the wall.

In Loeb's book on the kinetic theory (48) an analogous expression is given which is

$$u_o = \frac{\eta}{\phi} \left(\frac{du}{dr} \right) \quad (D3)$$

where η = viscosity of the gas

ϕ = friction coefficient of the tube sides.

Obviously then,

$$\frac{\eta}{\phi} = c \ell \quad (D4)$$

and comparison with equation (D1) shows that

$$b = \frac{4 \eta P_m}{\phi r} \quad (D5).$$

Loeb stated further that

$$\phi = \frac{P_m \rho_1^{1/2}}{\left(\frac{\pi}{2}\right)^{1/2} \left(\frac{2}{f} - 1\right)} \quad (D6)$$

where ρ_1 = gas density at unit pressure

f = fraction of the molecules randomly emitted rather than specularly reflected after striking wall.

The proper value for f is a moot question. Values from about 0.7 to 1.0 have been reported (38,48 p.239,69). Here the question is settled by assuming $f = 1$, i.e., all molecules that strike the pore wall are assumed to be re-emitted randomly.

If then f is taken as unity and the corresponding value for ϕ from equation (D6) is inserted in equation (D5) the result is

$$b = \frac{4 \left(\frac{\pi}{2}\right)^{1/2} \eta}{\rho_1^{1/2} r} \quad (D7).$$

The values for ρ_1 and η are temperature-dependent and 25 C is assumed (nearly correctly). The viscosity value for air at 25 C is 180 micropoise (56 p.790) and the equivalent molecular weight for air was taken as 28.8.

Substitution of all appropriate values in equation (D7) gives as the final result

$$b r = (1.98)(10^{-3}) \quad (13)$$

where b is in cm. Hg and r is in cm. As previously stated, the value of the product is temperature-dependent but not greatly so, i.e.,

$$\frac{d(br)}{dT} = (0.02)(10^{-3}) \text{ cm. Hg-cm./ deg.C.}$$

APPENDIX E

DERIVATION OF ABSORPTIVITY RELATIONSHIPS

The purpose of this section is the derivation of the equations which describe capillary absorption and which relate the absorp- tivity coefficient to the properties of the chosen model.

The model is that previously described with the exception that not all the pore space is postulated to be capable of being filled with water by capillarity. The "capillary porosity", i.e., the fraction of the bulk volume capable of filling by capillarity, is α . The tortuosity appropriate to this space is $k_{t\alpha}$ and its specific surface on a bulk volume basis is S_{α} , and on a weight basis $S_{w\alpha}$. When water enters this "capillary" pore space of complex shape a dynamic equilibrium is set up among the forces involved. For the case of upward capillary absorption from a free-water surface the driving force is the capillary force present at the meniscus. The retarding forces are the viscous drag and the weight of both the entering liquid and the gas being displaced. The vector sum of these forces will be equal to a residual acceleration force. This force balance is expressed mathematically by

$$\frac{a \gamma \cos\theta}{m} - \frac{k_o \eta a x}{m^2} \left(\frac{dx}{dt}\right) - \frac{k_o \eta_g (L_t - x) a}{m^2} \left(\frac{dx}{dt}\right) - a x \rho g \cos\beta - a (L_t - x) \rho_g g \cos\beta = a x \rho \left(\frac{d^2x}{dt^2}\right) \quad (E1)$$

- where a = area of capillary pores perpendicular to tortuous flow direction
- m = hydraulic radius

k_o = shape factor

x = tortuous distance the liquid has traversed in time t

L_t = tortuous length of complete flow path

η = viscosity (subscript g refers to the gas)

ρ = density (subscript g refers to the gas)

γ = surface tension of the liquid

θ = wetting angle

β = average angle of inclination of the pore from the vertical

g = gravitational acceleration.

Practically speaking, for porous systems of the sort considered here, all force terms are comparatively small except the first two in the foregoing equation — the capillary and viscous forces in the liquid. This amounts to saying that the presence of the gas, the weight of the liquid, and the force term due to acceleration can be ignored. The result is a force balance between the capillary and viscous effects for the liquid. With the further assumption that the true advancing wetting angle is zero the simplified result is

$$\gamma m = k_o \eta x \left(\frac{dx}{dt} \right) \quad (E2).$$

The volume, V , of liquid in the capillary pore space at time t is

$$V = a x \quad (E3)$$

so

$$\frac{dV}{dt} = a \left(\frac{dx}{dt} \right) \quad (E4).$$

Introducing the appropriate expressions for x and dx/dt from equations

(E3) and (E4) in equation (E2) gives

$$\gamma m = \frac{k_o \eta V}{a^2} \left(\frac{dV}{dt} \right) \quad (E5).$$

The volume of the capillary pores is aL_t . The bulk volume of the sample is AL . The ratio of the former to the latter is, by definition, the capillary porosity, i.e.,

$$\alpha = \frac{a L_t}{A L} = \frac{a k_{t\alpha}^{1/2}}{A} \quad (E6).$$

Substituting the value for a derived from this expression in equation (E5) gives

$$V dV = \frac{\gamma m \alpha^2 A^2 dt}{k_o \eta k_{t\alpha}} \quad (E7).$$

When this equation is solved and the initial condition of $V = 0$ for $t = 0$ is inserted the result is

$$\frac{V^2}{A^2} = \frac{2 \gamma m \alpha^2 t}{k_o \eta k_{t\alpha}} \quad (E8).$$

The absorptivity coefficient, K_a , is defined (50 p.365) by

$$\frac{V^2}{A^2} = K_a t \quad (E9)$$

so therefore

$$K_a = \frac{2 \gamma m \alpha^2}{k_o k_{t\alpha} \eta} \quad (E10).$$

For a system of round tubes equation (E10) becomes

$$K_a = \frac{r \gamma \alpha^2}{2 \eta k_{t\alpha}} \quad (E11).$$

The only further question with regard to equation (E10) is

the relation of the hydraulic radius m to the specific surface of the porous material. Since m is the ratio of the capillary porosity to the corresponding wetted area, i.e.,

$$m = \frac{\alpha}{S_{\alpha}} \quad (E12)$$

then

$$S_{g\alpha} = \frac{2 \gamma \alpha^3}{k_o k_{t\alpha} K_a \eta \rho_B} \quad (E13)$$

If, however, the non-capillary porosity is the same structurally as the capillary porosity then $\alpha/S_{\alpha} = \epsilon/S$ and

$$S_g = \frac{2 \gamma \epsilon \alpha^2}{k_o k_{t\alpha} K_a \eta \rho_B} \quad (E14)$$

where S_g = total specific surface, weight basis.

This distinction is referred to further in the Discussion section.

APPENDIX F

REEF ROCK DATA

The purpose of this section is to show the effect on some of the test results of varying the rock type drastically. The statement was frequently made in the text that the model and conclusions applied only to the general type of rocks used in this study. These were the fine-grained, intergranular type which have no large pores -- only 1-LS has some that are visible to the eye and these are still small in comparison with the large pores referred to in this section.

In order to be able to indicate the effect of the presence of large pores, a small sample of a very open reef rock was obtained in central Ohio. The pores at a plane surface range from a fraction of a millimeter to several millimeters in size. The contrast with the rocks used in the body of this work is obvious and striking. The bulk density by dimensional measurement and weighing was 2.469. A true density of 2.85 was assumed. The corresponding porosity was calculated by means of equation (7) to be 0.133. The rock was thus intermediate with respect to the others. The porosity was about the same as that of 3-LS-H and 47-2S. A portion of the sample was crushed and the sorption test was run on it but the results were unsatisfactory due to the small specific surface. A value of approximately $0.2 \text{ m.}^2/\text{g.}$ is probably close.

The results of the absorptivity tests are shown in Figure 21. The two upper curves are for a sample slightly immersed in the same manner as was the 9-LS sample (Figure 17). The lowest curve is for the usual test method. The salient feature of the curves is that

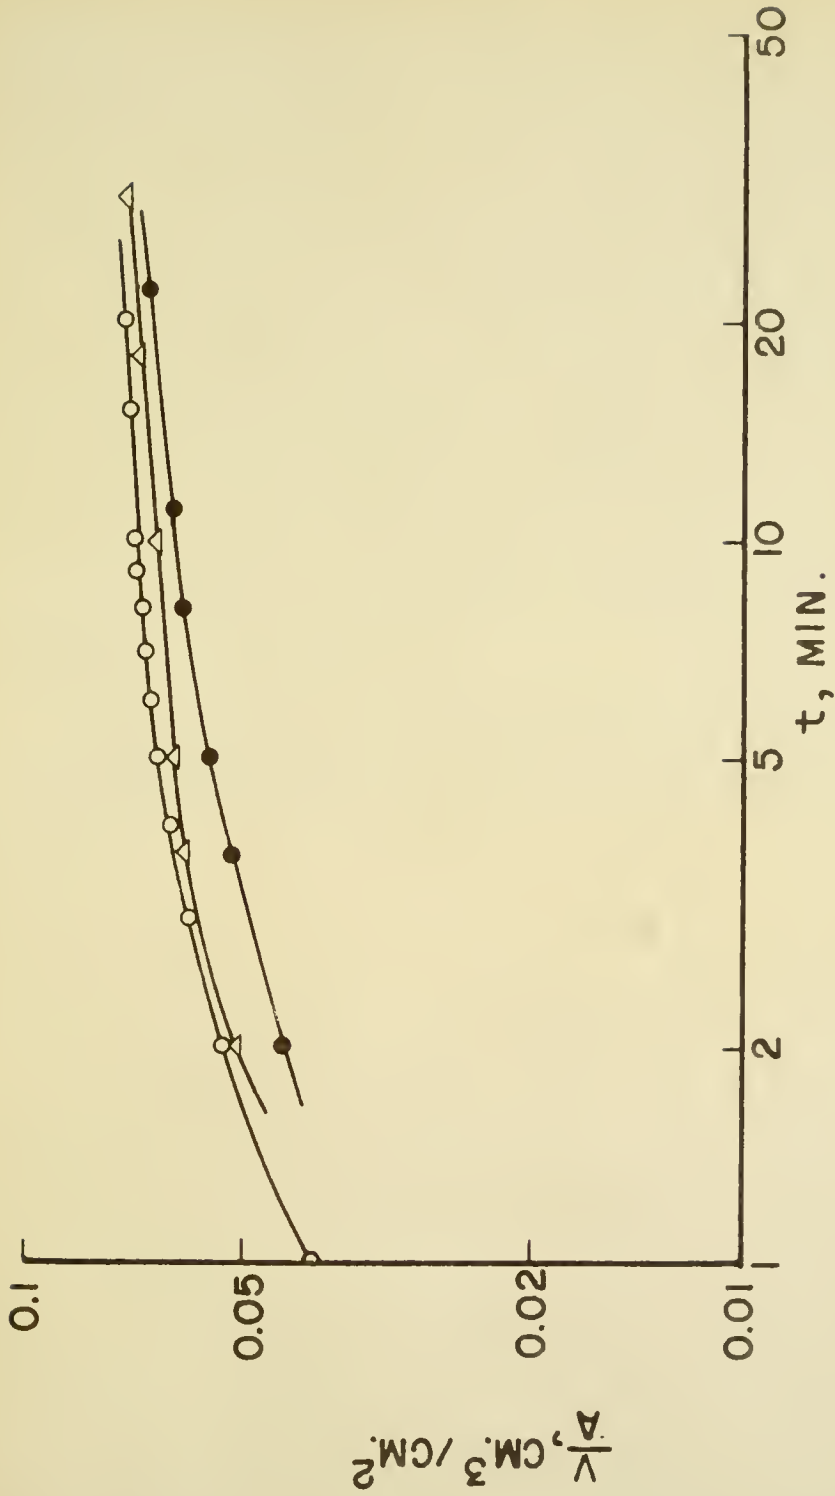


FIG. 21 ABSORPTIVITY OF REEF ROCK

even at 1-2 min. the sample was not obeying the model but was on the tapering portion of the curve. This is no doubt due to the non-uniform area of material that was being traversed by the water due to the uneven distribution of the very large pores which the water could not enter. An attempt was made to get values of the absorptivity coefficient and the capillary saturation from the curves by assuming that at 1 min. the data were still on the linear curves. The result for K_a was 1.81×10^{-5} cm.²/sec. (near that for 9-1S) and for α was 0.0236. This value corresponds to a saturation of only 0.17, a result which is readily understandable in view of the high proportion of the pore space which was composed of large pores that the water could not enter by capillarity.

The main point to be gained from these results is the inapplicability of this method of absorptivity determination for a rock of this type.

