

PAPER • OPEN ACCESS

Evaluating the Performance of Reclaimed Asphalt Pavement Incorporating PelletRAP as a Rejuvenator

To cite this article: Z H Al-Saffar *et al* 2021 *IOP Conf. Ser.: Earth Environ. Sci.* **682** 012068

View the [article online](#) for updates and enhancements.

You may also like

- [The Influence of PelletRAP™ Rejuvenator on the Mechanical Properties of Reclaimed Asphalt Pavement](#)
Z H Al-Saffar, H Yaacob, M K I Mohd Satar *et al.*
- [The reinforcement and healing of asphalt mastic mixtures by rejuvenator encapsulation in alginate compartmented fibres](#)
A Tabakovi, W Post, D Cantero *et al.*
- [Effectiveness of Different RAP Rejuvenators Obtained from Tests on Marshall Samples](#)
Wojciech Sorociak and Bartłomiej Grzesik



The Electrochemical Society
Advancing solid state & electrochemical science & technology

242nd ECS Meeting

Oct 9 – 13, 2022 • Atlanta, GA, US

Abstract submission deadline: **April 8, 2022**

Connect. Engage. Champion. Empower. Accelerate.

MOVE SCIENCE FORWARD



Submit your abstract



Evaluating the Performance of Reclaimed Asphalt Pavement Incorporating PelletRAP as a Rejuvenator

Z H Al-Saffar^{1,2}, H Yaacob^{1*}, M K I Mohd Satar¹, S N Mohd Usak¹, R P Jaya³, N A Hassan¹, H R Radeef¹, M N M Warid¹

¹Faculty of Engineering, School of Civil Engineering, Universiti Teknologi Malaysia, 81310 Johor Bahru, Malaysia

²Building and Construction Eng. Technical College of Mosul, Technical College of Mosul, Northern Technical University, 41002, Iraq

³Department of Civil Engineering, College of Engineering, Universiti Malaysia Pahang, 26300 Gambang, Pahang, Malaysia

Corresponding author: haryatiyaacob@utm.my

Abstract. In the recent years, the use of reclaimed asphalt pavement (RAP) in the pavement has become inevitable for economic and environmental reasons. However, the brittleness property of aged asphalt in the RAP restrict its usage in a high percentage. Nevertheless, the rejuvenators are introduced into the mixtures to reverse the effect of ageing processes, decrease the stiffness and increase the workability of RAP mixture. In the present research, various percentages of PelletRAP rejuvenator were added to 100% of RAP mixtures. The performance characteristics of rejuvenated mixtures were investigated via resilient modulus (M_R), dynamic creep, and wheel tracking tests. The results showed that when the PelletRAP was included into the mixture, the M_R values and the creep stiffness modulus (CSM) decreased, while the permanent creep, the creep strain slope (CSS) and the rutting depth increased. However, all the rejuvenated mixtures exhibited better results than that of virgin mixture. Such a trend of findings suggested that PelletRAP can be used as a rejuvenator without a negative effect on the high-temperature performance of asphalt mixtures.

1. Introduction

Fluctuations in asphalt price, limited resources of aggregates, environmental issues and sustainability have encouraged the usage of reclaimed asphalt pavement (RAP) in asphalt mixtures [1, 2]. Previous work indicates that the usage of 100% RAP in the asphalt mixtures results in an approximately 50-70% decrease in the price of hot mix asphalt (HMA) [3]. Furthermore, the literature reported that the use of 100% RAP mixture with a rejuvenating agent could reduce the CO₂ emissions by 35% and achieved 20% energy savings compared to virgin asphalt mixture without RAP material [3]. However, the properties and efficiency of RAP mixtures are highly influenced by ageing of its binder during the lifespan [4, 5]. Thus, using a high percentage of RAP in asphalt mixtures may deteriorate the mixture's characteristics [6] and cause fatigue and cracking problems [7-9]. These issues can be overcome using rejuvenators [10]. Rejuvenators are products (having chemical and physical characteristics) that added to asphalt mixtures containing high percentages of RAP [11]. These materials can enhance the dispersive of maltene phase and reduce the size of the asphaltene clusters, both contributing to improved ductility and decreased viscosity and rigidity of the aged asphalt [9]. Using rejuvenators date back to the late 1970s and early 1980s, where the ASTM D4552 was developed by classification of the rejuvenators into six grades depending on the viscosity measured at



60°C [12]. Some rejuvenators have been obtainable for decades. However, the usage of such rejuvenating agents has recently gained renewed interest with a move towards more sustainable practices, including the use of a high amount of RAP for economic and environmental reasons [12]. Nevertheless, some types of these rejuvenators can significantly diminish the stiffness of asphalt mixtures and cause potential rutting problem [7]. In other words, some softening and rejuvenating agents may be beneficial in cold region but unsuitable in hot region such as waste engine oil (WEO). The reason is associated with the fraction or chemical composition of agents. Therefore, using an additive such as nanomaterials or polymers in combination with rejuvenators as well as hybrid rejuvenators can be suitable solutions for overcoming this issue. For instance, Ziari et al. [7] explored the possibility of using nano-clay as a modifier to compensate the negative influence of rejuvenator on the performance of RAP. The outcomes reported that the reduction in flow number due to adding rejuvenator was compensated by adding nano-clay into the rejuvenated samples. Jahanbakhsh et al. [13] reported that the mechanical attributes of mixtures containing high percentages of RAP, waste engine oil, and crumb-rubber were better than or similar to that of virgin mixture. Al-Saffar et al. [10] evaluated the rheological properties of aged asphalt containing WEO and maltene as rejuvenators. The finding demonstrated that integration of WEO and maltene significantly enhanced the attributes of aged asphalt at both low and high temperatures. In the present research, the performance properties of 100% RAP mixtures containing different percentages of PelletRAP rejuvenator were investigated and compared with aged and virgin HMA mixtures. The aim is to evaluate the performance properties of 100% RAP mixture embraced with PelletRAP via resilient modulus (M_R), dynamic creep and wheel tracking tests.

2. Materials and experiments

2.1. RAP and virgin asphalt

Damaged pavement as the RAP material was collected within Yong Peng to Pagoh, Malaysia (134.6 km to 134.8 km) having a service life of about six years. Figure 1 shows the RAP material after sieving according to its gradation, while Figure 2 illustrates the distribution of the particle size of RAP aggregates at AC 14 gradation. Based on the distribution, the median gradation was selected between the lower and upper limits. The optimum asphalt content (OAC) of RAP was 5.1%. The aged asphalt was obtained via extraction method as per to ASTM D2172 [14] using methylene chloride. Virgin asphalt (PEN. 60-70) was obtained from Kemaman Bitumen Company (KBC), Malaysia. The characteristics of aged and virgin asphalt binders are shown in Table 1.



Figure 1. RAP material after sieving

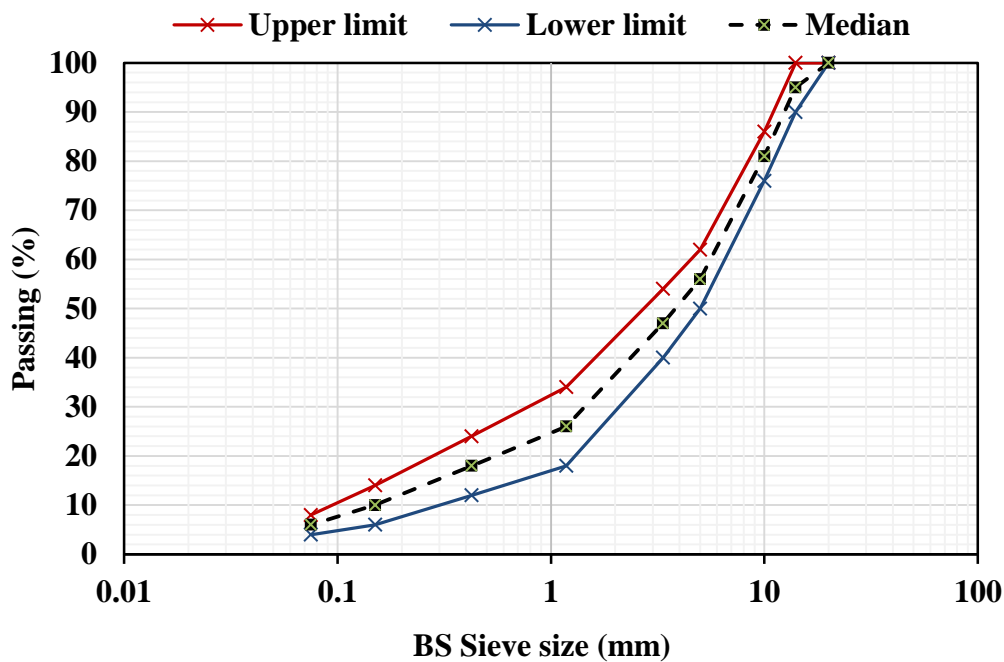


Figure 2. Gradation of RAP used in the research according to AC14

Table 1: Standard tests results of materials used in this research

Type of asphalt	Penetration (dmm)	Softening point (°C)	Ductility (cm)	Viscosity (mPa.s)	
				@ 135 °C	@ 160°C
Virgin asphalt	64	51.5	116	650	200
Aged asphalt	18.5	73	8	3500	700

2.2. PelletRAP

It is a high-performance rejuvenator brought from Phoenix Industries company-USA. It is composed of recycled scrap tires, asphalt cement, Bitunite, metal oxide and emulsion. The percentage of every material is presented in Table 2. It has different sizes similar to that of aggregates (see Figure 3), and it is utilised to improve the workability, compaction and performance characteristics of RAP mixtures.

Table 2. The components of PelletRAP

Chemical name	Concentration
Asphalt cement	45-65 %
Ground tire rubber	25-30
Bitunite	2-5
Portland cement II	2-4
Metal oxide	< 1
Latex emulsion pigment	< 1



Figure 3. PelletRAP material

2.3. Preparation of samples

2, 3, 4 and 5 % of PelletRAP (by weight of total mixture) were added to 100 % of RAP (AC 14 gradation). 1% of PelletRAP was not included since its effect on the mixture seems to semi neglected. The mixture was blended for 2 minutes using electrical mixer to rejuvenate the aged asphalt and obtain homogenous mixtures as well. Depending on the trial and error, it was found that increasing the mixing time with presence of high temperature will lead to increase the stiffness of aged asphalt. For comparison purposes, the OAC as well as the mixing and compacting temperatures (165°C and 156°C) for every mixture depended on the OAC and the viscosity results of VA at both 135°C and 165°C, respectively. This research comprised of six types of mixtures, namely the virgin mixture (VA), 100 % RAP mixture (R100-0PR), 100% RAP+2% of PelletRAP (R100-2PR), 100% RAP+3% of PelletRAP (R100-3PR), 100% RAP+4% of PelletRAP (R100-4PR) and 100% RAP+5% of PelletRAP (R100-5PR).

3. Tests

Universal Testing Machine (UTM-5P) IPC global brand, was used to conduct the resilient modulus (M_R) test at both 25 °C and 40 °C in accordance with ASTM D7369 [15] standard, as well as the dynamic creep test using performed in adherence to BS EN 12697-25 [16]. Later, the double wheel tracker (DWT) equipment was utilised to determine the rutting depth formed by repeated passes of a loaded wheel for 5 hours at 50 °C in accordance with EN 12697-22 standard [17] (See Figure 4). It is worthy of mentioning that M_R was calculated via Eq. (1). In addition, the data obtained from a repeated load creep test, as presented in the form of creep stiffness modulus (CSM) and creep strain slope (CSS), were calculated using Eqs. (2) and (3)

$$M_R = F/Ht (0.27 + \mu) \quad (1)$$

Where,

M_R = resilient modulus (MPa)

F = applied force (N)

t = sample thickness (m)

H = horizontal displacement (m)

μ = Poisson ratio

$$E = \sigma / \epsilon \quad (2)$$

$$CSS = (\text{Log } \varepsilon_{3600} - \text{Log } \varepsilon_{1200}) - (\text{Log } 3600 - \text{Log } 1200) \quad (3)$$

Where,

E = creep stiffness modulus (MPa)

σ = applied stress (kPa)

ε = Cumulative axial strain at 3600 cycles (mm)

ε_{3600} = Strain at 3600 cycles

ε_{1200} = Strain at 1200 cycles

CSS = Creep strain slope



Figure 4. (From left to right) Resilient modulus, dynamic creep and wheel tracking tests

4. Results

4.1. Resilient modulus (M_R)

Figure 5 illustrates the data of resilient modulus at 25°C and 40°C against different percentages of PelletRAP. It was found that R100-0PR recorded M_R value of 11765 Mpa at 25°C. This value was the highest compared to other samples, while VA mixture recorded the lowest values of M_R (3059 Mpa). This outcome is ascribed to the impact of stiffening in aged asphalt on RAP [18]. The highest M_R value at 25°C meaning the highest tendency of going back to original state after being loaded. Adding PelletRAP decreased the M_R values meaning that PelletRAP can reduce the stiffness, which was resulted from ageing process. The lowest M_R value of rejuvenated mixtures was recorded by R100-5PR (9109 Mpa). The reason is that adding PelletRAP (which contains 45-65% of soft asphalt) had decreased the stiffness of mixture, leading to decrease the M_R of sample. However, this value still much higher than VA, indicating that the RAP mixtures containing PelletRAP are less susceptible to fatigue deformation in comparison with VA mixture at 25°C. Upon increment in temperature, the variance in M_R turned more vivid, along with a decrease in stiffness at 40°C. M_R at 40°C results recorded the same trend as M_R at 25°C. In precise, R100-0PR recorded M_R value of 3544 Mpa, where VA recorded 1050 Mpa. In addition, rejuvenated mixtures showed lower M_R at 40°C compared to R100-PR. In precise the rejuvenated mixture containing the highest amount of PelletRAP (R100-5PR) exhibited M_R value of 2156 Mpa. The result was a slight higher than VA, meaning that the rejuvenated mixture is more resistant to rutting in comparison with the VA mixture.

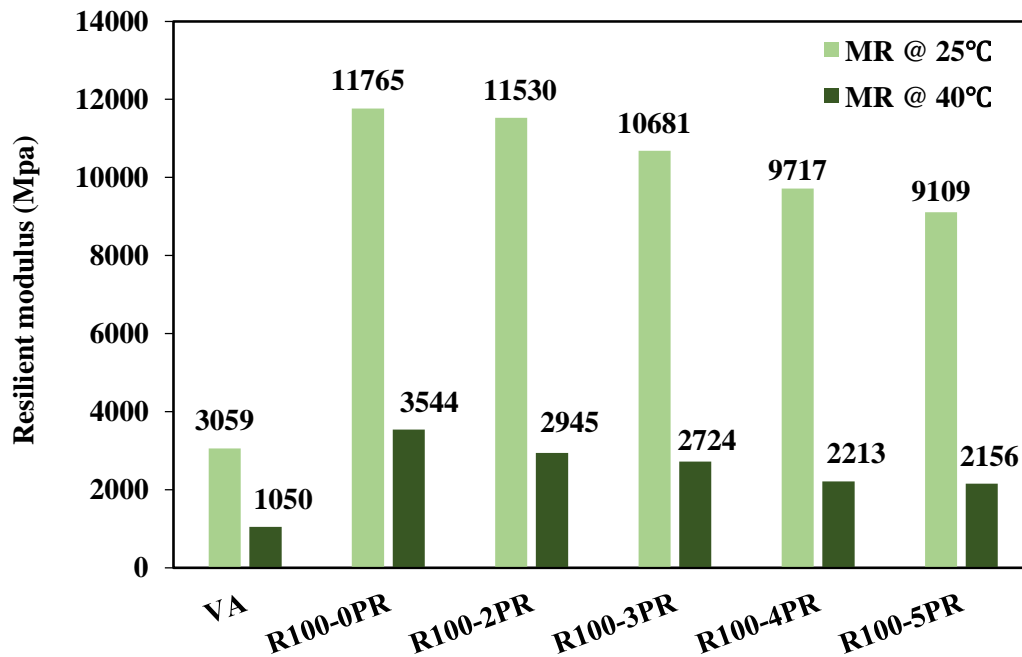


Figure 5. Resilient modulus results

4.2. Dynamic creep

Figure 6 illustrates the cumulative permanent strain of all mixtures. It was found that R100-0PR gave the lowest value of permanent strain (2010 μs), while VA mixture recorded the highest value (6393 μs). This is ascribed to the stiffening effect of ageing on the RAP, where maltene is low and asphaltene is high. However, when PelletRAP was included, the permanent strain of RAP mixture noticeably increased up to 4593 μs at 5% of PelletRAP. This is due to the reduction in stiffness of aged asphalt in the RAP mixture when mixed with rejuvenator [19]. On the other hand, the asphalt mixture resistance to permanent deformation was determined based on CSM and CSS. Figure 7 showed that R100-0PR recorded the lowest value of CSS (0.19), and this value increased by adding PelletRAP. In detail, R100-2PR recorded CSS value of (0.22), followed by R100-3PR (0.23), R100-4PR (0.25) and R100-5PR (0.26). Meanwhile, the CSS of VA mixture recorded the highest value of CSS (0.31). The highest CSS means the lowest resistance to permanent deformation.

Figure 8 presents that R100-0PR exhibited the highest value for CSM (849.64 Mpa), and this value decreased when PelletRAP was included into the mixture. Higher creep stiffness indicates high resistance to rutting. In precise, R100-2PR recorded a CSM value of 700.09 Mpa, followed by R100-3PR, which exhibited a value of 479.74 Mpa, R100-4PR (399.29 Mpa) and R100-5PR (286.85 Mpa). Meanwhile, VA mixture displayed the lowest value of CSM (182.27 Mpa). In other words, the rejuvenated mixtures exhibited better performance in term of rutting resistance than VA although inclusion of PelletRAP had reduced the stiffness of RAP mixture. The results obtained from the dynamic creep test are in agreement with M_R test.

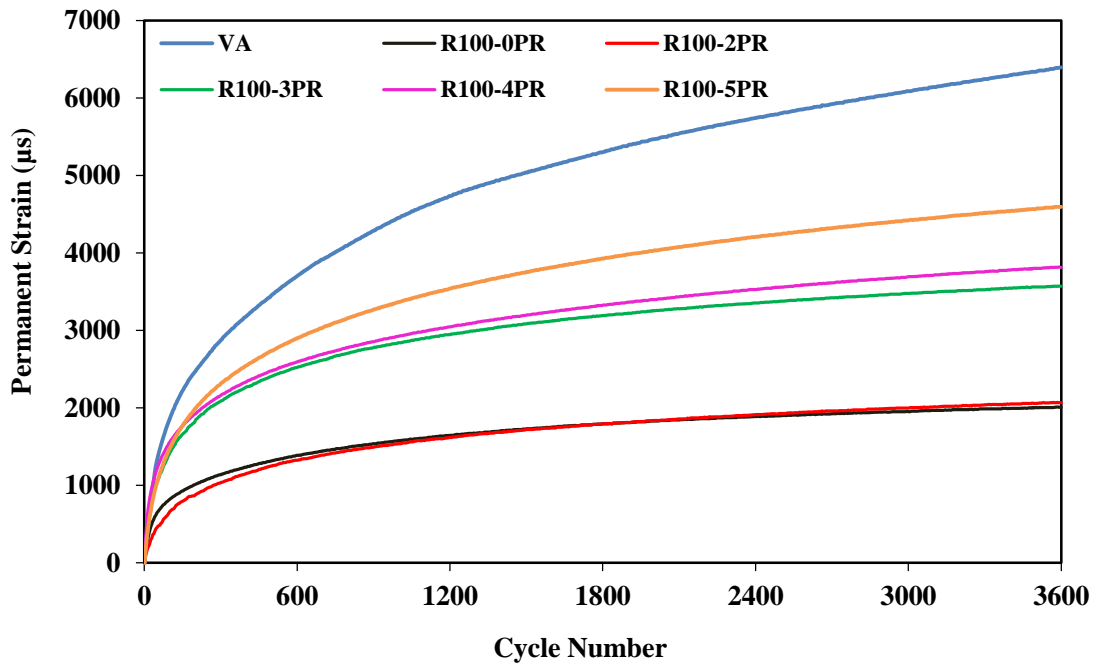


Figure 6. Permanent strain of selected mixtures

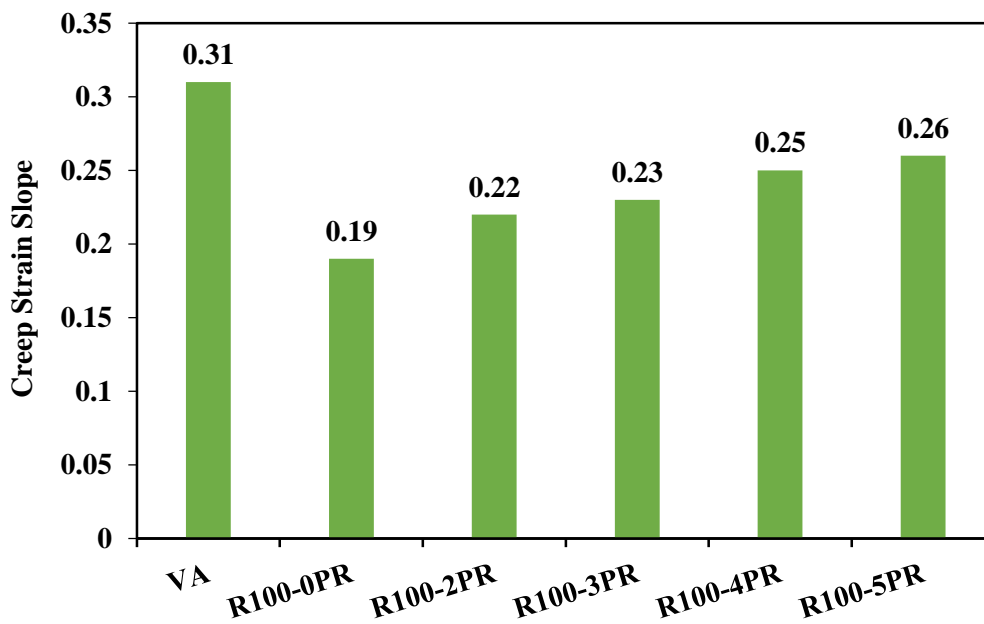


Figure 7. CSS of selected mixtures

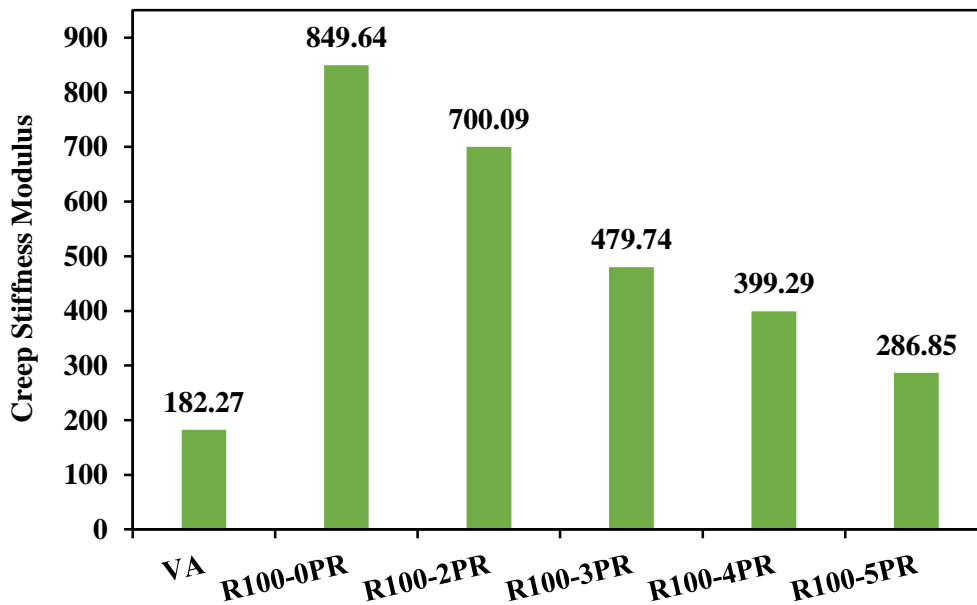


Figure 8. CSM of selected mixtures

4.3. Wheel tracking

Figure 9 reveals the development of rut depths for asphalt mixture samples. It can be seen that R100-0PR exhibited the lowest rutting depth after 10000 cycles of wheel loading (0.59 mm). This is due to the effect of short and long-term ageing with time. However, adding PelletRAP led to an increment in the rutting depth as a result of increasing the flexibility of asphalt. More specifically, R100-4PR exhibited rutting depth value of 0.84 mm, and followed by R100-5PR, which exhibited a rutting depth value of 1.24 mm. Meanwhile, VA mixture recorded the highest value of rutting depth (1.97 mm). These observations mean that the rejuvenated mixtures have better resistance to rutting than VA mixture. The outcomes obtained from wheel tracking are in agreement with findings obtained from M_R and dynamic creep tests.

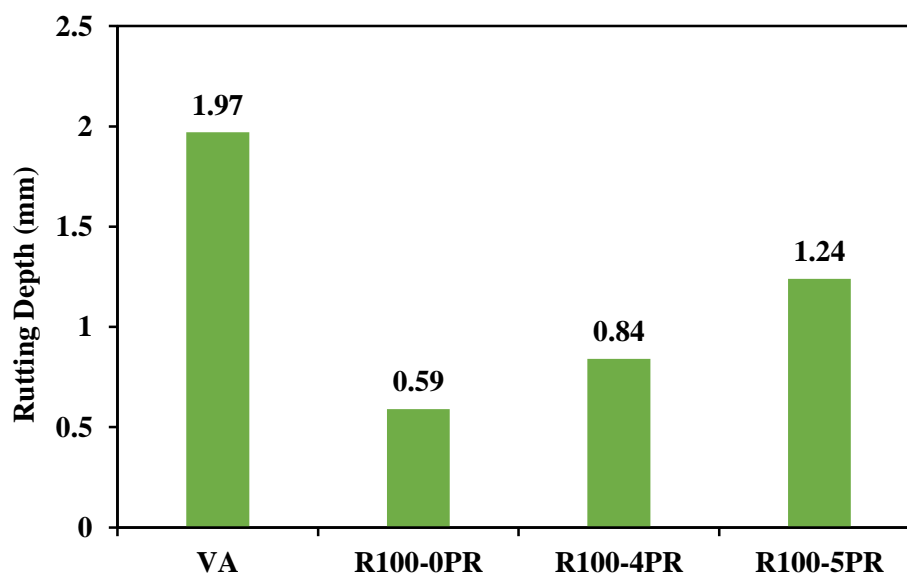


Figure 9. Rutting depth of selected mixtures

5. Conclusion

The PelletRAP significantly affected the characteristics of the RAP mixtures, where the resilient modulus and creep stiffness modulus of RAP mixtures decreased by inclusion of PelletRAP rejuvenator. On the contrary, the permanent strain, creep strain slope and rutting depth increased with the addition of PelletRAP. In other words, PelletRAP reduced the stiffness of aged asphalt, but it exhibited good resistance to deformation and even better than virgin asphalt mixtures. Thus, it can be used as a rejuvenator without any detrimental impact on the performance at high-temperature.

6. References

- [1] Ziari H, Moniri A, Bahri P, Saghafi Y 2019 Evaluation of performance properties of 50% recycled asphalt mixtures using three types of rejuvenators *Pet Sci Technol* **37** 2355-61.
- [2] Hussein Z, Yaacob H, Idham M, Abdulrahman S, Choy L, Jaya R Rejuvenation of hot mix asphalt incorporating high RAP content: issues to consider *IOP Conf. Ser.: Earth Environ. Sci.* **498** 012009
- [3] Zaumanis M, Mallick RB, Frank R 2014 100% recycled hot mix asphalt: A review and analysis. *Resour Conserv Recycl* **92** 230-45.
- [4] Izaks R, Haritonovs V, Klasa I, Zaumanis M 2015 Hot mix asphalt with high RAP content. *Procedia Eng.* **114** 676-84.
- [5] Hussein Z, Yaacob H, Idham M, Hassan N, Choy L, Jaya R 2020 Restoration of Aged Bitumen Properties Using Maltenes. *IOP Conf. Ser.: Mater. Sci. Eng.* **713** 012014
- [6] Moniri A, Ziari H, Aliha M, Saghafi Y 2019 Laboratory study of the effect of oil-based recycling agents on high RAP asphalt mixtures *Int. J. Pavement Eng.* 1-12.
- [7] Ziari H, Moniri A, Norouzi N 2019 The effect of nanoclay as bitumen modifier on rutting performance of asphalt mixtures containing high content of rejuvenated reclaimed asphalt pavement *Pet Sci Technol* **37** (17) 1946-51.
- [8] Yu B, Gu X, Wu M, Ni F 2017 Application of a high percentage of reclaimed asphalt pavement in an asphalt mixture: blending process and performance investigation *Road Mater. Pavement Des* **18** (3) 753-65.
- [9] Al Saffar ZH, Yaacob H, Idham MK, Saleem MK, Lai JC, Putra Jaya R 2020 A review on rejuvenating materials used with reclaimed hot mix asphalt. *Can. J. Civ. Eng.* 1-39
- [10] Al-Saffar ZH, Yaacob H, Mohd Satar MKI, Saleem MK, Jaya RP, Lai CJ, Ekarizan Shaffie 2020 Evaluating the chemical and rheological attributes of aged asphalt: synergistic effects of maltene and waste engine oil rejuvenators *Arab J Sci Eng* **45** (10) 8685-97
- [11] Shen J, Amirhanian S, Tang B 2007 Effects of rejuvenator on performance-based properties of rejuvenated asphalt binder and mixtures. *Constr Build Mater.* **21** (5) 958-64.
- [12] Kaseer F, Martin AE, Arámbula-Mercado E 2019 Use of recycling agents in asphalt mixtures with high recycled materials contents in the United States: A literature review *Constr Build Mater.* **211** 974-87.
- [13] Jahanbakhsh H, Karimi MM, Naseri H, Nejad FM 2020 Sustainable asphalt concrete containing high reclaimed asphalt pavements and recycling agents: Performance assessment, cost analysis, and environmental impact *J. Clean. Prod.* **244** 118837.
- [14] ASTM D2172/D2172M 2017 *Standard Test Methods for Quantitative Extraction of Asphalt Binder from Asphalt Mixtures* West Conshohocken PA: ASTM International.
- [15] ASTM D7369 2011 *Standard Test Method for Determining the Resilient Modulus of Bituminous Mixtures by Indirect Tension Test* West Conshohocken PA: ASTM International.
- [16] BS EN 12697-25 2013 *Bituminous mixtures - Test methods for hot mix asphalt-Part 25: Cyclic compression test* London, UK: BSI Standard.
- [17] BS EN 12697-22 2013 *Bituminous mixtures - Test methods for hot mix asphalt - Part 22: Wheel tracking* London, UK: BSI Standard.
- [18] Behbahani H, Ayazi MJ, Moniri A 2017 Laboratory investigation of rutting performance of warm mix asphalt containing high content of reclaimed asphalt pavement *Pet Sci Technol* **35** (15) 1556-61.

- [19] Farooq MA, Mir MS, Sharma A 2018 Laboratory study on use of RAP in WMA pavements using rejuvenator *Constr Build Mater.* **168** 61-72.

Acknowledgments

The authors express their gratitude to the Universiti Teknologi Malaysia for funding this work through the Fundamental Research Grant Scheme (Grant Number R.J130000.7851.5F019).