

## EFFECT OF CATALYST ON THE PRODUCER GAS COMPOSITION FROM CO-GASIFICATION OF GLYCEROL/FAT MIXTURES

A. Cruz<sup>1</sup>, E. Ramalho<sup>1</sup>, A. Ribeiro<sup>1</sup> and R. Pilão<sup>1</sup>

<sup>1</sup> CIETI – Instituto Superior de Engenharia do Porto (ISEP), R. Dr. Antonio Bernardino de Almeida 431, 4249-015 Porto, Portugal, 1140580@isep.ipp.pt; err@isep.ipp.pt; [rm@isep.ipp.pt](mailto:rm@isep.ipp.pt)

### ABSTRACT

In this work, steam reforming of crude glycerol and animal fat mixtures was studied. The tests were carried out at temperatures of 700 °C and 750 °C in a fixed bed reactor using activated alumina or dolomite particles, to evaluate the catalytic capacity of these minerals in the removal of tar from the producer gas. The gas produced was quantified and analyzed by gas chromatography, and it was concluded that its composition is greatly influenced by the bed material used. The results obtained showed that dolomite is more effective in reducing the tar content, evidencing its ability to catalyze the tar reform reactions and promoting the water-gas shift reaction. Consequently, using dolomite as a catalyst, a producer gas with 47-48 vol% in H<sub>2</sub> and 27-30 vol% in CO<sub>2</sub> was obtained, while using a bed of alumina particles, a gas with a high CO content (45-48 vol%) and lower H<sub>2</sub> content (34-37 vol%) was produced.

**Keywords:** alumina, dolomite, fat, co-gasification, glycerol, steam reforming

### 1. INTRODUCTION

In the global energy and environmental landscape, there has been an increase in the dynamics inherent in the move to renewable energy sources. The possibility of valuing waste is presented as a fundamental strategy in the context of environmental and economic sustainability, contributing to the model of transition to a circular economy and intensifying the use of renewable energy sources. In Portugal, there are by-products and industrial wastes for which it is urgent to find alternatives that aim at their recovery. In this context, the present study intends to evaluate the technical feasibility of the gasification process of two industrial by-products/wastes: crude glycerol from the biodiesel industry and animal fat from the leather industry. In this work the results of the effect of the use of dolomite as a catalyst in the composition of the produced gas are presented.

Despite the advances achieved in recent years in the design of more efficient gasifiers, the cleaning process of the gas produced is still a limitation on the use of biomass for electricity generation. The presence of tars (condensable organic compounds) in the producer gas can cause clogging and corrosion and reduce the overall efficiency of the process. For this reason, interest in the catalysis of biomass gasification has grown in recent decades. Dolomite is a biomass gasification catalyst that has been studied by several researchers (Sutton 2001, Tan et al. 2019, Islam, 2020, Shanmuganandam et al. 2020).

Delgado et al. (1997) investigated the use of Norte dolomite for the steam reforming of biomass tars. They reported that the tar conversion increased with increasing temperature and complete elimination was observed at 840 °C. They observed that an increase in the gas/catalyst contact time and in particle size results in an increase in the destruction of the tar present in the gas and in more H<sub>2</sub> and CO<sub>2</sub> produced.

Perez et al. (1997) investigated the biomass gasification in a bubbling fluidized bed gasifier using steam-oxygen mixtures as gasification agent and calcined dolomite located downstream from the gasifier. They have reported an increase in the H<sub>2</sub> content, a decrease in the CO content and a tar conversion of 90-95 vol% with space times of 0.06-0.15 kg calcined dolomite / (hm<sup>3</sup>).


Gil et al. (1999) investigated the performance improvement of a fluidized-bed biomass gasifier, by in-bed use of calcined dolomite. They reported that 15-30 wt% of (calcined) dolomite in the bed improves quite a lot the quality of the producer gas, presenting a tar content below 1 g/m<sup>3</sup> and an increase in the H<sub>2</sub>, CO and CH<sub>4</sub> contents.

Andrés et al. (2011) studied the catalytic gasification of sewage sludge in a fluidized bed reactor using air and air-steam mixtures as the gasification agent. The aim of the study was to study the influence of three catalysts: dolomite, olivine and alumina in the composition of the producer gas and in the production of tars during the gasification process. The results showed that dolomite has the greatest activity in the elimination of tar, followed by alumina and olivine, and it was found that the concentration of tar decreased by 75% using dolomite against 65% using alumina. The study also indicates that at 800 °C dolomite allows to obtain a higher amount of hydrogen (17%) when compared to alumina (15%) and that the highest H<sub>2</sub>/CO ratio was obtained using dolomite.


Pinto et al. (2020) studied the gasification of lignin-rich solids in a bubbling fluidized bed gasification reactor where 33% by mass of minerals such as limestone, dolomite or olivine were added to the silica sand bed. In the study, the effect of the presence of these minerals on the synthesis gas composition was analyzed. They concluded that the highest concentrations of H<sub>2</sub> and CO<sub>2</sub> and the lowest CO levels were obtained in the presence of dolomite. They also concluded that dolomite seems to be the most suitable catalyst to promote the destruction of tars.

Gasification is a thermochemical process involving an oxidant agent and consisting of a partial oxidation that allows the conversion of carbonaceous raw material into a gaseous fuel. The reaction mechanism of the gasification process is complex, and reactions 1 to 10 are some of the main reactions involved in the process (Basu 2018, Leal et al. 2016, Meng et al. 2012):


**Water-gas shift reaction:**





**Boudouard reaction:**




**Steam char reaction:**



**Methane steam reforming:**



**Methane dry reforming:**




**Tar reactions:**

$$\Delta H_f^{298 \text{ K}} = +[200 - 300] \text{ kJ/mol}$$


Thermal cracking:



Tar steam reforming:



Tar dry reforming:



Tar carbon formation:



## 2. MATERIALS AND METHODS

The co-gasification of crude glycerol/fat mixtures was studied in a down flow fixed bed reactor using steam as the gasification agent. Tests were performed with a fixed bed composed of catalyst particles of dolomite (2 to 5 mm of diameter) or alumina (6 mm of diameter). The results obtained with dolomite were compared with the ones obtained using alumina particles. The experimental tests were performed at 700 °C and 750°C using a mixture composed by 59% of glycerol, 3% of fat and 38% of water, having a C/H<sub>2</sub>O mass ratio of 0.72. Details on the experimental installation and test procedure can be found in Almeida et al. (2020).

Dolomite (MgCO<sub>3</sub>CaCO<sub>3</sub>) is one of the most common materials used as a catalyst in biomass gasification (Hervya, 2019). Dolomite is used with the main objective of reducing the tar content in the producer gas and its main operating problem is its fragility when calcined. The calcination of dolomite above 750 °C gives rise to the formation of MgO (21.3%) and CaO (30.4%) due to the loss of CO<sub>2</sub>.

After the gasification tests, the bed of alumina particles was calcinated at 900°C during 30 min and the dolomite bed was calcinated at 550°C during 2 h, to remove the deposited carbonaceous residue. The lower calcination temperature, in the case of dolomite, was selected to prevent the CO<sub>2</sub> mass loss with the consequent material fragilization.

## 3. RESULTS AND DISCUSSION

In Fig. 1 the results obtained for the average gas and liquid phase yields are presented for the two particle bed materials studied. These indicators represent the fraction of the feed that was converted to the gaseous phase and the one that remained in the condensed phase. The gaseous phase, called producer gas, is essentially composed of H<sub>2</sub>, CO, CH<sub>4</sub> and CO<sub>2</sub> and the liquid phase consisting of the condensable fraction of the gas produced in the gasification process, is composed mainly by water and tars (aromatic hydrocarbons).

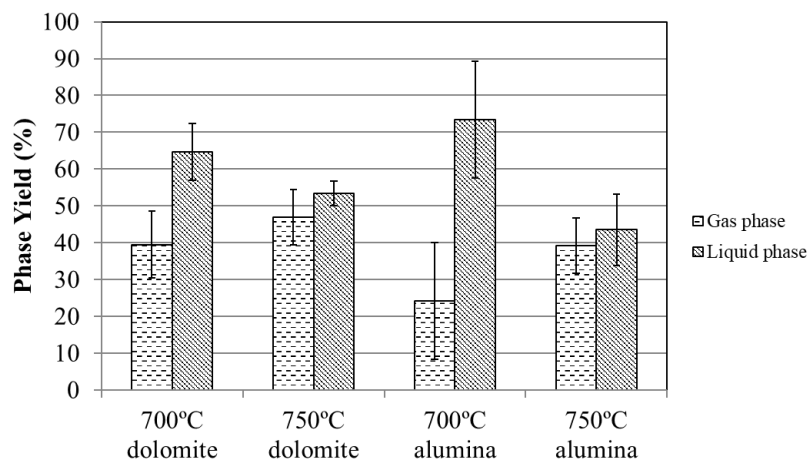


Fig. 1 – Gas and liquid phase yields.

The results obtained clearly show that when is used a bed of dolomite particles the gas phase yield is greater than that obtained when using alumina particles. They also show that the increase in temperature favors the production of the gas phase and the decrease of liquid phase production, for both materials studied. The determination of phase yields is affected by a large experimental error (standard deviation indicated as vertical bars in Fig. 1) however they are indicators of the behavior of the co-gasification process under the studied conditions.

The effect of temperature and bed material on the producer gas composition was studied. Fig. 2 shows the obtained results for CO, CO<sub>2</sub>, H<sub>2</sub> and CH<sub>4</sub>.

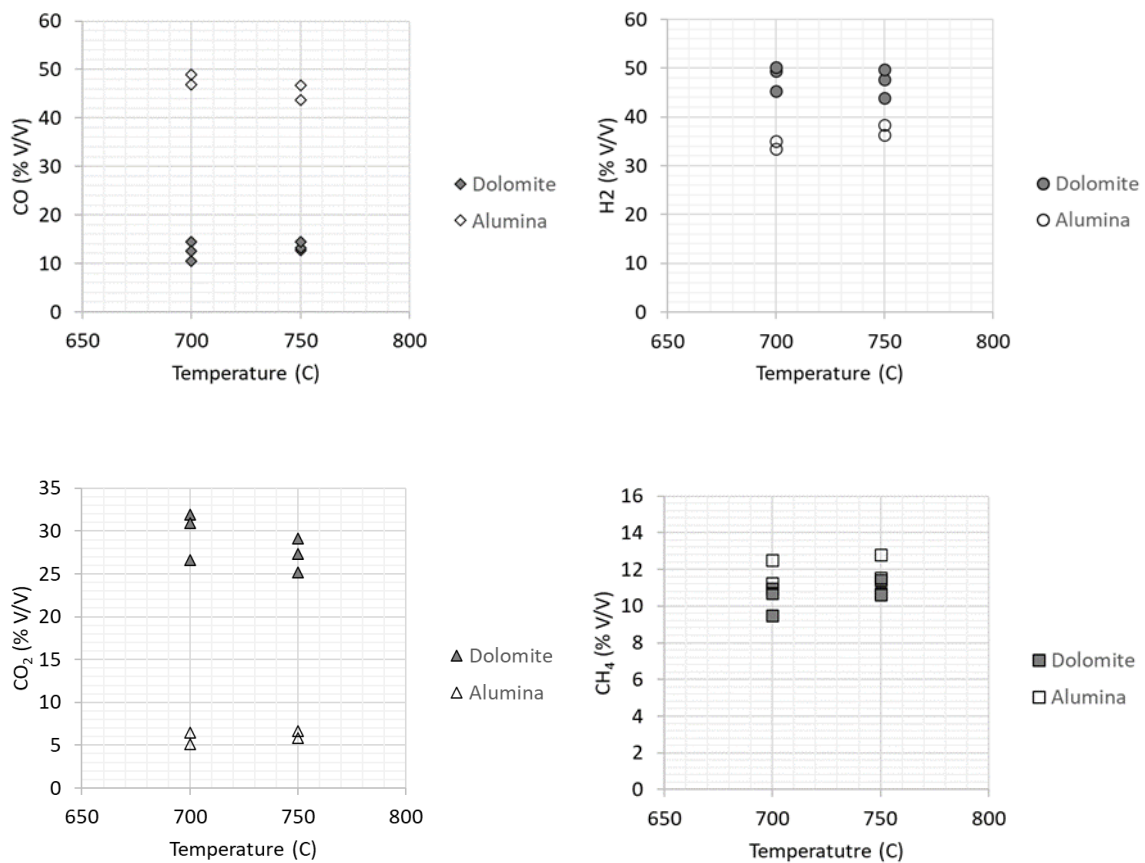


Fig. 2 – Producer gas composition.

With the increase in temperature, using a bed of alumina particles, there was a tendency to decrease the CO content in the producer gas from about 48 to 45 vol% while, when using dolomite as a catalytic bed, substantially lower values of CO concentration were registered (13 vol%).

Regarding the concentration of H<sub>2</sub> in the producer gas, it was found that, with the increase in temperature and using alumina, the average H<sub>2</sub> concentration increases from 34 to 37 vol% and that the use of dolomite as a catalyst promoted an increase in H<sub>2</sub> concentration values in the range of 48-47 vol%.

Concerning the concentration of CO<sub>2</sub> in the producer gas, there was also a large difference in results between the two bed materials tested. Using alumina, the recorded CO<sub>2</sub> concentrations were in the range of 5-6 vol% and when dolomite was used a substantial increase in this concentration was observed. In this case, with the increase in temperature, there was a slight decrease from 30 to 27 vol% of the mean CO<sub>2</sub> concentration.

For the temperatures tested, no significant differences were observed in the concentration of CH<sub>4</sub> between the tests with dolomite and with alumina. The average values ranged from 10 to 12 vol%.

The results show that the composition of the producer gas is strongly dependent on the material of the particle bed. Using dolomite as a catalyst, a producer gas rich in H<sub>2</sub> and CO<sub>2</sub> was obtained, as indicated in several studies (Andrés et al 2011, Delgado et al. 1997, Pinto et al. 2020, Vassilatou et al. 1992). When using a bed of alumina particles, it was observed that CO was the predominant component followed by H<sub>2</sub>, as reported by Andrés et al. (2011b).

This behavior is indicative that dolomite appears to be a suitable material to promote the destruction of tars by its action as a catalyst for tar reform reactions (8, 9), resulting in the promotion of the water gas shift reaction (1) as well. As a result of the higher level of H<sub>2</sub> and lower level in CO in producer

gas, a large increase in the average value of the H<sub>2</sub>/CO ratio was observed in the presence of dolomite (Fig. 3).

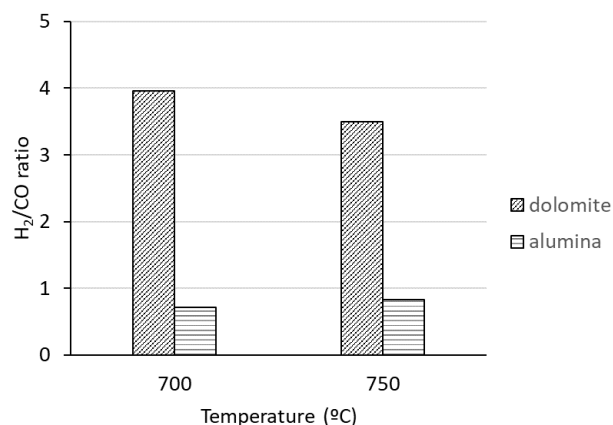


Fig. 3 – Effect of bed material on H<sub>2</sub>/CO ratio

#### 4. CONCLUSION

The catalytic co-gasification of glycerol/fat mixtures was studied using steam as a gasification agent. The results showed that dolomite is more effective than alumina in reducing the tar content of the producer gas. In the tested range temperatures, it was also found that the use of dolomite promotes the production of a producer gas rich in H<sub>2</sub> (47-48 vol%) and CO<sub>2</sub> (27-30 vol%) and with a mass ratio of H<sub>2</sub>/CO between 3.5 to 4, which gives the gas more suitable properties for its use in combustion engines and in chemical synthesis for biofuels production, than the gas produced using alumina.

#### FUNDING

This work was supported by Portugal 2020 (POCI-01-0145-FEDER-024067) and by Multi-year financing of FCT- Fundação para a Ciência e Tecnologia (grant UIDB/04730/2020)

#### REFERENCES

- Almeida A., Pilão R., Ribeiro A., Ramalho E., Pinho C., 2020, Co- Gasification of Crude Glycerol/Animal Fat Mixtures. *Energies*. 13 (7), 1699
- Andrés J.M., Narros A., Rodríguez M., 2011a. Behaviour of dolomite, olivine and alumina as primary catalysts in air-steam gasification of sewage sludge. *Fuel* (90), 521-527
- Andrés J.M., Narros A., Rodríguez M., 2011b. Air-steam gasification of sewage sludge in a bubbling bed reactor: Effect of alumina as a primary catalyst. *Fuel Processing Technology*. 92, 433-440
- Basu P, 2018. *Biomass Gasification, Pyrolysis and Torrefaction: practical design and theory*, 3rd Edition; Elsevier
- Delgado J., Aznar P., Corella L., 1997. Biomass gasification with steam in fluidized bed: effectiveness of CaO, MgO, and CaO-MgO for hot raw gas cleaning. *Industry and Engineering Chemical Research*. Res. 36, 1535
- Gil J., Caballero M. A., Martí n J. A., Aznar M, Corella J., 1999. Biomass Gasification with Air in a Fluidized Bed: Effect of the In-Bed Use of Dolomite under Different Operation Conditions. *Ind. Eng. Chem. Res*. 38, 4226-4235
- Hervya M., Olcese R., Bettaharb M., Malletc M., Renardc A., Maldonado L., Remya D., Mauviela G., Dufoura A., 2019. Evolution of dolomite composition and reactivity during biomass gasification. *Applied Catalysis A, General*. 572. 97-106
- Islam M. W., 2020. A review of dolomite catalyst for biomass gasification tar removal. *Fuel*. 267. 177095



- Leal, A.L., Soria, M.A., Madeira, L.M., 2016. Autothermal reforming of impure glycerol for H<sub>2</sub> production: Thermodynamic study including in situ CO<sub>2</sub> and/or H<sub>2</sub> separation. *Int. J. Hydrogen Energy*. 41 no. 4, 2607–2620.
- Meng, X., 2012. Biomass gasification: the understanding of sulfur, tar, and char reaction in fluidized bed gasifiers. PhD Thesis, Delft University of Technology.
- Peréz P., Aznar P., Caballero M., Gil J., J. Martín, J. Corella, 1997. Hot Gas Cleaning and Upgrading with a Calcined Dolomite Located Downstream a Biomass Fluidized Bed Gasifier Operating with Steam–Oxygen Mixtures. *Energy Fuel*. 11, 1194-1203
- Pinto F. André R., Marques P., Mata R., Costa P., Gírio F., 2020. Gasificação de biomassa rica em ligninha para produção de gás para usar em fermentação bacteriana. CIES 2020 – XVII Congresso Iberico y XIII Congresso Iberoamericano de Energia solar
- Shanmuganandam K., Thanikaikarasan S., Anichai J., 2020. Application of dolomite for tar mitigation in downdraft gasifier: an experimental analysis. *Materials Today: Proceedings*. 33. 3537-3539
- Sutton D., Kelleher B., Ross H., 2001. Review of literature on catalysts for biomass gasification. *Fuel Processing Technology*. 73, 155–173
- Tan R., Abdullah T., Mahmud S., Zin R., Isa K., 2019. Catalytic steam reforming of complex gasified biomass tar model toward hydrogen over dolomite promoted nickel catalyst. *International Journal of Hydrogen Energy*. 44. 21303-21314
- Vassilatos V., Taralas G., Sjöström K., Björnbom E., 1992. Catalytic cracking of tar in biomass pyrolysis gas in the presence of calcined dolomite. *Canadian Journal of Chemical Engineering*. 70 (5), 1008