

University of Groningen

Biodegradable microspheres for the sustained release of ppB-HSA to target PDGF β -receptors in fibrotic tissues

Teekamp, Naomi; van Dijk, Fransien; Beljaars, Eleonora; Post, Eduard; Hinrichs, Wouter; Poelstra, Klaas; Olinga, Peter

IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.

Publication date:
2016

[Link to publication in University of Groningen/UMCG research database](#)

Citation for published version (APA):

Teekamp, N., van Dijk, F., Beljaars, E., Post, E., Hinrichs, W., Poelstra, K., & Olinga, P. (2016). *Biodegradable microspheres for the sustained release of ppB-HSA to target PDGF β -receptors in fibrotic tissues*. Poster session presented at 14th European Symposium on Controlled Drug Delivery (ESCDD), Egmond aan Zee, Netherlands.

Copyright

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

Take-down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.



Biodegradable microspheres for the sustained release of pPB-HSA to target PDGF β -receptors in fibrotic tissues

university of
 groningen

N. Teekamp¹, F. van Dijk^{1,2}, L. Beljaars², W.L.J. Hinrichs¹, K. Poelstra² and P. Olinga¹

¹Department of Pharmaceutical Technology and Biopharmacy, University of Groningen, Groningen, The Netherlands

²Department of Pharmacokinetics, Toxicology and Targeting, University of Groningen, Groningen, The Netherlands

n.teekamp@rug.nl


Introduction

Fibrosis

Platelet Derived Growth Factor (PDGF) plays a key role in the development of fibrotic processes in several tissues. Accordingly, the PDGF β -receptor is abundantly present in these fibrotic tissues.

The cyclic peptide pPB

- pPB is a cyclic receptor binding peptide that contains the binding site of endogenous PDGF-BB.
- Coupling the cyclic peptide pPB to human serum albumin (HSA) prevents rapid renal excretion and allows for a better receptor presentation.
- The cyclic peptide can bind to the PDGF β -receptor without eliciting a response.
- pPB-HSA can be used as a carrier to target therapeutic drugs.

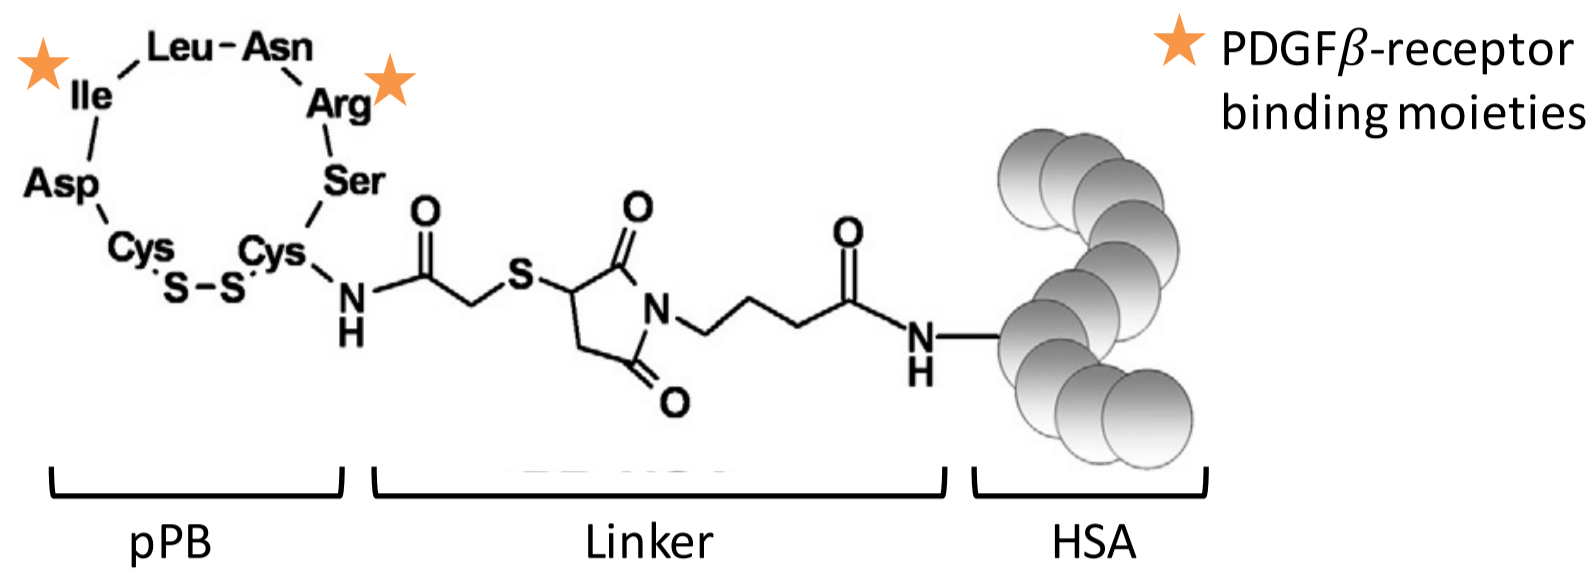

- Long term use of pPB-HSA requires a sophisticated formulation, such as polymeric microspheres for controlled and sustained release.

Aim

The aim of this research was to develop a solid formulation for the controlled and sustained release of pPB-HSA and assess the delivery and targeting of the intact protein construct *in vivo*.


Methods – formulation development

Microsphere production - Water-in-oil-in-water process

- 1.0 g microsphere batches with 5% protein content were prepared using a double emulsion evaporation production process. After filtration and washing, the microspheres were freeze dried.

Polymers

- Combination of 2 polymers provides flexibility for release profile
- Semi-crystalline block copolymers developed by InnoCore Pharmaceuticals (Groningen, The Netherlands).

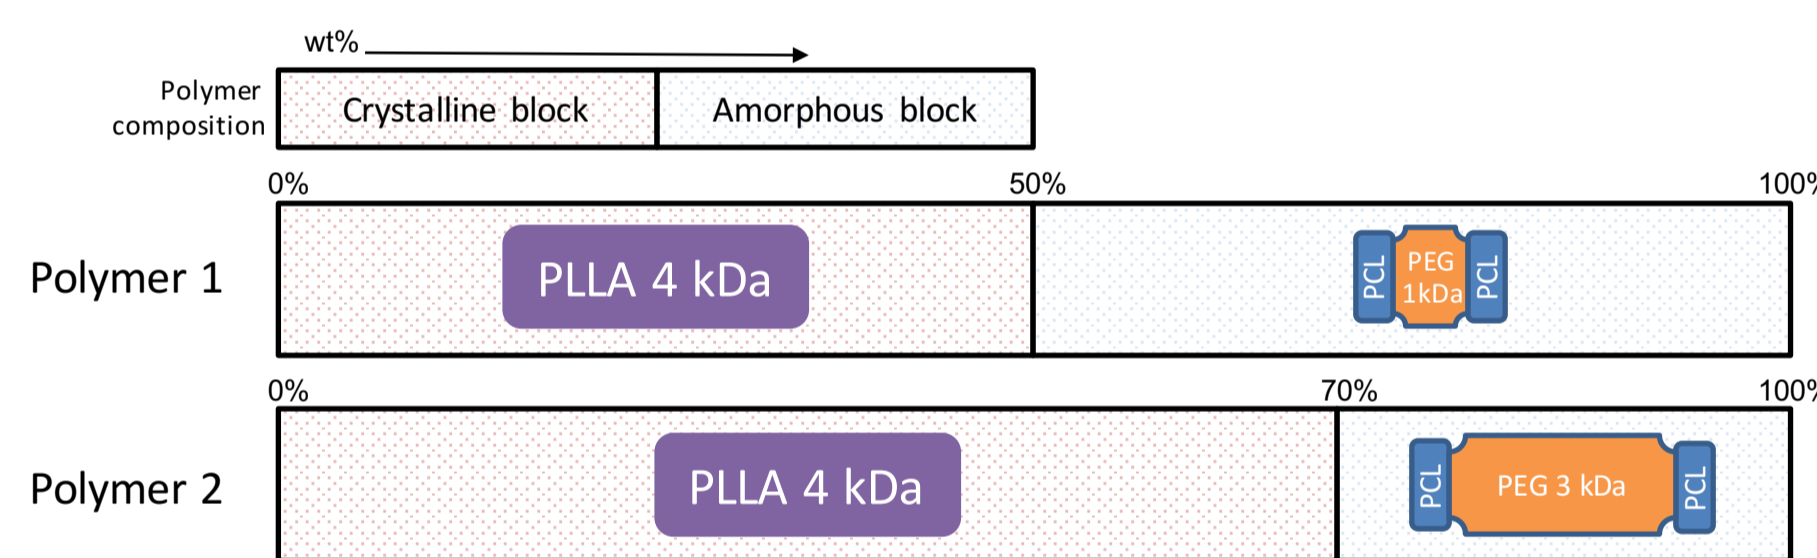

Microsphere characterization

- Particle size assessment:** laser diffraction and scanning electron microscopy
- Total protein content/encapsulation efficiency (EE):** microspheres were dissolved in a mixture of DMSO and 0.05N NaOH, 0.5% SDS. The total protein content was determined using the BCA assay.
- In vitro release:** microspheres were immersed in phosphate buffer (pH 7.4) and placed in a 37°C shaking water bath. Samples were taken at predetermined time points and replaced by fresh buffer. The total protein content was measured using BCA. The pPB-HSA content was determined using a sandwich ELISA.


Methods – in vivo experiment

Unilateral ureteral obstruction (UUO) renal fibrosis model in C57bl6 mice

- Ligation of the left ureter causes the development of (renal) tubulointerstitial fibrosis in 7 days
- Renal fibrosis in the UUO kidney is associated with increased PDGF β -receptor expression

Study design

- Day 0: UUO surgery
- Day 0: Subcutaneous administration of 31.5 mg microspheres (dispersed in 0.5 mL 0.4% carboxymethylcellulose solution)
 - n=3: 5% HSA microsphere administration
 - n=3: 3% pPB-HSA / 2% HSA microsphere administration
- Day 7: Sacrifice of animals
 - Collection of kidneys and blood for analysis

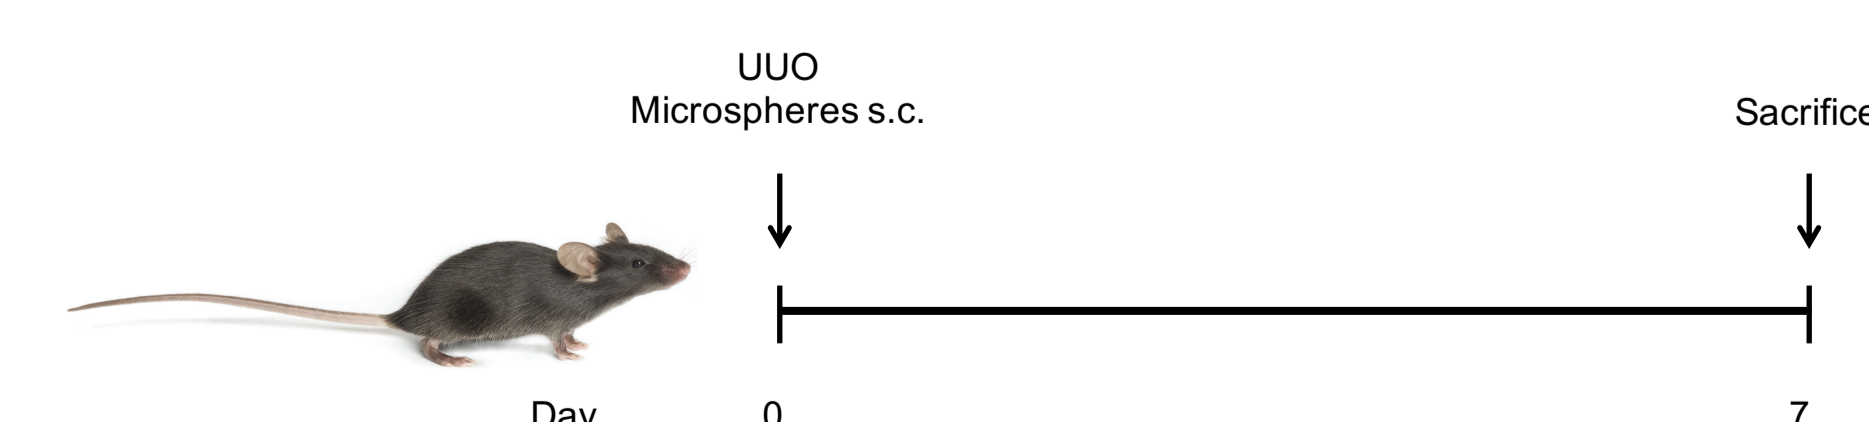

Analysis

- ELISA and western blot for pPB-HSA in plasma
- Western blot for HSA in kidney tissue
- Immunohistochemical staining on pPB-HSA in kidney sections

Conclusions


- pPB-HSA was successfully formulated in polymeric microspheres produced by a W/O/W method, which showed a first order release profile *in vitro* for 14 days.
- pPB-HSA was released from these microspheres *in vivo*.
- 7 days after administration, pPB-HSA was detectable in plasma and predominantly localized in fibrotic tissue with increased expression of the target, the PDGF β -receptor.

The delivery and site specific targeting of pPB-HSA from polymeric microspheres is feasible and opens opportunities for developing controlled release formulations with therapeutic proteins targeted to fibrotic tissue.

Results – formulation development


Microsphere size and appearance

- After 7 days of *in vitro* release, small pores are formed, but no substantial degradation is visible.
- The particle size distributions of the two microsphere batches are comparable and confirm the SEM photographs.

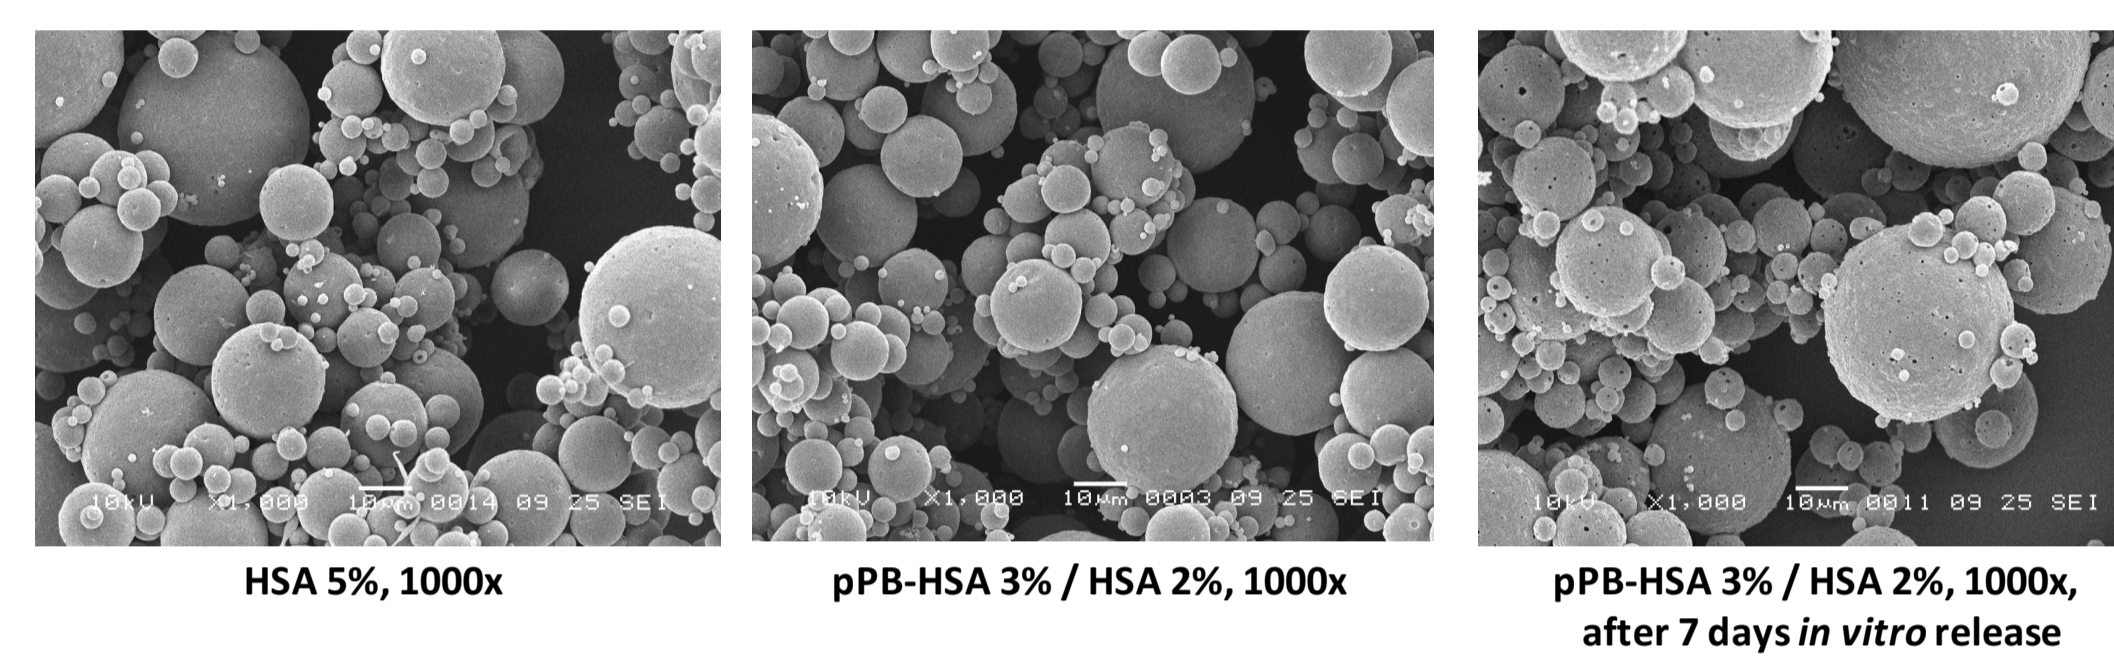

Protein	Particle size distribution			Encapsulation Efficiency	Recovery after 14d release
	X ₁₀ (μm)	X ₅₀ (μm)	X ₉₀ (μm)		
pPB-HSA/HSA	6.56	24.74	50.22	83%	95%
HSA	6.58	26.36	55.79	81%	105%


50:50 polymer composition shows most suitable release profile

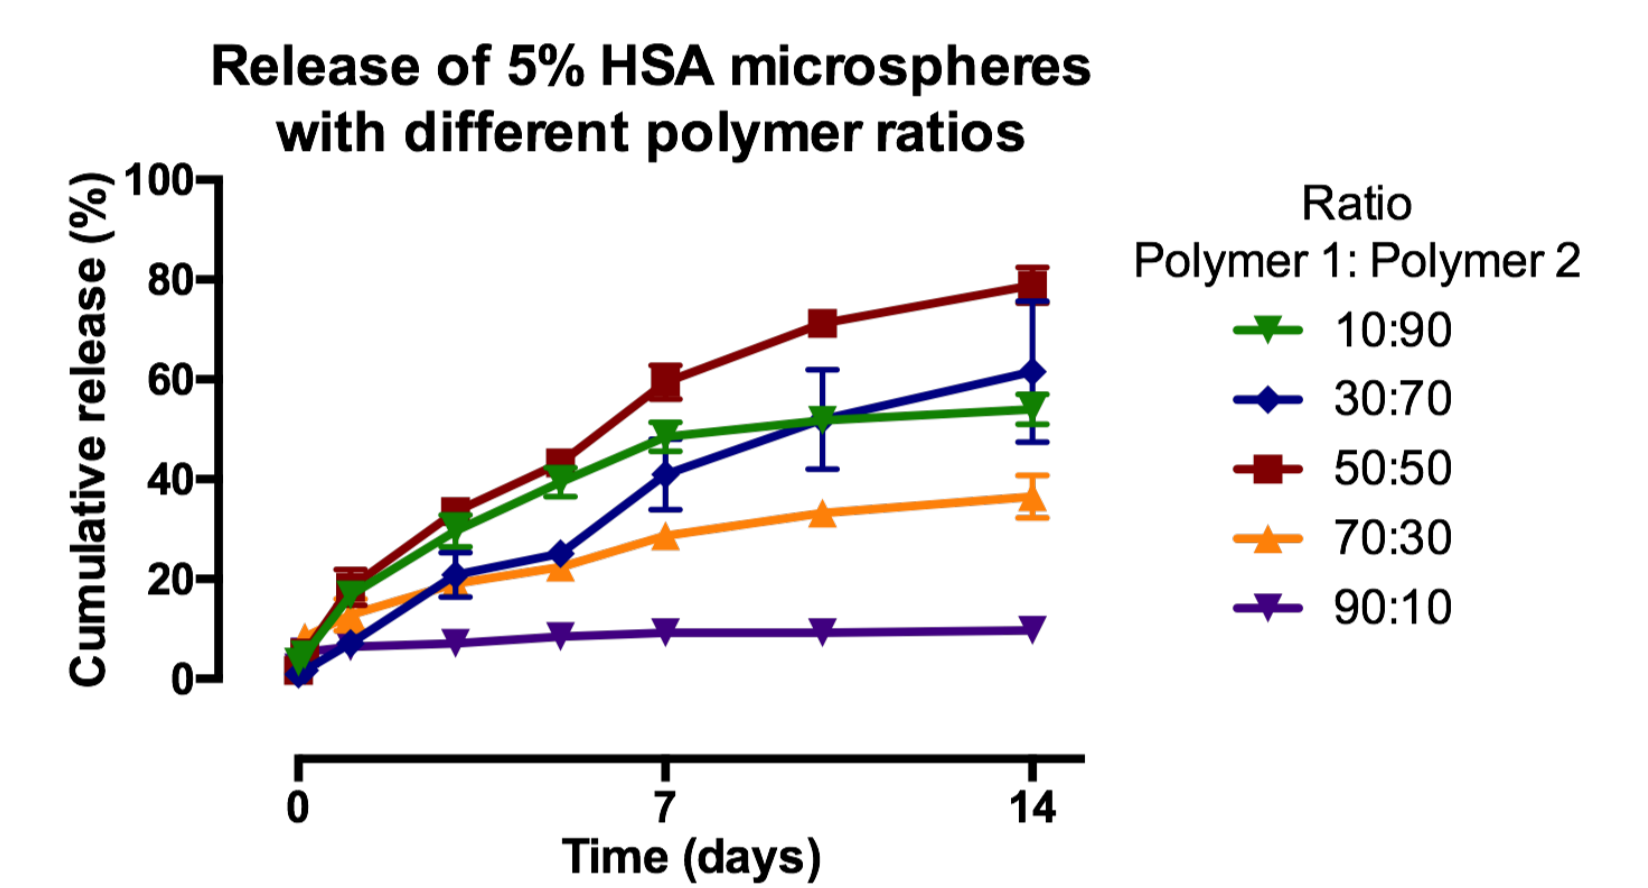

- Release accelerates with increasing content of polymer 2.
- 50:50 ratio is an exception: this formulation shows the fastest release.
- The burst release of all ratios is negligible.


In vitro release of microspheres for in vivo experiment

In vitro total protein release of 5% HSA and 3% pPB-HSA / 2% HSA microspheres

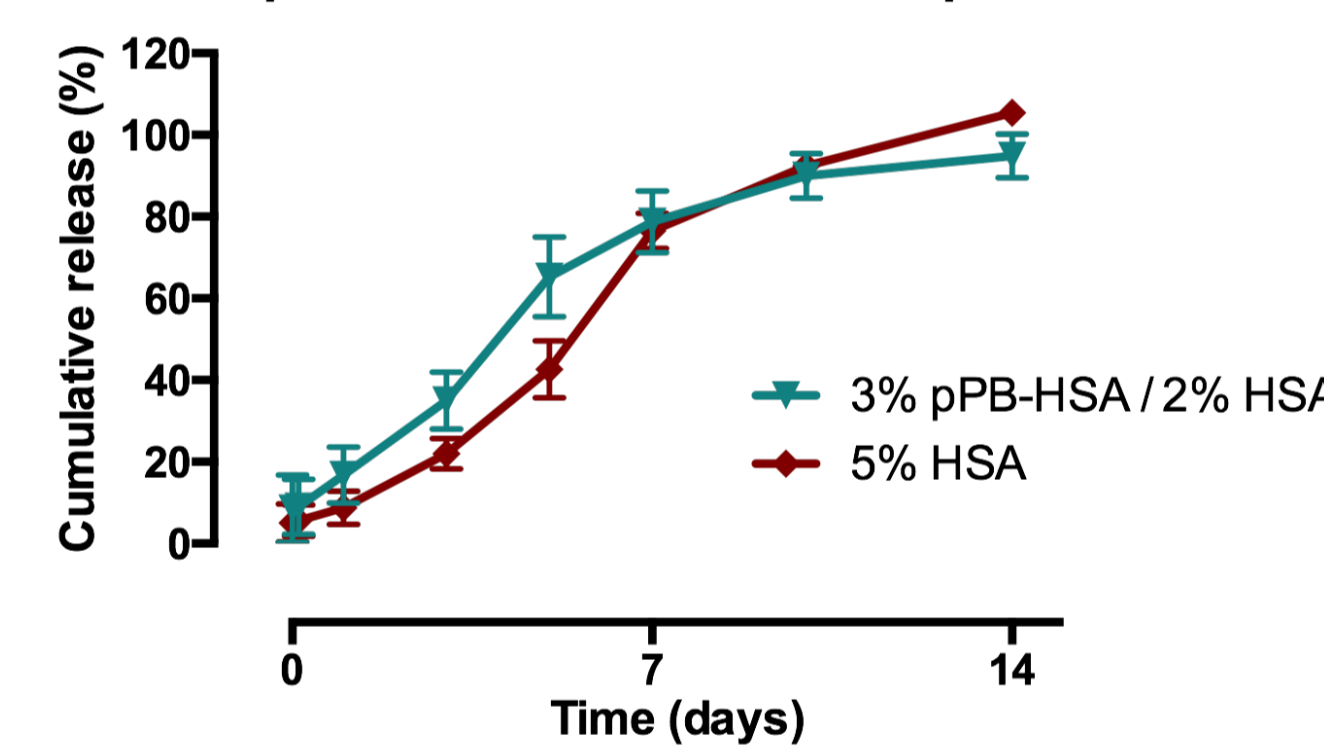

- The *in vitro* total protein release of the two batches is comparable. After 7 days, 80% has been released.
- The release of pPB-HSA from the microspheres shows the same profile as the total protein release.


In vitro release of 3% pPB-HSA / 2% HSA microspheres

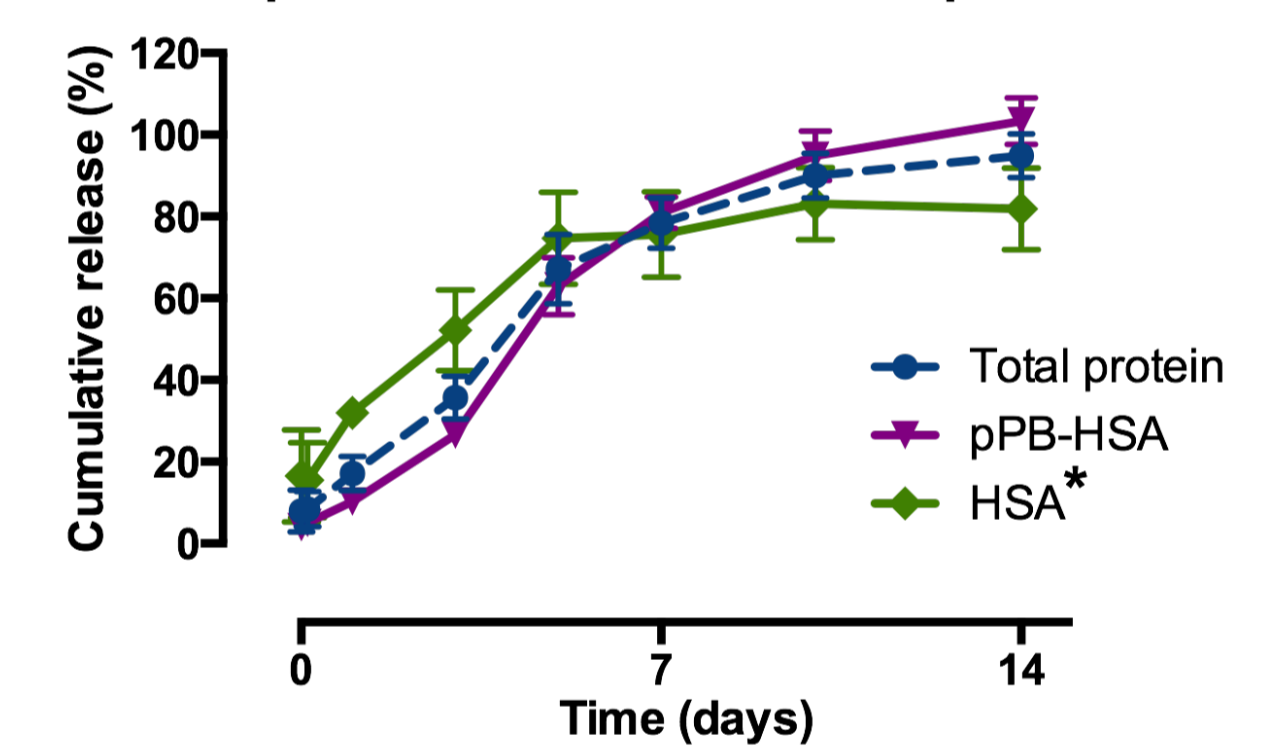

* HSA release data were calculated as: total protein released - pPB-HSA released.

Results – in vivo experiment


pPB-HSA in plasma of UUO mice

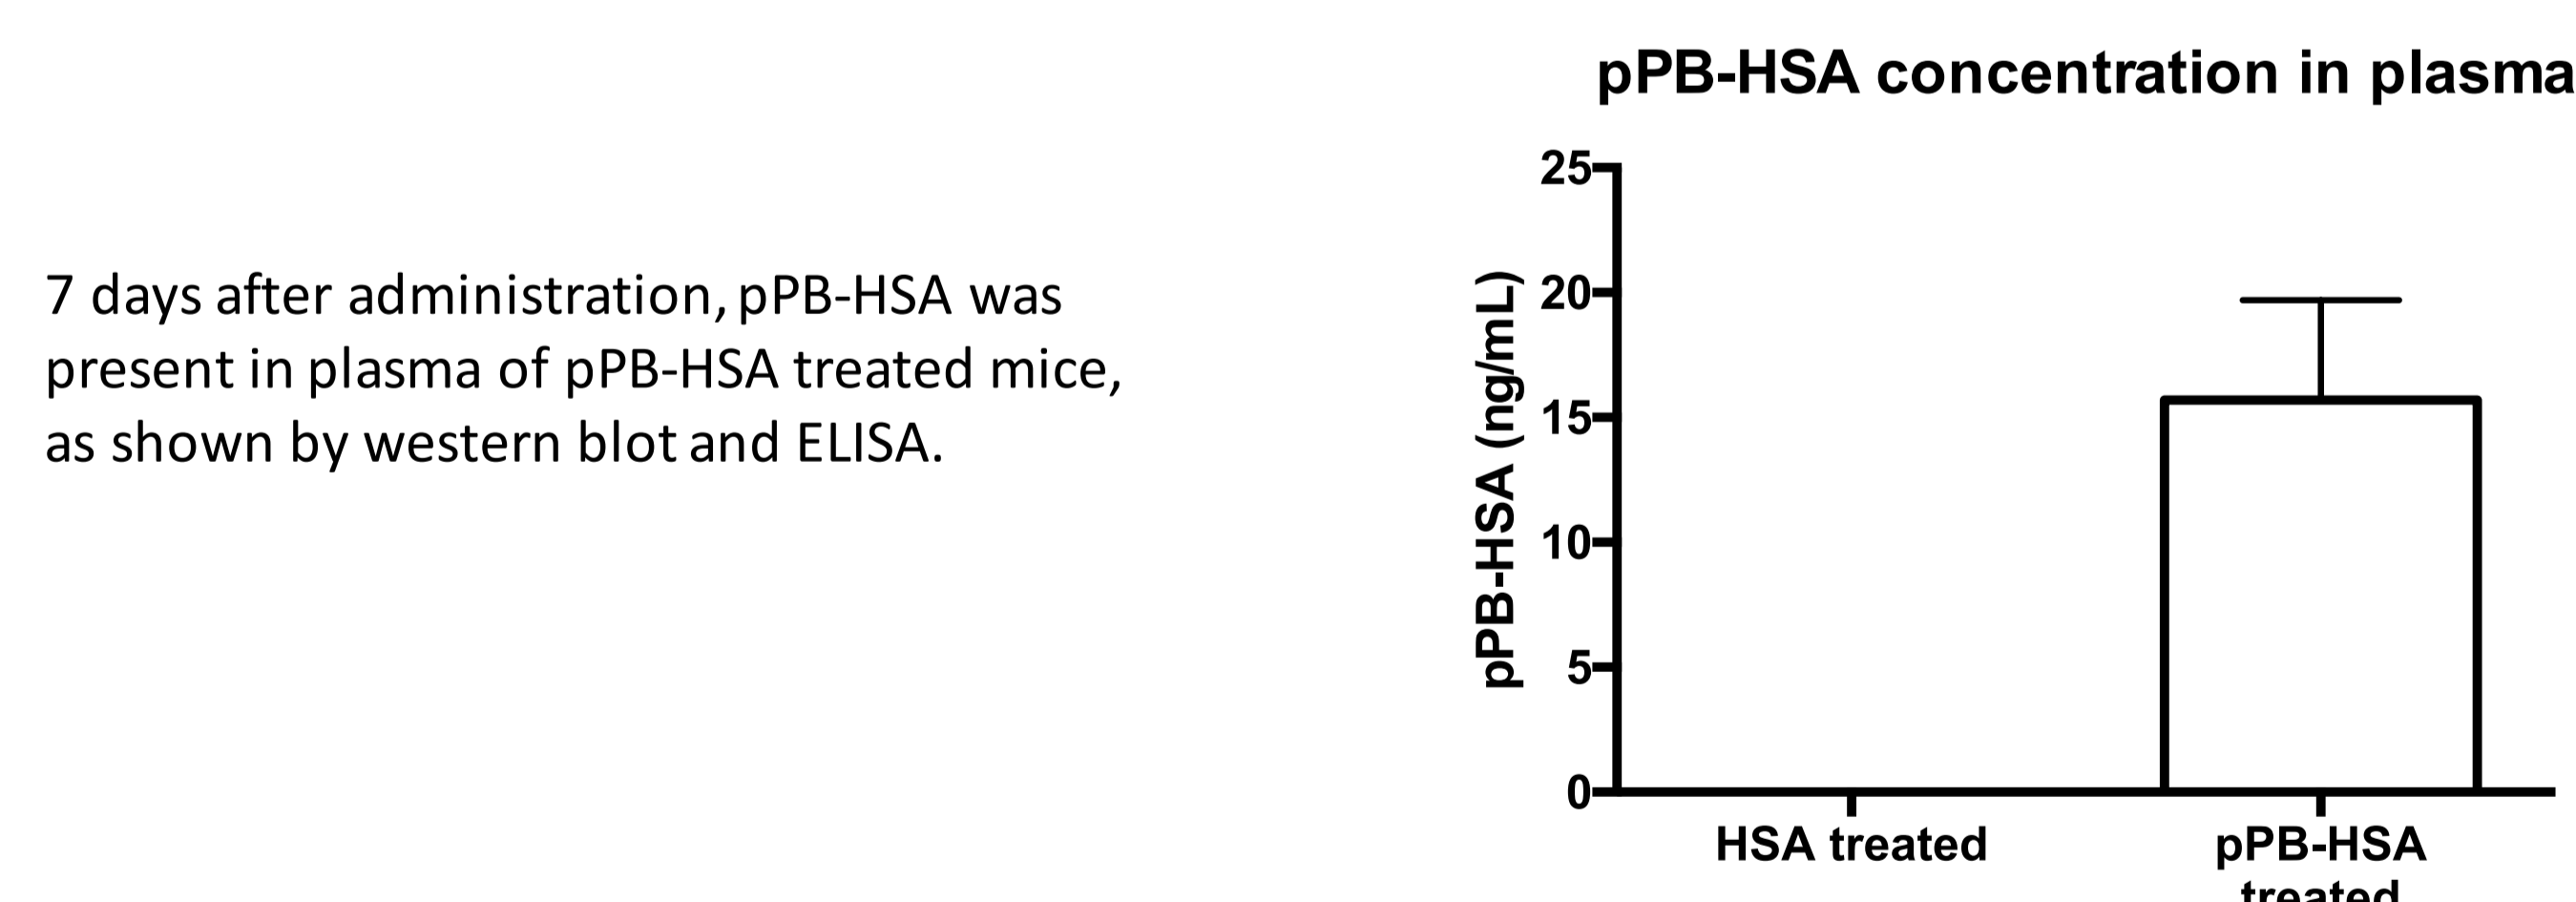

7 days after administration, pPB-HSA was present in plasma of pPB-HSA treated mice, as shown by western blot and ELISA.


pPB-HSA detection in the target organ: fibrotic kidney

Protein level of HSA in sham and UUO kidneys

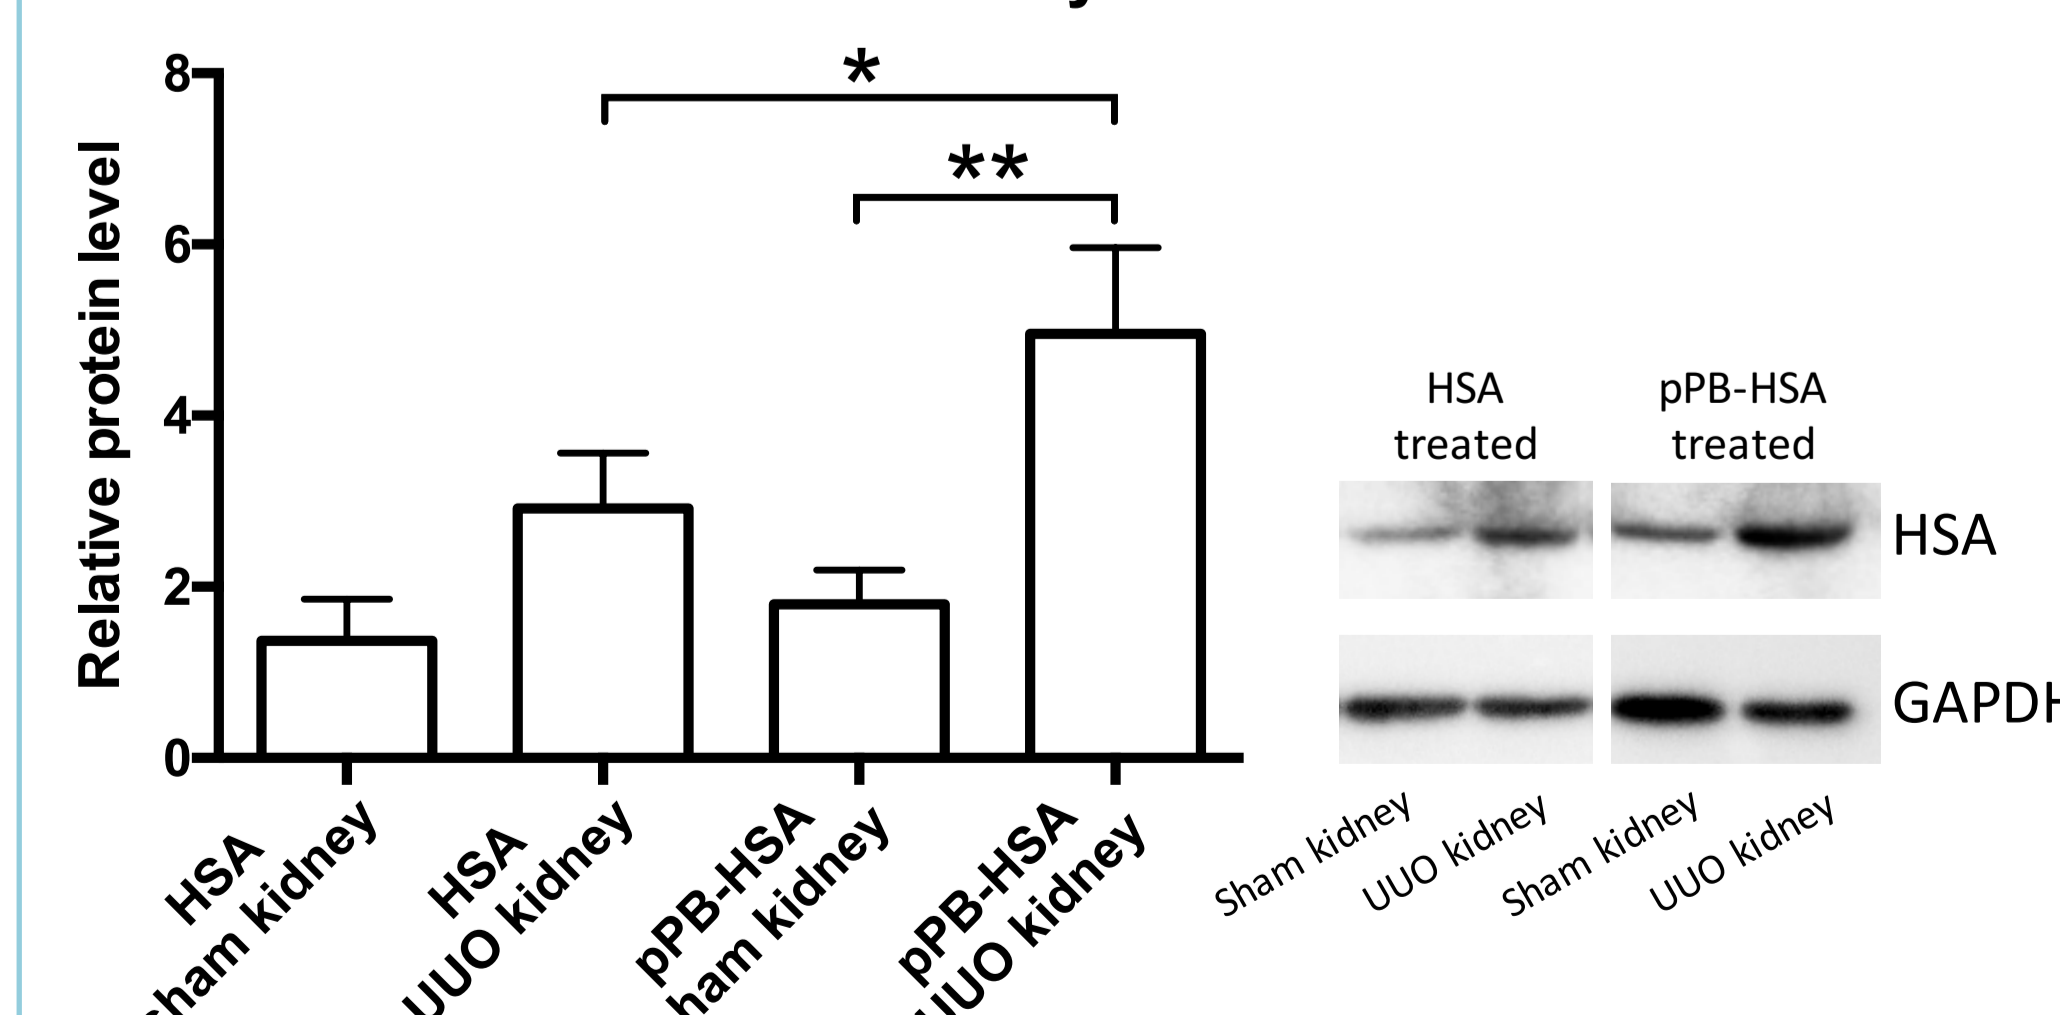

Western blot analysis convincingly shows specific targeting of released pPB-HSA to the fibrotic kidney. Moreover, the leakage of HSA to the fibrotic kidney is not significant.

pPB staining, pPB-HSA treated mice

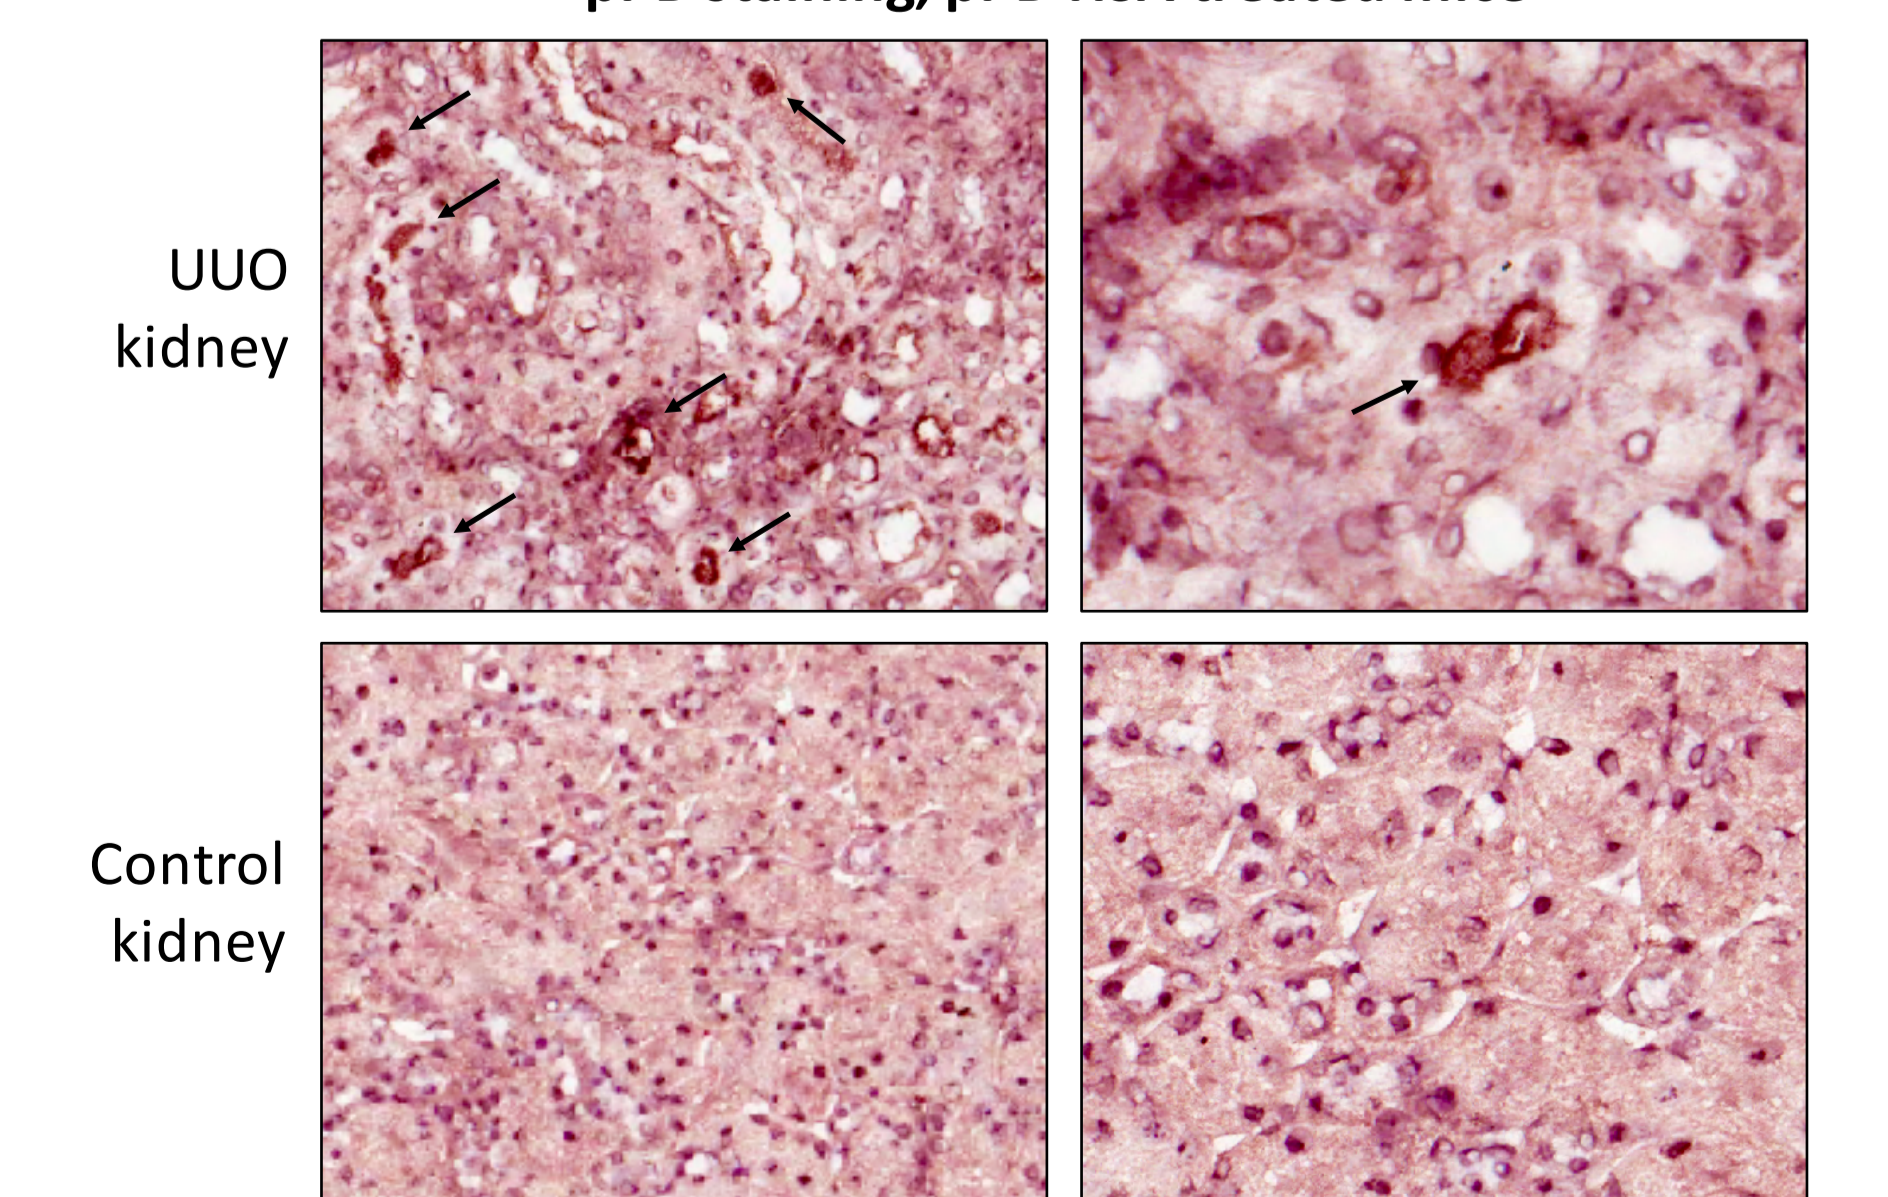

pPB-HSA is present in UUO kidney tissue of pPB-HSA treated mice.

