

Reactive melt infiltration of carbon fibre reinforced ZrB<sub>2</sub>/B composites with Zr<sub>2</sub>Cu

*Original*

Reactive melt infiltration of carbon fibre reinforced ZrB<sub>2</sub>/B composites with Zr<sub>2</sub>Cu / Vinci, A.; Zoli, L.; Galizia, P.; Kutemeyer, M.; Koch, D.; Sciti, D.. - In: COMPOSITES. PART A: APPLIED SCIENCE AND MANUFACTURING. - ISSN 1359-835X. - STAMPA. - 137:(2020), p. 105973. [10.1016/j.compositesa.2020.105973]

*Availability:*

This version is available at: 11583/2952099 since: 2022-01-21T14:09:24Z

*Publisher:*

Elsevier Ltd

*Published*

DOI:10.1016/j.compositesa.2020.105973

*Terms of use:*

openAccess

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

Elsevier postprint/Author's Accepted Manuscript

© 2020. This manuscript version is made available under the CC-BY-NC-ND 4.0 license  
<http://creativecommons.org/licenses/by-nc-nd/4.0/>. The final authenticated version is available online at:  
<http://dx.doi.org/10.1016/j.compositesa.2020.105973>

(Article begins on next page)

## Reactive melt infiltration of carbon fibre reinforced ZrB<sub>2</sub>/B composites with Zr<sub>2</sub>Cu

Antonio Vinci<sup>1</sup>, Luca Zoli<sup>1</sup>, Pietro Galizia<sup>1</sup>, Marius Küttemeyer<sup>2</sup>, Dietmar Koch<sup>3</sup>, Diletta Sciti<sup>1</sup>

<sup>1</sup> *CNR-ISTEC, Institute of Science and Technology for Ceramics, Via Granarolo 64, I-48018 Faenza, Italy*

<sup>2</sup> *Spicetech GmbH, Schloßstraße 59 C, 70176 Stuttgart, Germany*

<sup>3</sup> *University of Augsburg, Institute for Materials Resource Management, Am Technologiezentrum 5, 86159 Augsburg, Germany*

### Abstract

The microstructure and mechanical properties of carbon fibre reinforced ZrB<sub>2</sub> composites produced by slurry infiltration and consolidated by reactive melt infiltration were investigated. Fibres were preliminary infiltrated with ZrB<sub>2</sub>/B slurries with varying ZrB<sub>2</sub>/B ratios. Then the composites were infiltrated with Zr<sub>2</sub>Cu melt at 1200°C under vacuum. Boron was chosen as the reactant phase, while raw ZrB<sub>2</sub> was added as a filler to prevent excessive swelling. With increase of boron content the infiltration becomes more difficult due to the reaction of alloy and boron. The boron is completely converted to nano ZrB<sub>2</sub> grains. Some ZrC is produced from the side reaction between Zr<sub>2</sub>Cu and the carbon fibre, resulting in reduction of fibre diameter. The flexural strength increased from 360 to 560 MPa with the increase of boron content, while K<sub>Ic</sub> amounted to 10 MPa·m<sup>0.5</sup> but was affected by large scatter. The mechanical behaviour was mostly dominated by matrix properties.

### Keywords

Ceramic-matrix composites (CMCs); Liquid metal infiltration; Microstructural analysis; Mechanical properties;

### 1. Introduction

The increasing demand for materials able to withstand extreme conditions and surpass the current state of the art C/C or C/SiC based CMCs has led to the design and development of a new class of CMCs based on a UHTC matrix, called UHTCMCs [1][2][3][4][5][6]. UHTCs are a class of materials characterized by

Corresponding author: [antonio.vinci@istec.cnr.it](mailto:antonio.vinci@istec.cnr.it)

1 extremely high melting points and comprise the borides and carbides of early transition metals such as ZrB<sub>2</sub>,  
2 HfB<sub>2</sub>, ZrC, etc [7][8][9]. They possess high temperature strength, high thermal conductivity and good  
3  
4 oxidation resistance when doped with silicon-containing additives and have been extensively investigated as  
5  
6 candidates for the fabrication of reusable components for aerospace re-entry or hypersonic flight [10].  
7  
8 However their low fracture toughness and propensity to brittle fracture severely limits their application [11].  
9  
10 By substituting the ceramic matrix of conventional CMCs, based on silicon carbide which is not suitable  
11  
12 above 1600°C, with a UHTC matrix, it is possible to maintain the high damage tolerance provided by the  
13  
14 fibres and the high temperature resistance of UHTCs. Within the framework of the C<sup>3</sup>harne project, these  
15  
16 materials were tested and validated for the use in extreme environments [10][12]. Several routes have been  
17  
18 explored for the fabrication of this novel class of materials:  
19  
20

- 21 - Radiofrequency assisted chemical vapour infiltration (RF-CVI) of carbon on a 2.5 D carbon preform  
22  
23 impregnated with ZrB<sub>2</sub> or HfB<sub>2</sub> particles [13]  
24  
25
- 26 - Polymer infiltration and pyrolysis of carbon fibres with SiC precursors doped with UHTC particles,  
27  
28 [14].  
29  
30
- 31 - Slurry infiltration of carbon fibres with ZrB<sub>2</sub>/SiC based suspensions, followed by hot pressing or  
32  
33 spark plasma sintering [4][5][15].  
34

35 An alternative route for the fabrication of carbon fibre reinforced ZrB<sub>2</sub> composites is based on the slurry  
36  
37 infiltration of a fibre preform with boron-containing powders (i.e. B, B<sub>4</sub>C) followed by reactive melt  
38  
39 infiltration (RMI) with liquid zirconium alloys. Typically, Zr<sub>2</sub>Cu alloy is employed as liquid melt due to its  
40  
41 lower melting point (~1000°C) compared to elemental zirconium (1855°C), to form in-situ ZrB<sub>2</sub> and Cu  
42  
43 according to reaction 1:  
44  
45



53 This allows to obtain nearly full density materials without the need of high temperatures and pressures  
54  
55 required for the conventional sintering of UHTCs. The main drawbacks of this process are linked to the  
56  
57 powder wettability, which may hinder infiltration, and the presence of residual melt at the end of the  
58  
59 infiltration which can lower the high temperature mechanical properties. Moreover, the formation of in-situ  
60  
61

1 ZrB<sub>2</sub> leads to a volume expansion which may choke infiltration at the reaction front or delaminate the  
2 composite.

3  
4 In order to achieve the homogenous infiltration of the slurry infiltrated preform, a high degree of porosity and  
5 capillary forces are required, as well as a low contact angle between the reactive melt and the substrate.

6  
7  
8 Previous studies on the wettability of Zr- alloys with different substrates reported low contact angles between  
9 ZrB<sub>2</sub> and Zr-Cu alloys [16], and contact angles below 90° on a carbon substrate at 1200°C [17]. Furthermore,  
10 the addition of 1% boron in the Zr<sub>2</sub>Cu alloys allows to lower the melting temperature while still maintaining  
11 low contact angles with the substrates [17][18] [19]. It is essential to infiltrate a Si free preform in order to  
12 stay clear of Zr-Si phases and their large volume expansion.  
13  
14  
15  
16  
17  
18

19  
20 In the present work carbon fibre reinforced ZrB<sub>2</sub>/ZrC composites were fabricated via RMI. The use of  
21 a protective coating was intentionally avoided since the goal of this work was to study and limit the extent of  
22 reaction of the molten phase with the fibres [18]. Different compositions in terms of ZrB<sub>2</sub>/B volumetric filler  
23 ratio were evaluated. Microstructure and mechanical properties were analysed and compared.  
24  
25  
26  
27  
28  
29  
30

## 31 **2. Experimental**

### 32 *2.1. Materials*

33  
34  
35 For the preparation of ceramic slurries, the following powders were used: ZrB<sub>2</sub> powder (H.C. Starck,  
36 grade B, Germany, specific surface area 1.0 m<sup>2</sup>/g, particle size range 0.5-6 µm, impurities (wt.%): 0.25 C, 2  
37 O, 0.25 N, 0.1 Fe, 0.2 Hf), elemental Boron 95% (TRADIUM GmbH, Germany, particle size 1.08 µm,  
38 impurities (wt.%): 0.30 Mg, 0.12 H<sub>2</sub>O, 0.25 B(OH)<sub>3</sub>, 0.91 H<sub>2</sub>O<sub>2</sub>), Zr<sub>2</sub>Cu (Additional alloying element: 1%  
39 boron, HMW Hauner GmbH & Co. KG). Unidirectional Ultra-High modulus carbon fibre cloths were chosen  
40 for the infiltration processes (Granoc, XN80-6K fibres; tensile modulus 780 GPa, tensile strength 3.4 GPa, Ø  
41 = 10 µm, supplier: G. Angeloni).  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53



### 54 *2.2 Process*

55  
56  
57 Aqueous powder suspensions containing elemental boron and commercial zirconium diboride in varying  
58 ratios were prepared following the procedures described in previous works [20]. With these slurries,  
59  
60  
61  
62

63 Corresponding author: [antonio.vinci@istec.cnr.it](mailto:antonio.vinci@istec.cnr.it)  
64  
65

1 unidirectional fibre fabrics of dimensions  $50 \times 50$  mm were infiltrated, stacked in a unidirectional  
2 configuration and then dried at  $100^{\circ}\text{C}$  in an oven. The ratio between the fibre and the ceramic powder  
3 volumetric amount was maintained at 1:1 for all compositions by adjusting the slurry rheology. Composites  
4 were labelled based on the powder compositions: B25 (25% B, 75%  $\text{ZrB}_2$  vol), B50 (50% B, 50%  $\text{ZrB}_2$  vol),  
5 B75 (75% B, 25%  $\text{ZrB}_2$  vol). Then the green bodies were clamped between two graphite plates and attached  
6 to a sample holder by a screw inside a furnace, while the  $\text{Zr}_2\text{Cu}$  powder was placed in a graphite crucible at  
7 the bottom of the furnace: the furnace was heated to  $1200^{\circ}\text{C}$  at a rate of  $500^{\circ}\text{C}/\text{h}$  in argon atmosphere in order  
8 to melt the  $\text{Zr}_2\text{Cu}$  without causing bubbling of the melt. Once the target temperature was reached, the chamber  
9 was evacuated to a pressure  $< 5$  mbar and the sample was submerged in the melt for 2 min at half height and  
10 then taken out. After the RMI process, the chamber was cooled down to a rate of  $300^{\circ}\text{C}/\text{h}$ . Sample B75  
11 required a second infiltration cycle due to excessive volume expansion from the formation of in-situ  $\text{ZrB}_2$  and  
12 premature halt of the infiltration at the reaction front. The process is illustrated in figure 1.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

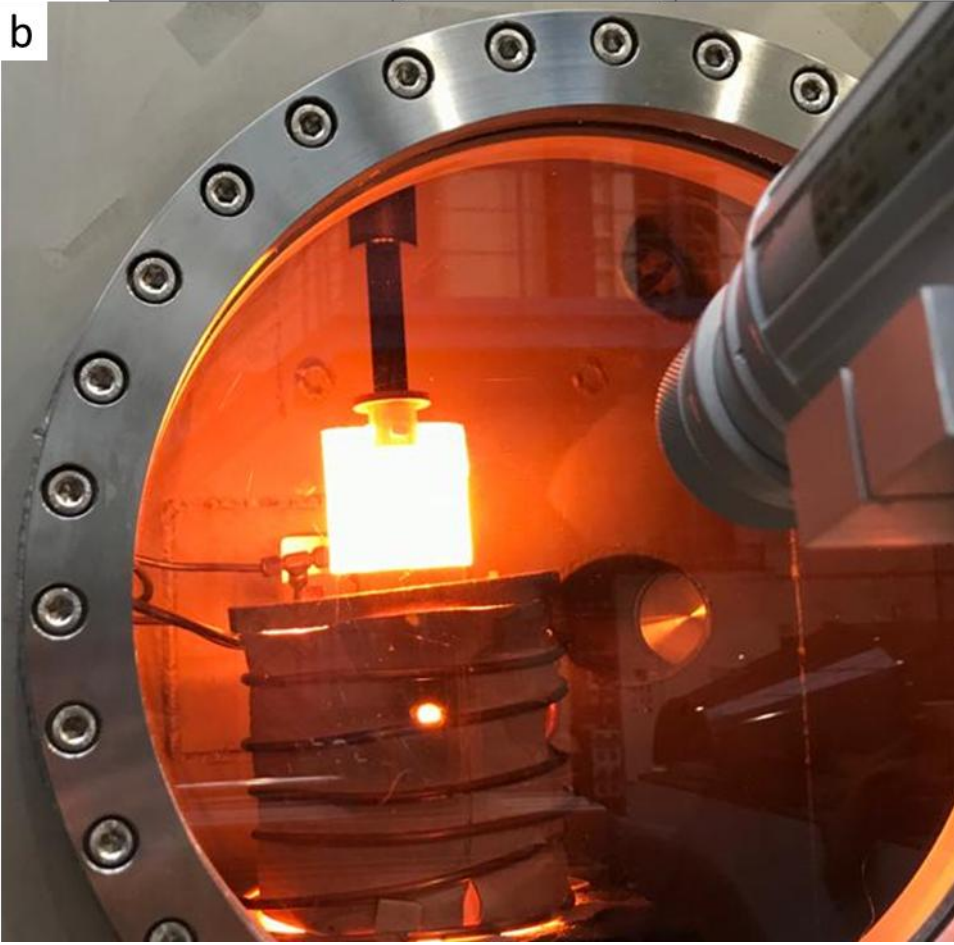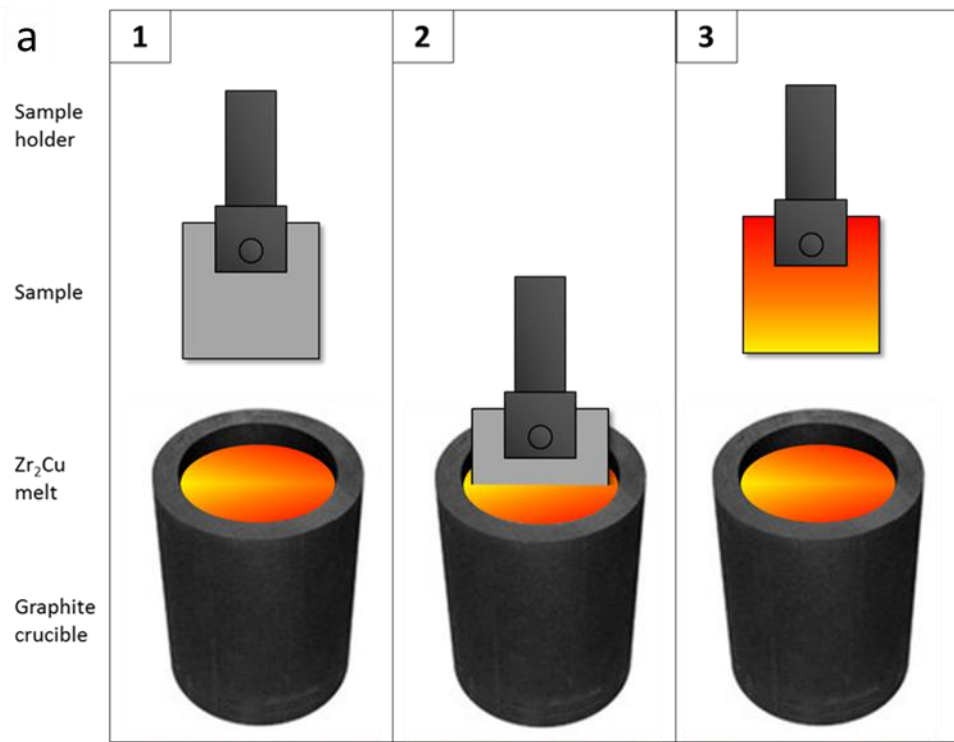

**Figure 1.** RMI process: a) the sample is clamped between two graphite plates and submerged at half height inside the  $Zr_2Cu$  melt. After 2 min, the melt has infiltrated the entire sample. b) Picture of the sample infiltrated with the reactive melt

Corresponding author: [antonio.vinci@istec.cnr.it](mailto:antonio.vinci@istec.cnr.it)

### 2.3. Microstructure analysis

The composites microstructure was analysed on polished and fractured surfaces by field emission scanning electron microscopy (FE-SEM, Carl Zeiss Ultra 55 Plus, Germany) and energy dispersive X-ray spectroscopy (EDX, AZtec, Oxford instruments, UK). Samples for microscopy were polished down to a 0.25  $\mu\text{m}$  finish with diamond abrasives using a semi-automatic polishing machine. The polished samples were then washed with ethanol in an ultrasonic bath for 5 min up to 3 times and then dried for 1h at 80°C in an oven. The slurry infiltrated carbon preform had a nominal porosity of 40%, determined as geometric porosity. Taking into account a fibre/matrix ratio of 1:1, the initial fibre amounts for all specimens was ~35%. The final fibre volumetric amount after RMI was measured by image analysis on the polished surfaces of the samples with software Image Pro Analyser 7.0. The composition and phases formed after RMI were also analysed by X-ray diffraction analysis (Bruker AXS D8 with Cu K $\alpha$  ( $\lambda = 154 \text{ pm}$ ), Germany). The final density was measured through the geometrical method.

### 2.4. Mechanical properties

Flexural strength was evaluated by four-point bending on specimens 25 mm  $\times$  2.5 mm  $\times$  2 mm in size using a fully articulated steel fixture having a lower span of 20 mm and an upper span of 10 mm and at a cross-head rate of 1 mm/min, following the guidelines of standard ISO 14704:2016 (EN). Even though for fibre reinforced composites a high span/thickness ratio is typically advised, the available material was not enough to fabricate larger specimens. Flexural strength was evaluated along the fibre orientation to better understand the contribution provided by the fibre reinforcement. Fracture toughness ( $K_{Ic}$ ) was evaluated by four-points chevron notch bending tests (CNB) following standard ASTM C1421. The specimens were 25 mm  $\times$  2 mm  $\times$  2.5 mm<sup>3</sup> (length  $\times$  width  $\times$  thickness) and were notched with a 0.1 mm-thick diamond saw. The chevron-notch tip depth and average side length were about 0.12 and 0.80 of the bar thickness, respectively. The crosshead speed was 0.05 mm/min. The “slice model” equation of Munz et al. [33] was used to calculate  $K_{Ic}$ .

### 3. Results and discussion

#### 3.1 Microstructure of the sintered material

Microstructural features of the materials fabricated are reported in Table 1. All composites were fully dense, with densities ranging between  $6.1 \text{ g/cm}^3$  and  $6.6 \text{ g/cm}^3$ . The final fibre volumetric amounts were lower than the starting ones due to sample swelling and fibre degradation. The grain size of  $\text{ZrB}_2$  filler increased slightly with the increase of boron content, but was still comparable with the starting size of the powders.


**Table 1.** Values of bulk density, porosity, fibre content, ZrC content and  $\text{ZrB}_2$  particle size (from powders and RMI respectively)

Sample	Density ( $\text{g/cm}^3$ )	Porosity (vol%)	Fibre volume after RMI (vol%)	$\text{ZrB}_2$ grain size powders ( $\mu\text{m}$ )	$\text{ZrB}_2$ grain size RMI (nm)
B25	6.36	< 1	$13.4 \pm 0.4$	2.30	140
B50	6.64	< 1	$16.5 \pm 1.4$	2.45	170
B75	6.12	< 1	$24.7 \pm 4.5$	3.00	290

X-Ray diffraction analysis was carried out on the polished cross section of sample B25 (Fig. 2), used as reference. The main peaks were indexed to  $\text{ZrB}_2$  (PDF#34-0423) and ZrC (PDF#65-0973). Only one  $\text{ZrB}_2$  phase was revealed, suggesting that the in-situ  $\text{ZrB}_2$  had the same structure of the one already present in the form of powders. No carbon was detected, while intense peaks from ZrC originating from carbon consumption were observed. Smaller peaks were attributed to the residual melt alloy Zr-Cu.




1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

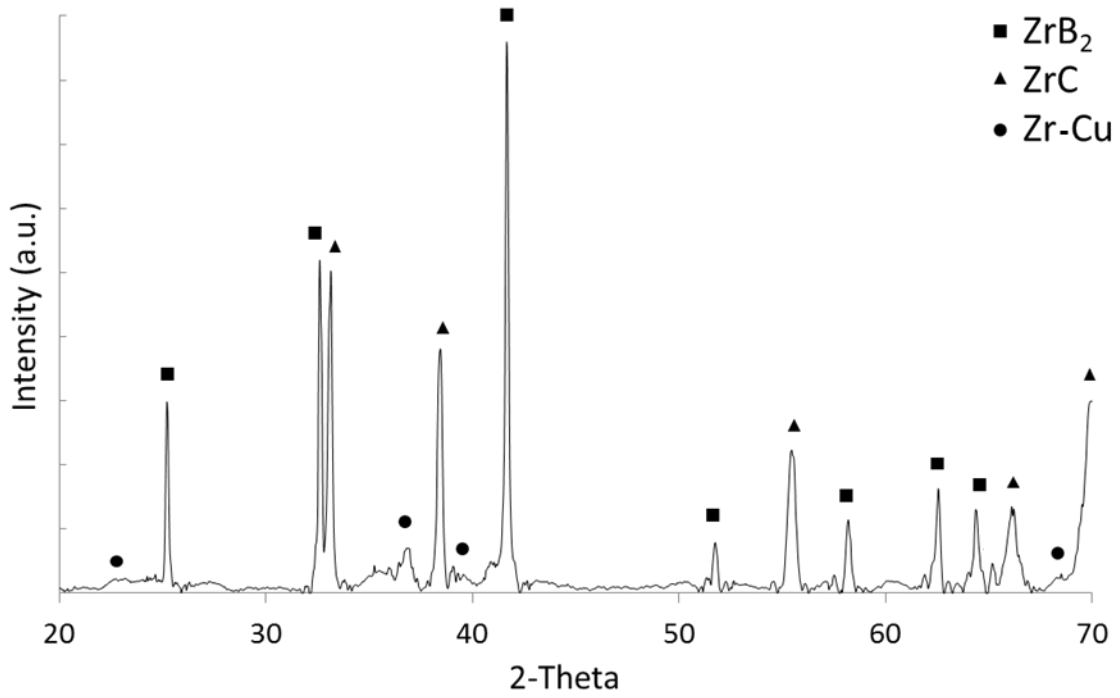

**Figure 2.** X-Ray diffraction pattern on the polished cross section of sample B25 after infiltration with  $Zr_2Cu$ . The phases detected were  $ZrB_2$  (PDF#34-0423),  $ZrC$  (PDF#65-0973) and the leftover alloy  $Zr-Cu$ .

All specimens were characterized by very similar microstructure. As an example, the low magnification micrograph of sample B25 is reported in figure 3.

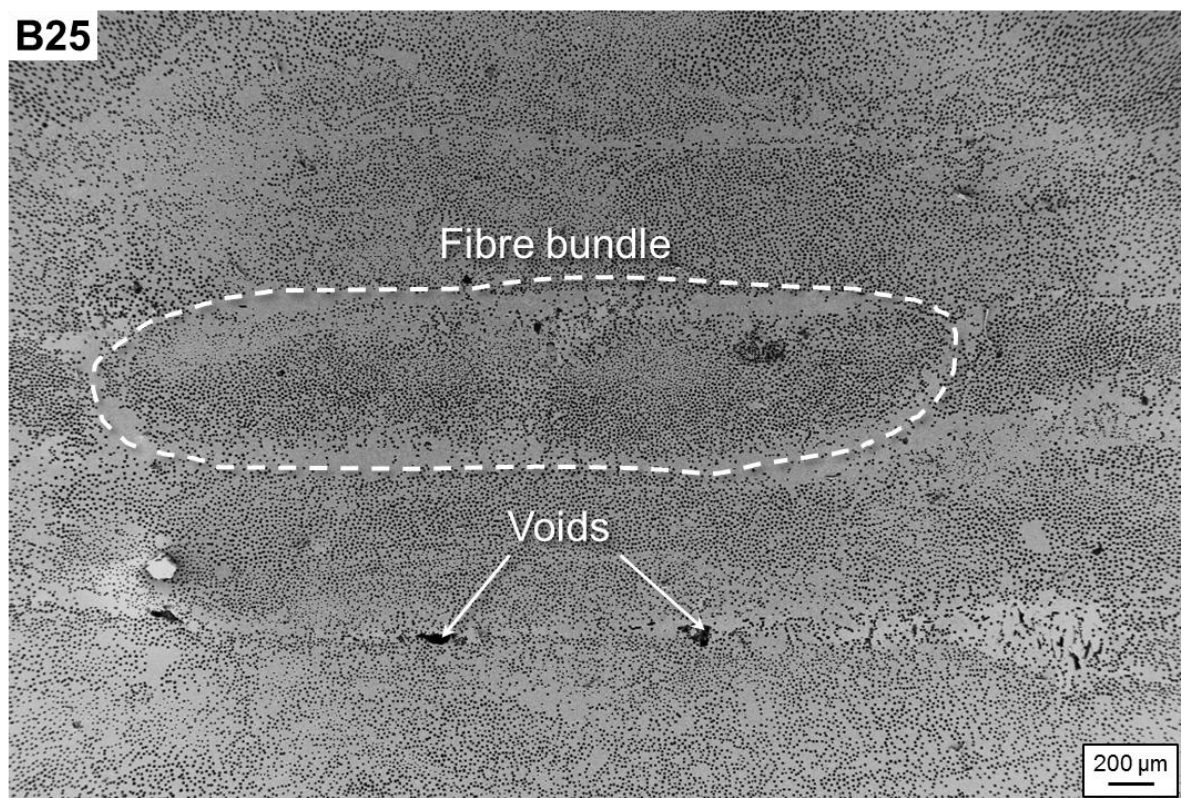

1  
2 **Figure 3.** Low magnification micrograph of sample B25 showing the fibre distribution in the ceramic matrix and the  
3 most common defects (voids) between layers.  
4  
5

6 All samples underwent due to RMI swelling and were covered with residual  $Zr_2Cu$  that was machined off.  
7

8 The microstructures were almost flawless with sporadic voids between fibre bundles or between layers due to  
9 incomplete infiltration. The fibres were homogeneously distributed in the ceramic matrix for all samples.  
10


11 SEM micrographs in figure 4 show the typical fiber distribution and the fiber/matrix interface. For all the  
12 samples the final fibre content measured by image analysis (Table 1) was much lower than the initial ones: 13,  
13 17, 25% for B25, B50 and B75 respectively, and this was reflected in the high densities of the specimens.  
14  
15  
16  
17  
18

19 There are two main explanations to this phenomenon:  
20

21 1) the starting fibre volumetric amount in the slurry infiltrated preform, taking into account a porosity of 40%,  
22 was ~35 vol%; since the specimens experienced a volume expansion, due to the formation of  $ZrB_2$  and  $ZrC$ , of  
23 up to ~30% during RMI, the final fibre content, normalized on the final composite volume, was lower (25 –  
24 30%)  
25  
26  
27  
28  
29

30 2) a large fraction of the fibres reacted with the surrounding  $Zr_2Cu$  melt leading to the formation of  $ZrC$  at the  
31 interface, further lowering the final carbon fibre content.  
32  
33

34 All samples contained large amounts of unreacted melt which contributed to increase the final density of the  
35 materials., essentially filling the voids in between the  $ZrB_2$  and  $ZrC$  grains. Earlier attempts aimed at reducing  
36 the final residual melt amount resulted in incomplete infiltration.  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

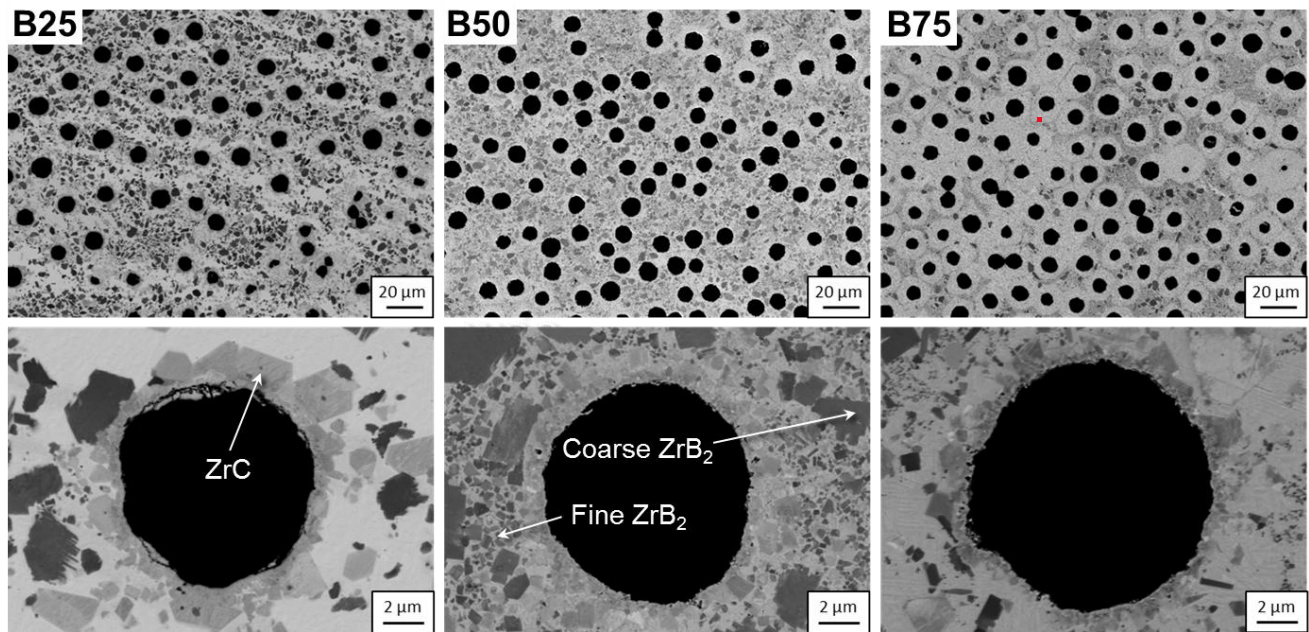


**Figure 4.** SEM image of the polished cross section of samples B25, B50 and B75. The black phase is carbon from the fibres, dark grey and light grey phases are  $ZrB_2$  and  $ZrC$  respectively while the white phase is the residual  $Zr_2Cu$  melt.

The microstructure of B50 was very similar to that of B75. Cubic  $ZrC$  grew on the surface of the fibres as the latter reacted with the melt. Fibre-dense regions were affected by fibre degradation to a lesser degree, whereas less infiltrated peripheral fibres were almost completely converted into  $ZrC$ . This effect was previously observed on  $ZrB_2/SiC$  composites obtained by sintering, in which peripheral fibres surrounded by large amount of ceramic matrix would often show strong signs of reaction [6].

Fibres were surrounded by a rim of  $ZrC$  which originated from the reaction between the carbon of the fibre and the liquid melt according to the reaction 1. In order to quantify the degree of fibre consumption, the fibre diameter distribution was evaluated by image analysis and compared with a standard sample containing the same fibres in a  $SiC$  matrix obtained by PIP (figure 5). The mean diameter of the fibres used in this work, XN80, was  $10\ \mu m$ . For sample B25, a bimodal distribution of fibres diameter was observed, with mean diameters of  $6.7\ \mu m$  and  $10\ \mu m$  respectively. This was attributed to the inhomogeneity of the sample that was characterized by fibre dense regions where fibres retained their size, and matrix dense regions where most fibres reacted. This measurement was likely overestimated because it was not possible to detect those fibres that were completely converted into  $ZrC$ . For samples B50 and B75 the degree of fibre degradation was lower. These samples were characterised by mean fibre diameters of  $9.3\ \mu m$  and  $8.6\ \mu m$  respectively, indicating that

1 up to 19% of the fibre was consumed in the process. B25 was the most affected by it because it also had a  
2 very high content of unreacted melt. On the other hand, B50 and B75 were very similar in this regard. The  
3 reason why B75 showed a slightly higher degree of fibre degradation could be attributed to the higher amount  
4 of energy generated from the exothermic reaction of boron with the reactive melt. The second infiltration  
5 might also have contributed. Even though B50 was characterized by the lowest degree of reaction, B75  
6 retained the highest fibre content (table 1). This was attributed to the higher extent of swelling after RMI for  
7 B50 compared to B75 and the higher amount of unreacted alloy in the matrix that contributed to further  
8 lowering the fibre content and increase the density. On the other hand, the infiltration of B75 was much more  
9 difficult because the infiltration process would come to an early halt, and not much residual alloy would be  
10 left over. Theoretically, the higher the boron content, the higher the volume expansion from the formation of  
11 new  $ZrB_2$ . However, with the increase of boron, infiltration also becomes more difficult. The result is that the  
12 majority of the swelling was mostly due to the melt infiltrating the sample and spreading the fibres. While  
13 infiltration was easy for B25 and B50 (higher melt mobility and lower viscosity because of medium/low  
14 amount of boron), it was very difficult for B75, which was the least subjected to swelling as it was barely  
15 infiltrated and required a 2nd infiltration that still did not lead to full material infiltration. Only 3 cm of  
16 material were infiltrated, while for B25 and B50 it was possible to infiltrate up to 5 cm.  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65




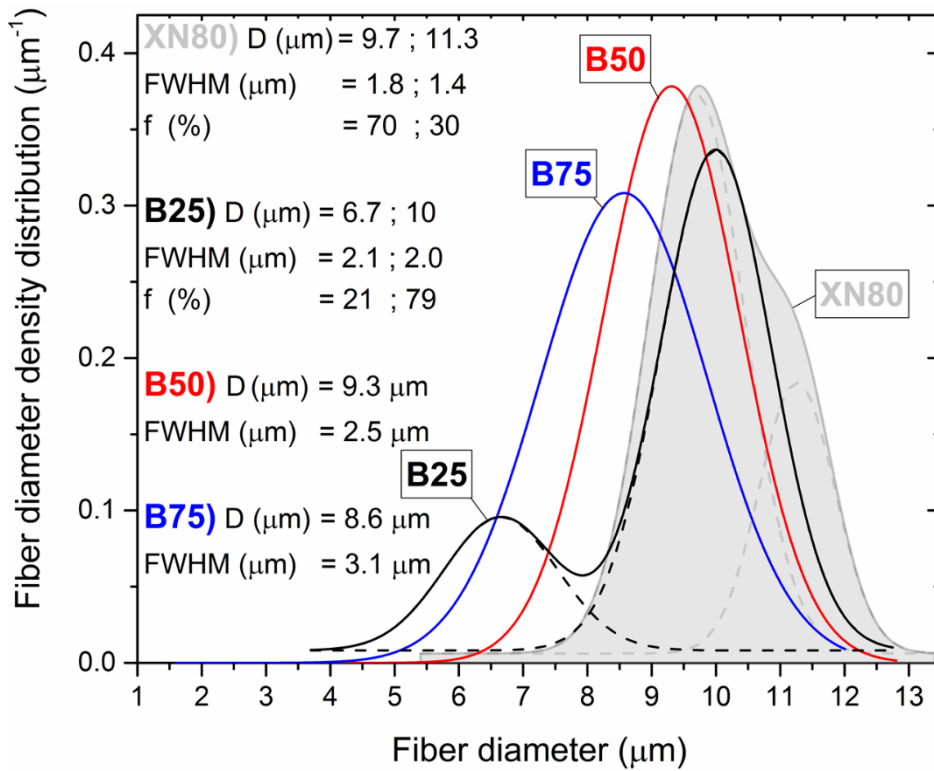

**Figure 5.** Mean fibre diameter distribution for a standard sample obtained by PIP where fibres were unreacted (XN80), compared to the samples obtained by RMI, B25, B50 and B75. For XN80 and B25, a bimodal distribution was observed.

From SEM-EDS analysis on the specimens after RMI (figure 6), two types of  $ZrB_2$  phases were identified: large grains (2 – 3 µm) came from the starting commercial powders that were used as a filler, while the fine grains (< 300 nm) originated from the reaction between boron and the reactive melt and were homogeneously dispersed in the Zr-Cu alloy. These small particles had very well defined borders and geometries and were often found as closely packed clusters. These are very typical of cermets obtained by RMI or reactive hot pressing, where the small reactant particles react with the melt and give rise to the formation of these plate-like crystals [21][22][23].


1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

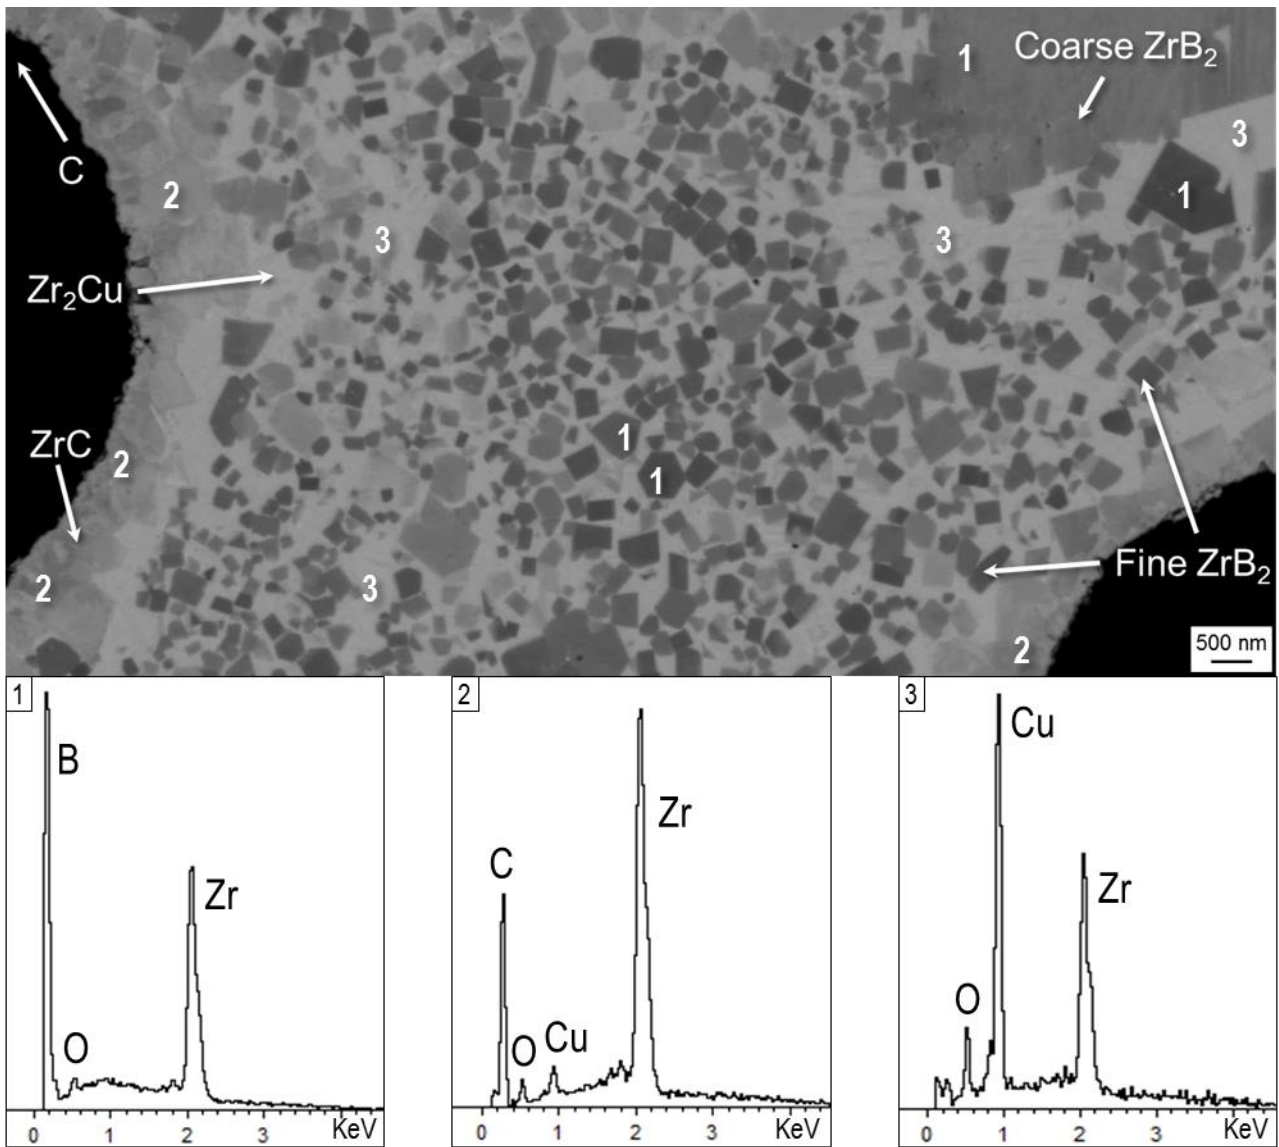

**Figure 6.** Detail of the microstructure of B75 showing the ZrC rim around fibres, coarse ZrB<sub>2</sub> from the starting powders (filler) and the fine grained ZrB<sub>2</sub> originating from the reaction between elemental boron and Zr<sub>2</sub>Cu melt and the respective EDX spectra below.

The volumetric fraction of the fine ZrB<sub>2</sub> particles increased with the increase of boron content in the starting powders, while no residual boron was observed. This was expected as the higher the starting boron content, the higher the resulting ZrB<sub>2</sub>. Small amounts of oxygen were detected from EDX analysis (figure 6); these could be attributed to oxide impurities already present in the starting powders or the oxidation of boron with water during the preparation of the ceramic slurries. Upon further inspection of the microstructure of the ceramic matrix, it was found that the majority of coarse ZrB<sub>2</sub> particles from powders did not retain their

1 original shape but were characterized by a peculiar jagged surface, resembling the phenomenon of grain  
2 twinning typically observed in minerals (figure 7). The degree of “jaggedness” was more pronounced in the  
3 case of B25, where the branches would reach a length equal or superior to the original grain dimension. With  
4 the increase of boron content, the irregularity and the branches length decreased, while the  $ZrB_2$  grains  
5 appeared larger. Moreover, the branches extending from the  $ZrB_2$  particles were perfectly parallel to each  
6 other. It is hypothesized that a fraction of the  $ZrB_2$  formed by RMI with the  $Zr_2Cu$  melt nucleated on the  
7 surface of the already present  $ZrB_2$  particles from the powders, and grew preferentially along specific planes.  
8 It could also be speculated that in the case of B25, due to the lower amount of available boron, boron particles  
9 had a higher mobility in the melt and could more easily dissolve and precipitate as  $ZrB_2$  crystals on the  
10 already present  $ZrB_2$  particles and grow continuously along preferential planes. Finally, the increase in size  
11 with increasing boron content could be attributed to the larger amount of fine  $ZrB_2$  that grew on the starting  
12  $ZrB_2$  grains from powders.

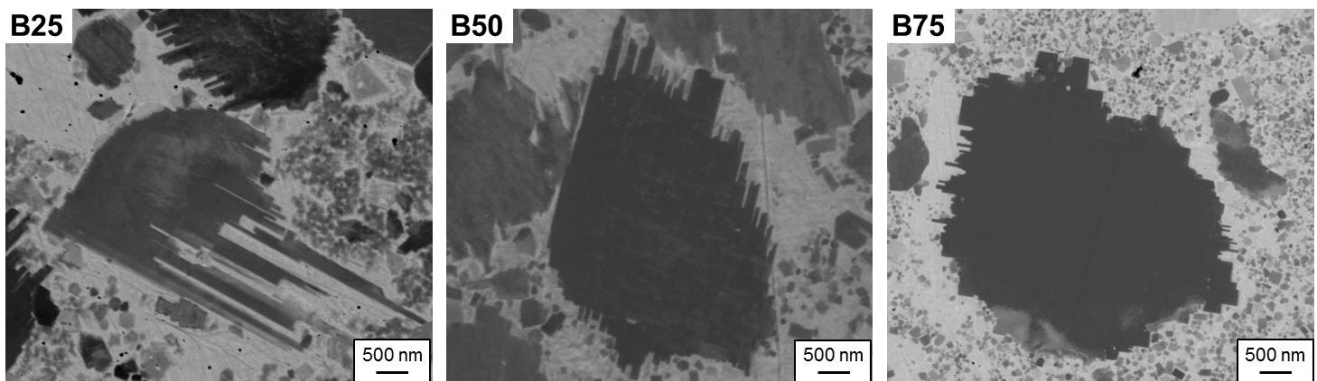

38 **Figure 7.** Detail of the jagged  $ZrB_2$  grains. The dark and light grey phase represents  $ZrB_2$  and  $Zr_2Cu$  respectively.  $ZrB_2$   
39 grain size increases with the increase of boron content.

### 44 3.2 Mechanical properties


45 The values of flexural strength and fracture toughness are reported in table 2. For sample B75 it was not  
46 possible to produce bars for fracture toughness testing because the infiltration came to a premature halt and  
47 there was not enough available material in spite of the second infiltration.

**Table 2.** Values of flexural strength and fracture toughness along the fibre orientation. Fibre vol% is reported.

Sample	Fibre volume after RMI (vol%)	Flexural Strength (MPa)	Fracture Toughness $0^\circ$ (MPa·m <sup>0.5</sup> )
B25	13.4 ± 0.4	332 ± 15	10.9 ± 0.6
B50	16.5 ± 1.4	452 ± 255	9.2 ± 6.5
B75	24.7 ± 4.5	563 ± 29	-

All specimens fracture in a predominantly brittle mode (figure 8); this was attributed to the predominantly ceramic nature of these materials due to the low fibre content. The higher strength of B50 and B75 compared to B25 could be attributed to the higher amount of fine ZrB<sub>2</sub> particles in the metal matrix that provide a better particle reinforcement. The highest strength was obtained for B75, which was also the most difficult to infiltrate. These materials displayed higher values of strength and toughness compared to those reported for 97% dense ZrB<sub>2</sub>/ZrC cermets obtained via RMI at 1200°C [24], while they are comparable to ZrB<sub>2</sub>-ZrC-Zr cermets obtained via reactive hot pressing [21][25][26], but were characterized by a lower density because of the presence of carbon fibres.


Sample B50 was affected by large data scatter. This was attributed to process-induced flaws in the specimen that resulted in premature failure of some bars during testing.

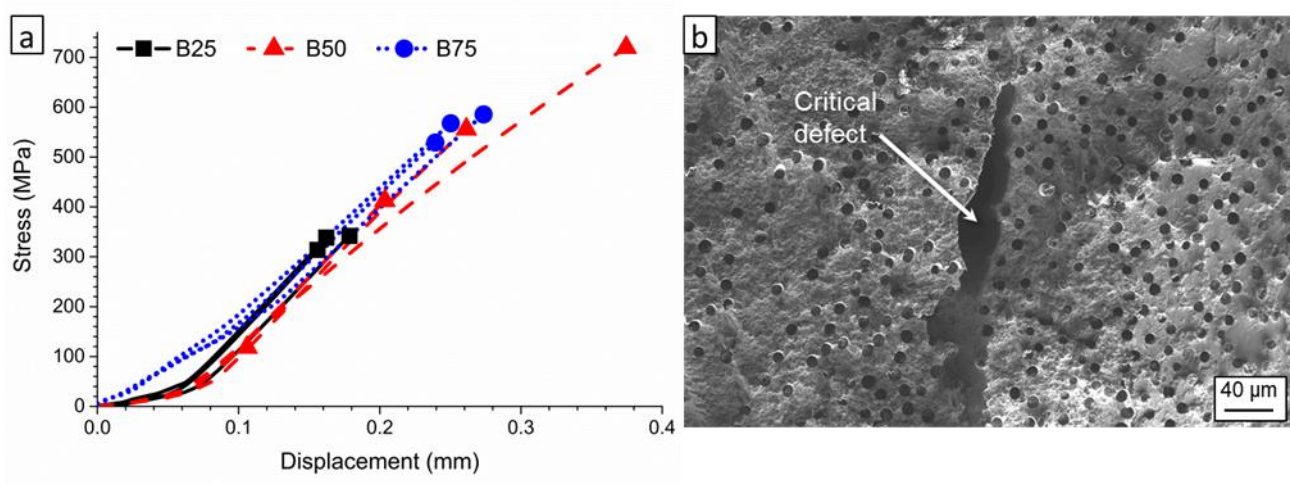

**Figure 8.** a) Stress/displacement curves for samples B25, B50 and B75. b) fracture surface of one of B50 bars which shows a large flaw in the material that resulted in premature failure of the specimen.




1 The fracture surface (Fig. 8b and fig. 9a, b) was typically characterized by very short fibre pull-out ( $< 5 \mu\text{m}$ )  
2 and was more similar to that of conventional ceramics. Compared to sintered fibre reinforced  $\text{ZrB}_2/\text{SiC}$   
3 composites previously studied by the same authors, the strength reported for these materials is roughly 50%  
4 higher because they did not suffer interlaminar shear and gave a valid bending failure under tensile stress.  
5  
6 Fracture toughness is comparable, in spite of the low fibre amount. The relatively high fracture toughness of  
7 these composites could be attributed to the partly metallic nature of the material rather than the fibre  
8 reinforcement. The jagged grains observed in figure 7 might also play a role. Looking at the detail of the  
9 fracture surface, it was observed that the ZrC rim around fibres was actually detached from the fibre (fig. 9d).  
10  
11 This could be attributed to the shrinkage of the metallic phase during cooling that led to the fibre/matrix  
12 debonding and suggested that fibres were not strongly involved in the strengthening and toughening  
13 mechanisms. In support of this it can be noted that a relevant amount of fibres close to the fractured matrix  
14 surface displayed little to no pull-out, even though the fibre/matrix interface was supposedly weak; this  
15 suggested a matrix dominated behaviour in these composites which was accompanied by a large energy  
16 release during crack propagation, see the brittle failure of Figure 8. The relative high values of “ $K_{Ic}$ ” could be  
17 overestimated because the plain strain condition would have not been guaranteed. In fact, the value of  
18  $2.5(K_I/\sigma)^2$  may have been greater than the specimen thickness and crack length. Hence further experiments  
19 with larger specimens are necessary to confirm if the measured  $K_I$  was the critical stress intensity factor.  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

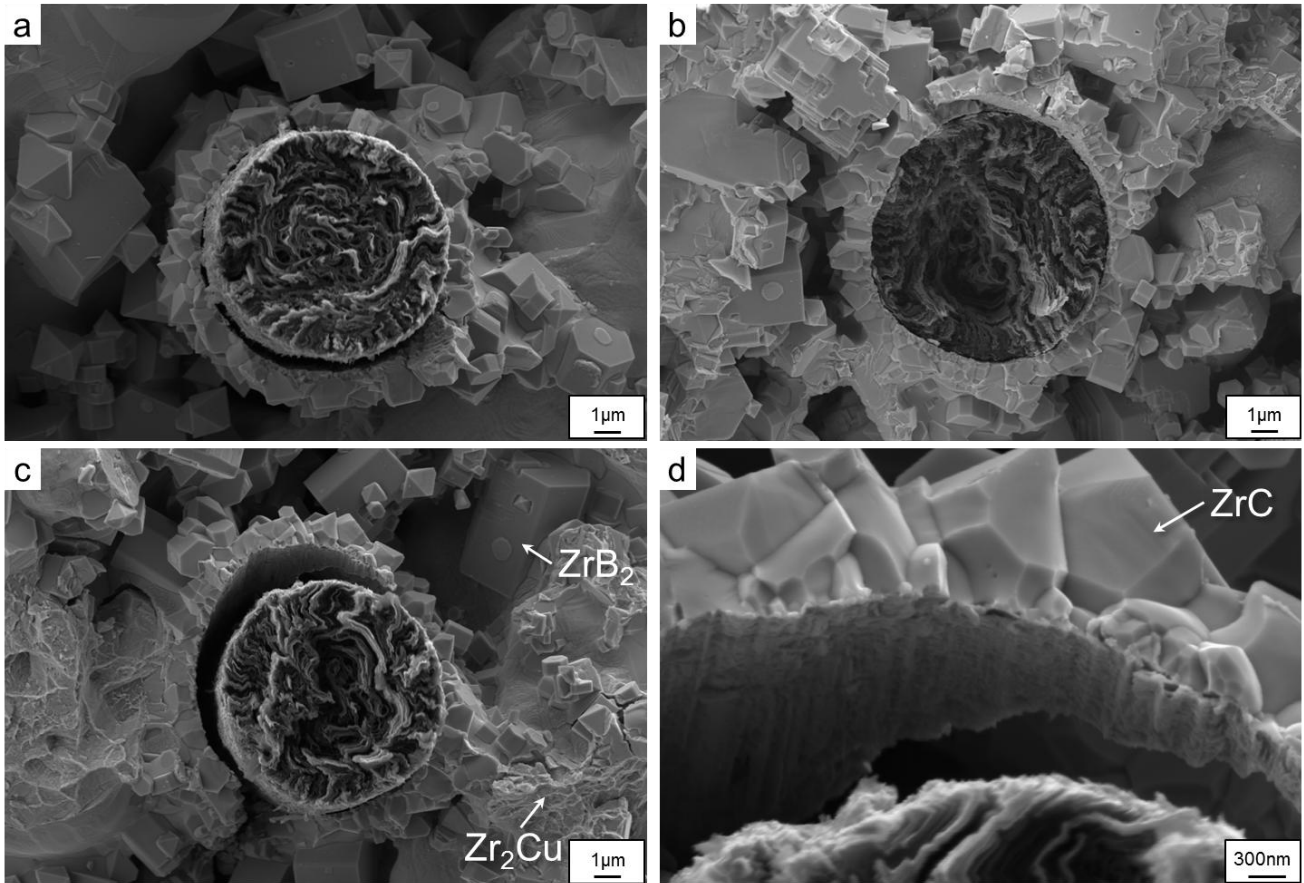

**Figure 9.** Fracture surface of samples B25 - B75: a) fibre surrounded by a ZrC rim in a hollow, b) typical fibre fracture surface, c) fibre detached from the ZrC rim, d) detail of the fibre/matrix interface

The fractured ceramic matrix was further investigated in order to find and study the behaviour of the jagged  $ZrB_2$  grains previously observed in the microstructure (Fig. 10). The branches protruding from the  $ZrB_2$  grain extended for the whole depth of the grain and gave origin to a terraced fracture. It is unclear whether these particles played a toughening role during fracture, as the grain itself showed brittle fracture, but the branches interlocked well with the surrounding residual melt and anchored the grain to the matrix.

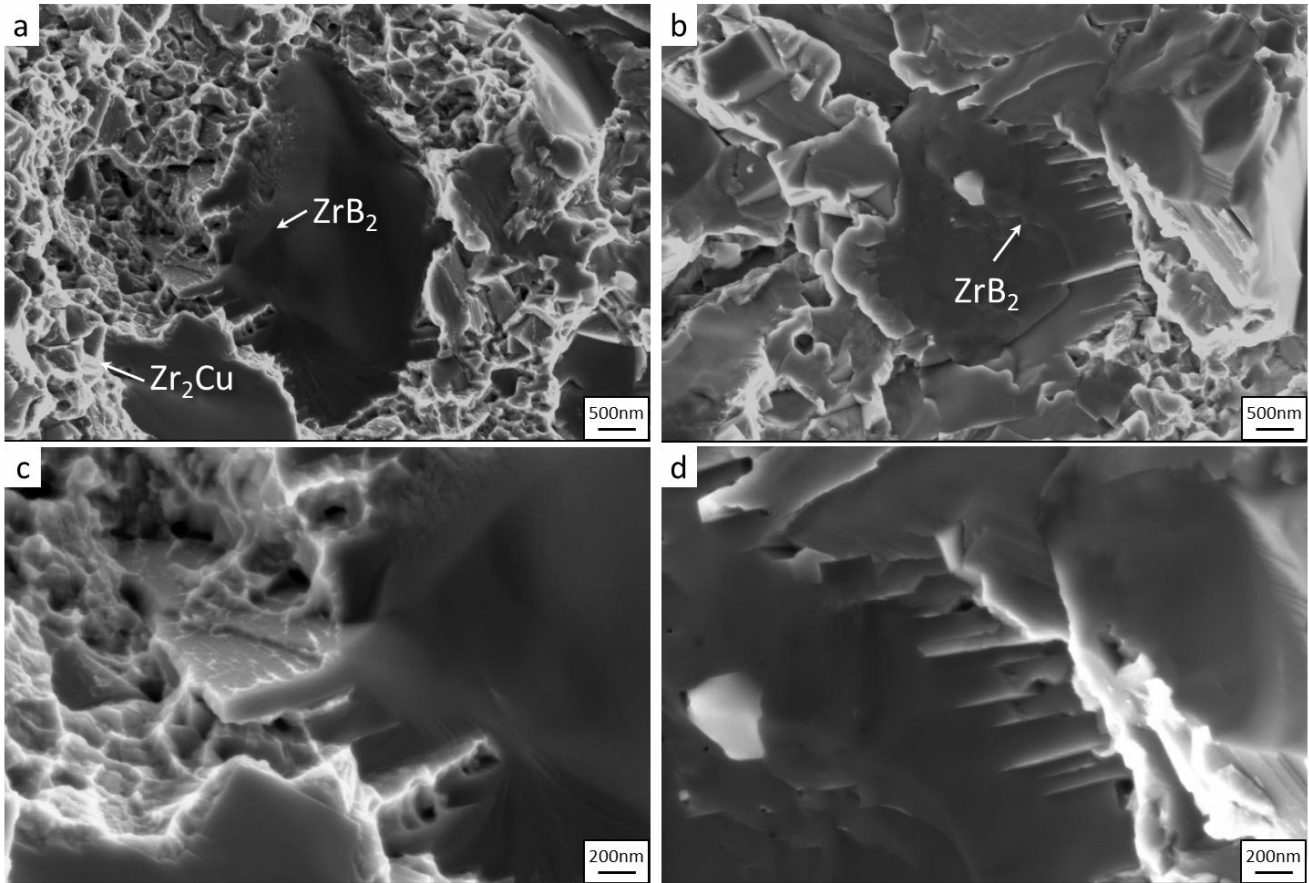

**Figure 10.** Fracture surface of the ceramic matrix showing the jagged  $ZrB_2$  grains and the terraced fracture with the branches of the grains interlocking with the metallic matrix.

## Conclusions

A new processing route for the fabrication of fibre reinforced UHTCs was investigated. Carbon fibre preforms containing B/ $ZrB_2$  mixtures in varying ratios were infiltrated with  $Zr_2Cu$  melt at  $1200^\circ C$ . All specimens were nearly fully dense and were characterized by  $< 1\%$  porosity. The microstructure was characterized by coarse  $ZrB_2$  from the commercial powders and fine  $ZrB_2$  particles originating from the reaction between B and  $Zr_2Cu$  embedded in a matrix of  $Zr_2Cu$ . Increasing the boron content in the starting powders led to an increase of the fine  $ZrB_2$  grains fraction originating from RMI. Sample B50 is characterized by the lowest degree of fibre degradation but also by a higher amount of residual melt that ultimately lowers the final fibre content and contributes to increase density. The strength of the composites is in the range of 350 – 560 MPa, with the highest values obtained for B50 and B75. This was attributed to a higher volumetric fraction of the fine  $ZrB_2$  that provided better reinforcement. All specimens failed catastrophically and the fracture surface was

1 characterized by minimal fibre pull-out, indicating that RMI samples behave more like cermet materials and  
2 the mechanical behaviour is dominated by the matrix. Future works will be aimed at limiting the amount of  
3 unreacted alloy phase and investigate the role of the jagged grains more in depth.  
4  
5

## 6 7 **Acknowledgements** 8

9  
10 This work has received funding from the European Union’s Horizon 2020 “Research and innovation  
11 programme” under grant agreement N°685594 (C<sup>3</sup>HARME). We wish to thank Cesare Melandri from ISTE  
12 C for mechanical testing. The authors also wish to thank German Aerospace Center DLR, Institute of Structures  
13 and Design, Stuttgart, for providing lab and furnace for RMI and Stefan Frick from DLR for running the RMI  
14 cycles.  
15  
16  
17  
18  
19  
20

- 21 • The raw/processed data required to reproduce these findings cannot be shared at this time due to  
22 technical or time limitations.  
23

## 24 25 **References** 26

- 27  
28  
29 [1] Rueschhoff LM, Carney CM, Apostolov ZD, Cinibulk MK. Processing of fiber-reinforced ultra-high  
30 temperature ceramic composites: A review. *International Journal of Ceramic Engineering & Science*  
31 2020;2:22–37. doi:10.1002/ces2.10033.  
32  
33 [2] Sciti D, Silvestroni L, Monteverde F, Vinci A, Zoli L. Introduction to H2020 project C3HARME–next  
34 generation ceramic composites for combustion harsh environment and space. *Advances in Applied*  
35 *Ceramics* 2018. doi:10.1080/17436753.2018.1509822.  
36  
37 [3] Zoli L, Sciti D. Efficacy of a ZrB<sub>2</sub>–SiC matrix in protecting C fibres from oxidation in novel  
38 UHTCMC materials. *Materials & Design* 2017;113:207–13. doi:10.1016/j.matdes.2016.09.104.  
39  
40 [4] Vinci A, Zoli L, Sciti D, Melandri C, Guicciardi S. Understanding the mechanical properties of novel  
41 UHTCMCs through random forest and regression tree analysis. *Materials and Design* 2018;145:97–  
42 107. doi:10.1016/j.matdes.2018.02.061.  
43  
44 [5] Zoli L, Vinci A, Galizia P, Gutiérrez-Gonzalez CF, Rivera S, Sciti D. Is spark plasma sintering suitable  
45 for the densification of continuous carbon fibre - UHTCMCs? *Journal of the European Ceramic*  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Society 2019. doi:<https://doi.org/10.1016/j.jeurceramsoc.2019.12.004>.

- 1  
2 [6] Galizia P, Failla S, Zoli L, Sciti D. Tough salami-inspired Cf/ZrB<sub>2</sub> UHTCMCs produced by  
3 electrophoretic deposition. *Journal of the European Ceramic Society* 2018;38:403–9.  
4  
5 doi:10.1016/J.JEURCERAMSOC.2017.09.047.  
6  
7  
8 [7] A. Paul, D.D. Jayaseelan, S. Venugopal, E. Zapata-Solvas, J. Binner, B. Vaidhyanathan, A. Heaton, P.  
9 Brown WEL, UHTC. UHTC-composites for hypersonic applications. *American Ceramic Society*  
10 *Bulletin* 2012;91:22.  
11  
12  
13 [8] Fahrenholtz WG, Hilmas GE, Talmy IG, Zaykoski JA. Refractory diborides of zirconium and hafnium.  
14 *Journal of the American Ceramic Society* 2007;90:1347–64. doi:10.1111/j.1551-2916.2007.01583.x.  
15  
16  
17 [9] Fahrenholtz WG, Wuchina EJ, Lee WE, Zhou Y, editors. *Ultra-High Temperature Ceramics: Materials*  
18 *for Extreme Environment Applications*. Hoboken, New Jersey: John Wiley & Sons Inc.; 2014.  
19  
20  
21 doi:10.1002/9781118700853.  
22  
23  
24 [10] Mungiguerra S, Di Martino GD, Savino R, Zoli L, Sciti D, Lagos MA. Ultra-High-Temperature  
25 *Ceramic Matrix Composites in Hybrid Rocket Propulsion Environment*. 2018 International Energy  
26 *Conversion Engineering Conference*, American Institute of Aeronautics and Astronautics; 2018.  
27  
28  
29 doi:doi:10.2514/6.2018-4694.  
30  
31  
32 [11] Opeka MM, Talmy IG, Wuchina EJ, Zaykoski J a., Causey SJ. Mechanical, Thermal, and Oxidation  
33 *Properties of Refractory Hafnium and zirconium Compounds*. *Journal of the European Ceramic*  
34 *Society* 1999;19:2405–14. doi:10.1016/S0955-2219(99)00129-6.  
35  
36  
37 [12] Mungiguerra S, Martino GD Di, Cecere A, Savino R, Silvestroni L, Vinci A, et al. Arc-jet wind tunnel  
38 *characterization of ultra-high-temperature ceramic matrix composites*. *Corrosion Science*  
39 *2019;149:18–28*. doi:<https://doi.org/10.1016/j.corsci.2018.12.039>.  
40  
41  
42 [13] Rubio V, Ramanujam P, Binner J. Ultra-high temperature ceramic composite. *Advances in Applied*  
43 *Ceramics* 2018;117:s56–61. doi:10.1080/17436753.2018.1475140.  
44  
45  
46 [14] Uhlmann F, Wilhelmi C, Schmidt-Wimmer S, Beyer S, Badini C, Padovano E. Preparation and  
47 *characterization of ZrB<sub>2</sub> and TaC containing Cf/SiC composites via Polymer-Infiltration-Pyrolysis*  
48 *process*. *Journal of the European Ceramic Society* 2017;37:1955–60.  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [15] Vinci A, Zoli L, Landi E, Sciti D. Oxidation behaviour of a continuous carbon fibre reinforced ZrB<sub>2</sub>-SiC composite. *Corrosion Science* 2017;123. doi:10.1016/j.corsci.2017.04.012.
- [16] Muolo ML, Ferrera E, Novakovic R, Passerone A. Wettability of zirconium diboride ceramics by Ag, Cu and their alloys with Zr. *Scripta Materialia* 2003;48:191–6. doi:https://doi.org/10.1016/S1359-6462(02)00361-5.
- [17] Küttemeyer M, Schomer L, Helmreich T, Rosiwal S, Koch D. Fabrication of ultra high temperature ceramic matrix composites using a reactive melt infiltration process. *Journal of the European Ceramic Society* 2016. doi:10.1016/j.jeurceramsoc.2016.04.039.
- [18] Küttemeyer M, Helmreich T, Rosiwal S, Koch D. Influence of zirconium-based alloys on manufacturing and mechanical properties of ultra high temperature ceramic matrix composites. *Advances in Applied Ceramics* 2018;117:s62–9. doi:10.1080/17436753.2018.1509810.
- [19] Küttemeyer M, Shandler D, Koch D, Friess M. Reactive Melt Infiltration of Boron Containing Fiber Reinforced Preforms Forming a ZrB<sub>2</sub> Matrix. *Processing and Properties of Advanced Ceramics and Composites VII*, John Wiley & Sons, Ltd; 2015, p. 169–80. doi:10.1002/9781119183860.ch18.
- [20] Vinci A, Zoli L, Sciti D, Melandri C, Guicciardi S. Understanding the mechanical properties of novel UHTCMCs through random forest and regression tree analysis. *Materials and Design* 2018;145. doi:10.1016/j.matdes.2018.02.061.
- [21] Guo S. Densification, microstructure, elastic and mechanical properties of reactive hot-pressed ZrB<sub>2</sub>-ZrC-Zr cermet. *Journal of the European Ceramic Society* 2014;34:621–32. doi:https://doi.org/10.1016/j.jeurceramsoc.2013.09.002.
- [22] Tarraste M, Juhani K, Pirso J, Viljus M. Reactive Sintering of Bimodal WC-Co Hardmetals. *Materials Science Medziagotyra* 2015;21. doi:10.5755/j01.ms.21.3.7511.
- [23] García J, Ciprés V [Collado, Blomqvist A, Kaplan B. Cemented carbide microstructures: a review. *International Journal of Refractory Metals and Hard Materials* 2019;80:40–68. doi:https://doi.org/10.1016/j.ijrmhm.2018.12.004.
- [24] Zhang S, Wang S, Li W, Zhu Y, Chen Z. Preparation of ZrB<sub>2</sub> based composites by reactive melt infiltration at relative low temperature. *Materials Letters* 2011;65:2910–2. doi:10.1016/j.matlet.2011.06.070.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [25] Guo S. Textured microstructure and anisotropic strength of hot-forged ZrB<sub>2</sub>-ZrC-Zr cermets. *Ceramics International* 2016;42:16063–70. doi:<https://doi.org/10.1016/j.ceramint.2016.07.116>.
- [26] Zhang S, Wang S, Li W, Zhu Y, Chen Z. Preparation of ZrB<sub>2</sub> based composites by reactive melt infiltration at relative low temperature. *Materials Letters* 2011;65:2910–2. doi:<https://doi.org/10.1016/j.matlet.2011.06.070>.