

# Identification of accelerated wet-ageing cycles

R. Le Riche<sup>1</sup>, A. Vinet<sup>2</sup> and S. Didierjean<sup>2</sup>

<sup>1</sup> CNRS URA 1884 / SMS, Ecole des Mines de St. Etienne, France  
leriche@emse.fr

<sup>2</sup> EADS Corporate Research Center, France  
{Alain.Vinet,Sebastien.Didierjean}@eads.net

## 1 Introduction

The increasing use of polymer-matrix composites in aircraft structural parts calls for a better knowledge of the long-term properties in cyclic hygro-thermal conditions. For example, the new A380 aircraft is composed of composite structural parts that are more than 20 *mm* thick. In such cases, wet-ageing, partially characterized as a through-the-thickness water concentration profile, evolves over several decades. Wet-ageing is, typically, so slow that characterization experiments based on direct reproduction of the hygro-thermal cycles are not possible within the development time of the aircraft. The identification of cycles leading to comparable through-the-thickness water concentrations in shorter times has been proposed using a Fickian water diffusion model in [7, 8].

This article presents a rigorous methodology and software development for the identification of accelerated wet-ageing cycles. Depending on the formulation, identification time and water concentration profiles are treated either as objective functions or as constraints. The results of the different identifications exhibit the trade-offs that exist between water profile accuracy and experiment time. The numerical implementation is performed in the LAMKIT © software ([3]), which is an object oriented platform for the analysis and optimization of composite laminates ([4]). An application is given for a thick and humid laminate.

## 2 Accelerated wet-ageing problem formulation

Let  $c(t, z)$  be an available through-the-thickness water diffusion model, where  $t$  is the time and  $z$  the thickness location. In this case, it is the one-dimensional multi-material Fickian model included in LAMKIT ([2]). The accelerated wet-ageing inverse problem determines thermal and hygral external conditions,  $T(t)$  and  $H(t)$ , such that two criteria,  $t_{final}$  and  $J_c$ , are properly controlled :  $t_{final}$  stands for the total conditioning time and  $J_c$  is the average Euclidean distance between the target water profile and the water profile at time  $t_{final}$ .

Thermal and hygral cycles are parameterized as  $nt$  plateaus of value  $T_i$  or  $H_i$ , respectively, starting at  $t_{i-1}$  and finishing at  $t_i$ .  $nc$  cycles are then repeated. The identification variables are summed up in the  $x$  array,

$$x \in \{(t_1 - t_0), \dots, (t_{nt} - t_{nt-1}), T_1 \dots T_{nt}, H_1 \dots H_{nt}, nc\}. \quad (1)$$

Now that the accelerated ageing variables and criteria are defined, two constrained mono-objective optimization problems are solved<sup>1</sup> :

$$(P_t) \quad \begin{cases} \min_x t_{final} \\ \text{such that } J_c \leq J_c^{lim} \\ \text{and } x^{min} \leq x \leq x^{max} \end{cases}$$

$$(P_J) \quad \begin{cases} \min_x J_c \\ \text{such that } t_{final} \leq t_{final}^{lim} \\ \text{and } x^{min} \leq x \leq x^{max} \end{cases}$$

$(P_t)$  minimizes the conditioning time such that the water profile is not too distant from the target, and vice versa with  $(P_J)$ .

### 3 Application

A 20 mm thick graphite-epoxy structure is considered where the saturation mass and the coefficient of water diffusion are

$$M_s = 0.001H^{1.5}, \quad (2)$$

$$D = 6.10^{-6} \exp(-2500/T). \quad (3)$$

The target concentration profile (symbol + in Figure 1) is humid (about 0.75% of the mass). A first  $(P_t)$  identification is performed where the maximum distance between the water profiles is  $J_c^{lim} = 0.02\%$ . The six continuous and bounded variables ( $nt = 2$ ) are  $0 \leq T_1, T_2 \leq 100^\circ C$ ,  $0 \leq H_1, H_2 \leq 100\%$ ,  $0 \leq (t_1 - t_0), (t_2 - t_1) \leq 200 h$ . The number of cycles is fixed at  $nc = 5$ . The problem is solved using the Globalized and Bounded Nelder-Mead algorithm [5]. A trivial solution is obtained where all variables hit their upper-bounds (maximum times, temperatures and humidities). The total conditioning time is  $2 \times 200 \times 5 = 2000 h \approx 83$  days. Despite the very fast diffusion conditions created by this tuning, the specimen center is not humid enough (see Figure 1). Clearly, a longer conditioning is necessary.

---

<sup>1</sup>A third problem associated to the multi-objective formulation

$$(P_{tJ}) \quad \begin{cases} \min_x t_{final} \\ \text{and } \min_x J_c \\ \text{such that } x^{min} \leq x \leq x^{max} \end{cases}$$

can be solved using LAMKIT but, for concision, it will not be discussed here.

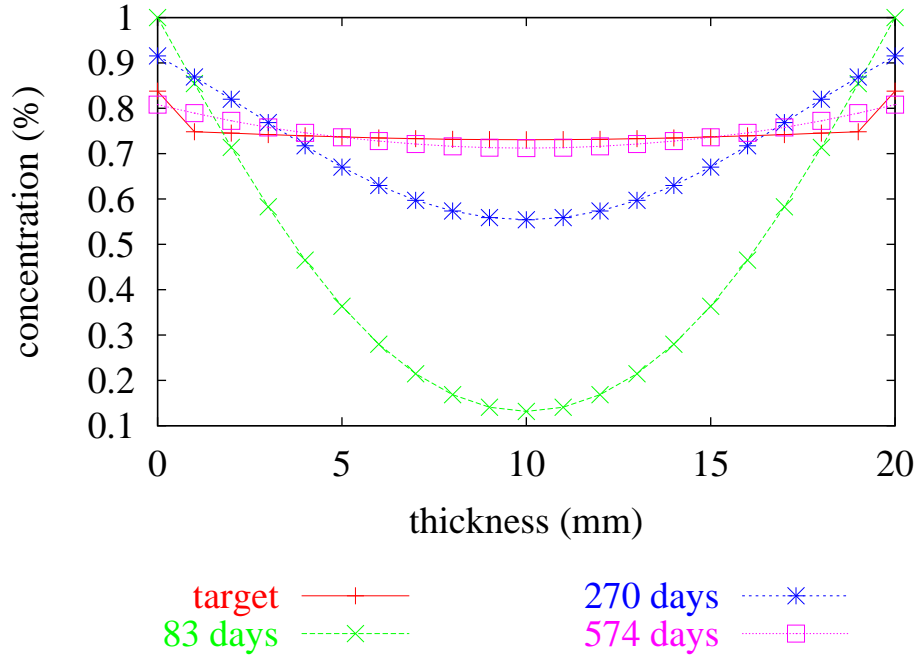


Figure 1: Comparison between a target water profile and three accelerated ageings of various  $t_{final}$ .

The  $(P_t)$  identification is therefore repeated but the largest possible experiment time is increased by the following changes :  $nc = 20$  cycles are made and  $0 \leq (t_1 - t_0), (t_2 - t_1) \leq 400 h$ . The solution is  $t_1 = 383. h$ ,  $t_2 = 688. h$ ,  $T_1 = 100. ^\circ C$ ,  $T_2 = 100. ^\circ C$ ,  $H_1 = 85. \%$ ,  $H_2 = 87. \%$ , which has  $t_{final} = 13776 h = 574$  days and  $J_c = 0.0207$ . The corresponding water concentration profile is plotted in Figure 1. This solution is not satisfactory because the conditioning remains too long.

In order to better understand what is feasible in terms of concentration profile resemblance within a realistic time, a  $(P_J)$  identification is carried out. The maximum conditioning time is set to  $t_{final}^{lim} = 270$  days. The discrete variable “number of cycles”,  $nc$ , is added to the identification variables  $x$ . Because there are both continuous and discrete variables, an evolutionary algorithm ([1, 3, 4]) that handles mixed variables is used for solving the optimization problem. The solution is  $nc = 10$ ,  $t_1 = 375. h$ ,  $t_2 = 649. h$ ,  $T_1 = 97. ^\circ C$ ,  $T_2 = 97. ^\circ C$ ,  $H_1 = 98. \%$ ,  $H_2 = 94. \%$ , which has  $t_{final} = 270$  days and  $J_c = 0.112$ . The associated concentration profile is plotted in Figure 1.

## 4 Concluding remark

The careful identification problem formulation and programming performed for the LAMKIT project has been applied to the acceleration of wet-ageing. Similar work is underway to accelerate inelastic strains setting ([6]).

## References

- [1] T. Bäck. *Evolutionary Algorithms in Theory and Practice*. Oxford Univ. Press, New York, USA, 1996.
- [2] S. Didierjean, A. Vinet, J.J. Barrau, and L. Michel. Modélisation de la reprise hydrique sur matériaux composites carbone/époxy. In Y. Rémond and J. Lamon, editors, *Actes des 13ièmes Journées Nationales des Composites*, volume 2, pages 657–666, Strasbourg Univ., France, March 2003.
- [3] EADS Corporate Research Center. *LAMKIT – Online Presentation*, 2001. available at <http://www.eads.net/lamkit>.
- [4] R. Le Riche, J. Gaudin, and J. Besson. An object-oriented simulation optimization interface. *Computers & Structures*, 81(17):1689–1701, 2003.
- [5] M. Luersen, R. Le Riche, and F. Guyon. A constrained globalized and bounded nelder-mead method for engineering optimization. *Structural and Multidisciplinary Optimization*, March 2003. accepted for publication.
- [6] F. Pellé and A. Vinet. Optimisation des matériaux stratifiés composites en fluage. Master’s thesis, EADS CCR and Ecole des Mines de Saint Etienne, France, september 2003. in French.
- [7] T. G. Reynolds and H. L. McManus. Understanding and accelerating environmentally-induced degradation and microcracking. In *Proc. of the 39th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf.*, Long Beach, CA, April 1998. paper no. AIAA-98-1961.
- [8] T. G. Reynolds and H. L. McManus. Accelerated tests of environmental degradation in composite materials. In P. Grant and C. Q. Rousseau, editors, *Composite Structures: Theory and Practice*, ASTM STP 1383, pages 513–525, West Conshohocken, PA, 2000. American Soc. for Testing and Materials.