



## Tricalcium silicate $\text{Ca}_3\text{SiO}_5$ superstructure analysis: a route towards the structure of the M1 polymorph

Marie-Noëlle De Noirfontaine, Mireille Courtial, Frederic Dunstetter, Gilles Gasecki, Marcel Signes-Frehel

### ► To cite this version:

Marie-Noëlle De Noirfontaine, Mireille Courtial, Frederic Dunstetter, Gilles Gasecki, Marcel Signes-Frehel. Tricalcium silicate  $\text{Ca}_3\text{SiO}_5$  superstructure analysis: a route towards the structure of the M1 polymorph. *Zeitschrift für Kristallographie*, 2012, 227 (2), pp.102-112. <10.1524/zkri.2011.1425>. <hal-00669025>

**HAL Id: hal-00669025**

**<https://hal.archives-ouvertes.fr/hal-00669025>**

Submitted on 13 Feb 2012

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Tricalcium silicate $\text{Ca}_3\text{SiO}_5$ superstructure analysis: a route towards the structure of the $\text{M}_1$ polymorph

Marie-Noëlle de Noirfontaine<sup>1,III,\*</sup>, Mireille Courtial<sup>1,II</sup>, Frédéric Dunstetter<sup>I</sup>,  
Gilles Gasecki<sup>III</sup>, Marcel Signes-Frehel<sup>III</sup>

<sup>I</sup> Laboratoire des Solides Irradiés, École Polytechnique- CNRS UMR 7642- CEA, 91128 Palaiseau, France

<sup>II</sup> Université d'Artois, 1230 Rue de l'Université, 62400 Béthune, France

<sup>III</sup> C.T.G.- Italcementi Group, rue des Technodes, 78931 Guerville, France

**Keywords:**  $\text{Ca}_3\text{SiO}_5$ ; Crystal Structure;  $\text{M}_1$  Alite; Polymorphism; Powder X-Ray Diffraction

## Abstract.

In this paper, we present a structural model for the  $\text{M}_1$  polymorph of tricalcium silicate  $\text{Ca}_3\text{SiO}_5$  from Powder X-Ray Diffraction (XRD) data, including weak intensity superstructure Bragg lines. As no single crystal is available, this structural model has been deduced using the structural relationships found between the previously known triclinic and monoclinic  $\text{M}_3$  polymorphs.

We find that the better starting set of atomic positions for Rietveld refinement is the triclinic set and not the monoclinic set. A key observation is that the monoclinic  $\text{M}_1$  structure is closer to the low temperature triclinic  $\text{T}_3$  structure (within the Golovastikov model) than to the higher temperature monoclinic  $\text{M}_3$  structure.


The unit cell and the set of atomic positions of the two best models, called  $3\langle\text{M}\rangle\text{Pc}$  and  $3\langle\text{T}\rangle\text{Pn}$  models, are provided. We prefer the  $3\langle\text{M}\rangle\text{Pc}$  model for it better reproduces the weak characteristic Bragg lines of the superstructure.

## Introduction

Anhydrous Portland cement is essentially composed of a synthetic rock named clinker, which contains at least four major phases: two calcium silicates called alite and belite, an aluminate phase and a ferrite phase, and minor phases depending on conditions. During the hydration of cement, the two silicates react with water to produce an ill-crystallised compound (C-S-H), which is responsible for the cohesive properties of hydrated cements, and crystals of portlandite. The same stands for aluminates, except that all the final compounds are crystallized.

Alite is the major constituent of the clinkers, in a concentration ranging from 40 to 70%: it is a solid solution of tricalcium silicate  $\text{Ca}_3\text{SiO}_5$  with various impurities which presents a complex phase diagram still not well known.  $\text{Ca}_3\text{SiO}_5$  is called  $\text{C}_3\text{S}$  with the oxide notations ( $\text{C} = \text{CaO}$ ,  $\text{S} = \text{SiO}_2$ ).

Pure  $\text{C}_3\text{S}$  exhibits six polymorphs from room temperature up to  $1100^\circ\text{C}$  [1]: three triclinic forms ( $\text{T}_1$ ,  $\text{T}_2$ ,  $\text{T}_3$ ), two monoclinic forms ( $\text{M}_1$  and  $\text{M}_2$ ) and one rhombohedral (R). At room temperature, impurities stabilise some of the high temperature forms of the pure compound, or another monoclinic phase called  $\text{M}_3$  alite [2,3]. A list of crystallographic data of the seven polymorphs is given in Table 1.



In industrial clinkers,  $\text{M}_1$  and  $\text{M}_3$  polymorphs are the most frequently stabilised phases. The only single crystal structures available in the literature are those of a triclinic polymorph and the  $\text{M}_3$  and R polymorphs.

The first single crystal study on  $\text{C}_3\text{S}$  has been proposed by Jeffery [4] who determined an average rhombohedral pseudo structure ( $R3m$  space group) for the triclinic,  $\text{M}_3$  and R polymorphs.

\* Corresponding author. Tel.: +33 1 69 33 44 83; fax: +33 1 69 33 45 54  
e-mail address: marie-noelle.de-noirfontaine@polytechnique.edu

In the late 1960's, Guinier, Regourd and co-workers studied the polymorphism of  $C_3S$  by powder X-Ray diffraction [1] and this remains the only systematic report. Their analysis of cell parameters in relation to temperature is consistent with displacive transformations [5,6]. The cell deformations have been discussed by the authors in the two characteristic planes of the structure, the monoclinic and the hexagonal plane. However, atomic positions and space groups were not available.

In 1975, Golovastikov *et al.* [7] were able to solve a triclinic structure with a Weissenberg experiment. In the 1980's, the  $M_3$  and R structures have been solved thanks to single crystal studies with a 4-circle diffractometer: the R structure was solved by Nishi & Takéuchi [8] and quasi simultaneously by Il'inets *et al.* [9,10]; the  $M_3$  structure was solved by Nishi & Takéuchi [11]. These structures are characterised by large unit cells, with very many atoms (228 atoms in the reduced unit cell of  $M_3$ ). Atoms distributed over two positions and complicated orientational disorder of the  $SiO_4$  groups were found in the high temperature phases. A smaller unit cell with average structure referred to as <M> was also proposed for the  $M_3$  polymorph. In 1995, Mummé [12] determined the crystal structure of an alite single crystal extracted from a clinker: the <M> unit cell was identified again, quite similar to that of Nishi, but now as the genuine structure.

During the 1990's, Rietveld's analysis became a powerful tool for powder diffraction data, starting from the atomic models determined by the previous single crystal experiments. In 1997, Berliner *et al.* [13] proposed simplified models of the  $M_3$  polymorph without atoms at split positions, refined on neutron and synchrotron powder diffraction data. De la Torre *et al.* [14] investigated the  $M_3$  polymorph using synchrotron X-Ray and neutron powder data; with the models of Berliner *et al.* [13] and Nishi & Takéuchi [11] as starting models for Rietveld refinement, they provided another superstructure model for  $M_3$ , better than the Berliner one.

In 2004, Peterson *et al.* [15,16] used the Golovastikov model of triclinic alite as an average starting model for Rietveld refinement with synchrotron powder diffraction data of the three triclinic polymorphs. They found superstructure Bragg lines in the  $T_1$  and  $T_2$  polymorphs, with decreasing intensity passing from  $T_1$  to  $T_2$ . As yet, no set of atomic positions for the real superstructures in  $T_1$  and  $T_2$  polymorphs is known: average models of Golovastikov-type are provided. The Golovastikov model can be used for  $T_3$  alite and as an averaged model for  $T_1$  and  $T_2$  alite. Finally, the Golovastikov model was again found appropriate for the  $T_3$  polymorph by De la Torre *et al.* [17], who used synchrotron data of  $T_1$  and  $T_3$  polymorphs. Their  $T_3$  model was validated for Rietveld quantitative analysis on laboratory Portland clinkers with less than 1% of MgO impurity. Guinier, Regourd and co-workers [1] already mentioned the appearance of such superstructure Bragg lines for the lower temperature triclinic polymorphs. In this paper, we label the Golovastikov model as the "T model".

In a series of papers [18-21] we have proposed an extensive analysis of the polymorphism of tricalcium silicate, based on the superstructure relationships between the known structures, together with powder X-ray diffraction data analysis of synthetic alites  $M_1$  and  $M_3$  compared to  $M_1$  and  $M_3$ -based industrial clinkers. Only averaged models were discussed in [19]. It is the aim of the present paper to present non-averaged models for the  $M_1$  polymorph and give the set of atomic positions.

The paper is organised as follows. The first section briefly describes the synthesis of the  $M_1$  polymorph samples and the collection of powder X-Ray diffraction (XRD) data. The second section is devoted to the construction of the starting atomic models needed for Rietveld refinement with our data. The last section presents the data analysis of the XRD data.

## 1. Experimental

Pure  $C_3S$  (in the triclinic form) and two alites,  $M_1$  and  $M_3$ <sup>1</sup>, were synthesised at C.T.G. Laboratory (Italcementi Group). The formulation for  $M_1$  is based on the data of Qing *et al.* [22]. As was already observed by Maki & Goto [23], sulphate impurities stabilise the  $M_1$  form and magnesium impurities stabilise the  $M_3$  form. The proportion (wt %) of the different impurities added to pure  $C_3S$  to synthesise the  $M_1$  form is the following: 93.13 %  $C_3S$  + 0.96 %  $Al_2O_3$  + 0.96 %  $MgO$  + 0.96 %  $Fe_2O_3$  + 4 %  $CaSO_4$ . The  $M_3$  alite was synthesised from a mixture of  $CaCO_3$ ,  $SiO_2$ ,  $MgO$ ,  $Al_2O_3$  in the stoichiometric proportion  $Ca_{2.879}Si_{0.971}Mg_{0.112}Al_{0.0439}O_5$ .

These compounds were analysed by X-Ray fluorescence and X-Ray powder diffraction. Using the usual stoichiometric oxide notations, the post-synthesis chemical analysis of the  $M_1$  alite is the following (wt%):  $CaO$ : 70.48%,  $SiO_2$ : 24.47%,  $SO_3$ : 1.55%,  $Al_2O_3$ : 1.05%,  $Fe_2O_3$ : 1.05%,  $MgO$ : 0.99%, (Ignition loss: 0.41%).

Powder XRD data were collected in the  $2\theta$  range 10-90°, step interval 0.02°, with a Philips PW 1050/70 diffractometer using  $CuK\alpha$  radiation. The diffraction patterns are discussed in the last section.

---

<sup>1</sup> The synthetic  $M_3$  alite is used here as a tool to confirm the validity of the averaging process of the atomic positions described in §2.3.

## 2. Superstructure analysis as a tool to build starting atomic positions

No atomic position is known for the  $M_1$  polymorph. In absence of single crystal data, some preliminary atomic model is needed to refine the models using powder diffraction data. A possible way is to extract a set of atomic positions from the available information on the other polymorphs and their mutual relationships.

In the phase diagram of doped  $C_3S$ , the  $M_1$  polymorph occupies an intermediate position between the low temperature triclinic polymorphs ( $T_1$ ,  $T_2$ ,  $T_3$ ) and the high temperature ( $M_2$ ,  $M_3$ ) polymorphs. Among these neighbouring polymorphs, the only known atomic models were triclinic and  $M_3$  models. Therefore, in the following, we consider the triclinic and  $M_3$  polymorphs as the closest known reference points.

Guinier, Regourd & coworkers [5,6] have shown that the transformations between the polymorphs are displacive transformations with a progressive deformation of the unit cell, especially the angles. Therefore, any atomic model for the  $M_1$  polymorph is supposed to be intermediate between the known atomic models of the triclinic and  $M_3$  polymorphs. However, the volumes of the unit cells of the three polymorphs  $T_1$ ,  $M_1$  and  $M_3$  are rather different due to various superstructure relations with respect to the underlying trigonal translational symmetry of the pattern. No direct link was found. However, an indirect link exists.

### 2.1. Relations between the unit cells of the various polymorphs

The first step is to find the coordinate transformation relationships between the three polymorphs.

We have shown [18,20] that introducing two elementary pseudo-monoclinic blocks of same volume named  $\langle M \rangle$  and  $\langle T \rangle$  provides the expected links between the three polymorphs. The pseudo-monoclinic unit cells  $\langle M \rangle$  and  $\langle T \rangle$  are equivalent; the various published unit cells (including the unit cells discussed in this paper) and their mutual relationships are summarised in the flowchart of Fig. 1 and Table 2.

(i) Unconventional unit cells are necessary for the structural relationships to become apparent. In Fig. 1 and Table 2,  $M'_1$  and  $M'_3$  are unconventional unit cells respectively equivalent to the  $M_1$  and  $M_3$  conventional monoclinic unit cells of references [1,11].

(ii) The G triclinic published unit cell [7] of the T polymorph exhibits no easy relationship with the other unit cells since none of its basis vectors lies in the hexagonal or monoclinic planes. Using the transformation matrix

$$[\mathbf{a}_{G'}, \mathbf{b}_{G'}, \mathbf{c}_{G'}] = [\mathbf{a}_G, \mathbf{b}_G, \mathbf{c}_G] \begin{bmatrix} 1 & 0 & 1 \\ 1 & 1 & 0 \\ 0 & 0 & 1 \end{bmatrix}$$

one finds another triclinic unit cell  $G'$  with basis vectors  $\mathbf{a}_{G'}$  and  $\mathbf{c}_{G'}$  now lying in the monoclinic plane; moreover,  $\mathbf{b}_G = 2\mathbf{a}_H$ , where  $\mathbf{a}_H$  is the hexagonal vector (Fig. 2a).

The cell transformation  $G' \rightarrow 3G'^{(1)}$

$$[\mathbf{a}_{3G'^{(1)}}, \mathbf{b}_{3G'^{(1)}}, \mathbf{c}_{3G'^{(1)}}] = [\mathbf{a}_{G'}, \mathbf{b}_{G'}, \mathbf{c}_{G'}] \begin{bmatrix} 1 & -2 & 0 \\ 0 & 3 & 0 \\ 0 & 1 & 1 \end{bmatrix}$$

leads to a tripled cell with a cell centring described by the centring vectors  $(0,0,0)$ ;  $(2/3, 1/3, 2/3)$ ;  $(1/3, 2/3, 1/3)$ . The  $3G'^{(1)}$  unit cell is pseudo-monoclinic. Among the various equivalent pseudo monoclinic unit cells of  $3G'^{(1)}$ , the only important one is the  $3G'$  unit cell<sup>2</sup> defined by the cell transformation  $G' \rightarrow 3G'$

<sup>2</sup> The unit cell transformation  $G' \rightarrow 3G'^{(2)} \rightarrow 3G'$  is defined as follows:

- $3G'^{(1)} \rightarrow 3G'^{(2)}$  is the standard transformation between choices 1 and 2 of the pseudo monoclinic unit cells,
- $3G'^{(2)} \rightarrow 3G'$  reverts the  $\mathbf{a}$  and  $\mathbf{c}$  axes of the  $3G'^{(2)}$  unit cell.

$$\left[ \mathbf{a}_{3G'}, \mathbf{b}_{3G'}, \mathbf{c}_{3G'} \right] = \left[ \mathbf{a}_{G'}, \mathbf{b}_{G'}, \mathbf{c}_{G'} \right] \begin{bmatrix} 1 & -2 & -1 \\ 0 & 3 & 0 \\ 1 & 1 & 0 \end{bmatrix}$$

with the centring vectors (0,0,0); (2/3,1/3,0); (1/3,2/3,0).

These various unit cells are listed in the upper part of Table 2.

(iii) The equivalence (Fig. 2b) between the two <M> and <T> blocks (related to choices 1 and 3 respectively in monoclinic symmetry) and the cell transformation <T> → <M>

$$\left[ \mathbf{a}_{<M>}, \mathbf{b}_{<M>}, \mathbf{c}_{<M>} \right] = \left[ \mathbf{a}_{<T>}, \mathbf{b}_{<T>}, \mathbf{c}_{<T>} \right] \begin{bmatrix} 1 & 0 & 1 \\ 0 & 1 & 0 \\ 0 & 0 & 1 \end{bmatrix}$$

provide the relationships for transformation of atomic coordinates, derived from the relationships between the unit cells, namely (Fig. 3):

$$\begin{aligned} M'_1 &\equiv 3 \langle M \rangle \equiv (3,1,1) \langle M \rangle \\ M'_3 &\equiv 6 \langle M \rangle \equiv (2,1,3) \langle M \rangle \\ 3G' &\equiv 9 \langle T \rangle \equiv (3,3,1) \langle T \rangle \end{aligned}$$

where the notation  $n\langle M \rangle$ ,  $n=pqr$ , stands for  $(p,q,r)\langle M \rangle$  as a condensed notation for a  $(p \mathbf{a}_{\langle M \rangle}, q \mathbf{b}_{\langle M \rangle}, r \mathbf{c}_{\langle M \rangle})$  supercell of  $\langle M \rangle$ . In the following a set of integers -  $n$  or  $(p,q,r)$  - is used to label the volume of the unit cell considered as a multiple of the two possible elementary blocks.

## 2.2. Atomic positions versus symmetry elements

The next step is to find the space groups to be considered in the data refinement.

Let us consider the various available monoclinic space groups.

As in ref. [20], models are labelled by combining the shape (and/or the volume of the unit cell) and the space group type used to generate the atomic positions. For example,  $3\langle T \rangle P\bar{1}$  labels a unit cell with a volume triple of that of the <T> elementary block and a space group  $P\bar{1}$ .

Due to the fact that the average pseudo-symmetry is described within the space group  $R3m$  (and not  $R\bar{3}m$ ), only symmetry operations belonging to this space group can be used in future discussion. This means explicitly that neither inversion centre nor two-fold axes are eligible for testing. The existence of a 2 axis would induce the equivalence between the silicate ions: this was already rejected with the first work of Jeffery [4] and has also been discussed by Il'inets *et al.* [9]. The  $R3m$  group being a polar space group, a free  $z$  parameter is allowed for any atom lying along the axis, giving a higher flexibility of the structure without drastic symmetry change.

The only remaining space groups are  $Pm$ ,  $Pc$ ,  $Cm$  and  $Cc$ .

To go further, one needs to take into account

- (i) the experimental results of a triple periodicity along the rhombohedral axis  $\mathbf{a}_R \equiv \mathbf{a}_{\langle M \rangle} \equiv \mathbf{a}_{\langle T \rangle}$  observed by TEM (Fig. 4),
- (ii) the atomic positions. Fig. 5 shows the skeleton of the  $\text{SiO}_4$  groups, more extensively discussed in ref. [18]. One can observe (Fig. 6) a stacking of two types of monoclinic planes: planes of calcium and silicon ions located at  $y_{\text{Si}}$  and  $y_{\text{Si}}+1/2$  referred to as mixed planes, separated by planes of calcium ions only, located at  $y_{\text{Si}}+1/4$ ,  $y_{\text{Si}}+3/4$ . In the mixed planes, one observes herringbone-like chains of ions, with axial  $\text{Si}_1$  ions and lateral  $\text{Si}_2$  and  $\text{Si}_3$  ions, separated by parallel and similar herringbone-like chains of calcium ions for which the discussion is identical.

The action of the pseudo-hexagonal symmetry is to relate parallel herringbones of adjacent mixed planes by the  $\mathbf{a}_H$  or  $\mathbf{b}_H$  hexagonal basis vectors. In  $R3m$  and its monoclinic subgroups, these average hexagonal translations are performed

by true translation or glide vectors in the rhombohedral and monoclinic space groups respectively; they are performed by the inversions in the  $P\bar{1}$  triclinic space group. More precisely, the  $Si_2$  and  $Si_3$  ions located on each side of the herringbones are related to other ions,  $Si'_2$  and  $Si'_3$ , located on the sides of chains that belong to the neighbouring planes of the same families, located at  $y = \pm 1/2$ . Always within an average view of the problem, all the calcium planes are related by a pseudo-translation  $\mathbf{b}/2$  where  $\mathbf{b}$  is the monoclinic axis of the elementary block. On the other hand, the mixed planes exhibit a periodicity  $\mathbf{b}$  along the monoclinic axis. This double periodicity is not compatible with any space group and any superstructure of the three possible elementary blocks.

The  $Cc$  group has two glide mirrors, axial and diagonal glide planes  $\mathbf{c}$  and  $\mathbf{n}$ . The diagonal glide plane  $\mathbf{n}$  ( $x+1/2, -y+1/2, z+1/2$ ) makes it necessary to double the unit cell along the  $\mathbf{a}$  direction to be consistent with the atomic positions in the mixed planes. Inasmuch as a tripling of the unit cell is observed experimentally (Fig. 4), the  $Cc$  group must be rejected. The  $Pm$ ,  $Pc$  and  $Cm$  space groups have either a mirror ( $Pm$ ), a glide mirror ( $Pc$ ) or both ( $Cm$ ). In order to achieve the  $\mathbf{b}$  pseudo-periodicity of the mixed Si-Ca planes, the  $m$  mirror must be in the Si-Ca plane. Likewise, the glide mirrors must be located in the calcium planes in order to be consistent with the  $\mathbf{b}/2$  pseudo-periodicity (Fig. 6).

Finally, three space group types are left:  $Pm$ ,  $Pc$ ,  $Cm$ . The tested models are the following:

$$\begin{aligned} 3\langle T \rangle Pn, 3\langle T \rangle Pm, 3\langle T \rangle Im \\ 3\langle M \rangle Pc, 3\langle M \rangle Pm, 3\langle M \rangle Am \end{aligned}$$

where the integer 3 is always related to the basis vector  $\mathbf{a}$ .

The last step is to find the list of starting atomic positions for each of these six models.

## 2.3. Building a starting atomic model

### 2.3.1. Averaging the literature data for the triclinic and $M_3$ polymorphs

Using the structural relationships, one can build various averaged atomic models derived either from the triclinic polymorph or from the  $M_3$  polymorph. To distinguish the origin of the averaged atomic positions, let us give – for the time being – the index T, Nishi or Mumme to a model derived from triclinic or  $M_3$  published data.

A  $3\langle T \rangle_T$  set of atomic positions can be derived directly by averaging the  $9\langle T \rangle_T$  set of atomic positions for the triclinic polymorph as follows. The Golovastikov structure G [7] is transformed into a  $3G' \equiv 9\langle T \rangle$  [18,20] set of atomic parameters using the transformation matrix  $P = 2, -1, -1; 1, 1, -1; 1, 1, 0$  and the centring vectors given in § 2.1. Then, two average structures  $3\langle T \rangle_T$  and  $\langle T \rangle_T$  are derived, validated on our triclinic samples powder data. The averaging procedure takes all the 486 atomic positions (i.e. the  $P1$  space group) into account. The averaged positions are found to be compatible with the  $P\bar{1}$  space group. Therefore, the two models  $3\langle T \rangle_T$  and  $\langle T \rangle_T$  arising from the triclinic data are referred to as  $3\langle T \rangle P\bar{1}$  and  $\langle T \rangle P\bar{1}$ .

No  $3\langle M \rangle$  set of atomic positions can be built by a simple averaging of a known structure, for the longest vector  $\mathbf{a}$  is found in the  $6\langle M \rangle$  structure, with  $\mathbf{a}_{6\langle M \rangle} = 2\mathbf{a}_{\langle M \rangle}$ . It is necessary to go through a smaller  $\langle M \rangle$  averaged set of atomic positions. Starting from the  $M_3$  polymorph, we used either the Mumme published structure [12]  $\langle M \rangle_{Mumme} Am$  or an averaged structure  $\langle M \rangle_{Nishi} Am$  derived from the published Nishi & Takéuchi data [11]. These models were validated on our  $M_3$  samples powder XRD data. Starting from the triclinic polymorph, we use the  $\langle T \rangle_T$  model and the equivalence<sup>3</sup> between the  $\langle M \rangle$  and  $\langle T \rangle$  pseudo-monoclinic unit cells to build a  $\langle M \rangle_T$  set of atomic positions. Then several  $3\langle M \rangle$  starting atomic models ( $3\langle M \rangle_{Mumme}$ ,  $3\langle M \rangle_{Nishi}$  and  $3\langle M \rangle_T$ ) are built by concatenation of three identical  $\langle M \rangle$  sets.

### 2.3.2. Starting model consistent with the monoclinic symmetry of the $M_1$ polymorph

a) Starting from  $M_3$  data

The averaged atomic models derived from the  $M_3$  polymorph can be directly used to refine the  $M_1$  polymorph data, with minor modifications intended to adapt the atomic positions to the symmetry elements of each space group.

<sup>3</sup>  $\langle T \rangle P\bar{1}$  and  $\langle M \rangle P\bar{1}$  triclinic structures are fully equivalent, due to the conservation of the inversion centres:  $\langle M \rangle P\bar{1} \equiv \langle T \rangle P\bar{1}$ .

Things are changing in the case of supercells  $n\langle M \rangle P\bar{1}$  or  $n\langle T \rangle P\bar{1}$ , with  $n > 1$ .

## b) Starting from triclinic data

The problem is to introduce a monoclinic symmetry in the set of triclinic atomic positions  $3\langle T \rangle P\bar{1}$ . Tables 3 & 4 illustrate the situation of the  $\text{SiO}_4$  groups for the simplest case  $\langle T \rangle P\bar{1}$ ; although less simple rational coordinates, the same situation is found in the  $3\langle T \rangle P\bar{1}$  case. In the  $\langle T \rangle$  unit cell, Si and Ca ions are close to rational coordinates. Transforming these rational coordinates from  $\langle T \rangle$  to  $\langle M \rangle$  leads to other rational coordinates in the  $\langle M \rangle$  unit cell (Table 3 & Fig. 5). Table 4 shows the exchange between the symmetry-related Si2 and Si3 ions. In the  $\langle M \rangle P\bar{1}$  symmetry, Si2 and Si2' are related by an inversion centre, and the same situation occurs for Si3 and Si3'. In the  $\langle M \rangle Pc$  symmetry, Si2 and Si3' on one side, Si3 and Si2' on the other side are now related by the glide mirror  $c$ . A similar behaviour is found for the calcium ions.

The same situation stands for  $3\langle T \rangle Pn$ , made easier since no  $\langle T \rangle$ - $\langle M \rangle$  transformation is needed.

The  $3\langle M \rangle Pm$  and  $3\langle M \rangle Am$  starting models were derived from the  $3\langle M \rangle Pc$  model.

## 3. Data analysis of the $M_1$ data

### 3.1. Method

The different models have been refined using Rietveld analysis. The two packages FullProf [24] and GSAS [25] were used. In each refinement, a pseudo-Voigt profile shape function was considered and the  $\text{SiO}_4$  tetrahedra were treated as rigid bodies, with  $d_{\text{Si-O}} = 1.62 \text{ \AA}$ . The refined parameters were the scale factor, the instrumental parameters (angular offsets, background, peak half-width parameters), the cell parameters, the atomic positions and a common Debye-Waller factor  $U_{\text{iso}} = 0.025 \text{ \AA}^2$ .

The agreement factors discussed in the following are the  $R_B$  (R-Bragg) and  $R_F$  (R-factor) given by the FullProf program. It is important to underline that an analysis of the agreement factors alone is not sufficient to choose among the models. A visual control of the reproduction of the small diffraction lines characteristic of the superstructures is absolutely necessary. This method was validated and controlled on our data for triclinic,  $M_1$  and  $M_3$  compounds [21].

### 3.2. Results

Among the six models tested (Table 5), the best refinements were obtained with the  $3\langle M \rangle Pc$  and  $3\langle T \rangle Pn$  models. The atomic positions for these two best models are given in Tables 6 & 7.

The change of glide to mirror ( $Pm$  or  $Cm$  space groups) always decreases the quality of the refinement: (i) the position of the calculated diffraction lines is not compatible with the position of the observed lines, and (ii) the best refinement with these space groups is the one with the orientational disorder closest to that of the  $3\langle M \rangle Pc$  model. For these reasons, we reject the  $Pm$  and  $Cm$  space groups.

It is interesting to note that the orientational disorder of the  $\text{SiO}_4$  tetrahedra of the best  $3\langle M \rangle Pc$  model is already very close to the orientational disorder described by Nishi & Takéuchi [11] in the  $M_3$  polymorph, which shows that the distinction between the  $M_1$  and  $M_3$  orientational disorder is more closely related to the presence of the mirror than to the very detail of the orientational disorder itself.

As far as the agreement factors are rather similar and the diffraction pattern is equally well reproduced by both models, the distinction between the  $3\langle M \rangle Pc$  and  $3\langle T \rangle Pn$  models is more difficult. The two calculated diffraction patterns are sketched on Fig. 7. A systematic discrepancy is observed for the line 900, due to textural effects observed in almost all the samples of all the polymorphs, especially in industrial clinkers. A visual comparison of the experimental and calculated diffraction patterns (Fig. 7) shows that the small superstructure diffraction line observed at  $2\theta_{\text{Cu}} = 25.45^\circ$  as the second line of a doublet is systematically better reproduced by the  $3\langle M \rangle Pc$  model than by the  $3\langle T \rangle Pn$  model for all our samples. Therefore, we finally choose the  $3\langle M \rangle Pc$  model as the best model, but the other one cannot be definitely rejected.

### 3.3. Discussion

The Golovastikov model can be considered as a good starting model for  $T_3$  data refinement, whereas the true structure of the  $T_1$  polymorph is in fact a superstructure of the structure described by the Golovastikov model. These results are

not in contradiction with our approach but, on the contrary, they improve our argument, for we can reasonably consider that our triclinic averaged models are close to a  $T_3$  model.

Therefore, we can conclude that concerning the atomic positions, the  $M_1$  structure is close to the  $T_3$  structure. The inversion centres of the triclinic structure are replaced by glide mirrors in the monoclinic structure, with only a slight effect on isolated atoms. The main effect of this change of symmetry concerns the  $SiO_4$  tetrahedra, which already exhibit in the  $M_1$  polymorph the trends of the disorder found in the  $M_3$  polymorph.

## Conclusion

Using the superstructure relationships between the polymorphs of tricalcium silicate, a structural model is proposed in this paper, as a first attempt to handle the  $M_1$  polymorph. The rhombohedral translation  $\mathbf{a}_R$  of the the trigonal underlying symmetry is related to the glide mirrors in the  $Cm$  symmetry of the  $M_3$  polymorph and to the inversions in the triclinic symmetry. The two monoclinic polymorphs  $M_1$  and  $M_3$  are two distinct superstructures of the same  $\langle M \rangle$  block and the triclinic polymorph is a superstructure of the  $\langle T \rangle$  block. The equivalence between the two  $\langle M \rangle$  and  $\langle T \rangle$  blocks (respectively choice 1 and choice 3 in pseudo-monoclinic symmetry) provides the relationships for transformation of atomic coordinates.

Starting from the published single crystal data of the triclinic and monoclinic  $M_3$  polymorphs, we derive various starting sets of atomic positions for the subsequent Rietveld analysis of powder X-Ray diffraction data. Six models are tested, consistent with (i) the multiplicity 3 along the monoclinic axis  $\mathbf{a}_{M1}$  and (ii) the trigonal underlying pseudo-translational symmetry of the pattern.

The final atomic model is found to be closer to the atomic positions of the Golovastikov model, which describes the structure of the  $T_3$  polymorph located just below the  $M_1$  polymorph in the phase diagram of tricalcium silicate, than to those of the  $M_3$  polymorph, except for the orientational disorder which already prefigures the disorder of the  $M_3$  polymorph.

Concerning the data analysis, the important point is that the two best models,  $3\langle M \rangle Pc$  and  $3\langle T \rangle Pn$ , only differ in one superstructure Bragg line: the crystallographic residues are rather similar and a specific inspection of the  $2\theta_{Cu}=24.5-26^\circ$  is needed in order to clearly identify the  $M_1$  polymorph. However, on the basis of our data we prefer the  $3\langle M \rangle Pc$  model.


### *Acknowledgements*

The authors would like to thank M. Pierre Jaugey (Ciments CALCIA, France) and Prof. H el ene Zanni for their constant support of this work, Prof. Micheline Moranville for many valuable discussions, Prof. Henri Szwarc for a critical reading of the manuscript, and Dr Spencer Brown for his kind linguistic assistance. The authors dedicate this paper to Gerard Jaskierowicz (deceased) for his enthusiastic collaboration for the TEM experiments.



## References

- [1] M. Bigare, A. Guinier, C. Mazieres, M. Regourd, N. Yannaquis, W. Eysel, T. Hahn, E. Woermann, Polymorphism of tricalcium silicate and its solid solutions, *Journal of the American Ceramic Society*. **1967**, 50(11), 609.
- [2] I. Maki, S. Chromy, Microscopic study on the polymorphism of  $\text{Ca}_3\text{SiO}_5$ , *Cement and Concrete Research*. **1978**, 8(4), 407.
- [3] M. Regourd, Polymorphisme du silicate tricalcique. Nouvelles données de la diffraction des rayons X, *Comptes rendus de l'Académie des Sciences de Paris*. **1979**, 289(B), 17.
- [4] J.W. Jeffery, The crystal structure of tricalcium silicate, *Acta Crystallographica*. **1952**, 5, 26.
- [5] A. Guinier, M. Regourd: Structure of Portland cement minerals; pp. 1 in *Proceedings of the 5th International Symposium on the Chemistry of Cement*. Tokyo, 1968.
- [6] M. Regourd, Cristallographie des constituants du clinker de ciment Portland, *Bulletin de Liaison-Laboratoires Routiers*. **1970**, N° spécial 0, 58.
- [7] N.I. Golovastikov, R.G. Matveeva, N.V. Belov, Crystal structure of the tricalcium silicate  $3\text{CaO}\cdot\text{SiO}_2 = \text{C}_3\text{S}$ , *Soviet Physics Crystallography*. **1975**, 20(4), 441.
- [8] F. Nishi, Y. Takéuchi, The rhombohedral structure of tricalcium silicate at 1200°C, *Zeitschrift für Kristallographie*. **1984**, 168, 197.
- [9] A.M. Il'inets, Y.A. Malinovskii, N.N. Nevskii, Crystal structure of the rhombohedral modification of tricalcium silicate  $\text{Ca}_3\text{SiO}_5$ , *Soviet Physics Doklady*. **1985**, 30(3), 191.
- [10] A.M. Il'inets, M.J. Bikbau: New rhombohedral modification  $\text{Ca}_3\text{SiO}_5$  and mechanism of atomic transformation during the phase transition; pp. 77 in *Proceedings of the XII European Crystallographic Meeting*. Moscow, 1989.
- [11] F. Nishi, Y. Takéuchi, Tricalcium silicate  $\text{Ca}_3\text{O}[\text{SiO}_4]$ : the monoclinic superstructure, *Zeitschrift für Kristallographie*. **1985**, 172, 297.
- [12] W.G. Mumme, Crystal structure of tricalcium silicate from a Portland cement clinker and its application to quantitative XRD analysis, *Neues Jahrbuch für Mineralogie*. **1995**, 4, 145.
- [13] R. Berliner, C. Ball, P.B. West, Neutron powder diffraction investigation of model cement compounds, *Cement and Concrete Research*. **1997**, 27(4), 551.
- [14] A.G. de la Torre, S. Bruque, J. Campo, M.A.G. Aranda, The superstructure of  $\text{C}_3\text{S}$  from synchrotron and neutron powder diffraction and its role in quantitative phase analyses, *Cement and Concrete Research*. **2002**, 32, 1347.
- [15] V.K. Peterson, A Rietveld refinement investigation of a Mg-stabilized triclinic tricalcium silicate using synchrotron X-ray powder diffraction data, *Powder Diffraction*. **2004**, 19(4), 356.
- [16] V.K. Peterson, B.A. Hunter, A. Ray, Tricalcium silicate T1 and T2 polymorphic investigations: Rietveld refinement at various temperatures using synchrotron powder diffraction, *Journal of the American Ceramic Society*. **2004**, 87(9), 1625.
- [17] Á.G. de la Torre, R.N. de Vera, A.J.M. Cuberos, M.A.G. Aranda, Crystal structure of low magnesium-content alite: Application to Rietveld quantitative phase analysis, *Cement and Concrete Research*. **2008**, 38(11), 1261.
- [18] F. Dunstetter, M.-N. de Noirfontaine, M. Courtial, Polymorphism of tricalcium silicate, the major compound of Portland cement clinker: 1. Structural data: review and unified analysis, *Cement and Concrete Research*. **2006**, 36(1), 39.
- [19] M.-N. de Noirfontaine, F. Dunstetter, M. Courtial, G. Gasecki, M. Signes-Frehel, Polymorphism of tricalcium silicate, the major compound of Portland cement clinker: 2. Modelling alite for Rietveld analysis, an industrial challenge, *Cement and Concrete Research*. **2006**, 36(1), 54.
- [20] M.-N. de Noirfontaine, F. Dunstetter, M. Courtial, G. Gasecki, M. Signes-Frehel, Tricalcium Silicate  $\text{Ca}_3\text{SiO}_5$ , the major component of anhydrous Portland Cement: on the conservation of distances and directions and their relationship to the structural elements, *Zeitschrift für Kristallographie*. **2003**, 218(1), 8.
- [21] M. Courtial, M.-N. de Noirfontaine, F. Dunstetter, G. Gasecki, M. Signes-Frehel, Polymorphism of tricalcium silicate in Portland cement: a fast visual identification of structure and superstructure, *Powder Diffraction*. **2003**, 18(1), 7.
- [22] Y. Qing, K. Jianmin, L. Baoyuan: Effect of fluorite-gypsum composite mineralizer on the microstructure and properties of Portland cement clinker phase; pp. 342 in *Proceedings of the 9th International Congress on the Chemistry of Cement*. New Delhi, 1992.
- [23] I. Maki, K. Goto, Factors influencing the phase constitution of alite in Portland cement clinker, *Cement and Concrete Research*. **1982**, 12(1), 301.
- [24] J. Rodriguez-Carvajal, Note prepared for the Nordic Research Course. The Rietveld Method in Practice: the Program FullProf. **1994**.
- [25] A.C. Larson, R.B. Von Dreele, GSAS General Structure Analysis System, *Operational Manual*. **2000**, 1.

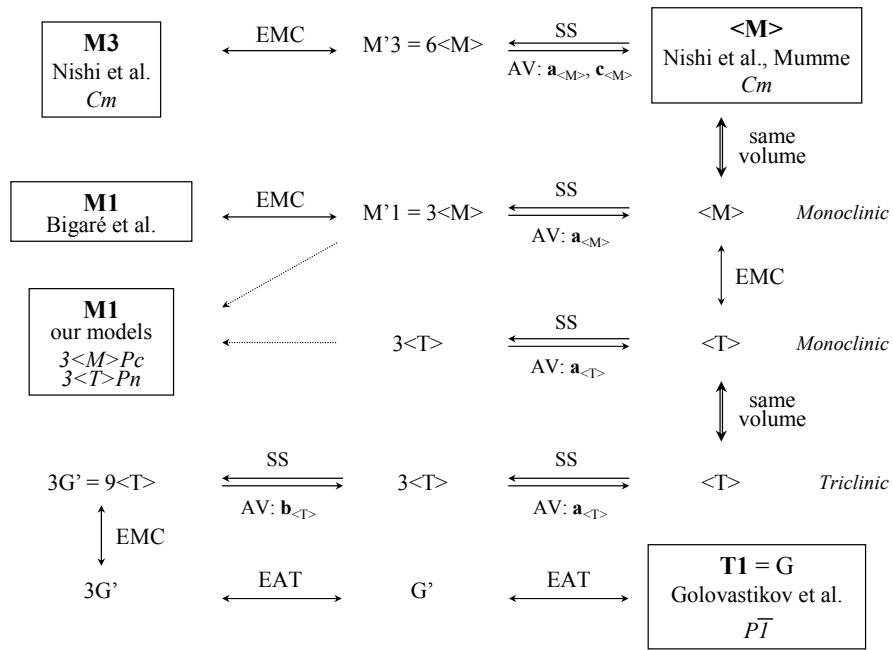

**Fig. 1.** Flowchart of the superstructure relationships between the unit cells introduced in this paper.

The boxes are related to the published experimental data


EMC Equivalent Monoclinic unit Cell

EAT Equivalent by Axes Transformation and/or use of non-primitive unit cell

SS Superstructure


AV: directions Average along the given direction(s)

- ←→ The simple arrows are related to the transformations which conserve the content of the unit cell: the models located on each side of such arrows constitute various alternatives to the production of the same diffraction pattern.
- ↔ The double arrows are related to a modification of the unit cell content: the models located on each side of such arrows produce distinct diffraction patterns due either to different volumes, different symmetry elements or different atomic positions.

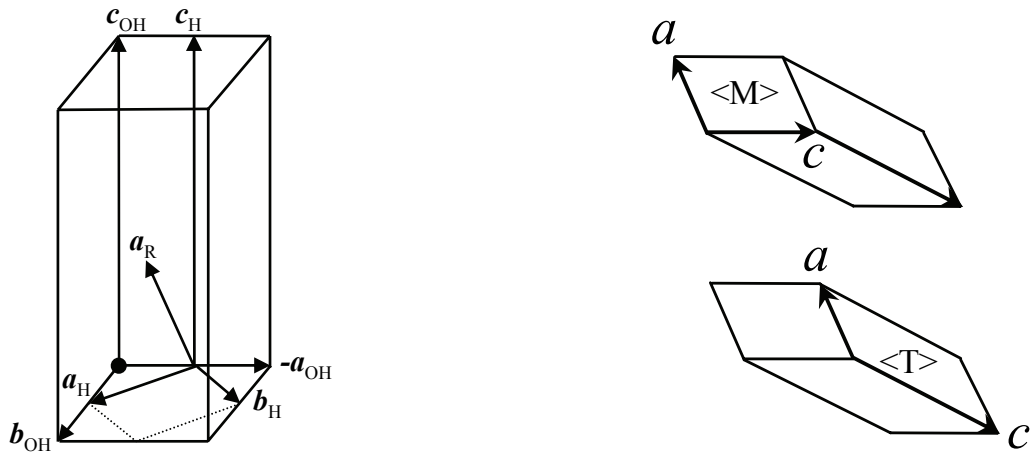


**Fig. 2.** Unit cells related to the various symmetries or pseudo-symmetries


- a) Unit cell vectors associated to the pseudo-rhombohedral symmetry: rhombohedral R, hexagonal H and orthohexagonal OH unit cells.  $V_{OH}=2V_H$ ;  $V_H=3V_R$ .
- b) Average triclinic  $\langle T \rangle$  unit cell, related to the  $\langle M \rangle$  and rhombohedral unit cell

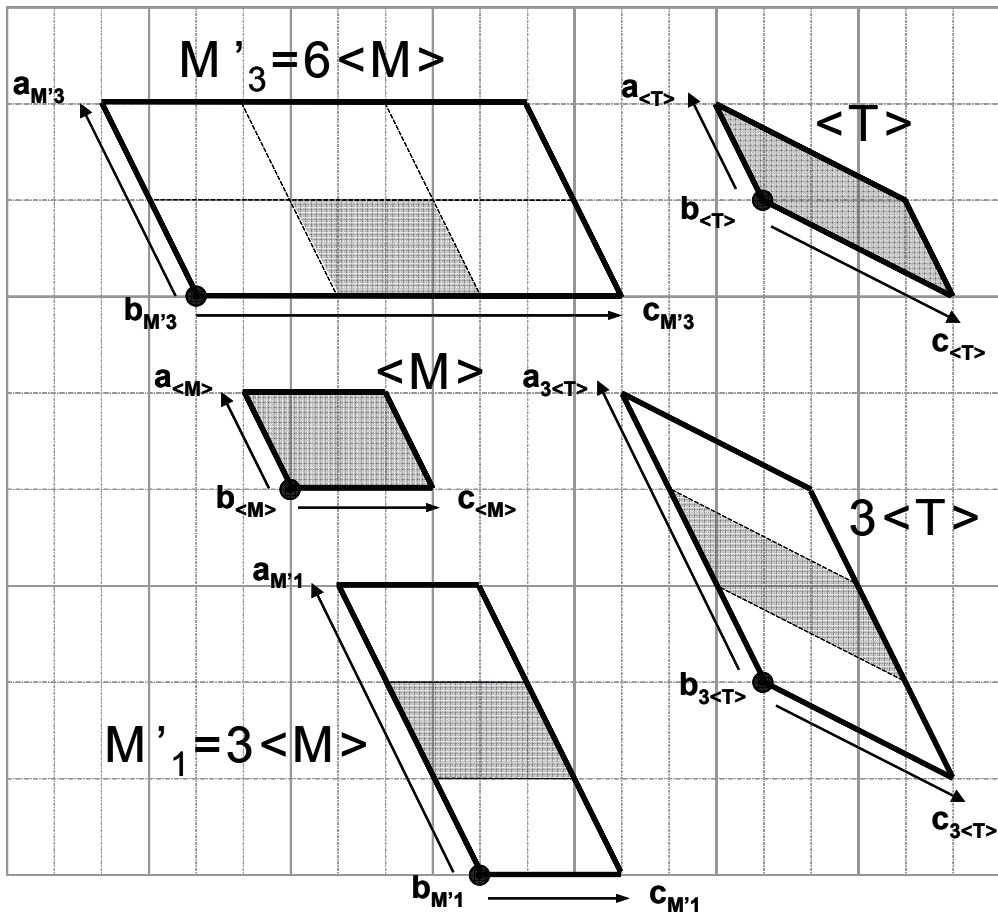


**Fig. 3.** Unconventional unit cells used in the flowchart of Fig. 1. The unit cell  $3G' \equiv 9\langle T \rangle \equiv (3,3,1)\langle T \rangle$  discussed in § 2.1 is a supercell of the  $3\langle T \rangle$  unit cell, with  $\mathbf{a}_{3G'} = \mathbf{a}_{3\langle T \rangle}$ ,  $\mathbf{b}_{3G'} = 3\mathbf{b}_{3\langle T \rangle}$ ,  $\mathbf{c}_{3G'} = \mathbf{c}_{3\langle T \rangle}$ . The primitive unit cell  $G'$  - given as an alternative unit cell for the Golovastikov unit cell  $G$  - is given by  $\mathbf{a}_{G'} = -\mathbf{c}_{3\langle T \rangle}$ ,  $\mathbf{b}_{G'} = \mathbf{b}_{\langle M \rangle} - \mathbf{c}_{\langle M \rangle}$ ,  $\mathbf{c}_{G'} = \mathbf{a}_{3\langle T \rangle} + \mathbf{c}_{3\langle T \rangle}$ .

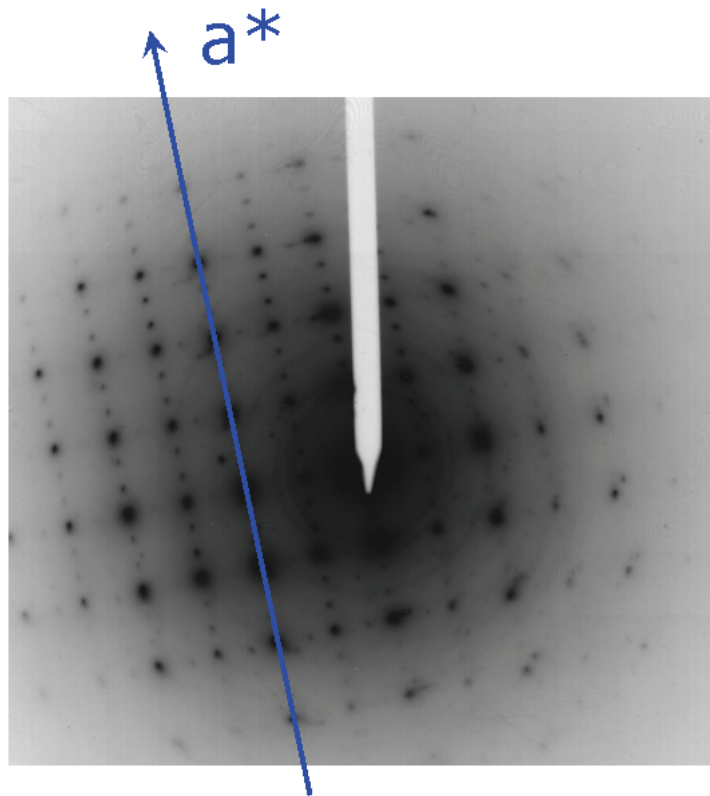


**Fig. 4** TEM diffraction pattern of  $M_1$  alite. Philips CM30 300KV (Laboratoire des Solides Irradiés). The polycrystalline sample was distributed on a carbon grid and the mono-crystalline grains were oriented with respect to the electron beam using sample holder rotations.

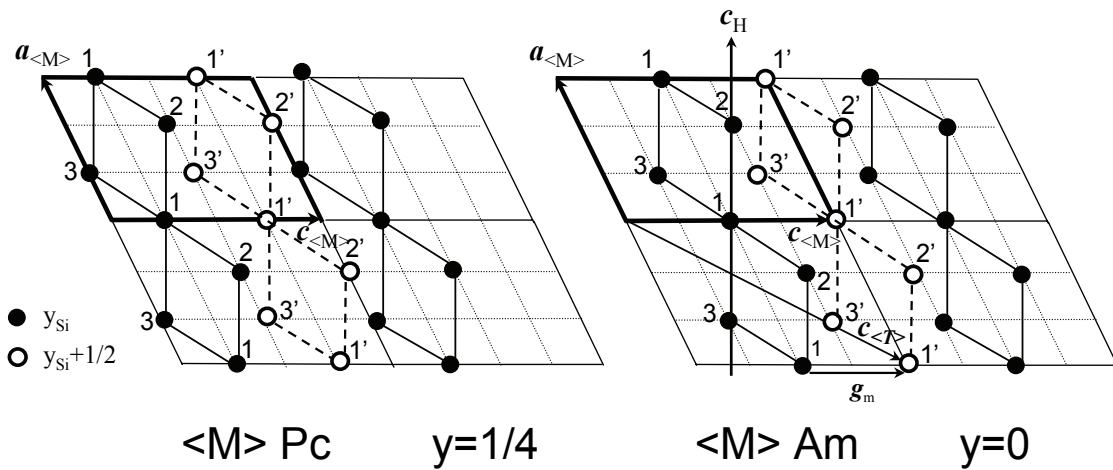

**Fig. 5.** The herringbones-like chains of silicate ions  $Si_1$ ,  $Si_2$  and  $Si_3$ . These chains are separated by the hexagonal vectors  $a_H$  or  $b_H$  relating a plane  $y_{Si}$  and a plane  $y_{Si} \pm 1/2$ .  $g_m$  is the projection of  $b_H$  onto the monoclinic plane.

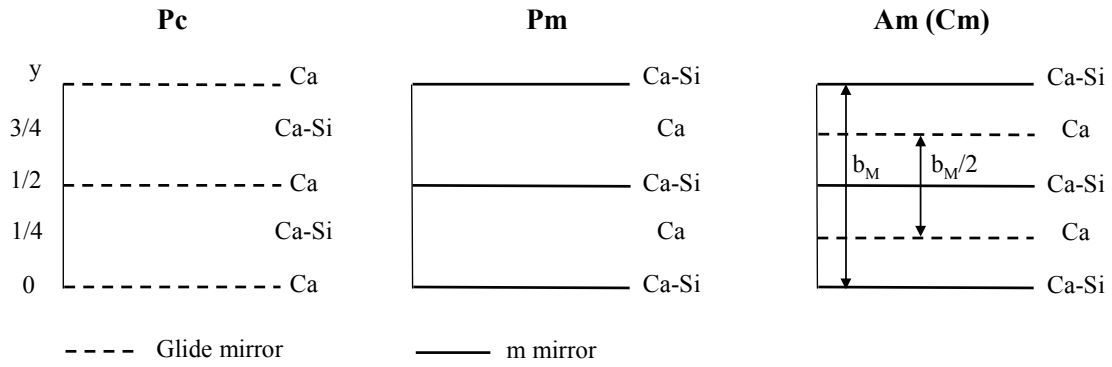

**Fig. 6.** Relations between the symmetry elements in the *Pc*, *Pm*, *Cm* space groups and the chemical content of monoclinic planes of the structure.

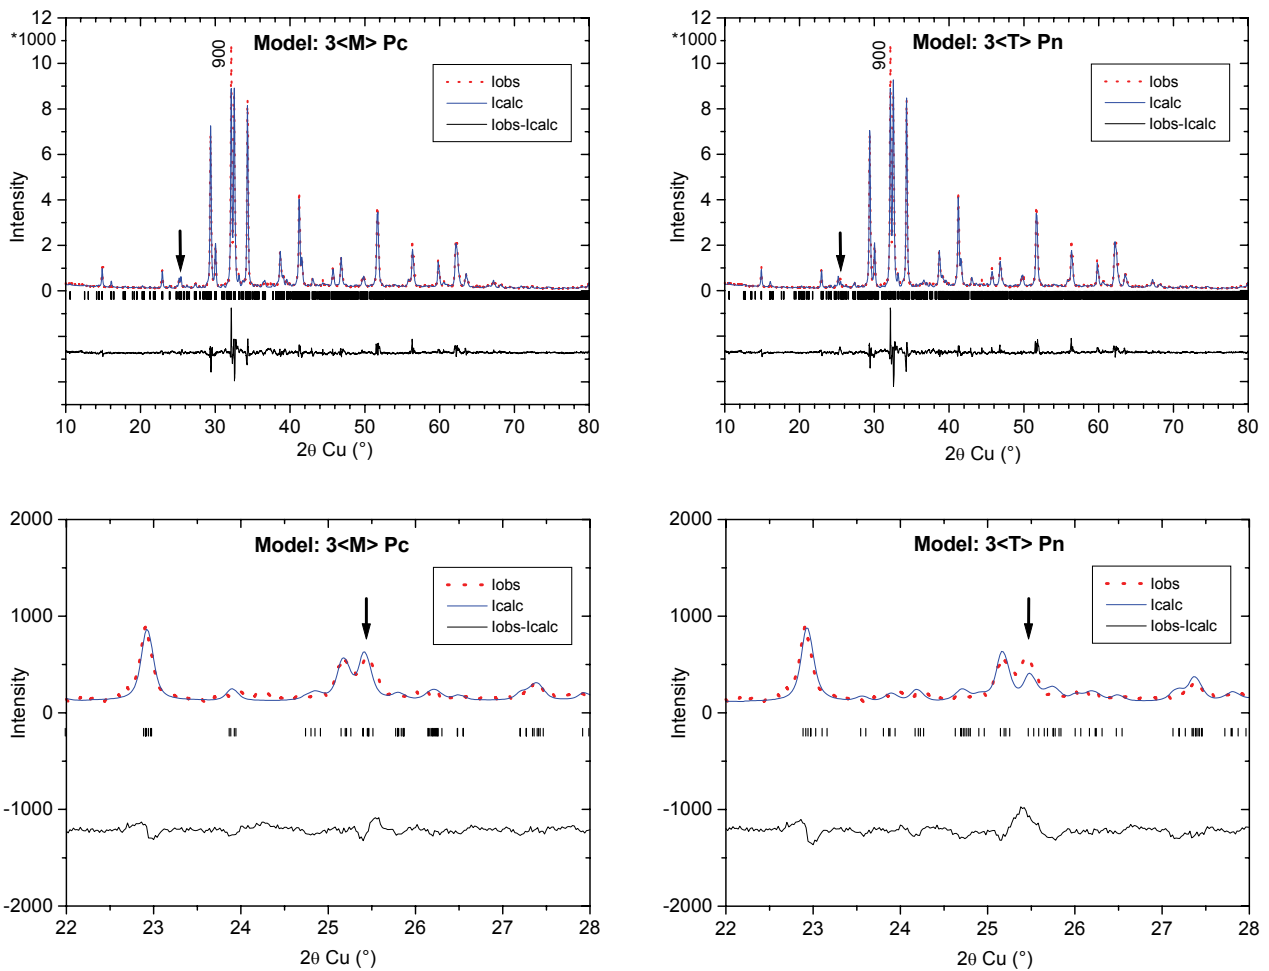

**Fig. 7.** Rietveld refinements of a powder diffraction pattern of  $M_1$  alite with the structural models  $3\langle M \rangle Pc$  and  $3\langle T \rangle Pn$  proposed in this paper. The  $3\langle M \rangle Pc$  superstructure is necessary to index and reproduce all the lines of the diagram, especially the second line of the doublet in the  $24.8\text{--}25.8^\circ 2\theta_{Cu}$  range, which is a characteristic superstructure line, related to the angular window W1 introduced in Fig. 2 of ref. [21].

**Table 1.** Crystallographic data of the seven polymorphs known for tricalcium silicate; (pOH) = pseudo-orthohexagonal symmetry; SC = single crystal data. PWD = powder diffraction data. SR = synchrotron radiation data. The column “xyz” indicates whether xyz data are provided or not in the given reference.

| Polymorph            | Symmetry group | Type of data | a (Å)   | b (Å)   | c (Å)   | $\alpha$ (°) | $\beta$ (°) | $\gamma$ (°) | xyz in ref. | Reference |
|----------------------|----------------|--------------|---------|---------|---------|--------------|-------------|--------------|-------------|-----------|
| R                    | <i>R3m</i>     | SC           | 7.135   | 7.135   | 25.586  | 90           | 90          | 120          | yes         | [8]       |
|                      |                | SC           | 7.0567  | 7.0567  | 24.974  |              |             |              | yes         | [9]       |
| M <sub>3</sub>       | <i>Cm</i>      | SC           | 33.083  | 7.027   | 18.499  | 90           | 94.12       | 90           | yes         | [11]      |
|                      | <i>Cm</i>      | PWD/SR       | 33.1078 | 7.0355  | 18.5211 | 90           | 94.137      | 90           | yes         | [14]      |
|                      | <i>Cm</i>      | PWD          | 33.0577 | 7.0330  | 18.5179 | 90           | 94.18       | 90           | no          | [21]      |
| M <sub>3</sub> : <M> | <i>Cm</i>      | SC           | 12.235  | 7.073   | 9.298   | 90           | 116.31      | 90           | yes         | [12]      |
| M <sub>2</sub>       | (pOH)          | PWD          | 12.342  | 7.143   | 25.434  | 90           | 90          | 90           | no          | [1]       |
|                      |                | PWD          | 12.333  | 7.137   | 25.442  |              |             |              | no          | [3]       |
| M <sub>1</sub>       | (pOH)          | PWD          | 12.332  | 7.142   | 25.420  | 90           | 89.85       | 90           | no          | [1]       |
|                      | <i>Pc</i>      | PWD          | 27.8736 | 7.0590  | 12.2575 | 90           | 116.030     | 90           | no          | [20]      |
| T <sub>3</sub> : <T> | (pOH)          | PWD          | 24.633  | 14.290  | 25.412  | 90.06        | 89.86       | 89.91        | no          | [1]       |
|                      | <i>P1</i>      | PWD/SR       | 11.6389 | 14.1716 | 13.6434 | 104.982      | 94.622      | 90.107       | yes         | [17]      |
| T <sub>2</sub> : <T> | (pOH)          | PWD          | 24.528  | 14.270  | 25.298  | 89.98        | 89.75       | 89.82        | no          | [1]       |
|                      | <i>P1</i>      | PWD/SR       | 11.7417 | 14.2785 | 13.7732 | 105.129      | 94.415      | 89.889       | yes         | [16]      |
| T <sub>1</sub>       | (pOH)          | PWD          | 24.398  | 14.212  | 25.103  | 89.91        | 89.69       | 89.69        | no          | [1]       |
| <T>                  | <i>P1</i>      | SC           | 11.67   | 14.24   | 13.72   | 105.5        | 94.33       | 90.0         | yes         | [7]       |

**Table 2.** Unit cell parameters used in our study, with both conventional and unconventional unit cells. For the  $T_1$  structure the intermediate unit cells used to pass from the original unit cell of Golovastikov *et al.* [7] to our  $3\langle T \rangle$  and  $\langle T \rangle$  averaged unit cells are given. To obtain the averaged unit cells  $\langle M \rangle$  of the Nishi and Mumme data ( $Cm$  space group) [11,12], reverted  $\mathbf{a}$  and  $\mathbf{c}$  axes are used. The - powder - data of Bigaré *et al.* are given in pseudo-orthohexagonal axes.

| Unit cell                       | a (Å)  | b (Å) | c (Å)  | $\alpha$ (°) | $\beta$ (°) | $\gamma$ (°) | V (Å <sup>3</sup> ) | Space group |
|---------------------------------|--------|-------|--------|--------------|-------------|--------------|---------------------|-------------|
| $T_1 \equiv G$                  | 11.67  | 14.24 | 13.72  | 105.50       | 94.33       | 90           | 2190                | $P\bar{1}$  |
| $G'$                            | 18.41  | 14.24 | 17.33  | 102.22       | 76.98       | 39.34        | 2190                | $P\bar{1}$  |
| Choice 1: $3G'^{(1)}$           | 18.41  | 21.14 | 17.33  | 90.03        | 76.98       | 89.66        | 6570                | $P\bar{1}$  |
| Choice 2: $3G'^{(2)}$           | 27.98  | 21.14 | 18.41  | 89.66        | 142.89      | 90.21        | 6570                | $P\bar{1}$  |
| $3G' \equiv 9\langle T \rangle$ | 27.98  | 21.14 | 18.41  | 90.34        | 142.89      | 89.79        | 6570                | $P\bar{1}$  |
| $3\langle T \rangle$            | 27.98  | 7.04  | 18.41  | 90.34        | 142.89      | 89.79        | 2190                | $P\bar{1}$  |
| $\langle T \rangle$             | 9.33   | 7.047 | 18.41  | 90.34        | 142.89      | 89.79        | 730                 | $P\bar{1}$  |
| $\langle M \rangle$             | 9.33   | 7.047 | 12.33  | 90.34        | 115.72      | 89.79        | 730                 | $P\bar{1}$  |
| Choice 1: $M_3$ Nishi           | 33.083 | 7.027 | 18.499 | 90           | 94.12       | 90           | 4289.4              | $Cm$        |
| Choice 3: $M'_3$ Nishi          | 18.499 | 7.027 | 36.725 | 90           | 116.04      | 90           | 4289.4              | $Im$        |
| $\langle M \rangle$ Nishi       | 9.250  | 7.027 | 12.242 | 90           | 116.04      | 90           | 715.0               | $Am$        |
| $\langle M \rangle$ Mumme       | 9.298  | 7.073 | 12.235 | 90           | 116.31      | 90           | 721.3               | $Am$        |
| Choice 1: $M_1$ Bigaré          | 12.332 | 7.142 | 25.420 | 90           | 89.85       | 90           | 2238.8              | ?           |
| Choice 2: $M'_1$ Bigaré         | 28.282 | 7.142 | 12.332 | 90           | 116.0       | 90           | 2238.8              | ?           |
| $\langle M \rangle$ Bigaré      | 9.427  | 7.142 | 12.332 | 90           | 116.0       | 90           | 746.3               | ?           |

**Table 3.** Transformation of the idealised coordinates of the Si ions.  $Si_1'$ ,  $Si_2'$  and  $Si_3'$  are related to  $Si_1$ ,  $Si_2$  and  $Si_3$  by the inversion centres.  $P_{\langle T \rangle \leftrightarrow \langle M \rangle}$  is the transformation matrix.

| Unit cell | $\langle T \rangle$ |     |     | $P_{\langle T \rangle \leftrightarrow \langle M \rangle}$ | $\langle M \rangle$ |     |     |
|-----------|---------------------|-----|-----|---|---------------------|-----|-----|
|           | x                   | y   | z   |   | x                   | y   | z   |
| $Si_1$    | 1/4                 | 1/4 | 1/4 |   | 0                   | 1/4 | 1/4 |
| $Si_2$    | 1/8                 | 1/4 | 1/2 |   | 5/8 (~2/3)          | 1/4 | 1/2 |
| $Si_3$    | 3/8                 | 1/4 | 0   |   | 3/8 (~1/3)          | 1/4 | 0   |
| $Si_1'$   | 3/4                 | 3/4 | 3/4 |   | 0                   | 3/4 | 3/4 |
| $Si_2'$   | 7/8                 | 3/4 | 1/2 |   | 1/3                 | 3/4 | 1/2 |
| $Si_3'$   | 5/8                 | 3/4 | 0   |   | 2/3                 | 3/4 | 0   |

**Table 4.** Effect of the glide mirror  $c$  ( $x, -y, z+1/2$ ) on the idealised coordinates of the Si ions in the  $\langle M \rangle$  unit cell. (see also Table 3 of ref [19]).

|        |     |     |     |                   |         |     |     |     |
|--------|-----|-----|-----|-------------------|---------|-----|-----|-----|
| $Si_1$ | 0   | 1/4 | 1/4 | $\longrightarrow$ | $Si_1'$ | 0   | 3/4 | 3/4 |
| $Si_2$ | 2/3 | 1/4 | 1/2 | $\xrightarrow{c}$ | $Si_2'$ | 1/3 | 3/4 | 1/2 |
| $Si_3$ | 1/3 | 1/4 | 0   | $\xrightarrow{c}$ | $Si_3'$ | 2/3 | 3/4 | 0   |

**Table 5.** Results of the Rietveld refinements for M<sub>1</sub>-alite data, in the angular range 10-80° (2θ<sub>Cu</sub>).

| Model           |                 | 3<M> <i>Pc</i> | 3<T> <i>Pn</i> | 3<T> <i>Pm</i> | 3<M> <i>Pm</i> | 3<M> <i>Am</i> | 3<T> <i>Im</i> |
|-----------------|-----------------|----------------|----------------|----------------|----------------|----------------|----------------|
| Cell parameters | a(Å)            | 27.8738(20)    | 27.8737(19)    | 27.8743(23)    | 27.8756(28)    | 27.8801(29)    | 27.8750(33)    |
|                 | b(Å)            | 7.0591(5)      | 7.0602(5)      | 7.0598(5)      | 7.0618(6)      | 7.0631(6)      | 7.0610(8)      |
|                 | c(Å)            | 12.2578(8)     | 18.3439(14)    | 18.3458(17)    | 12.2583(12)    | 12.2611(13)    | 18.3479(25)    |
|                 | α (°)           | 90             | 90             | 90             | 90             | 90             | 90             |
|                 | β (°)           | 116.031(6)     | 143.106(4)     | 143.110(4)     | 116.022(8)     | 116.021(9)     | 143.101(6)     |
|                 | γ (°)           | 90             | 90             | 90             | 90             | 90             | 90             |
| Shape function  | η               | 0.845(20)      | 0.857(21)      | 0.900(28)      | 0.872(30)      | 0.877(33)      | 0.878(41)      |
|                 | U               | 0.089(24)      | 0.130(25)      | 0.118(29)      | 0.287(40)      | 0.186(38)      | 0.133(46)      |
|                 | V               | -0.044(19)     | -0.081(20)     | -0.088(24)     | -0.246(33)     | -0.151(31)     | -0.104(39)     |
|                 | W               | 0.024(3)       | 0.031(4)       | 0.034(5)       | 0.067(7)       | 0.048(6)       | 0.038(8)       |
|                 | FWHM(°)         | 0.173          | 0.175          | 0.160          | 0.166          | 0.165          | 0.158          |
| Agreement       | R <sub>p</sub>  | 16.3           | 16.0           | 20.6           | 23.3           | 26.6           | 32.4           |
| Factors         | R <sub>wp</sub> | 19.1           | 18.8           | 23.8           | 27.0           | 29.4           | 35.6           |
|                 | R <sub>B</sub>  | 9.2            | 9.4            | 15.2           | 17.4           | 18.5           | 27.4           |
|                 | R <sub>F</sub>  | 8.0            | 6.8            | 9.1            | 11.3           | 15.1           | 16.5           |
|                 | χ <sup>2</sup>  | 8.2            | 8.2            | 13.0           | 17.2           | 18.4           | 26.8           |

**Table 6.** Refined atomic parameters within the 3<M> *Pc* model.

Unit cell parameters : a, b, c = 27.87438(20), 7.0591(5), 12.2578(8) Å; β = 116.031(6)°.

| Atom | x      | y      | z      | Atom | x      | y      | Z       |
|------|--------|--------|--------|------|--------|--------|---------|
| Ca1  | 0.0080 | 0.9825 | 0.4960 | Si2  | 0.2182 | 0.2391 | 0.4704  |
| Ca2  | 0.8952 | 0.0054 | 0.7136 | O14  | 0.1536 | 0.2538 | 0.4041  |
| Ca3  | 0.1110 | 0.9787 | 0.2546 | O15  | 0.2432 | 0.3952 | 0.4130  |
| Ca4  | 0.2244 | 0.0045 | 0.7376 | O16  | 0.2396 | 0.2782 | 0.6144  |
| Ca5  | 0.3395 | 0.0092 | 0.5037 | O17  | 0.2362 | 0.0291 | 0.4500  |
| Ca6  | 0.6731 | 0.9893 | 0.5042 | Si3  | 0.1209 | 0.2593 | 0.0637  |
| Ca7  | 0.4507 | 0.9790 | 0.2594 | O18  | 0.0903 | 0.4555 | 0.0608  |
| Ca8  | 0.5530 | 0.9868 | 0.7118 | O19  | 0.1143 | 0.2114 | -0.0714 |
| Ca9  | 0.7811 | 0.0022 | 0.2620 | O20  | 0.0955 | 0.0892 | 0.1102  |
| Ca10 | 0.8981 | 0.2812 | 0.9711 | O21  | 0.1837 | 0.2811 | 0.1554  |
| Ca11 | 0.0114 | 0.2257 | 0.7322 | Si4  | 0.3303 | 0.2352 | 0.2473  |
| Ca12 | 0.1088 | 0.2693 | 0.5261 | O22  | 0.2663 | 0.2025 | 0.1772  |
| Ca13 | 0.2272 | 0.2779 | 0.9564 | O23  | 0.3607 | 0.0487 | 0.2322  |
| Ca14 | 0.3346 | 0.2696 | 0.7477 | O24  | 0.3476 | 0.2729 | 0.3900  |
| Ca15 | 0.4419 | 0.2841 | 0.5324 | O25  | 0.3464 | 0.4167 | 0.1896  |
| Ca16 | 0.5570 | 0.2712 | 0.9720 | Si5  | 0.5484 | 0.2284 | 0.4510  |
| Ca17 | 0.6711 | 0.2364 | 0.7493 | O26  | 0.4838 | 0.2260 | 0.3922  |
| Ca18 | 0.7796 | 0.2465 | 0.5231 | O27  | 0.5694 | 0.0342 | 0.4160  |
| Ca19 | 0.0040 | 0.4962 | 0.0085 | O28  | 0.5726 | 0.2453 | 0.5973  |
| Ca20 | 0.7811 | 0.5225 | 0.2519 | O29  | 0.5680 | 0.4079 | 0.3986  |
| Ca21 | 0.8913 | 0.4809 | 0.7179 | Si6  | 0.4343 | 0.2469 | -0.0022 |
| Ca22 | 0.1045 | 0.5096 | 0.2864 | O30  | 0.3717 | 0.2981 | -0.0800 |
| Ca23 | 0.2272 | 0.5270 | 0.2235 | O31  | 0.4654 | 0.2801 | -0.0853 |
| Ca24 | 0.3356 | 0.4923 | 0.0115 | O32  | 0.4402 | 0.0274 | 0.0402  |
| Ca25 | 0.6642 | 0.5020 | 0.5098 | O33  | 0.4599 | 0.3822 | 0.1165  |
| Ca26 | 0.5579 | 0.4572 | 0.7260 | Si7  | 0.6607 | 0.2607 | 0.2591  |
| Ca27 | 0.4400 | 0.5219 | 0.2733 | O34  | 0.6040 | 0.3632 | 0.1790  |
| O1   | 0.0342 | 0.2523 | 0.6476 | O35  | 0.6669 | 0.0781 | 0.1863  |
| O2   | 0.9628 | 0.2276 | 0.8798 | O36  | 0.6631 | 0.1932 | 0.3877  |
| O3   | 0.8481 | 0.2655 | 0.7560 | O37  | 0.7089 | 0.4084 | 0.2834  |
| O4   | 0.1588 | 0.2790 | 0.7622 | Si8  | 0.8829 | 0.2503 | 0.4664  |
| O5   | 0.3509 | 0.2198 | 0.6501 | O38  | 0.8183 | 0.2552 | 0.4074  |
| O6   | 0.2684 | 0.2624 | 0.8770 | O39  | 0.9037 | 0.4098 | 0.4022  |
| O7   | 0.6316 | 0.2560 | 0.8640 | O40  | 0.9073 | 0.2930 | 0.6106  |
| O8   | 0.7106 | 0.2694 | 0.5913 | O41  | 0.9024 | 0.0431 | 0.4453  |
| O9   | 0.5120 | 0.2657 | 0.7533 | Si9  | 0.7856 | 0.2483 | 0.0219  |



|     |         |        |        |     |        |        |         |
|-----|---------|--------|--------|-----|--------|--------|---------|
| Si1 | 0.0049  | 0.2395 | 0.2612 | O42 | 0.7531 | 0.4285 | 0.0373  |
| O10 | -0.0218 | 0.0818 | 0.1555 | O43 | 0.7799 | 0.2433 | -0.1154 |
| O11 | 0.0083  | 0.4401 | 0.2007 | O44 | 0.7614 | 0.0550 | 0.0488  |
| O12 | -0.0312 | 0.2638 | 0.3337 | O45 | 0.8481 | 0.2665 | 0.1170  |
| O13 | 0.0645  | 0.1722 | 0.3547 |     |        |        |         |

**Table 7.** Refined atomic parameters within the 3<T> *Pn* model  
Unit cell parameters : a, b, c = 27.8737(19), 7.0602(5), 18.3439(14) Å;  $\beta$  = 143.106(4)°.

| Atom | x       | y      | z       | Atom | x       | y      | z       |
|------|---------|--------|---------|------|---------|--------|---------|
| Ca1  | 0.0189  | 0.9830 | 0.0153  | Si2  | 0.7580  | 0.2629 | 0.2503  |
| Ca2  | 0.1745  | 0.9790 | 0.4872  | O14  | 0.6637  | 0.2183 | 0.1454  |
| Ca3  | 0.1376  | 0.0263 | 0.7130  | O15  | 0.7690  | 0.4605 | 0.2199  |
| Ca4  | 0.97780 | 0.9977 | 0.2187  | O16  | 0.7996  | 0.2799 | 0.3803  |
| Ca5  | 0.3734  | 0.0340 | 0.7467  | O17  | 0.7998  | 0.0930 | 0.2555  |
| Ca6  | 0.2154  | 0.0296 | 0.2732  | Si3  | 0.1197  | 0.2458 | 0.0177  |
| Ca7  | 0.3015  | 0.9891 | 0.2228  | O18  | 0.0450  | 0.2834 | 0.9811  |
| Ca8  | 0.3367  | 0.9606 | -0.0163 | O19  | 0.0927  | 0.2880 | 0.9016  |
| Ca9  | 0.5358  | 0.9868 | 0.2492  | O20  | 0.1482  | 0.0272 | 0.0594  |
| Ca10 | 0.2182  | 0.2746 | 0.9566  | O21  | 0.1930  | 0.3846 | 0.1286  |
| Ca11 | 0.5612  | 0.2670 | 0.9672  | Si4  | 0.4718  | 0.2477 | 0.0335  |
| Ca12 | 0.2634  | 0.2171 | 0.7415  | O22  | 0.4617  | 0.0453 | 0.0617  |
| Ca13 | 0.5908  | 0.2494 | 0.7328  | O23  | 0.4016  | 0.2729 | -0.1119 |
| Ca14 | 0.2911  | 0.2654 | 0.5251  | O24  | 0.4660  | 0.4166 | 0.0859  |
| Ca15 | 0.6235  | 0.2716 | 0.5282  | O25  | 0.5580  | 0.2559 | 0.0982  |
| Ca16 | 0.8931  | 0.2608 | 0.9607  | Si5  | 0.0472  | 0.2353 | 0.4687  |
| Ca17 | 0.9214  | 0.2540 | 0.7379  | O26  | -0.0394 | 0.2066 | 0.4015  |
| Ca18 | 0.9624  | 0.2960 | 0.5286  | O27  | 0.0440  | 0.4160 | 0.4104  |
| Ca19 | 0.0133  | 0.4979 | 0.0038  | O28  | 0.1140  | 0.2715 | 0.6123  |
| Ca20 | 0.1745  | 0.5035 | 0.4976  | O29  | 0.0701  | 0.0471 | 0.4506  |
| Ca21 | 0.0371  | 0.5035 | 0.7556  | Si6  | 0.7105  | 0.2475 | 0.4634  |
| Ca22 | 0.8709  | 0.5138 | 0.25431 | O30  | 0.6273  | 0.2560 | 0.4073  |
| Ca23 | 0.1390  | 0.4720 | 0.7184  | O31  | 0.7189  | 0.0426 | 0.4347  |
| Ca24 | 0.9705  | 0.5212 | 0.2180  | O32  | 0.7846  | 0.2790 | 0.6090  |
| Ca25 | 0.2138  | 0.5163 | 0.2893  | O33  | 0.7111  | 0.4124 | 0.4028  |
| Ca26 | 0.3060  | 0.5287 | 0.2258  | Si7  | 0.0839  | 0.2786 | 0.2426  |
| Ca27 | 0.3439  | 0.4758 | 0.0122  | O34  | 0.9977  | 0.3625 | 0.1617  |
| O1   | 0.5924  | 0.2380 | 0.6493  | O35  | 0.0845  | 0.2400 | 0.1562  |
| O2   | 0.2509  | 0.2650 | 0.6478  | O36  | 0.1004  | 0.0819 | 0.3055  |
| O3   | 0.5859  | 0.2357 | 0.8661  | O37  | 0.1531  | 0.4302 | 0.3470  |
| O4   | 0.2585  | 0.2592 | 0.8779  | Si8  | 0.7992  | 0.2459 | 0.0293  |
| O5   | 0.0994  | 0.2535 | 0.7598  | O38  | 0.7329  | 0.3903 | 0.9814  |
| O6   | 0.4349  | 0.2570 | 0.7435  | O39  | 0.7772  | 0.1953 | 0.9189  |
| O7   | 0.7479  | 0.2775 | 0.7619  | O40  | 0.8000  | 0.0534 | 0.0784  |
| O8   | 0.9182  | 0.2215 | 0.6541  | O41  | 0.8865  | 0.3445 | 0.1386  |
| O9   | 0.8891  | 0.2672 | 0.8552  | Si9  | 0.3937  | 0.2219 | 0.4942  |
| Si1  | 0.4126  | 0.2397 | 0.2514  | O42  | 0.3089  | 0.3289 | 0.4017  |
| O10  | 0.3188  | 0.2139 | 0.1568  | O43  | 0.3862  | 0.0677 | 0.4201  |
| O11  | 0.4281  | 0.1766 | 0.1866  | O44  | 0.4179  | 0.1155 | 0.5987  |
| O12  | 0.4658  | 0.1087 | 0.3699  | O45  | 0.4620  | 0.3757 | 0.5565  |
| O13  | 0.4377  | 0.4597 | 0.2923  |      |         |        |         |