


On: 02 May 2014, At: 01:19

Publisher: Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK

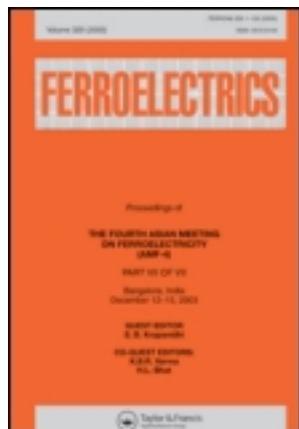

Ferroelectrics

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gfer20>

Electron Spectroscopy and the Electronic Structure of KNbO_3 : First Principle Calculations

S. Simsek ^a, H. Koc ^b, V. A. Trepakov ^c, A. M. Mamedov ^d & E. Ozbay ^d

^a Hakkari University, Turkey

^b Siirt University, Turkey

^c Institute of Physics ASCR, Czech Republic

^d Bilkent University, Nanotechnology Research Center, Turkey

Published online: 01 May 2014.

To cite this article: S. Simsek, H. Koc, V. A. Trepakov, A. M. Mamedov & E. Ozbay (2014) Electron Spectroscopy and the Electronic Structure of KNbO_3 : First Principle Calculations, *Ferroelectrics*, 461:1, 99-105, DOI: [10.1080/00150193.2014.889998](https://doi.org/10.1080/00150193.2014.889998)

To link to this article: <http://dx.doi.org/10.1080/00150193.2014.889998>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform. However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms &

Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>

Electron Spectroscopy and the Electronic Structure of KNbO_3 : First Principle Calculations

S. SIMSEK,¹ H. KOC,² V. A. TREPANOV,³ A. M. MAMEDOV,^{4,*}
AND E. OZBAY⁴

¹Hakkari University, Turkey

²Siirt University, Turkey

³Institute of Physics ASCR, Czech Republic

⁴Bilkent University, Nanotechnology Research Center, Turkey

The electronic structures of KNbO_3 were calculated within the density functional theory, and their evolution was analyzed as the crystal-field symmetry changes from cubic to rhombohedral via tetragonal phase. We carried out electron-energy loss spectroscopy experiments by using synchrotron radiation and compared the results with the theoretical spectra calculated within Density Functional Theory. The dominant role of the NbO_6 octahedra in the formation of the energy spectra of KNbO_3 compound was demonstrated. The anomalous behavior of plasmons in ferroelectrics was exhibited by the function representing the characteristic energy loss in the region of phase transition.

Keywords KNbO_3 ; electron energy loss; plasmon

Introduction

Over the past decades, electron energy loss (EEL) spectroscopy has developed into a major tool for the characterization of nonlinear structures and electronic structure of materials. Most of these studies focus on the ionization edges, where the position of the edges and their intensity provide a quantitative measure of the composition [1]. The low-loss energy region of the EEL spectrum (<50 eV) can also provide information on the composition and electronic structure, as well as optical properties [1, 2], although it has not found as wide an application as the energy-loss near-edge structure. In this low-loss region, interband transitions and plasmon losses are observed.

The plasmons hold a unique position among the quasiparticles in solids because of their special features. The spectra of plasmons are described by the functions $-\text{Im}\epsilon^{-1}$ (volume plasmons) and $-\text{Im}(\epsilon+1)^{-1}$ (surface plasmons). Experimentally, they are determined by measuring the characteristic electron energy losses (EEL) [2]. In general, the half-width of the principal W peak typically exceeds 4.0 eV. The intensity of the W peak critically depends on the orientation of the sample and the energy of the electron beam, their resolution being not finer than 1.0 eV. This severely hampers the determination of true plasmon spectra. Of great interest, in this connection, is a calculation procedure in which the experimental data

Received September 2, 2013; in final form November 5, 2013.

*Corresponding author. E-mail: mamedov@bilkent.edu.tr

on the reflection spectra and the Kramers-Kronig integral relations are used to determine the plasmon spectra [3].

The aim of the present paper is to apply Density Functional Theory (DFT) band structure calculations of the electronic structure, dielectric functions, and spectra of plasmons of both types to a wide variety of KNbO_3 in order to explore how low-loss EEL spectra can be predicted.

Our paper is organized as follows. In section 2, we describe the methodology, structure, and computational details. In sections 3–4, we illustrate the validity of the formalism by applying methodology and theory to KNbO_3 ferroelectrics.

Computational Details

The optical properties of ABO_3 type compounds were theoretically studied by means of first principles calculations in the framework of density functional theory and based on the local density approximation (LDA) as implemented in the ABINIT code [4, 5]. The self-consistent norm-conserving pseudopotentials are generated using the Troullier-Martiens scheme, which for the KNbO_3 , include the semicore s and p states of the K- and Nb- atoms (see Table 1) [6] which is included in the Perdew-Wang [7] scheme as parameterized by Ceperly and Alder [8]. For the calculations, the wave functions were expanded in plane waves up to a kinetic-energy cutoff of 40 Ha (tetragonal and rhombohedral KNbO_3). The level of accuracy for the Kohn-Sham eigenvalues and eigenvectors is required to calculate the response function. The Brillouin zone was sampled using an $8 \times 8 \times 8$ the Monkhorst-Pack [9] mesh of special k points. The coordinates of KNbO_3 [10, 11] are reported in Table 1. All the calculations of KNbO_3 have been used with experimental lattice constants and atomic positions. The lattice constants and atomic positions are given in Table 1. The coordinates of the other atoms can easily be obtained by using the symmetry operations of the space groups. These parameters were necessary to obtain converged results of the optical properties.

Table 1
Atomic position and lattice parameters of KNbO_3 [10, 11, 20]

Crystals	Symmetry Class	Lattice Parameters [\AA]	Atoms, WPa	Position
KNbO_3	$m\bar{3}m$	$a = b = c = 4.0214$	K(1a)	(0.0, 0.0, 0.0)
			Nb(1b)	(0.5, 0.5, 0.5)
			O(3c)	(0.5, 0.5, 0.0)
KNbO_3	4mm	$a = b = 3.9970$ $c = 4.0630$	K(1a)	(0.0, 0.0, 0.023)
			Nb(1b)	(0.5, 0.5, 0.5)
			O1(1b)	(0.5, 0.5, 0.04)
			O2(2c)	(0.5, 0.0, 0.542)
KNbO_3	3m	$a = b = c = 4.016$	K	(0.0112, 0.0112, 0.0112)
			Nb	(0.5, 0.5, 0.5)
			O1	(0.5295, 0.5295, 0.0308)
			O2	(0.5295, 0.0308, 0.5295)

Electronic Structure of the Valence and Conduction Bands

In this section, we describe the evolution of the electronic structure of KNbO_3 in the structural and ferroelectric phase transitions in relation with the evolution of the symmetry of the crystal field. The results from vacuum ultraviolet (VUV) reflectivity experiments are reported in the literature for some ABO_3 compounds [12–19]. We furthermore give a comparison of the theoretical band structure of the valence and conduction bands in various phases. Last, we report our results for the theoretical energy gap, and the energy gap values determined experimentally. Since ABO_3 ferroelectrics have been widely studied [12–19] we show in detail only the calculated band structures for KNbO_3 in different phases. The dispersion of the energy of the valence bands for the cubic (C), tetragonal (T) and rhombohedral (R) phases at the equilibrium lattice parameters are reported in Fig. 1. The top of the valence band is located at the R point in the cubic and tetragonal phases, and in the Z point in the rhombohedral phase. The DOS reported for all phases in Fig. 1(a)–(c) show a much higher density of states at and near the top of the valence bands. The valence bandwidth decreases by 0.3 eV between the different crystal fields, from 5.6 eV in the cubic phase to 4.3 eV in the rhombohedral phase. The bandwidth of the tetragonal phase is closer to the width of the cubic phase than to the rhombohedral one.

As we stated hereinabove, the electronic band structure of paraelectric cubic KNbO_3 along the symmetry lines of the cubic Brillouin zone is shown on Fig. 1(a). Let us now describe the electronic band structure of the KNbO_3 in more detail. It is clear that the indirect band gap appears between the topmost valence band and at the R point and at the bottom of conduction band at the Γ point. The overall profile of our band structure is qualitatively like the band structure obtained by previous studies [13, 14], where the same compound [14] was investigated in the cubic and tetragonal phases. It is observed that the conduction band minimum goes from the Γ point through Δ to the X point and always remains nearly flat in agreement with previous studies [14, 15, 18]. The calculated indirect band gap ($\text{R}-\Gamma$) is equal to 1.54 eV while the smallest direct band gap ($\Gamma_{\text{V}}-\Gamma_{\text{C}}$) is 2.51 eV. These calculated values are smaller than the experimental value of 3.1 eV for the indirect gap [16]. The origin of this discrepancy could be the use of DFT, which generally underestimates the band gap in semiconductors and insulators [3]. The band with the lowest energy in Fig. 1, lying between -16.0 eV and -17.0 eV, correspond to a very large extent, to O $2s$ states. The nine valence bands between -5.9 eV and the Fermi level (zero) are mainly due to the oxygen O $2p$ states hybridized with Nb $4d$ states. These nine valence bands are split into triple and double degenerate levels at the Γ point ($\Gamma_{15}, \Gamma_{25}, \Gamma_{25}$) separated by energies of 1.64 eV ($\Gamma_{15}-\Gamma_{25}$), of 0.3 eV (Γ_{25}, Γ_{15}), and of 1.94 eV ($\Gamma_{15}-\Gamma_{25}$) due to the crystal field and electrostatic interaction between mainly O $2p$ and Nb $4d$ orbitals. In the conduction band, the one two triply (Γ_{12}) degenerate levels represents Nb $4d t_{2g}$ and Nb e_g orbitals separated by energy of 4.2 eV. The topmost valence bands are the oxygen $2p_x, 2p_y$ states while the lowest valence bands are formed by the hybridization of Nb $4d e_g$ and O $2p_z$ states. In the conduction band region, the first conduction band from approximately 1.59 eV above the Fermi level to 5.6 eV arises from predominantly Nb t_{2g} states with small O $2p$ mixing. The bands in the conduction band that are shown in Fig. 1 belong to Nb $4d e_g$ states. In additions, some electrons from Nb $4d$ transform into the valence band and take part in the interaction between Nb and O. This implies that there is hybridization between Nb $4d$ and O $2p$.

The agreement between our density of states (DOS) and the experimental spectrum is good [12–19]. The dispersion curve of the conduction bands at the theoretical equilibrium lattice parameters are reported in Fig. 1(a)–(c). The bottom of the conduction band is found

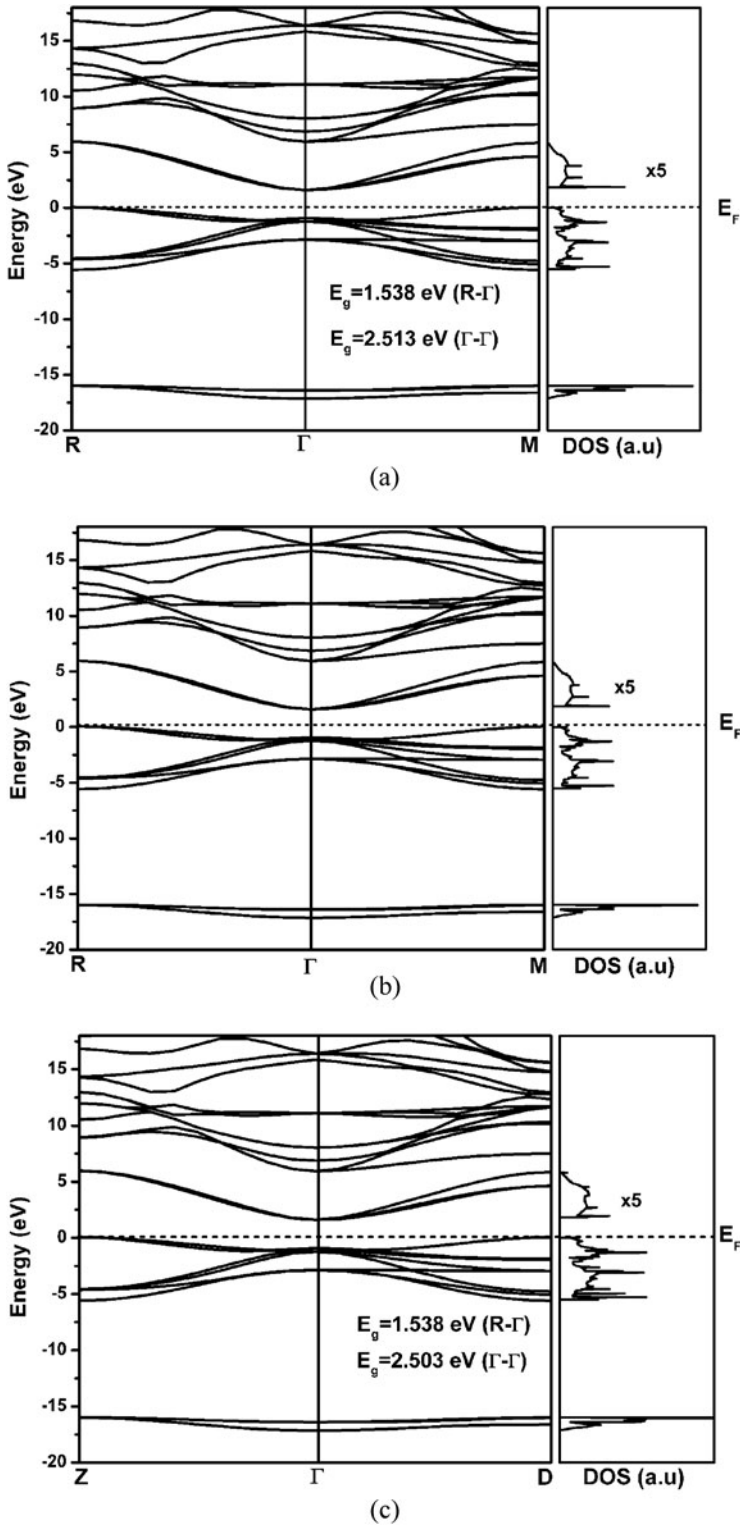


Figure 1. Electronic band structure and DOS of KNbO₃, cubic (a), tetragonal (b), rhombohedral (c).

Table 2
Theoretical and experimental data of plasmon energies and energy features of $-\text{Im}\epsilon^{-1}$ for KNbO_3

	Exp	Exp	Theory	Exp[12]	Theoretical
Material	E_p [eV]	E_s [eV *]	E_p [eV]	$-\text{Im}\epsilon^{-1}$	$-\text{Im}\epsilon^{-1}$
$\text{KNbO}_3/\text{Cubic}$	—	—	21.8	—	6.5, 15.0, 22.6, 28.1, 41.5
$\text{KNbO}_3/\text{Tetragonal}$	24.0	17.0	22.0	7.1, 14.0, 23.2, 29.5	6.4, 14.9, 22.5, 28.0, 41.0
$\text{KNbO}_3/\text{Rhombohedral}$	—	—	21.9	—	6.4, 14.9, 22.5, 28.1, 41.4

to be at the Γ point for all phases. The first conduction bands are found to have an e_g character at the Γ point in the cubic phase (Fig. 1). At higher energy, conduction bands have a_{1g} or t_{2g} character at the R and Γ points. The gap in the conduction band has a minimum of 1.3 eV at Γ point. The fundamental gap of KNbO_3 single crystal has been measured in the cubic and tetragonal phases [12]. More precisely, VUV spectroscopy has been performed in reflectivity in the 1.0–35.0 eV range, and the absorption spectrum has been deduced from a Kramers-Kronig analysis [15]. The band gap obtained from a fit of the low absorption is found to be of 2.86 eV. However, EEL spectroscopy experiments a large momentum transfer [17], give a gap value of about 2.9 eV. Our fitted value for E_g amounted to 2.45 eV in the cubic phase of KNbO_3 . We have also calculated the minimum and direct LDA band gap energy at the theoretical lattice parameters (Table 1). Within the accuracy of our calculations, the values of the direct and indirect band gap are within 2.35 eV of each other in all phases except the rhombohedral one, where the minimum gap is 1.5 eV smaller than the first direct gap. Our results are in a good agreement with the previous calculation [14, 17] performed at the experimental lattice parameters, with the exception of the rhombohedral phase (Table 2).

Energy Loss Spectroscopy

In this section, we first apply the theoretical framework defined in section 3 and report our theoretical EEL spectra. Valence EEL spectroscopy experiments have previously been performed in transmission at a large momentum transfer q [1] and also in the reflection [1, 12]. In this work, we have performed very low q and VUV reflectivity [12–14] experiments and compared them with the theoretical results. In Fig. 2, we report the dielectric functions (real and imaginary parts, and $\text{Im}\epsilon^{-1}$) for KNbO_3 in three phases: cubic, tetragonal, and rhombohedral, calculated in LDA. Three regions can be distinguished. First, we observe that the valence excitation region extends up to 15.0 eV. The form of the structure and the shape of ϵ_2 for the investigated crystal are determinate by the positions of the critical state density points. The similarity between the ϵ_2 for all the modifications of KNbO_3 in the region up to 14.0 eV points to a substantial role of NbO_6 octahedra in the formation of the band structure. This means that the NbO_6 octahedra determine the lowest limit of the conduction band and the upper valence band. These bands are similar for many ABO_3 compounds, since the d-orbitals of the transition metals and the p -orbitals of oxygen, which are joined in each octahedron, yield the main contribution to the bands indicated above. The real part of ϵ behaves mainly as a classical oscillator. It vanishes (from positive to negative value) around 5.52, 10.01, 11.88, and 13.48 eV, and correspondingly, ϵ_2 shows the maxima of absorption at these frequencies. The real part ϵ vanishes (from negative to positive) at 6.40, 11.29, 12.72, and 14.96 eV (not seen in the figure because of the small broadening).

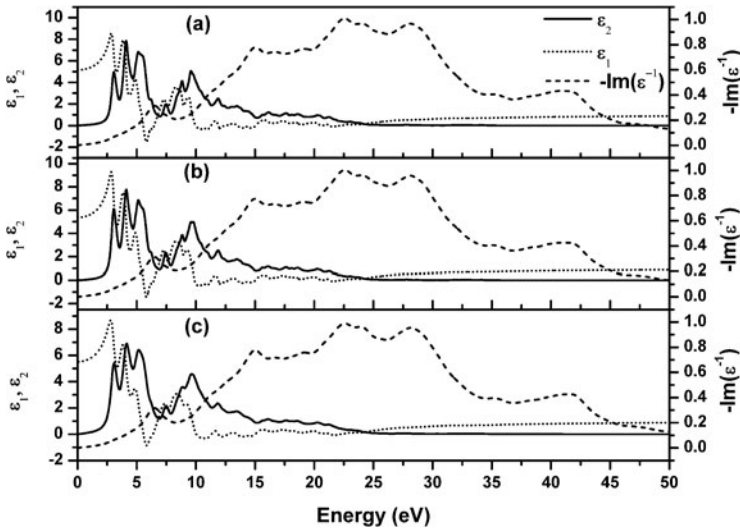


Figure 2. The calculated real (ϵ_1) and imaginary (ϵ_2) parts of the dielectric function and electron energy-loss spectra ($-\text{Im}\epsilon^{-1}$) of KNbO_3 in cubic (a), tetragonal (b) and rhombohedral (c) phases.

The loss function consequently shows peaks at these energies: 6.50 and 15.00 eV. In the absorption spectrum ϵ_2 the strong absorption below 8.0 eV stems from transitions from the valance band to the e_g states. The absorption band extending beyond 8.5 eV up to 14.0 eV is associated with transitions from the valance band to t_{2g} states in the conduction band. Second, we see that above 15.0 eV, corresponding to the O 2s and Nb 4p excitations, ϵ_1 also behaves as a classical oscillator: it vanishes (from positive to negative) at 21.30 eV. Peaks are observed in the loss function when ϵ_1 vanishes (from negative to positive) at 22.11 eV. Third, we remark that the region above 22.0 eV cannot be interpreted in terms of classical oscillators. Above 22.0 eV ϵ_1 and ϵ_2 are dominated by linear features, increasing for ϵ_1 and decreasing for ϵ_2 . The corresponding loss function exhibits a broadened peak at 41.3 eV that we assign not to plasmons but rather to their forms of collective excitations. The plasmons are defined by a vanishing real part of dielectric function and a minimum of the imaginary part, which is not the case for this peak. Such linear behavior for ϵ_1 and ϵ_2 has already been observed in the theoretical EEL spectra of ABO_3 . At higher energies, however, they drastically modify the triple 4p plasmons, both in line shape and peak position. We also find a small anisotropy for the xx and zz directions.

Conclusion

We have performed an ab initio study of the electronic structures of KNbO_3 . Within the DFT-LDA framework, we have found it necessary to include the semicore states in the calculations. We have then followed the effect on the electronic structure as the crystal field evolves from a cubic to a tetragonal structure, and then to a rhombohedral. We have described a fingerprint in the electronic structure of cubic and rhombohedral KNbO_3 . By using our earlier EEL spectroscopy experimental results on ABO_3 ferroelectrics and the theoretical investigation in the present paper, we found plasmon oscillation energy for the investigated compounds.

References

1. H. Ibach and D. L. Mills, *Electron Energy Loss Spectroscopy and Surface Vibrations*. N.Y: Academic Press, 1982.
2. P. E Batson, Electron Energy Loss Studies in Semiconductors, in: *Transmission Electron Energy Loss Spectrometry in Material Science and the EELS*. Weinheim: Wiley,-VCH Verlag, 2004.
3. M. Dressel and G. Grüner, *Electrodynamics of Solids: Optical Properties of Electrons in Matter*. Cambridge: Cambridge University Press, 2003.
4. X. Gonze, J. M. Beuken, R. Caracas, F. Detraux, M. Fuchs, G. M. Rignanese, L. Sindic, M. Verstraete, G. Zerah, F. Jollet, M. Torrent, A. Roy, M. Mikami, Ph Ghosez, J. Y. Raty, and D. C. Allan, First-principles computation of material properties: the ABINIT software project. *Comput Mater Sci.* **25**, 478–492 (2002).
5. X. Gonze, B. Amadon, P. M. Anglade, J. M. Beuken, F. Bottin, P. Boulanger, F. Bruneval, D. Caliste, R. Caracas, M. Cote, T. Deutsch, L. Genovese, P. H. Ghosez, M. Giantomassi, S. Goedecker, D. R. Hamann, P. Hermet, F. Jollet, G. Jomard, S. Leroux, M. Mancini, S. Mazevet, M. J. T. Oliveira, G. Onida, Y. Pouillon, T. Rangel, G. M. Rignanese, D. Sangalli, R. Shaltaf, M. Torrent, M. J. Verstraete, G. Zerah, and J. W. Zwanziger, ABINIT: First-principles approach to material and nanosystem properties. *Comput Phys Comm.* **180**, 2582–2615 (2009).
6. N. Troullier and J. L. Martins, Efficient pseudopotentials for plane-wave calculations. *Phys Rev B.* **43**, 1993–2006 (1991).
7. J. P. Perdew and Y Wang, Accurate and simple analytic representation of the electron-gas correlation energy. *Phys Rev B.* **45**, 13244–13249 (1992).
8. D. M. Ceperley and B. J. Alder, Ground state of the electron gas by a stochastic method. *Phys Rev Lett.* **45**, 566–569 (1980).
9. H. J. Monchorst and J. D. Pack, Special points for Brillouin-zone integrations. *Phys Rev B.* **13**, 5188–5192 (1976).
10. K. Rabe, C. H. Ahn, and J. M. Triscone, *Physics of Ferroelectrics: A Modern Perspective*. Heidelberg: Springer, 2007.
11. V. Gopalan, K. L. Schepler, V. Dierolf, and I. Biaggio, Ferroelectric Materials, in: *The Handbook of Photonics*. CRC Press Boca Baton, 2007.
12. A. M. Mamedov, Optical properties (VUV Region) of ABO_3 ferroelectrics: Application of synchrotron radiation. *Ferroelectrics.* **303**, 141–143 (2004). Mamedov AM: The Energy loss spectrum in oxygen –Octahedron. *Ferroelectrics.* **3**, 75–80(1985).
13. S. Cabuk, H. Akkus, and A. M. Mamedov, Electronic and optical properties of KTaO_3 : Ab initio calculation. *Phys B.* **394**, 81–85. (2007).
14. S. Cabuk and S. Simsek, First-principles calculation of the linear and nonlinear optical properties of LiTaO_3 . *Phys Scr.* **81**, 055703–055711 (2010).
15. A. M. Mamedov, Vacuum ultraviolet (VUV) reflectivity and electron states in LiNbO_3 . *Phys (B+C).* **128**, 61–68 (1985).
16. A. M. Mamedov, M. A. Osman, and L. C. Hajieva, VUV reflectivity of LiNbO_3 and LiTaO_3 single crystals. *Appl Phys A.* **34**, 189–192. (1984).
17. E. E. Krasovskii, O. V. Krasovskii, and W. Schattke, Ab initio calculation of the optical and photoelectron spectra of KNbO_3 and KTaO_3 . *J Electron Spectr Rel Phen.* **83**, 121–127 (1997).
18. C. M. I. Okoye, Theoretical study of the electronic structure, chemical bonding and optical properties of KNbO_3 in the paraelectric cubic phase. *J Phys: Cond Matter.* **15**, 5945–5959 (2003).
19. H. Wang, F. Wu, and H. Jiaug, Electronic band structures of ATaO_3 (A = Li, Na, and K) from first-principles many-body perturbation theory. *J Phys Chem C.* **115**, 16180–16186 (2011).
20. Y. Shiozaki, E. Nakamura, and T. Mitsui, *The Landolt-Bornstein Database*. Berlin: Springer New Ser. III/36, 2002.