

# **SYNTHESIS, CHARACTERIZATION AND EFFECT OF ATMOSPHERE ON SINTERING BEHAVIOR OF BaTiO<sub>3</sub> NANO-POWDERS**

A THESIS SUBMITTED IN PARTIAL FULFILLMENT  
OF THE REQUIREMENTS FOR THE DEGREE OF

**Bachelor of Technology  
In  
Ceramic Engineering**

By  
**RAHUL PRAKASH**

Under the Guidance of  
**Prof. Debasish Sarkar**



**Department of Ceramic Engineering  
National Institute of Technology  
Rourkela  
2011**



## National Institute of Technology Rourkela

### CERTIFICATE

This is to certify that this thesis entitled, “SYNTHESIS, CHARACTERIZATION AND EFFECT OF ATMOSPHERE ON SINTERING BEHAVIOR OF BaTiO<sub>3</sub> NANO-POWDER”, submitted by Mr. Rahul Prakash in partial fulfillments for the requirements for the award of Bachelor of Technology Degree in Ceramic Engineering at National Institute of Technology, Rourkela is an authentic work carried out by him under my guidance.

To the best of my knowledge, the matter embodied in the thesis has not been submitted to any other University / Institute for the award of any Degree or Diploma.

Date:

Prof. Debasish Sarkar  
Associate Professor  
Department of Ceramic Engineering,  
National Institute of Technology,  
Rourkela- 769 008

# **ACKNOWLEDGEMENTS**

I wish to express my deep sense of gratitude and indebtedness to Prof. Debasish Sarkar, Department of Ceramic Engineering, N I T Rourkela for introducing the present topic and for his inspiring guidance, constructive criticism and valuable suggestion throughout this project work. I would like to express my gratitude to Prof. J. Bera (Head of the Department), Prof. S. Bhattacharyya, Prof. S. K. Pratihar, Prof. S. K. Pal, Prof. Ritwik Sarkar, Prof. R. Majumdar and Prof. A. Chowdhury for their valuable suggestions and encouragements at various stages of the work. I am also thankful to all staff members of Department of Ceramic Engineering NIT Rourkela.

I am also grateful to Mr. Rajesh (Department of Metallurgy and Material Science) for helping me for doing SEM and analysis of my samples.

I am thankful to research scholars in Department of Ceramic Engineering for helping me out in different ways.

Last but not least, my sincere thanks to all my friends who have patiently extended all sorts of help for accomplishing this undertaking.

11<sup>th</sup> May 2011

RAHUL PRAKASH

# CONTENTS

	<b>Page No.</b>
<i>Abstract</i>	<i>i</i>
<i>List of Figures</i>	<i>ii</i>
<i>List of Tables</i>	<i>iii</i>
<b>Chapter 1 GENERAL INTRODUCTION</b>	<b>1-6</b>
1.1 Introduction to BaTiO <sub>3</sub>	2-4
1.2 Properties of BaTiO <sub>3</sub>	4-5
1.3 Applications of BaTiO <sub>3</sub>	5
1.4 Major research on BaTiO <sub>3</sub>	5
1.5 Outline of the report	6
<b>Chapter 2 LITERATURE REVIEW</b>	<b>7-11</b>
2.1 Synthesis of BaTiO <sub>3</sub> nano-powders	8
2.2 Sintering of green specimen of BaTiO <sub>3</sub> nano-powders in inert/reducing atmosphere.	9-10
2.3 Summary of Literature	10
2.4 Objectives of the present studies	11
<b>Chapter 3 EXPERIMENTAL WORK</b>	<b>12-16</b>
3.1 Synthesis of Barium Titanate (BaTiO <sub>3</sub> )	13
<i>3.1.1 Powder preparation</i>	14-15
<i>3.1.2 Powder characterization</i>	15
3.2 Preparation of binder and green specimens	16
3.3 Sintering behavior of green compacts	16
<i>3.3.1 Characterization of Sintered Specimens:</i>	16
<b>Chapter 4 RESULTS AND DISCUSSION</b>	<b>17-30</b>
4.1 Phase analysis of synthesized nano-powders of BaTiO <sub>3</sub>	18-23
4.2 Relative Density	24
4.3 Surface Area	25
4.4 Surface morphology analysis	26-28
4.5 Dilatometric Analysis of green specimen of BaTiO <sub>3</sub> nano-powder	29-30
<b>Chapter 5 CONCLUSIONS</b>	<b>31-32</b>
<b>References</b>	<b>33-34</b>

## **ABSTRACT**

Barium Titanate ( $\text{BaTiO}_3$ ) is a classic perovskite material for the manufacture of multilayer ceramic capacitor (MLCC) in electronic industry. Day to day miniaturization mobile device demands  $\text{BaTiO}_3$  nanoparticles to fabricate multilayer along with metal electrode and hence control atmosphere sintering is necessary to achieve best performance of this metal-ceramic composite layers. Hence, prime objective of this work was to synthesis of  $\text{BaTiO}_3$  nanopowders, their relevant characterization and finally their sintering behavior study at different atmospheres at different sintering profile. In this research, combined wet-chemical and subsequent calcination technique has been adapted to synthesis nanoscale  $\text{BaTiO}_3$  powders. Cosmetic grade  $\text{TiO}_2$  was used to prepare  $\text{BaTiO}_3$  nanoparticles from as-synthesized elongated  $\text{BaCO}_3$  nanoparticles. Pure, high crystalline,  $\text{BaTiO}_3$  powder was successfully synthesized at  $1100^\circ\text{C}$ . Powders were consolidate through uniaxial press and sintered in dilatometer furnace at different temperature profile in air, argon and nitrogen atmosphere. Maximum density was obtained in air and lowest in argon atmosphere, this is due to effect of partial pressure of oxygen. A significant change in d-spacing was also observed after control atmosphere sintering at  $1250^\circ\text{C}$  and  $1350^\circ\text{C}$ . The sintering behavior and their microstructure could be modified through synchronization of consolidation technique and gas flow rate.

## LIST OF FIGURES:

		<b>PAGE No.</b>
<b>Fig.1.1</b>	Perovskite Structure	2
<b>Fig 1.2</b>	BaTiO <sub>3</sub> Polymorphs showing direction of polarization	4
<b>Fig. 3.1</b>	Flow Diagram of the Procedure	13
<b>Fig.3.2</b>	For calcination at (A)1100°C and (B)900°C for 2 hours.	15
<b>Fig.4.1</b>	XRD pattern of BaCO <sub>3</sub> and TiO <sub>2</sub> precursor powder mix.	18
<b>Fig.4.2</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder calcined at 900°C for 2hours.	18
<b>Fig.4.3</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder calcined at 1100°C for 2hours	19
<b>Fig.4.4</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in air.	19
<b>Fig.4.5</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in argon.	20
<b>Fig.4.6</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in nitrogen	20
<b>Fig.4.7</b>	XRD pattern of BaTiO <sub>3</sub> nano-powder sintered at 1350°C for 2hours in nitrogen.	21
<b>Fig.4.8</b>	XRD pattern for sintered BaTiO <sub>3</sub> in different atmospheres at 1250°C.	22
<b>Fig.4.9</b>	XRD pattern for sintered BaTiO <sub>3</sub> in nitrogen atmosphere at 1250°C and 1350°C.	23
<b>Fig.4.10</b>	Relative density vs Temperature curve in air, argon and nitrogen.	22
<b>Fig.4.11</b>	FESEM image of BaCO <sub>3</sub> and TiO <sub>2</sub> mix precursors	26
<b>Fig.4.12</b>	BaTiO <sub>3</sub> nano-powder calcined at 1100°C for 2hours	26
<b>Fig.4.13</b>	Green specimen of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in air.	27
<b>Fig.4.14</b>	Green specimen of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in nitrogen	27
<b>Fig.4.15</b>	Green specimen of BaTiO <sub>3</sub> nano-powder sintered at 1250°C for 2hours in argon.	28
<b>Fig. 4.16 and Fig. 4.17</b>	Dilatometric curve for green specimen of BaTiO <sub>3</sub> nano-powder	29

sintered at 1250° for 2hours in air, argon and nitrogen.

<b>Fig. 4.18 and Fig. 4.19</b>	Dilatometric curve for green specimen of BaTiO <sub>3</sub> nano-powder sintered at 1350° for 2hours in air, argon and nitrogen.	30
--------------------------------	---	----

### **LIST OF TABLES:**

<b>Table 4.1</b>	Crystallite size and Crystal structure from XRD analysis	23
<b>Table 4.2</b>	Relative density of specimen sintered in air, argon and nitrogen at 1250°C and 1350°C.	24

# **Chapter 1**

## **General Introduction**




## 1.1 Introduction to $BaTiO_3$ :

**Chemical formula:**  $BaTiO_3$

**Compound type:** Inorganic

**Structure:** Perovskite

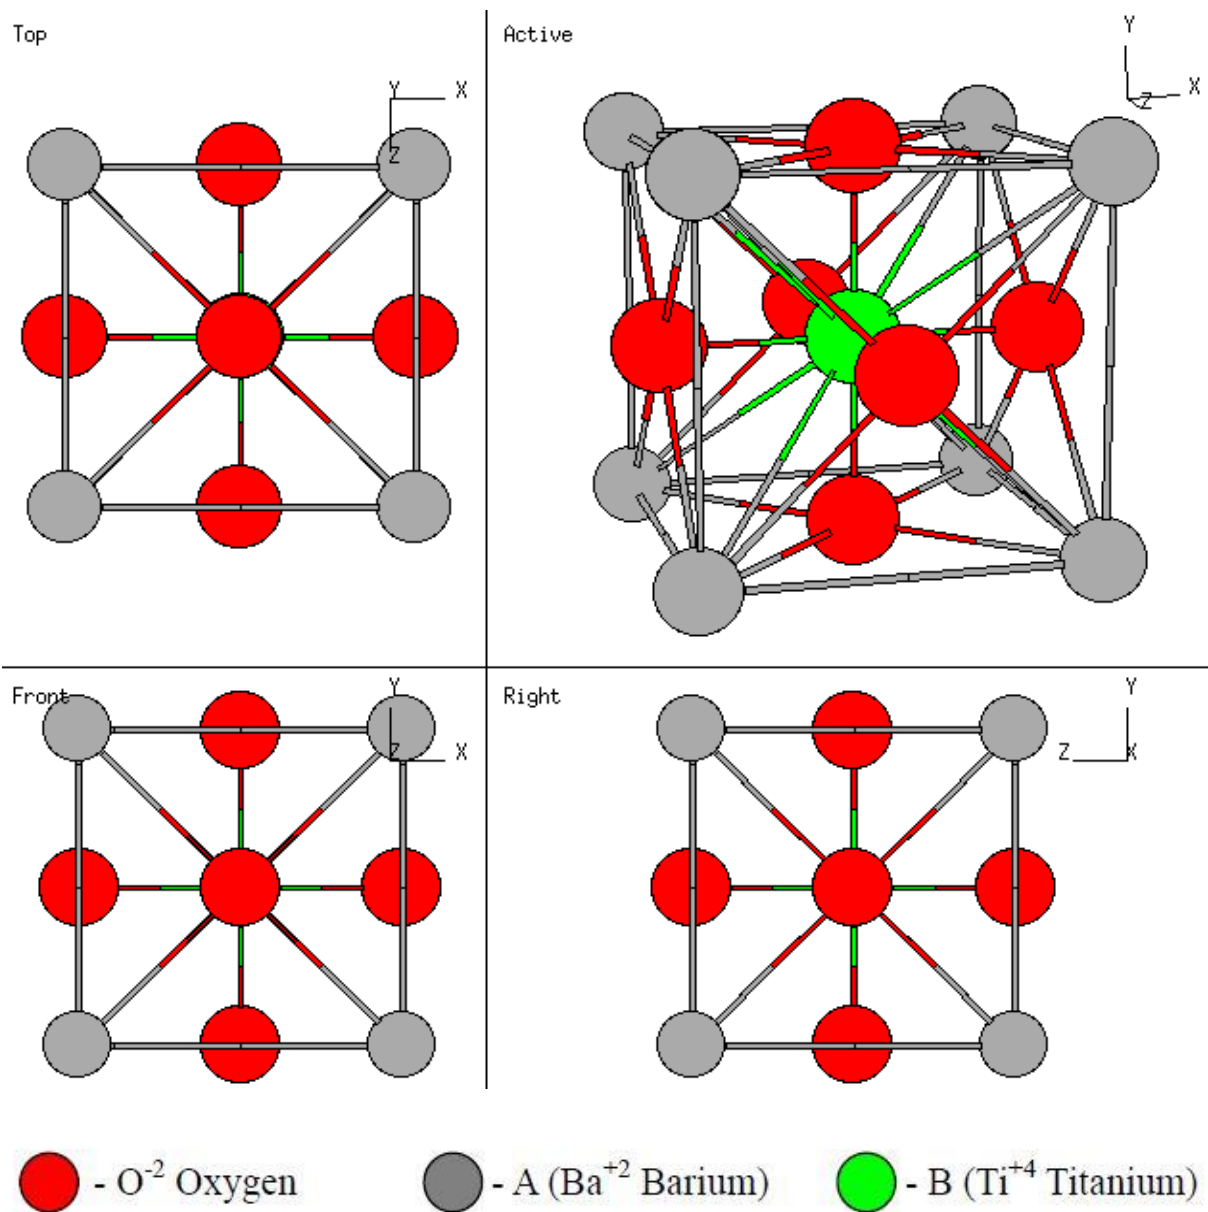

**Fig.1.1 Perovskite Structure<sup>[1]</sup>**

## **BaTiO<sub>3</sub> : The prototypical Ferroelectric**

The observation of ferroelectric behavior in BaTiO<sub>3</sub> made it first and probably the most extensively investigated of all ferroelectrics and is basically due to the properties of its polymorphs. The discovery led to the availability of dielectric constant ( $\kappa$ ) up to 2 orders of magnitude, greater than that had been known before.

Reasons that made BaTiO<sub>3</sub>, a curious field of study:


- Relatively simple crystal structure
- Ferroelectric at room temperature ( $\theta_c=120^\circ\text{C}$ )
- Durable
- Easily prepared in the form of thin film, single crystal, or polycrystalline ceramic [2]

### **1.2 Crystal Structure:**

The Ba<sup>2+</sup> and O<sup>2-</sup> forms a face centered cubic arrangement with Ti<sup>4+</sup> occupying the octahedral interstices. BaTiO<sub>3</sub> exhibits para-electricity and an isotropic di-electricity due to the high symmetry of its cubic phase. When cooled below  $\theta_c$ , there is a change in structure from cubic phase to distorted tetragonal with the displacement of positive and negative charge centers within the sub-lattice[3]. Due to this, a dipole moment parallel to one of the cubic axes of original phase arises and this spontaneous polarization generated in the tetragonal structure leads to piezoelectric and ferroelectric behavior.

Transformations:

Rhombohedral(<-90°C), Orthorhombic(<0°C), Tetragonal(<120°C), Cubic(>120°C)

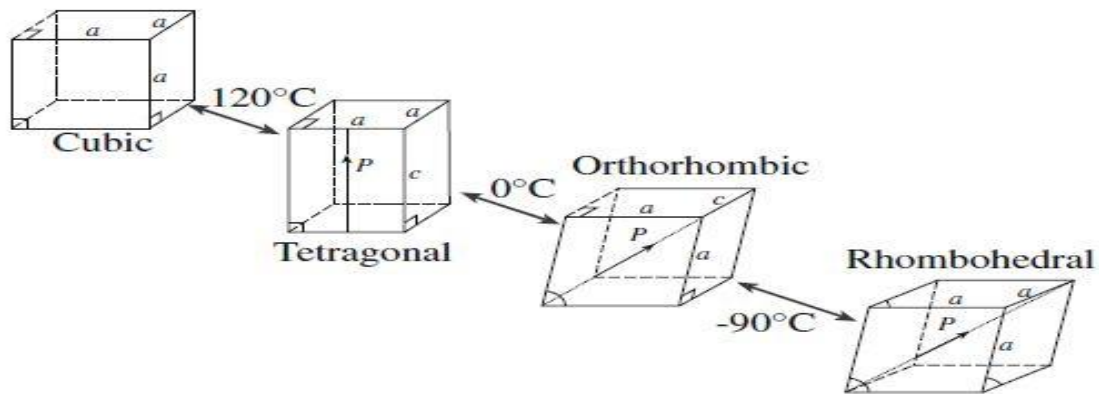

**Fig 1.2** BaTiO<sub>3</sub> Polymorphs showing direction of polarization <sup>[2]</sup>

However BaTiO<sub>3</sub> is rarely used in its pure form, solid-solution with an iso-structural compound is used to broaden the  $\theta_c$  as well as shifting it to the lower temperatures.

(Ex: solid solution of BaTiO<sub>3</sub> and SrTiO<sub>3</sub>) [2].

The firing of BaTiO<sub>3</sub> ceramics in an inert atmosphere (argon) , without sacrificing densification can lead to a dramatic increase of both the dielectric constant and dissipation factor of the samples[4].

### 1.3 Properties of BaTiO<sub>3</sub>:

- Ferroelectric
- By implication ,para-electric and also piezoelectric material
- Hysteresis loop for polycrystalline BaTiO<sub>3</sub> ceramic has a higher  $E_c$  and lower  $P_r$  than the single crystal.
- Melting point is 1625°C.
- Density is 6.02 gm/cc.
- Behaves as Relaxor dielectric,  $\kappa$  and  $\tan\delta$  changes with frequency.

To achieve high values of dielectric constant at room temperature stability over wide range of temperature T [2].

- Solid solution can be formed
- Grain size can be reduced
- Induction of mechanical stresses in thin films

So study of all these aspects are of great importance to enhance the applicability.

#### **1.4 Applications of BaTiO<sub>3</sub>:**

BaTiO<sub>3</sub> being a dielectric ceramic is used for capacitors (Disk capacitors, MLCC etc.). Also as a piezoelectric material it is used for transducers and microphones. The Curie point of BaTiO<sub>3</sub> is 120 °C and its spontaneous polarization is about 0.15 C/m<sup>2</sup> at room temperature [5]. Polycrystalline BaTiO<sub>3</sub> exhibits positive temperature co-efficient, making it useful for thermistors and self-regulating electric heating systems.

#### **1.5 Major Research on BaTiO<sub>3</sub>:**

The recent advances relating to electronic devices modeled from BaTiO<sub>3</sub> show the trend of improved performance with continuous miniaturization. For MLCCs, this means enhanced capacitance per unit volume of the component. This can be achieved by increasing the number of active layers to 200–400 and by lowering the dielectric layer thickness below 2–3µm [6]. For capacitors, important properties such as break down voltage and DC leakage are dependent on the pore defects, layer thickness and grain size. The effective thickness of dielectric layer is expected to be several, e.g. at least 3–5, grains. Therefore BaTiO<sub>3</sub> powders with particle size in nanometer- range, a large surface area with high homogeneity are required to achieve good sinterability as well as fine grained microstructure in sintered ceramics.

## **1.6 Outline of the Report:**

A brief introduction to the topic in hand is presented, has been displayed in this chapter. The next chapter covers the available literature, and towards the end of the chapter, is discussed the objectives and motivation of our work. Chapter 3 describes in detail the experimental methods and the characterization techniques employed during the research work. Chapter 4 discusses the results obtained, and seeks to provide an explanation to those results. The conclusions of the work are summarized in the final chapter, and along with it, is provided some hints to future work.

# **Chapter 2**

## **Literature Review**

## ***2.1 Synthesis of BaTiO<sub>3</sub> nano-powders.***

Different chemical methods have been established for the preparation of cubic and/or tetragonal BaTiO<sub>3</sub> nano-powders. The wet chemical process, carried out at room temperature, dominated to the formation of 30nm para-electric cubic phase. Hence, subsequent post-heat treatment is required to get tetragonal phase in BaTiO<sub>3</sub> powder; however increase in the particle size has been observed which is beyond the objective [7-9]. On the other hand, the hydrothermal method can be employed to synthesize < 100nm tetragonal **BaTiO<sub>3</sub>** nano-powders, but process is expensive and intra-particle porosity deteriorates the property [10-11].

D. Sarkar et. al [12] proposed a new combined technique for the preparation of pure, non-porous, near spherical and high *c/a* ratio(>1.009) of 125 nm grade tetragonal BaTiO<sub>3</sub> nano-powders. The technique involved wet-chemical method for the synthesis of powder precursor (BaCO<sub>3</sub>+TiO<sub>2</sub>) and for the calcination of dry precursor rapid heating (20°C/min.) and isothermal treatment at 1100°C was done followed by quenching of the calcined powder from 1100°C to 5°C in ~5 secs. Rapid cooling resulted into increment of *c/a* ratio and also it was observed that cooling below 5°C diminishes *c/a* ratio, presumably due to temperature dependent polymorphic transformation.

Buscaglia et. al.[13] reported a low temperature(700-800°C) synthesis method for the 70-85nm BaTiO<sub>3</sub> nano-powders with BaCO<sub>3</sub>+TiO<sub>2</sub> precursors as starting materials. The particle size obtained was much lower but the *c/a* ratio was lower than that reported by D. Sarkar et. al<sup>12</sup>.

## ***2.2 Sintering of green specimen of BaTiO<sub>3</sub> nano-powders in inert/reducing atmosphere.***

The interest in sintering of green specimen of BaTiO<sub>3</sub> nano-powders in inert / reducing atmosphere, is gaining popularity with an objective to reduce the cost of MLCC'S by developing BaTiO<sub>3</sub> based composition that can be sintered in inert/reducing atmospheres so that the use of cheap base metal (e.g., nickel) electrodes could be possible. To modify the variation of capacitance with temperature, generally, additives like Bi<sub>2</sub>O<sub>3</sub>, CaZrO<sub>3</sub>, Nb<sub>2</sub>O<sub>5</sub> (Curie peak suppressors) and CuO, Li<sub>2</sub>O, PbO (fluxes) are used with BaTiO<sub>3</sub> [14-16].

However, detailed information relating to the behavior of such complex mixtures during sintering in reducing/inert atmosphere (so that nickel electrodes can be used) is lacking and hence such process warrant detailed studies.

N. Halder et. al have investigated three basic composition viz. (BaTiO<sub>3</sub>+0.65%Li<sub>2</sub>B<sub>4</sub>O<sub>7</sub>; BaTiO<sub>3</sub>+0.65%Li<sub>2</sub>B<sub>4</sub>O<sub>7</sub>+0.40%Bi<sub>2</sub>O<sub>3</sub>; BaTiO<sub>3</sub>+0.65%Li<sub>2</sub>B<sub>4</sub>O<sub>7</sub>+0.40%Bi<sub>2</sub>O<sub>3</sub>+0.40%MnO<sub>2</sub>) and studied the effect of sintering atmosphere containing different percentages of oxygen and argon on various process parameters like bulk densities, dielectric constant and phase transformations [4].

It is very difficult for complexes like BaTiO<sub>3</sub>-MgO (MnO<sub>2</sub>)-Re<sub>2</sub>O<sub>3</sub> (where Re represents the rare earth elements with smaller ionic radius) to satisfy the R characteristics ( $\Delta C/C=\pm 15\%$ ) when the temperature is above 130°C as T<sub>c</sub> =125°C for BaTiO<sub>3</sub>. This complication can be overcome by adding smaller ionic radius rare earth elements, such as Sc, Tm, Er and Yb, because they shift the Curie temperature to higher temperatures [17].



Similar investigation was done by Shen wang et. al[18] studying the effect of Yb/Mg co-doping on the electrical properties and microstructure of BaTiO<sub>3</sub> ceramics, sintered under oxidizing, reducing and annealed atmospheric conditions. The suppression of the solubility, of the acceptor ions in BaTiO<sub>3</sub> under the annealed and reducing conditions was indicated by XRD analyses.

### **2.3 Summary of Literature:**

**Following are the key points of the literature survey;**

- a) Several mechanisms can be employed for the synthesis of BaTiO<sub>3</sub> nano-powders.
- b) To get the enhanced efficiency from BaTiO<sub>3</sub> ceramics at various temperature ranges, they are required to be doped.
- c) Without sacrificing densification, lithium tetraborate (as flux) and bismuth oxide (as flux and Curie peak suppressor) doped BaTiO<sub>3</sub> based capacitor compositions, can be fired in an inert (argon) atmosphere.
- d) Addition of a small amount of MnO<sub>2</sub> in the compositions, can suppress the increase of both the dissipation factor and dielectric constant of the samples containing Bi<sub>2</sub>O<sub>3</sub> when sintered in inert atmosphere.
- e) In case of Yb/Mg co-doping there is suppression of solubilities, of the acceptor ions when fired in reducing atmospheres.
- f) The formation of n-type electronic defects in case of bismuth containing composition without MnO<sub>2</sub> leads to a dramatic increase in both the DF and K values when firing is done in atmospheres containing < 25% O<sub>2</sub>, the annihilation of the defects and inhibition of the dramatic increase of both the DF and K values of bismuth containing samples can be achieved by doping with Mn<sup>2+</sup> ions which is well-known acceptor.

## 2.4 Objective of present studies:

Nano-structured BaTiO<sub>3</sub> has significant importance for the preparation of MLCC, which is preferably sintered at Ar and/or N<sub>2</sub> atmosphere during fabrication. Hence, systematic synthesis of BaTiO<sub>3</sub> nano-powders and their sintering study at different atmosphere is worthwhile. In this backdrop, the following objective needs to explore;

- a) Synthesis of BaTiO<sub>3</sub> nano-powders through combined wet chemical and calcination technique.
- b) Sintering study at different atmosphere (Air, Ar and N<sub>2</sub>) with different heating schedule.
- c) Microstructure Study of nano-structured BaTiO<sub>3</sub>.

# **Chapter 3**

**Experimental**

**Work**

### 3.1 Synthesis of Barium Titanate ( $BaTiO_3$ )

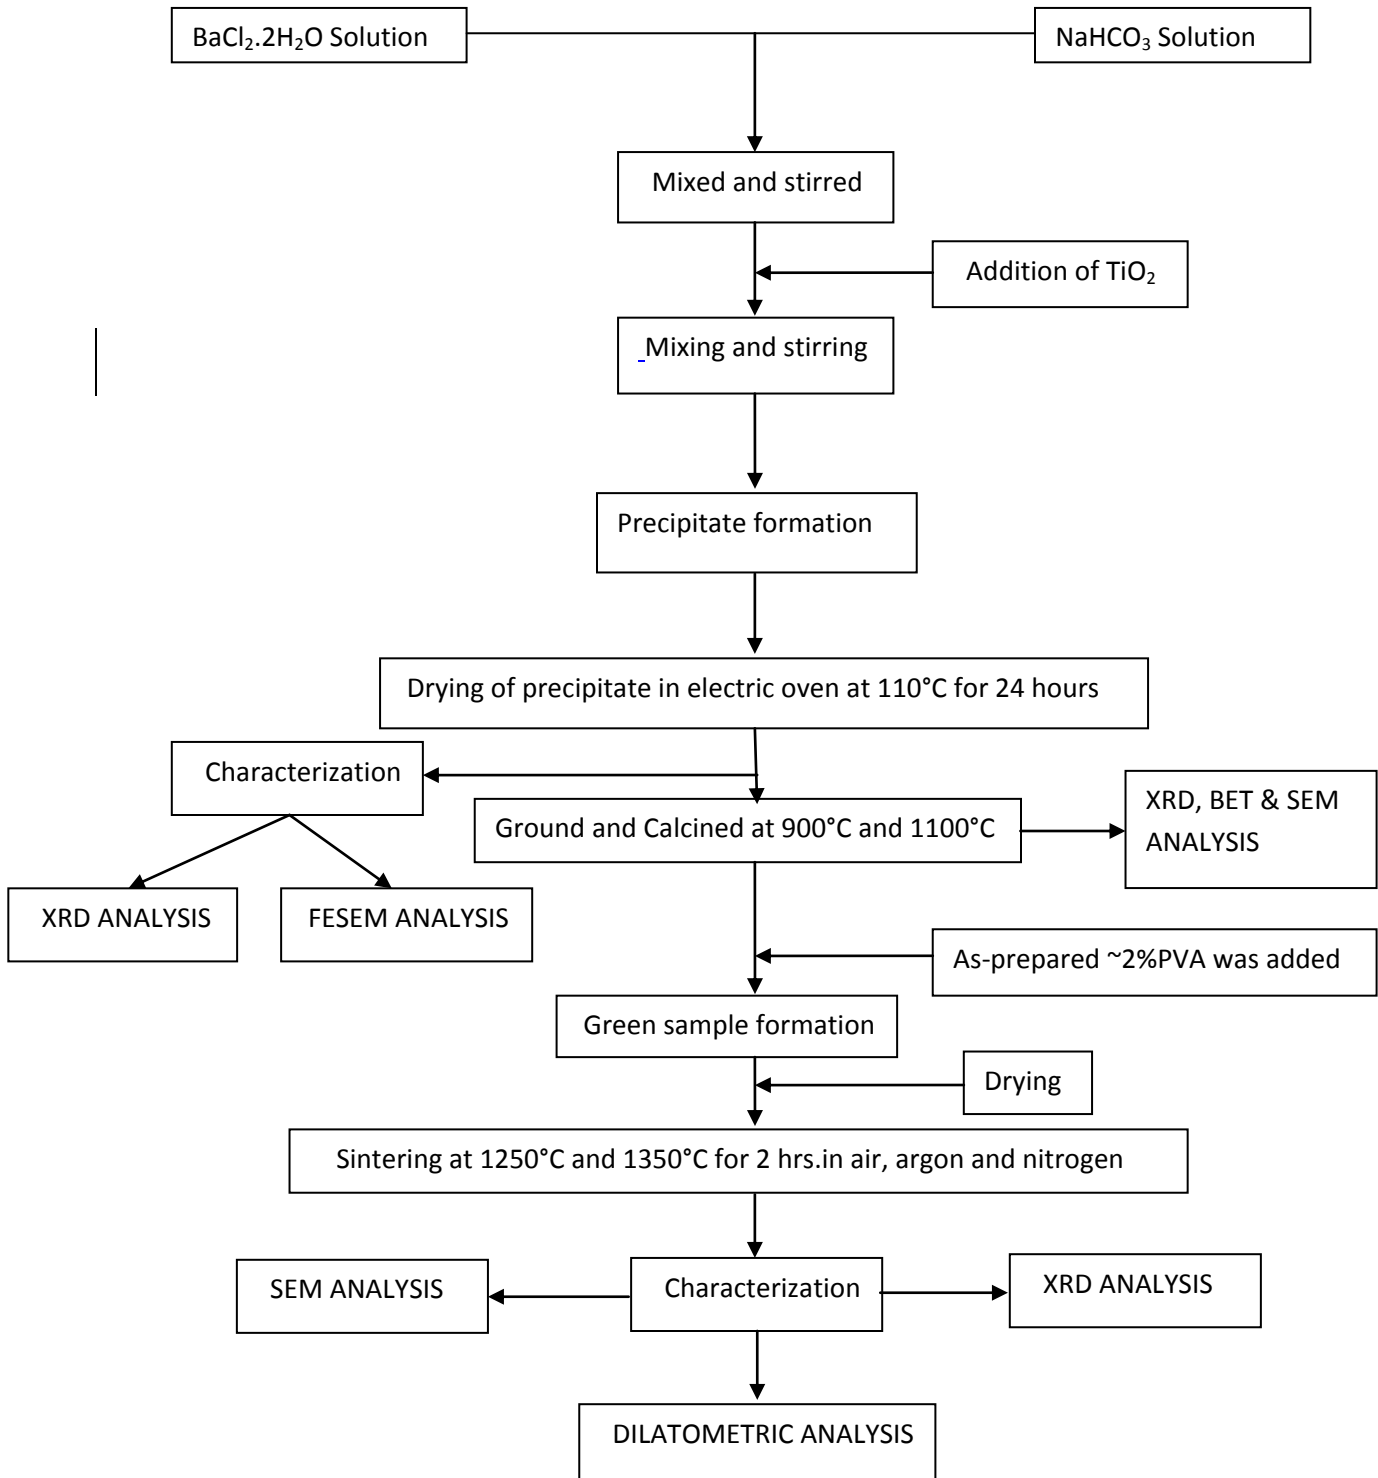


Fig. 3.1 Flow Diagram of the Procedure


### ***3.1.1 Powder Preparation:***

Solution of required amount of Barium Chloride dihydrate crystal ( $\text{BaCl}_2 \cdot 2\text{H}_2\text{O}$ ) and that of Sodium Bicarbonate ( $\text{NaHCO}_3$ ), in distilled water, were prepared in separate beakers, by using magnetic stirrer till the solution became transparent. After that  $\text{NaHCO}_3$  solution was added drop wise and slowly to the  $\text{BaCl}_2 \cdot 2\text{H}_2\text{O}$  solution, and required amount of Titanium Dioxide ( $\text{TiO}_2$ ) was added to the mix and stirred for 45mins. Then the beaker covered with a petri-dish, was left undisturbed for 24hours, at room temperature for precipitation to occur.


The precipitate thus formed was subsequently washed several times with distilled water and the drained water was tested for the presence of NaCl (by product of the reaction), using aqueous solution of Silver Nitrate ( $\text{AgNO}_3$ ).

So precipitate was washed till the whitening of  $\text{AgNO}_3$  solution stops. Finally, the precipitate was washed with 2-Propanol, through the wattman (41) filter paper and then kept in oven at  $110^\circ\text{C}$  for 24hours, for drying. The sample was then scrapped out from the petri-dish and weighed. The dried samples were ground and calcined at  $900^\circ\text{C}$  and  $1100^\circ\text{C}$  for 2hours.

➤ *Powder calcinations profile:*

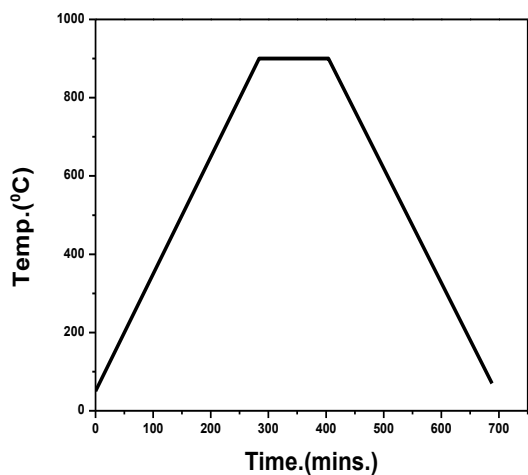

(A)

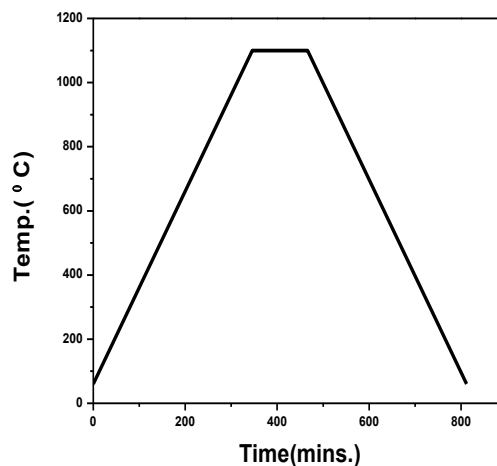

(B)

Fig.3.2 For calcination at (A)900°C and (B)1100°C for 2 hours.

### **3.1.2 Powder Characterization:**

X-ray diffraction patterns were obtained using X-ray diffractometer Phillips PANalytical (Model: PW 1830 diffractometer, Netherland) with Cu K $\alpha$  radiation. The pattern was obtained in the  $2\theta$  range from  $20^\circ$ - $90^\circ$  and the scan time range was 15mins to 58mins. Nitrogen physisorption was used to determine the surface area of the materials at the temperature of liquid nitrogen ( $-196^\circ\text{C}$ ) in a (Quantachrome, USA); prior to analysis, the samples were degasified for 3 hours at  $300^\circ\text{C}$ . To study the surface morphology of the samples, the powders were subjected to Scanning Electron Microscopy (SEM) and Field Emission Scanning Electron Microscopy (FESEM).

### ***3.2 Preparation of binder and green specimens:***

Initially, during pressing of powder (with force 4.5 Ton and dwell time 90 secs.) without any binder added, at the time of ejection, pellets started disintegrating at the edges. So, PVA (poly vinyl alcohol) was used for the binding purpose to provide green body strength. Prior to use of the PVA binder, 1.906gms of PVA granules was added slowly to the water kept on magnetic stirrer. Simultaneous, heating and stirring was carried out for around 45 mins. Then, with the formation of a clear solution, the stirring and heating was stopped. The solution was then stored in a bottle for further application.

### ***3.3 Sintering behavior of green compacts***

Powder calcined at 1100°C was mixed with small amount of previously prepared PVA solution. Then the mix was left for drying. Powder was then divided into 3 parts and pressed in a rectangular die (with force of 4.5 Ton and dwell time 90 secs.).

#### ***3.3.1 Characterization of Sintered Specimens:***

The dilatometric study was carried out with the help of NETZSCH DIL 402C instrument. The samples were analysed in the presence of 100% air, 100% nitrogen and 100% argon environments, with a heating rate of 10°C/min. in the temperature range of 30°C to 1250°C and 30°C to 1350°C after that keeping the samples in isothermal condition for 2 hours. The specimen did not stick with alumina holder.

X-ray diffraction patterns were obtained using X-ray diffractometer Phillips PANalytical (Model: PW 1830 diffractometer, Netherland) with Cu K $\alpha$  radiation. The pattern was obtained in the 2 $\theta$  range from 20°-90° and the scan time was 58mins. To study the surface morphology of the samples, the powders were subjected to Scanning Electron Microscopy.

# **Chapter 4**

## **Results And Discussions**



This chapter illustrates the relevant research data on BaTiO<sub>3</sub> nano-powders and their sintering characterization in different atmosphere.

#### 4.1 Phase analysis of synthesized nano-powders of BaTiO<sub>3</sub>:

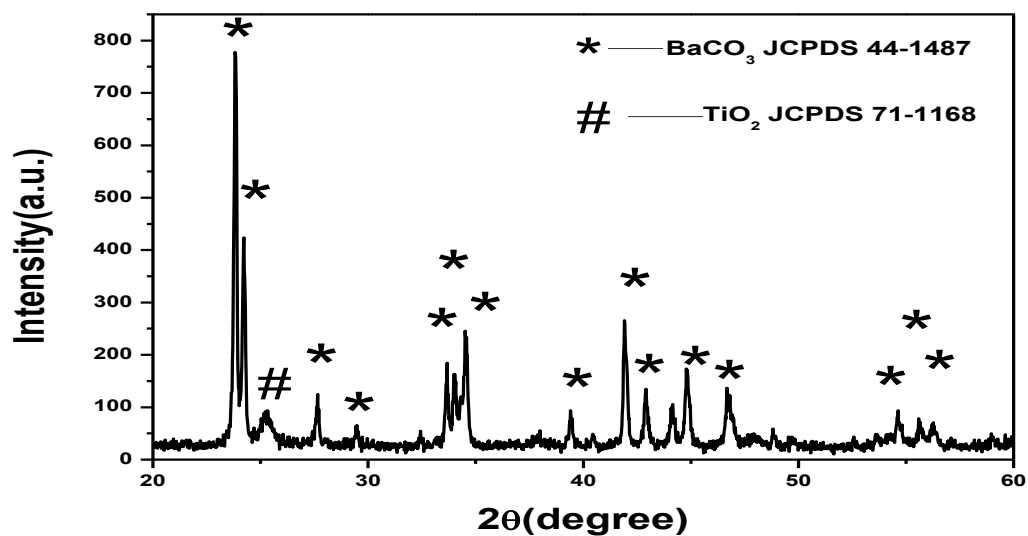


Fig.4.1 XRD pattern of BaCO<sub>3</sub> and TiO<sub>2</sub> precursor powder mix.

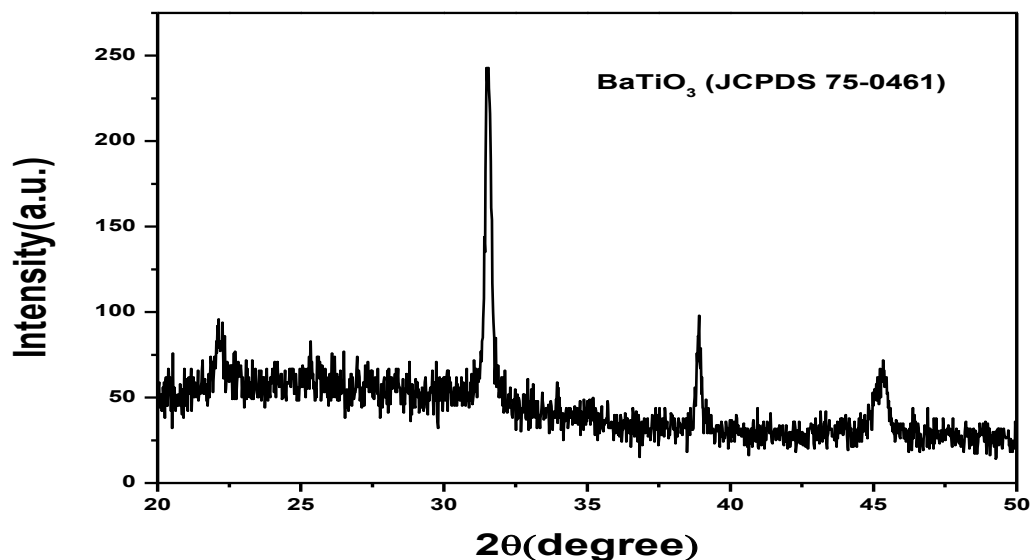


Fig.4.2 XRD pattern of BaTiO<sub>3</sub> nano-powder calcined at 900°C for 2 hours.

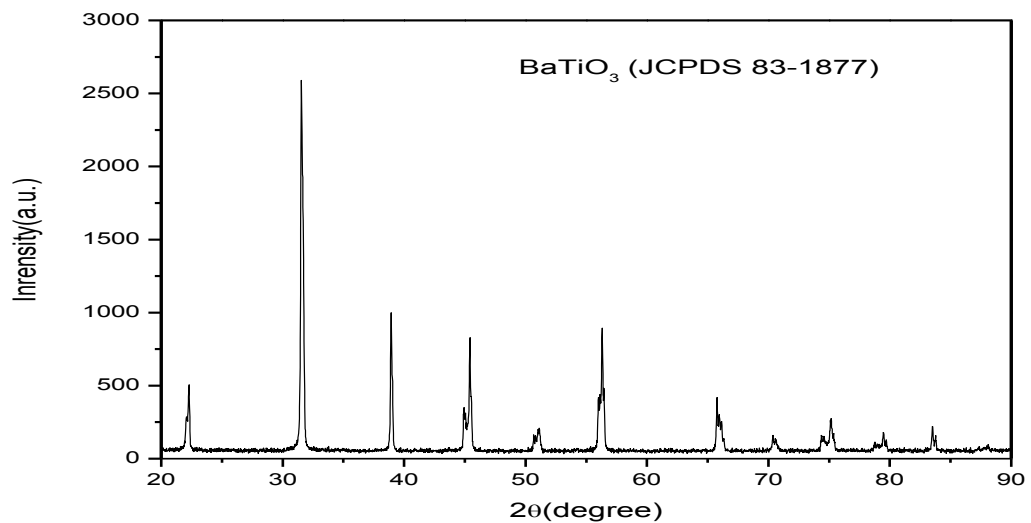


Fig.4.3 XRD pattern of BaTiO<sub>3</sub> nano-powder calcined at 1100°C for 2hours.

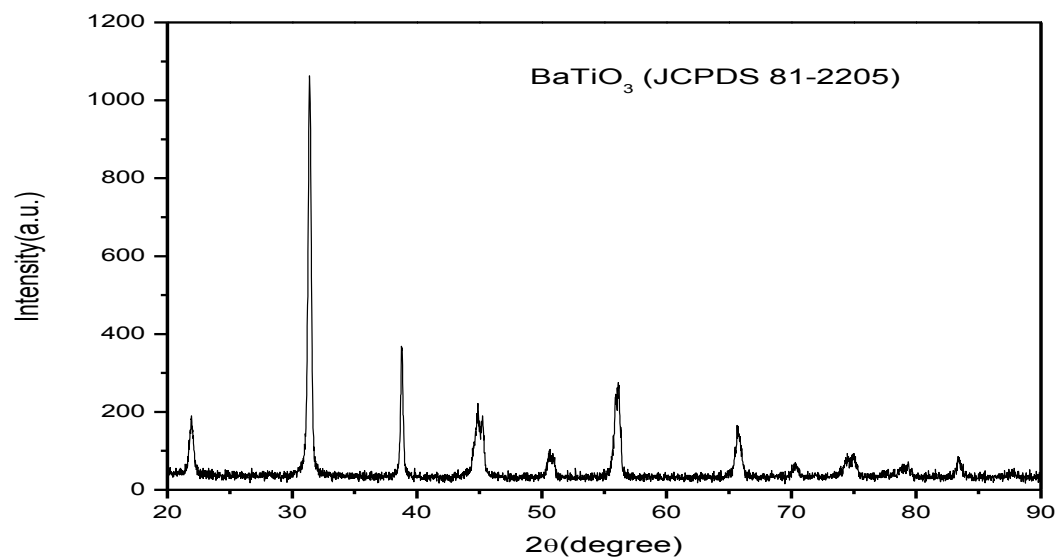


Fig.4.4 XRD pattern of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2hours in air.

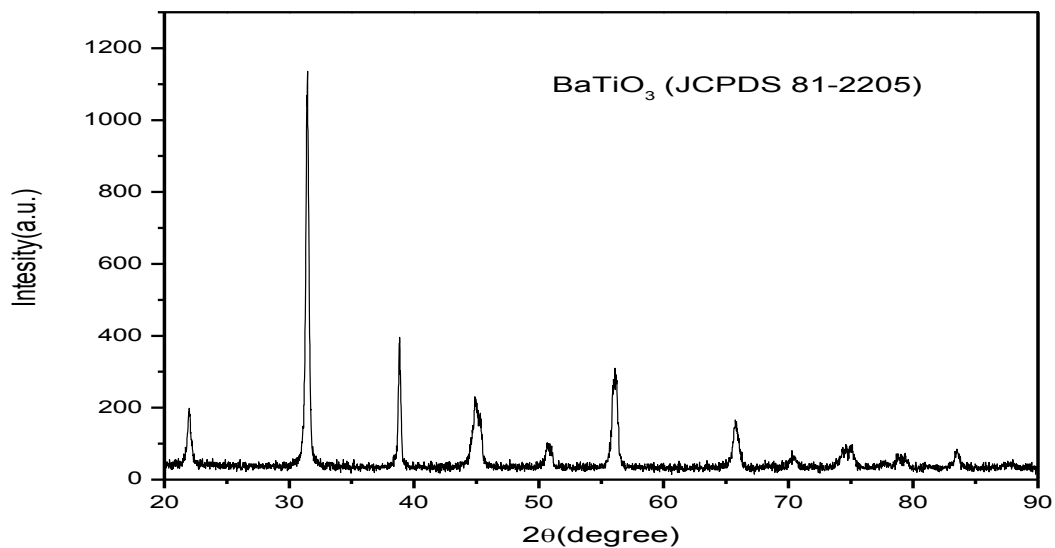


Fig.4.5 XRD pattern of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2 hours in argon.

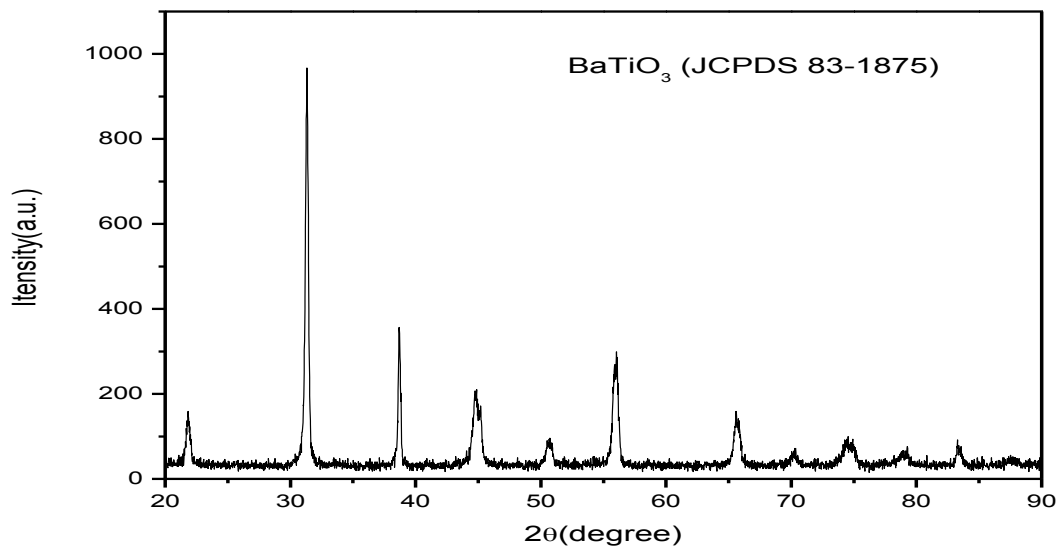


Fig.4.6 XRD pattern of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2 hours in nitrogen.



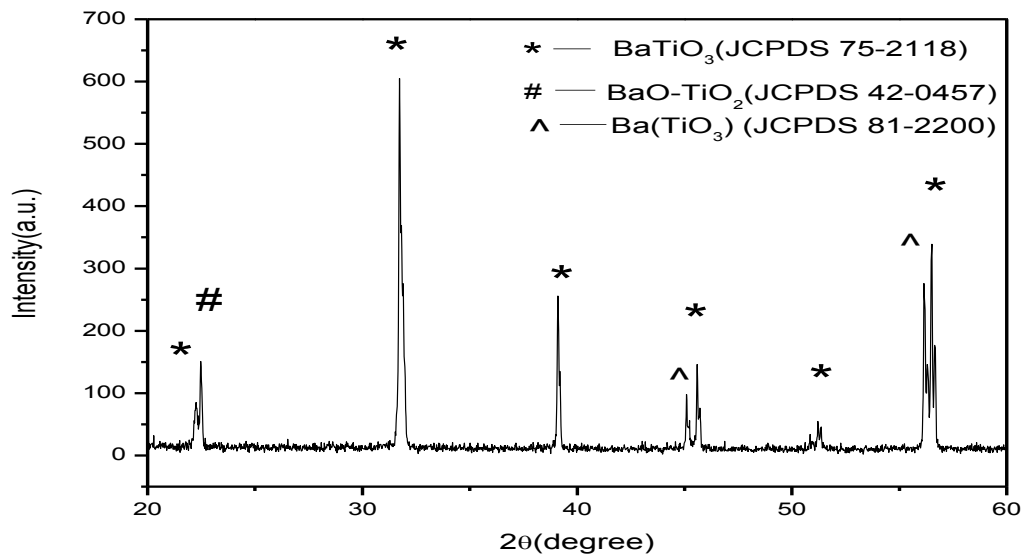


Fig.4.7 XRD pattern of BaTiO<sub>3</sub> nano-powder sintered at 1350°C for 2 hours in nitrogen.

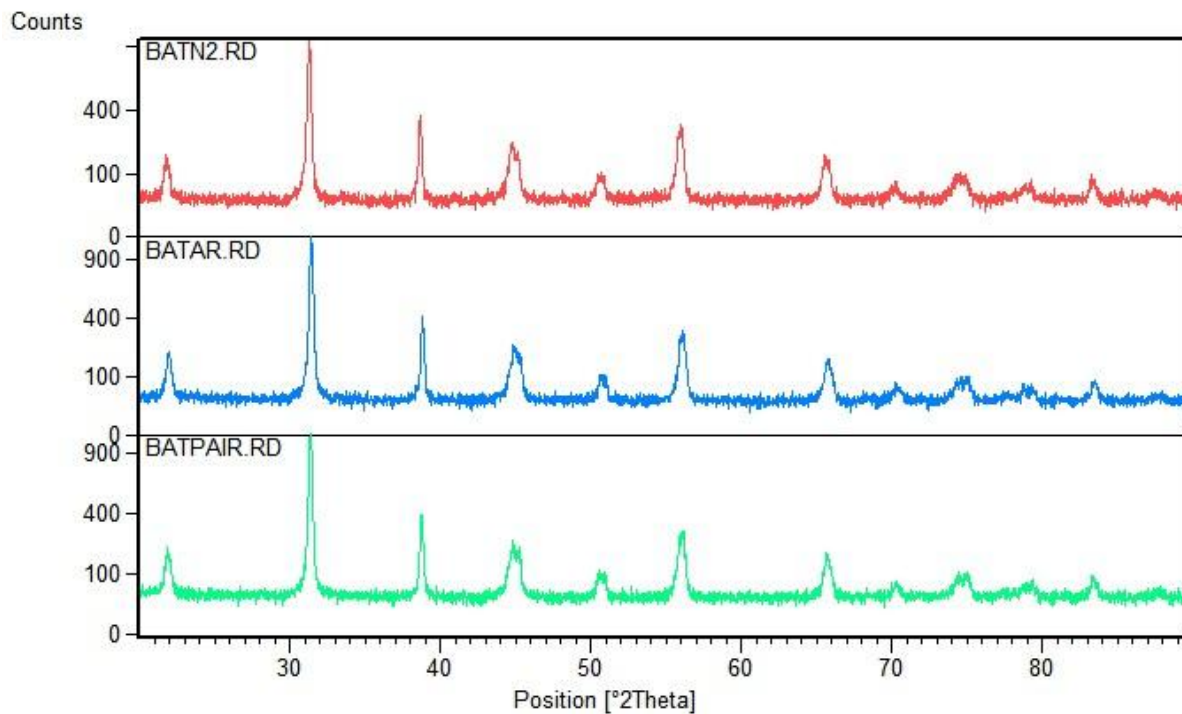


(A)

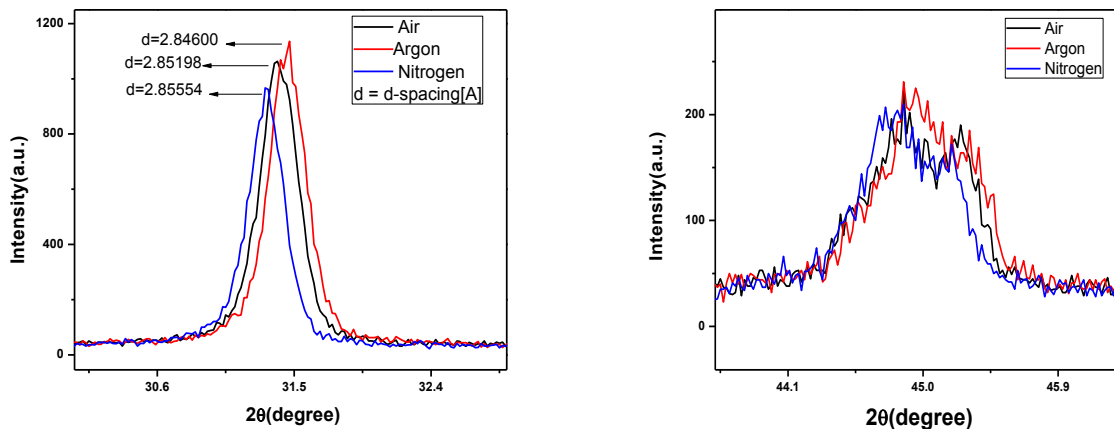

(B)

Fig.4.8 (A) and (B) XRD pattern for sintered BaTiO<sub>3</sub> in different atmospheres at 1250°C.

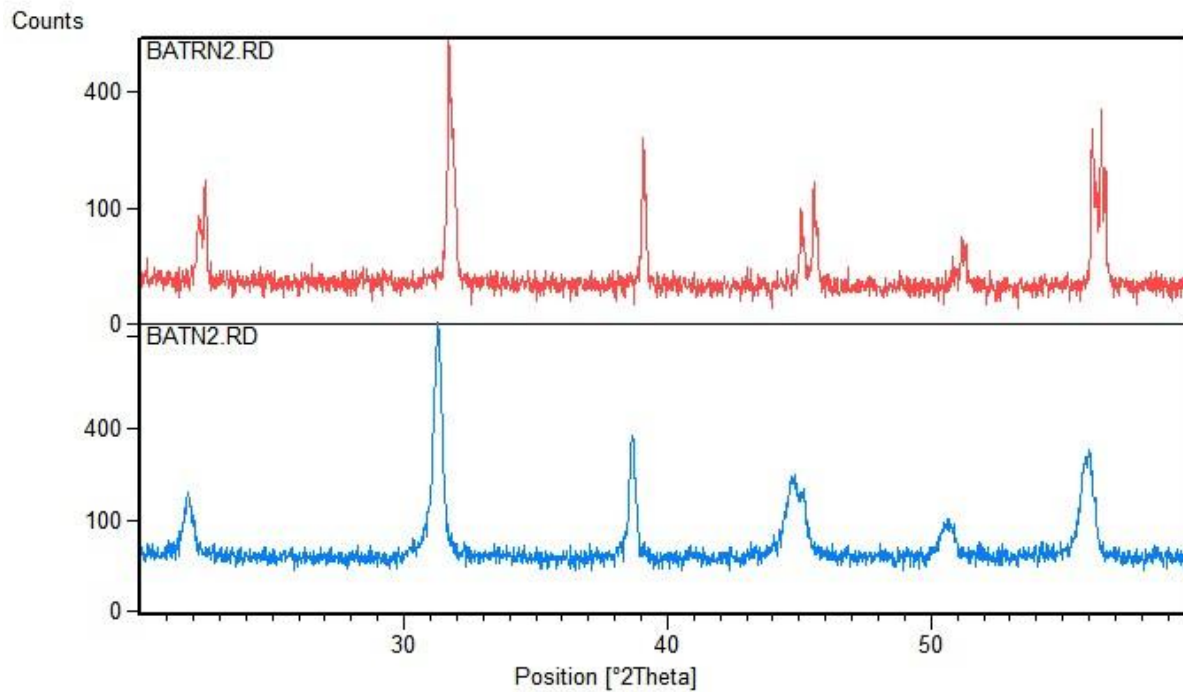

(A)

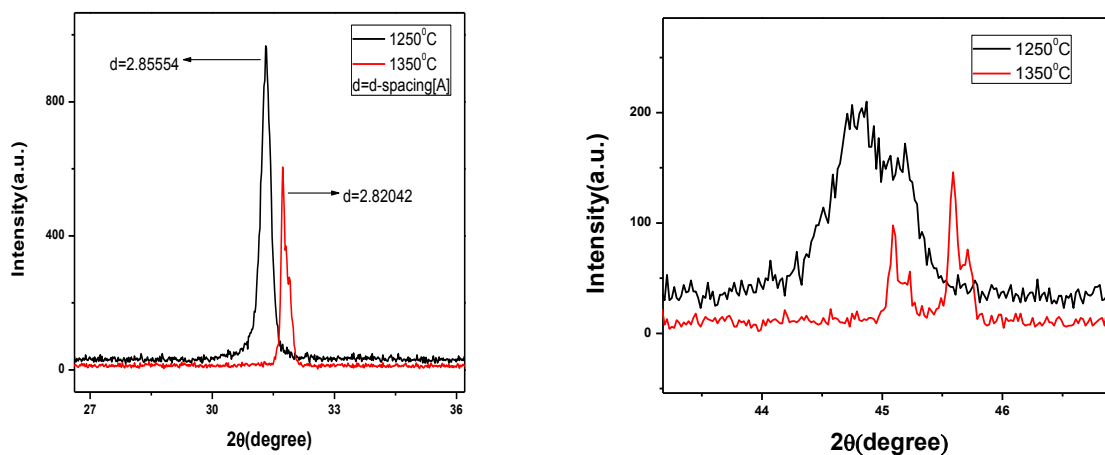


Fig.4.9 (A) and (B )XRD pattern for sintered BaTiO<sub>3</sub> in nitrogen atmosphere at 1250°C and 1350°C

(B)

Table 4.1

Sample	BAT1100 (Powder)	BATPAIR (1250°C)	BATAR (1250°C)	BATN2 (1250°C)	BATRN2 (1350°C)
Crystallite size(nm)	82.6	61.12	40.77	45.86	91.8
Crystal structure	tetragonal	tetragonal	tetragonal	tetragonal	tetragonal

Crystallite size and Crystal structure from XRD analysis

#### 4.2 Relative Density:

Table 4.2

Temp. \ Environ.	Air	Argon	Nitrogen
1250°C	0.925	0.887	0.92
1350°C	0.929	0.892	0.927

Relative density of specimen sintered in air, argon and nitrogen at 1250°C and 1350°C.

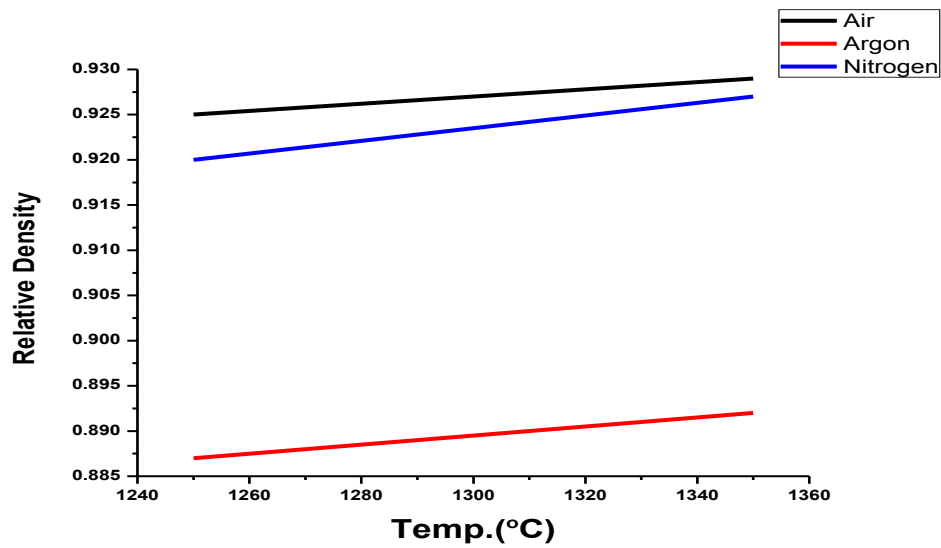


Fig.4.10 Relative density Vs Temperature curve in air, argon and nitrogen.

### 4.3 Surface Area

Using Brunauer-Emmett-Teller (BET), the surface area of the sample was determined. Equivalent particle size can be determined from the measured surface area using the equation:

$$D_{BET} = \frac{6000}{\rho \times S_{BET}}$$

where,

- I.  $D_{BET}$  (nm) is the average particle size
- II.  $S_{BET}$  is the surface area expressed in  $\text{m}^2/\text{g}$  and
- III.  $\rho$  is the theoretical density of  $\text{BaTiO}_3$  expressed in  $\text{g}/\text{cc}$ .

It was found that for  $\text{BaTiO}_3$  nano-powder calcined at  $900^\circ\text{C}$  for 2hours,  $S_{BET}$  value equals to  $7.295 \text{ m}^2/\text{g}$ , so  $D_{BET}$  calculated equals to 137nm.

While for  $\text{BaTiO}_3$  nano-powder calcined at  $1100^\circ\text{C}$  for 2hours,  $S_{BET}$  value equals to  $3.284 \text{ m}^2/\text{g}$ , so  $D_{BET}$  calculated equals to 303nm.



#### *4.4 Surface morphology analysis:*

##### *SEM Analysis:*

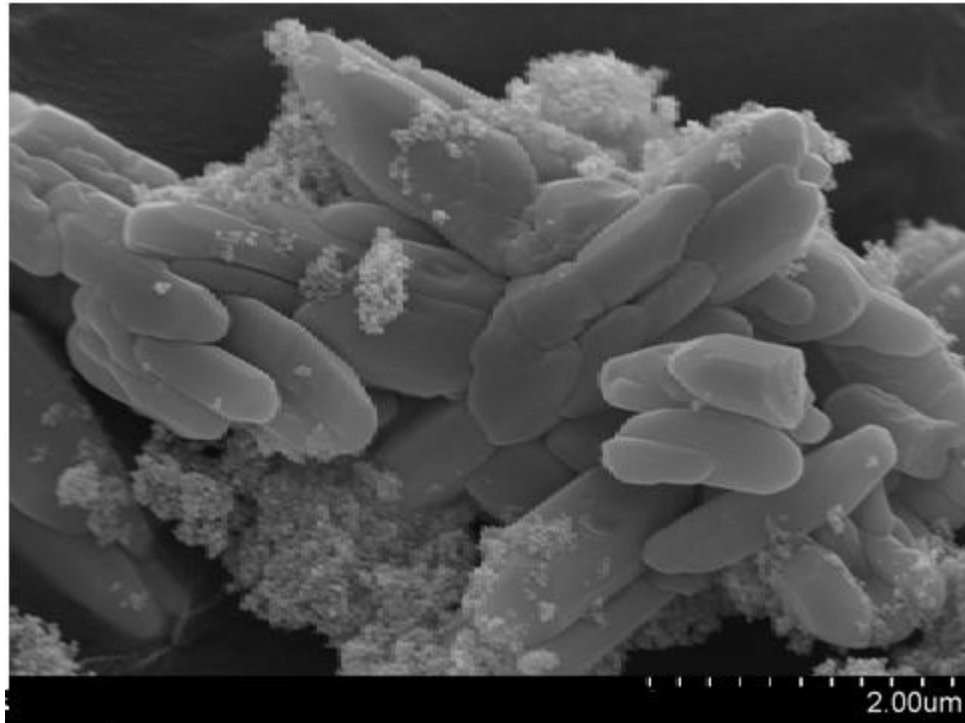


Fig.4.11 FESEM image of BaCO<sub>3</sub> and TiO<sub>2</sub> mix precursors

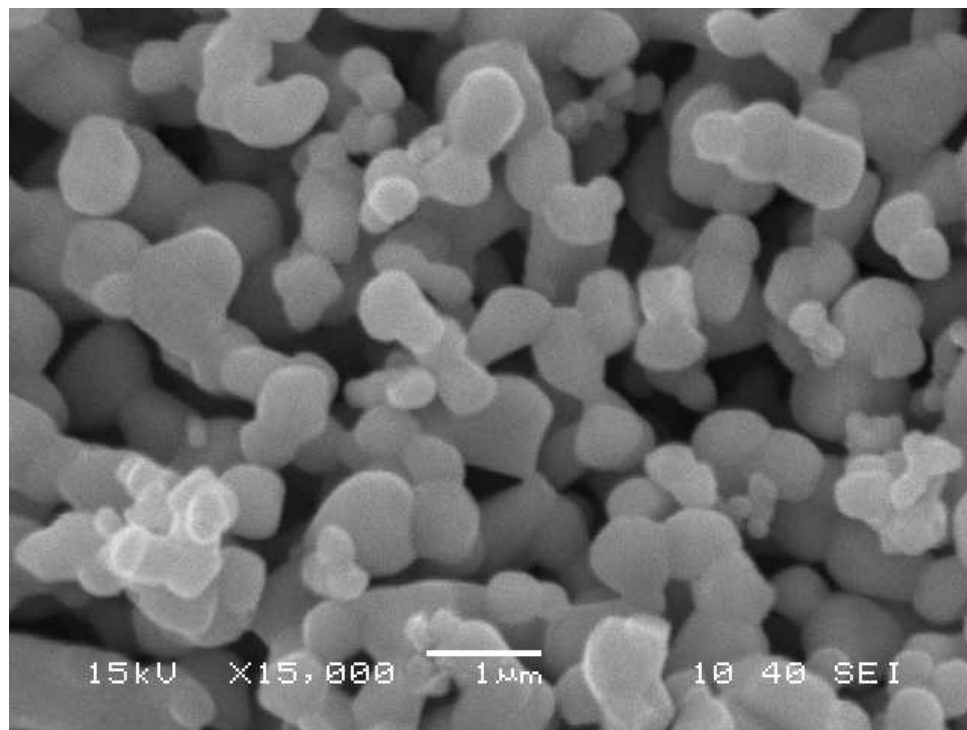


Fig.4.12 BaTiO<sub>3</sub> nano-powder calcined at 1100°C for 2hours.

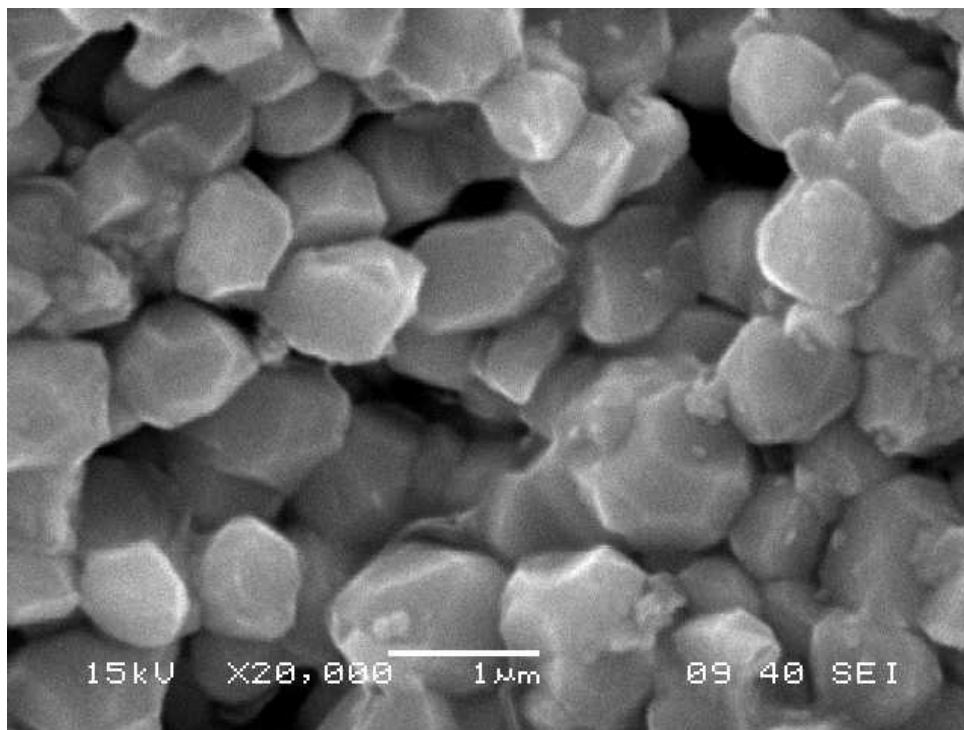


Fig.4.13 Green specimen of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2hours in air.

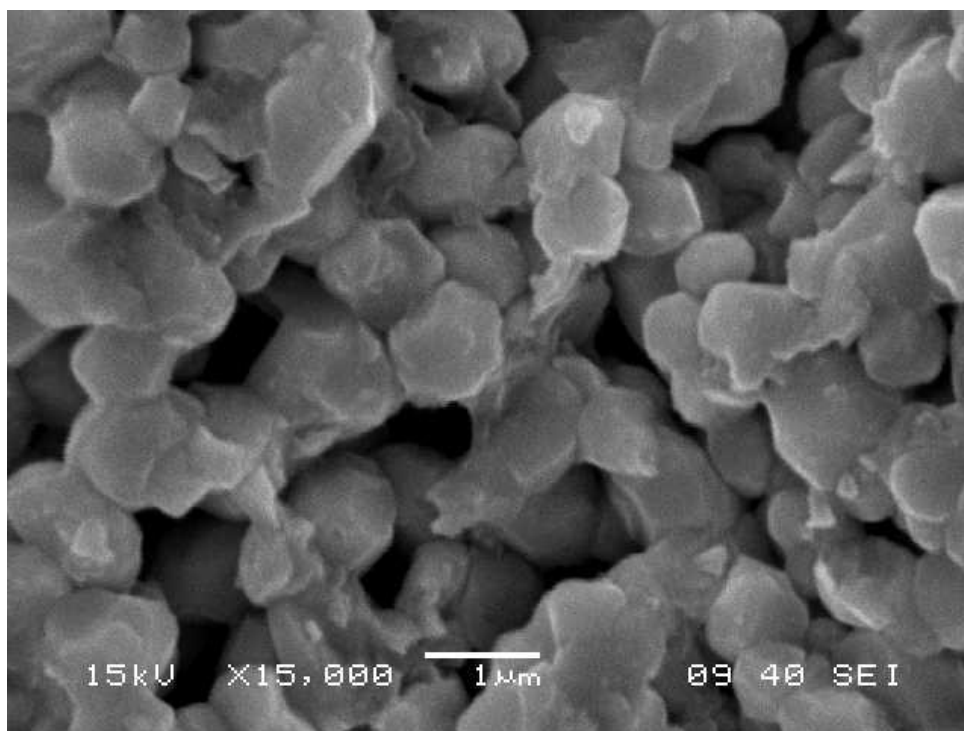


Fig.4.14 Green specimen of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2hours in nitrogen.

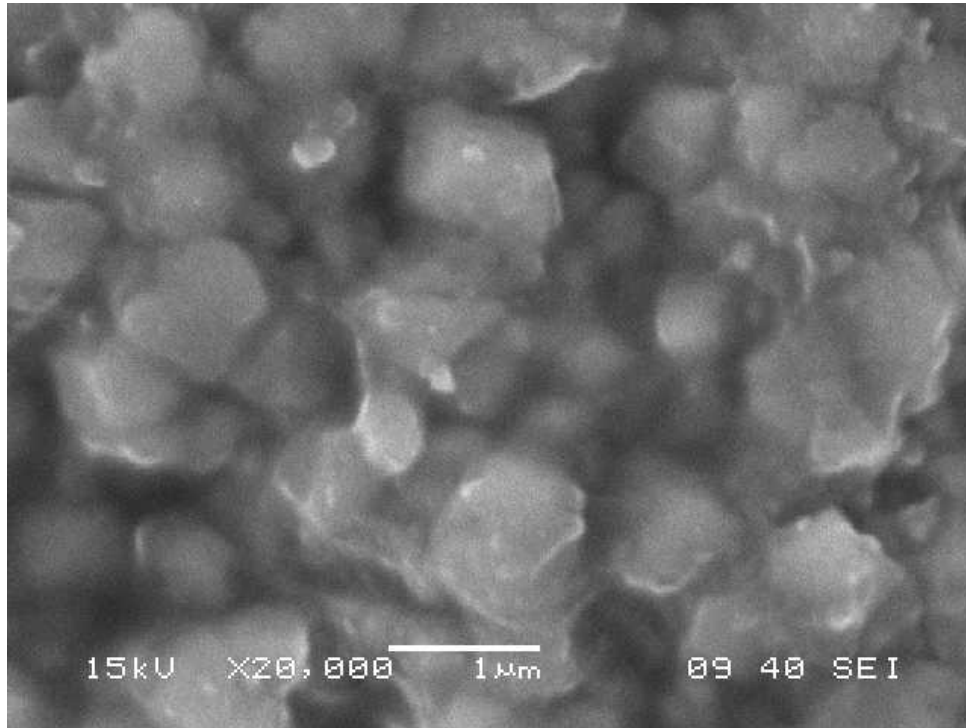


Fig.4.15 Green specimen of BaTiO<sub>3</sub> nano-powder sintered at 1250°C for 2hours in argon.

#### 4.5 Dilatometric Analysis of green specimen of BaTiO<sub>3</sub> nano-powder:

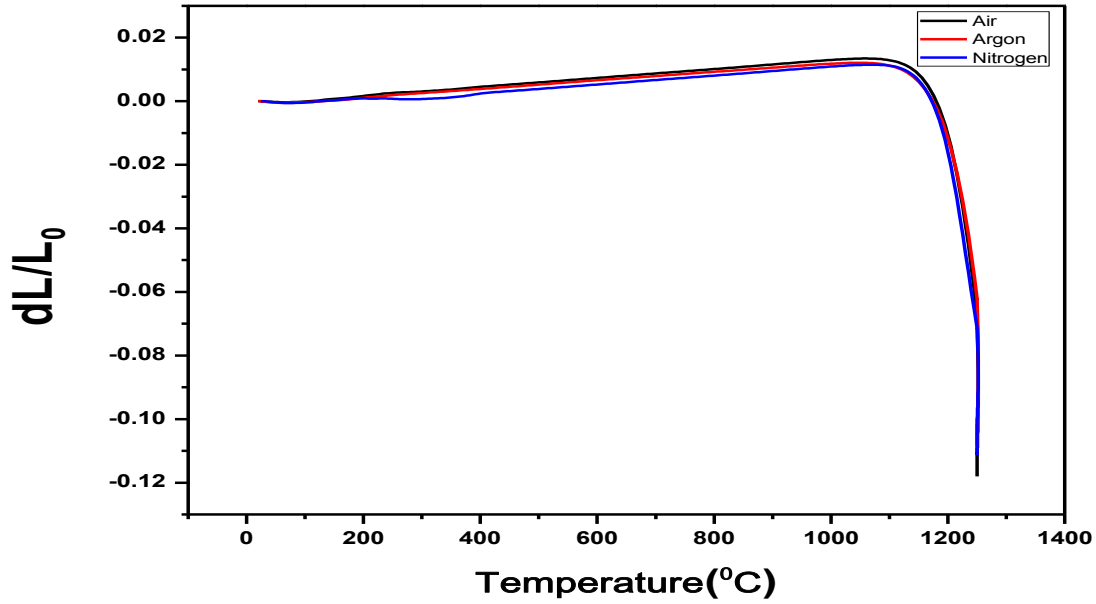


Fig. 4.16

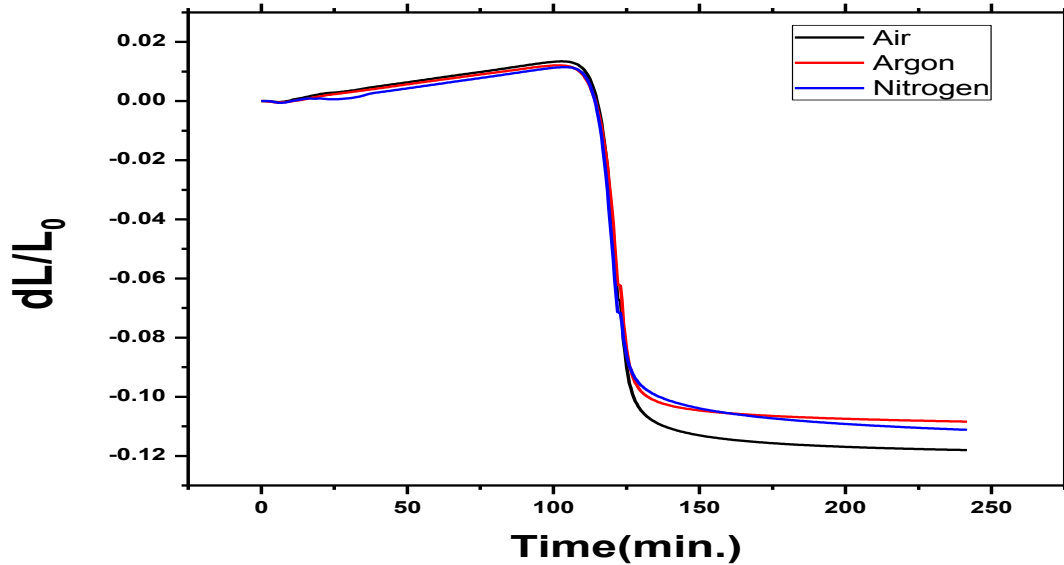


Fig. 4.17

Dilatometric curve for green specimen of BaTiO<sub>3</sub> nano-powder sintered at 1250° for 2hours in air, argon and nitrogen.

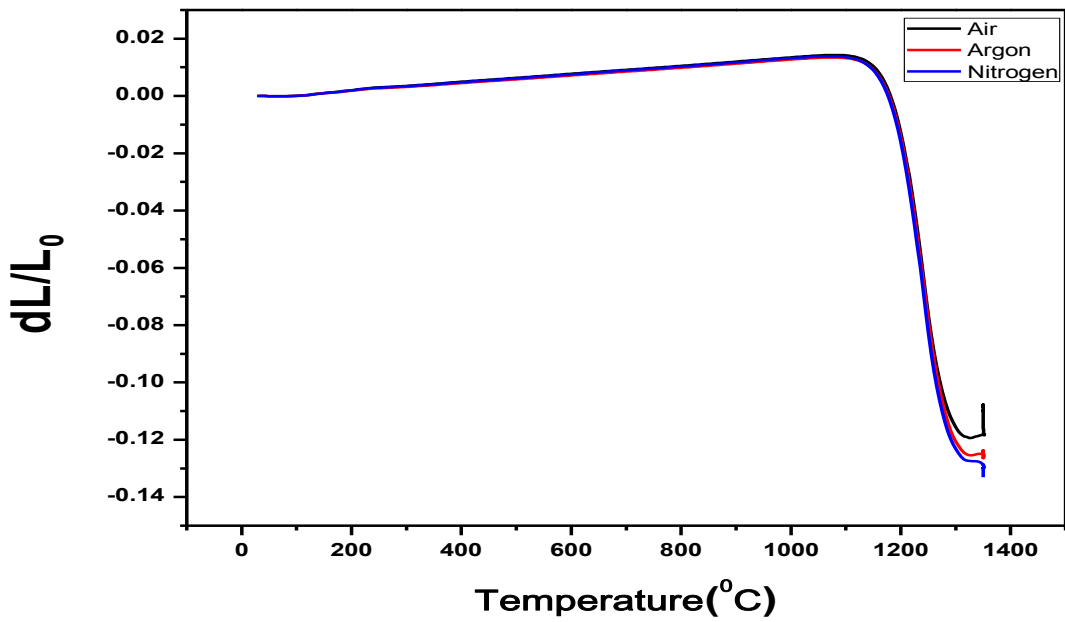


Fig. 4.18

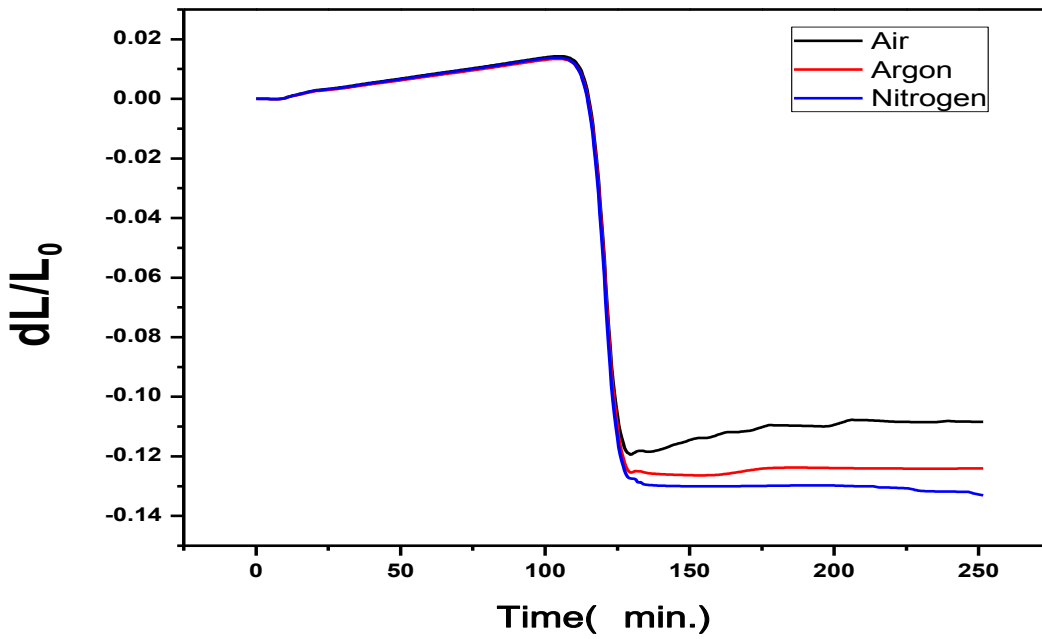


Fig. 4.19

Dilatometric curve for green specimen of  $BaTiO_3$  nano-powder sintered at  $1350^\circ$  for 2hours in air, argon and nitrogen.

# **Chapter 5**

## **Conclusions**

## Conclusions:

1. Low temperature 950°C develops 130nm BaTiO<sub>3</sub> nanoparticles with having small amount of BaCO<sub>3</sub> impurities and low c/a ratio.
2. Particle increases up to 300nm with increasing temperature up to 1100°C
3. Pure, high crystalline, high c/a ratio was obtained at 1100°C temperature.
4. Relative density of consolidate BaTiO<sub>3</sub> nanopowders in air, nitrogen and argon were densified up to 92.5%, 91.8% and 88.5%, respectively.
5. Lattice parameter and d-spacing of BaTiO<sub>3</sub> are changing with sintering atmosphere.

## REFERENCES

- [1] Wenk, Hans-Rudolf; Bulakh, Andrei (2004). Minerals: Their Constitution and Origin. New York, NY: Cambridge University Press. p. 413. ISBN 978-0521529587.
- [2] Carter C. Barry, Norton M. Grant, Ceramic materials – Science and Engineering, Springer, 2007, xxii, 716p., 848 illus.
- [3] W. Lu, M. Quilitz, H. Schmidt, “Nanoscaled BaTiO<sub>3</sub> powders with a large surface area synthesized by precipitation from aqueous solutions: Preparation, characterization and sintering”, Journal of the European Ceramic Society 27 (2007) 3149–3159.
- [4] N. Halder, D. Chattopadhyay, A. Das Sharma, D. Saha, A. Sen, H.S. Maiti, “Effect of sintering atmosphere on the dielectric properties of barium titanate based capacitors”, Materials Research Bulletin 36 (2001) 905–913.
- [5] Wadhawan, Vinod K. (2000). “Introduction to ferroic materials”. CRC Press. p. 10. ISBN 9789056992866.
- [6] Y. Jung, E. Na, U. Paik, J. Lee, J. Kim, Mater. Res. Bull. 37 (2002) 1633.
- [7] J. Bera, D. Sarkar, “Formation of BaTiO<sub>3</sub> from Barium Oxalate and TiO<sub>2</sub>”, J. Electroceram., 11[3] 131-7(2003).
- [8] D. Sarkar, M.C. Chu, S.J. Cho, K.Y. Yoon, “BaTiO<sub>3</sub> nano-particles and Method of preparing the same”, Korean Patent No.-10-2007-0119498, 2007.
- [9] X. Wang, J. Zhuang, Q. Peng, and Y. Li, “A General Strategy for Nanocrystal Synthesis”, Nature, 437, 121-4 (2005).
- [10] W.J. Dawson, “Hydrothermal Synthesis of Advanced Ceramic Powders”, Am. Ceram. Soc. Bull., 67, 1673-8 (1988).
- [11] D. Hennings, C. Metzmaier, and B.S. Schreinemacher, “Defect Chemistry and Microstructure of Hydrothermal Barium Titanate”, J. Am. Ceram. Soc., 84[1] 179-82 (2001).
- [12] D. Sarkar, “Synthesis and Properties of BaTiO<sub>3</sub> Nanopowders”, J. Am. Ceram. Soc., 94[1] 106-110(2011)
- [13] M.T. Buscaglia, M. Bassoli, V. Buscaglia, R. Vormberg, “Solid State Synthesis of nanocrystalline BaTiO<sub>3</sub>, Reaction Kinetics and Powder Properties”, J. Am. Ceram. Soc., 91, 2862-9 (2008).



- [14] M. Kahan, D.P. Burks, I. Burn, W.A. Schulze, in: L.M. Levinson (Ed.), "Electronic Ceramics—Properties, Devices and Applications", Marcel Dekker, New York, 1988,p. 2027
- [15] G. Goodman, in: R.C. Buchanan (Ed.), "Ceramic Materials for Electronics—Processing, Properties and Applications", Marcel Dekker, New York, 1986, p. 131.
- [16] I. Burn, J. Mat. Sc. 1398 (1982) 17.
- [17]Venigall, S., "Advanced materials and powders digest-barium titanate.", Am.Ceram. Soc. Bull., 2001, 80,63-64.
- [18] Sheng Wang\*, Shuren Zhang, Xiaohua Zhou, Bo Li, Zhu Chen, "Effect of sintering atmospheres on the microstructure and dielectric properties of Yb/Mg co-doped BaTiO<sub>3</sub> ceramics", Materials Letters 59 (2005) 2457 – 2460