

Title: "New trends on photoelectrocatalysis (PEC): nanomaterials, wastewater treatment and hydrogen generation"

Authors: Pilar Fernandez-Ibanez*, Stuart McMichael, Adriana Rioja Cabanillas, Salem Alkharabsheh, Alvaro Tolosana Moranchel, John Anthony Byrne.

Affiliation: Nanotechnology and Integrated BioEngineering Centre, School of Engineering, Ulster University, Northern Ireland, BT37 0QB, United Kingdom

*** Corresponding author:**

Pilar Fernandez-Ibanez

Email: p.fernandez@ulster.ac.uk

Tel: +44(0)2890368979

NIBEC - School of Engineering

Ulster University

BT37 0QB

United Kingdom

Abstract

The need for novel water treatment technologies has been recently recognised as concerning contaminants (organics and pathogens) are resilient to standard technologies. Advanced oxidation processes degrade organics and inactivate microorganisms via generated reactive oxygen species (ROS). Among them, heterogeneous photocatalysis may have reduced efficiency due to, fast electron-hole pair recombination in the photoexcited semiconductor and reduced effective surface area of immobilised photocatalysts. To overcome these, the process can be electrically assisted by using an external bias, an electrically conductive support for the photocatalyst connected to a counter electrode, this is known as photoelectrocatalysis (PEC). Compared to photocatalysis, PEC increases the efficiency of the generation of ROS due to the prevention of charge recombination between photogenerated electron-hole pairs thanks the electrical bias applied. This review presents recent trends, challenges, nanomaterials and different water applications of PEC (degradation of organic pollutants, disinfection and generation of hydrogen from wastewater).

Keywords: nanomaterials, organic pollutants, wastewater, disinfection, hydrogen generation

1. Introduction

Standard wastewater treatment technologies (typically bio-treatment) are effective to remove suspended matter, degrade most of the organic pollution and reduce partially the microbial contamination; nevertheless, they fail to remove some recalcitrant contaminants, to abate organic compounds concentration in the range between micrograms and nanograms per litre (micropollutants) which include pharmaceuticals and personal care products frequently found in urban wastewaters. These technologies also require the use of a post-treatment step for disinfection (tertiary) to reduce the presence of microbial contamination up to levels of acceptability for different restricted re-use, including aquifers recharge, environmental and recreational uses, agricultural irrigation and drinking water [1].

Advanced oxidation processes (AOPs) – known as those treatment technologies aimed at degrading and mineralizing recalcitrant organic matter from wastewater through reaction with hydroxyl radical ($\bullet\text{OH}$) – face these challenges has attracted great interest in the last decades. Heterogeneous photocatalysis utilises UV and visible light (solar or lamps) and oxygen from the air to inactivate microorganisms and degrade organic pollutants in water. If solar energy is used, then it is a clean water technology. Its main limitation is the fast charge carriers recombination in the photocatalyst, after photo-activation, reducing its efficiency.

Photoelectrocatalysis (PEC) consists of the immobilization of a photocatalyst on an electrode that will act as a photoanode or photocathode. In the case of a photoanode, when the energy of the incident radiation is equal or higher than the band gap energy ($h\nu \geq E_{\text{bg}}$) an electron is promoted from the valence band to the conduction band of the semiconductor, giving rise to the generation of electron-hole pairs (e^-h^+). An external anode potential or cell potential or a constant current density (j) is applied by using a power supply. This allows controlling the Fermi Level of a semiconductor, and therefore band bending, leading to an efficient separation of e^-h^+ pairs and reducing their recombination. While h^+ migrate to the semiconductor surface to oxidize water and produce hydroxyl radicals or to directly oxidize the organic compound, photogenerated electrons are transferred to the counter electrode through an external circuit [2]. Compared to photocatalysis, PEC increases the efficiency of the process and

yields higher production rates of holes [3], and other ROS, due to the prevention of charge recombination. Furthermore, in comparison to slurry photocatalytic systems, in PEC processes the photocatalyst is immobilized on a substrate, so no separations units are necessary to recover the photocatalyst [4]. One last advantage, when inactivating bacteria, which are negatively charged, they shift towards the positively charged photoanode, so mass transfer rates of bacteria are enhanced by electromigration [5]. There are several important reactions that can take place during PEC and are stated in Table 1.

Table 1 – Reduction and oxidation reactions and potentials [6].

Reaction	Potential/ V vs. NHE at pH 7	Application
$\text{OH}^- + \text{h}^+ \rightarrow \bullet\text{OH}$	+2.29	ROS generation
$\text{H}_2\text{O} + 4\text{h}^+ \rightarrow \text{O}_2 + 2\text{H}^+$	+0.82	Oxygen evolution
$\text{O}_2 + 2\text{e}^- + 2\text{H}^+ \rightarrow \text{H}_2\text{O}_2$	+0.281	ROS generation
$\text{O}_2 + \text{e}^- + \text{H}^+ \rightarrow \text{HO}_2^\bullet$	-0.05	ROS generation
$\text{O}_2 + \text{e}^- \rightarrow \text{O}_2^{\bullet-}$	-0.33	ROS generation
$2\text{H}^+ + 2\text{e}^- \rightarrow \text{H}_2$	-0.41	Hydrogen evolution
$\text{CO}_2 + 2\text{e}^- + 2\text{H}^+ \rightarrow \text{CO} + \text{H}_2\text{O}$	-0.53	CO ₂ reduction

One of the research niches in this area includes the development and selection of adequate materials for photoelectrochemical cells. These materials must have key properties including high photo-activity in the UV and visible range, chemical and physical stability, and high electrical conductivity that permits the design of the cells for an optimal mass transfer and radiation absorption [7].

Using PEC as treatment for organics removal from water can be challenging in the case of complex matrices, where there are chemical and optical interferences between light, dissolved organic matter, inorganic ions, and target pollutants, which may affect - negatively and sometimes positively- the PEC degradation efficiency [7]. Therefore, it is not surprising that many authors struggle to achieve ideal efficiencies (lab conditions) in real wastewater applications. This issue becomes even more challenging when targeting organic matter and microorganism simultaneously, as competition among them for the generated ROS may decrease the process efficiency. Moreover, key aspects of the design and scaling-up of PEC cells for water purification applications will be discussed. Lastly, the recent applications of PEC for the simultaneous treatment of wastewater and hydrogen production will be revised as one of the most

appealing applications [8], as they are a great opportunity for energy harvesting from wastewater as well as water remediation, becoming an excellent sustainable technology.

2. Nanomaterials for photoelectrocatalysis

In photocatalysis, the nanomaterials' band edge potentials must facilitate the production of hydroxyl and superoxide ion radical, nevertheless when PEC is applied the generation of both is not so important as the counter electrode can assist one side of the redox reaction. Also, the generation of ROS via PEC reduction reaction can be facilitated by the applied bias, completing the redox cycle. In this sense, materials with a smaller E_{bg} can be used and the counter electrode can be used to enable the electron transfer to the solution. Band gap energies and edge potentials of different nanomaterials is shown in Figure 1 [9].

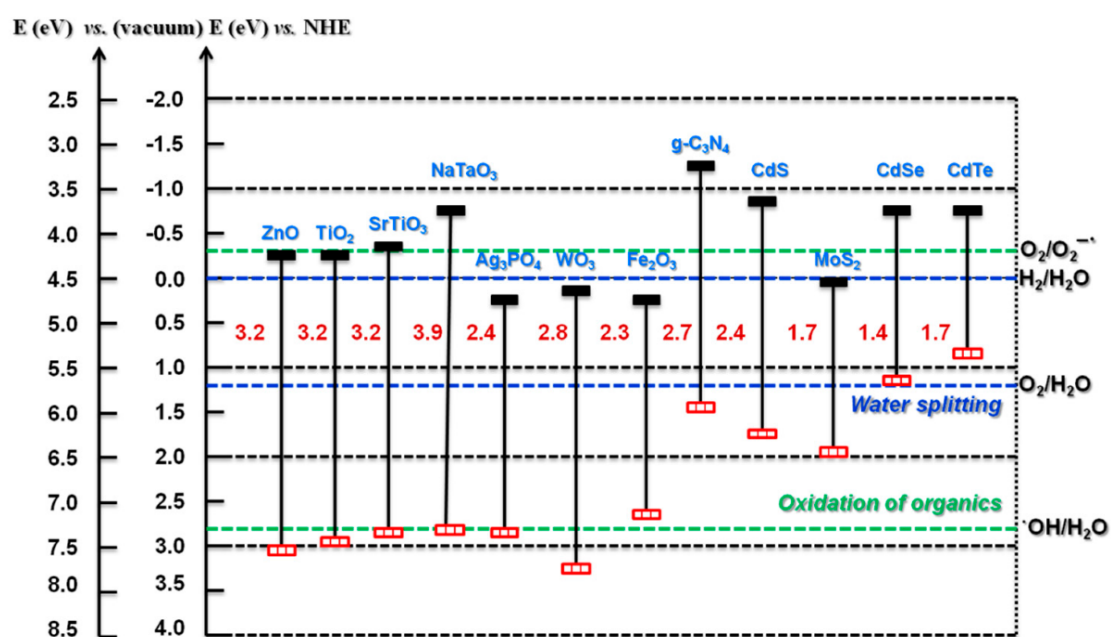


Figure 1 – Band gap and band edge potentials for different semiconductors. (Reproduced with permission from [10]).

The majority of PEC studies utilise n-type materials as photoanode (Figure 2), due to the instability of p-type photocathode materials [9]. As such, significant research has focused on the enhancement of the photoanodes performance, using lower band gap materials, heterostructures and the addition of co-catalyst to improve the visible light absorption, charge transfer, stability and overpotential of the oxidation reaction. The

improvement of photoelectrodes is of course important to enhance the overall performance. Lower band gap materials and/or heterostructures may offer improved solar performance by utilising more visible light, with extensive investigations primarily focused on solar energy harvesting rather than water treatment [11]. Moreover, not much consideration has been paid to the role of the counter electrode in PEC which can be used to generate additional ROS and impact the overall effectiveness of a system.

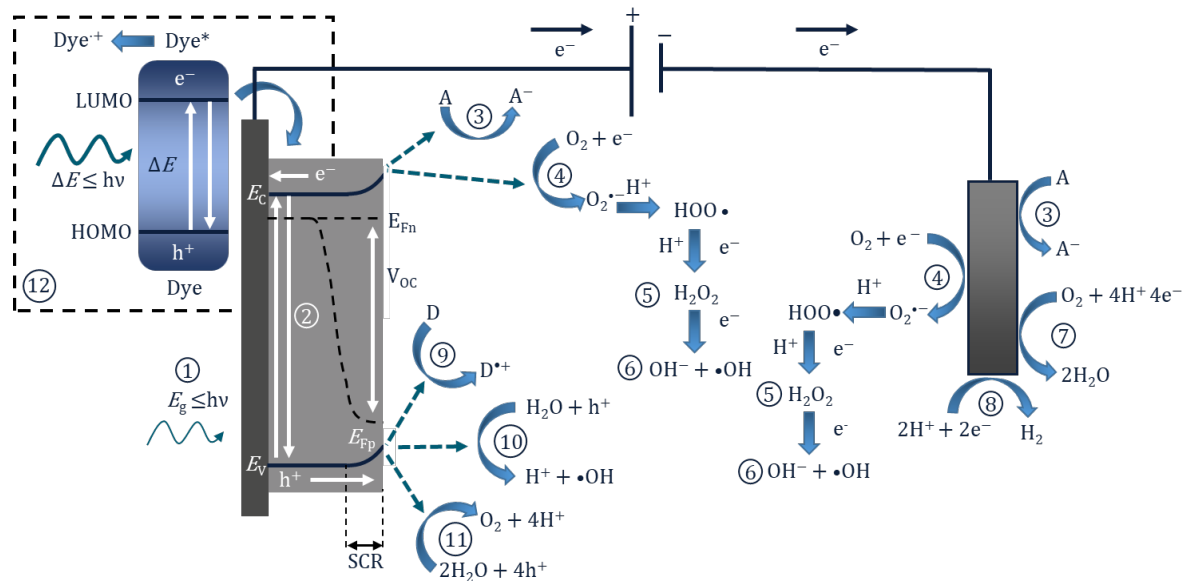


Figure 2 - Diagram of the PEC process and pathways for radical production using a photoanode and a non-semiconducting counter electrode. 1) Photon absorption, 2) photo-excitation and recombination, 3) electron transfer to an electron acceptor, 4) oxygen reduction to superoxide, 5) formation of hydrogen peroxide, 6) formation of hydroxyl radical, 7) oxygen and proton reduction to water, 8) proton reduction to hydrogen, 9) donor electron transfer, 10) oxidation of water to form hydroxyl radical, 11) oxygen evolution reaction, 12) dye sensitisation (* excited state) and electron transfer to the conduction band. (Reproduced with permission from [12]).

Many studies have focused on the development of semiconductor materials for use in PEC processes for various applications, such as pollutant degradation, microorganism inactivation [3,12,13,14,15] and hydrogen generation [16,17,18,19] (Table 2). For the purpose of PEC, semiconductor materials must exhibit, suitable band gap energies (E_{bg}), high charge carriers mobility and diffusion, optimal light absorption in the UV and visible range, stability, high catalytic activity, sustainability and low cost [7,20].

Several semiconductor photocatalysts have been applied as photoelectrodes for PEC processes including TiO_2 , ZnO , WO_3 , SnO_2 , Fe_2O_3 , BiVO_4 , CdS , Cu_2O , Bi_2WO_6 , BiPO_4 , MoS_2 , ZrO_2 , MoO_3 , and Bi_2MoO_6 [3,20,21,22]. These various semiconductor photocatalysts have been used as single, composite, and doped/metal-deposited Photoelectrode in PEC processes (Table 2).

Table 2 – Revision of nanomaterials investigated for different applications of PEC for water treatment and hydrogen generation with summary of information on their performance, key advantages of the material and the reference of publication.

Main application	Nano-material	Experimental conditions	Performance	Key advantages	Reference
Pollutant degradation in water	BiVO ₄ /FTO (F-SnO ₂)	10 mg/l Bisphenol A, Platinum cathode, 0.1 l 0.05 M NaClO ₄ , 300 W Xe lamp ($\lambda \geq 420$ nm), 0.25 V	100% removal in 120 min	low production cost & toxicity, high chemical & photostability, narrow band gap with VIS irradiation photoexcitation	[23]
	WO ₃ /W	20 mg/l Chlorfenvinphos, platinum cathode, pH=1, 100 mW/cm ² Xe lamp ($\lambda \geq 420$ nm), 1V	95% removal in 360 min	Non-toxic, low-cost, stability in acidic condition, photocorrosion resistance, high conductivity, VIS irradiation photoexcitation, deep valence band and high-oxidation-power holes	[4]
	WO ₃ /FTO (F-SnO ₂)	30 mg/l Urea, Pd/Au/PM cathode, PH=5, 0.05 M Na ₂ SO ₄ & 0.05 M NaCl, 100 mW/cm ² Xe lamp, 1.2 V	100% removal in 60 min		[4]
	WO ₃ /W	20 mg/l Fenamiphos, platinum cathode, PH =1, 100 mW/cm ² Simulated solar light, 1 V	100% removal in 120 min		[24]
	WO ₃ /ITO	10 mg/l Carbosulfan, platinum cathode, 0.1 M Na ₂ SO ₄ , Vis-light Irradiation, & 1 V	55% removal in 60 min		[24]
	WO ₃ /FTO	10 mg/l Atenolol, Pt cathode, 0.1 M NaClO ₄ , 15 mW/cm ² Hg lamp ($\lambda > 360$ nm), 1.5 V	100 Removal in 300 min		[25]
	Fe ₂ O ₃ /graphite & TiO ₂ /glass	200mg/l Berberine chloride, Stainless steel cathode, 0.6 L of 0.1 M Na ₂ SO ₄ , 0.078 mW/cm ² UV lamp, 9.0 mA/cm ²	93% removal in 60 min		low cost, non-toxic, & good chemical stability
	Fe ₂ O ₃ /FTO (F-SnO ₂)	10 mg/l Methylene blue, platinum cathode, pH=2.5, 1.0 M NaHCO ₃ , 100 mW/cm ² simulated solar light, 0.2 mA	>90% in 60 min	[4]	
	MoS ₂ /ITO	20 mg/L Ammonia nitrogen (AN), 10 mg/L Bovine Serum Albumine (BSA), platinum cathode, pH=10, 0.1 M Na ₂ SO ₃ , 95.5 mW/cm ² Xe lamp (> 420 nm), 0.6V	80% removal of AN for 360 min 70% removal of BSA in 240 min	Earth-abundant elements, simple fabrication, VIS irradiation photoexcitation	[4]
	ZnO/EG	0.01mM Eosin dye, platinum cathode, pH=1.5, 0.1 M Na ₂ SO ₄ , 300 W halogen lamp, 1.5V	95% removal in 120 min	low-cost, lower recombination rate due its wide band-gap, excellent chemical, and photochemical stability, non-toxic	[4]
	MoO ₃ /EG	0.1mM Methyl red & 0.1mM methylene blue dye, Pt cathode, 0.1 M Na ₂ SO ₄ , 400 W simulated solar light, 1.5V	92 % MR, 89 %MB removal 180 min	Easy preparation, high photoactivity & stability, large surface area, promising candidate for replacing TiO ₂ due it is wide band gap, & wide absorption spectrum	[4]
	MoO ₃ /Mo	10 μ M Methylene blue, Pt cathode, 0.2 M K ₂ SO ₄ , 150W simulated solar light, 0.6V	100% removal in 80 min		[4]
	Bi ₂ WO ₆ /CA	1 mg/l Nonylphenol, pH =10, 500 mW/cm ² simulated solar light, 0.6 V & electrosorption	99% Removal 480 min	Good adsorption performance & conductivity, high specific surface area, self-cleaning ability	[4]
	TiO ₂ /Ti	25mg /l Reactive Red 243, activated titanium cathode, 1.8 L of 635 μ S/cmM KCl, 15 W UV ($\lambda = 254$ nm), 1.5 V	99% decolourisation in 60 min	High UV light absorption, high electrode stability, high photocurrent density, short diffusion path for photoinduced holes to the supporting electrode, & high disinfection performance	[12]
TiO ₂ /Ti	10 mg /l Acetaminophen, titanium cathode, 1 L of 0.02 M Na ₂ SO ₄ , 14 W UV ($\lambda = 275$ nm), 8 V	95% degradation in 300 min	[12]		

Disinfection	TiO ₂ /Ti	10 ⁶ CFU/ml <i>E. coli</i> , Pt cathode, 0.19 L surface water 697 μS/cm, 5 mW/cm ² black light UV (λ= 365 nm), 1V	2.0-log reduction in 120 min	[14]	
	TiO ₂ /Ti	≥ 10 ⁶ CFU/ml <i>E. coli</i> & <i>P. aeruginosa</i> , carbon felt cathode, 0.3 L of rainwater 70 μS/cm, real solar radiation, 1V	5.5 log reduction of <i>E. coli</i> . 5.8-log reduction of <i>P. aeruginosa</i> in 240min	[13]	
	TiO ₂ / ITO	10 ³ CFU/ml <i>E. coli</i> , nickel mesh cathode, 1 L of 0.1 M Na ₂ SO ₄ , 0.047 mW/cm ² black light UV (λ= 362 nm), 1V	<i>E. coli</i> conc. < 1 CFU/ml in 200 min	[12]	
Pollutant degradation & disinfection	TiO ₂ /Ti	10 mg /l Benzophenone (BP), 10 ⁶ CFU/ml <i>Candida parapsilosis</i> , DSA cathode, 1 L of 0.1 M Na ₂ SO ₄ , 36 W UVB lamp irradiation, 2 V	100 % removal in 90 min for BP by PEC, 6-log reduction of <i>C. parapsilosis</i> by (PEC+O ₃) in 60 min	[26]	
H ₂ production & pollutant degradation	TiO ₂ /SS	Ni/SS cathode, 0.0768 g/L NaCl, 0.0082 g/L KCl, 0.0024 g/L MgCl ₂ ·6H ₂ O, 0.0191 g/L CaCl ₂ ·2H ₂ O, 0.05 g/L Phenol and 29.21 Na ₂ SO ₄ g/L (simulated wastewater) or oilfield-produced wastewater. 150 W metal-halide lamp with UV filter.	H ₂ production rate 12.36 μmol/h and phenol degradation 80% (simulated wastewater). Hydrogen production rate 9.11 μmol/h (oilfield-produced wastewater)	Low cost and toxicity, high stability. Filter-press reactor.	[27]
	TiO ₂ /Pt /FTO (F-SnO ₂)	Pt cathode. 0.1 mM methyl orange dye, 2 M methanol and 0.01M Na ₂ SO ₄ , UV light.	Hydrogen production rate of 11.4 mmol/h. Quantum yield of 3.70 %.	Improved charge separation.	[28]
	TiNT/WO ₃ /Ti	Pt cathode, 5 × 10 ⁻⁵ M, RB5 dye in 0.1M-Na ₂ SO ₄ . H-type reactor; Nafion membrane.	H ₂ generation efficiency (46%), dye removal (100% discoloration and 85% reduction in TOC)	Improved charge separation.	[29]
	C-N-TiNTs/Ti	Pt cathode. 40 mg/L of perfluorooctanoic acid. H-type reactor	After 180 min, removal of 56.1 % of perfluorooctanoic acid and production of 8.3 mmol H ₂ .	Improved charge transport and carrier lifetime.	[30]
	Bi/BiVO ₄ /ITO	Pt cathode, 0.2 M Na ₂ SO ₄ , 20 mg/L phenol	H ₂ production rate 27,8 μmol/cm ² .h	Narrow bandgap and reduced recombination rate.	[31]
	g-C ₃ N ₄ /Ni foam	Pt cathode, 20 mL NaOH(0.5M) and 10 mg/L Rhodamine B, Methyl Orange or Phenol. Visible light (λ > 420 nm).	H ₂ evolution rate 5.8 μmol/cm ² .h and 21.6 % PhB pollutant removal.	Strong visible light absorption.	[32]
	TiO ₂ -1wt% Au@TiO ₂ /Al ₂ O ₃ /Cu ₂ O	Pt anode. 30 mg/L humic acid, H-type reactor. Solar with AM 1.5 irradiation.	Solar-to-hydrogen conversion 0.5%. Humic acid degradation efficiency of 87% in 2h.	Wide-range photon absorption and efficient charge separation. Self-biased PEC.	[33]
	Ti-Fe ₂ O ₃ /FTO (F-SnO ₂)	Pt dispersed in carbon as cathode. 1M NaOH and 1 g/L glucose. H-type reactor. 100mW/cm ² Xenon lamp.	H ₂ production 2.3 μmol/min in presence of glucose.	Narrow bandgap.	[34]
H ₂ production, pollutant degradation & disinfection	g-C ₃ N ₄ /Ag/AgCl/BiVO ₄	Pt or MoS ₂ as cathode. Sewage with 2 ppm of benzophenone. H-type cell. Nafion-117 membrane. 1.5 A.M solar simulator 150W.	Benzophenone degradation efficiency of 11.15%/ cm ² .h , disinfection of ≤1000 CFU/100 mL/cm ²	Efficient charge transfer ability. H ₂ production coupled to EP's degradation and E.coli disinfection.	[35]

Among potential photocatalytic materials, TiO₂, ZnO, and WO₃ are the most common used photocatalysts in PEC processes. TiO₂ as an n-type semiconductor is the most widely used and investigated owing to its well-recognised properties such as photocatalytic activity compared to other semiconductor materials, non-toxicity, improved chemical stability, reusability, and adequate E_{bg} values ranging between 3.0–3.2 eV ensures its effectiveness under UV irradiation, accounting for 4–5 % of the solar spectrum [3,20].

ZnO has been widely studied for use in PEC processes as its properties are similar to TiO₂ as an n-type semiconductor. ZnO photocatalysts are considered cost-effective and environmentally friendly. However, the major limitation with ZnO is the chemical instability when placed in an aqueous medium. A limited pH range is established where ZnO remains chemically stable. WO₃ with E_{bg} values of 2.5–2.7 eV exhibit high stability in acidic solutions as well as photocorrosion resistance, photoexcitation by sunlight irradiation, and high conductivity [4,24]. WO₃ performance improves under visible light irradiation, resulting in easier generation of charge carriers due it is relatively low E_{bg} ; moreover, it has been widely applied for pollutant degradation [25]. The primary limitations of WO₃ are its irritant and toxicity properties [3].

Another type of thermally and chemically stable photocatalyst is SnO₂ with a higher E_{bg} than TiO₂, ranging between 3.5–3.8 eV. However, in SnO₂ the conduction band position limits its ability to reduce oxygen in PEC processes [20,24]. Therefore, this photocatalyst has not been used as photoelectrode material in PEC for water treatment. However, its coupling with other photocatalytic materials has been widely studied for use in PEC processes [24]. Fe₂O₃ is a cost-effective, chemically stable, and non-toxic semiconductor with a low E_{bg} between 2.1–2.2 eV. However, it has a high recombination rate and low conductivity, limits its application as a photoelectrode [3,4]. Another semiconductor with low E_{bg} (2.4–2.5 eV) is BiVO₄ which can be photoexcited under sunlight. BiVO₄ is nontoxic and stable under neutral pH conditions [23].

Semiconductor photoelectrodes including CdS, Cu₂O, Bi₂WO₆, MoS₂, Bi₂MoO₆, MoO₃, BiPO₄, and ZrO₂ have been applied primarily for the PEC degradation of pollutants. Their band gaps are lower than 3 eV excluding MoO₃ (3.2 eV), BiPO₄ (3.8 eV), and

ZrO₂ (5.0 eV). All materials were mostly applied for organic pollutant degradation in water, including dyes and pharmaceuticals [4]. Thus, the development of semiconductor materials for PEC process should be further researched for the various PEC process application and should be directed to the utilization of sunlight irradiation and the increase in their PEC activity in order to increase the process efficiency and decrease the costs of the treatment. Moreover, the PEC should facilitate simultaneous energy generation to make the processes sufficient and enable their practical application.

3. PEC reactors for removal of organic pollutants and pathogens in water

The degradation of organic compounds and inactivation of microorganisms in water using photoelectrocatalysis (PEC) is achieved by direct oxidation/reduction of the contaminate or indirectly by the generation of ROS [36]. There are several reactor configurations reported in literature; however, a commonality with them highlights the need for a high surface to volume ratio with minimal distance between electrodes, mass transport can impact/improve the degradation rates, an adequate supply of oxygen is important for the reductive pathways to produce ROS, and depending on the contaminate and electrolyte used there is an optimal bias [26, 37]. Given the number of variables, the generation of a computer-simulated model may identify optimal designs.

Ideally, a scaled-up reactor design should enable a continuous flow, in which the effluent is treated to a required standard and enables a suitable quantity of potable water in a reasonable time. One such design is the growing area of PEC membrane reactors, the design Wang et al [38] (figure 3), demonstrated that the reactor could degrade phenol by 94% with a bias of +1.5 V; while the membrane alone could only remove 7% via absorption. The PEC reactor also displayed anti-foiling capabilities; therefore, increasing the lifetime of the membrane and in theory decrease the cost per unit treated. Sheydaei et al. [39] examined degradation of diazinon with a continuous flow PEC/reverse osmosis hybrid set-up, in which non-degraded diazinon returned to the PEC reactor for further degradation.

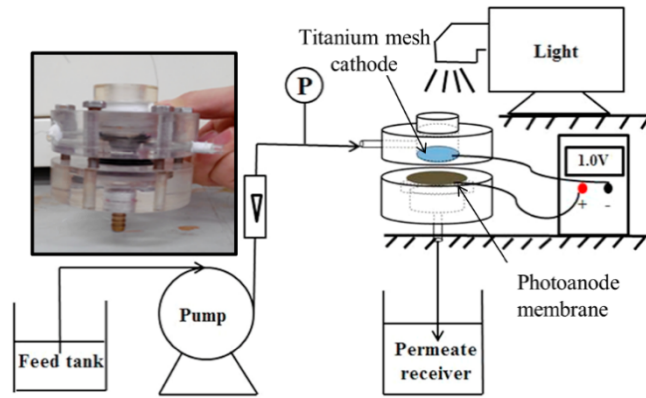


Figure 3 –PEC membrane reactor set-up, insert photo of the reactor (Adapted with permission from [20]).

The inclusion of aeration into a reactor has dual purposes, ensuring oxygen for the reductive pathway to form an ROS and improving mass transport. Kim et al. [26] (figure 4) examined purging with both O_2 and O_3 for the degradation of benzophenone-3 and *Candida parapsilosis*. The economics of the reactor was examined by using figures-of-merit as proposed by Bolton et al. [40]. The results demonstrated that the use of O_3 resulted in a lower figures-of-merit than O_2 . Though this method only considers the electrical usage per order of reduction (i.e. the running cost) and not the capital cost.

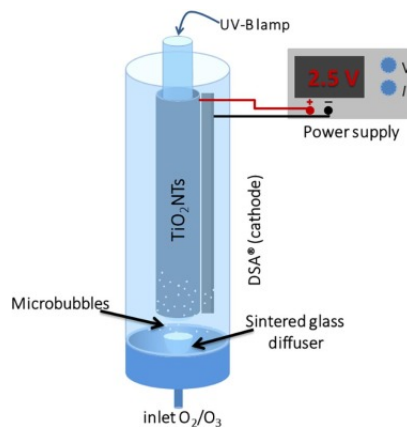


Figure 4 – Annular bubble column reactor (Reproduced with permission from [26]).

As these systems require an irradiance source there are only 2 options, solar or artificial. The use of energy-efficient LED's enables a PEC reactor to be operated at any time but there is an additional capital and running cost associated [41]. The reactor design of Montenegro-Ayo et al. (Figure 5) [42] reported a small-scale (350 mL) point-of-use device, which consisted of a TiO_2 nanotube photoanode, a titanium

cathode and a UVA-LED (365 nm) for inactivation of *E. coli* in natural water within 6 minutes, showing promising application of UV-LEDs for PEC.

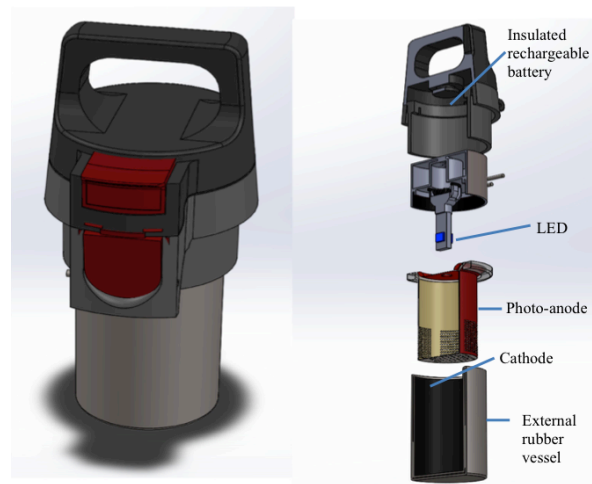


Figure 5 – Left – Diagram of the point-of-use ‘e-DRINK’ device (Reproduced with permission from [42]).

The use of real solar irradiation eliminates the need for an artificial irradiation source, which should reduce the cost of a system. Though this introduces additional problems, such as adequate reactor designs and variance in solar irradiation, which in turn will change the treatment time. The reactor design of McMichael et al. [13] (Figure 6) reported testing under real solar irradiation, for the inactivation of *E. coli* and *P. aeruginosa*, more importantly it demonstrated that photocurrent correlates linearly with changing UV intensity (for a titanium nanotube photoanode), which could potentially be developed into a quality assurance method when using real solar irradiation.

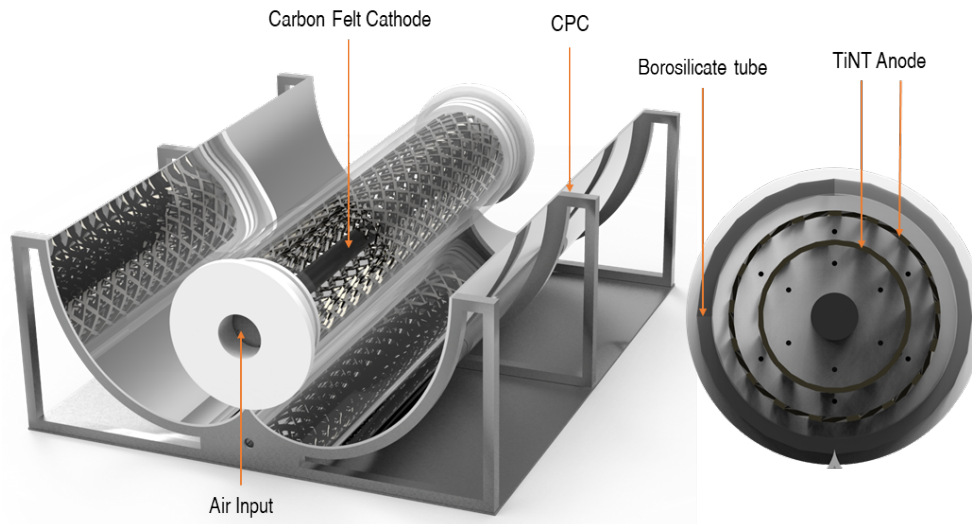


Figure 6 – Solar PEC reactor configuration (Reproduced with permission from [13]).

4. PEC for wastewater treatment and scale-up

The ultimate goal is to use PEC systems for real-world applications; however, currently most studies are based on lab-scale experiments with volumes less than 3 L [43]. The absence of scaled up systems may be due to the lack of predictive models that can be used to design and develop of PEC systems [44]. Only a few manuscripts have been published in which they report an empirical model to remove organic pollutants [45]. However, several models have been reported for the design and optimisation of photoelectrochemical reactors for water splitting into hydrogen and oxygen [46]. The models were developed using Multiphysics software since it allows coupling and solving the different physics that govern the process, such as radiation absorption, electrochemistry or fluid flow. The existing models [44] can be adapted for wastewater treatment by developing intrinsic kinetic models, estimating the intrinsic kinetic parameters and the chemical reactions taking place at the electrode-electrolyte interface, akin to models reported for photocatalytic simulation [47]. The water splitting model of Hankin et al. [46] (Figure 7) could potentially be adapted to simulate the assessment of different electrode geometries, electrode configurations and the resulting performance by evaluating the spatial distributions of potential, photon flux and current densities.

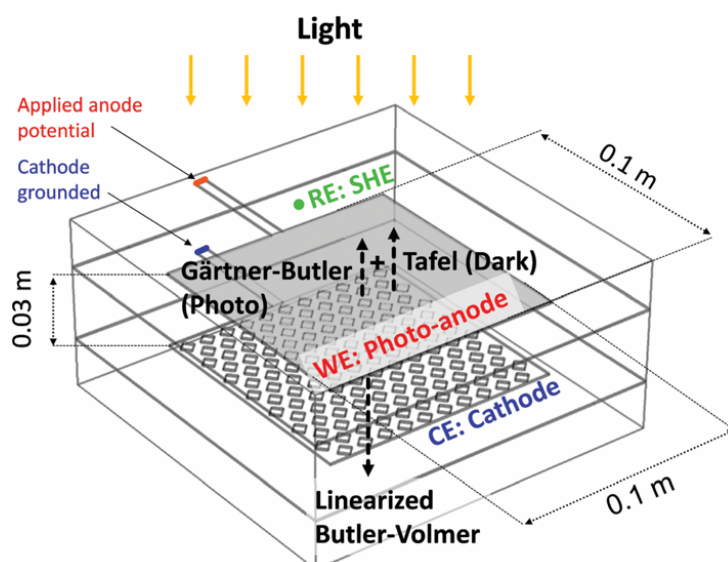


Figure 7 – Isometric view of the reactor showing relative positions of the working (Ti|SnIV-Fe₂O₃ photo-anode), counter (Ti|Pt) and reference (SHE) electrodes as well as the kinetic models applied at each electrode|solution interface (Reproduced with permission from [47]).

Moreover, many studies use unrealistic water solutions i.e. ultrapure water with an inorganic salt e.g. Na₂SO₄. To scale up PEC systems more research is required with synthetic or real wastewater. Real water matrixes will contain a mixture of organic and inorganic compounds that will compete for the ROS and would be expected to result in slower reaction rates [43]. Though the presence of chlorine can be beneficial as it results in reactive chlorine species, which can inactivate bacteria and react with organic compounds [48]. Commonly, only one contaminant is tested at a time, though it is of interest to examine the effect of having a combination of pollutants i.e. organic microcontaminants and microorganisms as performed by Salmeron et al. [14]. Their work used a TiO₂ nanotube photoanode and a carbon-felt cathode to remove a mixture of *E. coli* and three organic microcontaminants (terbutryn, clorfenvinphos and diclofenac) dissolved in surface water. They successfully proved both the inactivation of bacteria and degradation of the pollutants, without adding any supporting electrolytes was possible. Though more research is required to move from lab-scale systems to scaled-up pilot systems treating real wastewater, the use of simulation may help facilitate in the design process or to optimise existing designs.

5. PEC generation of H₂ from wastewater

The PEC -based generation of hydrogen can be coupled to pollutant removal from wastewater. In this configuration, the benefit of energy recovery as hydrogen fuel is

combined to the reduction of environmental pollution in the water ecosystem. In this photoelectrochemical system, the holes oxidate the wastewater compounds in the photoanode, while the electrons are drawn to the photocathode through the external circuit, where the reduction occurs, producing hydrogen.

Very diverse photoanodes have been used in the degradation of wastewater pollutants coupled to hydrogen production including TiO_2 [27], TiO_2/WO_3 [29], TiO_2/Pt [28], C-N- TiO_2 nanotubes (TiNTs) [30], Bi/ BiVO_4 [31], g- C_3N_4 [32], Ti- Fe_2O_3 [34] and g- $\text{C}_3\text{N}_4/\text{Ag}/\text{AgCl}/\text{BiVO}_4$ [35]. Platinum is the most used cathode material, as it has generally shown the best performance as a hydrogen evolution catalyst, with low overpotential and high reaction rates in acidic environments. However, due to the high cost and scarcity of Pt, the development of this technology should involve the utilisation of alternative inexpensive and abundant materials. Alternatively, a recent study reported the use of a z-scheme photocathode formed by TiO_2 -1wt% Au@ $\text{TiO}_2/\text{Al}_2\text{O}_3/\text{Cu}_2\text{O}$, resulting in a self-biased PEC with good charge separation [33].

Most of the research does not study the effect of different reactor configurations in this process. Commonly, studies are performed using small volume (i.e. <100 mL) one compartment reactors; alternatively, other studies use a H-type reactor where the anolyte and catholyte compartments are usually separated by a membrane [29,34]. It has also been proven the possibility of using a filter-press reactor operated in batch recirculation mode [27].

Wastewater composition varies greatly depending on its origin, it usually consists of a complex mixture containing organic and inorganic compounds, microorganisms, and metals. Nevertheless, the majority of the research is centred on the study of hydrogen production from the degradation of just one pollutant. Studies have mainly focused on the following compounds: ammonia, urea, formamide, glucose, phenol, ethanol and glycerol [49]. Only limited works have proven the feasibility of hydrogen production using real wastewater samples as sewage from a wastewater treatment plant [35] or wastewater produced from oil fields [27]. Moreover, it has been shown the possibility of coupling as well water disinfection to pollutant degradation and hydrogen production [35].

Techno-economic reports on PEC for hydrogen (with a STH 10%) and PV-electrolysis have been done [50]. With PEC projected to be more expensive than their competitors, therefore the dual treatment of water and hydrogen production may improve cost effectiveness and become an economically sustainable technology.

6. Conclusions

For the optimisation of the effectiveness of the PEC processes, the most important step is the proper selection of the electrode materials, the optimisation of the photoelectrode (including TiO_2 , ZnO , SnO_2 , WO_3 , Fe_2O_3 , BiVO_4 , CdS , Cu_2O , Bi_2WO_6 , BiPO_4 , MoS_2 , ZrO_2 , MoO_3 , and Bi_2MoO_6) and the reactor design is required, while the counter electrode is not usually analysed (stainless steel, carbon paper/felt, platinum, titanium). The reactor design will require the surface to volume ratio to be maximised, reduce the separation between electrodes and non-limiting mass transfer and dissolved oxygen levels.

Most of the published articles report lab and very controlled conditions of water matrix and pollution, therefore research using synthetic and real wastewater is required to assess the applicability of these systems in real case scenarios. This will bring additional insights into the possible side reactions and the interactions between different pollutants and inorganic compounds in the photoelectrochemical cell.

PEC reactors for wastewater remediation and hydrogen production need to be considered as dual solution for water remediation and energy solution, as this reduces the cost of the technology, including the capital cost, effective cost per unit treated and it's potential for real-world adoption against existing technologies.

Acknowledgements

The authors wish to acknowledge the Department for Economy (DfE) Northern Ireland for funding Stuart McMichael, the funding from the European Union's Horizon 2020 research and innovation programme under grant agreement No 820718 (PANIWATER) and under the Marie-Curie grant agreement No 812574 (REWATERGY).

Conflict of interest

The authors declare no conflict of interest.

References

- [1] Y. Deng, R. Zhao, Advanced Oxidation Processes in Wastewater Treatment, *Curr. Pollution Rep.* 1 (2015) 167–176. <https://doi.org/10.1007/s40726-015-0015-z>
- [2] M. Coha, G. Farinelli, A. Tiraferri, M. Minella, D. Vione, Advanced oxidation processes in the removal of organic substances from produced water: Potential, configurations, and research needs. *Chem. Eng. J.* 414 (2021) 128668. <https://doi.org/10.1016/j.cej.2021.128668>
- [3] S. Garcia-Segura, E. Brillas, Applied photoelectrocatalysis on the degradation of organic pollutants in wastewaters, *J. Photochem. Photobiol. C Photochem. Rev.* 31 (2017) 1–35. <https://doi.org/10.1016/j.jphotochemrev.2017.01.005>
- [4] E. Kusmieriek, Semiconductor Electrode Materials Applied in Photoelectrocatalytic Wastewater Treatment—an Overview, *Catalysts* 10 (2020) 439. <https://doi.org/10.3390/catal10040439>
- [5] C. Pablos, J. Marugán, C. Adán, M. Osuna, and R. van Grieken, “Performance of TiO₂ photoanodes toward oxidation of methanol and *E. coli* inactivation in water in a scaled-up photoelectrocatalytic reactor,” *Electrochim. Acta* (2017) 599-606. <https://doi.org/10.1016/j.electacta.2017.11.103>.
- [6] Li, X.; Yu, J.; Jaroniec, M. Hierarchical photocatalysts. *Chem. Soc. Rev.* 45 (2016) 2603–2636, <https://doi.org/10.1039/c5cs00838g>.
- [7] E. Brillas, C.A. Martinez-Huitle, Decontamination of wastewaters containing synthetic organic dyes by electrochemical methods. An updated review, *App. Catal. B: Environ.* 166-167 (2015) 603-643. <http://dx.doi.org/10.1016/j.apcatb.2014.11.016>
- [8] J. Tang, T. Liu, S. Miao, Y. Cho, Emerging Energy Harvesting Technology for Electro/Photo-Catalytic Water Splitting Application, *Catalysts* 11 (2021) 142. <https://doi.org/10.3390/catal11010142>
- [9] Q. Huang, Z. Ye, X. Xiao, Recent progress in photocathodes for hydrogen evolution *J. Mater. Chem. A* 3 (2015) 15824–37. <https://doi.org/10.1039/C5TA03594E>
- [10] S. Kumar, S. Karthikeyan, A. Lee, g-C₃N₄-Based Nanomaterials for Visible Light-Driven Photocatalysis, *Catalysts* 8 (2018) 74. <https://doi.org/10.3390/catal8020074>
- [11] A.H. Hendi, A.M. Osman, I. Khan, T.A. Saleh, T.A. Kandiel, T.F. Qahtan, M.K. Hossain, Visible Light-Driven Photoelectrocatalytic Water Splitting Using Z Scheme Ag-Decorated MoS₂/RGO/NiWO₄ Heterostructure, *ACS Omega* 5 (2020) 31644-31656. <https://doi.org/10.1021/acsomega.0c03985>
- [12] S. McMichael, P. Fernández-Ibáñez, J.A. Byrne, A Review of Photoelectrocatalytic Reactors for Water and Wastewater Treatment. *Water* 2021a, 13, 1198. <https://doi.org/10.3390/w13091198>
- [13] S. McMichael, M. Waso, B. Reyneke, W. Khan, J.A. Byrne, P. Fernandez-Ibanez, Electrochemically assisted photocatalysis for the disinfection of rainwater under solar irradiation, *Applied Catalysis B: Environmental* 281 (2021b) 119485. <https://doi.org/10.1016/j.apcatb.2020.119485> (••)

- [14] I. Salmerón, P.K. Sharma, M.I. Polo-López, A. Tolosana, S. McMichael, I. Oller, J.A. Byrne, P. Fernández-Ibáñez, Electrochemically assisted photocatalysis for the simultaneous degradation of organic micro-contaminants and inactivation of microorganisms in water, *Process Safety and Environmental Protection* 147 (2021) 488-496. <https://doi.org/10.1016/j.psep.2020.09.060> (••)
- [15] M.C. Collivignarelli, A. Abbà, M.C. Miino, F.M. Caccamo, V. Torretta, E.C. Rada, S. Sorlini, Disinfection of wastewater by UV-based treatment for reuse in a circular economy perspective. Where are we at?, *Int. J. Environ. Res. Public Health*. 18 (2021) 1–24. <https://doi.org/10.3390/ijerph18010077>
- [16] Ješić, D., Lašič Jurković, D., Pohar, A., Suhadolnik, L., Likozar, B., Engineering photocatalytic and photoelectrocatalytic CO₂ reduction reactions: Mechanisms, intrinsic kinetics, mass transfer resistances, reactors and multi-scale modelling simulations, *Chem. Eng. J.* (2021). <https://doi.org/10.1016/j.cej.2020.126799>.
- [17] Wang, L., Wei, Y., Fang, R., Wang, J. , Yu, X., Chen, J., Jing, H., Photoelectrocatalytic CO₂ reduction to ethanol via graphite-supported and functionalized TiO₂ nanowires photocathode, *J. Photochem. Photobiol. A Chem.* (2020). <https://doi.org/10.1016/j.jphotochem.2020.112368>.
- [18] Wang, J., Wei, Y., Yang, B., Wang, B., Chen, J., Jing, H., In situ grown heterojunction of Bi₂WO₆/BiOCl for efficient photoelectrocatalytic CO₂ reduction, *J. Catal.* (2019). <https://doi.org/10.1016/j.jcat.2019.06.007>.
- [19] Han, B., Wang, J., Yan, C., Dong, Y., Xu ,Y., Nie, R., Jing, H., The photoelectrocatalytic CO₂ reduction on TiO₂@ZnO heterojunction by tuning the conduction band potential, *Electrochim. Acta.* (2018). <https://doi.org/10.1016/j.electacta.2018.07.216>
- [20] Y. Wang, M. Zu, X. Zhou, H. Lin, F. Peng, S. Zhang, Designing efficient TiO₂-based photoelectrocatalysis systems for chemical engineering and sensing, *Chem. Eng. J.* 381 (2020) 122605. <https://doi.org/10.1016/j.cej.2019.122605>
- [21] P. Bhunia, K. Dutta, Photocatalysts and Photoelectrocatalysts in Fuel Cells and Photofuel Cells. In: Rajendran S., Naushad M., Ponce L., Lichtfouse E. (eds) *Green Photocatalysts for Energy and Environmental Process. Environmental Chemistry for a Sustainable World*, vol 36. Springer, 2020 Cham. https://doi.org/10.1007/978-3-030-17638-9_2
- [22] P. Arunachalam, A.M. Al Mayouf, Photoelectrochemical Water Splitting. In: S. Mohapatra, T.A. Nguyen, P. Nguyen-Tri (eds) *Micro and Nano Technologies, Noble Metal-Metal Oxide Hybrid Nanoparticles*. Woodhead Publishing, 2019, pp 585-606. <https://doi.org/10.1016/B978-0-12-814134-2.00028-0>
- [23] B.O. Orimolade, O.A. Arotiba, Bismuth vanadate in photoelectrocatalytic water treatment systems for the degradation of organics: A review on recent trends, *Journal of Electroanalytical Chemistry* 878(1) (2020) 114724. <https://doi.org/10.1016/j.jelechem.2020.114724>
- [24] M.G. Peleyeju, E.L. Viljoen, WO₃-based catalysts for photocatalytic and photoelectrocatalytic removal of organic pollutants from water – A review, *J. Water Process Eng.* 40 (2021), 101930. <https://doi.org/10.1016/j.jwpe.2021.101930>
- [25] G. Longobucco, L. Pasti, A. Molinari, N. Marchetti, S. Caramori, V. Cristino, R. Boaretto, C.A. Bignozzi, Photoelectrochemical mineralization of emerging contaminants at porous WO₃ interfaces, *Appl. Catal. B Environ.* 204(5) (2017) 273-

282. <https://doi.org/10.1016/j.apcatb.2016.11.007>

[26] J.Y.U. Kim, G.G. Bessegato, B.C. de Souza, J.J. da Silva, M.V.B. Zanoni, Efficient treatment of swimming pool water by photoelectrocatalytic ozonation: Inactivation of *Candida parapsilosis* and mineralization of Benzophenone-3 and urea, *Chem. Eng. J.* 378 (2019) 122094. <https://doi.org/10.1016/j.cej.2019.122094>

[27] M. I. Jaramillo-Gutiérrez, E.P. Rivero, M.R. Cruz-Díaz, M.E. Niño-Gómez, J.A. Pedraza-Avella, Photoelectrocatalytic hydrogen production from oilfield-produced wastewater in a filter-press reactor using TiO₂-based photoanodes, *Catal. Today* 266 (2016) 17–26. <https://doi.org/10.1016/j.cattod.2015.12.008>

[28] A. Bahramian, M. Rezaeivala, K. He, D.D. Dionysiou, Enhanced visible-light photoelectrochemical hydrogen evolution through degradation of methyl orange in a cell based on coral-like Pt-deposited TiO₂ thin film with sub-2 nm pores, *Catal. Today* 335 (2019a) 333–344. <https://doi.org/https://doi.org/10.1016/j.cattod.2018.12.018>.

[29] T.T. Guaraldo, V.R. Gonçalves, B.F. Silva, S.I.C. Torresi, M.V.B. Zanoni, Hydrogen production and simultaneous photoelectrocatalytic pollutant oxidation using a TiO₂/WO₃ nanostructured photoanode under visible light irradiation, *J. Electroanal. Chem.* 765 (2016) 188–96. <http://dx.doi.org/10.1016/j.jelechem.2015.07.034>

[30] Y.-P. Peng, H. Chen, C.P. Huang, The Synergistic Effect of Photoelectrochemical (PEC) Reactions Exemplified by Concurrent Perfluorooctanoic acid (PFOA) Degradation and Hydrogen Generation over Carbon and Nitrogen codoped TiO₂ Nanotube Arrays (C-N-TNTAs) photoelectrode, *Appl. Catal. B Environ.* 209 (2017) 437–446. <https://doi.org/10.1016/j.apcatb.2017.02.084>.

[31] F. Li, W. Zhao, D.Y.C. Leung, Enhanced photoelectrocatalytic hydrogen production via Bi/BiVO₄ photoanode under visible light irradiation *Appl. Catal. B Environ.* 258 (2019) 117954. <https://doi.org/10.1016/j.apcatb.2019.117954>

[32] X. Zhao, D. Pan, X. Chen, R. Li, T. Jiang, W. Wang, G. Li, D.Y.C. Leung, g-C₃N₄ photoanode for photoelectrocatalytic synergistic pollutant degradation and hydrogen evolution *Appl. Surf. Sci.* 467–468 (2019) 658–65. <https://doi.org/10.1016/j.apsusc.2018.10.090>

[33] A. Bahramian, M. Rezaeivala, K. He, D.D. Dionysiou, Enhanced visible-light photoelectrochemical hydrogen evolution through degradation of methyl orange in a cell based on coral-like Pt-deposited TiO₂ thin film with sub-2 nm pores, *Catal. Today* 335 (2019b) 333–344. <https://doi.org/https://doi.org/10.1016/j.cattod.2018.12.018>.

[34] G. Iervolino, I. Tantis, L. Sygellou, V. Vaiano, D. Sannino, P. Lianos, Photocurrent increase by metal modification of Fe₂O₃ photoanodes and its effect on photoelectrocatalytic hydrogen production by degradation of organic substances, *Appl. Surf. Sci.* 400 (2017) 176–183. <https://doi.org/10.1016/j.apsusc.2016.12.173>

[35] R.A. Rather, I.M.C. Lo, Photoelectrochemical sewage treatment by a multifunctional g-C₃N₄/Ag/AgCl/BiVO₄ photoanode for the simultaneous degradation of emerging pollutants and hydrogen production, and the disinfection of *E. coli*, *Water Res.* 168 (2020) 115166. <https://doi.org/10.1016/j.watres.2019.115166> (••)

[36] Z. Feng, Q. Tian, Q. Yang, Y. Zhou, H. Zhao, G. Zhao, Selectively photoelectrocatalytic reduction of oxygen to hydroxyl radical and singlet oxygen: Mechanism and validation in coal wastewater, *Appl. Catal. B* 286 (2021) 119908. <https://doi.org/10.1016/j.apcatb.2021.119908>

- [37] J. Bai, Y. Liu, J. Li, B. Zhou, Q. Zheng, W. Cai, A novel thin-layer photoelectrocatalytic (PEC) reactor with double-faced titania nanotube arrays electrode for effective degradation of tetracycline, *Appl. Catal. B* 98 (2010) 154-160. <https://doi.org/10.1016/j.apcatb.2010.05.024>
- [38] X. Wang, G. Wang, S. Chen, X. Fan, X. Quan, H. Yu, Integration of membrane filtration and photoelectrocatalysis on g-C₃N₄/CNTs/Al₂O₃ membrane with visible-light response for enhanced water treatment, *J. Membr. Sci.* 541 (2017) 153-161. <https://doi.org/10.1016/j.memsci.2017.06.046>
- [39] M. Sheydaei, M. Karimi, V. Vatanpour, Continuous flow photoelectrocatalysis/reverse osmosis hybrid reactor for degradation of a pesticide using nano N-TiO₂/Ag/Ti electrode under visible light, *J. Photochem. Photobiol. A* 2019, 384, 112068. <https://doi.org/https://doi.org/10.1016/j.jphotochem.2019.112068>.
- [40] Bolton, J.R.; Bircher, K.G.; Tumas, W.; Tolman, C.A. Figures-of-merit for the technical development and application of advanced oxidation technologies for both electric- and solar-driven systems. *Pure Appl. Chem.* 2001, 73, 627-637, <https://doi.org/10.1351/pac200173040627>.
- [41] N. Kangkun, C. Ponchio, Photoelectrodeposition of BiVO₄ layer on FTO/WO₃ photoanodes for highly efficient photoelectrocatalytic chemical oxygen demand sensor applications, *Applied Surface Science* 526 (2020) 146686. <https://doi.org/10.1016/j.apsusc.2020.146686>
- [42] R. Montenegro-Ayo, A.C. Barrios, I. Mondal, K. Bhagat, J.C. Morales-Gomero, M. Abbaszadegan, P. Westerhoff, F. Perreault, S. Garcia-Segura, Portable point-of-use photoelectrocatalytic device provides rapid water disinfection, *Sci. Total Environ.* 737 (2020) 140044. <https://doi.org/10.1016/j.scitotenv.2020.140044>
- [43] H. Rajput, R. Changotra, V. Kumar Sangal, A. Dhir, Photoelectrocatalytic treatment of recalcitrant compounds and bleach stage pulp and paper mill effluent using Au-TiO₂ nanotube electrode, *Chem. Eng. J.* 408 (2021) 127287. <https://doi.org/10.1016/j.cej.2020.127287>
- [44] F.E. Bedoya-Lora, A. Hankin, G.H. Kelsall, En route to a unified model for photoelectrochemical reactor optimisation. i - Photocurrent and H₂ yield predictions, *J. Mater. Chem. A* 5 (2017) 22683-22696. <https://doi.org/10.1039/c7ta05125e>
- [45] A. Turolla, M. Bestetti, M. Antonelli, Optimization of heterogeneous photoelectrocatalysis on nanotubular TiO₂ electrodes: Reactor configuration and kinetic modelling, *Chem. Eng. Sci.* 182 (2018) 171-179. <https://doi.org/10.1016/j.ces.2018.02.041>
- [46] A. Hankin, F.E. Bedoya-Lora, C.K. Ong, J.C. Alexander, F. Petter, G.H. Kelsall, From millimetres to metres: the critical role of current density distributions in photoelectrochemical reactor design, *Energy Environ. Sci.* 10 (2017) 346-360. <https://doi.org/10.1039/C6EE03036J>
- [47] C. Casado, J. Marugán, R. Timmers, M. Muñoz, R. van Grieken, Comprehensive multiphysics modeling of photocatalytic processes by computational fluid dynamics based on intrinsic kinetic parameters determined in a differential photoreactor, *Chem. Eng. J.* 310 (2017) 368-380. <https://doi.org/10.1016/j.cej.2016.07.081>
- [48] A. Farhat, J. Keller, S. Tait, J. Radjenovic, Assessment of the impact of chloride on the formation of chlorinated by-products in the presence and absence of

electrochemically activated sulfate, Chem. Eng. J. 330 (2017) 1265–1271. <https://doi.org/10.1016/j.cej.2017.08.033>

[49] A. Rioja-Cabanillas, D. Valdesueiro, P. Fernández-Ibáñez, J.A. Byrne, Hydrogen from wastewater by photocatalytic and photoelectrochemical treatment, J. Phys. Energy 3(2020) 12006. <https://doi.org/10.1088/2515-7655/abceab>

[50] A. Grimm, A.J. Wouter, G. J. Kramer, Renewable hydrogen production: A techno-economic comparison of photoelectrochemical cells and photovoltaic-electrolysis, International journal of hydrogen energy 45(43). (2020) 22545-22555. <https://doi.org/10.1016/j.ijhydene.2020.06.092> (•)