

Lab-on-a-Tip Based on a Bimetallic Nanoarchitecture Enabling Catalytic 4-Nitrophenol Switch-off [†]

Annalisa Scroccarello *, Flavio Della Pelle and Dario Compagnone

Faculty of Bioscience and Technology for Food, Agriculture and Environment, University of Teramo, Via Renato Balzarini 1, 64100 Teramo, Italy; fdellapelle@unite.it (F.D.P.); dcompagnone@unite.it (D.C.)

* Correspondence: ascroccarello@unite.it

[†] Presented at the 1st International Electronic Conference on Biosensors, 2–17 November 2020; Available online: <https://iecb2020.sciforum.net/>.

Published: 2 November 2020

Abstract: Mono- and multi-metal nanoparticles (MNPs), thanks to their unique and tunable features, still fascinate the analytical sciences, from their widespread use in sensing and biosensing as nanoplasmonic tags or catalysts up to MNPs-decorated surfaces. Here, a lab μ -Tip decorated with plasmonic-active polymeric films embodying gold/silver nanostructures is presented. The proposed lab-on-a-tip device speed-up the 4-nitrophenol conversion in 4-aminophenol, retaining the performances for more than 10 consecutive measures, acting as an enzyme-like catalyst.

Keywords: metal nanoparticles; polydopamine film; self-assembled nanoparticles; nanohybrid; nanodecored; catalyst; 4-nitrophenol

1. Introduction

Mono- and multi-metal nanoparticles (MNPs) are more and more protagonists of cutting-edge technology, demonstrating unique potentialities in different fields such as medicine, biotechnology, agriculture, etc. [1]. In particular, MNPs, thanks to their unique and tunable optical features, formally named localized surface plasmon resonance, have inspired the development of a new generation of optical (bio)sensing strategies. Among these, colorimetric strategies based on the MNPs formation or aggregation have permitted the selective detection of a plethora of analytes (e.g., ascorbic acid, glucose, polyphenols, pesticides, etc.) giving rise to effective assays [1–6]. Furthermore, rationally synthesized MNPs have been also widely employed in bioanalytical applications as nanotags and catalysts [7–10]. MNPs are often defined as ‘nanozyme’ due to their ability to catalyze chemical and biochemical reactions with notable effectiveness [7–9], allowing both homogeneous and heterogeneous catalysis [7–9].

The dyes regeneration aims to convert a dye from a non-active to an active state or from a toxic to a non-toxic form [11]. The 4-nitrophenol (4-NP) is a toxic substance potentially dangerous for the environment widely used in pesticides, drugs, and synthetic dyes production [7–9]; besides this, the 4-NP is also the product of several enzymatic reactions (phosphatase, glycosidase, etc.). Fortunately, the 4-NP can be converted into 4-aminophenol (4-AP) resulting in less toxicity; this conversion can be obtained in presence of sodium borohydride, a strong reducing agent, and can be catalyzed throughout different strategies.

Among the non-enzyme catalyzer, chemically or biologically synthesized MNPs, with different metal composition and structure, are widely studied [7–9,11]. The MNPs catalytic efficiency toward 4-NP reduction has been widely demonstrated; Berahim et al. [7] and Wang et al. [9] reported the catalytic performance of bi- (Au@AgNPs) and mono- (AuNPs) metallic nanoarchitectures, whereas

Kästner et al. [12] discussed the influence of the surfactant around the MNPs in the catalytic performances.

Commonly, nanozyme catalyzers reported in literature are used in solution as nanodispersions, and the related drawbacks of colloidal MNPs such as low stability and storability (due to their tendency to aggregate, precipitate, self-oxidize, etc.) need to consider tracing a limit in large-scale application (e.g., wastewater treatment plant). More important, the nature of the nanodispersions makes the reusability of the nano catalyzer not simple, requiring time-consuming washing and recovering steps, which can lead to nanodispersion morphology changing with loss of efficiency.

The adhesive nano-films proposed here are composed of AuNPs and AgNPs self-assembled thanks to polydopamine onto the μ -Tips internal surfaces. The μ -Tips modified with the here proposed films result in the ability to catalyze the 4-NP conversion up to 10 reaction cycles, allowing the 4-NP colorimetric decay monitoring. The proposed adhesive nanocomposite represents a springboard for the MNPs-based catalyst, potentially projectable in large-scale production, able to give rise to user-friendly devices as demonstrated by the lab-on-a-tips reported here.

2. Materials and Methods

2.1. Reagents, Materials, Samples and Apparatus

Dopamine hydrochloride ($C_9H_{11}NO_2 \cdot HCl$; DA), hydrogen tetrachloroaurate ($HAuCl_4 \cdot 3H_2O$, 99.9%; Au(III)), silver nitrate ($AgNO_3$), sodium hydroxide (NaOH), trizma hydrochloride ($C_4H_{11}NO_3 \cdot HCl$), 4-nitrophenol ($C_6H_5NO_3$, 4-NP), sodium borohydride ($NaBH_4$), and 1 mL polypropylene laboratory tips were purchased from Sigma-Aldrich (St. Louis, MO, USA).

Polystyrene Cuvette and Gilson pipette were purchased from Sigma-Aldrich (St. Louis, MO, USA). Spectrophotometric measurements were carried out using a JENWAY 6400 Spectrophotometer from Barlworld Scientific (Staffordshire, UK).

2.2. Metal Nanocomposite Fabrication in Laboratory-Tip

The metal-based nanocomposite formation was performed in 1 mL laboratory μ -Tips. The lab-Tips decoration was performed according to Scroccarello et al. [13,14], with some modifications. A schematization of the whole process is reported in Figure 1 and the main steps are described below.

2.2.1. PDA Film Self-Assembly

DA at a concentration of 0.5 g L^{-1} was prepared in Trizma buffer (10 mM, pH 8.5) and freshly used to fill lab-Tips (800 μL per tip). DA polymerization was carried out in static condition, in a white incubation room, at $25 \pm 2 \text{ }^\circ\text{C}$, under a light source (20 W, warm light bulb) placed at 50 cm of distance for a total polymerization time of 15 h. Finally, the polydopamine (PDA) formation was blocked, subsequently emptying the tips, which were washed and rinsed with abundant Milli-Q water. The PDA modified laboratory μ -Tips ($\mu\text{-T@PDA}$) were let dry at room temperature.

2.2.2. Gold and Silver Nanodecoration

- AuNPs decoration: The PDA modified μ -Tips were filled with 800 μL of 100 μM Au(III) aqueous solution and incubated in the dark at room temperature for 8 h. The reaction was blocked emptying the Tips subsequently washed and rinsed with abundant Milli-Q water. The AuNPs decorated $\mu\text{-T@PDA}$ were let dry at room temperature.
- AgNPs decoration: The AuNPs-decorated $\mu\text{-T@PDA}$ ($\mu\text{-T@Au}$) were filled with 740 μL of Milli-Q water and 40 μL of 20 mM $AgNO_3$; afterward, 20 μL of 4 M NaOH was added to trig the reaction (final volume 800 μL). The reaction mix was orbitally shaken (SSL1, Stuart equipment, Belfast, UK150) at 150 rpm at room temperature, in the dark, for 4 h. The reaction was blocked, subsequently emptying the Tips, which were washed and rinsed with abundant Milli-Q water. The AgNPs decorated $\mu\text{-T@Au}$ ($\mu\text{-T@Au@Ag}$) were left to dry at room temperature.

- Au@AgNPs decoration: For the bimetallic nanocomposite formation, the previous two steps were performed consecutively.

2.3. 4-Nitrophenol Reduction

The 4-nitrophenol (4-NP) reduction was performed directly in the modified μ -Tips (μ -T@PDA, μ -T@Au, μ -T@Ag, and μ -T@Au@Ag) in presence of NaBH_4 . The reaction mix was directly prepared in cuvette with 980 μL of 0.01 M NaBH_4 and 10 μL of 4-NP at different concentrations (final volume 1 mL). Then, the mix of reaction was sucked in the μ -Tips through Gilson pipette and incubated in the dark. The 4-NP color decay evolution kinetics (conversion at 4-AP, colorless) was monitored in cuvette through absorbance recording every 5 min at 400 nm (t_n) against the absorbance at time 0 (t_0), according to the following equation:

$$Abs_{t_n/t_0} = Abs_{t_n} / Abs_{t_0} \quad (1)$$

Finally, for each tip, the dose–response curve was built up measuring the 4-NP decoloration ($D\%$, see equation below), after 15 min of incubation, against increasing amounts of 4-NP.

$$D (\%) = \left(\frac{Abs_{t_0} - Abs_{t_{15}}}{Abs_{t_0}} \right) \times 100 \quad (2)$$

3. Results and Discussion

3.1. μ -Tip-Surfaces Nanodecoration

The aim of this work was the development of a reusable and smart nano-catalyst system for the monitoring and degradation of 4-NP. One-milliliter laboratory μ -tips (μ -T) were modified with a PDA film and subsequently decorated with AuNPs, AgNPs, and a bimetallic Au@AgNPs nanocomposite, respectively, and the tips catalytic performance were evaluated against 4-NP reduction (Figure 1). Dopamine (DA) and metal-precursors concentrations, pH, growth time of both the polymer and the nanoparticles (see Section 2.2) were selected according to our group's previous works [13,14]. In brief, the formation of the PDA thin-film onto the μ -T surface was achieved through a DA polymerization in mild alkaline condition; the resulting polymer, thanks to its redox-active chemistry, allowed the MNPs' (AuNPs and AgNPs) growth and anchorage. The PDA chemistry allows a strong adhesivity permitting an in-situ nanocomposite formation onto different surfaces. Then, exploiting the PDA features, reproducible nanometallic-based films were obtained onto several substrates (Pasteur pipette, Eppendorf, ELISA plate, cuvette, tips, etc.) composed of different materials (glass, polyethylene terephthalate, etc.) (Figure 1).

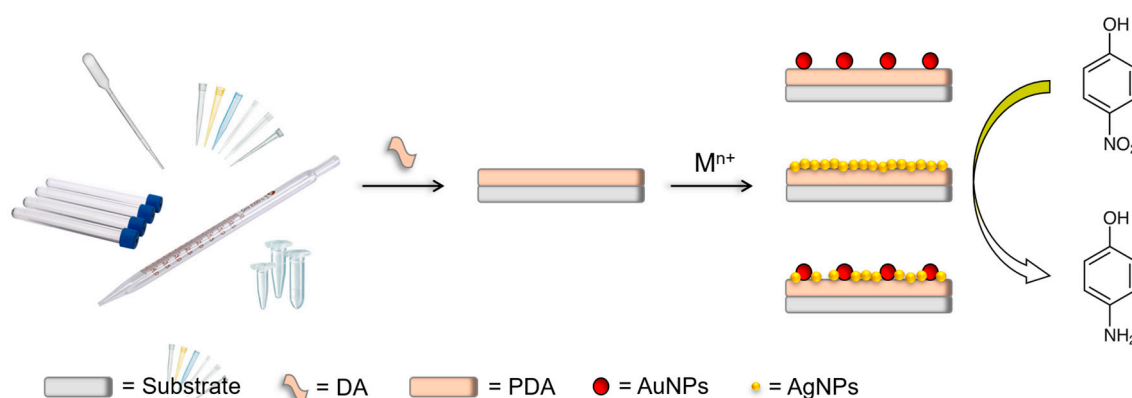


Figure 1. Graphical schematization of lab-devices nanodecoration.

3.2. Reduction of 4-Nitrophenol by Using Nanodecorated μ -Tips

As illustrated in Figure 2, the 4-NP reduction by the nanodecorated μ -Tips occurs in three main steps: (i) Reaction mix absorbance reading at time zero ($\lambda = 400$ nm); (ii) reaction mix suction in the μ -Tips and incubation (15 min), (iii) reacted mix color decay reading ($\lambda = 400$ nm).

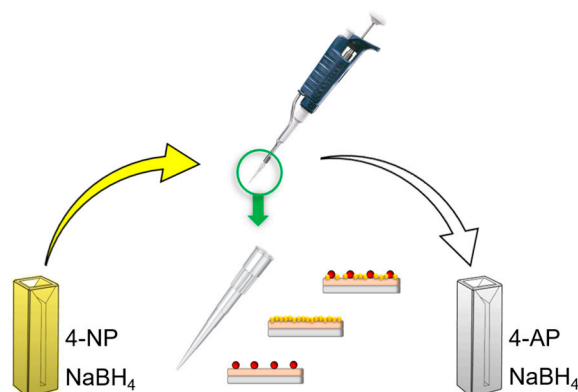


Figure 2. Schematization of the 4-NP reduction at 4-AP, associated with a colorimetric decay, driven by the catalytic action of the nanodecorated μ -Tips.

As reported in Figure 3a, it is possible to notice how in the same reaction conditions, the reduction rate of the three different nanodecorated μ -Tips were significantly different. Noteworthy, by using the undecorated polypropylene and PDA decorated μ -Tips, no discoloration occurs, confirming the catalytic role of the nanodecorated surfaces towards the 4-NP reduction (Figure 3a). Among the different nanodecorated μ -Tips the μ -T@Au@Ag result the most catalytic, followed by the μ -T@Ag and the μ -T@Au. The μ -T@Au@Ag allows the 4-NP complete reduction (discoloration) in 25 min.

The obtained data result in being totally in accordance with the literature, where it was demonstrated how multi-metallic nanodispersions improves reaction rates compared to single metals. Besides, it is well recognized how the catalytic activity towards the 4-NPs reduction is strictly related to the size, shape, and electron density of the employed nanomaterials [7]. In the case of the μ -T@Au@Ag, it is noticeable that the catalytic performance of the μ -T@Au@Ag is ascribable to the catalyst behavior of the Au and AgNPs (Figure 3a). In our case, for the μ -T@Au@Ag, the superior catalytic performance can be ascribed to the nano Au and Ag catalytic synergistic action; nevertheless, in order to better understand the Au and Ag role, an accurate modeling and parameterization of the kinetic curves is required.

Finally, to study the 4-NP concentration effect on the catalytic reaction, and to obtain quantitative monitoring of the 4-NP decay, dose–response curves in the range of 50–500 μ M were built-up with the nanodecorated μ -Tips (Figure 3b). As expected, the μ -Tips previously observed catalytic behaviors results resumed in the dose–response curves' slopes (see Table 1), where the slope obtained with the μ -T@Au@Ag resulted in being the highest, followed by the μ -T@Ag and the μ -T@Au. As expected, no dose–response curve was obtained with the PDA-modified μ -Tip. The proposed devices result usable up to 10 consecutive 'measures' ensuring the same catalytic activity (RSD \leq 5%), demonstrating a significant advantage compared to MNPs-based catalysis in colloidal solutions. The devices are storable at room temperature for one month without significant loss in the catalytic activity.

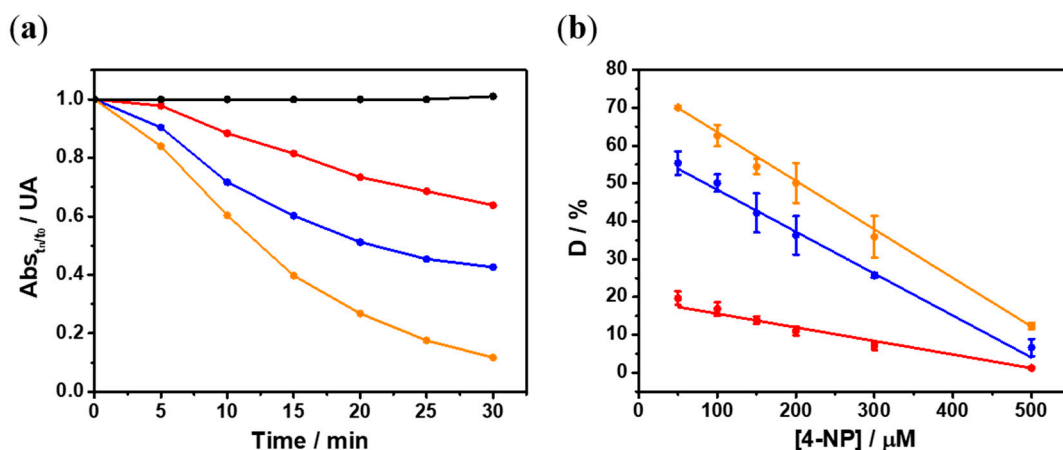


Figure 3. (a) Kinetic curves of 4-NP (100 μM) reduction at 4-AP in the presence of 0.01 M NaBH_4 by using the $\mu\text{-T@PDA}$ (black curve), $\mu\text{-T@Au}$ (red curve), $\mu\text{-T@Ag}$ (blue curve), and $\mu\text{-T@Au@Ag}$ (orange curve). (b) Dose–response curves of 4-NP carried out in presence of 0.01 M NaBH_4 by using the $\mu\text{-T@Au}$ (red curve), $\mu\text{-T@Ag}$ (blue curve), and $\mu\text{-T@Au@Ag}$.

Table 1. Dose–response curve parameter obtained with the $\mu\text{-T@Au}$, $\mu\text{-T@Ag}$, and $\mu\text{-T@Au@Ag}$.

$\mu\text{-Tip}$	Concentration Range (μM)	Linear Equation	Slope	R^2
$\mu\text{-T@Au@Ag}$	50–500	$y = -0.13 (0.00) x + 76.40 (0.30)^1$	−0.13	0.999
$\mu\text{-T@Ag}$	50–500	$y = -0.11 (0.01) x + 59.47 (1.62)^1$	−0.11	0.998
$\mu\text{-T@Au}$	50–500	$y = -0.04 (0.00) x + 19.18 (0.95)^1$	−0.04	0.985

¹ All the dose response curve was performed in triplicates (n = 3).

4. Conclusions

Here, a nanodecoration strategy to modify laboratory $\mu\text{-tips}$ has been proposed for the first time. The proposed procedure allows decorating $\mu\text{-tips}$ surfaces with AuNPs, AgNPs and their nanocomposites. The superior catalytic activity of the bimetallic films (t@PDA@Au@Ag) for the 4-NP reduction was demonstrated. The here-proposed lab-on-a-tip catalyzer results reusable (up to 10 times), elegantly overcoming the colloidal MNPs limitations, also ensuring a 4-NP quantitatively monitoring. The here-proposed nanodecorated films proved to be versatile and potentially usable on different supports allowing tailored nanodecorations, proposing themselves as new and useful analytical tools potentially suitable for catalysts and biosensors developments.

References

- Della Pelle, F.; Compagnone, D. Nanomaterial-Based Sensing and Biosensing of Phenolic Compounds and Related Antioxidant Capacity in Food. *Sensors* **2018**, *18*, 462, doi:10.3390/s18020462.
- Della Pelle, F.; Scroccarello, A.; Sergi, M.; Mascini, M.; Del Carlo, M.; Compagnone, D. Simple and rapid silver nanoparticles based antioxidant capacity assays: Reactivity study for phenolic compounds. *Food Chem.* **2018**, *256*, 342–349, doi:10.1016/j.foodchem.2018.02.141.
- Della Pelle, F.; Vilela, D.; González, M.C.; Lo Sterzo, C.; Compagnone, D.; Del Carlo, M.; Escarpa, A. Antioxidant capacity index based on gold nanoparticles formation. Application to extra virgin olive oil samples. *Food Chem.* **2015**, *178*, 70–75, doi:10.1016/j.foodchem.2015.01.045.
- Della Pelle, F.; Sergi, M.; Del Carlo, M.; Compagnone, D.; Escarpa, A. Gold Nanoparticles-based Extraction-Free Colorimetric Assay in Organic Media: An Optical Index for Determination of Total Polyphenols in Fat-Rich Samples. *Anal. Chem.* **2015**, *87*, 6905–6911, doi:10.1021/acs.analchem.5b01489.
- Della Pelle, F.; Scroccarello, A.; Scarano, S.; Compagnone, D. Silver nanoparticles-based plasmonic assay for the determination of sugar content in food matrices. *Anal. Chim. Acta* **2019**, *1051*, 129–137, doi:10.1016/j.aca.2018.11.015.
- Yu, L.; Li, N. Noble metal nanoparticles-based colorimetric biosensor for visual quantification: A mini review. *Chemosensors* **2019**, *7*, doi:10.3390/chemosensors7040053.

7. Berahim, N.; Basirun, W.; Leo, B.; Johan, M. Synthesis of Bimetallic Gold-Silver (Au-Ag) Nanoparticles for the Catalytic Reduction of 4-Nitrophenol to 4-Aminophenol. *Catalysts* **2018**, *8*, 412, doi:10.3390/catal8100412.
8. Choi, Y.; Choi, M.J.; Cha, S.H.; Kim, Y.S.; Cho, S.; Park, Y. Catechin-capped gold nanoparticles: Green synthesis, characterization, and catalytic activity toward 4-nitrophenol reduction. *Nanoscale Res. Lett.* **2014**, *9*, 1–8, doi:10.1186/1556-276X-9-103.
9. Wang, J.G.; Hua, X.; Li, M.; Long, Y.T. Mussel-inspired polydopamine functionalized plasmonic nanocomposites for single-particle catalysis. *ACS Appl. Mater. Interfaces* **2017**, *9*, 3016–3023, doi:10.1021/acsami.6b14689.
10. Kumar, S.; Sharma, R.K. Work Function Based Catalytic Activity of Metallic Nanoparticles for Dye Degradation. *Catal. Lett.* **2019**, doi:10.1007/s10562-019-02744-4.
11. Baruah, D.; Goswami, M.; Yadav, R.N.S.; Yadav, A.; Das, A.M. Biogenic synthesis of gold nanoparticles and their application in photocatalytic degradation of toxic dyes. *J. Photochem. Photobiol. B Biol.* **2018**, *186*, 51–58, doi:10.1016/j.jphotobiol.2018.07.002.
12. Kästner, C.; Thünemann, A.F. Catalytic Reduction of 4-Nitrophenol Using Silver Nanoparticles with Adjustable Activity. *Langmuir* **2016**, *32*, 7383–7391, doi:10.1021/acs.langmuir.6b01477.
13. Scroccarello, A.; Della Pelle, F.; Ferraro, G.; Fratini, E.; Tempera, F.; Dainese, E.; Compagnone, D. Plasmonic active film integrating gold/silver nanostructures for H₂O₂ readout. *Talanta* **2021**, *222*, 121682, doi:10.1016/j.talanta.2020.121682.
14. Scroccarello, A.; Della Pelle, F.; Fratini, E.; Ferraro, G.; Scarano, S.; Palladino, P.; Compagnone, D. Colorimetric determination of polyphenols via gold nanoseeds decorated polydopamine film. *Microchim. Acta* **2020**, *187*, 1–10, doi:10.1007/s00604-020-04228-4.

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



© 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).