



Aalborg Universitet

AALBORG UNIVERSITY
DENMARK

Making Transparent Er³⁺-Yb³⁺ Ions Doped Oxyfluoride Glass-Ceramics with Enhanced Luminescence via heat-treatment

Li, Zhencai; Yue, Yuanzheng

Publication date:
2022

[Link to publication from Aalborg University](#)

Citation for published version (APA):

Li, Z., & Yue, Y. (2022). *Making Transparent Er³⁺-Yb³⁺ Ions Doped Oxyfluoride Glass-Ceramics with Enhanced Luminescence via heat-treatment*. Poster presented at The International Year of Glass Symposium, Aalborg, Denmark.

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.




Making Transparent Er³⁺-Yb³⁺ Ions Doped Oxyfluoride Glass-Ceramics with Enhanced Luminescence via heat-treatment

AALBORG
UNIVERSITET

Zhencai Li*, Yuanzheng Yue

Department of Chemistry and Bioscience, Aalborg University, Aalborg, Denmark


*Presenting and contacting author. E-mail: zhli@bio.aau.dk

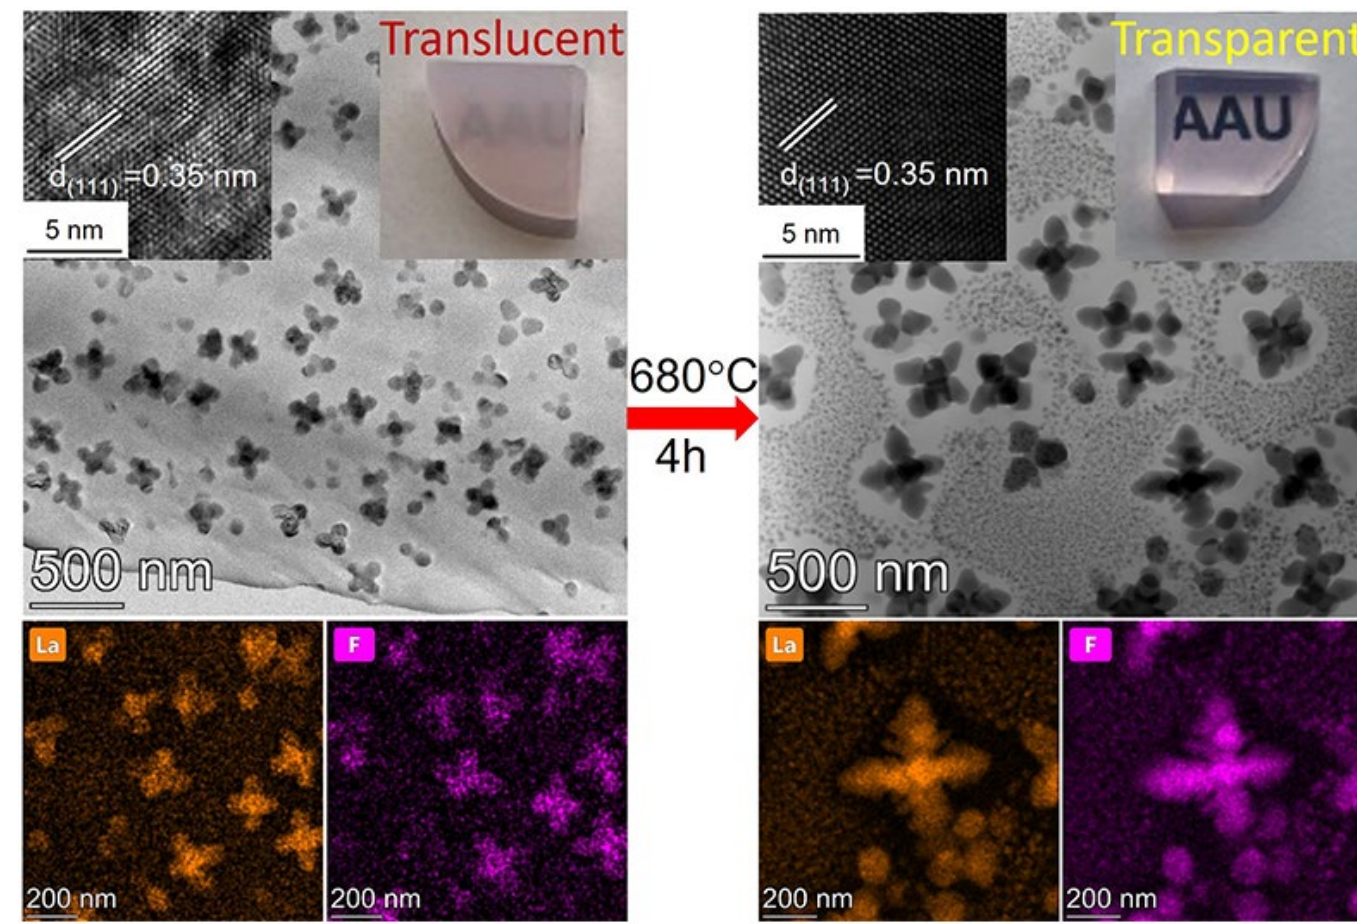

Abstract

It is known that the optical transparency of an oxide glass decreases with an increase of the size and fraction of crystals in the glass during heat-treatment (HT). Here we report an opposite scenario, where a translucent Er³⁺-Yb³⁺ doped oxyfluoride glass-ceramic (GC) becomes transparent with increasing crystal size and crystallinity. Specifically, in the heat-treated GC samples, we observed that the growth of the existing Ba₂LaF₇ crystals and particularly the formation of small spherical Ba₂LaF₇ crystals greatly enhanced the light transmittance. The results show that the composition of the residual glass phase was altered (e.g., depletion of F⁻ and La³⁺) in the way that the differences in refractive index between the glass matrix and the crystals are greatly reduced. As a consequence, the light scattering of the heat-treated GC was suppressed, and hence, the derived GC became transparent. In addition, a proper HT can also enhance the luminescence of the studied GC system.

Light Transmittance and Up-conversion (UC) Luminescence

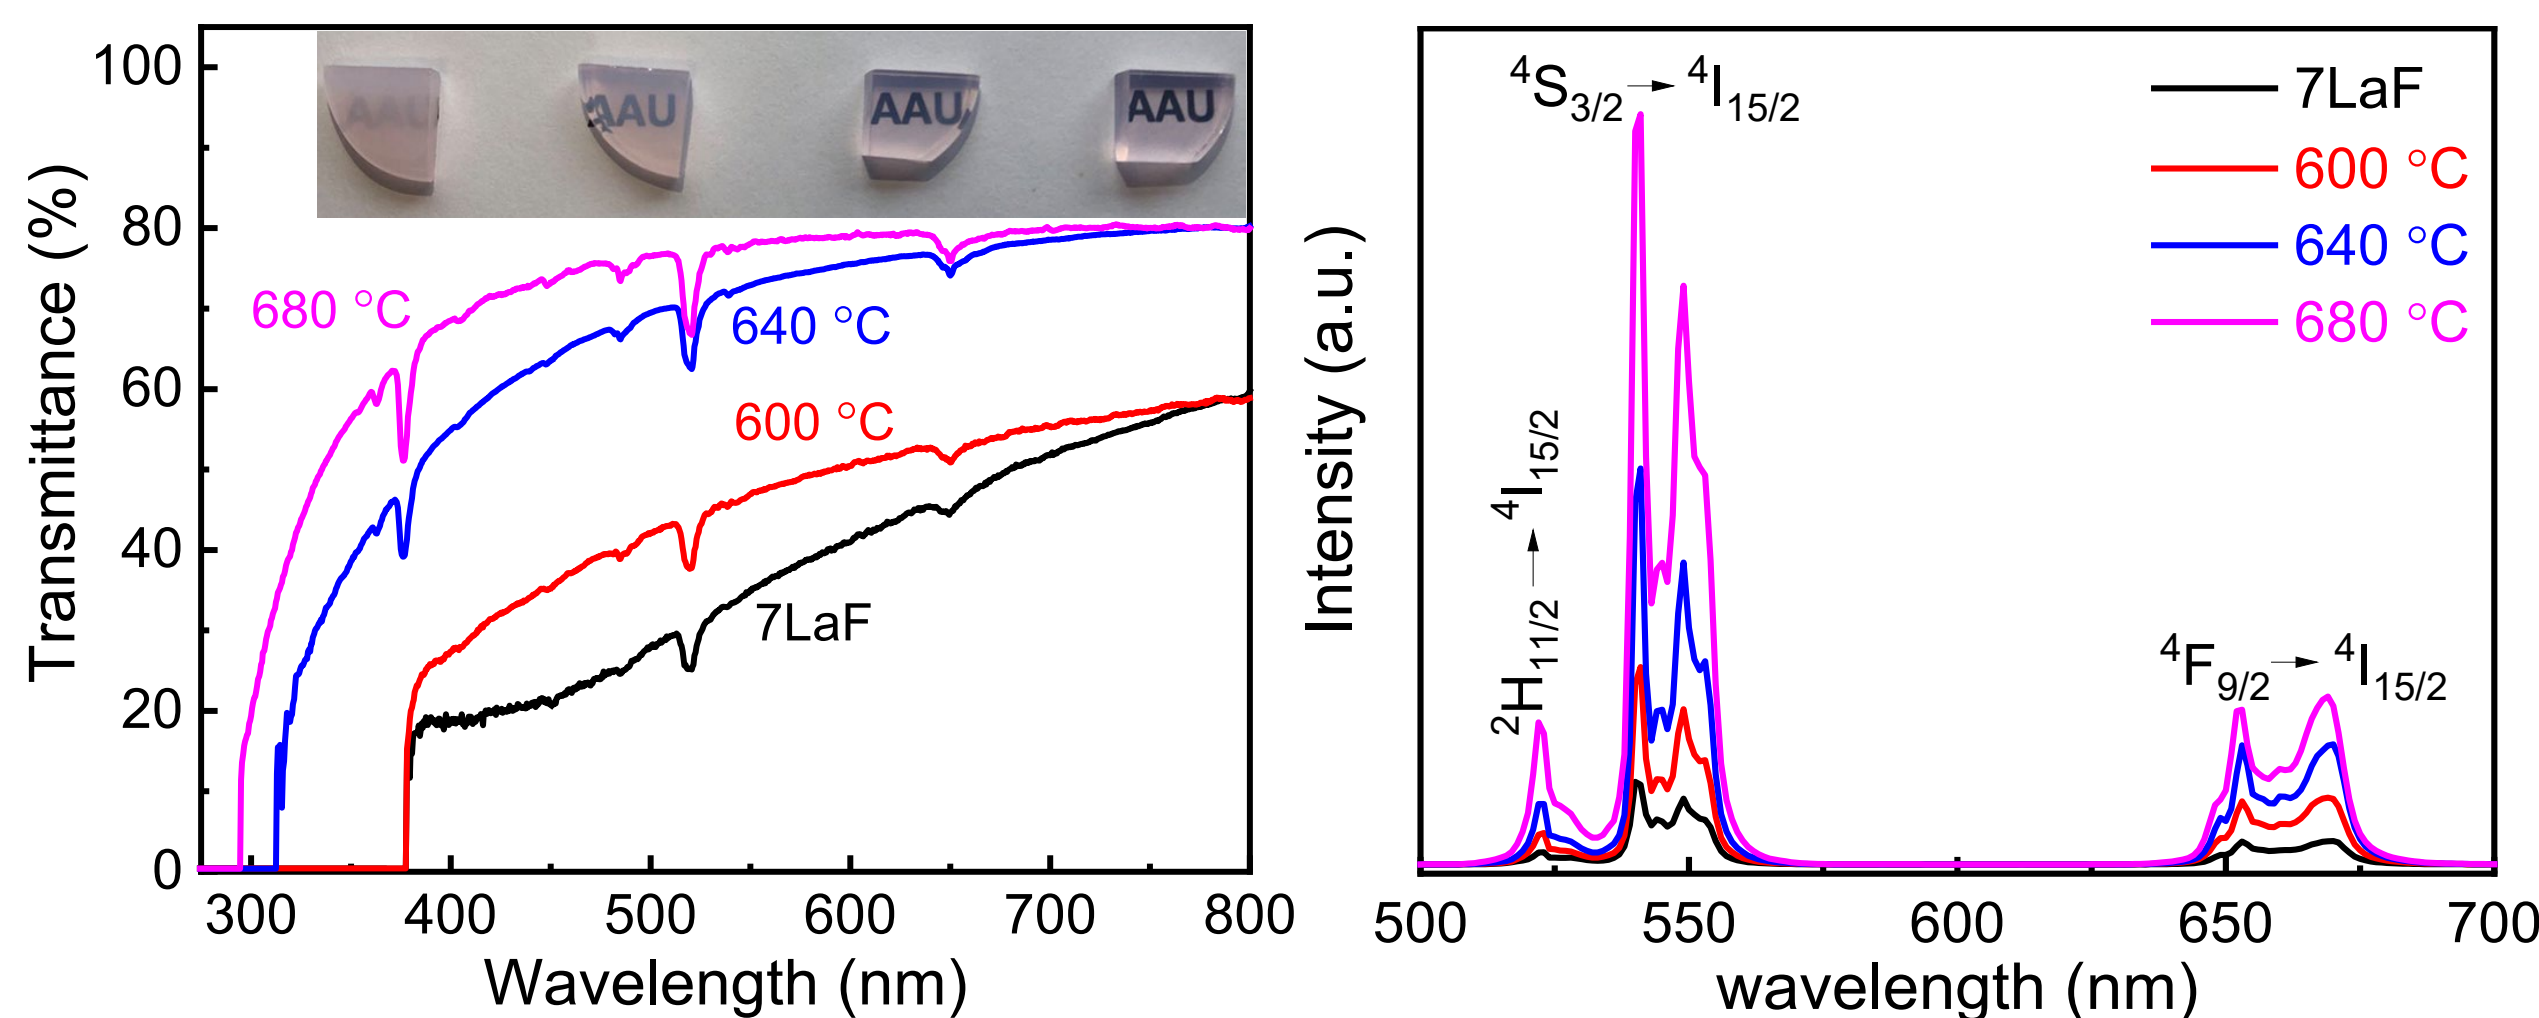


Light transmittance and UC Luminescence:

- Light transmittance increases upon HT.
- UC luminescence is 9 times higher than the 7LaF sample.


➤ **Two conditions for producing high transparent oxyfluoride GCs**

1. Nanocrystals should be considerably smaller (< 50 nm) than the wavelength of visible light
2. The difference in refractive index between nanocrystals and residual glass phase should be minimized (< 0.01) ★


DSC, XRD and Raman spectroscopy Characterizations

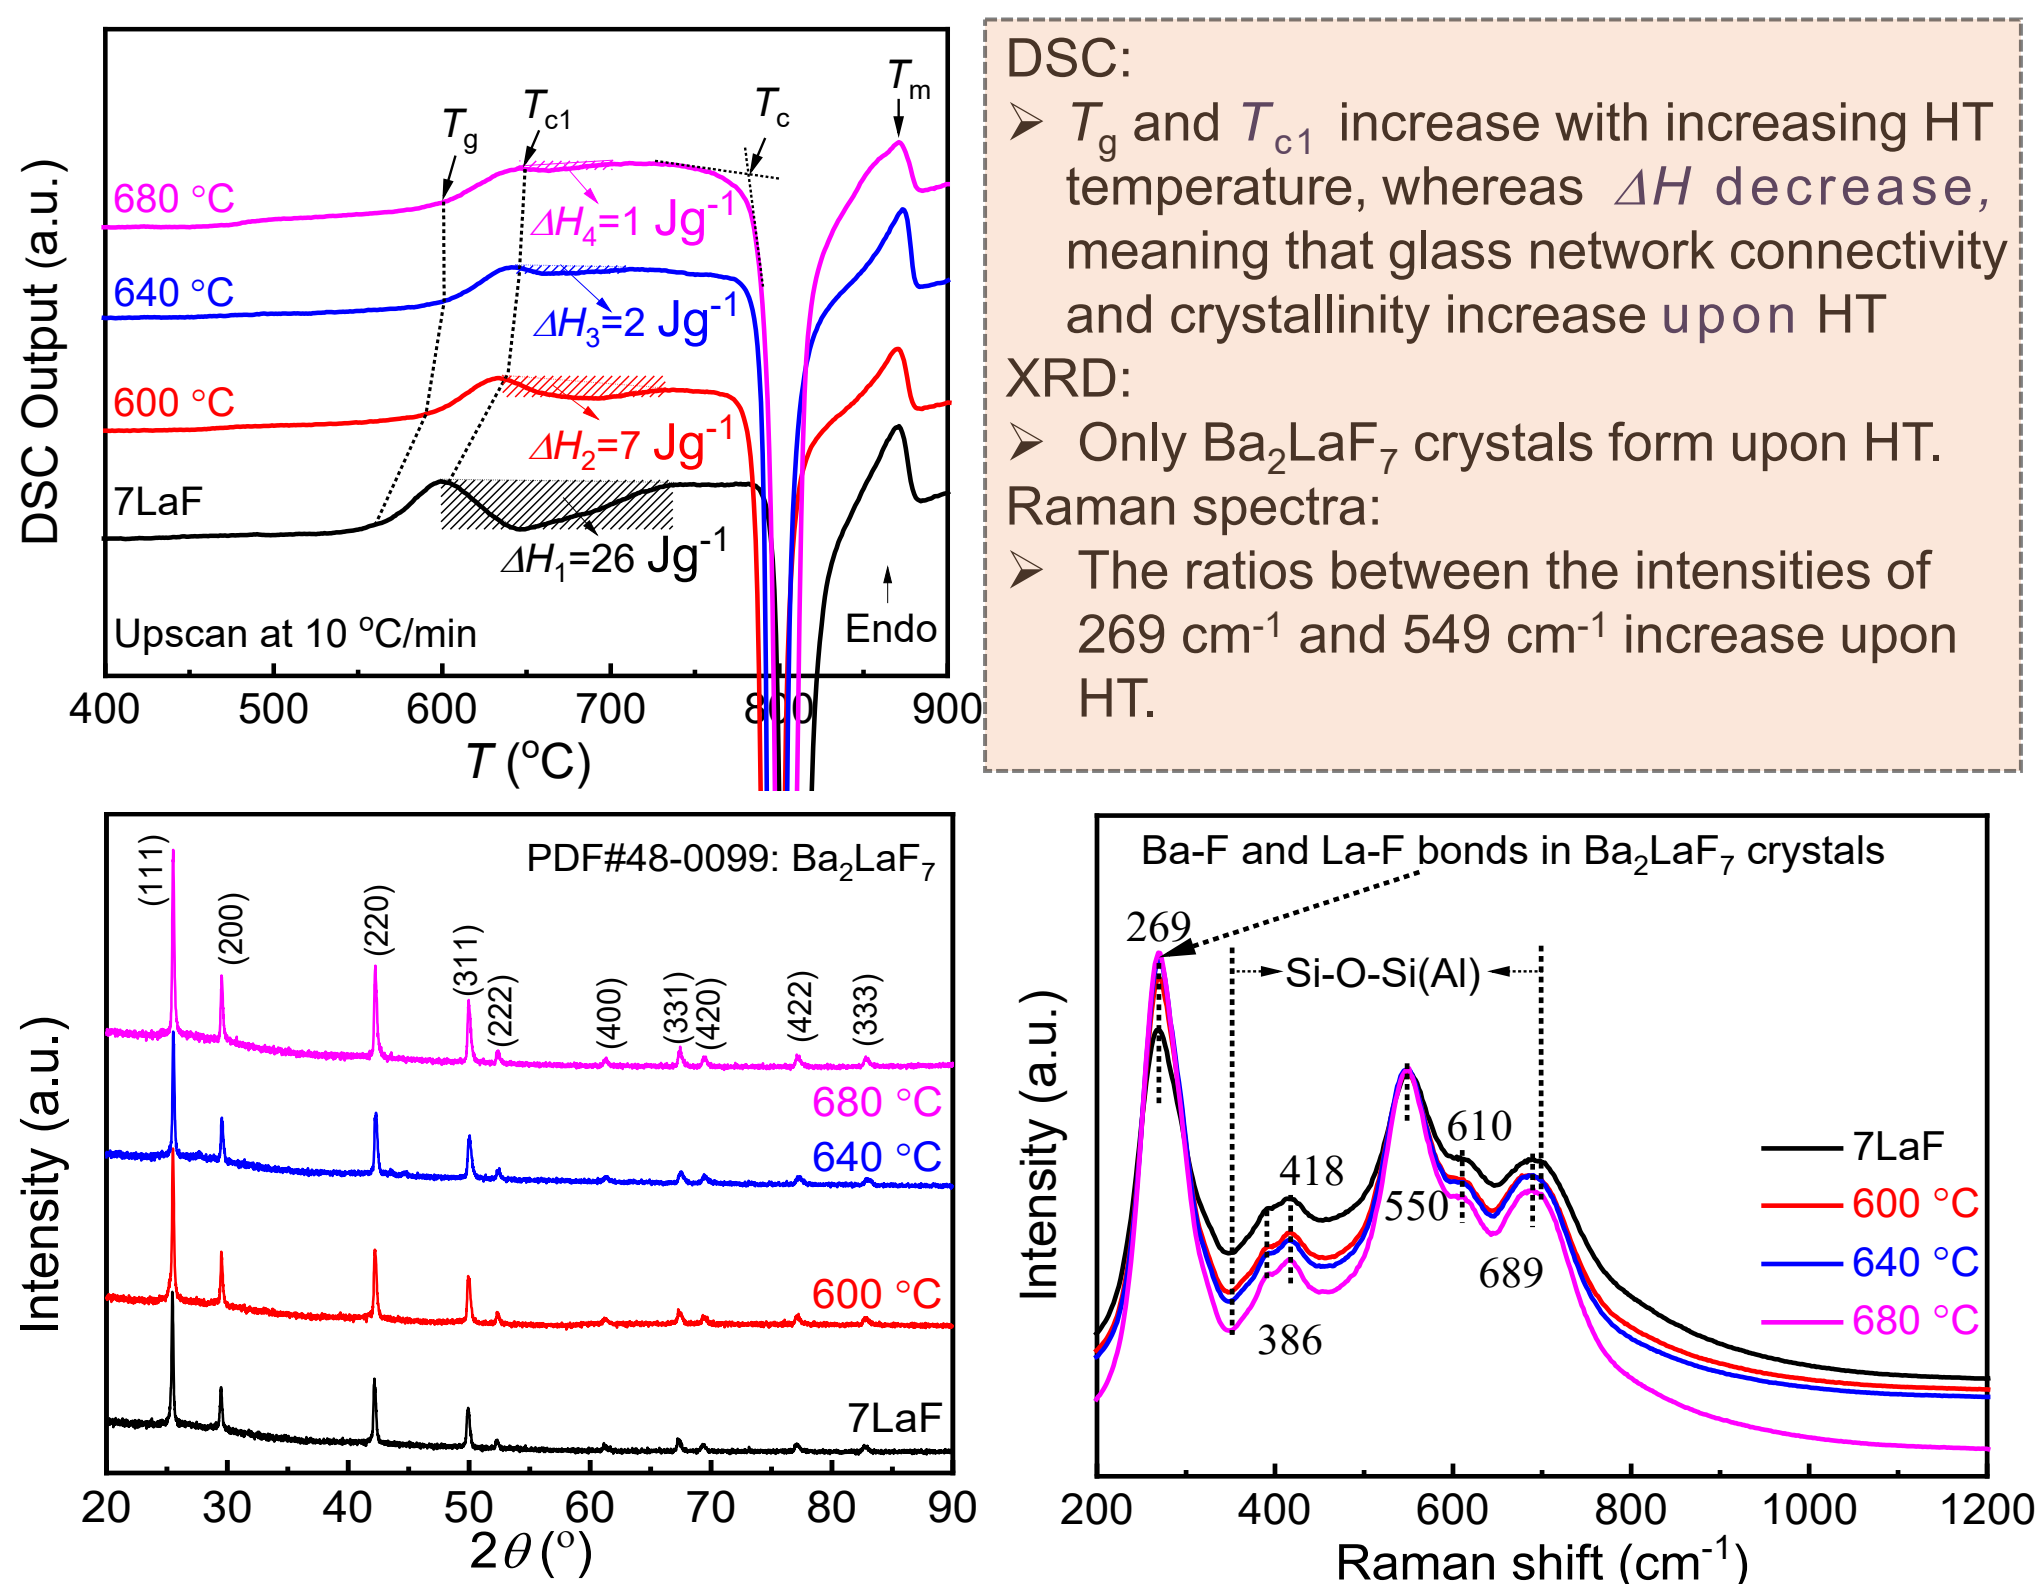

Refractive Index and EDS Mapping Characterizations

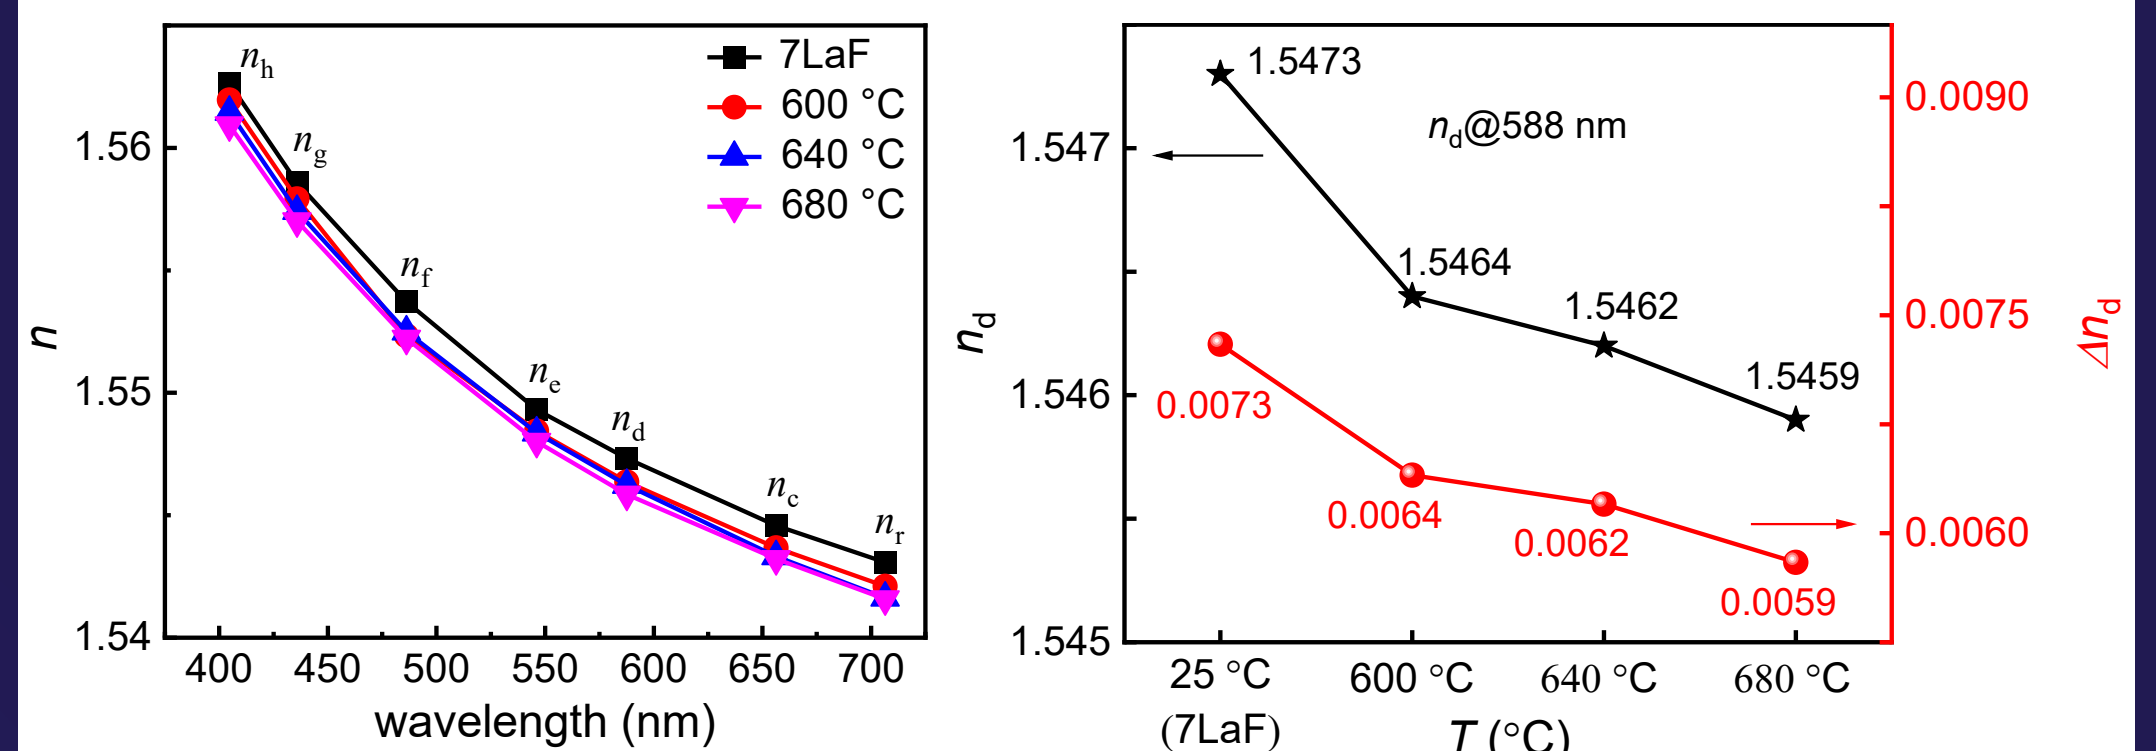

HAADF STEM and Elemental Mapping

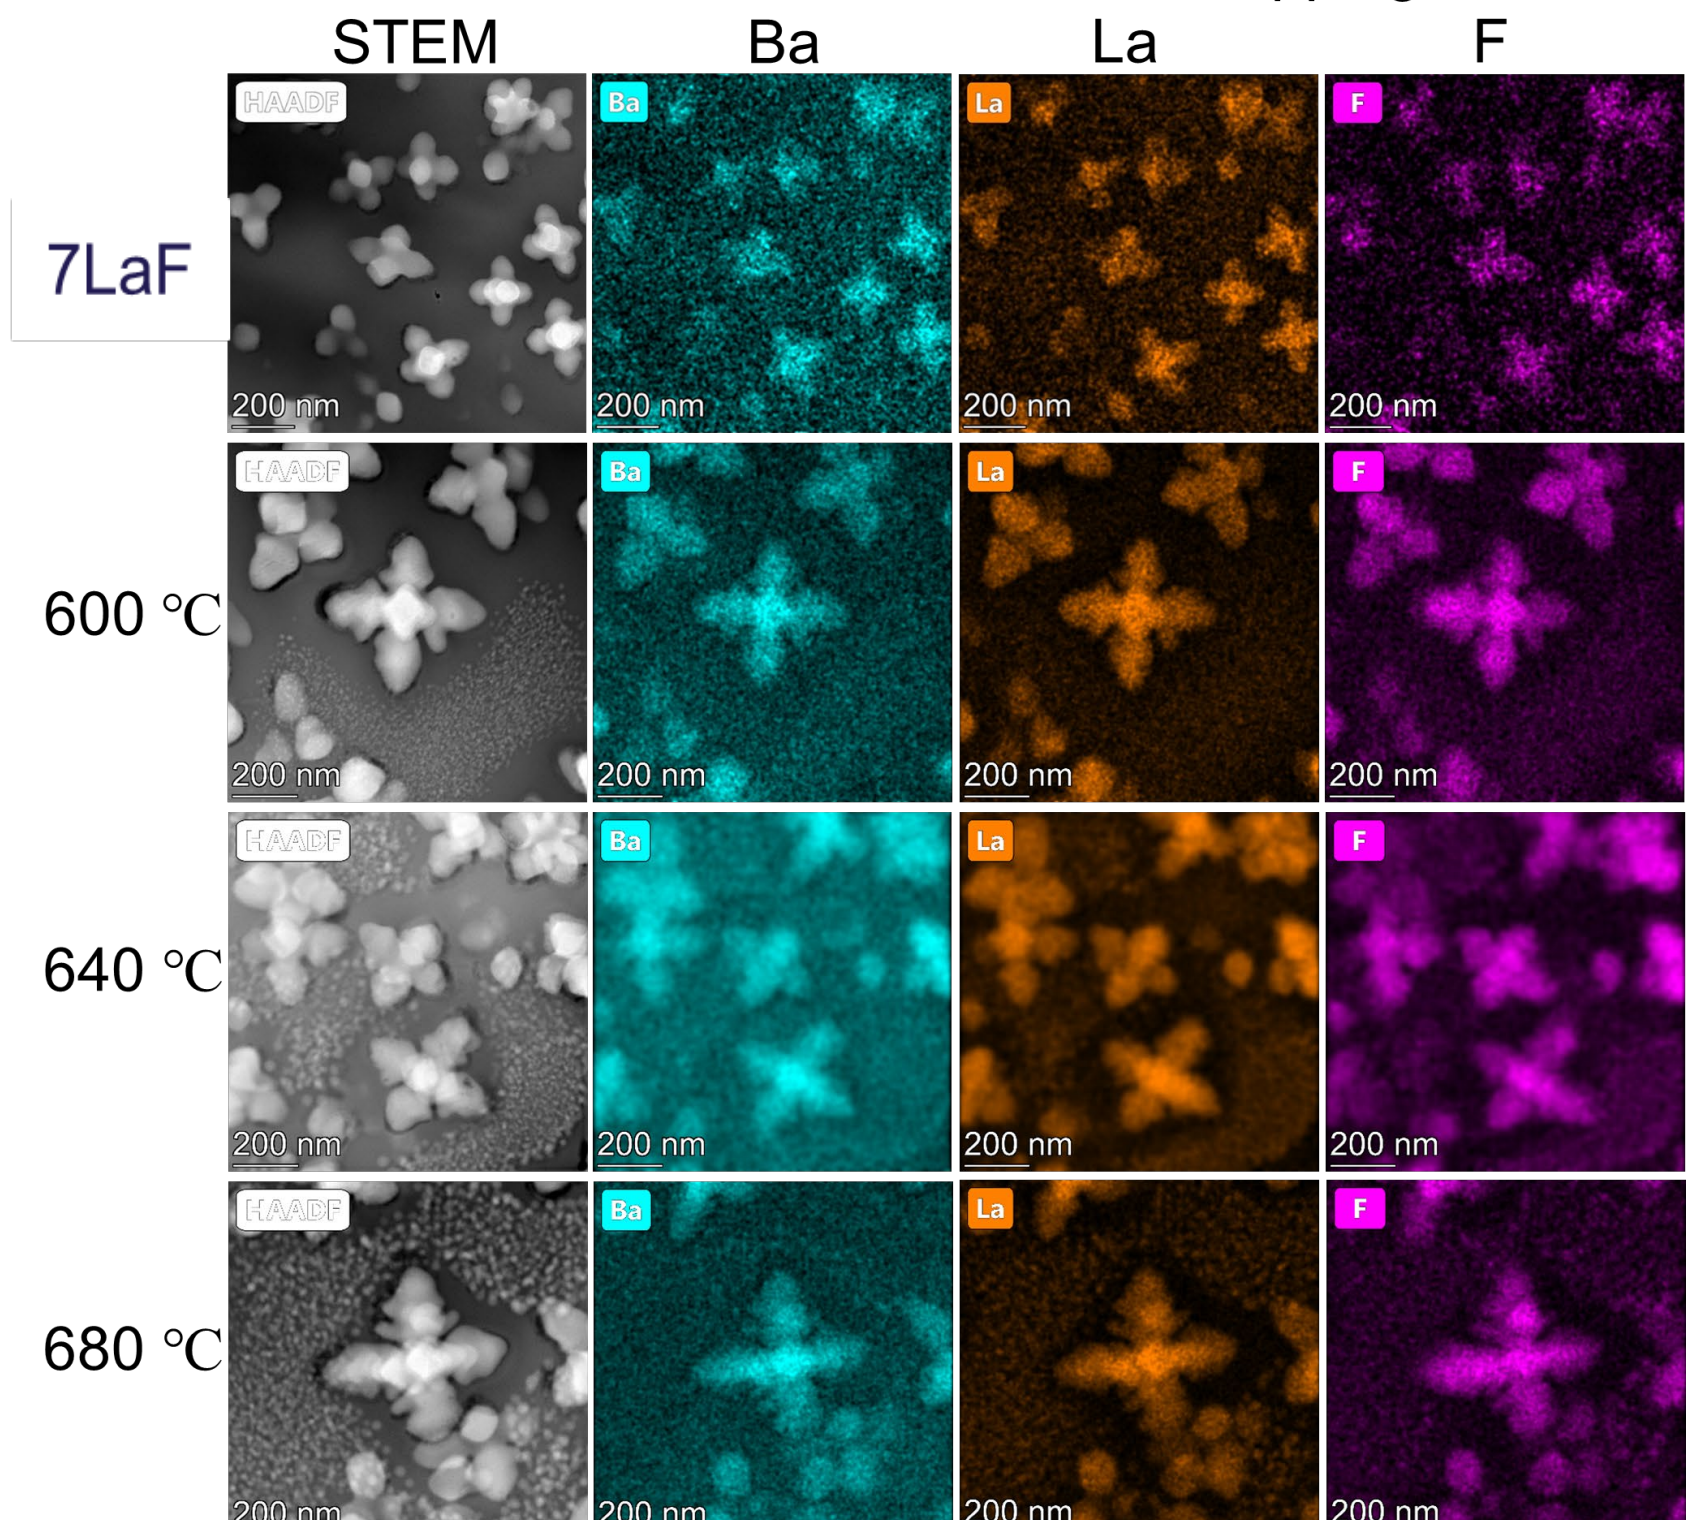

Conclusions

- A translucent Er³⁺-Yb³⁺ doped oxyfluoride GC containing large flower-like Ba₂LaF₇ crystals is prepared via melt-quenching.
- The translucent oxyfluoride GC becomes transparent with increasing the crystal size and crystallinity as a result of HT, which is attributed to the suppression of the light scattering.
- The derived transparent GCs show strong UC luminescence.

Acknowledgements

This work is supported by the China scholarship council (CSC, No. 201808530502), the National Natural Science Foundation of China (No. 51862020), Shandong Province (ZR2020ME025), and the Taishan Youth Scholar Project of Shandong Province (tsqn202103098). We are grateful to Dr. Xiaoming Zhang and Jingbo Yu for conducting refractive index measurements.

Refractive index (n):

- n decreases upon HT
- nd of Ba₂LaF₇ crystal is 1.54
- nd difference (Δnd) is 0.0059, which is < 0.01

STEM and EDS Mapping

- Flower-like and tiny Ba₂LaF₇ crystals grow with HT.
- Most La³⁺, F⁻ ions, and few Ba²⁺ ions diffuse from glass phase to Ba₂LaF₇ upon HT.