

8-1-2021

The Effects of Ceria Loading on Three-Way Catalysts for Passive SCR Operation

Calvin R. Thomas
Oak Ridge National Laboratory

Josh A. Pihl
Oak Ridge National Laboratory

Vitaly Y. Prikhodko
Oak Ridge National Laboratory

Michelle K. Kidder
Oak Ridge National Laboratory

Jochen A. Lauterbach
University of South Carolina - Columbia, lauteraj@cec.sc.edu

See next page for additional authors

Follow this and additional works at: https://scholarcommons.sc.edu/eche_facpub

 Part of the [Biochemical and Biomolecular Engineering Commons](#)

Publication Info


Catalysis Communications, Volume 156, 2021, pages 106308-

© 2021 The Author(s). Published by Elsevier B.V. This is an open access article under the [CC BY-NC-ND license](#).

This Article is brought to you by the Chemical Engineering, Department of at Scholar Commons. It has been accepted for inclusion in Faculty Publications by an authorized administrator of Scholar Commons. For more information, please contact dillarda@mailbox.sc.edu.

Author(s)

Calvin R. Thomas, Josh A. Pihl, Vitaly Y. Prikhodko, Michelle K. Kidder, Jochen A. Lauterbach, and Todd J. Toops



Short communication

The effects of ceria loading on three-way catalysts for passive SCR operation

Calvin R. Thomas^a, Josh A. Pihl^a, Vitaly Y. Prikhodko^a, Michelle K. Kidder^a,
Jochen A. Lauterbach^b, Todd J. Toops^{a,*}

^a Oak Ridge National Laboratory, 1 Bethel Valley Rd, Oak Ridge, TN 37830, United States of America

^b University of South Carolina, Columbia, SC 29208, United States of America



ABSTRACT

Passive SCR systems, which employ both a three-way catalyst and SCR catalyst, are effective for the reduction of nitrogen oxide (NO_x) emissions from lean burn gasoline engines. However, questions remain regarding the effect of three-way catalyst formulations on their performance in these systems. Here, Pd/CeO_x/Al₂O₃ catalysts with variable CeO_x loading were synthesized, characterized, and evaluated to determine the effects of CeO_x on catalyst performance. While a small amount of ceria was beneficial for promoting essential reactions, excess ceria was detrimental due to the increase in oxygen storage capacity. Additionally, insights into potential reaction pathways for NH₃ production were determined.

1. Introduction

Passive selective catalytic reduction (pSCR) is a potential approach for controlling nitrogen oxide (NO_x) emissions from lean burn gasoline engines [1]. These engines are more efficient than conventional, stoichiometrically operated engines [2]. However, because of the excess oxygen in the exhaust, while the engine is operating lean, it is not possible to reduce NO_x in the exhaust with a traditional three-way catalyst (TWC). Passive SCR employs both a close coupled TWC and a downstream SCR catalyst. The system works by periodically operating the engine in a fuel-rich regime. This provides the TWC with enough reductants to reduce the NO_x in the exhaust to ammonia (NH₃). This NH₃ is stored on a downstream SCR catalyst, typically a Cu-exchanged zeolite. During fuel-lean operation, the stored NH₃ is used to reduce the NO_x in the exhaust. This approach avoids the need for additional hardware typically used in diesel SCR applications, which require urea storage tanks and injectors.

While much research has been conducted to optimize TWC activity for traditional stoichiometric operation, commercially available formulations have not yet been designed around the needs of a pSCR system. Three-way catalyst components can have a significant effect on the production of NH₃ in a pSCR system. Many of these differences have been investigated in previous literature. Adams et al. [3] investigated the differences in NH₃ production when adding barium or ceria to the catalyst formulation, showing that ceria addition is useful when CO is used as a reductant in NH₃ production. Another study by Adams et al.

[4] investigated the effectiveness of Pd-based vs. Pt-based catalysts for the operation of pSCR, showing that Pd was more effective due to its increased activity for the water-gas shift reaction at lower temperatures. Water-gas shift is important for pSCR since it converts the criteria pollutant CO to CO₂ and H₂, mitigating CO emissions during fuel-rich operation.

Ceria is often used in commercial TWCs for several beneficial attributes [5–7], including oxygen storage and promotion of the water-gas shift reaction. Oxygen storage is a beneficial attribute of TWCs on stoichiometrically operated gasoline engines because it allows for the oxidation of CO and HCs during brief oscillations into rich operation. Ceria loading also promotes water-gas shift, which is highly beneficial in a pSCR system because it aids in the production of NH₃ and, as previously mentioned, mitigates CO emissions [8,9]. This increase in water-gas shift reaction activity should plateau at fairly low ceria loading because the reaction occurs at the interface between the ceria and precious metal [10]. However, in a pSCR system, high levels of oxygen storage inhibit the reduction of the catalyst at the beginning of the rich phase, preventing NH₃ formation for a significant portion of the rich phase, as shown in a previous work [11]. This effect should scale with the amount of ceria in the formulation. To balance these effects, there will likely be an optimum ceria loading for NH₃ production. No research to date has isolated these individual effects of ceria on TWC performance in pSCR.

In the present work, model Pd/CeO_x/Al₂O₃ catalysts have been synthesized to investigate the effects of variable ceria loading on TWC

* Corresponding author.

E-mail address: toopstj@ornl.gov (T.J. Toops).

<https://doi.org/10.1016/j.catcom.2021.106308>

Received 25 November 2020; Received in revised form 16 March 2021; Accepted 18 March 2021

Available online 25 March 2021

1566-7367/© 2021 The Author(s).

Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license

(<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

performance in pSCR. Pd was used as the PGM due to its high pSCR performance as reported in previous evaluations [12]. The catalysts have been characterized using BET analysis and x-ray diffraction (XRD), and have been evaluated for their catalytic activity in a flow reactor. The activity measurements were focused on the production of NH₃ using H₂ or CO as a reductant, as well as the production of H₂ from the water-gas shift reaction under cycling conditions. These measurements allowed us to directly track the multiple effects ceria has on the performance of TWCs in pSCR systems.

2. Experimental

2.1. Catalysts preparation

Several model Pd/CeO_x/Al₂O₃ catalysts were synthesized to investigate the effects of Ce loading on several reactions in a pSCR system. The formulations are shown in Table 1. The Pd/CeO_x/Al₂O₃ samples were synthesized with 1 wt% Pd and 0–10 wt% Ce. The model catalysts were synthesized via sequential wet impregnation of Ce then Pd onto a γ-Al₂O₃ support. After each impregnation, the catalysts are calcined in air for 3 h at 650 °C.

2.2. Catalysts characterization

Powder XRD was used to characterize the catalysts synthesized via wet impregnation and identify what crystalline phases were present in each sample. The instrument was a Rigaku Mini Flex II diffractometer using Cu Kα radiation. The calcined powdered catalyst samples were scanned at 2θ values between 10° and 80° to capture all observable peaks in the samples. Additionally, the crystallite size was estimated using the Scherrer equation (Eq. (1)). This equation allows for the estimation of the crystallite size (τ) from the x-ray wavelength (λ), the full width at half maximum of the peak (β), and the Bragg angle of the peak (θ), and K the crystallite geometrical shape (K = 0.9 for sphere).

$$\tau = \frac{K\lambda}{\beta \cos\theta} \quad (1)$$

Additionally, surface area (m² g⁻¹) measurements were conducted on the calcined catalyst samples using a Autosorb-1-C analyzer produced by Quantachrome. Samples were outgassed at 180 °C overnight before analysis. Physisorption isotherms were collected under N₂ gas flow and the surface areas were determined through a multipoint BET analysis.

2.3. Catalysts performance evaluation

The powder catalysts were evaluated in a flow reactor (quartz U-tube). The introduction of gases into the reactor was controlled through several mass flow controllers. Water was introduced into the apparatus through a temperature-controlled bubbler. The temperature of the catalyst was controlled through a furnace surrounding the quartz tube. During the reaction, the catalyst effluent gas was analyzed with an MKS MultiGas 2030HS gas phase Fourier transform infrared (FTIR) spectrometer.

The catalysts were pre-reduced at 550 °C in 1% H₂ and 5% H₂O before being evaluated using the cycling reactive conditions outlined in Table 2. These reactions were used to evaluate each catalyst for the production of NH₃ when H₂ was used as a reductant (H₂ + NO + H₂O), the production of H₂ from the water-gas shift reaction (CO + H₂O), and the production of NH₃ when CO was used as the reductant

Table 1
Model Pd/CeO_x/Al₂O₃ formulations.

Catalyst	1Pd	1Pd 0.5Ce	1Pd 1Ce	1Pd 2Ce	1Pd 5Ce	1Pd 10Ce
Pd Loading	1.0%	1.0%	1.0%	1.0%	1.0%	1.0%
Ce Loading	None	0.5%	1.0%	2.0%	5.0%	10.0%

Table 2

Various feed gas compositions under Rich and Lean reaction conditions.

Phase	H ₂ + NO + H ₂ O		CO + H ₂ O		CO + NO + H ₂ O	
	Rich	Lean	Rich	Lean	Rich	Lean
O ₂ (%)	0	10	0	10	0	10
H ₂ (%)	1	1	0	0	0	0
CO (%)	0	0	1	1	1	1
NO (%)	0.05	0.05	0	0	0.05	0.05
H ₂ O (%)	5	5	5	5	5	5

(CO + NO + H₂O). In each case, 100 mg of catalyst was evaluated using 333 S cm³ min⁻¹ (evaluated at 0 °C, 1 atm) feed gas volume flow rate balanced by Ar. During each reaction, the catalyst was exposed to 5 min of rich operation, where no O₂ was present, and 5 min of lean operation, where there was 10% O₂ in the reactive gas mixture. The effluent gas was diluted to 1 S L min⁻¹ (evaluated at 0 °C, 1 atm) with Ar to improve the time resolution of the FTIR measurements. The performance metrics were calculated during rich operation and averaged across six cycles. Because the system was cycled between lean and rich conditions, the influence of oxygen storage appeared as a delay in the NH₃ production.

3. Results and discussion

The XRD spectra for the Pd/CeO_x/Al₂O₃ catalysts after impregnation and calcination are shown in Fig. 1. The catalysts show diffraction peaks corresponding to PdO, CeO₂, and γ-Al₂O₃. From these diffraction patterns, both PdO and CeO₂ are highly crystalline. At low Ce loadings (0.5–1 wt%), the characteristic peaks of CeO₂ are too broad and their magnitude is too low to determine meaningful crystallite size. As the Ce loading is increased, the CeO₂ diffraction pattern becomes dominant, and the CeO₂ particles become larger, up to a maximum of 11.2 nm for the 1Pd10Ce sample (determined from the peak at 2θ = 29 degrees). However, despite the changing relative magnitude of the Pd diffraction pattern, the crystallite size of Pd does not change significantly as more ceria is added, and the Pd maintains a crystallite size of 20–25 nm for all samples (determined from the peak at 2θ = 34 degrees).

The surface areas of the catalyst samples determined from BET measurements are shown in Table 3. Overall, the surface areas of the catalysts did not significantly change based on Ce loading, with all samples showing values in the 47–58 m² g⁻¹ range. This indicates that the Ce loading does not significantly affect the surface area, and the minor changes in surface area are unlikely to play a large role in catalyst activity.

The rich phase production of NH₃ during H₂ + NO + H₂O exposure over each Ce loading is shown in Fig. 2. Each catalyst shows between 84% and 87% NH₃ yield regardless of temperature or ceria loading. The reason there is little change with respect to ceria loading is likely because the ceria does not play a large role in the reduction of NO by H₂ to form NH₃. This reaction has been shown to occur primarily on the noble metal surface [13]. Because each of these catalysts have sufficient Pd surface area to allow for the reduction to occur, they show similar activity.

Fig. 3a shows the production of H₂ from CO + H₂O exposure. The H₂ production is measured based on the disappearance of H₂O, tracked by gas phase FTIR. Here, there is a significant dependence of H₂ production on the ceria loading, which is consistent with previous literature [10,14]. At 350 °C, the 1Pd catalyst has no discernible activity for the water-gas shift reaction. As more ceria is added to the formulation, there is a significant increase in H₂ production at 350 °C, resulting in a H₂ yield of ~ 0.7 at 10 wt% ceria. However, at elevated temperatures of 450–550 °C, increasing the ceria loading beyond 1–2 wt% has a negative effect on the cycle-averaged production of H₂. This is because, at these temperatures, ceria is highly active for oxygen storage [7]. This leads to an inhibition in the reduction of the catalyst, which is a necessary step for H₂ production to begin. This effect is shown in Fig. 3b, which shows

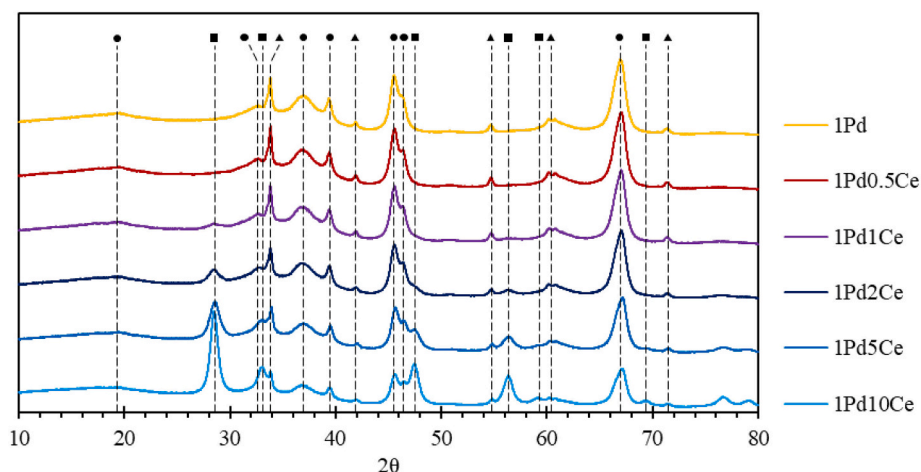


Fig. 1. Powder XRD for Pd/CeO₂/Al₂O₃ catalysts. Diffraction peaks for γ -Al₂O₃ (●), CeO₂ (■), and PdO (▲) are identified and labeled in the diffraction patterns.

Table 3
Catalyst surface areas determined by BET analysis.

Sample	Surface area m ² g ⁻¹
1 Pd	58.1
1Pd-0.5Ce	52.2
1Pd-1Ce	54.9
1Pd-2Ce	54.1
1Pd-5Ce	47.0
1Pd-10Ce	47.6

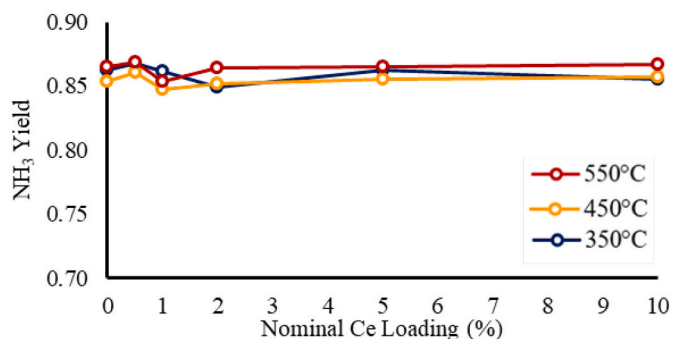


Fig. 2. Rich phase production of NH₃ from NO + H₂ + H₂O during lean/rich cycling operation.

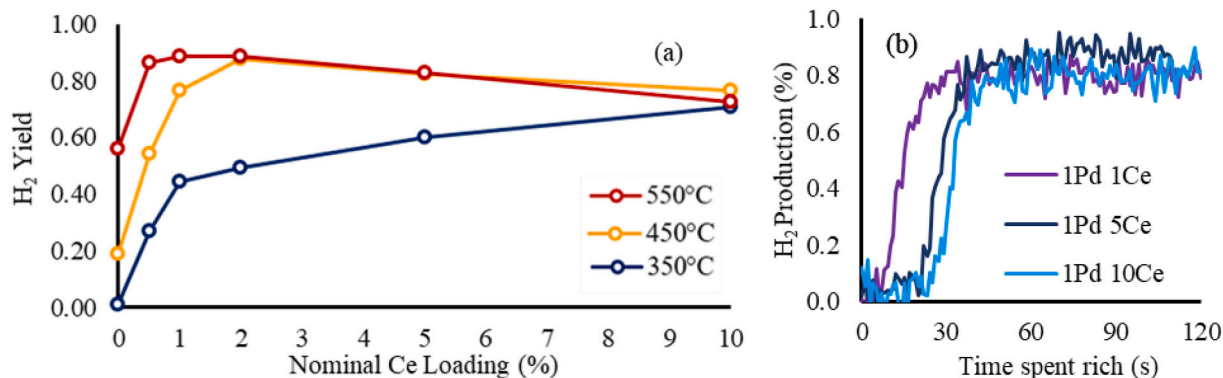


Fig. 3. (a) Rich phase production of H₂ from CO + H₂O during lean/rich cycling operation, (b) time delay in H₂ production at 550 °C after switching to rich operation.

the rate of H₂ production as a function of time since the beginning of rich operation. The 1Pd—10Ce catalyst sample takes ~20 s longer to begin producing H₂ than the 1Pd—1Ce catalyst sample at 550 °C. Because of this delay, the presence of excess oxygen storage beyond 1–2 wt% ceria has a negative effect on the overall generation of H₂ from the water-gas shift reaction on a TWC.

Fig. 4 shows the production of NH₃ during exposure to CO + NO + H₂O. The trends in this reaction mirrored those of H₂ production quite closely. However, at 350 °C, on the 1Pd catalyst, with no ceria loading, there was still a fractional NH₃ yield of 0.72, when there was negligible water-gas shift activity. Looking at these two reactions together leads to the conclusion that the formation of molecular H₂ is not a necessary step in the production of NH₃ over Pd catalysts. This means that, at least under some conditions, NH₃ production likely occurs through the isocyanate hydrolysis pathway discussed in the literature [15,16]. However, as the ceria content of the catalyst was increased, leading to higher production of H₂, the NH₃ yield also increases notably. Therefore, while it is not strictly necessary to produce H₂, catalysts that enhance the production of molecular H₂ in WGS have a positive impact on the reduction of NO to NH₃. This is further illustrated by looking at higher temperature experiments, where the 1Pd catalyst showed activity for the water-gas shift reaction, and the NH₃ yield increased accordingly. In this reaction, the same detrimental effect of excess oxygen storage was seen at 450 and 550 °C, where ceria content in excess of 2 wt% prevented the reduction of the catalyst and outweighed the beneficial effects.

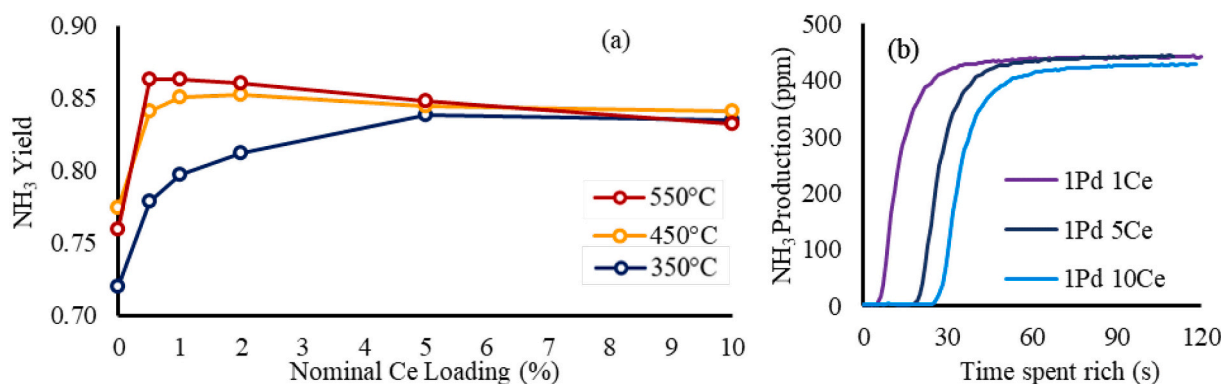


Fig. 4. (a) Rich phase production of NH₃ from CO + NO + H₂O during lean/rich cycling operation, (b) time delay in NH₃ production at 550 °C after switching to rich operation.

4. Conclusions

Understanding the fundamental role(s) of each component and promoter in commercially formulated automotive catalysts is an ongoing challenge. This is particularly relevant in the implementation of pSCR, where a catalyst must operate under several reactive conditions effectively. In this work, it was shown that ceria loading does not have a significant effect on the NH₃ production when H₂ is used as a reductant. However, the loading of ceria did have a large impact on the production of H₂ from the water-gas shift reaction. The ceria-free 1Pd catalyst showed no H₂ production at 350 °C, while adding even 0.5 wt% ceria increased the H₂ yield to 25%. Still, the 1Pd catalyst showed high activity to produce NH₃ at 350 °C when CO was used as a reductant despite showing no activity for the water-gas shift reaction at the same temperature. This indicates that it is possible to produce NH₃ over Pd without the formation of molecular H₂, which suggests that, at these low operating temperatures, the isocyanate hydrolysis pathway illustrated in previous literature might play a role. Adding 0.5 wt% Ce allowed for the catalyst to be active for the water-gas shift reaction and greatly improved the NH₃ yield, showing that the production of molecular H₂ is still greatly beneficial to the production of NH₃. However, when more than 2 wt% ceria was added to the catalyst formulation, the overall cycling activity began to suffer at elevated temperatures. This is because the oxygen storage provided by ceria inhibits the reduction of the catalyst, which prevents the formation of NH₃ for a longer period of rich operation under cycling conditions. Based on these results, a ceria loading of 0.5–2 wt% appears to be optimal for TWC formulations intended for use in pSCR applications.

Disclaimer

This manuscript has been authored by UT-Battelle, LLC, under contract DE-AC05-00OR22725 with the US Department of Energy (DOE). The US government retains and the publisher, by accepting the article for publication, acknowledges that the US government retains a nonexclusive, paid-up, irrevocable, worldwide license to publish or reproduce the published form of this manuscript, or allow others to do so, for US government purposes. DOE will provide public access to these results of federally sponsored research in accordance with the DOE Public Access Plan (<http://energy.gov/downloads/doe-public-access-plan>).

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

Funding was provided by the U.S. Department of Energy's Vehicle Technologies Office (VTO). The authors greatly appreciate support from Ken Howden, Siddiq Khan, and Gurpreet Singh at VTO.

References

- [1] W. Li, K.L. Perry, K. Narayanaswamy, C.H. Kim, P. Najt, Passive ammonia SCR system for lean-burn SIDI engines, *SAE Int. J. Fuels Lubr.* (2010), <https://doi.org/10.4271/2010-01-0366>.
- [2] J.E. Parks, V. Prikhodko, W. Partridge, J.-S. Choi, K. Norman, S. Huff, P. Chambon, Lean gasoline engine reductant chemistry during lean NOx trap regeneration, *SAE Int. J. Fuels Lubr.* 3 (2010), <https://doi.org/10.4271/2010-01-2267>, 2010-01-2267.
- [3] E.C. Adams, M. Skoglundh, P. Gabriellsson, M. Laurell, P.A. Carlsson, Ammonia formation over Pd/Al₂O₃ modified with cerium and barium, *Catal. Today* 267 (2016) 210–216, <https://doi.org/10.1016/j.cattod.2016.01.012>.
- [4] E.C. Adams, M. Skoglundh, M. Folic, E.C. Bendixen, P. Gabriellsson, P.A. Carlsson, Ammonia formation over supported platinum and palladium catalysts, *Appl. Catal. B Environ.* 165 (2015) 10–19, <https://doi.org/10.1016/j.apcatb.2014.09.064>.
- [5] B.B. Harrison, A.F. Diwell, C. Hallett, Promoting platinum metals by ceria - metal-support interactions in autocatalysts, *Platin. Met. Rev.* (1988) 73–83.
- [6] A. Törnroona, M. Skoglundh, P. Thormählen, E. Fridell, E. Jobson, Low temperature catalytic activity of cobalt oxide and ceria promoted Pt and Pd: -influence of pretreatment and gas composition, *Appl. Catal. B Environ.* 14 (1997) 131–146, [https://doi.org/10.1016/S0926-3373\(97\)00018-0](https://doi.org/10.1016/S0926-3373(97)00018-0).
- [7] H.C. Yao, Y.F.Y. Yao, Ceria in automotive exhaust catalysts. I. Oxygen storage, *J. Catal.* 86 (1984) 254–265, [https://doi.org/10.1016/0021-9517\(84\)90371-3](https://doi.org/10.1016/0021-9517(84)90371-3).
- [8] R.J. Gorte, S. Zhao, Studies of the water-gas-shift reaction with ceria-supported precious metals, *Catal. Today* 104 (2005) 18–24, <https://doi.org/10.1016/j.cattod.2005.03.034>.
- [9] E.C. Adams, M. Skoglundh, T. Elmøe, P.A. Carlsson, Water-gas-shift assisted ammonia formation over Pd/Ce/alumina, *Catal. Today* 307 (2018) 169–174, <https://doi.org/10.1016/j.cattod.2017.05.035>.
- [10] S. Aranifard, S.C. Ammal, A. Heyden, On the importance of metal-oxide interface sites for the water-gas shift reaction over Pt/CeO₂ catalysts, *J. Catal.* 309 (2014) 314–324, <https://doi.org/10.1016/j.jcat.2013.10.012>.
- [11] C.R. Thomas, J.A. Pihl, M.J. Lance, T.J. Toops, J.E. Parks, J. Lauterbach, Effects of four-mode hydrothermal aging on three-way catalysts for passive selective catalytic reduction to control emissions from lean-burn gasoline engine, *Appl. Catal. B Environ.* 244 (2019) 284–294, <https://doi.org/10.1016/j.apcatb.2018.11.051>.
- [12] J. Parks, T.J. Toops, J.A. Pihl, Emissions Control for Lean Gasoline Engines. https://www.energy.gov/sites/prod/files/2015/06/f23/ace033_parks_2015_o.pdf, 2015. (Accessed 14 March 2018).
- [13] K. Rahkamaa-Tolonen, Investigation of NO reduction by H₂ on Pd monolith with transient and isotopic exchange techniques II. H₂/D₂ exchange in the reduction of NO, *J. Catal.* 210 (2002) 30–38, <https://doi.org/10.1006/jcat.2002.3669>.
- [14] V. Easterling, Y. Ji, M. Crocker, J. Ura, J.R. Theis, R.W. McCabe, Effect of ceria on the desulfation characteristics of model lean NOx trap catalysts, *Catal. Today* 151 (2010) 338–346, <https://doi.org/10.1016/j.cattod.2009.12.007>.
- [15] M.L. Unland, Isocyanate intermediates in the reaction nitrogen monoxide + carbon monoxide over a platinum/aluminum oxide catalyst, *J. Phys. Chem.* 77 (1973) 1952–1956, <https://doi.org/10.1021/j100635a006>.
- [16] P.R. Dasari, R. Muncieff, M.P. Harold, Elucidating NH₃ formation during NO x reduction by CO on Pt-BaO/Al₂O₃ in excess water, *Catal. Today* 184 (2012) 43–53, <https://doi.org/10.1016/j.cattod.2011.12.009>.