

VTT Technical Research Centre of Finland

## New tools to study water interactions of microfibril bundles: Molecular modelling based on nanoscale characterization

Paajanen, Antti; Penttilä, Paavo; Zitting, Aleks; Ketoja, J A

*Published in:*  
Advances in Pulp and Paper Research, Cambridge 2022

Published: 01/09/2022

*Document Version*  
Publisher's final version

[Link to publication](#)

*Please cite the original version:*  
Paajanen, A., Penttilä, P., Zitting, A., & Ketoja, J. A. (2022). New tools to study water interactions of microfibril bundles: Molecular modelling based on nanoscale characterization. In D. W. Coffin, & W. J. Batchelor (Eds.), *Advances in Pulp and Paper Research, Cambridge 2022: Transactions of the 17th Fundamental Research Symposium* (Vol. 1, pp. 483-494). Pulp & Paper Fundamental Research Society.



VTT  
<http://www.vtt.fi>  
P.O. box 1000FI-02044 VTT  
Finland

By using VTT's Research Information Portal you are bound by the following Terms & Conditions.

I have read and I understand the following statement:

This document is protected by copyright and other intellectual property rights, and duplication or sale of all or part of any of this document is not permitted, except duplication for research use or educational purposes in electronic or print form. You must obtain permission for any other use. Electronic or print copies may not be offered for sale.

# NEW TOOLS TO STUDY WATER INTERACTIONS OF MICROFIBRIL BUNDLES: MOLECULAR MODELLING BASED ON NANOSCALE CHARACTERIZATION

*A. Paajanen<sup>1\*</sup>, P. Penttilä<sup>2</sup>, A. Zitting<sup>2</sup> and J. A. Ketoja<sup>1</sup>*

<sup>1</sup> VTT Technical Research Centre of Finland Ltd, Finland

<sup>2</sup> Department of Bioproducts and Biosystems, Aalto University, Finland

## ABSTRACT

The picture of the smallest structural units of wood fibres, that is, cellulose microfibrils and their bundles, has become more accurate during the last couple of decades, when information gained from several experimental characterisations has been drawn together. This work has been supported by computational methods that allow one to test the behaviour of postulated structures on the nanometre scale, and thus help in interpreting the experimental data. Bound water is an essential component in these models, as it affects both the structural swelling and the mechanical properties of the fibre wall nanostructure. Moreover, mechanisms on this scale can be expected to drive similar properties of macroscopic fibres. We suggest that several large-scale problems in papermaking and converting could be approached with atomistic molecular dynamics simulations for varied chemical compositions and external conditions. We demonstrate this by first showing that simulated moisture diffusion rates agree with measured ones at room temperature, and then determine diffusion

\* Corresponding Author

rates at elevated temperatures that lack reliable experimental data. These predictions provide key knowledge for further development of high-temperature drying and pressing processes. The results are important also when linking material performance at varied external conditions to the composition of the fibres.

## 1 INTRODUCTION

Many of the macroscopic properties of cellulosic fibres and fibre materials are sensitive to moisture. As bound water can be generally associated with the fibre wall nanostructure [1], we can expect the macroscopic properties to be also dominated by mechanisms at this scale. The smallest structural units of the fibre wall are cellulose microfibrils (diameter 3–4 nm) and their bundles, whose main components are crystalline and amorphous cellulose and different hemicelluloses. The chemical composition of the fibre wall determines the distribution of bound water, which affects both the structure and the mechanical properties of paper, including properties such as elasticity and creep.


Earlier experimental studies [2–4] have found both elastic modulus and creep to depend exponentially on moisture content (MC). A thorough explanation for this behaviour is still missing. [5] In earlier papers, the moisture-induced changes in mechanical behaviour have been often associated with softening of the amorphous polymer components as described by underlying glass transitions for lignin, hemicellulose and cellulose (see e.g. [6]). In his classic paper, Goring [7] considered sorbed water to act as diluent in plasticising the polymers. He reported a pronounced decrease of the softening temperature coming from sorption of water by isolated lignin and hemicellulose. Crystalline cellulose lacked a similar effect, and Goring concluded that water did not plasticise individual cellulose chains but would rather be adsorbed on the microfibril surfaces. Later Salmén and Olsson [8] refined the picture of the structural arrangement of the wood polymers within the secondary fibre wall. By studying delignified fibres, they found that xylan was responsible for the observed softening (at c.a. 75 % RH, 80°C), while attachment of glucomannan to the cellulose surface appeared to prevent softening of that hemicellulose.

Water diffusivity is another example of exponential dependence on MC. Topgaard and Söderman [9] used nuclear magnetic resonance (NMR) measurements to determine the self-diffusion coefficient of water absorbed in cellulose fibres, and they found the diffusivity to depend exponentially on MC in the range 0.15–0.2 g/g (water mass/dry mass). Quantitatively similar behaviour had been found indirectly by Gupta and Chatterjee [10] when modeling moisture

diffusivity through paper samples. Perkins and Batchelor [11] carried out NMR diffusion measurements at an intermediate MC range of 0.2–1.2 g/g for varied pulps, and they found good agreement with a model of slow and fast diffusion components. The diffusion along the paper plane was described by the slow component up to about 0.5 g/g moisture level. For fully saturated fibres, the level of diffusion constant,  $2\text{--}12 \times 10^{-10} \text{ m}^2/\text{s}$  [11, 12], has also been obtained by molecular simulations of water bound to crystalline cellulose [13]. The speeding up of diffusion in saturated redwood at increased temperature was measured to be described by an activation energy of 28 kJ/mol in the range of 4–55°C. [12]

We expect all these phenomena, including equilibrium bound water content [8], moisture diffusion and fibre softening to originate from the same nano-scale structural level. In this paper, we discuss this idea by using water diffusivity as an example of the interplay between fibre wall nanostructure and the studied macroscopic property. The rate of moisture diffusion is important for many phenomena in paper physics such as drying processes [14] and dimensional stability in printing [15, 16]. This relevance is caused mainly by slow diffusion at a low MC, which often becomes either a bottleneck for water transport (like for the final stage of web drying) or causes unwanted interactions with the process time scales (like for subsequent printing units). For uneven moistening, the impact can be multiple: increasing MC speeds up moisture diffusion that exponentially accelerates the relaxation of a fibre network causing severe cockling or curling of the paper web. Thus, it is important to understand how the fibre ultrastructure and chemical composition and external parameters like temperature affect the molecular diffusion rate.

Molecular simulations have been recently introduced to the study of the fibre wall nanostructure. [17] Their main advantage is the capability to probe molecular-level structures and processes that are difficult to observe experimentally. In the present work, we use models of cellulose microfibril bundles to study the effects of water sorption on their structure and on the mobility of bound water. We assume that hemicelluloses are bound to the fibril surfaces and thus present within the bundles. Similarly, we assume that the bound water of the fibre wall resides on the fibril surfaces. A previously developed nanoscale structural model (Figure 1) [17–19] is taken as a starting point for diffusion simulations at room temperature at varied MCs. The idea is to confirm that our simulations are able to describe the earlier experimental diffusion results with sufficient accuracy. The model is then used for taking a closer look at how bundle swelling and surface interactions affect the observed dynamics. Moreover, we repeat the simulations in a wide temperature range of 27–407°C and compare the results with simple activation models.

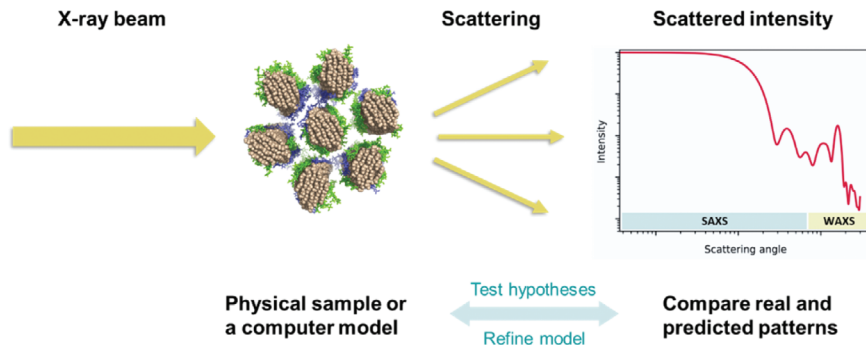

**Figure 1.** The models of cellulose microfibril bundles are based on previous work that combines molecular simulations and X-ray/neutron scattering measurements to study the moisture behaviour of the fibre wall nanostructure. [17, 18, 19] The molecular visualisation represents a cellulose microfibril bundle with hemicelluloses adsorbed on the fibril surfaces.


## 2 SIMULATION METHODS

Molecular models of cellulose microfibril bundles were used to study the effects of MC on bound water diffusivity within fibre walls. A recently proposed model for the nanostructure of spruce secondary cell walls [20] was used as the basis for model building.


The basic structural unit is the cellulose microfibril (Figure 2a). The microfibrils were chosen to consist of 18 cellulose chains arranged in the hexagonal 2-3-4-4-3-2 stacking (Figure 2a) [21]. Each chain consists of 34 glucose units, and the last unit of the chain is bonded to the first one across the periodic boundary of the simulation box. The fibril model was generated based on the cellulose I $\beta$  unit cell [22]. Eight models of hemicellulose coated fibrils were then created by simulating the adsorption of galactoglucomannan (GGM) and glucuronoarabinoxylan (GAX) chains on the fibril surfaces (Figure 2b). The hemicelluloses were assumed to be aligned with the microfibrils and to reside on their surfaces. Cellulose-GGM mass ratio was chosen to be roughly 9:2, and the cellulose-GAX mass ratio roughly 9:1. The mass ratios and the chemical structures of the hemicelluloses were chosen to mimic those found in spruce secondary cell walls (see [18] for further details). Both the GGM and the GAX chains consist of 30 repeat units.

The hemicellulose-coated fibrils were then used to build a periodic model of a fibril bundle. Four such fibrils were arranged in a periodic simulation domain to form an infinite hexagonal lattice (Figure 3). The initial inter-fibril distance was chosen to be 5 nm. The space between the fibrils was then filled with water, which resulted in a system with an MC of at least 100% ( $m_{\text{water}}/m_{\text{dry}}$ ).

*New Tools to Study Water Interactions of Microfibril Bundles*

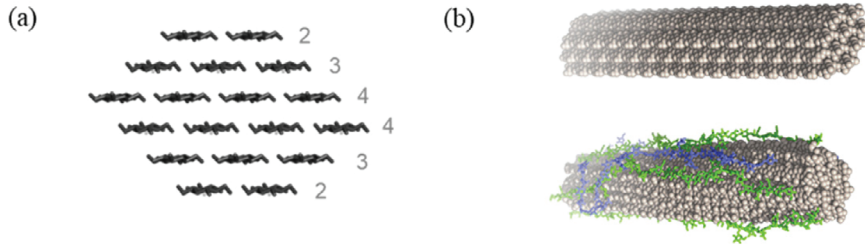

**Figure 2.** (a) Cross-section of an 18-chain microfibril model. Cellulose chains are shown in the stick-representation of covalent bonds. The hydrogen bonded layers of cellulose  $I_{\beta}$  are labelled according to the number of constituent chains. (b) Space-filling representation of a microfibril segment of 30 anhydroglucose units with and without adsorbed hemicelluloses. Cellulose chains are coloured brown, GGM chains green and GAX chains blue. The hemicellulose-coated fibril displays a helical twist.

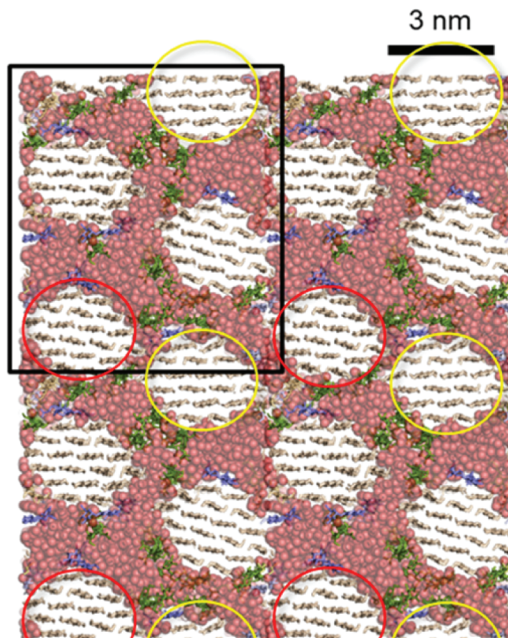

**Figure 3.** Cross-sectional view of the microfibril bundle model. The periodic simulation domain is outlined in black. Periodic images of two of the fibrils are highlighted by red and yellow outline. Cellulose chains are coloured brown, GGM chains green and GAX chains blue. Water is coloured red. The MC of the system is 40 % ( $m_{\text{water}}/m_{\text{dry}}$ ).


A hybrid Monte Carlo and molecular dynamics (MD) scheme [23] was used to study the response of the fibril bundle to changing MC. In the simulation protocol, 10 randomly chosen water molecules were removed from the system in between 100 ps simulations of molecular dynamics. After each percentage point decrease in moisture content, a longer 1 ns simulation was carried out. This procedure was followed until the system was completely dry. Sampling simulations of 200 ns were then carried out for chosen moisture contents. After this, molecular configurations for MCs 5–65 % at 300 K were heated to 480 K over 200 ns to obtain corresponding configurations at 360 K, 420 K and 480 K. Lastly, sampling simulations of 200 ns were carried out for these configurations at the corresponding temperatures. All simulations were performed in the isothermal-isobaric ensemble at 1 atm external pressure.

The simulations were performed using GROMACS [24] and the GLYCAM06H force field [25]. Water was described using the TIP3P model [26]. Temperature control was implemented using a stochastic variant of the Berendsen thermostat [27]. Pressure control was implemented using the Berendsen barostat [28]. Damping parameters of 200 fs and 2 ps were used for temperature and pressure control, respectively. The equations of motion were integrated using the velocity-Verlet algorithm with a 2 fs time step. Trajectory analysis was performed using GROMACS utilities. Molecular models of the hemicelluloses were generated using the doGlycans tool [29].

### **3. RESULTS AND DISCUSSION**

Changes in moisture content affect the microfibril bundles in a number of ways. Our previous work using non-periodic models shows that water molecules penetrate the fibril bundles, which causes changes in the inter-fibril spacing and the bundle diameter. [18, 19] Comparison against models without hemicelluloses [30] indicates that the amorphous polysaccharides have a key role in the swelling. The periodic models with hemicelluloses predict a moisture-dependent inter-fibril spacing that is in quantitative agreement with small-angle X-ray and neutron scattering experiments (Figure 4). [18, 19] Changes in moisture content also affect the internal structure of the fibrils. Most notably, the hydrogen-bonded layers of cellulose chains move further apart at low moisture contents and the chain length slightly contracts. Structural changes to the microfibril bundles are discussed in detail in [19]. In what follows, we focus on the effects of moisture content and temperature on bound water diffusivity.

We determined the diffusion coefficients at each MC and temperature based on the Einstein relation, which links molecular diffusivity with mean-square displacement:

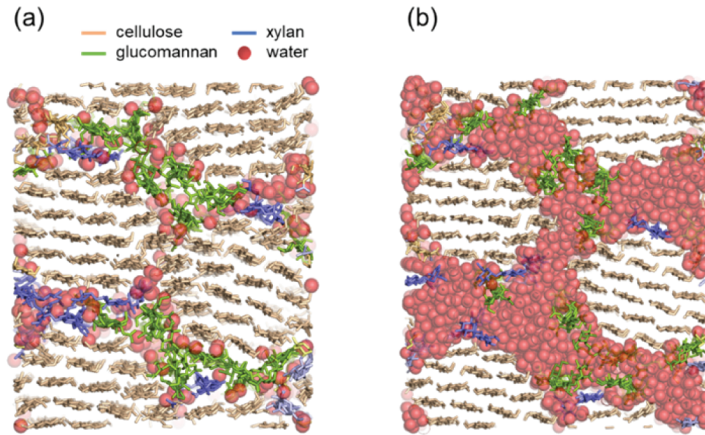

**Figure 4.** Microfibril bundle at (a) MC 5 % and (b) MC 40 % (water mass/dry mass). [18]

$$\langle r_i^2(t) \rangle = \frac{1}{N} \sum_{i=1}^N [r_i(t) - r_i(0)]^2 = 6Dt \quad (1)$$


where  $r_i(t)$  is the position of water molecule  $i$  at time  $t$ ,  $N$  is the total number of water molecules and  $D$  is the diffusion coefficient. Figure 5a shows the predictions for the axial direction of the bundles. Diffusion in the transverse direction is markedly slower. The limiting behaviour is particularly interesting. At MCs below 15–20%, the diffusivity grows exponentially with MC:

$$D \sim e^{\mu MC} \quad (2)$$

The value of the exponent  $\mu$  at room temperature, 0.28, is in agreement with the result of Topgaard and Söderman for water absorbed in cellulose fibres, approximately 0.24 (see Figure 15 of [9]). The rate of change decreases above MC 25–35%, and the diffusivity ultimately reaches a level of 50–75% of the self-diffusivity of water. Our results for room temperature are similar to those of Kulasinski et al. [31], who studied water diffusion in amorphous polysaccharides and aggregated cellulose microfibrils. Inspection of the molecular trajectories shows that the exponential increase in diffusivity coincides with the formation of nanoscale channels of water, in which the water molecules are not in direct contact with the interfacial hemicelluloses.

Our results at elevated temperatures display the expected increase in diffusion rate. Otherwise, the diffusion behaviour remains similar to that observed at room



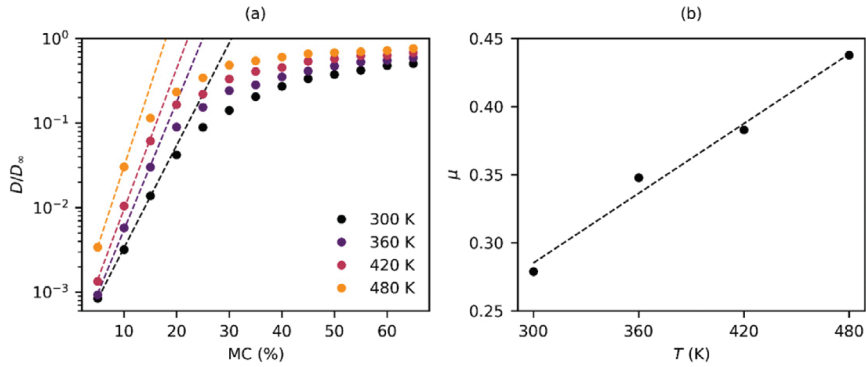


**Figure 5.** (a) Water diffusivity within the periodic microfibril aggregate at different moisture contents and temperatures. The diffusivity is normalised by an estimate for the self-diffusion coefficient of water  $D_\infty$  (to account for systematic over-estimation due to the TIP3P water model). (b) Exponential factor  $\mu$  of Eq. (2), determined at low moisture contents, as a function of temperature.

temperature. The exponential growth becomes more pronounced with increasing temperature, and the onset of deviation from simple exponential behaviour shifts towards lower MCs. The value of the exponent  $\mu$  depends roughly linearly on temperature, as shown in Figure 5b. Figure 6a shows Arrhenius plots of the logarithmic diffusivity versus inverse temperature for the MC range 15–65 %. Diffusivities for the lower MCs are omitted, since they clearly deviate from an Arrhenius-like temperature dependence

$$D = D_0 \exp\left(\frac{-E_a}{RT}\right) \quad (3)$$

where  $E_a$  is the activation energy and  $R$  is the gas constant. We determined the apparent activation energy and prefactor  $D_0$  for the above MC range through linear least squares fits, as shown by the dashed lines in Figure 6a. Figures 6b and c show the activation energy and the prefactor as a function of MC, respectively. The obtained activation energy has a similar level as the one measured earlier for saturated redwood [12].

Eqs. 2 and 3 can be used to estimate how moisture and temperature affect the paper web drying processes. The water removal is limited by the diffusion of bound water inside fibres during the final falling-rate phase of drying. The associated decay in drying rate originates from the exponential dependence of diffusion on moisture content as depicted by Eq. (2). However, the diffusion can be greatly

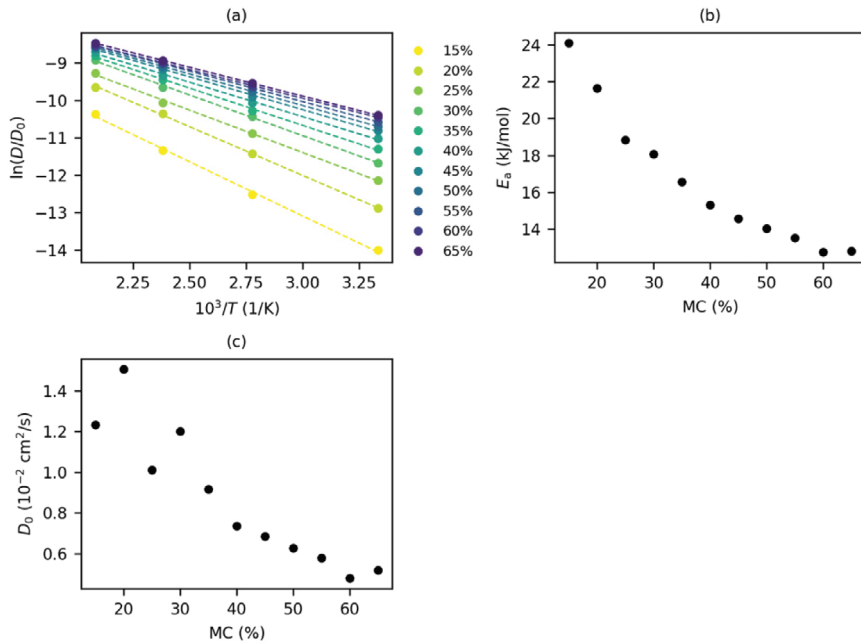

**Figure 6.** (a) Arrhenius plots for water diffusivity at different moisture contents. Linear least-squares fits are shown as dashed lines. (b) Apparent activation energy and (c) pre-exponential factor as a function of moisture content.

speeded up by increasing the temperature. For example based on Eq. (3), water removal at a temperature of 200°C, which is typical for hot-pressing [32] or heatset printing, can be expected to be an order of magnitude faster than in conventional cylinder drying [14] at temperature of 80°C (here we assume that  $MC < 20\%$ ). Direct measurements of the diffusion rate at such high temperatures would be extremely difficult.

Analysis of the molecular trajectories shows that a significant amount of water is confined within the hemicellulose-coated surfaces of the fibrils. In addition, the simulations predict the existence of two bound water populations with distinct diffusion behaviour. The presence of distinct water populations in wood cell walls has been observed in both two-dimensional low-field NMR and neutron scattering studies. [33] Similar behaviour has also been reported in a previous molecular modelling study of water diffusion in amorphous hydrophilic polymers. [31]

## CONCLUSIONS

We have introduced a molecular model that describes the internal structure of microfibril bundles within wood fibre walls. The essential structural features of the model agree with X-ray and neutron scattering results on the crystal lattice parameters of the microfibrils and the packing of the microfibrils in bundles at varied MC. This structural level is expected to be the origin of many central phenomena in paper physics, such as bound water content, chirality, swelling, stress relaxation, and water transport. The model was applied to predict moisture diffusion rate at varied temperature and MC, and the results were linked to interactions of water molecules with cellulose and hemicelluloses and to changes in the bundle structure. We found good agreement with earlier discovered experimental trends, which makes the simulation results highly interesting at conditions where diffusion experiments are difficult or even impossible.

The above example shows that modern characterisation and simulation tools enable moving from phenomenological models to direct molecular descriptions of the phenomena underlying measured fibre properties. The atomistic models can be further extended to coarse-grained models that describe a higher level of the fibre wall structural hierarchy. Information from such models can then be used at the fibre network level. This kind of approach not only helps in getting a more coherent picture of the phenomena at various scales but also removes unknown parameters from the models, improving their predictability.

## REFERENCES

- [1] Maloney, T.C., Johansson, T. and Paulapuro, H. Removal of water from the cell wall during drying. *Pap. Technol.* 39(6): 39–47 (1998)
- [2] Zauscher, S., Caulfield, D.F. and Nissan A.H. The influence of water on the elastic modulus of paper, Part I: Extension of the H-bond theory. *Tappi J.* 79(12): 178 (1996)
- [3] Coffin, D.W. The creep response of paper. Transactions of the *13th Fundamental Research Symposium*, vol. 2:651–747, FRC, Cambridge (2005)
- [4] Lehti, S.T., Ketoja, J.A. and Niskanen, K.J. Measurement of paper rheology at varied moisture contents. Proceedings of the *International Paper Physics Conference 57*, PAPTAC (2003)
- [5] Paavilainen, S., McWhirter, J.L., Róg, T., Järvinen, J., Vattulainen, I. and Ketoja, J. Mechanical properties of cellulose nanofibrils determined through atomistic molecular dynamics simulations, *Nord. Pulp Pap. Res. J.* 27: 282–286 (2012) <https://doi.org/10.3183/npprj-2012-27-02-p282-286>
- [6] Back, E.L. and Salmén, N.L. Glass transitions of wood components hold implications for molding and pulping processes. *Tappi J.* 65(7): 107–110 (1982).

- [7] Goring, D.A.I. Thermal softening, adhesive properties and glass transitions in lignin, hemicellulose and cellulose. In *Consolidation of the Paper Web, Trans. of the IIIrd Fund. Res. Symp. Cambridge, 1965* (F. Bolam, ed.), pp. 555–568, FRC, Manchester, 2018. DOI: 10.15376/frc.1965.1.555.
- [8] Salmén, L., Olsson, A.M. Interaction between hemicelluloses, lignin and cellulose: Structure-property relationships. *J. Pulp Paper Sci.* 24(3): 99–103 (1998).
- [9] Topgaard, D. and Söderman, O. Diffusion of Water Absorbed in Cellulose Fibers Studied with <sup>1</sup>H-NMR. *Langmuir* 17: 2694–2702 (2001) <https://doi.org/10.1021/la000982l>
- [10] Gupta, H. and Chatterjee, S.G. Parallel diffusion of moisture in paper. Part 1: Steady-state conditions. *Ind. Eng. Chem. Res.* 42: 6582–6592 (2003).
- [11] Perkins, E.L. and Batchelor, W.J. Water interaction in paper cellulose fibres as investigated by NMR pulsed field gradient. *Carbohydr. Polym.* 87: 361–367 (2012) <https://doi.org/10.1016/j.carbpol.2011.07.065>
- [12] Araujo, C.D., Mackay, A.L., Whittall, K.P. and Hailey, J.R.T. A diffusion model for spin-spin relaxation of compartmentalized water in wood. *J. Magnetic Resonance B*101(3): 248–261 (1993) <https://doi.org/10.1006/jmrb.1993.1041>
- [13] O’Neill, H., Pingali, S.V., Petridis, L., He, J., Mamontov, E., Hong, L., Urban, V., Evans, B., Langan, P., Smith, J.C. and Davison, B.H. Dynamics of water bound to crystalline cellulose. *Sci. Rep.* 7(1): 11840 (2017). <https://doi.org/10.1038/s41598-017-12035-w>
- [14] Stenström, S. Drying of paper: A review 2000–2018. *Dry. Technol.* 38(7): 825–845 (2020) DOI: 10.1080/07373937.2019.1596949
- [15] Ketoja, J.A., Kananen, J., Niskanen, K.J., Tattari, H. Sorption and web expansion mechanisms. In *The Science of Papermaking, Trans. of the XIIth Fund. Res. Symp. Oxford, 2001*, (C.F. Baker, ed.), pp. 1357–1370, FRC, Manchester, 2018. DOI: 10.15376/frc.2001.2.1357
- [16] Larsson, P.A., Hoc, M. and Wågberg, L. The influence of grammage, moisture content, fibre furnish and chemical modifications on the hygro- and hydro-expansion of paper. In *Advances in Pulp and Paper Research, Oxford 2009, Trans. of the XIVth Fund. Res. Symp. Oxford, 2009*, (S.J. P’Anson, ed.), pp. 355–388, FRC, Manchester, 2018. DOI: 10.15376/frc.2009.1.355
- [17] Penttilä, P.A., Paajanen, A. and Ketoja, J.A. Combining scattering analysis and atomistic simulation of wood-water interactions. *Carbohydr. Polym.* 251: 117064 (2021) <https://doi.org/10.1016/j.carbpol.2020.117064>
- [18] Zitting, A., Paajanen, A., Rautkari, L. and Penttilä, P.A. Deswelling of microfibril bundles in drying wood studied by small-angle neutron scattering and molecular dynamics. *Cellulose* 28:10765–10776 (2021) <https://doi.org/10.1007/s10570-021-04204-y>
- [19] Paajanen A., Zitting A., Rautkari L., Ketoja J.A. and Penttilä P.A. Nanoscale mechanism of moisture-induced swelling in wood microfibril bundles. *Nano Letters* (2022) <https://doi.org/10.1021/acs.nanolett.2c00822>.
- [20] Terrett, O.M., Lyczakowski, J.J., Yu, L., Iuga, D., Franks, W.T., Brown, S.P., Dupree, R. and Dupree, P. Molecular architecture of softwood revealed by solid-state NMR. *Nat. Commun.* 10(1): 4978 (2019) <https://doi.org/10.1038/s41467-019-12979-9>

- [21] Yang, H. and Kubicki, J.D. A density functional theory study on the shape of the primary cellulose microfibril in plants: effects of C6 exocyclic group conformation and H-bonding. *Cellulose* 27(5): 2389–2402 (2020) <https://doi.org/10.1007/s10570-020-02970-9>
- [22] Nishiyama, Y., Langan, P. and Chanzy, H. Crystal structure and hydrogen-bonding system in cellulose I-beta from synchrotron X-ray and neutron fiber diffraction. *J. Am. Chem. Soc.* 124(31): 9074–9082 (2002) <https://doi.org/10.1021/ja0257319>
- [23] Kulasinski, K., Guyer, R., Derome, D. and Carmeliet, J. Water adsorption in wood microfibril-hemicellulose system: Role of the crystalline-amorphous interface. *Biomacromolecules* 16(9): 2972–2978 (2015) <https://doi.org/10.1021/acs.biomac.5b00878>
- [24] Abraham, M.J., Murtola, T., Schulz, R., Pall, S., Smith, J.C., Hess, B. and Lindahl, E. GROMACS: high performance molecular simulations through multi-level parallelism from laptops to supercomputers. *SoftwareX* 1–2: 19–25 (2015) <https://doi.org/10.1016/j.softx.2015.06.001>
- [25] Kirschner, K.N., Yongye, A.B., Tschampel, S.M., Gonzalez-Outeirino, J., Daniels, C.R., Foley, B.L. and Woods, R.J. (2008) GLYCAM06: a generalizable biomolecular force field. *Carbohydrates. J. Comput. Chem.* 29(4): 622–655 (2008) <https://doi.org/10.1002/jcc.20820>
- [26] Jorgensen, W.L., Chandrasekhar, J., Madura, J.D., Impey R.W. and Klein, M.L. Comparison of simple potential functions for simulating liquid water. *J. Chem. Phys.* 79(2): 926–935 (1983) <https://doi.org/10.1063/1.445869>
- [27] Bussi, G., Donadio, D. and Parrinello, M. Canonical sampling through velocity rescaling. *J. Chem. Phys.* 126(1): 014101 (2007) <https://doi.org/10.1063/1.2408420>
- [28] Berendsen, H.J.C, Postma, J.P.M, van Gunsteren, W.F., DiNola, A. and Haak, J.R. Molecular dynamics with coupling to an external bath. *J. Chem. Phys.* 81(8): 3684–3690 (1984) <https://doi.org/10.1063/1.448118>
- [29] Danne, R., Poojari, C., Martinez-Seara, H., Rissanen, S., Lolicato, F., Rog, T. and Vattulainen, I. doGlycans-tools for preparing carbohydrate structures for atomistic simulations of glycoproteins, glycolipids, and carbohydrate polymers for GROMACS. *J. Chem. Inf. Model.* 57(10): 2401–2406 (2017) <https://doi.org/10.1021/acs.jcim.7b00237>
- [30] Paajanen, A., Ceccherini, S., Maloney, T. and Ketoja, J.A. Chirality and bound water in the hierarchical cellulose structure. *Cellulose* 26: 5877–5892 (2019) <https://doi.org/10.1007/s10570-019-02525-7>
- [31] Kulasinski, K., Guyer, R., Derome, D. and Carmeliet, J. Water diffusion in amorphous hydrophilic systems: A stop and go process. *Langmuir* 31: 10843–10849 (2015) <https://doi.org/10.1021/acs.langmuir.5b03122>
- [32] Mattsson, A., Joelsson, T., Miettinen, A., Ketoja, J.A., Pettersson, G. and Engstrand, P. Lignin inter-diffusion underlying improved mechanical performance of hot-pressed paper webs. *Polymers* 13(15): 2485 (2021) <https://doi.org/10.3390/polym13152485>
- [33] Engelund Thybring, E. and Fredriksson, M. Wood modification as a tool to understand moisture in wood. *Forests* 12: 372 (2021) <https://doi.org/10.3390/f12030372>