

Fabric-Reinforced Cementitious Matrix (FRCM) carbon yarns with different surface treatments embedded in a cementitious mortar: mechanical and durability studies

Francesca Bompadre, Jacopo Donnini*

Department of Materials, Environmental Sciences and Urban Planning (SIMAU), Marche Polytechnic University, Ancona, Italy; f.bompadre@univpm.it

*Correspondence: jacopo.donnini@staff.univpm.it

Abstract: FRCM systems are nowadays increasingly used for strengthening and retrofitting of existing masonry and reinforced concrete structures. Their effectiveness strongly depends on the bond that develops at the interface between multifilament yarns, which constitutes the reinforcing fabric, and the inorganic matrix. It is well known that fabric yarns, especially when constituted by dry carbon fibers, have a poor chemical-physical compatibility with inorganic matrices. For this reason, many efforts are being concentrated on trying to improve the interface compatibility by using different surface treatments on multifilament yarns.

In this paper, three different surface treatments have been considered, the first two consisting of yarns pre-impregnation with flexible epoxy resin or nano-silica coating while the third one is a process of fibers oxidation. Uniaxial tensile tests have been carried out on single carbon yarns to evaluate tensile strength, elastic modulus and ultimate strain, before and after surface treatments, and also after yarns exposure to accelerated artificial aging conditions (1000 h in saline or alkaline solutions at 40 °C), to evaluate the long-term behavior in aggressive environments.

Pull-out tests on single carbon yarns embedded in a cementitious mortar were also carried out, under normal environmental conditions and after artificial exposure. Epoxy proved to be the most effective treatment, by increasing the yarn tensile strength of 34% and the pull-out load of 138%, followed by nano-silica (+9%; +40%). All surface treatments showed to remain effective even after artificial environmental exposures, with a maximum reduction of yarns tensile strength of about 13%.

Citation: Lastname, F.; Lastname, F.; Lastname, F. Title. *Materials* **2022**, *15*, x. <https://doi.org/10.3390/xxxxx>

Academic Editor: Firstname Lastname

Received: date

Accepted: date

Published: date

Keywords: Fabric-Reinforced Cementitious Matrix (FRCM); carbon yarn; carbon fibers; surface treatments; coating; interface; bond; environmental exposure; durability.

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Fabric-Reinforced Cementitious Matrix (FRCM), also known in the international literature as Textile-Reinforced Mortar (TRM), is a new class of composite material that generated considerable interest as strengthening technique for concrete and masonry structures. FRCMs are constituted by open grids of perpendicularly connected multifilament yarns (made of carbon, glass, aramid, basalt or PBO fibers), which are applied on concrete or masonry structural elements through lime or cement-based matrices [1–4]. Although the use of FRCM systems as externally bonded reinforcement is nowadays a common practice in civil engineering, there are still some issues that need to be addressed, such as the most adhesion at the interface between the fabric reinforcement, made of multifilament yarns, and the inorganic matrix.

Experimental studies on FRCM systems showed that the main failure mode is by debonding and slippage of the fabric yarns within the inorganic matrix [5,6]. **Slippage of multifilament yarns within the matrix is emphasized in the case of yarns made up of carbon fibers [7].** The absence of hydrophilic groups on the carbon chain indeed results in a relatively poor **chemical** compatibility between **the surface of** carbon fibers and inorganic matrices [8]. **Moreover, the inorganic matrix (usually cement-based) is not able to fully penetrate between the filaments of the yarn, due to its high viscosity, thus allowing the innermost filaments to slip over each other, showing the so-called telescopic behavior [9].**

Several solutions have been proposed to improve the bond at the fiber-to-matrix interface: some of them directly modify the fiber surface by means of chemical-physical reactions (e.g. fibers oxidation [8,10]) while others provide for **partial or complete pre-impregnation** of the fibers with additional materials (usually organic polymers). Pre-impregnation of the fibers with organic coatings has been reported by many studies as a promising technique to improve the mechanical performance of FRCM systems [11–16]. **Donnini et al. found out that the use of epoxy coatings on carbon fabrics [17] or yarns [7] are very promising in increasing the bond at the interface with the inorganic matrix, depending on the level of pre-impregnation. Signorini et al. investigated the effect of epoxy resin viscosity on the mechanical properties of pre-impregnated FRCM systems, showing that epoxy can penetrate inside the yarn and prevents telescopic failure [18].**

In general, the main consequence of pre-impregnation with organic coatings is that the inorganic matrix is prevented to penetrate within the filaments of the yarn and the interface bond is no longer dependent on the matrix ability to wet the single filaments but rather on the interaction between the coating and the matrix. Moreover, when the single filaments are embedded in an organic coating, a higher number of filaments is engaged in the stress-transfer mechanisms, thus improving the yarn tensile strength and also leading to a change in the failure mode (usually from fabric slippage to fabric breakage) [19]. However, the main disadvantage of using organic coatings is the reduced ability of the composite system to withstand high temperatures [20–22].

Alternatively, the use of inorganic coatings has also been investigated, in order to overcome the issue of polymeric matrices subject to high temperatures [23–25]. The use of inorganic coatings, usually based on silica, cement or other nano-particles [24,26,27], allows for a stronger fiber-matrix interaction, thanks to the reaction and chemical bonds that can develop between the coating and the inorganic matrix, thus providing a better adhesion at the fiber-to-matrix interface. **The interfacial behavior between nano-silica modified carbon fibers and cementitious matrices has been recently studied by Li et al. [28], showing that the interfacial adhesion at fiber-matrix interface is improved compared to untreated fibers, due to the formation of C-S-H gel in the vicinity of the fiber surface. The effects of silica nano-coatings on carbon fibers have been also investigated by Signorini et al. [29], showing a good improvement in the performance of the composite, even if lower than those obtained with polymeric coatings.**

The durability of FRCM systems is also a very topical issue [13,30–33]. Carbon fibers have high resistance to chemical attacks and their properties remain almost unchanged when subjected to artificial aging conditions [34,35]. However, when the fibers are coated or modified with other surface treatments, the mechanical properties and durability of the yarns could be compromised.

The objective of this study is to evaluate the effectiveness of three different surface treatments applied to multifilament carbon yarns, to improve their mechanical performance and chemical-physical compatibility with cement-based matrices. The treatments investigated consist of epoxy pre-impregnation, nano-silica coating and sonication through an oxidative solution. The effectiveness of the treatments was evaluated both considering the tensile properties of the yarns (uniaxial tensile tests on single yarns) and the bond with a cement-based mortar (pull-out tests). Moreover, mechanical properties have been also evaluated after having exposed the specimens under different artificial aging conditions, to verify their effectiveness even in aggressive environments (Figure 1).

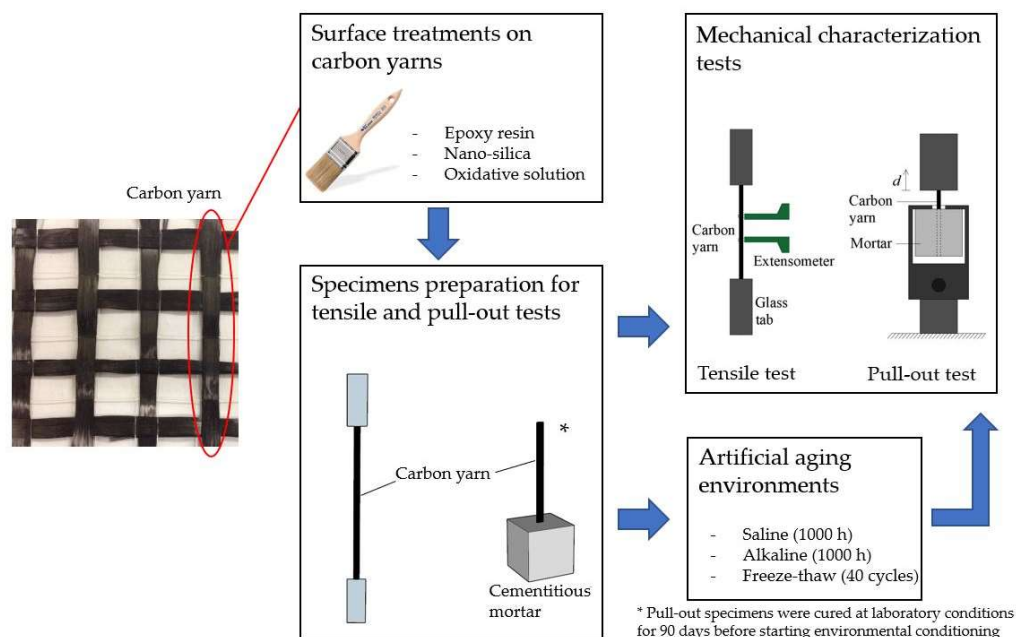


Figure 1. Schematic representation of the experimental campaign.

2. Materials and Methods

2.1. Materials

Two different types of specimens were manufactured to evaluate the effectiveness of different surface treatments on the tensile properties of single carbon yarns and on the adhesion with an inorganic cement-based mortar (as schematically reported in Figure 1). Carbon yarns used in experiments have been taken from a commercially available bidirectional dry carbon fabric. The 24 K carbon yarn has a cross-sectional area equal to 1.04 mm², as reported by the manufacturer, according to ISO 527- 4,5: 2021 [36]. Preparation of carbon yarns for tensile tests, test procedure and mechanical properties are reported in the experimental results section.

Pull-out specimens have been manufactured by embedding single carbon yarns in a cube of cement-based mortar (side of 40 mm), whose mix proportions and mechanical properties have been reported in Table 1. Compressive and flexural strength of the mortar have been evaluated on prismatic specimens (40 × 40 × 160 mm³) after 28 days of curing in laboratory conditions (20 ± 2°C, RH=70%), according to UNI EN 1015-11 [37].

Table 1. Mix proportions and mechanical properties of the inorganic matrix.

Material	CEM II/B-LL 32.5 R (kg/m ³)	CEM II/B-LL 42.5 R (kg/m ³)	CaCO ₃ 400 (kg/m ³)	CaCO ₃ 600 (kg/m ³)	Aerial lime (kg/m ³)	Water (kg/m ³)	Compressive strength (MPa)	Flexural strength (MPa)
Cement-based mortar	82	165	715	205	110	260	17.95	5.66

2.2. Surface treatments

Three different surface treatments have been employed. The first one consists in the application of a highly flexible two-component epoxy resin (C-E), whose mechanical

properties are reported in Table 2. Yarns were fully impregnated with the epoxy by means of a plastic spatula, then cured at 60 °C for 24 hours.

The second treatment involved the application of a nano-silica coating (C-NS). Carbon yarns were immersed in a nano-silica dispersion under stirring for 15 minutes and then dried at room temperature. The nano-silica dispersion was obtained by sol-gel method adding an acidic solution (distilled water: 65% Nitric Acid in the molar ratio 1:0.032) to a 98% Tetraethyl orthosilicate (TEOS) by Evonik, Ethanol (Analytical grade) solution as described in [38].

Finally, the third treatment (C-Ox) consists of carbon yarns sonication in a HNO₃/H₂SO₄ oxidative solution for 15 minutes, followed by washing with distilled water until a decrease of the washing water pH to a value of 6. 65% nitric acid (HNO₃) and 95% sulfuric acid (H₂SO₄) are purchased from Sigma-Aldrich. The oxidative solution was prepared according to [39], with 1:3 HNO₃ /H₂SO₄ volume ratio. Yarns were dried at room temperature before testing.

Table 2. Physical and mechanical properties of the epoxy resin (from manufacturer).

Material	Viscosity (mPas)	Tensile strength (MPa)	Elongation at break
Elan-tech EC 98N/W52	2000-3000	0.7-0.9	60-80%

2.3. Tensile and pull-out tests

To evaluate the effectiveness of the different surface treatments on the mechanical properties of carbon yarns and on the bond with the inorganic matrix, a total of 60 tensile and 80 pull-out tests have been carried out. Tensile tests on single carbon yarns were performed by using a tensile testing machine with a load bearing capacity of 50 kN, with a loading rate of 0.5 mm/min, according to ISO 10406-1 [33]. FRP glass tabs were epoxy-bonded at the ends of the specimen to ensure a better grip during the test. A macro-extensometer with a gauge length of 50 mm was positioned at the center of each specimen to evaluate the elastic modulus and to measure the strain at failure (Figure 2a). Mechanical parameters have been reported as the average on 5 specimens for each type. Tensile strength has been calculated by dividing the tensile load by the cross-sectional area of the yarn (provided by manufacturer). The elastic modulus has been calculated as the slope of the stress-strain curve in the elastic branch comprised between 20% and 50% of the maximum tensile capacity [33]. The average tensile strength (σ_{max}), ultimate strain (ϵ_u) and elastic modulus (E), are reported in Table 4, together with the corresponding coefficient of variation (CoV).

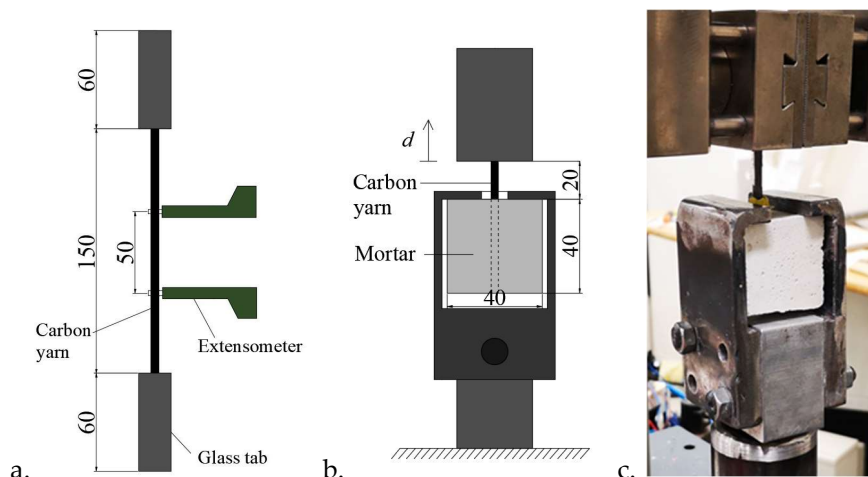


Figure 2. a) Tensile and b) pull-out test layout, c) actual pull-out test setup.

Pull-out tests were carried out on carbon yarns embedded in a cubic specimen of cementitious mortar ($40 \times 40 \times 40 \text{ mm}^3$). The free length is kept constant and equal to 20 mm. Pull-out tests were performed using a tensile testing machine with a load bearing capacity of 5 kN. The specimen is fixed at the bottom by a metallic frame anchored to the testing machine and the upper part of the yarn is gripped and pulled in displacement control at 0.5 mm/min (Figure 2b). The average maximum pull-out load and the total displacement corresponding to the maximum load (d_{\max}) are reported in Table 5, together with the corresponding coefficient of variation (CoV).

2.4. Aging Conditioning Protocol

Same tests have been carried out after subjecting the specimens to various artificial aging environments, as summarized in Table 3. In the case of pull-out specimens, the artificial conditioning started after 90 days of specimens curing at laboratory conditions ($20 \pm 2^\circ\text{C}$, RH=70%).

Table 3. Artificial aging test environments.

Environment	Temp	RH	Solution	Exposure Time	N° of samples (5 for each surface treatment)
None (Ref)	$20 \pm 2^\circ\text{C}$	70%	-	-	20 tensile tests 20 pull-out tests
Saline	$40 \pm 2^\circ\text{C}$	100%	2.45% NaCl + 0.41% Na_2SO_4	1000 h	20 tensile tests 20 pull-out tests
Alkaline	$40 \pm 2^\circ\text{C}$	100%	4% NaOH	1000 h	20 tensile tests 20 pull-out tests
Freeze-Thaw	$-18 \pm 2^\circ\text{C}/$ $+40 \pm 2^\circ\text{C}$	40%/ 100%	-	960 h (40 cycles)	20 pull-out tests

The first environment (Saline) comprises a 2.45% weight sodium chloride (NaCl) and 0.41% weight of sodium sulphate (Na_2SO_4) aqueous solution. The concentration of NaCl and Na_2SO_4 was chosen according to ASTM D1141–98 [34]. In order to accelerate the aging process without promoting unrealistic chemical reactions a temperature of 40°C was chosen.

The second environment (Alkaline) comprises a 4% weight sodium hydroxide (NaOH) aqueous solution with pH of 13. The exposure to alkaline and saline environments was conducted by completely immersing the carbon yarns in the solution, while the pull-out specimens were immersed for 3 cm, in order to keep the free length of the yarn out of the solution (Figure 3).

Freeze-thaw cycles consisted of freezing at -18 °C for more than 6 h and thawing at 40 °C for about 12 hours. A total of 40 cycles have been carried out both for carbon yarns and pull-out specimens. Finally, after artificial conditioning, all specimens have been dried at 40 °C for 24 h before testing.

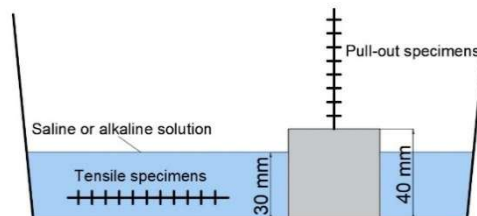


Figure 3. Conditioning exposure of tensile and pull-out specimens in saline and alkaline solutions

2.5. SEM and EDX analysis

SEM and EDX analysis have been carried out, using a FESEM ZEISS SUPRA40 with EDX-Detector Bruker Quantax 200-Z10, to investigate on the atomic percentages of carbon, silicon, oxygen and on the surface morphology of carbon yarns after different surface treatments.

3. Experimental results

3.1. Tensile tests


Experimental results of tensile tests on carbon yarns with different surface treatments, subjected to different environmental exposures, are reported in Table 4.

Table 4. Results of tensile tests on carbon yarns.

Specimen	Environment		Tensile Strength σ_{max} (MPa)	Variation of tensile strength	Elastic Modulus E (GPa)	Ultimate Strain ϵ_u (%)
C-Dry	None (Ref)	Average	1732	-	145	1.39
		CoV	6.9%		1.1%	1%
	Saline	Average	1594	-8.0%	144	1.25
		CoV	4.8%		4.7%	19.5%
	Alkaline	Average	1681	-2.9%	152	1.07
		CoV	10.1%		9.2%	5.8%
C-E	None (Ref)	Average	2327	-	142	1.76%
		CoV	7.6%		4.5%	5.1%
	Saline	Average	2201	-5.4%	147	1.50
		CoV	14.1%		5.2%	20.5%
	Alkaline	Average	2226	-4.3%	151	1.47
		CoV	11.4%		9.6%	17%
C-NS	None (Ref)	Average	1900	-	143	1.6
		CoV	3.3%		3.4%	6.1%
	Saline	Average	1672	-12.0%	149	1.08
		CoV	10.4%		3.4%	9.9%
	Alkaline	Average	1651	-13.1%	150	1.24
		CoV	3.3%		4.6%	12.3%
C-Ox	None (Ref)	Average	1667	-	139	1.39
		CoV	8.4%		4.3%	12%
	Saline	Average	1626	-2.4%	155	1.10

	CoV	9.7%		6.3%	15.1%
Alkaline	Average	1597	-4.2%	154	1.15
	CoV	9.2%		12.6%	13.2%

197

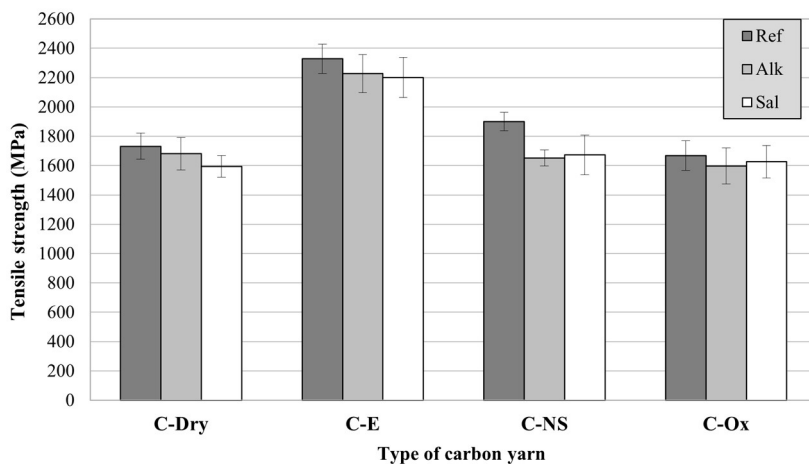

198

Figure 4. Tensile strength of carbon yarns with different surface treatments exposed to different environments.

199

200

Carbon yarns impregnated with epoxy resin (C-E) showed the highest tensile strength, equal to 2327 MPa, which corresponds to an increase of the tensile strength of about 34%, if compared to untreated yarns. The impregnation with nano-silica dispersion also leads to a slight increase of the tensile strength, of about 10%, while apparently the oxidative treatment has barely influenced the mechanical properties of the yarn. The ability of organic and inorganic coatings to improve the mechanical properties of multi-filament yarns has been reported in different studies, and it is attributed to the stress transfer increase between single filaments [35,36]. The effectiveness of a coating to improve the yarn tensile strength depends on its ability to simultaneously engage the single filaments of the yarn during the test. This is in accordance with the results obtained by C-E_Ref and C-NS_Ref. Different failure modes can also be observed for treated carbon yarns. C-Dry_Ref, C-NS_Ref and C-Ox_Ref yarns failed before all the carbon filaments have reached their maximum tensile strength (Figures 5a,c,d), suggesting that the nano-silica coating is not able to effectively activate all the yarn’s filaments during tensile test. On the contrary, C-E_Ref yarns showed an abrupt and simultaneous breakage of all the yarns’ filaments (Figure 5b). These results confirm the superior ability of the epoxy resin to uniformly distribute the stress between the single filaments, thus increasing the yarn tensile strength. The elastic modulus seems not be particularly affected by the surface treatment employed.

201

202

203

204

205

206

207

208

209

210

211

212

213

214

215

216

217

218

219

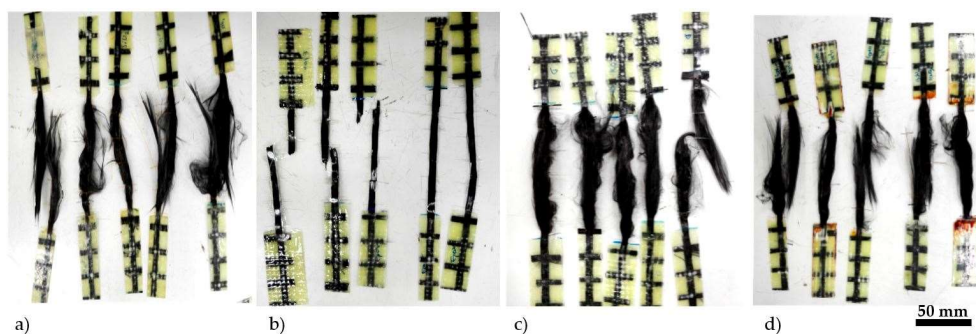


Figure 5. Failure modes: a) C-Dry_Ref, b) C-E_Ref, c) C-NS_Ref, d) C-Ox_Ref.

220

221

Looking at the results of durability tests (Figure 4), it can be observed that the tensile strength of carbon yarns is slightly affected by the exposure to saline and alkaline environments, regardless of the type of surface treatment applied. The most significant reduction of tensile strength is observed for C-NS yarns. After immersion in the alkaline solution, the tensile strength of C-NS yarn showed a decrease of about 13%. Similar results are obtained after immersion in the saline solution, with a 12% decrease of the tensile strength. The nanosilica coating is therefore effective in increasing the yarn tensile performance in laboratory environmental conditions (C-NS) but it seems to suffer the exposure to saline and alkaline solutions. This effect was also found in other studies [42], where the ineffectiveness of nanosilica coatings is attributed not only to the reduced particle size (50 nm) but also to a partial wash out of the small particles when the reinforcement is immersed in the fresh cementitious paste washing. In this study, immersion of carbon yarns in saline and alkaline solution at 40 °C could have caused this washout phenomenon. However, since SEM analysis of the yarn surface after exposure to various artificial environments have not yet been performed, these results will have to be confirmed by more detailed investigations.

3.2. Pull-out tests

Results of pull-out tests for all carbon yarns tested are reported in Table 5, while load-displacement curves are reported in Figure 6.

Table 5. Results of pull-out tests of carbon yarns subjected to different aging protocols.

Specimen	Environment		Max pull-out load (N)	Variation of max load (%)	Displacement at max load (mm)
C-Dry	None (Ref)	Average	321	-	0.86
		CoV	4%		13%
	Saline	Average	329	+2.5	0.87
		CoV	11%		11%
	Alkaline	Average	307	-4.4	0.69
		CoV	2%		23%
	Freeze-Thaw	Average	290	-9.7	0.96
		CoV	23%		16%
C-E	None (Ref)	Average	766	-	4.59
		CoV	2%		5%
	Saline	Average	823	+7.4	4.98
		CoV	2%		17%
	Alkaline	Average	857	+11.9	4.99
		CoV	2%		12%
	Freeze-Thaw	Average	660	-13.8	4.23
		CoV	5%		6%
C-NS	None (Ref)	Average	452	-	0.94
		CoV	2%		7%
	Saline	Average	397	-12.2	0.7
		CoV	8%		3%
	Alkaline	Average	436	-3.5	0.71
		CoV	10%		19%
	Freeze-Thaw	Average	395	-12.6	0.91
		CoV	6%		11%
C-Ox	None (Ref)	Average	413	-	0.94
		CoV	5%		7%
	Saline	Average	364	-11.9	0.94
		CoV	10%		5%

Alkaline	Average	407	-1.5	0.78
	CoV	5%		7%
Freeze-Thaw	Average	301	-27.1	0.74
	CoV	8%		5%

At first, it can be observed that all the surface treatments investigated in this study are able to increase the maximum pull-out load with respect to reference yarns.

Dry carbon yarns fail at low load values, due to poor chemical-physical interaction between dry carbon filaments and the cementitious matrix. The failure is due to the breakage of some external filaments of the yarn and consequent slippage of the inner ones (telescopic effect). This failure mode can be observed in the broken specimen of Figure 7a, where only few external filaments remained attached to the inorganic matrix after pull-out test.

The use of epoxy-based coating showed to be the most effective treatment, by increasing the pull-out load of about 138% with respect to dry carbon yarns. This is due to the greater and more homogeneous stress distribution between all the filaments of the yarn (as also observed in tensile tests), and to the high friction which develops at the epoxy-to-inorganic matrix interface. These results are in agreement with some findings from the literature, where an average 2-3 times increase of the mechanical performance of FRCM composites with polymer impregnated carbon yarns, compared to dry fiber yarns, is observed [7,43]. Similar results have been found by Signorini et al. for epoxy coated glass fibers [13].

The maximum pull-out load of C-E samples occurred for very large displacements. In fact, once the yarn detaches from the inorganic matrix (first peak in Figure 6, C-E), it starts to slip within the matrix and the pull-out load increases up to reach the maximum value. This stress-hardening behavior can be explained by looking at the surface of the C-E yarns after pull-out (Figure 7b), which shows that the epoxy coating has been partially removed by friction with the inorganic matrix.

The maximum pull-out load of carbon yarns treated with oxidative solution (C-Ox) and nano-silica dispersion (C-NS) was respectively 28% and 40% higher than that of dry yarns (C-Dry). Looking at the load-displacement curves, C-Dry, C-NS and C-Ox specimens showed a similar pull-out behavior, characterized by a first linear increase of the load, followed by a quick load decrease after the peak. Since neither the nano-silica coating nor the oxidation treatment influenced the graph shape in the post-debonding region, it can be assumed that these treatments did not affect the frictional shear stress at the composite interface. Therefore, the higher peak loads obtained in both cases are the consequence of a higher chemical bond with the cementitious matrix. For C-NS yarns this can be attributed to the chemical reaction of silica particles with the $\text{Ca}(\text{OH})_2$ of the cementitious mortar, forming a calcium silicate hydrate (C-SH) layer in the proximity of the fibers [26]. For what it concerns C-Ox samples, the oxidation process is expected to modify the carbon fibers surface, with the formation of oxygen-containing functional groups which help the wettability of the fibers by the cementitious mortar [44]. Some studies in the literature show the effectiveness of different oxidative treatments in improving the bond strength between carbon fibers and cementitious mortars, and therefore also the mechanical properties of the composite. However, it is difficult to compare the results of this study to others from the literature, due to a large number of variables. Some studies indeed refer only to short carbon fibers (instead of multifilament yarns) [44,45] while others use different oxidation processes or different setups for mechanical tests [46,47].

Regarding the oxidative treatment used in this study, some observations on its effectiveness are reported in Section 3.3, following SEM and EDX analysis on the yarn surface.

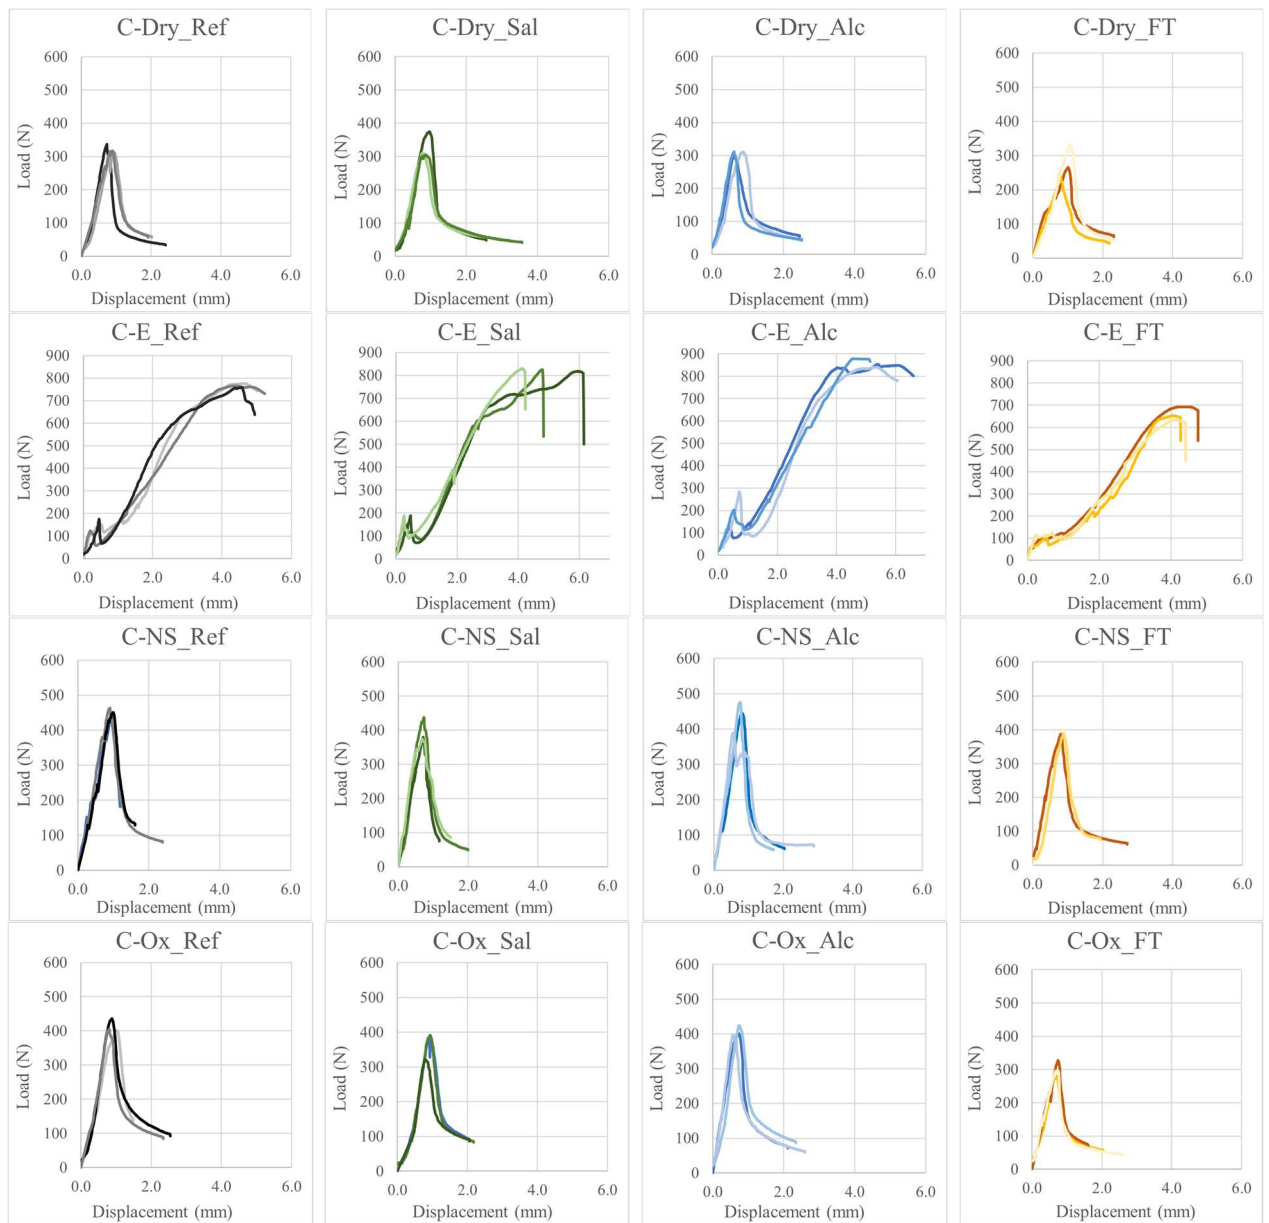


Figure 6. Load-displacement curves of pull-out tests.

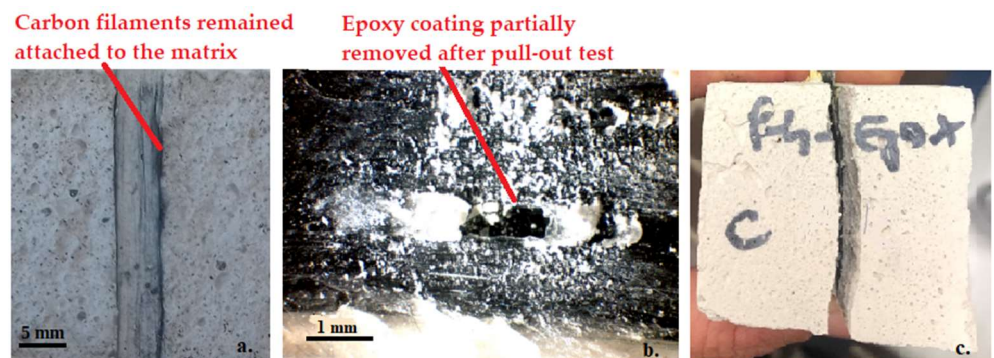


Figure 7. a) Contact surface between dry carbon yarns (C-Dry) and inorganic matrix after pull-out tests, b) external surface of epoxy coated carbon yarn (C-E) after pull-out, c) matrix breakage.

Regarding the results of pull-out tests after exposure to various artificial environments, a graphical representation of the outcomes is reported in Figure 8. It can be observed that, regardless of the environmental exposure, the unmodified yarns always show the lowest pull-out load. Moreover, the different environments do not seem to significantly affect the results of pull-out tests, regardless of the type of surface treatment employed.

It is interesting to note that C-E yarns subjected to alkaline and saline environments show a slight increase of the pull-out load, suggesting that the epoxy resin is able to further protect the carbon fibers from aggressive environments and that immersion in solution at 40°C has even increased the bond at the epoxy-matrix interface. However, in some cases a brittle failure at the yarn-matrix interface was observed, with the complete separation of the matrix into two parts (Figure 7c). This phenomenon can also be observed in some load-displacement curves, with an abrupt decay of the load corresponding to the matrix breakage (Figure 6, C-E_Sal, C-E_FT). This is a confirmation that the superior properties of epoxy-coated carbon yarns are mainly due to the friction that develops during the slippage of the yarn within the matrix more than to the chemical adhesion between the cured epoxy resin and the matrix (very low). Therefore, the presence of an epoxy coating can act as separating layer and promote delamination failures, as also observed in other studies [13,48].

Surface treatments based on nano-silica (C-NS) and fibers oxidation (C-Ox) showed to be adequately resistant to the aggressive environments, confirming their superior properties compared to dry yarns. In this study the most degrading environment was that of freeze-thaw cycles, which caused a decay of the pull-out load for all the specimens investigated (up to -27% for C-Ox specimens). This can be attributed to internal damage of the cementitious matrix, as well as to an incomplete curing of the matrix due to the low temperature and humidity of the conditioning environment, which could have led to premature failure (although the matrix did not show any significant cracks due to freeze-thaw cycles).

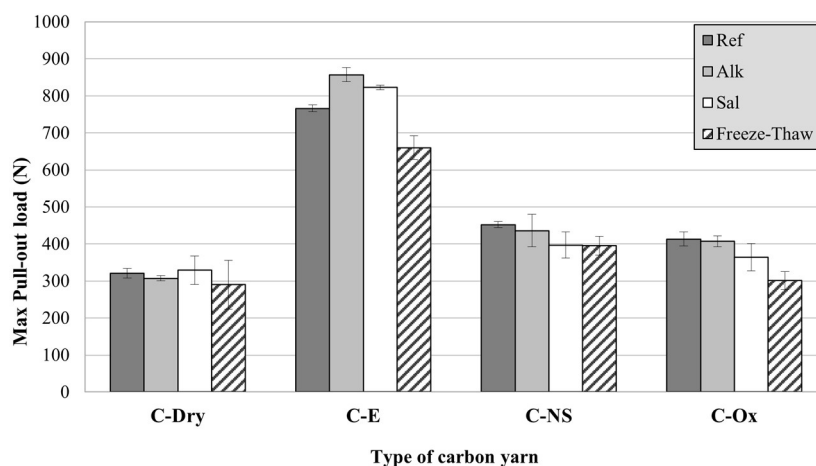


Figure 8. Pull-out load of carbon yarns with different surface treatments after artificial exposure.

3.3. EDX and SEM analysis

The results of EDX analyses on the surfaces of C-Dry, C-NS and C-Ox yarns are reported in Table 6. The atomic percentage of carbon ranges from 83% up to 94%. The presence of oxygen atoms can be attributed to the organic sizing applied to carbon filaments during the manufacturing process of the fabric.

It is interesting to observe that EDX analyses conducted on C-Ox yarns excluded the formation of new oxygen bearing groups on the carbon fiber surface (Table 6). A possible explanation of the improved interaction observed for C-Ox samples in pull-out tests is

that the chemical treatment was not sufficient to promote the oxidation of the carbon backbone, but it was able to attack the fibers surface causing an improvement of its roughness. An experimental study conducted on cement-based composites reinforced with carbon fibers (although short fibers) treated with concentrated acid, attributed the improved interaction between the matrix and the fibers to the formation of hydroxyl and carboxyl groups on the fibers surface [45]. However, in this study the results of SEM analysis showed no significant difference on the surface morphology of the fibers before and after the treatment with the oxidative solution (Figures 9a,b). A further explanation is that no oxidation took place, but the acid was able to catalyze other chemical reactions which did not change the chemical composition of the fibers but could modify the oxygen bearing groups on the fibers surface. Acids are known to catalyze different chemical reactions, however, since the exact chemical composition of the sizing is unknown, it is not possible to state which phenomenon may have occurred. Moreover, because no clear FTIR spectrum of the fibers before and after chemical treatment could be acquired this hypothesis cannot be confirmed.

On the other hand, the clear increase in the percentage of oxygen and silicon atoms observed for C-NS samples, compared to the untreated yarn, confirms the presence of nano-silica particles between the yarn filaments. However, SEM analysis (Figure 10) shows that the nano-silica coating is not uniformly distributed between the filaments, thus forming a discontinuous layer on the fibers surface. This is probably due to the manual impregnation process, which is not able to adequately control the uniformity of the application.

Table 6. Atomic percentages of carbon, silicon and oxygen detected by EDX analyses on the surfaces of the yarns C-Dry, C-NS and C-Ox

Sample	C [At %]	Si [At %]	O [At %]
C-Dry	93.47	0.23	6.31
C-NS	83.9	1.47	14.63
C-Ox	94.11	0.12	5.76

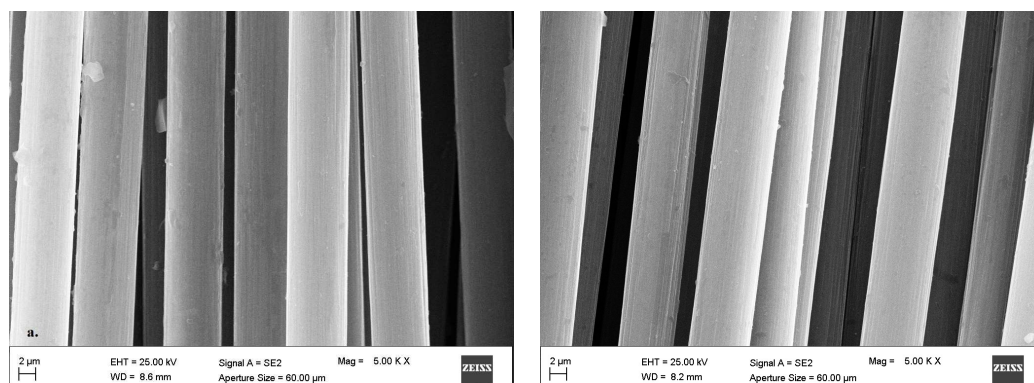


Figure 9. SEM images of a) C-Dry, and b) C-Ox multifilament yarns. Magnification 5.00 Kx.

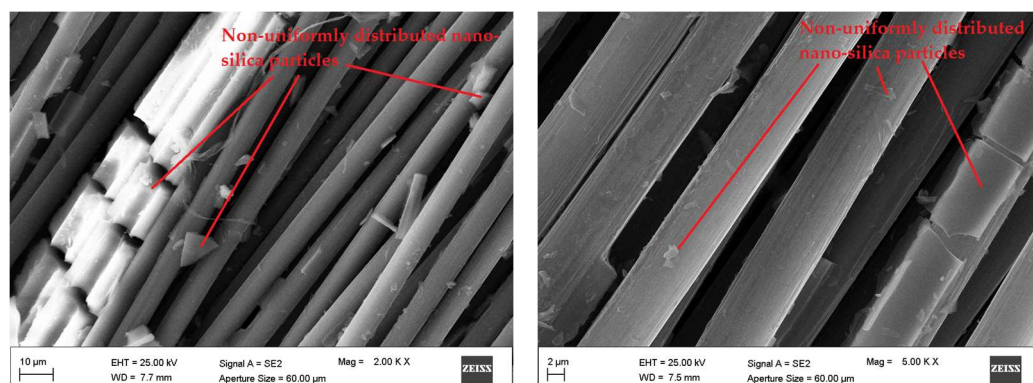


Figure 10. SEM images of C-NS yarns. Magnification (a) 2.00 Kx and (b) 5.00 Kx.

4. Conclusions

Based on the results of this experimental investigation, the following conclusions can be drawn:

- Pre-impregnation of multifilament carbon yarns with epoxy proved to be the most effective treatment, capable of increasing both the yarn tensile strength and the bond with the cement-based mortar. Epoxy was able to increase the carbon yarn tensile strength of about 34% and the pull-out load of about 138%. These effects, as well known from the literature, can be attributed to the ability of the low-viscosity epoxy to penetrate between single filaments of the yarn, thus guaranteeing a more homogeneous stress distribution through the yarn cross-section. However, it must be remembered that the use of organic polymers remains a weakness as regards the mechanical behavior of the composite when exposed to high temperatures.
- Nano-silica coating was less effective than epoxy, but still able to increase the yarn tensile strength of 10% and the pull-out load of about 40%. However, the effectiveness of this treatment can be improved by optimizing the manufacturing process, trying to ensure a more homogeneous distribution of the particles on the yarn surface.
- The oxidation of carbon fibers with $\text{HNO}_3/\text{H}_2\text{SO}_4$ solution seems not to substantially modify the mechanical properties of the carbon yarns. SEM analyses did not show significant changes in the surface of the carbon filaments after the oxidation process. However, this treatment was able to increase the pull-out load of about 28%. Further analyses are certainly needed to better investigate this aspect.
- Artificial aging in saline and alkaline environments caused only a slight reduction of the yarns tensile strength, which was always lower than 13%, regardless of the type of surface treatment applied.
- Pull-out tests carried out after exposure of the specimens in saline and alkaline environments showed no significant decrease of mechanical performances. Also in this case, carbon yarns with epoxy impregnation showed the highest load values. Exposure to freeze-thaw cycles caused the greatest reduction in the pull-out load (between -10% and -27%), probably due to internal damage of the inorganic matrix (which in some cases broke in half during the test), rather than to deterioration of the carbon yarn.

Funding: This research received no external funding.

Data Availability Statement: Not applicable.

Conflicts of Interest: The authors declare no conflict of interest.

References

- [1] Nanni A. A New Tool for Concrete and Masonry Repair. *Concr Int* 2012. 404
405
- [2] Awani O, El-Maaddawy T, Ismail N. Fabric-reinforced cementitious matrix: A promising strengthening technique for concrete structures. *Constr Build Mater* 2017. doi:10.1016/j.conbuildmat.2016.11.125. 406
407
- [3] Papanicolaou C, Triantafillou T, Lekka M. Externally bonded grids as strengthening and seismic retrofitting materials of masonry panels. *Constr Build Mater* 2011. doi:10.1016/j.conbuildmat.2010.07.018. 408
409
- [4] Donnini J, Maracchini G, Lenci S, Corinaldesi V, Quagliarini E. TRM reinforced tuff and fired clay brick masonry: Experimental and analytical investigation on their in-plane and out-of-plane behavior. *Constr Build Mater* 2021;272. doi:10.1016/j.conbuildmat.2020.121643. 410
411
412
- [5] D'Ambrisi A, Feo L, Focacci F. Experimental and analytical investigation on bond between Carbon-FRCM materials and masonry. *Compos Part B Eng* 2013. doi:10.1016/j.compositesb.2012.10.018. 413
414
- [6] Carozzi FG, Bellini A, D'Antino T, de Felice G, Focacci F, Hojdys Ł, et al. Experimental investigation of tensile and bond properties of Carbon-FRCM composites for strengthening masonry elements. *Compos Part B Eng* 2017. doi:10.1016/j.compositesb.2017.06.018. 415
416
417
- [7] Donnini J, Lancioni G, Corinaldesi V. Failure modes in FRCM systems with dry and pre-impregnated carbon yarns: Experiments and modeling. *Compos Part B Eng* 2018;140. doi:10.1016/j.compositesb.2017.12.024. 418
419
- [8] Tiwari S, Bijwe J. Surface Treatment of Carbon Fibers - A Review. *Procedia Technol* 2014. doi:10.1016/j.protcy.2014.08.064. 420
421
- [9] Alatawna A, Sripada R, Nahum L, Birenboimi M, Regev O, Peled A. Textile-cement bond enhancement: Sprinkle some hydrophilic powder. *Cem Concr Compos* 2021;120. doi:10.1016/j.cemconcomp.2021.104031. 422
423
- [10] Jang J, Yang H. Effect of surface treatment on the performance improvement of carbon fiber/polybenzoxazine composites. *J Mater Sci* 2000;35. doi:10.1023/A:1004791313979. 424
425
- [11] Schleser M, Walk-Laufer B, Raupach M, Diltthey U. Application of Polymers to Textile-Reinforced Concrete. *J Mater Civ Eng* 2006;18. doi:10.1061/(asce)0899-1561(2006)18:5(670). 426
427
- [12] Mäder E, Plonka R, Schiek M, Hempel R. Coatings on alkali-resistant glass fibres for the improvement of concrete. *J Ind Text* 2004;33. doi:10.1177/1528083704039833. 428
429
- [13] Messori M, Nobili A, Signorini C, Sola A. Mechanical performance of epoxy coated AR-glass fabric Textile Reinforced Mortar: Influence of coating thickness and formulation. *Compos Part B Eng* 2018. doi:10.1016/j.compositesb.2018.05.023. 430
431
432
- [14] Tayeh BA, EL dada ZM, Shihada S, Yusuf MO. Pull-out behavior of post installed rebar connections using chemical adhesives and cement based binders. *J King Saud Univ - Eng Sci* 2019;31. doi:10.1016/j.jksues.2017.11.005. 433
434
435
- [15] Bompadre F, Donnini J. Surface modification of glass textile for the reinforcement of a cement-based composite: A review. *Appl Sci* 2021;11. doi:10.3390/app11052028. 436
437
- [16] Bompadre F, Scheffler C, Utech T, Donnini J. Polymeric coatings for ar-glass fibers in cement-based matrices: Effect of nanoclay on the fiber-matrix interaction. *Appl Sci* 2021;11. doi:10.3390/app11125484. 438
439
- [17] Donnini J, Corinaldesi V, Nanni A. Mechanical properties of FRCM using carbon fabrics with different coating treatments. *Compos Part B Eng* 2016. doi:10.1016/j.compositesb.2015.11.012. 440
441
- [18] Signorini C, Nobili A, Sola A, Messori M. Designing epoxy viscosity for optimal mechanical performance of coated Glass Textile Reinforced Mortar (GTRM) composites. *Constr Build Mater* 2020. doi:10.1016/j.conbuildmat.2019.117325. 442
443
444
- [19] Brameshuber W. Textile Reinforced Concrete (TRC). *Mater Struct* 2005. doi:10.1617/14402. 445

- [20] Bisby L. Fire Resistance of Textile Fiber Composites Used in Civil Engineering. *Text. Fibre Compos. Civ. Eng.*, 2016. doi:10.1016/B978-1-78242-446-8.00008-2. 446
447
- [21] Donnini J, De Caso y Basalo F, Corinaldesi V, Lancioni G, Nanni A. Fabric-reinforced cementitious matrix behavior at high-temperature: Experimental and numerical results. *Compos Part B Eng* 2017;108. doi:10.1016/j.compositesb.2016.10.004. 448
449
450
- [22] Trapko T. The effect of high temperature on the performance of CFRP and FRCM confined concrete elements. *Compos Part B Eng* 2013. doi:10.1016/j.compositesb.2013.05.016. 451
452
- [23] Di Maida P, Radi E, Sciancalepore C, Bondioli F. Pullout behavior of polypropylene macro-synthetic fibers treated with nano-silica. *Constr Build Mater* 2015. doi:10.1016/j.conbuildmat.2015.02.047. 453
454
- [24] Nadiv R, Peled A, Mechtcherine V, Hempel S, Schroefl C. Micro- and nanoparticle mineral coating for enhanced properties of carbon multifilament yarn cement-based composites. *Compos Part B Eng* 2017. doi:10.1016/j.compositesb.2016.12.005. 455
456
457
- [25] Schneider K, Michel A, Liebscher M, Terreri L, Hempel S, Mechtcherine V. Mineral-impregnated carbon fibre reinforcement for high temperature resistance of thin-walled concrete structures. *Cem Concr Compos* 2019;97. doi:10.1016/j.cemconcomp.2018.12.006. 458
459
460
- [26] Lu M, Xiao H, Liu M, Li X, Li H, Sun L. Improved interfacial strength of SiO₂ coated carbon fiber in cement matrix. *Cem Concr Compos* 2018. doi:10.1016/j.cemconcomp.2018.04.007. 461
462
- [27] Signorini C, Sola A, Nobili A, Siligardi C. Lime-cement textile reinforced mortar (TRM) with modified interphase. *J Appl Biomater Funct Mater* 2019;17. doi:10.1177/2280800019827823. 463
464
- [28] Li H, Zhao D, Liebscher M, Yin B, Yang J, Kaliske M, et al. An experimental and numerical study on the age depended bond-slip behavior between nano-silica modified carbon fibers and cementitious matrices. *Cem Concr Compos* 2022;128. doi:10.1016/j.cemconcomp.2022.104416. 465
466
467
- [29] Signorini C, Nobili A, Cedillo González EI, Siligardi C. Silica coating for interphase bond enhancement of carbon and AR-glass Textile Reinforced Mortar (TRM). *Compos Part B Eng* 2018;141. doi:10.1016/j.compositesb.2017.12.045. 468
469
470
- [30] Franzoni E, Gentilini C, Santandrea M, Carloni C. Effects of rising damp and salt crystallization cycles in FRCM-masonry interfacial debonding: Towards an accelerated laboratory test method. *Constr Build Mater* 2018. doi:10.1016/j.conbuildmat.2018.04.164. 471
472
473
- [31] Franzoni E, Santandrea M, Gentilini C, Fregni A, Carloni C. The role of mortar matrix in the bond behavior and salt crystallization resistance of FRCM applied to masonry. *Constr Build Mater* 2019. doi:10.1016/j.conbuildmat.2019.03.059. 474
475
476
- [32] Donnini J. Durability of glass FRCM systems: Effects of different environments on mechanical properties. *Compos Part B Eng* 2019;174:107047. doi:10.1016/j.compositesb.2019.107047. 477
478
- [33] Donnini J, Bompadre F, Corinaldesi V. Tensile behavior of a glass FRCM system after different environmental exposures. *Processes* 2020;8. doi:10.3390/pr8091074. 479
480
- [34] Micelli F, Aiello MA. Residual tensile strength of dry and impregnated reinforcement fibres after exposure to alkaline environments. *Compos Part B Eng* 2019. doi:10.1016/j.compositesb.2017.03.005. 481
482
- [35] Micelli F, Nanni A. Durability of FRP rods for concrete structures. *Constr Build Mater* 2004. doi:10.1016/j.conbuildmat.2004.04.012. 483
484
- [36] ISO 527-4:2021. *Plastics — Determination of tensile properties — Part 4: Test conditions for isotropic and orthotropic fibre-reinforced plastic composites* n.d. 485
486
- [37] EN 1015-11. *Methods of Test for Mortar for Masonry. Part 11 Determ Flexural Compressive Strength Hardened* 487

- Mortar 2006. 488
- [38] Weichold O, Möller M. A cement-in-poly(vinyl alcohol) dispersion for improved fibre-matrix adhesion in continuous glass-fibre reinforced concrete. *Adv Eng Mater* 2007. doi:10.1002/adem.200700113. 489
- [39] Thi Mai Hoa L. Characterization of multi-walled carbon nanotubes functionalized by a mixture of HNO₃/H₂SO₄. *Diam Relat Mater* 2018. doi:10.1016/j.diamond.2018.08.008. 491
- [40] Thomason JL. Glass fibre sizing: A review. *Compos Part A Appl Sci Manuf* 2019. doi:10.1016/j.compositesa.2019.105619. 493
- [41] Igarashi S ichi, Kawamura M. Effects of a size in bundled fibers on the interfacial zone between the fibers and the cement paste matrix. *Cem Concr Res* 1994. doi:10.1016/0008-8846(94)90193-7. 495
- [42] Cohen Z, Peled A. Effect of nanofillers and production methods to control the interfacial characteristics of glass bundles in textile fabric cement-based composites. *Compos Part A Appl Sci Manuf* 2012;43. doi:10.1016/j.compositesa.2012.01.022. 497
- [43] D'Antino T, Papanicolaou C. Mechanical characterization of textile reinforced inorganic-matrix composites. *Compos Part B Eng* 2017;127:78–91. doi:10.1016/j.compositesb.2017.02.034. 500
- [44] Fu X, Lu W, Chung DDL. Improving the bond strength between carbon fiber and cement by fiber surface treatment and polymer addition to cement mix. *Cem Concr Res* 1996;26. doi:10.1016/0008-8846(96)00084-1. 502
- [45] Lavagna L, Musso S, Ferro G, Pavese M. Cement-based composites containing functionalized carbon fibers. *Cem Concr Compos* 2018. doi:10.1016/j.cemconcomp.2018.02.007. 504
- [46] Li H, Liebscher M, Michel A, Quade A, Foest R, Mechtcherine V. Oxygen plasma modification of carbon fiber rovings for enhanced interaction toward mineral-based impregnation materials and concrete matrices. *Constr Build Mater* 2021;273. doi:10.1016/j.conbuildmat.2020.121950. 506
- [47] Li H, Liebscher M, Ranjbarian M, Hempel S, Tzounis L, Schröfl C, et al. Electrochemical modification of carbon fiber yarns in cementitious pore solution for an enhanced interaction towards concrete matrices. *Appl Surf Sci* 2019;487. doi:10.1016/j.apsusc.2019.04.246. 509
- [48] Hegger, J, Will, N., Bentur, A., Curbach, M., Jesse, F., Mobasher, B., Peled, A., Wastiels J. Mechanical behaviour of textile reinforced concrete. *Text Reinf Concr - State-of-the-Art Rep RILEM TC 201-TRC* 2006. 512