

DOI:10.4067/S0718-221X2023005XXXXXX

1
2
3 **INFLUENCE OF SOIL PHYSICOCHEMICAL PROPERTIES ON**
4 **BIOMETRICAL AND PHYSICAL FEATURES OF PERSIAN OAK**
5 **WOOD**
6

7 **Huijun Dong¹, Mohammad Dahmardeh Ghalehno², Mohsen Bahmani^{3*}, Elham**
8 **Ghehsareh Ardestani³, Leila Fathi³**

9 ¹ Nanjing Forestry University, College of Material Science and Engineering, Nanjing, China.

10 ² Department of Wood and Paper Sciences and Technology, Zabol, Iran.

11 ³ Shahrekord University, Department of Natural Resources and Earth Science, Shahrekord,
12 Iran.

13
14 *Corresponding author: mohsen.bahmani@sku.ac.ir

15 **Received:** September 22, 2021

16 **Accepted:** October 12, 2022

17 **Posted online:** October 13, 2022

18 **ABSTRACT**

19 This article investigates the relationships between soil characteristics (physical and chemical)
20 and wood properties of Persian oak in three different elevation sites. For this purpose, 27 trees
21 were randomly chosen and cut in Zagros forests in western Iran. The test samples were prepared
22 at the stem (breast height) to examine physical and biometrical properties. For each elevation
23 site, four soil samples were obtained at a 0-20 cm soil depth under the canopy of each tree to
24 measure soil properties, including clay, silt soil, sand soil, electrical conductivity, pH, nitrogen,
25 phosphorus, potassium, and organic matter content. Then, the relationship of soil and wood
26 properties was determined by principal component analysis. Results specified that there are a
27 positive correlation between wood density and volumetric swelling with clay and available
28 potassium. Moreover, the results revealed a positive correlation between fiber length, cell wall
29 thickness, and fiber diameter with electrical conductivity, sand percentage, and total nitrogen
30 content, respectively.

31 **Keywords:** *Quercus brantii*, soil properties, wood density, wood fiber, wood quality.

32

33

INTRODUCTION

34
35 Zagros forest in western Iran covers more than five million ha (Nazari *et al.* 2021). This forests
36 consists sub-Mediterranean, semiarid temperate climate, mainly consisting of deciduous,
37 broad-leaved trees (Olfat and Pourtahmasi 2010). *Crategus spp.* and *Pyrus spp.*, *Quercus spp.*
38 (oaks), and *Pistacia mutica* (wild pistachio) (Ghazanfari *et al.* 2004) are the three main wood
39 tree species in this district. The ring-porous tree species *Quercus brantii* (covering more than
40 50 % of the Zagros forest area) has dominated tree woody species in the Zagros forests growing
41 at 450 m to 2700 m altitudes (Sagheb-Talebi 2005). Native to western Asia and with more than
42 50 % coverage of the Zagros forests in Iran, it is one of the ecologically and economically most
43 important tree species (Safari *et al.* 2022). They play an important role in water protection,
44 water regulation, and soil protection, as well as perform sanitary and recreational functions.
45 Persian oak is a big tree with height of 20 m and a big spherical crown and it has generally
46 ovoid leaves with serrated margins. The fruit of *Q. brantii* is elongated and oval in velvety
47 white bowl and conical (Alikhani *et al.* 2014). It has been reported that climate and
48 environmental factors affect the quality of wood (Zobel and van Buijtenen 1989, Nazari *et al.*
49 2020). Climatic factors (temperature and rainfall), geographic features (latitude, elevation, and
50 slope), biotic factors (animals, plants, humans, fungi, bacteria), and physical and chemical
51 properties of soil can impact wood properties (Topaloglu *et al.* 2016, Nazari *et al.* 2021).
52 Although numerous studies investigated the relationships between ecological indexes and
53 wood properties (Rossi 2015, Topaloglu *et al.* 2016, Sousa *et al.* 2018, Kiaei 2019), our
54 knowledge is still limited regarding the relation between soil properties and variations in wood
55 quality.
56 Research on the physical and chemical properties of the soil that determine the properties of
57 wood is complicated because it is affected by many other factors, such as the age of the tree,
58 heredity, etc., and the relationship between parameters. Although the physical and chemical

59 properties of the soil have a key role in the growth of trees and wood quality, their effects on
60 wood properties are still rarely investigated. (Marini *et al.* 2021). Rigatto *et al.* (2004) indicated
61 that there is a significant correlation between soil physicochemical properties and wood quality.
62 Cutter *et al.* (2004) found that sites with favorable soil properties significantly influenced the
63 wood density. Tufekcioglu *et al.* (2005) studied the influence of soil characteristics on hybrid
64 poplar growth in Turkey and concluded that the content of clay and Mg^{+2} was negatively
65 correlated with the pH of the soil, while the range of phosphorus and sand of the soil was
66 positively correlated with hybrid poplar growth. Bektas *et al.* (2003) investigated the site effect
67 on heartwood and sapwood portions of Turkish Calabrian pine. They stated that the differences
68 in heartwood and sapwood might be related to ecological indicators such as elevation, lime
69 content, soil organic matter, and soil type. Yanez Espinosa *et al.* (2001) indicate that soil texture
70 and water salinity are closely associated with the anatomical characteristics of Mexican
71 mangrove populations. Kiaei (2014) pointed out that there is a significant correlation between
72 soil clay and sand with wood properties of Eldar pine (*Pinus eldarica*), in contrast a negative
73 relationship between wood properties and soil chemical properties was found. In Iran, there is
74 no study related to the influence of soil physical and chemical properties on the wood properties
75 of Persian oak.

76 Principal Component Analysis (PCA) is an algorithm in biometrics. It is a statistical technique
77 that makes use of orthogonal transformation to transform a set of data of probably linked
78 variables into a set of values of unrelated linear variables. It is also a tool that reduces
79 multidimensional data to lower dimensions while retaining most of the information.
80 (Karamizadeh *et al.* 2013). PCA is a sorting method that develops theoretical variables and
81 reduces the total residual sum of squares after fitting a straight line to the species data. The best
82 wood properties values for the sites are selected by PCA (Kooch *et al.* 2008).

83 Considering the importance of the chemical and physical properties of the soil to the wood
84 quality and the value of Persian oak to Iranian forests, this research aimed was to investigate
85 the influence of soil properties on physical properties (dry density and volumetric swelling)
86 and wood fiber properties (fiber length, cell wall thickness, and fiber diameter) in three
87 different elevations and to inspect the relationship between wood properties with soil. The
88 relationship of mentioned variables was determined by PCA.

89

90

MATERIALS AND METHODS

91 Study site and sampling

92 This study was carried out in trees of Persian oak (*Quercus brantii* Lindl) collected from tree
93 sites (three forest sample stands along an altitudinal gradient, below 1900, 1900-2000 and above
94 2200 m a.s.l.) in the oak forests of Bazoft. Due to their remote location and the absence of
95 evidence of human impact, it is assumed that all stands have been developed under the
96 influence of natural impacts and disturbances. In each site, nine plots were implemented,
97 accordingly the 27 plots were selected in study area. In each plot, all live trees of at least 7,5
98 cm diameter at breast height (DBH, 1,3 m above the root collar) were identified, and their
99 diameter at breast height, height, crown length and perpendicular diameters were recorded
100 within 0,1-hectare plot. The caliper, Vertex and diameter tape were used to measurements of
101 trees diameters, height and crown diameter, respectively. Then stand-level variables such as
102 stand basal area (square meter per hectare), stand density (the number of trees per hectare),
103 stand quadratic mean diameter (QMD) (cm) and tree-level variables such as stem basal area
104 (m^2), stem volume (m^3), crown diameter (m) and crown basal area (m^2) in each site were
105 calculated. Then in each plot, those dominant trees that healthy with the largest diameters at
106 breast height (DBH) without any defects and reaction wood were sampled and one disc was
107 taken from the tree trunk at DBH for the determination of wood properties. Then, the tree age
108 at breast height (ABH) was obtained by counting the annual rings of the sampled disks. Finally,

109 the mean annual diameter increment (MADI) was obtained by dividing DBH by the number of
110 annual rings. In total, 27 healthy trees (9 trees× 3 sites) were selected. The main dimensions of
111 the tree and site properties are presented in Table 1.

112 **Wood Physical properties**

113 Physical properties, namely oven-dry density and volumetric swelling were measured from 5
114 cm thick disks cut down from each tree. The disks were cut from the stem diameter at breast
115 height (DBH = 1,30 m aboveground). Sample tests were prepared following ISO 13061-14
116 (2016). The wood sample size was 3×2×2 cm³. Two hundred seventy samples were prepared
117 from various portions of the disks. The size of samples in both green and oven-dry situations
118 was measured with a slide caliper. An electronic balance was used to measure the oven-dry
119 density. Dimensional changes from the green to dry conditions were considered to calculate
120 the volumetric swelling. The mentioned physical properties were determined in accordance
121 with the formula (Eq. 1-2):

$$D_0 = \frac{M_0}{V_0} \quad (1)$$

$$\alpha_v = \frac{V_s - V_0}{V_0} \quad (2)$$


122 Where: D_0 - oven-dry density (g·cm⁻³), M_0 - oven-dry mass (g), V_0 - oven-dry volume
123 (cm³), α_v - volumetric swelling (%), V_s - volume in state of saturate (cm³).

124

125 **Morphologic wood properties**

126 Franklin's method (1945) was applied to separate the individual wood fiber. In detail,
127 Saturation of wood samples (15×10×2 mm³) in a mixture (1:1) of oxygenized water and acetic
128 acid were performed, and then the samples were maintained inside an oven for 48 hours at 65°C
129 ± 5°C. After maceration, the samples were washed in distilled water. Finally, they were
130 submerged to distilled water, shacked, and fiber parameters such as fiber length, cell wall
131 thickness, and fiber diameter were evaluated under a light microscope. From each slice, at least
132 50 fibres were used for the measurements.

133

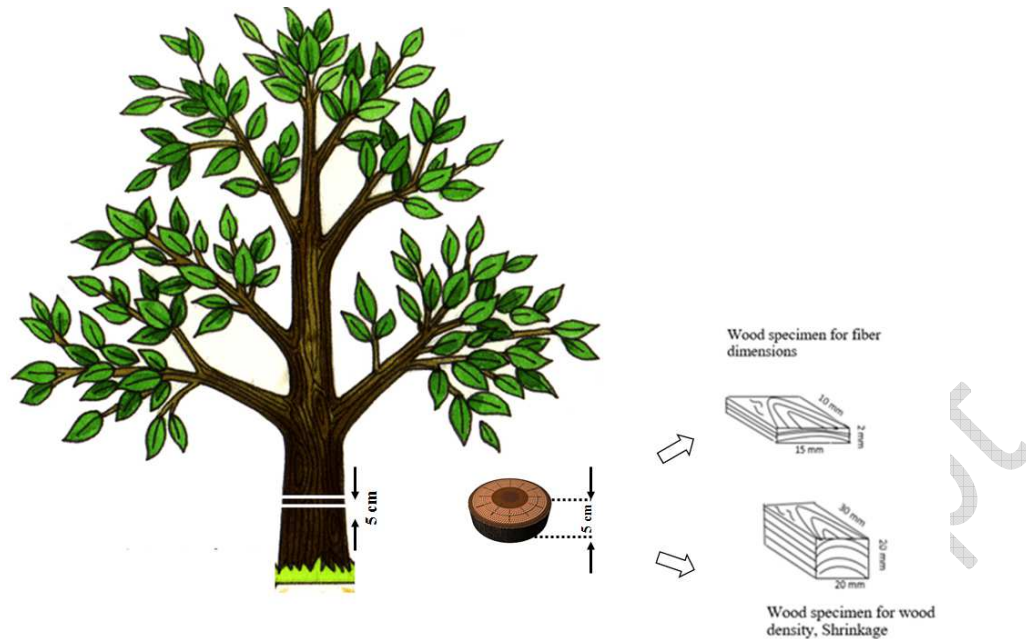

134

135 **Figure 1:** Diagram of sample preparation from a disk of *Q. brantii* to measure the
136 physical properties and fiber dimensions.

137 Soil study

138 To calculate soil properties, four soil samples were obtained at a 0-20 cm soil depth under the
139 canopy of each tree and mixed. Physicochemical properties of soil were measured, including
140 the percentage of clay, percentage of silt, percentage of sand, electrical conductivity (Ec), soil
141 reaction (pH), total nitrogen (N), available phosphorus (P), available potassium (K), and
142 percentage of organic matter.

143 Soil treatments were air-dried, then passed through a 2 mm sieve. Analysis of soil samples was
144 carried out at the laboratory of Agricultural and Natural Resources Research Center of Isfahan
145 Province, Isfahan, Iran. Percentage of clay, percentage of silt, percentage of sand were
146 calculated by the hydrometer method (Bouyoucos 1962). The pH and EC were determined
147 using a pH/EC meter. The total nitrogen was calculated using the Kjeldahl method (Zarinkafsh
148 1993). Phosphorus content was calculated by the Olsen method (Nelson and Sommers 1996).
149 Available potassium was measured by Flame photometry (Zarinkafsh 1993). Organic matter
150 content was estimated as in Walkley and Black (1934).

151

152 **Analysis study**

153 In this study, the influence of different sites was studied on the wood properties. Analysis of
 154 variance (ANOVA) and Duncan's test were applied to differentiate the significance of means
 155 and their grouping, respectively. PCA was also considered for determining the relationships of
 156 the site conditions and soil properties with the wood properties.

157

158

RESULTS AND DISCUSSION

159 Table 1 gives descriptive statistics analysis of *Q. brantii* population in three studied sites.

160 **Table 1:** Site conditions, soil physical and chemical properties, and stand-level variables at
 161 three altitudes.

	Site	1	2	3
Site conditions	Altitude (m a.s.l)	<1900	1900-2200	2200<
	Latitude (N) m	3558237	3558169	3556283
	Longitude (W) m	416736	418247	416161
	Mean annual precipitation (mm)	329	329,5	330
	Mean annual temperature (°C)	15,3	13,8	12,8
Stand-level traits	Basal Area (m ²)	79,94	100,84	97,80
	Stand Density (N/ha)	147	94	126
	Quadratic mean diameter (cm)	86,46	118,18	98,97
Soil physical properties	Percentage of clay (%)	32,56	33,82	36,13
	Percentage of silt (%)	43,24	45,43	42,66
	Percentage of sand (%)	24,20	20,75	21,41
	electrical conductivity (Ec)	1,06	0,77	0,72
	soil reaction (pH)	7,74	7,74	7,72
Soil chemical properties	Total nitrogen (Nsoil)(%)	0,18	0,25	0,21
	Available phosphorus (Psoil)(mg/kg)	9,45	9,57	9,06
	Available potassium (Ksoil)(mg/kg)	448,30	470,08	538,07
	Percentage of organic matter (OM) (%)	1,81	2,47	2,96

162

163 **Physical properties**

164 According to the ANOVA results, there are no significant differences in dry wood density
 165 between different sites. However, the sites affected the volumetric swelling (V_s) ($P < 0,01$)
 166 (Table 3), with the highest and lowest values measured at sites 2 and 1, respectively.
 167 Nevertheless, no significant differences were found between sites 2 and 3. The average values
 168 of V_s were $17,34 \% \pm 4,13 \%$. (Table 4).

169

170 **Biometric properties**

171 The analysis of variance shows that, in addition to the regular changes of fiber length at
172 different sites, the influence of sites on fiber length was highly significant ($p < 0,01$, Table 2).
173 In addition, the value of fiber length declined with raising altitudes (Table 3). The average
174 values of fiber length were $0,87 \text{ mm} \pm 0,08 \text{ mm}$. ANOVA results indicated significant
175 differences in fiber diameter among the sites ($P < 0,01$; Table 2), with the maximum and
176 minimum values which are measured at sites 1 and 2, respectively. It was found that there are
177 no significant differences between sites 2 and 3. The mean fiber diameter values were $20,50$
178 $\mu\text{m} \pm 1,25 \mu\text{m}$ (Table 3). Analysis showed no statistically significant differences between the
179 sites for cell wall thickness.

180

181

182

183

184

185

186

187

188

189

190

191

192 **Table 2:** Analysis of variance (ANOVA) of wood properties at different sites.

Wood properties		Sum of squares	df	Mean square	F	Sig.
H	Height (m)	27,04	2	13,52	2,98	0,07 ^{ns}
		108,80	24	4,53		
		135,84	26			
DBH	DBH (cm)	7240,52	2	3620,26	4,78	0,18 ^{ns}
		18172,22	24	757,18		
		25412,74	26			
SBA	Stem basal area (m ²)	2,50	2	1,25	5,586	0,01 ^{**}
		5,39	24	0,22		
		7,89	26			
SV	Stem volume (m ³)	76,04	2	38,02	4,10	0,03 [*]
		222,35	24	9,26		
		298,40	26			
CBA	Crown basal area (m ²)	180,98	2	90,49	1,74	0,19 ^{ns}
		1247,85	24	51,99		
		1428,84	26			
CD	Crown diameter (m)	3,10	2	1,55	2,12	0,14 ^{ns}
		17,54	24	0,73		
		20,64	26			
WDD	Wood dry density (g/cm ³)	0,00	2	0,00	0,35	0,71 ^{ns}
		0,09	24	0,00		
		0,1	26	194,36		
VS	Volumetric swelling (%)	388,72	2	2,25	86,27	0,00 ^{**}
		54,07	24			
		442,79	26			
FL	Fiber length (mm)	0,13	2	0,07	40,44	0,00 ^{**}
		0,04	24	0,00		
		0,18	26			
FD	Fiber diameter (μm)	18,02	2	9,01	9,51	0,00 ^{**}
		22,74	24	0,95		
		40,77	26			
CWT	Cell wall thickness (μm)	0,02	2	0,01	0,19	0,83 ^{ns}
		1,33	24	0,05		
		1,35	26			
ADI	Annual diameter increment	0,05	2	0,03	2,27	0,12 ^{ns}
		0,27	24	0,01		
		0,33	26			

* Significant at p < 0,05 probability level; ** Significant at p < 0,01 probability level; ns not-significant at p < 0,05 probability level.

193
 194
 195
 196
 197
 198
 199
 200

201 **Table 3:** Average (\pm SD) of physical and morphological properties of *Q. brantii*.

Site		1	2	3
Height (m)	H	9,92 \pm 1,74a	7,47 \pm 1,24a	8,56 \pm 1,00a
DBH (cm)	DBH	84,33 \pm 16,41a	85,56 \pm 20,69a	119,67 \pm 39,67a
Stem basal area (m ²)	SBA	0,57 \pm 0,23b	0,60 \pm 0,30b	1,23 \pm 0,72a
Stem volume (m ³)	SV	2,99 \pm 1,75b	2,37 \pm 1,53b	6,20 \pm 4,72a
Crown basal area (m ²)	CBA	23,05 \pm 7,22a	19,15 \pm 5,87a	16,77 \pm 8,32a
Crown diameter (m)	CD	5,36 \pm 0,84a	4,89 \pm 0,73a	4,53 \pm 0,96a
Wood dry density (g/cm ³)	WDD	0,77 \pm 0,04a	0,79 \pm 0,09a	0,78 \pm 0,06a
Volumetric swelling (%)	VS	12,01 \pm 1,31b	20,55 \pm 1,32a	19,46 \pm 1,81a
Fiber length (mm)	FL	0,94 \pm 0,02a	0,90 \pm 0,03b	0,77 \pm 0,06c
Fiber diameter (μ m)	FD	21,64 \pm 1,64a	19,87 \pm 0,24b	19,95 \pm 0,29b
Cell wall thickness (μ m)	CWT	5,76 \pm 0,22a	5,75 \pm 0,33a	5,81 \pm 0,05a
Annual diameter increment	ADI	1,00 \pm 0,12a	0,95 \pm 0,13a	1,06 \pm 0,06a
Values with different letters per row have significant differences with Duncan's test.				

202

203 **Principal Component Analysis (PCA)**

204 PCA discoveries hypothetical components that account for most of the variance in multivariate
 205 data (Davis 1986; Harper 1999). For plotting goals, PCA can reduce the data set to only two
 206 components (the first two variables). It can also be assumed that the most critical components
 207 are related to other main variables. In other words, it is necessary to discover the best axis
 208 between each axis before PCA can obtain a real axis. PCA scree plot of the studied variables
 209 is illustrated in Figure 2. The 'Scree plot' can also indicate the number of essential components.
 210 The plot showed a line plot of principal components in multivariate statistics. It can indicate
 211 the number of variables to retain in main components to keep in PCA.


212 **Correlation between soil, wood properties, and sites using PCA**

213 In Table 4, the eigenvalues and proportion of variance showed using the component axes. The
 214 first six principal components (PCs) have eigenvalues > 1 and contribute $\sim 89,09\%$ of the total
 215 variation in the set of data. Therefore, these PCs provide a decent approximation of the
 216 variation in the 21 axes (Figure 2). Jolliffe and Cadima (2016) showed that the threshold of
 217 cumulative $\sim 70\%$ variation is appropriate to keep the PCs for PCA. Although the first four

218 PCs have eigenvalues > 1 and contribute $\sim 75,42\%$, these PCs will be complicated to visualize
219 at once, and these PCs need to implement pairwise visualization (Table 4).

220

221

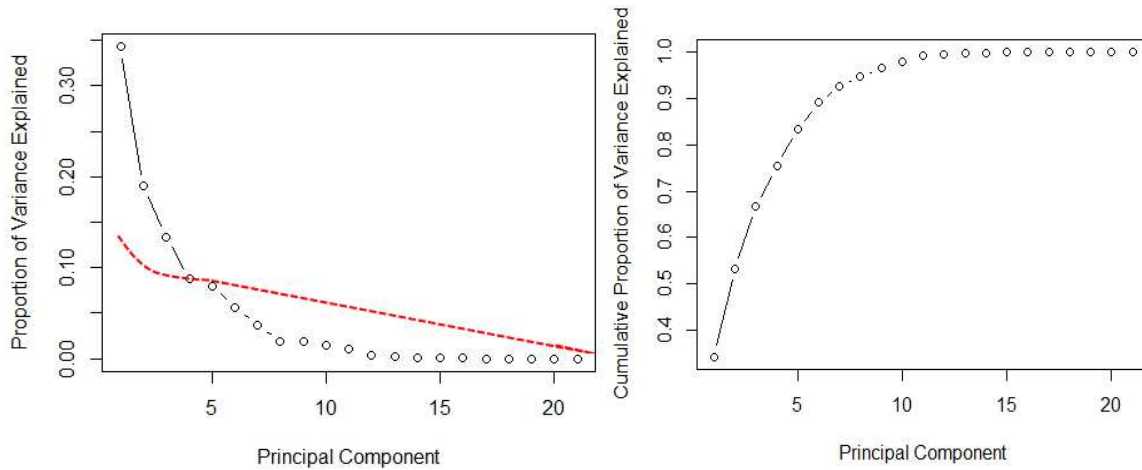

222 **Figure 2:** The scree plot for finding the optimal number of principal components (left plot),
223 and cumulative proportion of variance is explained (right plot).

224

225 In Table 4, the first and second PCs are the major to describe variance across the factors (soil
226 and wood factors). The percentage of eigenvalue for the two PCs is 34,31 % and 18,95 %, respectively.
227 The place of soil variables, wood features, and sites in different parts of Figures
228 2 and 3 is based on the correlation coefficient between factors.

229

230

231

232

233

234

235

236

237

Table 4: Percentage of variance and eigenvalues of PCA.

Axis	Eigenvalue	Percentage of variance
1	7,21	34,31
2	3,98	18,95
3	2,81	13,36
4	1,85	8,80
5	1,68	8,00
6	1,19	5,67
7	0,77	3,67
8	0,40	1,92
9	0,39	1,84
10	0,32	1,52
11	0,23	1,10
12	0,08	0,38
13	0,05	0,23
14	0,02	0,09
15	0,02	0,07
16	0,01	0,05
17	0,00	0,01
18	0,00	0,01
19	0,00	0,01
20	0,00	0,00
21	0,00	0,00

238

239 **Eigenvectors and correlation coefficients between soil and wood factors**

240 As shown in Table 5, eigenvectors include scores that show the weight of each factor (soil and
241 wood factors) on the two PCs ($-1 < \text{eigenvectors} < +1$); Kent and Coker (2001) demonstrated
242 that if the score of the eigenvector is close to ± 1 for each factor, the factor is more important
243 to weigh on the PCs. The eigenvectors for fiber length, volumetric swelling, percentage of clay,
244 percentage of organic matter, and Ec for the first PC, the value of DBH, height, stem basal
245 area, and stem volume for the second PC is more significant relative to other eigenvectors
246 factors. These factors perform the main role in explaining the first and second PCs of alteration.

247

248

249

250

251


Table 5: Eigenvectors of soil and wood factors for the first six PCs.

	PC 1	PC 2	PC 3	PC 4	PC 5	PC 6
DBH	-0,23	-0,35*	-0,06	0,21	-0,07	0,08
H	0,04	-0,43*	-0,08	0,16	-0,27	0,04
CD	0,16	0,13	0,32	0,43*	-0,06	-0,23
SBA	-0,24	-0,35*	-0,05	0,20	-0,06	0,05
CBA	0,15	0,13	0,34	0,42*	-0,05	-0,24
SV	-0,20	-0,39*	-0,05	0,17	-0,11	0,07
ADI	-0,09	-0,11	0,28	0,18	0,46*	-0,02
WDD	-0,03	-0,12	-0,30	0,20	0,10	-0,61*
FL	0,30*	-0,10	-0,26	0,19	-0,03	0,15
FD	0,21	-0,24	-0,06	-0,27*	-0,15	0,02
CWT	-0,05	0,05	0,31	0,22	-0,03	0,63*
VS	-0,29*	0,18	-0,22	0,16	-0,04	0,07
Nsoil	-0,06	0,16	-0,10	0,32	-0,35*	0,03
Psoil	0,04	0,17	0,01	-0,15	-0,61*	-0,08
Ksoil	-0,18	0,10	0,25	-0,03	-0,39*	-0,11
pH	0,30	0,08	-0,27*	0,17	-0,02	0,13
sand	0,26	-0,25	0,26*	-0,10	-0,04	-0,06
clay	-0,36*	0,01	0,10	-0,11	0,00	-0,10
silt	0,07	0,28	-0,38*	0,26	0,08	0,16
OM	-0,36*	0,09	-0,01	-0,06	0,01	-0,03
Ec	0,34*	-0,18	0,10	-0,03	-0,02	-0,01

Notes: ADI, mean annual diameter increment; CBA, crown basal area; CD, crown diameter; CWT, cell wall thickness; DBH, tree diameter at breast height; FL, fiber length; FD, fiber diameter; H, tree height; SBA, stem basal area; SV, stem volume; VS, volumetric swelling; WDD, oven-dry density; clay, percent of clay; Ec, electrical conductivity; Ksoil, available potassium; N soil, total nitrogen; OM, percent of organic matter; pH, soil reaction; Psoil, available phosphorus; sand, percent of sand; silt, percent of silt. * Features that contributed most for Axes 1–6.

252

253 As shown in Figure 3, the first PC describes 34,31 % of the total alteration. This PC is most
 254 greatly correlated with the soil properties available potassium, pH, percentage of sand,
 255 percentage of clay, percentage of organic matter, Ec; and wood properties crown basal area,
 256 crown diameter, fiber length, and volumetric swelling. The second PC explains 18,95 % of the
 257 alteration highly influenced by the soil properties total nitrogen, available phosphorus,
 258 percentage of silt, and wood properties DBH, height, stem basal area, stem volume, annual
 259 diameter increment, wood dry density, and fiber diameter.

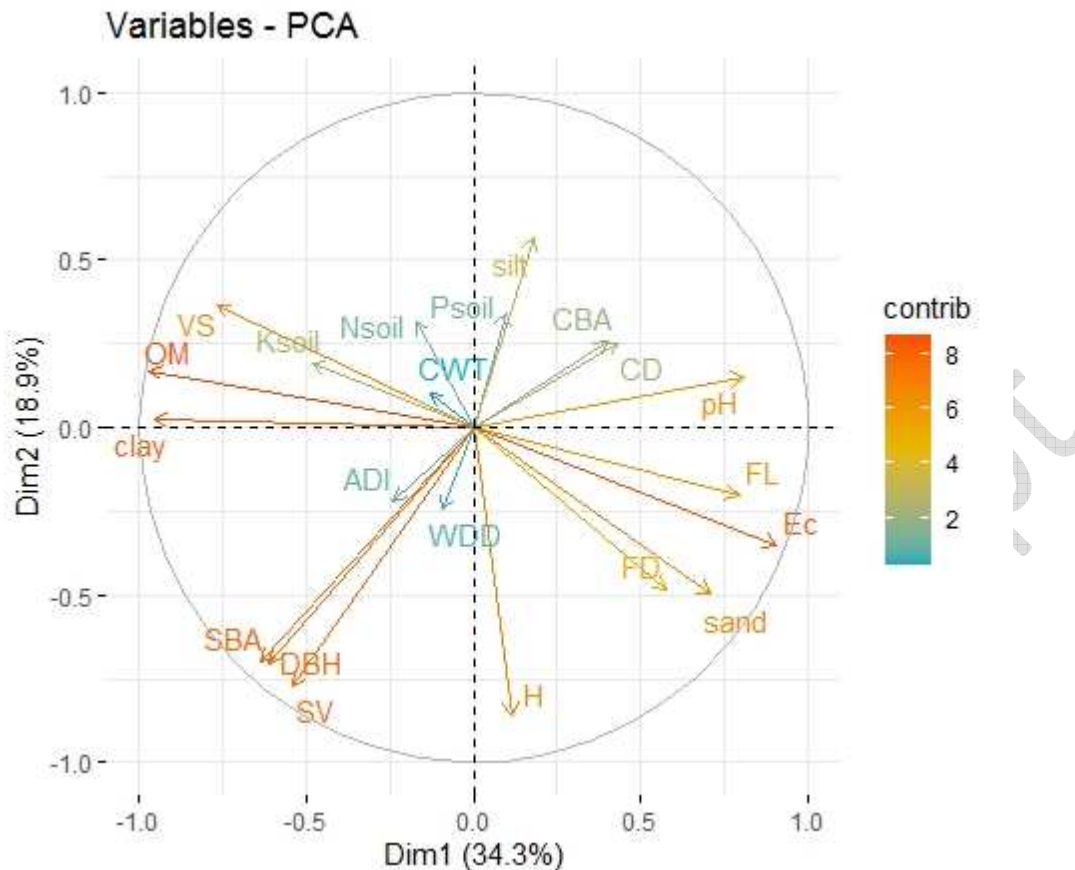

260

261

Figure 3: Distribution of soil and wood factors in the two first PCs.

262

Notes: ADI, mean annual diameter increment; CBA, crown basal area; CD, crown diameter; CWT, cell

263

wall thickness; DBH, tree diameter at breast height; FL, fiber length; FD, fiber diameter; H, tree height;

264

SBA, stem basal area; SV, stem volume; VS, volumetric swelling; WDD, oven-dry density; clay,

265

percent of clay; Ec, electrical conductivity; Ksoil, available potassium; Nsoil, total nitrogen; OM,

266

percent of organic matter; pH, soil reaction; Psoil, available phosphorus; sand, percent of sand; silt,

267

percent of silt.

268

In Figure 4, we see that sites were placed separately from each other. The PCA analysis of the

269

soil physical and chemical factors and wood physical and biometric parameters drive an

270

independent distribution of the samples that seem grouped when they relate to the same site

271

(Figure 4). Therefore, PCA displays apparent relationships of wood features fiber length and

272

fiber diameter and soil properties Ec, pH, and percentage of sand in site 1 (bottom right). The

273

PCA data also shows that site 2 (upper center) has the highest relationship with the crown basal


274

area, crown diameter, cell wall thickness and percentage of silt, total nitrogen, and available

275

phosphorus. Site 3 (left) has the best relationship with volumetric swelling, stem basal area,

276 DBH, and stem volume, and percentage of organic matter, percentage of clay, and available
277 potassium (Figure 4).

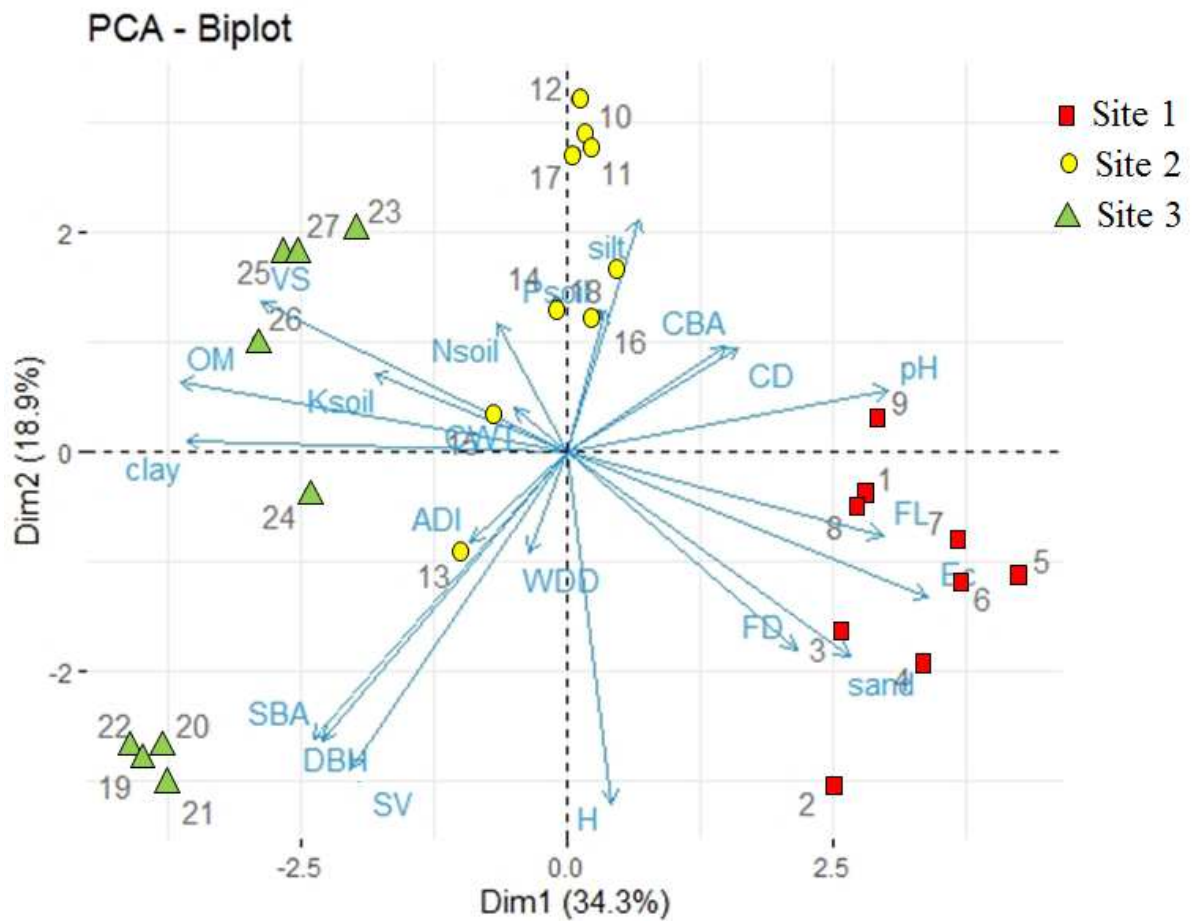

278

279 **Figure 4:** Distribution of soil and wood factors and forest sites in the two first PCs
280 axes. Notes: ADI, mean annual diameter increment; CBA, crown basal area; CD, crown diameter;
281 CWT, cell wall thickness; DBH, tree diameter at breast height; FD, fiber diameter; FL, fiber length; H,
282 tree height; SBA, stem basal area; SV, stem volume; VS, volumetric swelling; WDD, wood oven-dry
283 density; clay, percent of clay; Ec, electrical conductivity; Ksoil, available potassium; Nsoil, total
284 nitrogen; OM, percent of organic matter; pH, soil reaction; Psoil, available phosphorus; sand, percent
285 of sand; silt, percent of silt; 1-27, number of trees.

286 The width of the annual rings will be closely related to the wood density, which is important
287 in ring-porous species. The density of wood affect the main features of wood quality.
288 Therefore, wood quality can change with tree genetic, site conditions e.g. the soil components,
289 light and water, and other factors (Vintoniv *et al.* 2007; Grzeńkiewicz 2007; Hemery *et al.*
290 2008; Sopushynskyy and Teischinger 2013). The density of wood is generally lower on more
291 fertile soils, which are conducive to faster tree growth. This lead to an increase in the

292 percentage of wood vessels with thinner fiber walls on fertile soils (Lima *et al.* 2010;
293 Mevanarivo *et al.* 2020).

294 According to PCA results, wood density has a negatively correlate with silt and phosphorus
295 and a weak positive correlation with clay, sand, and potassium content. Similar results were
296 also observed by Kiaei (2014). Parsa (1993) stated that sandy soils reduce the density of the
297 wood. Maharani and Fernandes (2015) demonstrated that mineral elements (N, P, K) had a
298 major correlation with fiber length and wood density on *Shorea leprosula*, and these elements
299 had a notable correlation with wood density on *S. parvifolia*. In the meantime, these elements
300 had a non- considerable correlation with fiber length.

301 A number of studies have reported how components in the soil, especially the nitrogen content,
302 affect wood properties. Variation of wood density with components in the soil might vary
303 according to the amount of the nutrients present or applied, and on the species (Downes *et al.*
304 2014; Euftrade-Junior *et al.* 2017; Mevanarivo *et al.* 2020).

305 Volumetric swelling is positively correlated with available potassium, organic matter content,
306 clay, and total nitrogen. Meanwhile, it is negatively correlated with Ec. Moya and Perez (2008)
307 reported that normal radial shrinkage and normal tangential shrinkage were the best-correlated
308 factors with soil properties, even though that the less correlated factors were normal volumetric
309 shrinkage and specific gravity.

310 In the current study, fiber length positively correlated with the Ec and negatively correlated
311 with the available potassium, while fiber diameter positively correlated with soil sand
312 percentage. It was found that the fiber diameter had no significant correlation with elements of
313 N, P, and K. Cell wall thickness is positively correlated with the total nitrogen and available
314 potassium. In contrast, available phosphorus and percentage of organic matter presented a weak
315 relationship with cell wall thickness. Larson (1994) demonstrated that the mineral elements

316 have direct effects on vascular cambium. For the particular case of phosphorous, this element
317 increases cell division in the vascular cambium, and this element allows improved performance
318 in plants. The increase in cambial activity is followed by changes in the structure, mainly
319 because of pores of larger size, fibers with thinner cell walls, and more significant, presence of
320 parenchyma cells. Moya and Perez (2008) found such anatomical structures make a diminution
321 in the normal tangential shrinkage.

322 **CONCLUSIONS**

323 In this study, the relationship between soil physicochemical properties and some wood
324 properties of Persian oak was investigated. Soil characteristics (physical and chemical) had a
325 significant influence on oak wood properties. It can be stated that soil physical properties
326 correlated with fiber diameter, while soil chemical properties associated with cell wall
327 thickness. Meanwhile, soil physical and chemical properties correlated with wood dry density,
328 volumetric swelling, and fiber length. Zagros forests are particularly important for protecting
329 soil and water supply and they are known as a second renewable source of cellulose in Iran that
330 are threatened by environmental factors such as climate change, disease and pests, and human
331 activities. To forests rehabilitate with oak species, soil with a high content of potassium,
332 nitrogen, and organic matter is suggested because these factors play a crucial role in the wood
333 properties and wood quality.

334 **ACKNOWLEDGEMENTS**

335 We are grateful for financial support from the University of Zabol (Grant No. UOZ-GR-9618-
336 111).
337

338

339

340

341

342

REFERENCES

- 343
344 **Alikhani, L.; Rahmani, M.S.; Shabani, N.; Badakhshan, H.; Khadivi-Khub, A. 2014.**
345 Genetic variability and structure of *Quercus brantii* assessed by ISSR, IRAP and SCoT
346 markers. *Gene* 552(1): 176-183. <https://doi.org/10.1016/j.gene.2014.09.034>
- 347 **Bektas, I.; Alma, M.H.; Goker, Y.; Yuksel, A.; Gundogan, R. 2003.** Influence of site on
348 sapwood and heartwood ratios of Turkish calabrian pine. *Forest Prod J* 53(4): 48-50.
- 349 **Bouyoucos, G.J. 1962.** Hydrometer Method Improved for Making Particle Size Analysis of
350 Soils. *Agro J* 54: 464-465. <https://doi.org/10.2134/agronj1962.00021962005400050028x>
- 351 **Chaharmahal Va Bakhtiari Meteorological Administration. 2021.** *Koohrang Synoptic*
352 *Meteorological Station*. http://www.chbmet.ir/st_koohrang.asp.
- 353 **Cutter, B.E.; Coggeshall, M.V.; Phelps, J.E.; Stokke, D.D. 2004.** Impacts of forest
354 management activities on selected hardwood wood quality attributes: a review. *Wood Fiber*
355 *Sci* 36(1): 84-97. <https://wfs.swst.org/index.php/wfs/article/view/684>
- 356 **Davis, J.C. 1986.** *Statistics and Data Analysis in Geology*. John Wiley & Sons.
- 357 **Downes, G.M.; Harwood, C.; Washusen, R.; Ebdon, N.; Evans, R.; White, D.; Dumbrell,**
358 **I. 2014.** Wood properties of *Eucalyptus globulus* at three sites in Western Australia: Effects of
359 fertiliser and plantation stocking. *Aus For* 77(3-4): 179-188.
360 <https://doi.org/10.1080/00049158.2014.970742>.
- 361 **Eufrade-Junior, H.J.; Ballarin, A.W.; Villamagua-Vergara, G.C.; Guerra, S.P.S. 2017.**
362 Effect of silvicultural management on wood density from short rotation forest systems.
363 *Maderas-Cienc Tecnol* 9(3): 285-292. <https://doi.org/10.4067/S0718-221X2017005000024>.
- 364 **Franklin, G.L. 1945.** Preparation of thin sections of synthetic resins and wood-resin
365 composites, and a new macerating method for wood. *Nature* 155: 51.
366 <https://doi.org/10.1038/155051a0>.
- 367 **Ghazanfari, H.; Namiranian, M.; Sobhani, H.; Mohajer, R.M. 2004.** Traditional forest
368 management and its application to encourage public participation for sustainable forest
369 management in the northern Zagros Mountains of Kurdistan Province, Iran. *Scan J For*
370 *Res* 19(S4): 65-71. <https://doi.org/10.1080/14004080410034074>.
- 371 **Grzeńkiewicz, M. 2007.** COST Action E53: *Quality Control for Wood and Wood Products*.
372 Warsaw University of Life Sciences, Faculty of Wood Technology, pp: 178.

- 373 **Harper, D.A.T. 1999.** *Numerical Palaeobiology*. John Wiley & Sons.
- 374 **Hemery, G.; Spiecker, H.; Aldinger, E.; Kerr, G.; Collet, C.; Bell, S. 2007.** *Quality Control*
375 *for Wood and Wood Products*. COST E 53. The First Conference. Warsaw University of Life
376 Sciences, Faculty of Wood Technology: 1–173 p.
- 377 **International Organization for Standardization. ISO. 2016.** *Determination of Volumetric*
378 *Shrinkage*. 13061-14. International Organization for Standardization: Geneva, Switzerland.
- 379 **Jolliffe, I.T.; Cadima, J. 2016.** Principal component analysis: a review and recent
380 developments. *Philosophical Transactions of the Royal Society A: Mathematical, Physical and*
381 *Engineering Sciences* 374: 20150202. <https://doi.org/10.1098/rsta.2015.0202>
- 382 **Karamizadeh, S.; Abdullah, S.M.; Manaf, A.A.; Zamani, M.; Hooman, A. 2013.** An
383 overview of principal component analysis. *J Signal Infor Process* 4(3B): 173.
384 <http://dx.doi.org/10.4236/jsip.2013.43B031>
- 385 **Kaygin, B.; Esnaf, S.; Aydemir, D. 2016.** The effect of altitude difference on physical and
386 mechanical properties of Scots pine wood grown in Turkey- Sinop Province. *Drvna Ind* 67:
387 393-397. <https://doi.org/10.5552/drind.2016.1524>.
- 388 **Kent, M.; Coker, P. 1992.** *Vegetation description and analysis: A practical approach*. New
389 York: John Wiley and Sons.
- 390 **Kiaei, M. 2014.** Investigation on wood properties of Eldar pine (*Pinus eldarica* Medw) and its
391 relations to soil chemical and physical characteristics (in western of Mazandarn province
392 plantation). *Iranian J Wood Paper Sci Res* 29(2): 199-207.
393 <https://dx.doi.org/10.22092/ijwpr.2014.5683>
- 394 **Kiaei, M.; Moosavi, V.; Ebadi, S.E. 2019.** Effects of altitude on density and biometric
395 properties of hornbeam wood (*Carpinus betulus*). *Forest System* 28: e011.
396 <https://doi.org/10.5424/fs/2019282-14490>.
- 397 **Kooch, Y.; Jalilvand, H.; Bahmanyar, M.A.; Pormajidian, M.R. 2008.** The use of principal
398 component analysis in studying physical, chemical and biological soil properties in southern
399 Caspian forests (north of Iran). *Pakistan J Bio Sci* 11(3):
400 <https://doi.org/10.3923/pjbs.2008.366.372>.
- 401 **Lima, I.L.; Longui, E.L.; Santini Junior, L.; Garcia, J.N.; Florsheim, S.M.B. 2010.** Effect
402 of fertilization on cell size in wood of *Eucalyptus grandis* Hill ex Maiden. *Cerne* 16(4): 465-
403 472. <https://doi.org/10.1590/S0104-77602010000400006>.

- 404 **Maharani, R.; Fernandes, A. 2015.** Correlation between wood density and fiber length with
405 essential macro-nutrients on base of stem of *Shorea leprosula* and *Shorea parvifolia*. *KnE Life*
406 *Sciences* 625-629. <https://www.knepublishing.com/index.php/KnE-Life/article/view/231>
- 407 **Marini, F.; Manetti, M.C.; Corona, P.; Portoghesi, L.; Vinciguerra, V.; Tamantini, S.**
408 **Romagnoli, M. 2021.** Influence of forest stand characteristics on physical, mechanical
409 properties and chemistry of chestnut wood. *Sci Rep* 11: 1549. [https://doi.org/10.1038/s41598-](https://doi.org/10.1038/s41598-020-80558-w)
410 [020-80558-w](https://doi.org/10.1038/s41598-020-80558-w)
- 411 **Mevanarivo, Z.E.; Ramananantoandro, T.; Tomazello Filho, M.; Napoli, A.;**
412 **Razafimahatratra, A.R.; Razakamanarivo, H.R.; Chaix, G. 2020.** Variability in the
413 physico-chemical properties of wood from *Eucalyptus robusta* depending on ecological
414 growing conditions and forestry practices: The case of smallholdings in the Highlands of
415 Madagascar. *Maderas-Cienc Tecnol* 22(4): 425-438. [http://dx.doi.org/10.4067/S0718-](http://dx.doi.org/10.4067/S0718-221X2020005000401)
416 [221X2020005000401](http://dx.doi.org/10.4067/S0718-221X2020005000401)
- 417 **Moya, R.; Pérez, D. 2008.** Effects of physical and chemical soil properties on physical wood
418 characteristics of *Tectona grandis* plantations in Costa Rica. *J Trop For Sci* 248-257.
419 <https://www.jstor.org/stable/23616701>.
- 420 **Nazari, N.; Bahmani, M. Kahyani, S.; Humar, M.; Koch, G. 2020.** Geographic variations
421 of the wood density and fiber dimensions of the Persian oak wood. *Forests* 11(9): 1003.
422 <https://doi.org/10.3390/f11091003>.
- 423 **Nazari, N.; Bahmani, M.; Kahyani, S.; Humar, M. 2021.** Effect of site conditions on the
424 properties of hawthorn (*Crataegus azarolus* L.) wood. *J For Sci* 67(3): 113-124.
425 <https://doi.org/10.17221/125/2020-JFS>.
- 426 **Olfat, O.A.; Pourtahmasi, K. 2010.** Anatomical Characters in Three Oak Species (*Q. libani*,
427 *Q. brantii* and *Q. infectoria*) from Iranian Zagros Mountains. *AJBAS* 4(8): 3230-3237.
- 428 **Parsa, d. 1993.** *Wood Technology*. Tehran University Press.
- 429 **Rigatto, P.A.; Dedecek, R.A.; Monteiro de Matos, J.L. 2004.** Influence of soil attributes on
430 quality of *Pinus taeda* wood for cellulose Kraft production. *Rev Arv* 28: 267-273.
431 <https://doi.org/10.1590/S0100-67622004000200013>.

- 432 **Rossi, S.; Cairo, E.; Krause, C.; Deslauriers, A. 2015.** Growth and basic wood properties of
433 black spruce along an alti-latitudinal gradient in Quebec, Canada. *Ann For Sci* 72: 77–87.
434 <https://doi.org/10.1007/s13595-014-0399-8>.
- 435 **Safari, E.; Moradi, H.; Seim, A.; Yousefpour, R.; Mirzakhani, M.; Tegel, W.; Soosani, J.;**
436 **Kahle, H.P. 2022.** Regional Drought Conditions Control *Quercus brantii* Lindl. Growth within
437 Contrasting Forest Stands in the Central Zagros Mountains, Iran. *Forests* 13(4): p.495.
438 <https://doi.org/10.3390/f13040495>.
- 439 **Sagheb-Talebi, Kh. 2005.** Rehabilitation of temperate forests in Iran. In *Restoration of boreal*
440 *and temperate forests*. Stanturf, J.A.; Madsen, P. (eds.) CRC Press, 397-407.
- 441 **Sopushynskyy, I.; Teischinger, A. 2013.** *Diagnostic features of Fraxinus excelsior L. with*
442 *wavy-grained wood growing in Ukraine*. <https://depot.ceon.pl/handle/123456789/5274>
- 443 **Sousa, V.B.; Louzada, J.L.; Pereira, H. 2018.** Variation of ring width and wood density in
444 two unmanaged stands of the Mediterranean Oak *Quercus faginea*. *Forests* 9: 44.
445 <https://doi.org/10.3390/f9010044>.
- 446 **Topaloglu, E.; Ay, N.; Altun, L.; Serdar, B. 2016.** Effect of altitude and aspect on various
447 wood properties of Oriental beech (*Fagus orientalis* Lipsky) wood. *Turk J Agri For* 40: 397-
448 406. <https://doi.org/10.3906/tar-1508-95>.
- 449 **Tufekcioglu, A.; Kalay, H.Z.; Yilmaz, M. 2005.** Effects of some soil properties on the growth
450 of hybrid poplar in the Terme-Golardi region of Turkey. *Turk J Agri For* 29(3):221-226.
- 451 **Vintoniv, I.; Sopushynskyy, I.; Teischinger, A. 2007.** *Derevinoznavstvo* [Wood Science].
452 Navčal'nij posibnik, Lviv, Apriori, Ukraine.312 p.
- 453 **Walkley, A.; Black, I.A. 1934.** An examination of Degtjareff method for determining soil
454 organic matter and a proposed modification of the chromic acid titration method. *Soil Sci* 37:
455 29-37.
456 [https://journals.lww.com/soilsci/Citation/1934/01000/An_Examination_of_the_Degtjareff_M](https://journals.lww.com/soilsci/Citation/1934/01000/An_Examination_of_the_Degtjareff_Method_for.3.aspx3)
457 [ethod_for.3.aspx3](https://journals.lww.com/soilsci/Citation/1934/01000/An_Examination_of_the_Degtjareff_Method_for.3.aspx3)
- 458 **Yáñez-Espinosa, L.; Terrazas, T.; López-Mata, L. 2001.** Effects of flooding on wood and
459 bark anatomy of four species in a mangrove forest community. *Trees* 15(2): 91-97.
460 <https://doi.org/10.1007/s004680000081>.
- 461 **Zarinkafsh, M. 1993.** *Soil survey, methods of assessment morphologic and analysis for soil,*
462 *water and plant*. Tehran University Publication, Tehran, Iran.

- 463 **Zobel, B.J.; Van Buijtenen, J.P. 1989.** *Wood variation: its causes and control.* Springer
464 Science and Business Media. <https://doi.org/10.1007/978-3-642-74069-5>.

Accepted manuscript