

**Dieses Dokument ist eine Zweitveröffentlichung (Postprint) /**

**This is a self-archiving document (accepted version):**

Min Hyuk Park, Young Hwan Lee, Thomas Mikolajick, Uwe Schroeder, Cheol Seong Hwang

**Review and perspective on ferroelectric HfO<sub>2</sub>-based thin films for memory applications**

**Erstveröffentlichung in / First published in:**

*MRS Communications*. 2018, 8, S. 795-808 [Zugriff am: 17.10.2022]. Springer. ISSN 2159-6867.

DOI: <https://doi.org/10.1557/mrc.2018.175>

Diese Version ist verfügbar / This version is available on:

<https://nbn-resolving.org/urn:nbn:de:bsz:14-qucosa2-814866>

# Review and perspective on ferroelectric HfO<sub>2</sub>-based thin films for memory applications

**Min Hyuk Park**, NaMLab gGmbH, Noethnitzer Str. 64, 01187 Dresden, Germany; School of Materials Science and Engineering, College of Engineering, Pusan National University, 2 Busandaehak-ro 63beon-gil, Geumjeong-gu, Busan 46241, Republic of Korea

**Young Hwan Lee**, Department of Materials Science and Engineering, Inter-University Research Center, College of Engineering, Seoul National University, 1 Gwanak-ro, Gwanak-gu, Seoul 08826, Republic of Korea

**Thomas Mikolajick**, NaMLab gGmbH, Noethnitzer Str. 64, 01187 Dresden, Germany; Chair of Nanoelectronic Materials, TU Dresden, Dresden 01069, Germany

**Uwe Schroeder**, NaMLab gGmbH, Noethnitzer Str. 64, 01187 Dresden, Germany

**Cheol Seong Hwang**, Department of Materials Science and Engineering, Inter-University Research Center, College of Engineering, Seoul National University, 1 Gwanak-ro, Gwanak-gu, Seoul 08826, Republic of Korea

Address all correspondence to Uwe Schroeder at [Uwe.Schroeder@namlab.com](mailto:Uwe.Schroeder@namlab.com), Cheol Seong Hwang at [cheolsh@snu.ac.kr](mailto:cheolsh@snu.ac.kr)

## Abstract

The ferroelectricity in fluorite-structure oxides such as hafnia and zirconia has attracted increasing interest since 2011. They have various advantages such as Si-based complementary metal oxide semiconductor-compatibility, matured deposition techniques, a low dielectric constant and the resulting decreased depolarization field, and stronger resistance to hydrogen annealing. However, the wake-up effect, imprint, and insufficient endurance are remaining reliability issues. Therefore, this paper reviews two major aspects: the advantages of fluorite-structure ferroelectrics for memory applications are reviewed from a material's point of view, and the critical issues of wake-up effect and insufficient endurance are examined, and potential solutions are subsequently discussed.


## Introduction

Ferroelectric properties in fluorite-structure oxides were first reported in 2011 by Böscke et al. and have since attracted increasing interest in the field of ferroelectricity and nonvolatile memories.<sup>[1-6]</sup> Figure 1 shows the variations in the annual number of papers on fluorite-structure ferroelectrics and the annual citations of the original paper by Böscke et al.<sup>[1]</sup> since 2011. As shown in the figure, the number of papers is rapidly increasing, and more than 100 papers are expected to be published in 2018 despite 8 years short history of fluorite-structure ferroelectrics. Various applications, such as ferroelectric memories,<sup>[3,7-10]</sup> energy harvesters,<sup>[11,12]</sup> electrostatic supercapacitors,<sup>[12-14]</sup> electrocaloric coolers,<sup>[11,12,15,16]</sup> and pyroelectric sensors,<sup>[17,18]</sup> have been suggested for fluorite-structure ferroelectrics due to their advantages over the conventional perovskite-structure ferroelectrics. Ferroelectric memories with ferroelectric doped HfO<sub>2</sub> have also been suggested to be useful for neuromorphic devices and random-number generators.<sup>[19,20]</sup>

The ferroelectric memory is one of the most important applications of fluorite-structure ferroelectrics.<sup>[21-23]</sup> Two spontaneous polarization states can be written electrically, and the written states can be retained even without power supply. The write speed and energy efficiency are sufficiently high for realizing a nonvolatile random access memory. As a result, ferroelectrics have been considered as a promising

material for future memory devices. One version of a memory device based on ferroelectrics is the capacitor-based ferroelectric random access memory (FeRAM), whose cell generally consists of one transistor and one capacitor (1T-1C). Its overall structure is very similar to that of a dynamic random access memory (DRAM), except that the capacitive layer of the capacitor was replaced by a ferroelectric material, and the plate line of FeRAM does not remain at a constant voltage, as in DRAM, but needs to be pulsed to switch the ferroelectric polarization. The addition of the plate line increases the capacitive load during the read-write operations, limiting the access speed, and additionally complicates the layout of the memory.

Due to the limited memory array size of perovskite-based FeRAM capacitors, the commercialization of FeRAM is currently limited to niche markets. Further scaling is not possible due to the high physical thickness of the perovskite layer (typically ~70 nm) and the inability to create three-dimensional (3D) capacitors, as in DRAM.<sup>[23]</sup> The state-of-the-art technology node is still 130 nm,<sup>[3,24,25]</sup> a value one order of magnitude higher than the values of the current technology nodes of DRAM and NAND flash memory. Such a large feature size limits the use of the devices for applications where a high operation speed and low power consumption are essential, due to the much higher cost per bit compared to DRAM and NAND

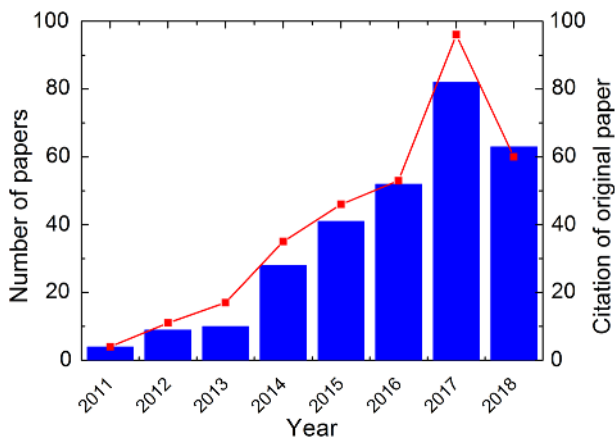

**Figure 1.** Annual number of papers (blue bars, left  $y$ -axis) and annual citations of the original paper (Ref. 1, red dots, right  $y$ -axis) on fluorite-structure ferroelectrics (source: Google Scholar, June 6th, 2018). The result was searched using keywords ((HfO<sub>2</sub>) or (hafniumoxide) or (hafniumdioxide) or (ZrO<sub>2</sub>) or (zirconiumoxide) or (zirconiumdioxide)) and ((ferroelectric) or (piezoelectric) or (pyroelectric)), and irrelevant results were manually screened out. It should be noted that the only the number of papers and citations until June 6 is shown in 2018.

flash memory combined at the equivalent functionality. Other critical issues will be reviewed in the next section.

The fluorite-structure ferroelectrics are expected to resolve most of the aforementioned critical issues of perovskite-structure ferroelectrics. In fact, HfO<sub>2</sub> and ZrO<sub>2</sub>, the two most frequently studied fluorite-structure materials in the semiconductor field, are already being utilized as the materials for the gate oxide layer of the logic field effect transistors (FETs) and the dielectric layers of the DRAM capacitors, respectively.<sup>[26]</sup> Thus, matured atomic layer deposition (ALD) techniques are already available. Simply adding a rapid thermal process for the appropriate crystallization of HfO<sub>2</sub> or ZrO<sub>2</sub> thin films prompts ferroelectric behavior in these materials. Nonetheless, the fluorite-structure ferroelectrics still have several issues that need to be resolved before they can be adopted for memory applications. Among these, the problems of the wake-up effect and insufficient endurance are critical, and numerous studies have been conducted on these issues. In this review paper, therefore, the aforementioned reliability issues of fluorite-structure ferroelectrics for memory applications are intensively reviewed, and perspectives for resolving such issues are provided based on the data published in the recent literature.


### **Advantages of fluorite-structure ferroelectrics over conventional ferroelectrics for memory applications**

In the case of the conventional Pb(Zr,Ti)O<sub>3</sub>(PZT)- or SrBi<sub>2</sub>Ta<sub>2</sub>O<sub>9</sub>(SBT)-based 1T-1C FeRAMs using planar capacitors, the main scaling issue is the limited availability of charge for stable sensing. According to Maruyama et al.<sup>[27]</sup>, at least double remanent polarization ( $2P_r$ ) of 84  $\mu\text{C}/\text{cm}^2$  is required

for a stable operation of a 1T-1C FeRAM with a 90 nm technology node. For practical polycrystalline PZT thin films,  $2P_r$  is limited to  $<\sim 80 \mu\text{C}/\text{cm}^2$ , and other polycrystalline ferroelectrics, such as SBT and (Bi,La)<sub>4</sub>Ti<sub>3</sub>O<sub>12</sub> (BLT), have even lower  $2P_r$  values.<sup>[28]</sup> BiFeO<sub>3</sub> (BFO) can have  $2P_r$  values above 200  $\mu\text{C}/\text{cm}^2$  and was suggested as a solution to extend the scalability.<sup>[27]</sup> BFO's low bandgap and associated large leakage current,<sup>[29]</sup> however, limit its practical application in memory devices. The  $2P_r$  values of perovskite-structure ferroelectrics are usually degraded at several-tens-of-nm-scale devices due to the damaging effect of the side wall regions, which may be caused by the patterning processes.

Therefore, the fabrication of 3D nanoscale capacitors is essential to overcome the scaling issue of 1T-1C FeRAM. There are several critical issues, however, with regard to the fabrication of 3D capacitors based on the conventional ferroelectrics. The first issue is the difficulty of depositing perovskite-structure ferroelectrics with two or more cation components in high-aspect-ratio structures via ALD. There have been several reports on the ALD of perovskite-structure oxide, but it is very difficult to achieve sufficient ferroelectric properties for memory applications using ALD.<sup>[30,31]</sup> The even more fundamental issue is the scaling of the physical thickness of ferroelectric thin films. To fabricate 3D capacitors, the total thickness of the capacitor needs to be smaller than  $\sim 1/3$  the technology node. The thickness of the conventional perovskite-structure ferroelectrics, however, is limited to 50–70 nm to achieve robust ferroelectricity.<sup>[32]</sup> As a result, the conventional perovskite-structure ferroelectrics cannot be utilized for the sub-130 nm technology node. There have been extensive discussions on the critical thickness of the ferroelectric properties of perovskite-structure materials because the ferroelectric properties of perovskite oxides have been experimentally shown to become degraded with decreasing thickness below a certain level.<sup>[33–36]</sup> It is now accepted that the ferroelectric properties can be retained even with several atomic layers' thickness for epitaxial films grown on selective single-crystalline substrates. Such films lack complementary metal oxide semiconductor (CMOS) compatibility, however, and are thus not suitable for mass production.<sup>[33–36]</sup> Nonetheless, in practical metal-ferroelectric-metal capacitors that have ferroelectric materials with a polycrystalline structure, degradation of the ferroelectric properties with decreasing film thickness is generally observed. Until now, there is no fabrication method that is known to integrate single-crystalline perovskite structures into CMOS devices, and to maintain defect-free properties up to the end of the integration process.

As mentioned earlier, FeRAM based on perovskite-structure ferroelectrics cannot be scaled down to below 130 nm, but the ferroelectric HfO<sub>2</sub>-based film can make a breakthrough and achieve 3D capacitors. Polakowski et al.<sup>[37]</sup> reported the ferroelectric properties of the TiN/Al:HfO<sub>2</sub>/TiN-based deep-trench capacitors with a  $P_r$  per projected area of 152  $\mu\text{C}/\text{cm}^2$ . Figure 2 shows a cross-sectional transmission electron microscopy (TEM) image of the fabricated deep-trench capacitor with

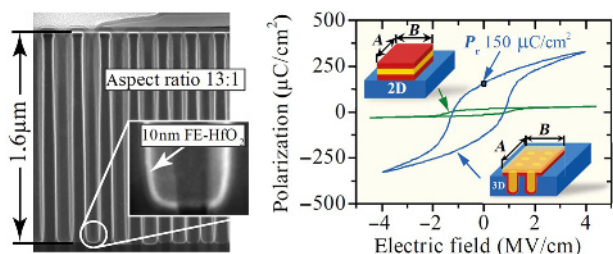

**Figure 2.** Cross-sectional TEM image (left panel) and projected polarization-electric field curve (right panel) of the 3D TiN/Al:HfO<sub>2</sub>/TiN capacitor. In the right panel, A and B are width and length of the projected area, respectively, so the projected area can be calculated from (A × B). Adapted with permission from Ref. 9 (IEEE, 2013).


Al:HfO<sub>2</sub> (left panel) and its projected polarization-electric field (P-E) curve (right panel).<sup>[37]</sup> Although the  $P_r$  value of the planar capacitor was only  $15 \mu\text{C}/\text{cm}^2$ , the  $1.6\text{-}\mu\text{m}$ -deep-trench capacitor with an aspect ratio of 13:1 could increase the  $P_r$  per projected area by one order of magnitude, which is very close to the degree of increase of the capacitor area.<sup>[37]</sup> To date, the largest  $P_r$  value ever reported for fluorite-structure (planar) ferroelectrics is  $45 \mu\text{C}/\text{cm}^2$  for a La:HfO<sub>2</sub>.<sup>[7]</sup> If this film is grown in the previous 3D capacitor structure, a  $P_r$  of  $\sim 450 \mu\text{C}/\text{cm}^2$  per projected area can be achieved.

The scaling limit of HfO<sub>2</sub>-based FeRAM can be estimated through a simple calculation.<sup>[38]</sup> Using HfO<sub>2</sub>-based ferroelectrics, a FeRAM capacitor can be fabricated with dimensions similar to those of a DRAM capacitor, since the equivalent material (HfO<sub>2</sub>) is being utilized as a capacitive layer. Therefore, a potential scaling limit can be estimated through simple comparison with the state-of-the-art DRAM. The amount of charge that can be stored in a DRAM capacitor ( $Q$ ) can be calculated using the simple equation  $Q = \epsilon_0 \epsilon_r V/t$ , where  $\epsilon_0$ ,  $\epsilon_r$ ,  $V$ , and  $t$  are the permittivity of vacuum, the dielectric constant of the dielectric layer, the operation voltage, and the film thickness, respectively. For the DRAM capacitors, the  $\epsilon_r$ ,  $V$ , and  $t$  are roughly 20, 0.5 V, and 6 nm, respectively. With these values, the charge on a DRAM capacitor is calculated to be approximately  $1.5 \mu\text{C}/\text{cm}^2$ , which is about 5–10% of the  $2P_r$  value of ferroelectric-HfO<sub>2</sub>-based films with a similar film thickness. With a polarization value that is more than one order of magnitude higher, HfO<sub>2</sub>-based FeRAMs are expected to scale better than DRAM. For the practical scaling of FeRAMs, however, the effect of the film thickness needs to be carefully examined especially if the required film thickness is below 5 nm.

Two other types of ferroelectric memories, the ferroelectric field effect transistor (FeFET) and the ferroelectric tunnel junction (FTJ), have also been considered promising candidates.<sup>[39]</sup> FeFET is a simple nonvolatile memory cell consisting of only a single transistor, where the gate oxide layer of the metal-oxide-semiconductor FET was replaced by a ferroelectric layer. Depending on the polarization orientation, the threshold voltage is modulated, and information can be directly stored in a 1T memory cell. Unlike in FeRAM, the data stored in

FeFET can be read non-destructively. FTJ is based on the tunneling conduction of electrical carriers through an extremely thin ferroelectric layer (generally a few nm level), and the tunneling current density is determined by the polarization direction of the ferroelectric layer relative to the configuration of the two different electrodes. FTJ is also considered as a promising candidate for the next-generation nonvolatile memory, but it also has critical issues that are not easy to overcome. For practical device fabrication with a large wafer area (300 mm in diameter), it is very difficult to have a uniform thickness over the entire area. As FTJ is based on the tunneling conduction mechanism, only small thickness non-uniformity in atomic scale can make significant differences. Even worse, for uniform device performance, precise control of the interface property between the thin ferroelectric layer and the semiconductor or electrode layers is critical. To simplify the device design and to relax the requirements for the ferroelectric layer, an alternative structure with additional tunneling (dielectric) layer was proposed. In the structure, the polarization is switched in the ferroelectric, but the tunneling current is limited by a thin tunneling layer.<sup>[40–42]</sup> Several issues, however, including the insufficient read current, still need to be resolved before putting such structure in practical memory arrays. Thus, FeFET is considered a nearer-future candidate compared with FTJ. Accordingly, in this review, the focus is mainly on the capacitor-based 1T-1C FeRAM and FeFET devices.

The conventional perovskite-structure ferroelectrics have been intensively studied to date, but the perovskite-based FeFETs still have critical issues. First, Si compatibility is more important for FeFET than for 1T-1C FeRAM because in the former, the ferroelectric layer is in direct contact with the Si channel. The conventional ferroelectric materials, such as PZT, SBT, and BLT, are not Si-compatible, and interface reactions like silicate formation prevent them from having direct contact with Si, and further deter any high-temperature procedure afterward. Additionally, in a FET arrangement, the ferroelectric will be in a serial connection with the depleted channel capacitance. As perovskite-structure ferroelectrics have very high  $\epsilon_r$  in the range of a few hundred, the applied voltage is divided in an unbalanced manner. This voltage divider effect becomes even more severe when a low- $\epsilon_r$  interfacial layer is formed between the ferroelectric layer and the Si channel to avoid the aforementioned interfacial reactions, and a severe depolarization field is generated in the retention condition as a result.<sup>[25,43,44]</sup> Several methods, such as the insertion of a high- $k$  buffer layer below the ferroelectric layer and replacing the Si channel with an oxide semiconductor, have been suggested to resolve this issue.<sup>[25,44–47]</sup> Figure 3(a) shows a cross-sectional TEM image of a FeFET with a Ca:SBT ferroelectric and a HfO<sub>2</sub> buffer layer on a Si substrate.<sup>[48]</sup> The HfO<sub>2</sub> buffer layer was inserted to prevent low-quality interface formation between Ca:SBT and the Si substrate.<sup>[48]</sup> It is noteworthy that a HfO<sub>2</sub> or doped HfO<sub>2</sub> layer was also used as a high- $\epsilon_r$  buffer layer due to its good Si compatibility.<sup>[44–48]</sup> The best retention properties for FeFET with the conventional

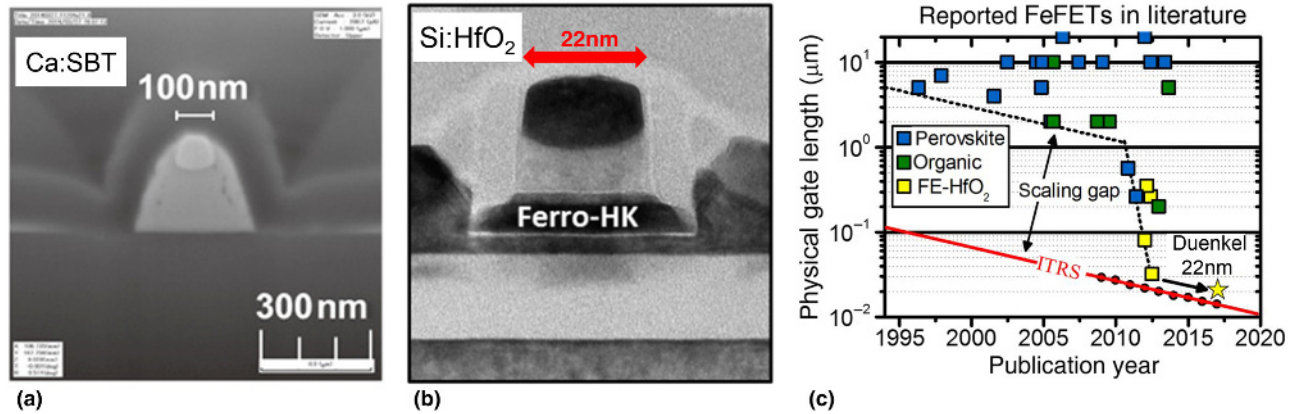


**Figure 3.** Cross-sectional TEM images of a FeFET with (a) Ca:SBT and (b) Si:HfO<sub>2</sub> ferroelectric gate oxide layer, respectively. (c) Physical gate length of logic FETs and FeFETs in the literature. Figure 3(a) was reproduced from Ref. 48 with permission (The Japan Society of Applied Physics, 2015), and Fig. 3(b) and 3(c) were reproduced from Ref. 49 with permission (IEEE, 2017).

ferroelectrics have been reported with a rather thick SBT ferroelectric in combination with a HfO<sub>2</sub>-based buffer layer.<sup>[44-48]</sup>

Figure 3(b) shows the cross-sectional TEM image of a FeFET with a ferroelectric-Si:HfO<sub>2</sub> thin film with a 22 nm technology node.<sup>[49]</sup> Unlike the SBT-based FeFET in Fig. 3(a), the thickness of the ferroelectric layer and the gate length can be reduced by ~80%. It is important to note that the memory window (MW) of a FeFET is determined by the voltage margin for switching ferroelectric polarization, which can be estimated as  $MW = 2E_c \times t_{Fe}$ , where  $E_c$  is the coercive field, and  $t_{Fe}$  is the thickness of the ferroelectric layer. As a result, the rather low  $E_c$  of perovskite-structure ferroelectrics (typically 50-100 kV/cm) will require a very thick ferroelectric in the 100 nm range. This, in turn, significantly limits the scalability of a FeFET device based on perovskite-structure ferroelectrics.<sup>[2-6,44]</sup> Therefore, a high  $E_c$  of fluorite-structure ferroelectrics with a

0.8-2.0 MV/cm range is more advantageous for FeFET applications. Figure 3(c) shows the scaling in the physical gate length of logic FET and FeFET over a period of about 20 years. As shown in the figure, there was a technology gap of one to two orders of magnitude between logic FET and FeFET before the adoption of fluorite-structure ferroelectrics, but the gap almost disappeared after the introduction of ferroelectric HfO<sub>2</sub>. Currently, the smallest reported technology node for FeFET is 22 nm.<sup>[49]</sup>

The high  $E_c$  together with the rather low  $\epsilon_r$  of ferroelectric HfO<sub>2</sub> can significantly improve the retention of FeFET,<sup>[50]</sup> which has been the most critical issue for FeFETs with conventional perovskite-structure ferroelectrics. To date, the best retention property reported for a conventional material was the use of an SBT-based FeFET with a HfAlO<sub>x</sub> buffer layer [Fig. 4(a)].<sup>[47]</sup> As shown in the figure, the retention was measured for a period of 37 days, and an extrapolated  $I_{on}/I_{off}$

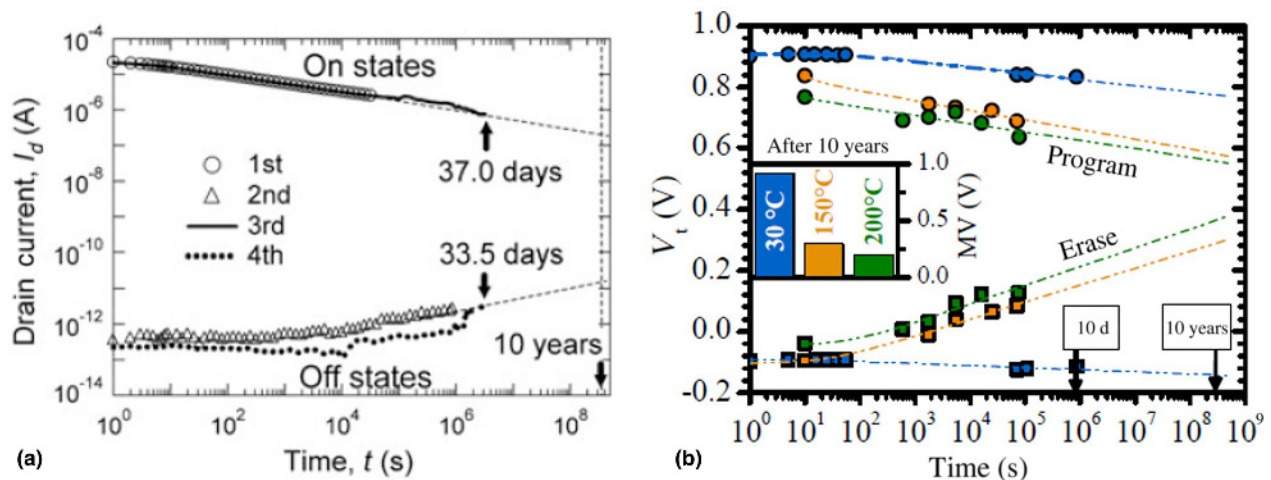

**Figure 4.** Retention test results for FeFETs with (a) an SBT/HfAlO gate oxide layer and (b) a Si:HfO<sub>2</sub> gate oxide layer, respectively. Figure 4(a) was reproduced from Ref. 47 with permission (The Japanese Society of Applied Physics, 2005), and Fig. 4(b) was reproduced from Ref. 9 with permission (IEEE, 2013).

ratio of  $10^4$  after 10 years was achieved.<sup>[47,51]</sup> Figure 4(b) shows the retention test result of the FeFET with ferroelectric Si:HfO<sub>2</sub>.<sup>[52]</sup> As shown in the figure, a memory window of 0.9 V was extrapolated after 10 years, and even at 200 °C, a memory window of 0.2 V was retained. Despite its short development time of only 8 years, the retention property of HfO<sub>2</sub>-based FeFET is comparable with or even better than the best-reported retention properties from the perovskite-based FeFETs. It is important to note that on the integrated memory arrays of 28 and 22 nm technology nodes, comparable retention data were achieved.<sup>[8,49]</sup>

The spatially inhomogeneous distribution of  $E_c$  of polycrystalline fluorite-structure ferroelectrics can be another potential issue for scaled FeFETs. Since the lateral grain diameter of ALD grown fluorite-structure ferroelectrics are generally comparable with their film thickness, only a few grains are expected to present in the gate stack of a scaled 28 or 22 nm device. Each grain may have a different  $E_c$  for switching, resulting from a different orientation or the inhomogeneity of the material. The grain size dependent coercive field is also known for perovskite structure ferroelectrics.<sup>[53]</sup> Accordingly, a different region within the channel may have a slightly different threshold voltage, leading to the stepwise switching of the devices.<sup>[10,54]</sup> Hence, if the grain distribution cannot be precisely controlled, the threshold voltage distribution, which is strongly related to the  $E_c$  distribution in the ferroelectric layer, of scaled devices can increase as scaling proceeds.<sup>[49]</sup> With further scaling, however, FinFET or gates around the structures are necessary, where the effective gate area is larger compared with the planar devices, which will mitigate this issue.

Fluorite-structure ferroelectrics have other advantages over perovskite-structure ferroelectrics for memory applications. For perovskite materials like PZT, special electrode materials such as Ir, IrO<sub>2</sub>, and SrRuO<sub>3</sub> are required to show reliable properties.<sup>[55]</sup> In layered perovskites like SBT, this is not necessary, but due to the complicated crystal structure of SBT, a very high thermal budget for annealing is necessary, leading to severe problems in integration, specifically for the stacked 1T-1C memory cells.<sup>[56]</sup> The metal nitride electrodes, however, which are the standard electrode materials in the semiconductor industry, can be utilized for fluorite-structure ferroelectrics. This will improve the cost-effectiveness and CMOS compatibility of fluorite-structure ferroelectrics. Furthermore, Park et al. reported that the ferroelectric (Hf,Zr)O<sub>2</sub> (HZO) film could endure the adverse effect of hydrogen annealing,<sup>[57]</sup> whereas the ferroelectric properties of perovskite oxides could be seriously degraded by hydrogen annealing.<sup>[58,59]</sup> TiN does not bear the catalytic activity of dissociating the H<sub>2</sub> molecules into the H atoms, which is the case for the Pt electrode for the conventional perovskite-structure ferroelectrics, making TiN/HZO/TiN even more robust against the H<sub>2</sub> effect.<sup>[57]</sup>

## Remaining issues in fluorite-structure ferroelectrics


In the previous section, the advantages of fluorite-structure ferroelectrics over the conventional perovskite-structure

ferroelectrics for ferroelectric memories were reviewed. This section will discuss the remaining issues in fluorite-structure ferroelectrics for the same applications, the wake-up effect, and endurance (or fatigue), which will be dealt with in the sections Wake-up effect and Limited endurance, respectively. The other critical issue in ferroelectric memories is imprint, which is the tendency of a ferroelectric to stabilize the state it is stored in, and leads to a loss of retention of the opposite state.<sup>[60]</sup> The imprint effect is generally associated with charge trapping at the defect sites related to oxygen vacancies, but to date, only basic studies have been conducted on this topic for doped HfO<sub>2</sub> ferroelectrics.<sup>[61,62]</sup> As fatigue and imprint generally have the same origin,<sup>[63,64]</sup> it is expected that the imprint would be improved when the other reliability issues such as wake-up effect and endurance are mitigated. Therefore, the main focus in the following two subsections will be on the wake-up effect and endurance issues.

### Wake-up effect

The first critical issue is the so-called “wake-up effect,” which was first studied by Zhou et al. in ferroelectric Si:HfO<sub>2</sub> thin films.<sup>[65]</sup> This effect can also be observed in perovskite-structure ferroelectrics,<sup>[66]</sup> but the number of cycles to the woken-up state of the order of  $10^3$  is negligible compared with the overall cycling stability of the order of  $10^{13}$ – $10^{15}$  as long as the initial  $P_r$  is sufficiently high.<sup>[67]</sup> Moreover, optimized PZT films using oxide electrodes show negligible wake-up effect, which is not the case for the HfO<sub>2</sub>-based ferroelectrics. Figure 5(a) shows the general switching current-electric field curves of ferroelectric-HfO<sub>2</sub>-based thin films within three different stages (pristine, woken-up, and fatigued) of field cycling, while Fig. 5(b) accordingly shows the changes in  $P_r$  with the increasing number of field cycles. In the pristine state [the blue dotted curve in Fig. 5(a)], the switching current curve has two peaks in both the positive and negative bias regions. This is different from the ideal switching current curve of a ferroelectric, where only a single switching current peak is seen at each  $E_c$ . During the electric field cycling process, the switching current peaks are merged [the black curve in Fig. 5(a)]. With a further increased number of field cycles, the switchable polarization decreases, which corresponds to the generally observed fatigue in many ferroelectrics.

Schenk et al. discussed the possible mechanisms of the splitting of the switching current peaks in the pristine state.<sup>[69]</sup> First-order reversal curve (FORC) measurement was conducted, and a locally distributed inhomogeneous internal field resulted in a divided switching current peak.<sup>[70]</sup> The inhomogeneous internal electric field distribution can originate from the spatially unevenly distributed charged defects, such as oxygen vacancies.<sup>[68]</sup> A high oxygen vacancy concentration is expected to be present near the electrodes due to the reduction of the doped HfO<sub>2</sub> layer by the metal nitride electrodes, whose distribution may be mostly asymmetric. The resulting asymmetric distribution of the oxygen vacancies can be an origin of the internal field in the pristine material.<sup>[68]</sup> During the

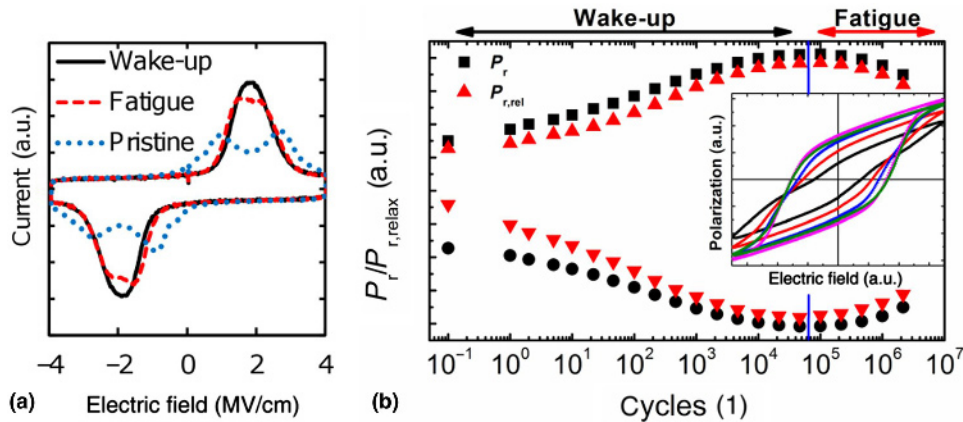


**Figure 5.** (a) Current-voltage and the corresponding polarization-voltage characteristics (b inset) of ferroelectric Sr:HfO<sub>2</sub> for the pristine, woken-up, and fatigued states. (b) Extracted evolution of the positive and negative remanent polarization with field cycling. The difference between the positive and negative remanent polarization,  $P_r/P_{r,relax}$ , is related to the memory window. Adapted from Ref. 68 with permission (John Wiley and Sons, 2016).

electric field cycling process, the oxygen vacancies may diffuse into the bulk regions of the ferroelectric-HfO<sub>2</sub>-based films, in which case the wake-up process will occur, accompanied by the merging of the switching current peaks [the black solid curve in Fig. 5(a)].<sup>[68]</sup> In subsequent studies, a redistribution of the charges related to the oxygen vacancies was reported.<sup>[64]</sup>

Another mechanism of the wake-up effect can be the field-cycling-induced phase transition. It was Lomenzo et al. who first suggested that the phase transition from the tetragonal (t-) to the ferroelectric orthorhombic phase (o-phase) is the origin of the wake-up effect.<sup>[71]</sup> They observed a decrease in the  $\epsilon_r$  as well as an increase in  $P_r$  with an increasing number of electric field cycles. The  $\epsilon_r$  decrease and  $P_r$  increase could be related to a phase transition from a non-ferroelectric higher- $\epsilon_r$  phase to a ferroelectric lower- $\epsilon_r$  phase. In fluorite-structure ferroelectrics, the phase transition from the t- to the o-phase corresponds to this case.<sup>[71]</sup> A similar trend was confirmed in other

studies.<sup>[72,73]</sup> Kim et al. examined the changes in the interfacial capacitance ( $C_i$ ), which originates from the non-ferroelectric interfacial layer, and found that the  $C_i$  value increased with an increasing number of field cycles, suggesting a decrease in the thickness of the interfacial layer, which is most probably in the t-phase.<sup>[72]</sup> A phase transition from the monoclinic (m-) to the o-phase was observed by Grimley and Schenk et al. using scanning TEM (STEM) and impedance spectroscopy.<sup>[7,74]</sup> Figure 6 shows (a) a schematic and cross-sectional TEM images of the (b) pristine, (c) woken-up, and (d) fatigued states of the ferroelectric-Gd:HfO<sub>2</sub> film near the TiN top electrode. In the pristine state, the interfacial region is highly defective, and the crystalline structure was identified to be the t-phase. On the other hand, the dominant crystalline phase in the bulk region was the m-phase. Ten different regions were analyzed using the STEM to obtain a statistically reliable result, and the overall capacitor performance was analyzed using

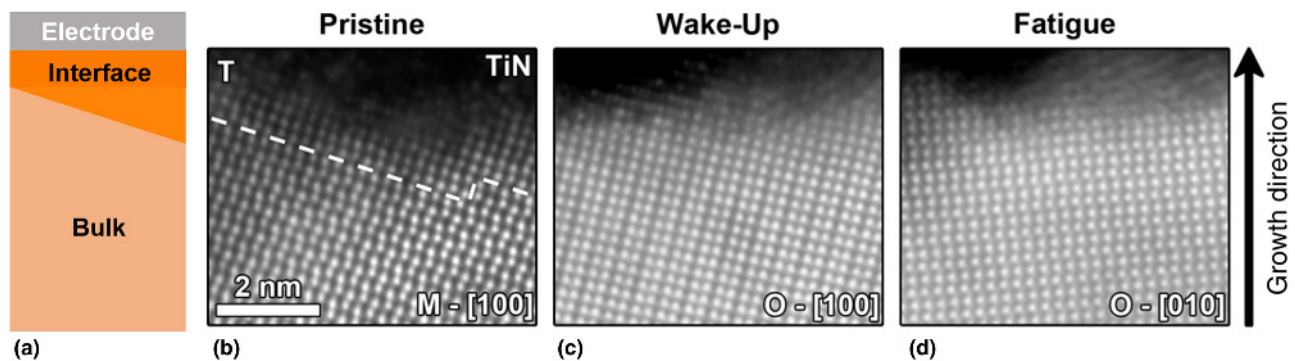

**Figure 6.** Single-grain segments of the capacitor stack near the electrode interface. (a) Sketch of the interfacial region next to the electrode. STEM images of doped HfO<sub>2</sub> in (b) pristine, (c) woken-up, and (d) fatigued conditions showing relaxation of the bulk monoclinic and tetragonal symmetries at the electrode interfaces towards the ferroelectric phase. This trend is most pronounced in the pristine state and least pronounced in the fatigued state. The intensity levels were adjusted to enhance the contrast near the electrode. Adapted from Ref. 68 with permission (John Wiley and Sons, 2016).


impedance spectroscopy.<sup>[74]</sup> After electric field cycling, the thickness of the highly defective interface significantly decreased, and the dominant crystalline phase of the bulk region changed to the ferroelectric o-phase, as shown in Fig. 6(c). As discussed earlier, in the woken-up state,  $P_r$  enhancement was observed, which was well matched with the results of other studies on the wake-up effect. With the onset of fatigue, an increase in the bulk defect density could be confirmed by the increase in the leakage current and the changes in the impedance spectra.<sup>[74]</sup>

It should be noted that a migration of oxygen vacancies is not an origin of ferroelectric hysteresis as Shimizu et al. experimentally examined.<sup>[75]</sup> They compared ferroelectric properties of  $\text{Hf}_{0.5}\text{Zr}_{0.5}\text{O}_2$  thin films annealed under the  $\text{O}_2$  or  $\text{N}_2$  atmosphere at various temperatures and switching pulses, and proved that  $\text{Hf}_{0.5}\text{Zr}_{0.5}\text{O}_2$  thin films show an intrinsic ferroelectric properties which should originate from the sub-unit-cell motion of ions.<sup>[75]</sup> However, according to computational simulation, free energies of various crystalline phases of  $\text{HfO}_2$  are affected by oxygen vacancy concentration.<sup>[76]</sup> According to Hoffmann et al.'s work,<sup>[76]</sup> the free energy of high symmetry phases such as the t- and c-phase decreases with increasing oxygen vacancy concentration compared with that of the o-phase in a high oxygen vacancy concentration range of a few %. Such high oxygen vacancy concentration is unreasonable for the entire doped  $\text{HfO}_2$  thin films but might be possible

in the interfacial regions which are generally more defective compared to the bulk region of thin films. Therefore, a local phase evolution during repetitive electric field cycling is a plausible mechanism for the wake-up effect.

Pešić et al. comprehensively examined the wake-up effect through both an experiment and a computational simulation.<sup>[68]</sup> Figure 7(a) shows the simulation results of the oxygen vacancy distribution in the ferroelectric- $\text{HfO}_2$  capacitor at three different times, and Fig. 7(b) depicts the corresponding electric field distribution in the capacitor. Figure 7(c) describes the simulated switching current-voltage and the polarization voltage curve in the pristine and woken-up states. At  $t = 0$  s in Fig. 7(a), the oxygen vacancy concentration is high in the interface regions. As a result, the spatially inhomogeneous electric field can be observed as shown in the left panel of Fig. 7(b). With the increasing number of field cycles, the oxygen vacancies diffuse into the bulk region of the film, and their distribution becomes more homogeneous, as shown in Fig. 7(a). At the same time, the electric field distribution also becomes more homogeneous with an increasing number of field cycles, as seen in Fig. 7(b). With this simple model, the I-V and P-V curves can be simulated as shown in Fig. 7(c).

Starschich et al. showed that even a single DC pulse with a sufficient length could wake up the ferroelectric doped  $\text{HfO}_2$  capacitors.<sup>[77]</sup> Thus, the total pulse length rather than the number of switching cycles may be critical for the wake-up effect,

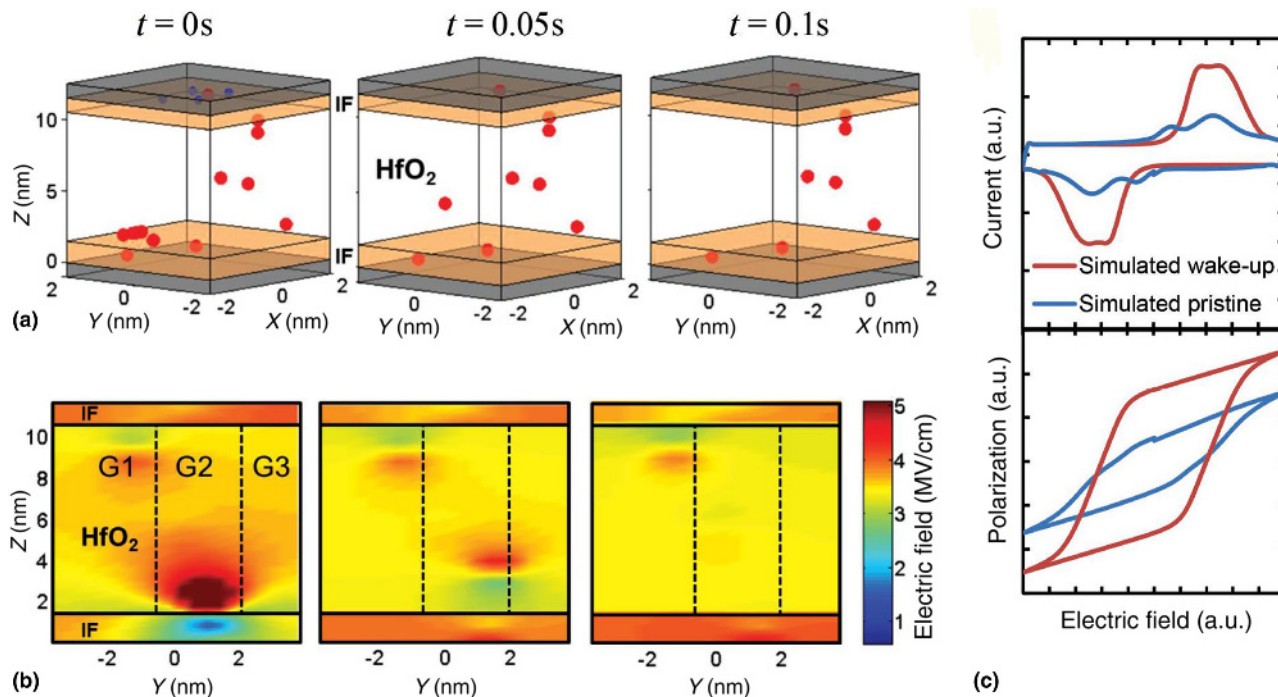

**Figure 7.** Simulated wake-up effect of the device: (a) vacancy diffusion and (b) the corresponding electric field evolution within the device with the field cycling of the ferroelectric capacitor at three different points in time at a 4 MV/cm externally applied field. IF represents a low- $\epsilon_r$  interfacial layer whereas G1–G3 represent three different grains within the stack. (c) The I-V and P-V characteristics obtained by removing the charges from the interface and changing the  $k$ -value of the grains undergoing phase transformation. Adapted from Ref. 68 with permission (John Wiley and Sons, 2016).



implying that a time-dependent phenomenon such as diffusion may be the origin of such effect. Starschich et al. also showed that both resistive and polarization switching could be observed in a single sample, although an initial forming process was required for resistive switching.<sup>[78]</sup> It is generally accepted that the resistive switching in HfO<sub>2</sub> is governed by the formation and rupture of an oxygen vacancy filament, and that the operating electric fields for resistive and ferroelectric switching have the same order of MV/cm. Recently, it was shown that the resistive switching curves of a Sr-doped HfO<sub>2</sub> film could show a deep reset after the conduct of significant field cycling in a ferroelectric mode.<sup>[79]</sup> This could indicate the depletion of oxygen, or in other words, an increase in oxygen vacancy concentration towards the interface.<sup>[80]</sup> Therefore, it can be deduced that the wake-up effect can be attributed to the diffusion of the oxygen vacancies under the electric field.

The wake-up phenomenon is strongly affected by the annealing temperature. Park et al. reported that the cycle numbers required for waking up HZO thin films decrease with increasing annealing temperature, with an increased  $P_r$  in the pristine state.<sup>[81]</sup> At the same time, the field cycle number to a hard breakdown decreased as well.<sup>[81]</sup> Lomenzo et al. also reported that the P-E curves of Si:HfO<sub>2</sub> thin films showed stronger pinching when the annealing was performed at a lower temperature of 700 °C, and that the breakdown strength decreased while the leakage current increased for a higher annealing temperature of 900 °C.<sup>[82]</sup> Both the decrease in breakdown strength and the increase in leakage current are likely related to the reduced number of field cycles until the hard breakdown occurrence. Such a trend was also confirmed by Richter et al. in Si:HfO<sub>2</sub> thin films, and by Schroeder et al. in La:HfO<sub>2</sub> films.<sup>[83,84]</sup> Thus, increasing the annealing temperature can degrade the endurance of ferroelectric-HfO<sub>2</sub>-based films, although it is effective in reducing the wake-up effect.

The doping concentration is another important factor influencing the degree of wake-up effect. Park et al. reported that the wake-up effect could be reduced by optimizing the doping concentration of HZO thin films.<sup>[72]</sup> In their study, a Zr doping concentration slightly lower than that for the largest  $P_r$  most effectively optimized the wake-up effect.<sup>[72]</sup> In general, the wake-up effect is less obvious in HfO<sub>2</sub> films with a higher doping concentration, which generally shows dielectric or antiferroelectric properties.<sup>[72,83,84]</sup> Another important factor is the electrode material. Hoffmann et al. examined the ferroelectric properties of Gd:HfO<sub>2</sub> thin films with TiN or TaN electrodes, and reported that the TaN electrode led to a longer wake-up phase.<sup>[76]</sup>

Based on the aforementioned research results, it is very likely that the wake-up effect can be attributed to the diffusion and redistribution of the oxygen vacancies by repetitive electric field cycling. Therefore, the wake-up effect is a thermally activated process whose degree is proportional to the process time and temperature. Starschich et al. showed that the pulse length rather than the number of switching cycles is a key factor causing the wake-up effect,<sup>[77,78]</sup> which is consistent with the

observation that the wake-up effect is weakened when the annealing temperature is increased. Higher annealing temperature should help distribute the oxygen vacancies more uniformly in the entire film. The effect of the electrode material is not easy to understand, as Park et al. discussed elsewhere, and this topic needs further study.<sup>[85]</sup>


### Limited endurance

Besides the wake-up effect, an insufficient lifetime during field cycling is another critical problem of ferroelectric-HfO<sub>2</sub>-based thin films. The best field cycling endurance reported to date ( $4 \times 10^{10}$  <sup>[86]</sup>) in the ferroelectric-HfO<sub>2</sub>-based thin film is much smaller than that in the conventional perovskite-based ferroelectrics ( $10^{15}$  for the MSP430 FR573x microcontroller, Texas Instruments). In general, the failure mechanism of ferroelectric-HfO<sub>2</sub>-based thin films is a hard breakdown after a significant increase in the leakage current.<sup>[1,72,82-84,87]</sup> This effect is then followed by polarization fatigue, a mechanism that has also been observed in perovskite-structure ferroelectrics.

The smaller number of field cycles to break down for ferroelectric-HfO<sub>2</sub>-based films is a natural consequence of such films' high  $E_c$  relative to their breakdown field strength. The  $E_c$  value of ferroelectric HfO<sub>2</sub> is generally in the range of  $\sim 0.8$ – $2.0$  MV/cm, which is higher by  $\sim$ one order of magnitude than that of perovskite thin films.<sup>[2,6,88]</sup> As a result, to achieve a saturated P-E curve, a field equal to or higher than  $\sim 3$  MV/cm needs to be applied. The apparent (extrinsic) breakdown strength of HfO<sub>2</sub> is generally  $\sim 5$  MV/cm.<sup>[89]</sup> Therefore, the applied electric field for polarization switching is  $\sim 60$ – $80\%$  of the breakdown strength, suggesting an inherently small margin in securing the allowed number of field cycles before the breakdown. The intrinsic breakdown strength, however, was suggested to be  $\sim 20$  MV/cm without any involvement of defective factors like oxygen vacancies.<sup>[90]</sup> Such high intrinsic field to breakdown ( $E_{bd}$ ) leaves room for improving the limited endurance through defect engineering. In a normal experiment, nevertheless, the breakdown of the oxide materials is always governed by extrinsic factors.

The higher  $E_c$  value of ferroelectric-HfO<sub>2</sub>-based films can be attributed to the higher kinetic energy barrier between the two spontaneous polarization states. Figure 8(a) and 8(b) show the free energy curves of tetragonal BaTiO<sub>3</sub> and orthorhombic HfO<sub>2</sub> from computational simulations. BaTiO<sub>3</sub> has a 6.5 meV/f.u. kinetic energy barrier while o-phase HfO<sub>2</sub> has  $\sim 100$  meV/f.u..<sup>[88,91]</sup> A similar kinetic energy barrier was reported for o-phase HfO<sub>2</sub> by other researchers.<sup>[92,93]</sup> Although the switching kinetics is generally governed by the reverse-domain nucleation and growth, the electric field required for polarization switching is expected to be affected by the kinetic energy barrier between the two spontaneous polarization states.

The hard breakdown event after an increase in leakage current is generally attributed to the formation of a permanent conducting path possibly due to the accumulation of defects such as oxygen vacancies.<sup>[68]</sup> It is generally known that oxygen vacancies tend to accumulate near defects like grain

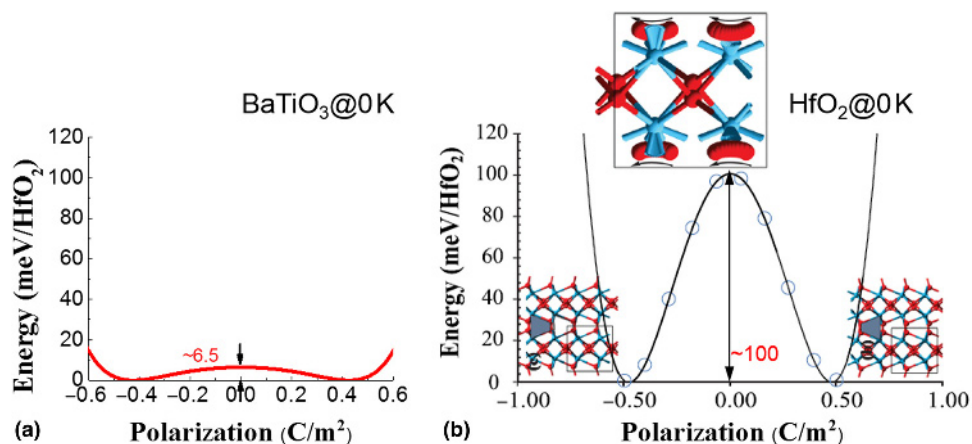


**Figure 8.** Free energy polarization curve of (a) tetragonal BaTiO<sub>3</sub> and (b) orthorhombic HfO<sub>2</sub> at 0 K. Figure 8(b) was adapted from Ref. 88 with permission (AIP Publishing LLC, 2014).

boundaries.<sup>[94]</sup> In the case of the ferroelectric o-phase HfO<sub>2</sub> thin films, a polycrystalline nature with a nanoscale grain size is generally observed.<sup>[14,78,84,95–101]</sup> Such small grain size results in a high grain boundary area-to-volume ratio, indicating that the oxygen vacancies can reach the grain boundaries and accumulate there, with a short diffusion distance. Therefore, increasing the grain size can be a promising method of improving the endurance of ferroelectric HfO<sub>2</sub>-based thin films. The effect of the grain size on endurance, however, has not yet been carefully studied. On the other hand, in many previous studies, it was shown that increasing the grain size could result in an increased m-phase fraction due to the weakened interface/grain boundary energy effect. Therefore, there may be a trade-off between optimizing the non-ferroelectric m-phase fraction and endurance.

The doping concentration also affects the endurance of doped HfO<sub>2</sub> or HZO thin films. Figure 9(a) shows the changes

in the 2P<sub>r</sub> and endurance of HZO thin films for various Zr/(Hf + Zr) ratios. The largest 2P<sub>r</sub> of 40 μC/cm<sup>2</sup> could be observed for the 0.5 Zr/(Hf + Zr) ratio, but this composition showed the smallest number of switching cycles to a hard breakdown. The effect of the doping concentration on the breakdown of the HfO<sub>2</sub> film has not yet been clearly elucidated to date. In many previous studies, however, it was reported that the HfO<sub>2</sub> thin film with a higher doping concentration, resulting in dielectric or antiferroelectric properties, could endure longer than the film with a composition that renders the largest P<sub>r</sub>.<sup>[72,82,83]</sup>

Based on the observation that the endurance of antiferroelectric films is superior to the endurance of ferroelectrics, Pešić et al. suggested a clever method of utilizing antiferroelectric films for nonvolatile memory applications.<sup>[8,70]</sup> Generally, antiferroelectrics cannot be utilized for nonvolatile memory applications because its P<sub>r</sub> is zero when no field is applied,

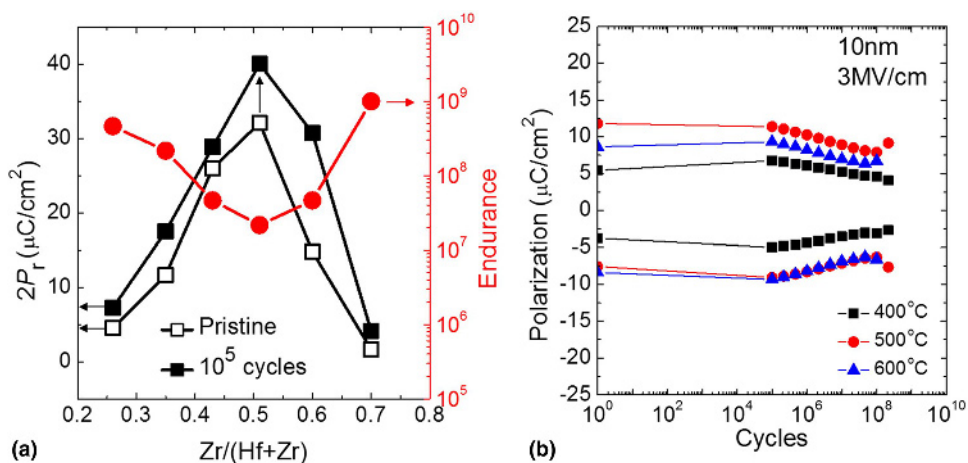

**Figure 9.** (a) Changes in 2P<sub>r</sub> (left axis) and endurance (right axis) with a varying Zr/(Hf + Zr) ratio of (Hf,Zr)O<sub>2</sub> thin films. (b) Endurance test results for 10-nm-thick Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> films annealed at 400–600 °C. Figure 9(b) was adapted from Ref. 87 with permission (John Wiley and Sons, 2014).


but shifting the P-E curve of antiferroelectric materials by intentionally inducing a high internal electric field will enable nonvolatile memory storage. The internal bias field can be generated either by using asymmetric electrodes or by adding additional fixed charges in the dielectric layer stack through the combination of different dielectrics.<sup>[102]</sup> With this method, antiferroelectric ZrO<sub>2</sub> could have a reasonable P<sub>r</sub> value even at zero electric field.<sup>[103]</sup> Although its P<sub>r</sub> value is smaller than that of the ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> film, the E<sub>c</sub> value, which is another critical factor for endurance, can be significantly lowered as well.<sup>[104]</sup>

Based on the preceding observations, it can be stated that decreasing the oxygen vacancy concentration may be another pathway for improving the endurance, which can deter the generation of permanent conducting paths between the top and bottom electrodes. Decreasing the annealing temperature is a potential way to achieve this goal, which can be understood from the observation that a higher annealing temperature resulted in a lower number of switching cycles to break down.<sup>[81–84,87]</sup> Figure 9(b) shows the endurance test results of Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films annealed at 400–600 °C for 30 s in an N<sub>2</sub> atmosphere.<sup>[87]</sup> Although the P<sub>r</sub> decreased at the lower annealing temperature, the 400 °C-annealed sample lasted the longest among the three samples.

Fabricating ferroelectric-HfO<sub>2</sub>-based films with the preferred orientation or with a high ferroelectric phase fraction should also be beneficial for endurance improvement. The polar axis of the ferroelectric o-phase is the c-axis. Thus, an uncompensated polarization charge at the grain boundaries between two different orientations can induce the accumulation of trapped charges or charged defects such as oxygen vacancies. Moreover, a highly oriented film is expected to have a narrower distribution of E<sub>c</sub> values, which can decrease the electric field required for a saturated P-E curve. This can also be applied to the phase boundary between the ferroelectric and non-ferroelectric phases. The existence of phase and domain boundaries in nanoscale grains in ALD-grown doped HfO<sub>2</sub> thin films was confirmed by Grimley et al. based on the STEM results they had obtained.<sup>[73,104]</sup>

Figure 10 summarizes the P<sub>r</sub> and endurance of ferroelectric-HfO<sub>2</sub>-based films from the existing literature. In general, the number of endurable cycles decreases with increasing 2P<sub>r</sub> value. Therefore, this phenomenon can be called “P<sub>r</sub>-endurance dilemma”. The largest endurance value to date of 4.0 × 10<sup>10</sup> was reported for La:Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> (La:HZO) thin films with a maximum P<sub>r</sub> value of 15 μC/cm<sup>2</sup>.<sup>[86]</sup> Figure 10(b) shows the endurance test result for the La:HZO thin film.<sup>[86]</sup> La doping in the HZO film decreased the leakage current, which contributed to the enhanced endurance. The data points in Fig. 10(a), however, are quite scattered, suggesting that further research is necessary to achieve a more thorough understanding of this matter.

Finally, it is important to note that almost all the studies described in the literature were performed using large-scale test capacitors with high capacitance. Moreover, the endurance

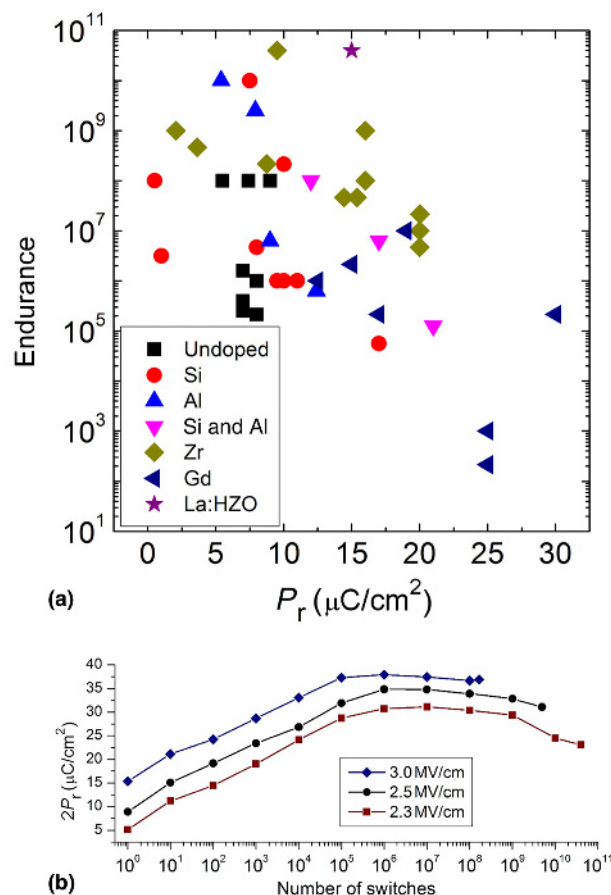

**Figure 10.** (a) P<sub>r</sub>-endurance plot from the existing literature. The data were taken from the literature [undoped: 96,105; Si: 6,106–108; Al: 37; Si and Al: 107; Zr: 73,86,108; Gd: 84; La:HZO: 86]. (b) The best endurance result from the La:Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films with three different fatigue pulse height values. Figure 10(b) was adapted from Ref. 86 with permission (ACS Publications, 2018).

test is normally performed using the standard needles, which need to come in contact with the device. As a result, the electrical stress on the device is significantly higher than the electrical stress an integrated capacitor or FeFET structure would experience in a memory array. Therefore, the absolute number of endurable field cycles, in particular, will increase in a realistic 1T-1C memory cell. To obtain a better impression of the achievable endurance specification, measurement data from integrated 1T-1C arrays will be highly desirable, but these are not yet available in the literature. For FeFET, in contrast, the memory window is much more limited by charge trapping and decreases significantly to below the cycle number, leading to fatigue or breakdown.<sup>[111]</sup>

## Conclusion

In this perspective paper, fluorite-structure ferroelectrics were reviewed for memory applications. Compared with the conventional perovskite-structure ferroelectrics, fluorite-structure

ferroelectrics have numerous advantages. They are Si- and CMOS-compatible and can have strong ferroelectricity for a sub-10 nm film thickness. As a result, films can be scaled down for simple integration in the FeFET or FeRAM capacitor applications to the technology nodes in the 20 nm range. For a 1T-1C FeRAM application, fluorite-structure ferroelectrics enable 3D capacitors with  $P_r$  values sufficient for reliable operation with a state-of-the-art sense amplifier. The sub-10 nm thickness is another significant merit of the 3D capacitor structure. For FeFET application, fluorite-structure ferroelectrics can have sufficient retention for nonvolatile memory application (10 years) due to their lower depolarization field attributed to their low  $\epsilon_r$  of  $\sim 30$ – $35$ , lower than the  $\epsilon_r$  of perovskite-structure ferroelectrics.

There are remaining issues, however, regarding fluorite-structure ferroelectrics. The first issue is the wake-up effect, which is believed to result from the non-uniform high oxygen vacancy concentration near the interface adjacent to the electrodes and/or from the phase transition during electric field cycling. Based on the experimental observations in previous studies, the wake-up effect has been attributed to the diffusion and redistribution of the oxygen vacancies or charges in thin films. The temperature and the time-dependent charging of these films can cause imprint effects. The other critical issue regarding fluorite-structure ferroelectrics is their insufficient endurance, which is attributed to a relatively high  $E_c$ -to-breakdown field strength ratio. The general failure mechanism is a hard breakdown after a significant leakage current increase, which is known to result from the formation of a permanent conducting path possibly due to the accumulation of oxygen vacancies at the grain boundaries. Finally, imprint, another critical issue in ferroelectric memory devices, is by far less intensively studied in fluorite-structure ferroelectrics than in the conventional ferroelectrics. In perovskite-structure ferroelectrics, however, the imprint improvement is based on measures similar to those for endurance improvement because both are caused by the oxygen-vacancy-related defects, which are also critical for the wake-up effect and endurance of fluorite-structure ferroelectrics. To overcome the aforementioned issues, various methodologies were suggested in this study based on the reported experimental observations.

## Acknowledgment

CSH acknowledges the support given by the Global Research Laboratory Program (2012 1A1A2040157) of the National Research Foundation of the South Korean government. TM and US acknowledge the EFRE fund of the European Commission and the Free State of Saxony (Germany). MHP was supported by Humboldt Postdoctoral Fellowship from Alexander von Humboldt Foundation.

## References

1. T.S. Böske, J. Müller, D. Bräuhäus, U. Schröder, and U. Böttger: Ferroelectricity in hafnium oxide thin films. *Appl. Phys. Lett.* **99**, 102903 (2011).

2. M.H. Park, Y.H. Lee, H.J. Kim, Y.J. Kim, T. Moon, K.D. Kim, J. Müller, A. Kersch, U. Schroeder, T. Mikolajick, and C.S. Hwang: Ferroelectricity and antiferroelectricity of doped thin  $\text{HfO}_2$ -based films. *Adv. Mater.* **27**, 1811 (2015).
3. T. Mikolajick, S. Slesazeck, M.H. Park, and U. Schroeder: Ferroelectric hafnium oxide for ferroelectric random-access memories and ferroelectric field-effect transistors. *MRS Bull.* **43**, 340 (2018).
4. J. Müller, P. Polakowski, S. Mueller, and T. Mikolajick: Ferroelectric hafnium oxide based materials and devices: assessment of current status and future prospects. *ECS. J. Solid State Sci. Technol.* **4**, N30 (2015).
5. C.S. Hwang: Prospective of semiconductor memory devices: from memory system to materials. *Adv. Electron. Mater.* **1**, 1400056 (2015).
6. U. Schroeder, E. Yurchuk, J. Müller, D. Martin, T. Schenk, P. Polakowski, C. Adelman, M.I. Popovici, S.V. Kalinin, and T. Mikolajick: Impact of different dopants on the switching properties of ferroelectric hafnium oxide. *Jpn. J. Appl. Phys.* **53**, 08LE02 (2014).
7. J. Müller, E. Yurchuk, T. Schlösser, J. Paul, R. Hoffmann, S. Mueller, D. Martin, S. Slesazeck, P. Polakowski, J. Sundqvist, M. Czernohorsky, K. Seidel, P. Kücher, R. Boschke, M. Trentzsch, K. Gebauer, U. Schröder, and T. Mikolajick: Ferroelectricity in  $\text{HfO}_2$  enables nonvolatile data storage in 28 nm HKMG. *VLSI Technology (VLSIT), 2012 Symposium on*, 2012; pp. 25–26.
8. M. Pešić, S. Knebel, M. Hoffmann, C. Richter, T. Mikolajick, and U. Schroeder: How to make DRAM non-volatile? Anti-ferroelectrics: A new paradigm for universal memories. *Electron Devices Meeting (IEDM), 2016 IEEE International*, 2016; pp. 11.6.1–11.6.4.
9. J. Müller, T.S. Böske, S. Müller, E. Yurchuk, P. Polakowski, J. Paul, D. Martin, T. Schenk, K. Khüller, A. Kersch, W. Weinreich, S. Riedel, K. Seidel, A. Kumar, T.M. Arruda, S.V. Kalinin, T. Schlösser, R. Böschke, R. van Bentum, U. Schröder, and T. Mikolajick: Ferroelectric hafnium oxide: A CMOS-compatible and highly scalable approach to future ferroelectric memories. *Electron Devices Meeting (IEDM), 2013 IEEE International*, 2013; pp. 10.8.1–10.8.4.
10. H. Mulaosmanovic, S. Slesazeck, J. Ocker, M. Pešić, S. Müller, S. Flachowsky, J. Müller, P. Polakowski, J. Paul, S. Jansen, S. Kolodinski, C. Richter, S. Piontek, T. Schenk, A. Kersch, C. Kuenneth, R. van Bentum, U. Schroeder, and T. Mikolajick: Evidence of single domain switching in hafnium oxide based FeFETs: Enabler for multi-level FeFET memory cells. *Electron Devices Meeting (IEDM), 2015 IEEE International*, 2015; pp. 26.8.1–26.8.3.
11. M.H. Park, H.J. Kim, Y.J. Kim, T. Moon, K.D. Kim, and C.S. Hwang: Toward a multifunctional monolithic device based on pyroelectricity and the electrocaloric effect of thin antiferroelectric  $\text{Hf}_{1-x}\text{Zr}_x\text{O}_2$  films. *Nano Energy* **12**, 131 (2015).
12. M. Hoffmann, U. Schroeder, C. Künneth, A. Kersch, S. Starschich, U. Böttger, and T. Mikolajick: Ferroelectric phase transitions in nanoscale  $\text{HfO}_2$  films enable giant pyroelectric energy conversion and highly efficient supercapacitors. *Nano Energy* **18**, 154 (2015).
13. M.H. Park, H.J. Kim, Y.J. Kim, T. Moon, K.D. Kim, and C.S. Hwang: Thin  $\text{Hf}_{1-x}\text{Zr}_x\text{O}_2$  films: a new lead-free system for electrostatic supercapacitors with large energy storage density and robust thermal stability. *Adv. Energy Mater.* **4**, 1400610 (2014).
14. K.D. Kim, Y.H. Lee, T. Gwon, Y.J. Kim, H.J. Kim, T. Moon, S.D. Hyun, H. W. Park, M.H. Park, and C.S. Hwang: Scale-up and optimization of  $\text{HfO}_2\text{-ZrO}_2$  solid solution thin films for the electrostatic supercapacitors. *Nano Energy* **39**, 390 (2017).
15. M.H. Park, H.J. Kim, Y.J. Kim, T. Moon, K.D. Kim, Y.H. Lee, S.D. Hyun, and C.S. Hwang: Giant negative electrocaloric effects of  $\text{Hf}_{0.5}\text{Zr}_{0.5}\text{O}_2$  thin films. *Adv. Mater.* **28**, 7956 (2016).
16. M.H. Park, T. Schenk, M. Hoffmann, S. Knebel, J. Gärtner, T. Mikolajick, and U. Schroeder: Effect of acceptor doping on phase transitions of  $\text{HfO}_2$  thin films for energy-related applications. *Nano Energy* **36**, 381 (2017).
17. S.W. Smith, A.R. Kitahara, M.A. Rodriguez, M.D. Henry, M.T. Brumbach, and J.F. Ihlefeld: Pyroelectric response in crystalline hafnium zirconium oxide ( $\text{Hf}_{1-x}\text{Zr}_x\text{O}_2$ ) thin films. *Appl. Phys. Lett.* **110**, 072901 (2017).
18. S. Jachalke, T. Schenk, M.H. Park, U. Schroeder, T. Mikolajick, H. Stöcker, E. Mehner, and D.C. Meyer: Pyroelectricity of silicon-doped hafnium oxide thin films. *Appl. Phys. Lett.* **112**, 142901 (2018).

19. H. Mulaosmanovic, J. Ocker, S. Müller, M. Noack, J. Müller, P. Polakowski, T. Mikolajick, and S. Slesazek: Novel ferroelectric FET based synapse for neuromorphic systems. *VLSI Technology, 2017 Symposium on*. doi: 10.23919/VLSIT.2017.7998165.
20. H. Mulaosmanovic, T. Mikolajick, and S. Slesazek: Random number generation based on ferroelectric switching. *IEEE Electron Device Lett.* **39**, 135–138 (2018).
21. J.F. Scott: *Ferroelectric Memories* (Springer-Verlag, Berlin, Heidelberg, 2000). doi: 10.1007/978-3-662-04307-3.
22. J.F. Scott and C.A.P. de Araujo: Ferroelectric memories. *Science* **246**, 1400 (1989).
23. J.-M. Koo, B.-S. Seo, S. Kim, S. Shin, J.-H. Lee, H. Baik, J.-H. Lee, J. H. Lee, B.-J. Bae, J.-E. Lim, D.-C. Yoo, S.-O. Park, H.-S. Kim, H. Han, S. Baik, J.-Y. Choi, Y.J. Park, and Y. Park: Fabrication of 3D trench PZT capacitors for 256Mbit FRAM device application. *IEDM Tech. Digest.* 340–343 (2005). DOI: 10.1109/IEDM.2005.1609345.
24. International Technology Roadmap for Semiconductors 2011 Edition. [https://www.dropbox.com/sh/r51grus06k6ehrc/AACQYSRnTdLGUCDZ\\_FhB6\\_iXua/2011Chapters?dl=0&preview=2011ERD.pdf&subfolder\\_nav\\_tracking=1](https://www.dropbox.com/sh/r51grus06k6ehrc/AACQYSRnTdLGUCDZ_FhB6_iXua/2011Chapters?dl=0&preview=2011ERD.pdf&subfolder_nav_tracking=1)
25. M. Okuyama: Features, Principles and development of ferroelectric-gate field-effect transistor. Ch. 1. In *Ferroelectric-gate Field Effect Transistor Memories*, edited by B.-E. Park, H. Ishiwara, M. Okuyama, S. Sakai, and S.-M. Yoon, Topics in Applied Physics 131, (Springer Science+Business Media Dordrecht, Dordrecht, Netherlands, 2016).
26. C.S. Hwang (ed.): *Atomic Layer Deposition for Semiconductors*, (Springer, New York, 2013).
27. K. Maruyama, M. Kondo, S.K. Singh, and H. Ishiwara: New ferroelectric material for embedded FRAM LSIs. *Fujitsu Sci. Tech. J* **43**, 502–507 (2007).
28. M.E. Lines and A.M. Glass: *Principles and Applications of Ferroelectrics and Related Materials* (Oxford University Press, New York, USA, 2001). doi: 10.1093/acprof:oso/9780198507789.001.0001.
29. Y. Shuai, S. Zhou, S. Streit, H. Reuther, D. Bürger, S. Slesazek, T. Mikolajick, M. Helm, and H. Schmidt: Reduced leakage current in BiFeO<sub>3</sub> thin films with rectifying contacts. *Appl. Phys. Lett.* **98**, 232901 (2011).
30. T. Watanabe, S. Hoffmann-Eifert, F. Peter, S. Mi, C. Jia, C.S. Hwang, and R. Waser: Liquid injection ALD of Pb(Zr,Ti)O<sub>3</sub> thin films by a combination of self-regulating component oxide processes. *J. Electrochem. Soc.* **154**, G262 (2007).
31. M.D. McDaniel, T.Q. Ngo, S. Hu, A. Posadas, A.A. Demkov, and J. G. Ekerdt: Atomic layer deposition of perovskite oxides and their epitaxial integration with Si, Ge, and other semiconductors. *Appl. Phys. Rev.* **2**, 041301 (2015).
32. J.F. Ihlefeld, D.T. Harris, R. Keech, J.L. Jones, J. Maria, and S. Trolier-McKinstry: Scaling effects in perovskite ferroelectrics: fundamental limits and process-structure-property relations. *J. Am. Ceram. Soc.* **99**, 2537–2557 (2016).
33. T. Tybell, C.H. Ahn, and J.-M. Triscone: Ferroelectricity in thin perovskite films. *Appl. Phys. Lett.* **75**, 856 (1999).
34. J. Junquera and P. Ghosez: Critical thickness for ferroelectricity in perovskite ultrathin films. *Nature* **422**, 506 (2003).
35. D.D. Fong, G. Brian Stephenson, S.K. Streiffer, J.A. Eastman, O. Auciello, P.H. Fuoss, and C. Thompson: Ferroelectricity in ultrathin perovskite films. *Science* **304**, 1650 (2004).
36. N. Sai, A.M. Kolpak, and A.M. Rappe: Ferroelectricity in ultrathin perovskite films. *Rhys. Rev. B* **72**, 020101 (2005).
37. P. Polakowski, S. Riedel, W. Weinreich, M. Rudolf, J. Sundqvist, K. Seidel, and J. Müller: Memory Workshop (IMW), 2014 *IEEE 6th International*, doi: 10.1109/IMW.2014.6849367.
38. M. Pešić, U. Schroeder, and T. Mikolajick: HfO<sub>2</sub> based FeRAM and capacitor for 1T/1C memory cell. Ferroelectric one transistor-one capacitor memory cell: Ferroelectricity in Hafnium and Zirconium oxide: materials and devices (Elsevier), in preparation.
39. International Technology Roadmap for Semiconductors 2013 Edition. [https://www.dropbox.com/sh/6xq737bg6pww9gq/AACQWcdHLffUeVloszVY6Bkla?dl=0&preview=2013ERD\\_Summary.pdf](https://www.dropbox.com/sh/6xq737bg6pww9gq/AACQWcdHLffUeVloszVY6Bkla?dl=0&preview=2013ERD_Summary.pdf)
40. S. Fujii, Y. Kamimuta, T. Ino, Y. Nahasaki, R. Takaishi, and M. Saitoh: First demonstration and performance improvement of ferroelectric HfO<sub>2</sub>-based resistive switch with low operation current and intrinsic diode property, *VLSI Technology 2016 IEEE Symposium*, 2016.
41. B. Max, M. Hoffmann, S. Slesazek, and T. Mikolajick: Ferroelectric Tunnel Junctions based on Ferroelectric-Dielectric HfZrO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> Capacitor Stack, *European Solid State Device Research Conference (ESSDERC)*, 2018.
42. M. Pesic, V. di Lecce, M. Hoffmann, H. Mulaosmanovic, B. Max, U. Schröder, S. Slesazek, L. Larcher, and T. Mikolajick: Physical and circuit modeling of HfO<sub>2</sub> based ferroelectric memories and devices. *SOI-3D-Subthreshold Microelectronics Technology Unified Conference (S3S) IEEE*, 2017.
43. T.P. Ma and J. -P. Han: Why is nonvolatile ferroelectric memory field-effect transistor still elusive?. *IEEE Electron Device Lett.* **23**, 386 (2002).
44. U. Schroeder, S. Slesazek, and T. Mikolajick: Nonvolatile field-effect transistors using ferroelectric doped HfO<sub>2</sub> films. Ch. 3. In *Ferroelectric-gate Field Effect Transistor Memories*, edited by B.-E. Park, H. Ishiwara, M. Okuyama, S. Sakai, and S.-M. Yoon, Topics in Applied Physics 131, (Springer Science+Business Media Dordrecht, Dordrecht, Netherlands, 2016).
45. K. Aizawa, B.-E. Park, Y. Kawashima, K. Takahashi, and H. Ishiwara: Impact of HfO<sub>2</sub> buffer layers on data retention characteristics of ferroelectric-gate field-effect transistors. *Appl. Phys. Lett.* **85**, 3199 (2004).
46. S. Sakai, R. Ilangoan, and M. Takahashi: Pt/SrBi<sub>2</sub>Ta<sub>2</sub>O<sub>9</sub>/Hf-Al-O/Si Field-effect-transistor with long retention using unsaturated ferroelectric polarization switching. *Jpn. J. Appl. Phys.* **43**, 7876 (2004).
47. M. Takahashi and S. Sakai: Self-aligned-gate Metal/Ferroelectric/Insulator/Semiconductor field-effect transistors with long memory retention. *Jpn. J. Appl. Phys.* **44**, L800 (2005).
48. L.V. Hai, M. Takahashi, W. Zhang, and S. Sakai: 100-nm-size ferroelectric-gate field-effect transistor with 10<sup>9</sup>-cycle endurance. *Jpn. J. Appl. Phys.* **54**, 088004 (2015).
49. S. Dünkel, M. Trentzsch, R. Richter, P. Moll, C. Fuchs, O. Gehring, M. Majer, S. Wittek, B. Müller, T. Melde, H. Mulaosmanovic, S. Slesazek, S. Müller, J. Ocker, M. Noack, D.-A. Löhr, P. Polakowski, J. Müller, T. Mikolajick, J. Höntschel, B. Rice, J. Pellerin, and S. Beyer: A FeFET based super-low-power ultra-fast embedded NVM technology for 22 nm FDSOI and beyond. Electron Devices Meeting (IEDM), 2017 *IEEE International*, 2017; pp. 19.7.1–19.7.4.
50. N. Gong, and T.P. Ma: Why is retention time for HfO<sub>2</sub>-based ferroelectric longer than those for PZT or SBT in 1-T memory cell?, *IEEE Electron Device Lett.* **37**, 1123 (2016).
51. K. Takahashi, K. Aizawa, B.-E. Park, and H. Ishiwara: Thirty-day-long data retention in ferroelectric-gate field-effect transistors with HfO<sub>2</sub> buffer layers. *Jpn. J. Appl. Phys.* **44**, 6218 (2005).
52. E. Yurchuk, J. Müller, J. Paul, T. Schlösser, D. Martin, R. Hoffmann, S. Müller, S. Slesazek, U. Schröder, R. Boschke, R. van Bentum, and T. Mikolajick: Impact of scaling on the performance of HfO<sub>2</sub>-based ferroelectric field effect transistors. *IEEE Trans. Electron Devices* **61**, 3699 (2014).
53. Y.A. Genenko, S. Zhukov, S.V. Yampolskii, J. Schüttrumpf, R. Dittmer, W. Jo, H. Kungl, M.J. Hoffmann, and H. von Seggern: Universal polarization switching behavior of disordered ferroelectrics. *Adv. Funct. Mater.* **22**, 2058 (2012).
54. H. Mulaosmanovic, J. Ocker, S. Müller, U. Schroeder, J. Müller, P. Polakowski, S. Flachowsky, R. van Bentum, T. Mikolajick, and S. Slesazek: Switching kinetics in nanoscale hafnium oxide based ferroelectric field-effect transistors. *ACS Appl. Mater. Interfaces* **9**, 3792 (2017).
55. N. Setter, D. Damjanovic, L. Eng, G. Fox, S. Gevorgian, S. Hong, A. Kingon, H. Kohlstedt, N.Y. Park, G.B. Stephenson, I. Stolitchnov, A. K. Taganste, D.V. Taylor, T. Yamada, and S. Streiffer: Ferroelectric thin films: review of materials, properties, and applications. *J. Appl. Phys.* **106**, 051606 (2006).
56. C.-U. Pinnow and T. Mikolajick: Material aspects in emerging nonvolatile memories. *J. Electrochem. Soc.* **151**, K13–K19 (2004).
57. M.H. Park, H.J. Kim, Y.J. Kim, W. Lee, H.K. Kim, and C.S. Hwang: Effect of forming gas annealing on the ferroelectric properties of Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub>

- thin films with and without Pt electrodes. *Appl. Phys. Lett.* **102**, 112914 (2013).
58. W. Hartner, P. Bosk, G. Schindler, H. Bachhofer, M. Mört, H. Wendt, T. Mikolajick, C. Dehm, H. Schroeder, and R. Waser: SrBi<sub>2</sub>Ta<sub>2</sub>O<sub>9</sub> ferroelectric thin film capacitors: degradation in a hydrogen ambient. *Appl. Phys. A* **77**, 571 (2003).
59. S. Aggarwal, S.R. Perusse, C.W. Tipton, R. Ramesh, H.D. Drew, T. Venkatesan, D.B. Romero, V.B. Podobedov, and A. Weber: Effect of hydrogen on Pb(Zr,Ti)O<sub>3</sub>-based ferroelectric capacitors. *Appl. Phys. Lett.* **73**, 1973 (1998).
60. J. Rodriguez, K. Remack, J. Gertas, L. Wang, C. Zhou, K. Boku, J. Rodriguez-Latorre, K.R. Udayakumar, S. Summerfelt, and T. Moise: Reliability of ferroelectric random access memory embedded within 130 nm CMOS. in Reliability Physics Symposium (IRPS), 2010 IEEE International 750-758 (2010). DOI: 10.1109/IRPS.2010.5488738.
61. K. Florent, S. Lavizzari, L. Di Piazza, M. Popovici, J. Duan, G. Groeseneken, and J. Van Houdt: Reliability study of ferroelectric Al: HfO<sub>2</sub> thin films for DRAM and NAND applications. *IEEE Trans. Electron Devices* **64**, 4091 (2017).
62. M. Pešić, U. Schroeder, S. Slesazeck, and T. Mikolajick: Comparative study of reliability of ferroelectric and anti-ferroelectric memories. in IEEE Transactions on Device and Materials Reliability **18**, 154-162 (2018).
63. V.C. Lo: Modeling the role of oxygen vacancy on ferroelectric properties in thin films. *J. Appl. Phys.* **92**, 6778-6786 (2002).
64. F.P.G. Fengler, M. Hoffmann, S. Slesazeck, T. Mikolajick, and U. Schroeder: On the relationship between field cycling and imprint in ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub>. *J. Appl. Phys.* **123**, 20 (2018).
65. D. Zhou, J. Xu, Q. Li, Y. Guan, F. Cao, X. Dong, J. Müller, T. Schenk, and U. Schröder: Wake-up effects in Si-doped hafnium oxide ferroelectric thin films. *Appl. Phys. Lett.* **103**, 192904 (2013).
66. F.P.G. Fengler, M. Pešić, S. Starschich, T. Schneller, C. Künne, U. Böttger, H. Mulaosmanovic, T. Schenk, M.H. Park, R. Nigon, P. Muralt, T. Mikolajick, and U. Schroeder: Domain pinning: comparison of hafnia and PZT based ferroelectrics. *Adv. Electron. Mater.* **3**, 1600505 (2017).
67. Y.A. Genenko, J. Glaum, M.J. Hoffmann, and K. Albe: Mechanisms of aging and fatigue in ferroelectrics. *Mater. Sci. Eng. B* **192**, 52 (2015).
68. M. Pešić, F.P.G. Fengler, L. Larcher, A. Padovani, T. Schenk, E. D. Grimley, X. Sang, J. M. LeBeau, S. Slesazeck, U. Schroeder, and T. Mikolajick: Physical mechanisms behind the field-cycling behavior of HfO<sub>2</sub>-based ferroelectric capacitors. *Adv. Funct. Mater.* **26**, 4601 (2016).
69. T. Schenk, E. Yurchuk, S. Mueller, U. Schroeder, S. Starschich, U. Böttger, and T. Mikolajick: About the deformation of ferroelectric hysteresis. *Appl. Phys. Rev.* **1**, 041103 (2014).
70. T. Schenk, M. Hoffmann, J. Ocker, M. Pešić, T. Mikolajick, and U. Schroeder: Complex internal bias fields in ferroelectric hafnium oxide. *ACS Appl. Mater. Interfaces* **7**, 20224 (2015).
71. P.D. Lomenzo, Q. Takmeel, C. Zhou, C.M. Fancher, E. Lambers, N. G. Rudawski, J.L. Jones, S. Moghaddam, and T. Nishida: TaN interface properties and electric field cycling effects on ferroelectric Si-doped HfO<sub>2</sub> thin films. *J. Appl. Phys.* **117**, 134105 (2015).
72. H.J. Kim, M.H. Park, Y.J. Kim, Y.H. Lee, T. Moon, K.D. Kim, S.D. Hyun, and C.S. Hwang: A study on the wake-up effect of ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> films by pulse-switching measurement. *Nanoscale* **8**, 1383 (2016).
73. M.H. Park, H.J. Kim, Y.J. Kim, Y.H. Lee, T. Moon, K.D. Kim, S.D. Hyun, F. Fengler, U. Schroeder, and C.S. Hwang: Effect of Zr content on the wake-up effect in Hf<sub>1-x</sub>Zr<sub>x</sub>O<sub>2</sub> films. *ACS Appl. Mater. Interfaces* **8**, 15466 (2016).
74. E.D. Grimley, T. Schenk, X. Sang, M. Pešić, U. Schroeder, T. Mikolajick, and J.M. LeBeau: Structural changes underlying field cycling phenomena in ferroelectric HfO<sub>2</sub> thin films. *Adv. Electron. Mater.* **2**, 1600173 (2016).
75. T. Shimizu, T. Yokouchi, T. Oikawa, T. Shiraiishi, T. Kiguchi, A. Akama, T. J. Konno, A. Gruverman, and H. Funakubo: Contribution of oxygen vacancies to the ferroelectric behavior of Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films. *Appl. Phys. Lett.* **106**, 112904 (2015).
76. M. Hoffmann, U. Schroeder, T. Schenk, T. Shimizu, H. Funakubo, O. Sakata, D. Pohl, M. Drescher, C. Adelman, R. Materlik, A. Kersch, and T. Mikolajick: Stabilizing the ferroelectric phase in doped hafnium oxide. *J. Appl. Phys.* **118**, 072006 (2015).
77. S. Starschich, S. Menzel, and U. Böttger: Evidence for oxygen vacancies movement during wake-up in ferroelectric hafnium oxide. *Appl. Phys. Lett.* **108**, 032903 (2016).
78. S. Starschich, S. Menzel, and U. Böttger: Pulse wake-up and breakdown investigation of ferroelectric yttrium doped HfO<sub>2</sub>. *J. Appl. Phys.* **121**, 154102 (2017).
79. B. Max, M. Pešić, S. Slesazeck, and T. Mikolajick: Interplay between ferroelectric and resistive switching in doped crystalline HfO<sub>2</sub>. *J. Appl. Phys.* **123**, 134102 (2018).
80. A. Schönhals, C.M.M. Rosário, S. Hoffmann-Eifert, R. Waser, S. Menzel, and D.J. Wouters: Role of the electrode material on the RESET limitation in oxide ReRAM devices. *Adv. Electron. Mater.* **4**, 1700243 (2018).
81. M.H. Park, H.J. Kim, Y.J. Kim, W. Lee, T. Moon, and C.S. Hwang: Evolution of phases and ferroelectric properties of thin Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> films according to the thickness and annealing temperature. *Appl. Phys. Lett.* **102**, 242905 (2013).
82. P.D. Lomenzo, Q. Takmeel, S. Moghaddam, and T. Nishida: Annealing behavior of ferroelectric Si-doped HfO<sub>2</sub> thin films. *Thin Solid Films* **615**, 139 (2016).
83. C. Richter, T. Schenk, M.H. Park, F.A. Tscharrntke, E.D. Grimley, J. M. LeBeau, C. Zhou, C.M. Fancher, J.L. Jones, T. Mikolajick, and U. Schroeder: Si doped hafnium oxide—a "fragile" ferroelectric system. *Adv. Electron. Mater.* **3**, 1700131 (2017).
84. U. Schroeder, C. Richter, M.H. Park, T. Schenk, M. Pešić, M. Hoffmann, F.P.G. Fengler, D. Pohl, B. Rellinghaus, C. Zhou, C.C. Chung, J.L. Jones, and T. Mikolajick: Lanthanum-doped hafnium oxide: a robust ferroelectric material. *Inorg. Chem.* **57**, 2752 (2018).
85. M.H. Park, T. Schenk, C.S. Hwang, and U. Schroeder: Electrodes for fluorite-type ferroelectrics, Ferroelectricity in Hafnium and Zirconium oxide: materials and devices (Elsevier). In preparation.
86. A.G. Chernikova, M.G. Kozodaev, D.V. Negrov, E.V. Korostylev, M. H. Park, U. Schroeder, C.S. Hwang, and A.M. Markeev: Improved ferroelectric switching endurance of La-doped Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films. *ACS Appl. Mater. Interfaces* **10**, 2701 (2018).
87. M.H. Park, H.J. Kim, Y.J. Kim, W. Jeon, T. Moon, and C.S. Hwang: Ferroelectric properties and switching endurance of Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> films on tin bottom and tin or RuO<sub>2</sub> top electrodes. *Phys. Status Solidi RRL* **8**, 532 (2014).
88. S. Clima, D.J. Wouters, C. Adelman, T. Schenk, U. Schroeder, M. Jurczak, and G. Pourtois: Identification of the ferroelectric switching process and dopant-dependent switching properties in orthorhombic HfO<sub>2</sub>: a first principles insight. *Appl. Phys. Lett.* **104**, 092906 (2014).
89. S. Migita, H. Ota, H. Yamada, A. Sawa, and A. Toriumi: Thickness-independent behavior of coercive field in HfO<sub>2</sub>-based ferroelectrics. *IEEE Electron Devices Technology and Manufacturing Conference Proceedings of Technical Papers*.
90. L.-M. Wang: Relationship between Intrinsic Breakdown Field and Bandgap of Materials. *25th International Conference on Microelectronics*. doi: 10.1109/ICMEL.2006.1651032.
91. W. Lu, H. Li, and W. Cao: Landau expansion parameters for BaTiO<sub>3</sub>. *J. Appl. Phys.* **114**, 224106 (2013).
92. T.D. Huan, V. Sharma, G.A. Rossetti Jr., and R. Ramprasad: Pathways towards ferroelectricity in hafnia. *Phys. Rev. B* **90**, 064111 (2014).
93. S.V. Barabash, D. Pramanik, Y. Zhai, B. Magyari-Kope, and Y. Nishi: Ferroelectric switching pathways and energetics in (Hf,Zr)O<sub>2</sub>. *ECS Trans.* **75**, 107 (2017).
94. K. McKenna and A. Shluger: The interaction of oxygen vacancies with grain boundaries in monoclinic HfO<sub>2</sub>. *Appl. Phys. Lett.* **95**, 222111 (2009).
95. M.H. Park, H.J. Kim, Y.H. Lee, Y.J. Kim, T. Moon, K.D. Kim, S.D. Hyun, and C.S. Hwang: Two-step polarization switching mediated by a nonpolar intermediate phase in Hf<sub>0.4</sub>Zr<sub>0.6</sub>O<sub>2</sub> thin films. *Nanoscale* **8**, 13898 (2016).
96. T. Mittmann, F.P.G. Fengler, C. Richter, M.H. Park, T. Mikolajick, and U. Schroeder: Optimizing process conditions for improved Hf<sub>1-x</sub>Zr<sub>x</sub>O<sub>2</sub>

- ferroelectric capacitor performance. *Microelectron. Engineer.* **178**, 48 (2017).
97. K.D. Kim, M.H. Park, H.J. Kim, Y.J. Kim, T. Moon, Y.H. Lee, S.D. Hyun, T. Gwon, and C.S. Hwang: Ferroelectricity in undoped-HfO<sub>2</sub> thin films induced by deposition temperature control during atomic layer deposition. *J. Mater. Chem. C* **4**, 6864 (2016).
98. Y.H. Lee, H.J. Kim, T. Moon, K.D. Kim, S.D. Hyun, H.W. Park, Y.B. Lee, M.H. Park, and C.S. Hwang: Preparation and characterization of ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films grown by reactive sputtering. *Nanotechnology* **28**, 305703 (2017)
99. H.J. Kim, M.H. Park, Y.J. Kim, Y.H. Lee, W. Jeon, T. Gwon, T. Moon, K. D. Kim, and C.S. Hwang: Grain size engineering for ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> films by an insertion of Al<sub>2</sub>O<sub>3</sub> interlayer. *Appl. Phys. Lett.* **105**, 192903 (2014).
100. E.D. Grimley, T. Schenk, T. Mikolajick, U. Schroeder, and J.M. LeBeau: Atomic structure of domain and interphase boundaries in ferroelectric HfO<sub>2</sub>. *Adv. Mater. Interfaces* **5**, 1701258 (2018).
101. S. Mueller, J. Mueller, A. Singh, S. Riedel, J. Sundqvist, U. Schroeder, and T. Mikolajick: Incipient ferroelectricity in Al-doped HfO<sub>2</sub> thin films. *Adv. Funct. Mater.* **22**, 2412 (2012).
102. M. Pešić, T. Li, V. Di Lecce, M. Hoffmann, M. Materano, C. Richter, B. Max, S. Slesazeck, U. Schroeder, L. Larcher, and T. Mikolajick: Built-in bias generation in anti-ferroelectric stacks: methods and device applications. *IEEE Journal of the Electron Devices Society*. doi: 10.1109/JEDS.2018.2825360.
103. M. Pešić, M. Hoffmann, C. Richter, T. Mikolajick, and U. Schroeder: Nonvolatile random access memory and energy storage based on anti-ferroelectric like hysteresis in ZrO<sub>2</sub>. *Adv. Funct. Mater.* **26**, 7486 (2016).
104. F.P.G. Fengler, R. Nigon, P. Muralt, E.D. Grimley, X. Sang, V. Sessi, R. Hentschel, J.M. LeBeau, T. Mikolajick, and U. Schroeder: Analysis of performance instabilities of hafnia-based ferroelectrics using modulus spectroscopy and thermally stimulated depolarization currents. *Adv. Electron. Mater.* **4**, 1700547 (2018).
105. P. Polakowski and J. Mueller: Ferroelectricity in undoped hafnium oxide. *Appl. Phys. Lett.* **106**, 232905 (2015).
106. S. Mueller, S.R. Summerfelt, J. Muller, U. Schroeder, and T. Mikolajick: Ten-nanometer ferroelectric Si:HfO<sub>2</sub> films for next-generation FRAM capacitors. *Electron Device Lett.* **33**, 1300 (2012).
107. S. Mueller, J. Muller, U. Schroeder, and T. Mikolajick: Reliability characteristics of ferroelectric Si:HfO<sub>2</sub> thin films for memory applications. *IEEE Trans. Device Mater. Rel.* **13**, 93 (2013).
108. S. Mueller, J. Muller, R. Hoffmann, E. Yurchuk, T. Schlosser, R. Boschke, J. Paul, M. Goldbach, T. Herrmann, A. Zaka, U. Schroeder, and T. Mikolajick: From MFM capacitors toward ferroelectric transistors: endurance and disturb characteristics of HfO<sub>2</sub>-based FeFET devices. *IEEE Trans. Electron Devices* **60**, 4199 (2013).
109. P.D. Lomenzo, Q. Takmeel, C. Zhou, C.-C. Chung, S. Moghaddam, J. L. Jones, and T. Nishida: Mixed Al and Si doping in ferroelectric HfO<sub>2</sub> thin films. *Appl. Phys. Lett.* **107**, 242903 (2015).
110. M.H. Park, H.J. Kim, Y.J. Kim, T. Moon, K.D. Kim, Y.H. Lee, S.D. Hyun, and C.S. Hwang: Study on the internal field and conduction mechanism of atomic layer deposited ferroelectric Hf<sub>0.5</sub>Zr<sub>0.5</sub>O<sub>2</sub> thin films. *J. Mater. Chem. C* **3**, 6291 (2015).
111. E. Yurchuk, S. Mueller, D. Martin, S. Slesazeck, U. Schroeder, and T. Mikolajick: Origin of the endurance degradation in the novel HfO<sub>2</sub>-based 1T ferroelectric non-volatile memories, 2014 *IEEE International Reliability Physics Symposium*, Waikoloa, HI, 2014, pp. 2E.5.1–2E.5.5. doi: 10.1109/IRPS.2014.686060.