

## Silver Nanoparticles Loaded Activated Carbon Synthesis Using *Clitorea Ternatea* Extract for Crystal Violet Dye Removal

Mohamad Aizad Mohd Mokhtar, Roshafima Rasit Ali \* and Eleen Dayana Mohamed Isa

Malaysia Japan International Institute of Technology, Universiti Teknologi Malaysia, Jalan Sultan Yahya Petra, 54100 Kuala Lumpur, Malaysia

\* Correspondence: [roshafima@utm.my](mailto:roshafima@utm.my); Tel.: +6016-7775724  
<https://doi.org/10.37934/jrnn.3.1.2636>

### ABSTRACT

Dyes are coloured compound which are widely used in textile, painting, rubber, cosmetics, plastics and leather industry to colour their products. However, the irresponsibility of certain manufacturer results in producing dye waste and channel it to water resources had become one of the biggest challenges in water pollution. In this study, an effective solid adsorbent derived from sustainable sources for adsorption capacity study was produced which is silver nanoparticles loaded activated carbon (Ag NPs – AC) to remove crystal violet (CV) dye. Adsorption process are cost – effective, simple and flexible with various dye pollutants. Silver nanoparticles (Ag NPs) was synthesized from *Clitorea Ternatea* flower extract that utilizes functions as stabilizing agents for silver nitrate ( $\text{AgNO}_3$ ) to promotes environmental friendly with no toxic chemicals produced and loaded in activated carbon (AC). Characterization of Ag NPs was analysed using UV-Visible which correspond to peak at 408 nm and XRD analysis. Four peaks values for silver at  $2\theta$  of  $38.19^\circ$ ,  $44.43^\circ$ ,  $64.57^\circ$ ,  $77.43^\circ$  and average crystallite size of Ag NPs and Ag NPs – AC were calculated to be 16.11 nm and 36.13 nm respectively that were obtained from XRD pattern. The adsorption capacity of Ag NPs – AC was analysed and the optimum conditions were determined using different parameters which are the Ag NPs - AC ratio (1.0 g), contact time (240 min), adsorbent dosage (30 mg) and pH of CV dye (10). The highest percentage removal of CV dye using Ag NPs – AC was recorded up to 97% at 240 min with 30 mg dosage. Ag NPs – AC as adsorbent is a promising advanced materials in removing water pollutants with viable conditions and can applied in the wastewater treatment industry.

*Keywords: Silver nanoparticles, activated carbon green synthesis, dye adsorption*

Received: 28 May 2021

Revised: 16 June 2021

Accepted: 27 June 2021

Published: 7 August 2021

### 1. Introduction

Water pollution associated with dye pollutants are becoming worsen since the annual worldwide production of commercial dyes are expected more than 100,000 types [1]. Even worse, it is also

1 reported that the worldwide industrial effluent estimated 280,000 tons of textile dyes are being  
2 discharge every year [2]. The existence of dyes and paints from various industries such as textiles,  
3 plastics, cosmetics, food and petroleum refineries contain heavy loads of mixed colours from its  
4 discharged effluent that reflect toxicity to aquatic life [3]. Moreover, the presence of dyes in  
5 wastewater provide significant source of water pollution because even at low concentration the dye  
6 waste is visible and can harm aquatic life [4]. For instance, high concentration of crystal violet (CV)  
7 dye in water can affect the oxygenation and photosynthesis capacity in the water [5].

8 Generally, there are three methods in removing dye which are biological, chemical and physical  
9 methods. Biological methods promote microorganism such as algae, yeast, fungi and bacteria that  
10 can transform dye into less harmful forms [6]. Meanwhile, chemical methods includes photocatalytic  
11 degradation, ozonation and electrochemical treatment while physical method include precipitation-  
12 flocculation, adsorption, ion exchange and membrane filtration [4]. Among all the methods,  
13 adsorption process in removing dye pollutants shows promising results because it is low cost, ease  
14 in operation, can eliminate all type of contaminants, flexible, simple and insensitivity towards toxic  
15 pollutants [7].

16 Recently, various nanoparticles that had been studied for the application of dye removal in water  
17 and wastewater remediation. The application of adsorption process commonly used nanoparticles  
18 such as carbon-based, metal, ceramic, polymeric and lipid-based nanoparticles [8]. Among the  
19 nanoparticles involved, silver nanoparticles (Ag NPs) had successfully remove dye for water and  
20 wastewater treatment due to its nano-size that provide high surface area to volume ratio in adsorbing  
21 dye [9]. However, the drawback of using Ag NPs alone in dye treatment is aggregation of silver (Ag)  
22 ions in water that may cause hazard towards environment. Hence, Ag NPs incorporated with surface  
23 adsorbent can reduce the limitations and provide even higher adsorption capacity due to great  
24 potential of both Ag NPs and adsorbent such as activated carbon (AC) which is low cost and high  
25 porosity properties and widely used adsorbent to remove pollutants [10].

26 Silver nanoparticles loaded activated carbon (Ag NPs – AC) had shown great performance in  
27 removing dye pollutants. For instance, CV dye was removed with adsorption capacity of 82.2 mg/g  
28 and the reusability of this materials in optimum condition was 7 consecutive times [11]. Moreover, it  
29 is reported that Ag NPs – AC capable of removing Sudan red 7B with a maximum adsorption capacity  
30 of 90.909 mg.g<sup>-1</sup> and low removal time [12]. Hence, the use of Ag NPs – AC is very promising with  
31 potential benefits in removing dye by adsorption process for water and wastewater treatment  
32 application and promoting higher active sites of AC for better adsorption process.

33 Green synthesis method in producing Ag NPs via plant extract are eco-friendly, rapid, cost-  
34 effective and non-pathogenic which drawn attention of researcher in replacing sodium borohydride,  
35 hydrazine and sodium citrate as reducing and stabilizing agents. This provides minimal waste,  
36 reduced energy use, renewable materials and low risk methods [13]. Butterfly pea or *Clitoria Ternatea*  
37 (CT) flower belongs to the family of Fabaceae that are available in tropical Asia such as India,  
38 Thailand, Myanmar, Indonesia, Philippines and Malaysia [14]. In this research, CT flower extract was  
39 used as the stabilizing agent in producing Ag NPs. It contains high amount of anthocyanin pigments  
40 compare to other flowers which is the main components in the green synthesis process [15].

## 41 42 **2. Materials and Methods**

43 All chemicals and materials used were analytical grade with silver nitrate (AgNO<sub>3</sub>), sodium  
44 hydroxide (NaOH), hydrochloric acid, (HCl) and CV dye powder were purchased from R&M  
45 Chemicals, Malaysia. Meanwhile, AC powder was purchased from Chemiz, Malaysia with no further  
46 heating or activation. Fresh CT flowers were collected at a community farm near Keramat, Kuala

1 Lumpur, Malaysia. The flowers were grown under no specific care of watering and fertilizer since  
2 the flowers grew freely and abundant without maximal care. All aqueous solutions were used with  
3 deionized water.

#### 4 2.1. Synthesis and characterization of Ag NPs – AC

5  
6 The collected CT flowers were double wash with tap water and deionized water to remove dirt  
7 and sand at the surface of the flowers. Then, the flowers were dried for 2 hr at 70°C in an oven. The  
8 dried CT flowers were crush into powder using conventional home blender (Phillip Blender Core  
9 Series 5000) and stored in an airtight container to ensure no moisture and preventing mould and  
10 fungus grown. Next, 0.05 g of powdered CT flowers were mixed with 100 ml of deionized water with  
11 continuous stirred at 500 rpm for 1 hr in room temperature to produce CT flower extract.

12 Then, the aqueous extract was centrifuged (KUBOTO Tabletop Micro Centrifuge Model 3300) for  
13 30 min at 4000 rpm and filtered using Whatman grade 1 filter paper. The flower extract was then  
14 transferred into a centrifuge tube for further use and stored in a freezer. 1 ml of 0.1 M NaOH were  
15 used to alter 20 ml of prepared CT flower extract to pH 10. Next, the extract was stirred for 10 min at  
16 500 rpm and mixed with 4 ml of 3 mM AgNO<sub>3</sub> at 50°C for 30 min to produce Ag NPs solution.

17 Nanocomposite of Ag NPs – AC were prepared by added 4 ml of 3 mM AgNO<sub>3</sub> with mass  
18 variation of AC (0.25, 0.5, 0.75 and 1.25 g) and stirred for 10 min at 500 rpm. Then, CT flower extract  
19 of pH 10 were mixed with the solution at 50°C for 30 min. Then, the solution was centrifuged,  
20 sonicated and washed for 3 consecutive times. Finally, the produce Ag NPs – AC were dried at 60°C  
21 for 24 hr and ready to be used as adsorbent powder.

22 Ag NPs was characterized using UV – Visible Spectroscopy (UV – Vis) (Shimadzu UV – 2600) to  
23 study the formation of Ag NPs via green synthesis method. Furthermore, Ag NPs and Ag NPs – AC  
24 were characterized with X – ray diffraction (XRD) using XRD-Empyrean (PAN analytical, United  
25 Kingdom). XRD analysis pattern at 2θ angle from 20° to 80° were analysed for both materials.

#### 26 27 2.2. Batch adsorption of CV dye

28  
29 The batch adsorption of CV dye started with the preparation of 200 ppm or 200 mg/L CV dye  
30 solution. 50 ml of CV dye solution was transferred into a 100 ml conical flask for further used for  
31 every parameter. Next, 30 mg of Ag NPs – AC was used initially and mixed in the conical flasks that  
32 were place on an orbital shaker (IKA Shakers KS 260 basic) at a constant 300 rpm with different  
33 parameter such as Ag NPs - AC ratio (0.25, 0.5, 0.75 and 1.25 g), contact time, adsorbent dosage (10,  
34 20, 30 and 40 mg) and CV dye pH (3, 7, 9 and 10). Analysis of initial and final concentration of CV  
35 dye were analysed using UV-Vis and calculated using Eq. 1 below to know the percentage of removal  
36 by using Ag NPs – AC as adsorbent where Abs = Absorbance.


$$\% \text{ CV Dye Removal} = \frac{\text{Initial Abs} - \text{Final Abs}}{\text{Initial Abs}} \times 100\% \quad (1)$$

### 37 38 3. Results and Discussion


#### 39 3.1. Synthesis of Ag NPs – AC

40  
41 The green synthesis of Ag NPs was successfully conducted using CT flower extract. The CT  
42 flower extract acts as stabilizing agent for AgNO<sub>3</sub>. Anthocyanin pigments that present in the CT  
43 flower is the key element in the green synthesis of Ag NPs that replaced conventional reducing agent.

1 The synthesis route is simple and fast as shown in Figure 1 where the total time from preparing the  
2 flower extract to producing Ag NPs was only 90 min. Besides, the heating used was low which was  
3 50°C to fasten the reaction. In this study, 0.1 M of NaOH was used to alter the flower extract to alkaline  
4 medium. It is because it took longer time to produce Ag NPs in neutral medium. This finding was  
5 also supported by Khwannimit *et al.* [16] that uses NaOH to fasten the reaction. Observation directly  
6 by naked eye clearly shows the colour changes from light blue to dark brown indicating the formation  
7 of Ag NPs and reduction of  $\text{Ag}^+$  to  $\text{Ag}^0$  as shown in Figure 2. Furthermore, Ag NPs – AC was  
8 successfully synthesized from Ag NPs solution and AC with mass variation ranging from 0.25, 0.5,  
9 0.75 and 1.25 g via in-situ method. Ag NPs – AC was produced in the form of black powdered mainly  
10 came from the AC. Naked eye observation shows that the Ag NPs – AC contain very fine shiny silver  
11 particles which is the Ag particles. This confirm the loading was successful and the technique was  
12 valid.

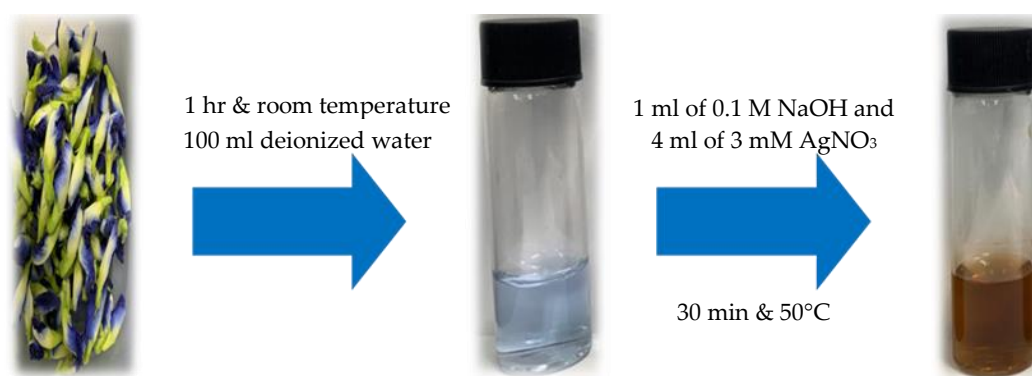

13  
14 **Figure 1.** Green synthesis of Ag NPs from CT flower extract.

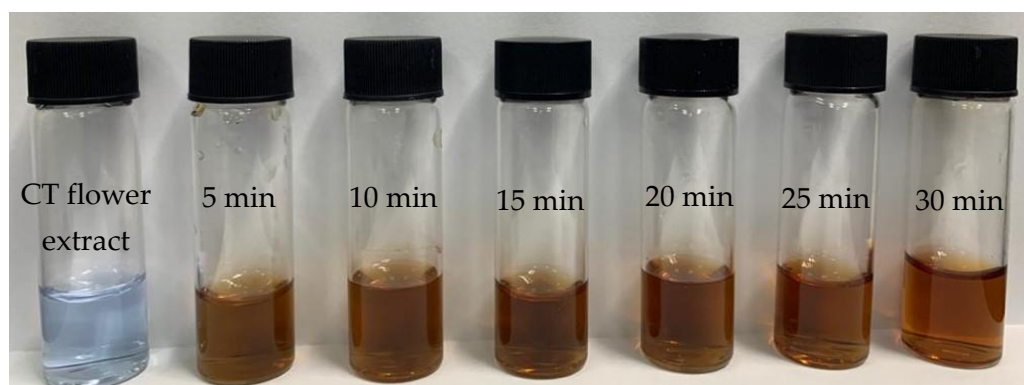


15  
16  
17 **Figure 2.** Complete formation of Ag NPs in 30 min.

### 18 3.2. UV-Visible spectroscopy analysis

19  
20 UV-Vis analysis was carried out to study the formation of Ag NPs via the green synthesis method.  
21 Figure 3 shows the UV-Vis graph for Ag NPs solution with peaks at 408 nm. The UV-Vis graph  
22 pattern from this study correspond with the research done by Khwannimit *et al.* [16] which confirm  
23 the formation of Ag NPs but with different peak value which is 430 nm that indicates even smaller  
24 nanoparticles produces. This is because the optimum condition for the green synthesis of Ag NPs  
25 which range from the temperature, pH, reaction time,  $\text{AgNO}_3$  concentration and volume ratio of

1 AgNO<sub>3</sub> to the CT flower extract were not analysed in this study. Analysing these parameters can  
2 obtain the optimum synthesis condition in producing smaller Ag NPs. This is because loading smaller  
3 Ag NPs into AC need to be achieved since it can increase the adsorption capacity and reactive center  
4 of AC compared to pure AC [11].

5

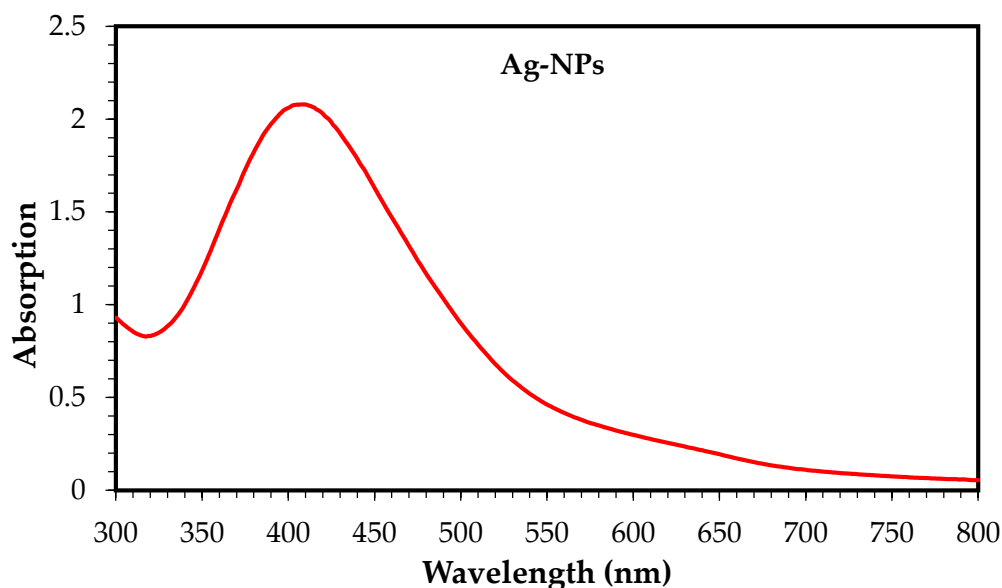

6

7

**Figure 3.** UV-Vis graph for the formation of Ag NPs.

### 8 3.2. XRD analysis

9

10 The nanostructured and crystal of Ag NPs and Ag NPs – AC was analysed by using XRD. The  
11 XRD graph as shown in Figure 4 shows two graph for Ag NPs and Ag NPs – AC respectively. Four  
12 peaks values for Ag NPs – AC at 2θ of 38.13°, 44.28°, 64.32° and 77.46° were identified. Meanwhile  
13 four peak values for Ag at 2θ of 38.19°, 44.43°, 64.57° and 77.43° corresponding with the face-centred  
14 cubic structure (FCC) of Ag [17] and its crystalline nature with sets of lattice planes of (111), (200) and  
15 (311) [18-21]. Furthermore, the crystallite size of Ag NPs and Ag NPs – AC was calculated based on  
16 the XRD pattern using Scherrer's equation as shown in Eq.2 where D = average crystallite size, k =  
17 constant, λ = wavelength, β = full width at half maximum (FWHM) and θ = Bragg angle [22-24].  
18 According to the equation, k = 0.94 and λ = 1.54060. The average of crystallite size of Ag NPs and Ag  
19 NPs – AC for this work is 16.11 nm and 36.13 nm respectively.

$$D = \frac{k\lambda}{\beta\cos\theta} \quad (2)$$

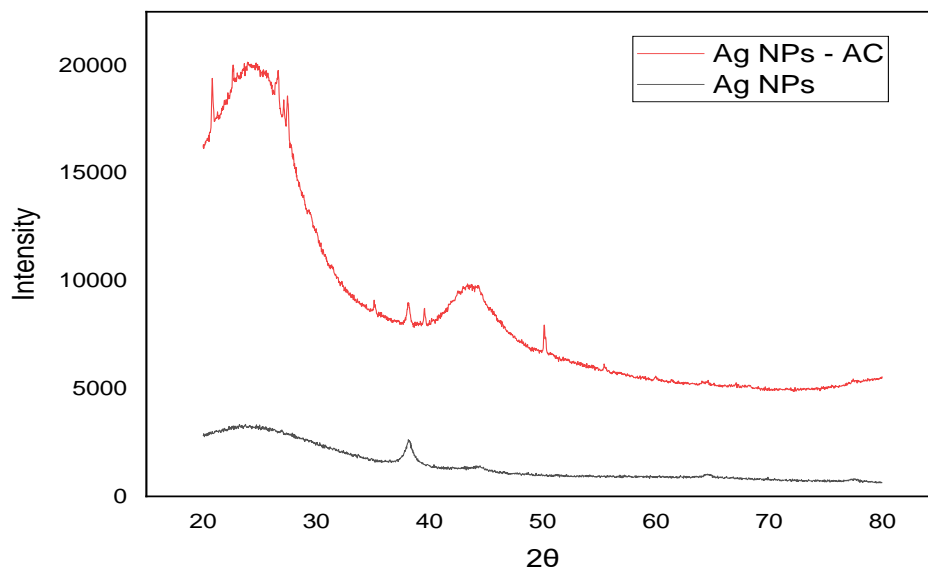


Figure 4. XRD analysis for Ag NPs and Ag NPs – AC.

### 3.3. Batch adsorption

#### 3.3.1 Effect of Ag NPs - AC ratio

The first parameter studied in this research is the effect of AC mass variation during the synthesis of Ag NPs – AC. The mass variation was ranging from 0.25, 0.5, 0.75 and 1.25 g with Ag NPs that was kept constant since the Ag NPs was in aqueous solution form. The experiment conducted is to study the effect of Ag NPs – AC ration as compared to pure AC. Figure 5 shows the effect of pure AC and variation of Ag NPs – AC ration on the percentage of CV dye removal. From the graph, pure AC removed around 70.9% of CV dye.

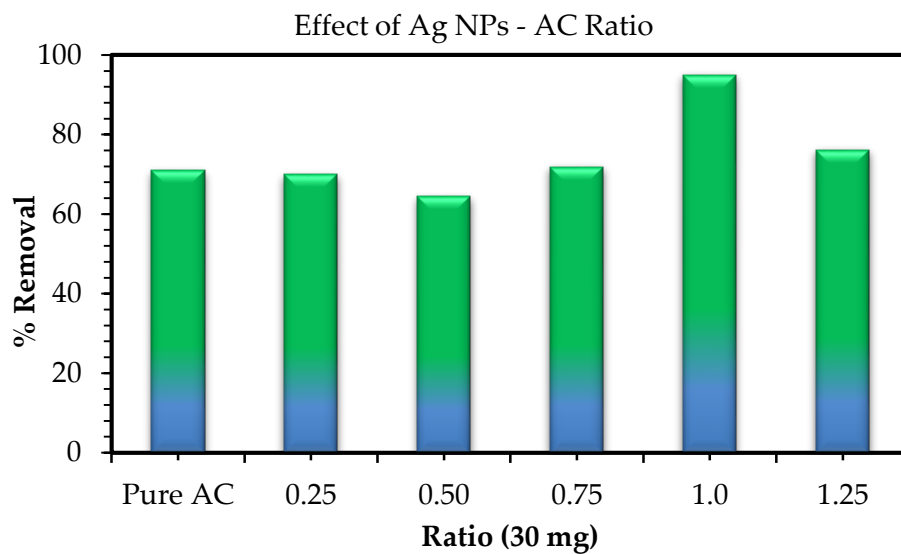



Figure 5. Effect of Ag NPs - AC ratio.

However, the data also shows that for AC ratio of 0.5 and 0.25 g the percentage removal was lower than pure AC indicating that the ratio is not suitable for Ag NPs – AC formation mainly

1 because the amount of AC is insignificant or less since AC is the main adsorbent in removing  
2 CV dye. Meanwhile, for ratio from 0.75 until 1.25 g shows promising results as it is higher than  
3 pure AC. In this experiment, 1.0 g ratio shows excellent results as it can remove up to 94.9% of  
4 CV dye that specify the ratio is acceptable for the synthesis of Ag NPs - AC. Hence, 1.0 g ratio is  
5 the most suitable for the removal of CV dye.

### 6 3.3.1 Effect of adsorption contact time

7  
8 The effect of contact time is very important to design an economical wastewater treatment. This  
9 is because longer time in removing the pollutants will cause more utilities and energy need to be  
10 used. Therefore, having a shorter contact time for the process to be carried out can give high impact  
11 and significant changes in a wastewater treatment for dye removal. The data and information shows  
12 that the adsorption was rapidly increased from 10 to 90 min indicating more active sites available in  
13 AC to remove CV dye as shown in Figure 6. Meanwhile, from 120 to 240 min the removal percentage  
14 were slow which indicates that the active sites were decreasing upon increasing of time. It is also  
15 because of concentration gradient and diffusion rate that are lowering in increasing of contact time  
16 [25]. At 240 min, the percentage removal was up to 97.7% which correspond to nearly all CV dye was  
17 adsorb with the observation of colorless solution. Therefore, the optimum contact time in removing  
18 CV dye is 240 min where the adsorption above the time will further decrease because of the  
19 unavailability and limited active sites present in the adsorbent [26].  
20

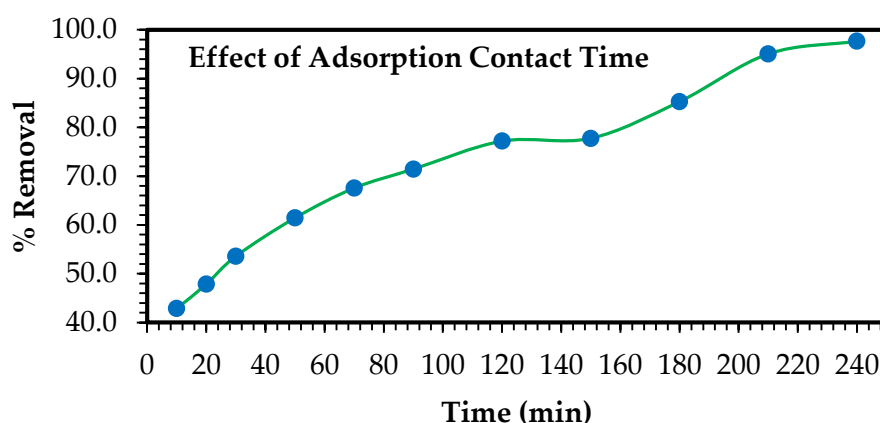


21  
22 **Figure 6.** Effect of adsorption contact time.

### 23 3.3.1 Effect of adsorbent dosage

24  
25 The effect of adsorbent dosage is crucial since it is relatable to the economic and environmental  
26 evaluation. This is because the more the dosage, the more the cost and effect in environment. This  
27 parameter tested the adsorbent dosage of Ag NPs – AC ranging from 10 – 40 mg. The preliminary  
28 hypothesis indicates that the more the adsorbent dosage, the higher the removal percentage. Hence,  
29 Figure 7 approves the hypothesis since 30 and 40 mg dosage shows high adsorption capacity. In this  
30 experiment, the adsorbent dosage that shows promising results were 30 and 40 mg with removal  
31 percentage of 97.7% and 98.1% at 240 min respectively. Since, the optimum contact time is 240 min,  
32 the adsorbent dosage was chosen based on 240 min contact time from previous parameter [26].  
33 However, adsorbent dosage of 40 mg was not choose as the best condition of CV removal since the  
34 adsorption capacity was not significantly high compare to 30 mg. Therefore, 30 mg was choosing as


1 the best condition in removing CV dye since the adsorption capacity is high and to maintain less  
2 adsorbent dosage, low cost and effect towards the environment.

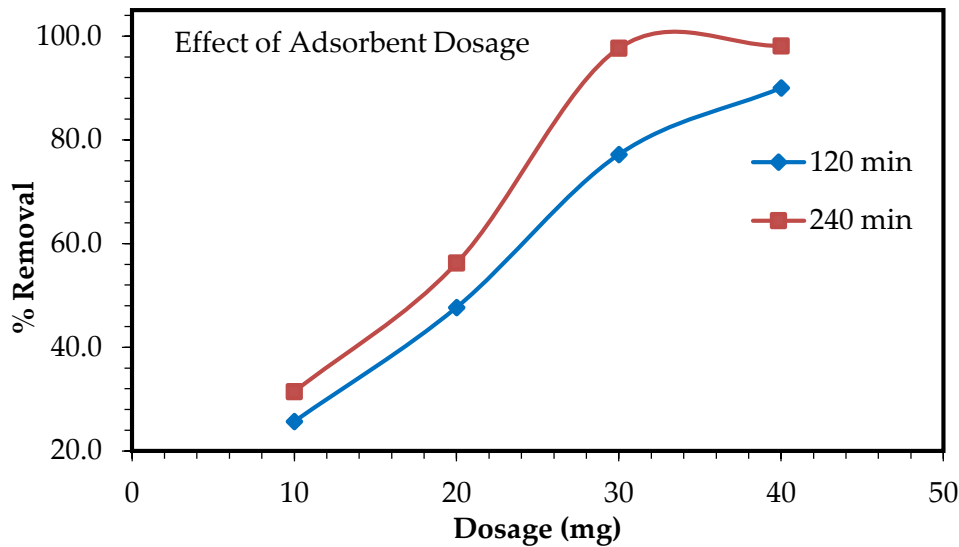

3  
4 **Figure 7.** Effect of adsorbent dosage.

### 5 3.3.1 Effect pH of CV dye

6  
7 The last parameter is the effect of dye pH which is to know the best condition of the solution for  
8 better adsorption capacity study. In this study, pH of CV dye ranging from 3, 7, 9 and 10 were tested  
9 in order to study the best medium in which Ag NPs – AC can absorb CV dye with the highest capacity.  
10 The CV dye pH was adjusted by using NaOH and HCl for alkaline and acidic medium respectively  
11 with initial pH was 5. The data shows that the best condition is the alkaline medium since pH 9 and  
12 10 shows the highest adsorption capacity for Ag NPs – AC as shown in Figure 8 with similar result  
13 reported by AbdeI-Salam, Ewais [11]. Meanwhile, in acidic medium which is at pH 3, the adsorption  
14 was only 84% compared to alkaline medium that can reach to 100% removal. This is because in  
15 alkaline medium, strong electrostatic attraction between cationic CV dye and negative charge of Ag  
16 NPs – AC that results with increase in CV dye adsorption [25]. Hence, pH 9 and 10 is the best medium  
17 in removing CV dye but pH 10 was chose in this study because the adsorption process was rapid for  
18 the first 5 min compared to pH 9.

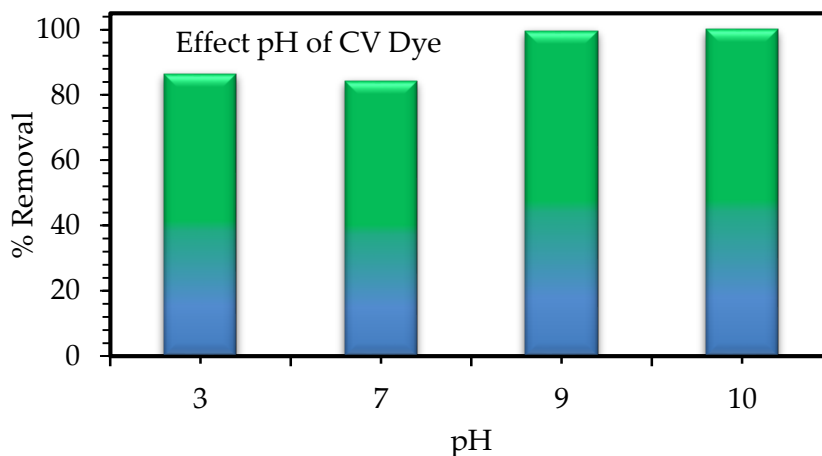

19  
20  
21 **Figure 8.** Effect pH of CV dye.



#### 1 4. Conclusions

2 Water pollution causes by dye from dyeing industry need to be tackle with cost-effective and  
3 sustainable methods. In this present study, adsorption process was introduced in removing CV dye  
4 by using Ag NPs – AC that promotes high surface area and porous structure. Ag NPs – AC as  
5 adsorbent was produced by plant mediated synthesis of Ag NPs using CT flowers that promotes  
6 stabilizing agents and loaded with AC. The Ag NPs was characterized using UV – Vis which  
7 correspond at 408 nm. Moreover, The XRD analysis for Ag NPs and Ag NPs – AC provide significant  
8 information regarding crystallite size which is 16.11 nm and 36.13 nm. The adsorption capacity of Ag  
9 NPs – AC were determined by analysing the effect of Ag NPs - AC ratio (1.0 g), adsorption contact  
10 time (240 min), adsorbent dosage (30 mg) and pH of CV dye (10). In future, the study regarding  
11 removal of dye using Ag NPs - AC can be improving by implementing reusability or regenerating  
12 study of the adsorbent to fully maximise the adsorption capacity. Furthermore, the study regarding  
13 the adsorbent waste management need to be analysed to ensure the water will not be polluted with  
14 the adsorbent. Finally, the study on the aggregation of Ag ions in aqueous solution can be determine  
15 to analysed the health and hazard potential towards human and aquatic life.

#### 16 17 Funding

18 This research was funded by CRG National Grant (R.K130000.7343.4B539).

#### 19 20 Acknowledgement

21 The authors are grateful for the full support from Chemical and Environmental Engineering (ChEE)  
22 Department, Malaysia-Japan International Institute of Technology (MJIIT), Universiti Teknologi  
23 Malaysia, Kuala Lumpur under funding of CRG National Grant (R.K130000.7343.4B539).

#### 24 25 References

- 26 1. Pang, Yean L., and Ahmad Z. Abdullah. "Current Status of Textile Industry Wastewater  
27 Management and Research Progress in Malaysia: A Review." *CLEAN - Soil, Air, Water* 41, no. 8  
28 (2013): 751-64. doi: 10.1002/clen.201000318.
- 29 2. Ali, Hazrat. "Biodegradation of Synthetic Dyes—a Review." *Water, Air, & Soil Pollution* 213, no. 1  
30 (2010/11/01 2010): 251-73. doi: 10.1007/s11270-010-0382-4.
- 31 3. Sheeja, J., K. Sampath, and R. Manivel. "Silver Nanoparticles Doped Slaked Lime as Adsorbent  
32 for the Removal of Basic Dyes." *Rasayan Journal of Chemistry* 12, no. 1 (2019): 262-71. doi:  
33 10.31788/rjc.2019.1215002.
- 34 4. Ruan, Wenqian, Jiwei Hu, Jimei Qi, Yu Hou, Chao Zhou, and Xionghui Wei. "Removal of Dyes  
35 from Wastewater by Nanomaterials : A Review." *Advanced Materials Letters* 10, no. 1 (2019): 9-20.  
36 doi: 10.5185/amlett.2019.2148.
- 37 5. Monash, P., and G. Pugazhenth. "Adsorption of Crystal Violet Dye from Aqueous Solution  
38 Using Mesoporous Materials Synthesized at Room Temperature." *Adsorption* 15, no. 4 (2009/08/01  
39 2009): 390-405. doi: 10.1007/s10450-009-9156-y
- 40 6. McMullan, G., C. Meehan, A. Conneely, N. Kirby, T. Robinson, P. Nigam, I. M. Banat, R.  
41 Marchant, and W. F. Smyth. "Microbial Decolourisation and Degradation of Textile Dyes." [In  
42 eng]. *Appl Microbiol Biotechnol* 56, no. 1-2 (Jul 2001): 81-7. doi: 10.1007/s002530000587.
- 43 7. Crini, Grégorio. "Non-Conventional Low-Cost Adsorbents for Dye Removal: A Review."  
44 *Bioresource Technology* 97, no. 9 (2006/06/01/ 2006): 1061-85. doi: 10.1016/j.biortech.2005.05.001.

- 1 8. Abegunde, Segun Michael, Kayode Solomon Idowu, Olorunsola Morayo Adejuwon, and  
2 Tinuade Adeyemi-Adejolu. "A Review on the Influence of Chemical Modification on the  
3 Performance of Adsorbents." *Resources, Environment and Sustainability* 1 (2020). doi:  
4 [10.1016/j.resenv.2020.100001](https://doi.org/10.1016/j.resenv.2020.100001).
- 5 9. Khalil, K. A., H. Fouad, T. Elsarnagawy, and F. N. Almajhdi. "Preparation and Characterization  
6 of Electrospun Plga/Silver Composite Nanofibers for Biomedical Applications." Article.  
7 *International Journal of Electrochemical Science* 8, no. 3 (2013): 3483-93.
- 8 10. Fierro, V., V. Torné-Fernández, D. Montané, and A. Celzard. "Adsorption of Phenol onto  
9 Activated Carbons Having Different Textural and Surface Properties." *Microporous and*  
10 *Mesoporous Materials* 111, no. 1 (2008/04/15/ 2008): 276-84. doi: [10.1016/j.micromeso.2007.08.002](https://doi.org/10.1016/j.micromeso.2007.08.002).
- 11 11. AbdEl-Salam, A. H., H. A. Ewais, and A. S. Basaleh. "Silver Nanoparticles Immobilised on the  
12 Activated Carbon as Efficient Adsorbent for Removal of Crystal Violet Dye from Aqueous  
13 Solutions. A Kinetic Study." *Journal of Molecular Liquids* 248 (2017): 833-41. doi:  
14 [10.1016/j.molliq.2017.10.109](https://doi.org/10.1016/j.molliq.2017.10.109).
- 15 12. Marahel, F., M. Ghaedi, and S. N. Kokhdan. "Silver Nanoparticle Loaded on Activated Carbon  
16 as an Adsorbent for the Removal of Sudan Red 7b from Aqueous Solution." 2012.
- 17 13. Ioana-Raluca, Șuică-Bunghez, Rodica-Mariana Ion, Alexandrina Nuță, and Ana-Alexandra  
18 Sorescu. "Green Synthesis of Silver Nanoparticles Using Plant Extracts." Proceedings of The 4th  
19 International Virtual Conference on Advanced Scientific Results, 2016.
- 20 14. Chan, J. Z., R. Rasit Ali, K. Shameli, M. S. N. Salleh, K. X. Lee, and E. D. Mohamed Isa. "Green  
21 Synthesis of Gold Nanoparticles Using Aqueous Extract of Clitoria Ternatea Flower." *IOP*  
22 *Conference Series: Materials Science and Engineering* 808 (2020/04/01 2020): 012036. doi:  
23 [10.1088/1757-899x/808/1/012036](https://doi.org/10.1088/1757-899x/808/1/012036).
- 24 15. Jamil, Nadzirah, Mohd Naquiddin Mohd Zairi, Nur A'in Mohd Nasim, and Furzani Pa'ee.  
25 "Influences of Environmental Conditions to Phytoconstituents in Clitoria Ternatea (Butterfly Pea  
26 Flower) – a Review." *Journal of Science and Technology* 10, no. 2 (2018). doi:  
27 [10.30880/jst.2018.10.02.029](https://doi.org/10.30880/jst.2018.10.02.029).
- 28 16. Khwannimit, Duangruedee, Rasimate Maungchang, and Parawee Rattanakit. "Green Synthesis  
29 of Silver Nanoparticles Using Clitoria Ternatea Flower: An Efficient Catalyst for Removal of  
30 Methyl Orange." *International Journal of Environmental Analytical Chemistry* (2020): 1-17. doi:  
31 [10.1080/03067319.2020.1793974](https://doi.org/10.1080/03067319.2020.1793974).
- 32 17. Fatimah, Is, Habibi Hidayat, Bambang Hernawan Nugroho, and Saddam Husein. "Ultrasound-  
33 Assisted Biosynthesis of Silver and Gold Nanoparticles Using Clitoria Ternatea Flower." *South*  
34 *African Journal of Chemical Engineering* 34 (2020): 97-106. doi: [10.1016/j.sajce.2020.06.007](https://doi.org/10.1016/j.sajce.2020.06.007).
- 35 18. Krithiga, Narayanaswamy, Athimoolam Rajalakshmi, and Ayyavoo Jayachitra. "Green Synthesis  
36 of Silver Nanoparticles Using Leaf Extracts of *Clitoria Ternatea* and *Solanum Nigrum* and Study of  
37 Its Antibacterial Effect against Common Nosocomial Pathogens." *Journal of Nanoscience* 2015  
38 (2015): 1-8. doi: [10.1155/2015/928204](https://doi.org/10.1155/2015/928204).
- 39 19. Shameli, K., Ahmad, M., Jazayeri, S.D., Shabanzadeh, P., Jahangirian, H. "Synthesis and  
40 characterization of polyethylene glycol mediated silver nanoparticles by the green method." *International Journal of Molecular Sciences* 12 (2012): 6639-6650. doi: [10.3390/ijms13066639](https://doi.org/10.3390/ijms13066639).
- 41 20. Ahmad, M., Shameli, K., Darroudi, M., Yunus, W.M.Z.W., Ibrahim, N.A. "Synthesis and  
42 characterization of silver/clay/chitosan bionanocomposites by UV-irradiation method". *American*  
43 *Journal of Applied Sciences* 6 (2009) 2030. doi:[10.3844/ajassp.2009.2030.2035](https://doi.org/10.3844/ajassp.2009.2030.2035).
- 44 21. Izadiyan, Z., Shameli, K., Hara, H., Mohd Taib, S.H. "Cytotoxicity assay of biosynthesis gold  
45 nanoparticles mediated by walnut (*Juglans regia*) green husk extract." *Journal of Molecular Structure*  
46 1151 (2018) 97-105. doi: [10.1016/j.molstruc.2017.09.039](https://doi.org/10.1016/j.molstruc.2017.09.039).
- 47

- 1 22. Shameli, K., Ahmad, M., Al-Mulla, E.A.J., Shabanzadeh, P., Bagheri, S. "Antibacterial effect of  
2 silver nanoparticles on talc composites." *Research on Chemical Intermediates* 41 (2015) 251-263. doi:  
3 [10.1007/s11164-013-1188-y](https://doi.org/10.1007/s11164-013-1188-y).
- 4 23. Jazayeri, S.D., Ideris, A., Zakaria, Z., Shameli, K., Moeini, H., Omar, A.R. "Cytotoxicity and  
5 immunological responses following oral vaccination of nanoencapsulated avian influenza virus  
6 H5 DNA vaccine with green synthesis silver nanoparticles." *Journal of Controlled Release* 161 (2012)  
7 116-123. doi: [10.1016/j.jconrel.2012.04.015](https://doi.org/10.1016/j.jconrel.2012.04.015).
- 8 24. Shabanzadeh, P., Yusof, R., Shameli, K. "Artificial neural network for modeling the size of silver  
9 nanoparticles' prepared in montmorillonite/starch bionanocomposites". *Journal of Industrial and*  
10 *Engineering Chemistry* 24 (2015) 42-50. doi: [10.1016/j.jiec.2014.09.007](https://doi.org/10.1016/j.jiec.2014.09.007).
- 11 25. Mortazavi, K., H. Rajabi, A. Ansari, M. Ghaedi, and K. Dashtian. "Preparation of Silver  
12 Nanoparticle Loaded on Activated Carbon and Its Application for Removal of Malachite Green  
13 from Aqueous Solution." *Synthesis and Reactivity in Inorganic, Metal-Organic, and Nano-Metal*  
14 *Chemistry* (2016): 00-00. doi: [10.1080/15533174.2016.1228670](https://doi.org/10.1080/15533174.2016.1228670).
- 15 26. Manimekalai, T., N. Sivakumar, and S. Periyasamy. "Catalytic Pyrolysis of Plastic Waste into  
16 Activated Carbon and Its Adsorption Studies on Acid Red 114 as Model Organic Pollutant." 2015.