



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Harnessing DNA nanotechnology and chemistry for applications in photonics and electronics

Citation for published version:

Dunn, K & Elfick, APD 2022, 'Harnessing DNA nanotechnology and chemistry for applications in photonics and electronics', *Bioconjugate chemistry*. <https://doi.org/10.1021/acs.bioconjchem.2c00286>

Digital Object Identifier (DOI):

[10.1021/acs.bioconjchem.2c00286](https://doi.org/10.1021/acs.bioconjchem.2c00286)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Peer reviewed version

Published In:

Bioconjugate chemistry

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.



TOPICAL REVIEW: Harnessing DNA nanotechnology and chemistry for applications in photonics and electronics

Katherine E. Dunn* & Alistair Elfick

School of Engineering, Institute for Bioengineering, University of Edinburgh, The King's Buildings, Edinburgh, EH9 3DW, Scotland, UK


*Corresponding author: k.dunn@ed.ac.uk

ORCID IDs:

KED: 0000-0002-5068-4354

AE: 0000-0002-4429-6232

Table of Contents Graphic

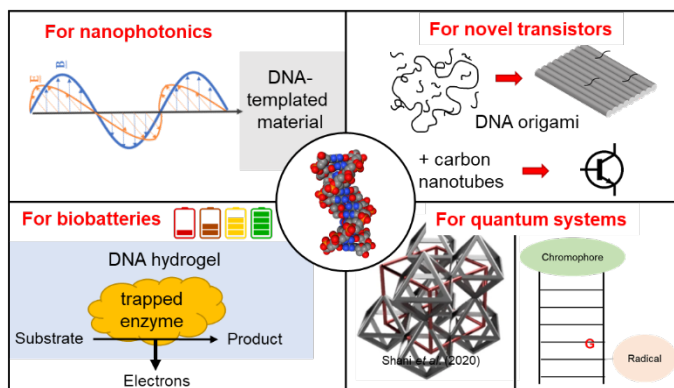

Abstract

Many photonic and electronic devices rely on nanotechnology and nanofabrication, but DNA-based approaches have yet to make a significant commercial impact in these fields even though DNA molecules are now well-established as versatile building blocks for nanostructures. As we describe here, DNA molecules can be chemically modified with a wide variety of functional groups enabling nano-cargoes to be attached at precisely determined locations. DNA nanostructures can also be used as templates for the growth of inorganic structures. Together, these factors enable the use of DNA nanotechnology for the construction of many novel devices and systems. In this topical review, we discuss four case studies of potential applications in photonics and electronics: carbon nanotube transistors, devices for quantum computing, artificial electromagnetic materials and enzymatic fuel cells. We conclude by speculating about the barriers to the exploitation of these technologies in real-world settings.

Introduction

Since the field of DNA nanotechnology was founded by the late Ned Seeman¹, researchers have succeeded in building an enormous variety of self-assembling nanostructures using DNA molecules as building blocks^{2,3}, often using the technique of DNA origami as invented by Paul Rothemund⁴. Through the specificity of base-pairing, DNA nanotechnology offers unsurpassed programmability in achieving exceptionally accurate self-assembly in 3D, and evaluation of patent filings and company creation suggests that the field is now sufficiently mature to support commercialization⁵. Many proposed applications lie in biomedicine⁶ but there are also valuable opportunities in physics and engineering that have so far been under-exploited. Examples include improved manufacture of nanoscale devices for electronics and computing⁷, construction of photonic devices that provide new ways to manipulate light⁸, and the generation of electricity. For these purposes the key advantages of DNA are the ability to chemically modify DNA for tethering to surfaces or cargoes, the possibility of using DNA structures for spatially organizing moieties with nanoscale precision and the potential for using DNA to build nanoscale templates. The benign conditions for assembly (aqueous solution, no extreme chemicals or temperatures) bring ‘green’ credentials as an added bonus. Here, we discuss these attributes and present case studies demonstrating the use of DNA nanotechnology to enable advances in photonics, electronics, computing and electricity generation.

Chemical modifications

DNA synthesis companies offer a rich catalogue of chemical modifications of DNA, both on the backbone and the bases. Chemical modifications suitable for tethering include biotin, thiol, amino, alkyne or azide groups⁹. Such modifications are commonly used to immobilize

DNA constructs, as in the use of thiol-gold bonds to form a surface-bound DNA nanostructure monolayer¹⁰. In a more exotic example, DNA oligonucleotides modified with alkyne (octadiynyl) or azide groups were used, in combination with copper-catalyzed azide-alkyne click chemistry, to selectively coat highly doped silicon-based ring resonators that had been functionalized with the appropriate complementary group¹¹. Chemical modification is also key for attaching functional cargoes to DNA nanostructures, including fluorophores¹², quantum dots¹³, other nanoparticles¹⁴, proteins¹⁵ etc (Fig. 1a).

Precise spatial localization

Many applications of DNA nanotechnology depend on the fact that each constituent oligonucleotide in a DNA nanostructure is unique and may be tagged independently with a specific cargo, enabling the cargoes to be placed at precise positions in the final structure (Fig. 1b). Examples of cargoes include proteins such as enzymes^{16,17}. Recently a number of studies have shown that spatial control over DNA nanostructure cargoes can be used to form the specific patterns of biological signaling molecules that are required to cause cells to undergo apoptosis^{18,19} or induce immune activation²⁰. Such work demonstrates in a biological setting the capability of DNA nanostructures to arrange cargoes precisely, which is also extremely valuable for applications in electronics, nanophotonics and other engineering-based technologies. One such example is the use of a DNA origami breadboard for construction of a nanoparticle heterotrimer, where energy transfer between two gold nanoparticles was mediated by a silver nanoparticle placed in the gap between them²¹. Further examples will be discussed below.

Templating for nanofabrication

Many conventional electronic and photonic technologies rely on nanofabrication. Existing nanofabrication manufacturing approaches can be classed as ‘top-down’ or ‘bottom-up’²². Top-down approaches such as photolithography, electron beam lithography, scanning probe lithography, Molecular Beam Epitaxy, Liquid Phase Epitaxy, Focused Ion Beam lithography and so forth can produce sub-100nm geometries with features smaller than 20nm, however they are fundamentally hamstrung by their inability to deliver such features over centimeter-scale surfaces or out-of-plane, with affordability and speed. In contrast, DNA nanotechnology offers an alternative route for nanofabrication, via a versatile combination of customizable nanoscale shapes and chemical reactions that enable them to act as three-dimensional templates²³ for metallization, mineralization, lithography and casting (Fig. 1c-e). DNA nanostructures can be used for many applications other than the direct assembly of inorganic structures, for example as a 3D mask for reactive ion etching²⁴, a template for assembly of stamps for soft lithography²⁵ or a means to deliver site-specific doping of semiconductor substrates²⁶. Recent studies have also begun to shed more light on the underlying mechanisms of processes that involve depositing material on the DNA nanostructure^{27,28}.

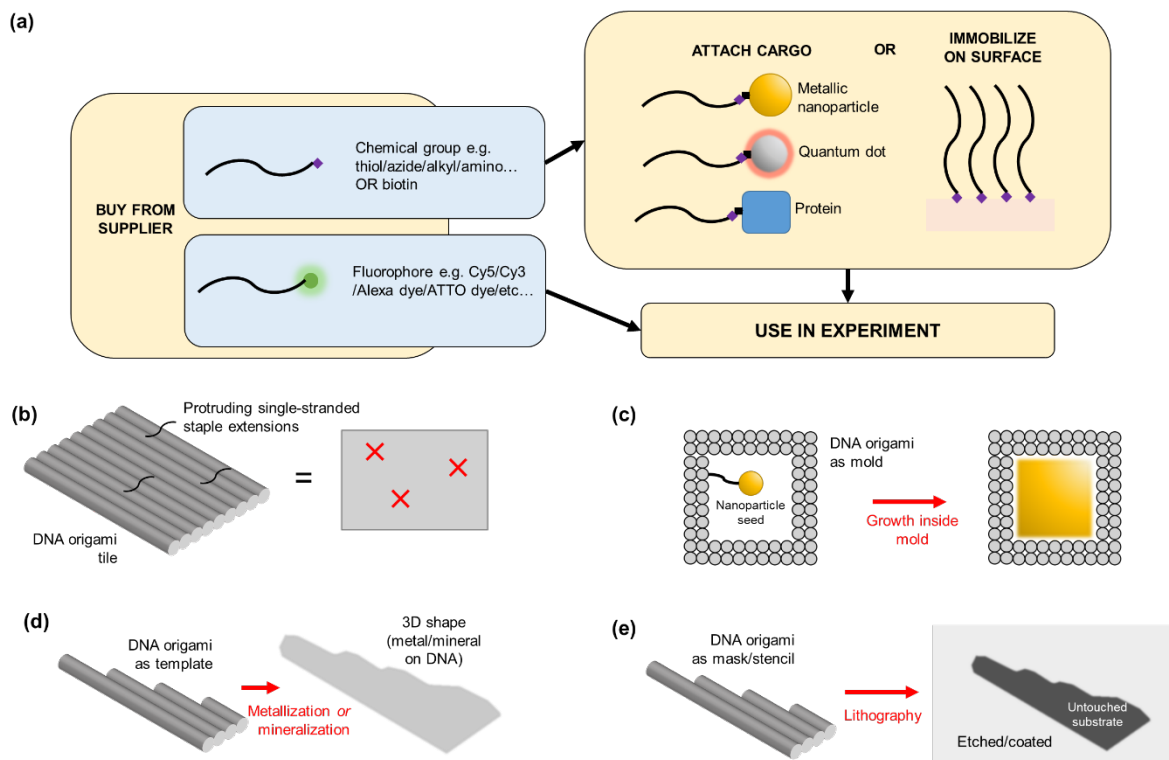


Figure 1 (a) A selection of some of the key chemical modifications and cargoes that can be used with DNA oligonucleotides. Some modifications can be acquired with ease from commercial suppliers whereas more complex conjugations require extended laboratory protocols to be carried out by the end user. The black curved line represents a DNA oligonucleotide, the shapes represent modifications/cargoes as shown by the labels, and the black square represents a linker moiety. (b) The use of DNA origami as a nanoscale breadboard. Individual staples are extended such that single-stranded DNA segments protrudes from the surface of the origami tile. As each staple has a unique sequence, corresponding to a precise location in the structure, the position of the extensions is determined to a high degree of precision and this may be used for spatial organization of functional groups or bioconjugates. (c) Casting: the use of a DNA origami shell as a mold for the growth of metallic structures around a nanoparticle seed. (d) Metallization/mineralization: a DNA nanostructure of the desired shape is coated in a substance such as metal, silica etc, resulting in an object having approximately the shape of the original nanostructure. (e) Lithography: different variations on the process exist. In the approach shown here, the DNA nanostructure is used to construct a mask, protecting an underlying substrate (dark gray) from a coating/etching (pale gray).

Case studies

1. Computing and carbon nanotube transistors

Semiconductor devices and systems underpin modern electronics. The state of the art in the semiconductor industry is reviewed annually by a team sponsored by IEEE (the Institute of Electrical and Electronics Engineers), resulting in an international roadmap. The most recent such roadmap²⁹ shows that the semiconductor industry continues to try to squeeze more and more computing power into the same space without overheating. This involves moving to smaller feature sizes, often exploiting extreme ultraviolet lithography (at great expense and complexity), but also utilizing the third dimension, while changing both hardware and software to reduce power consumption.

Conventional computing is based on bits, which can be in one of two discrete states. Information processing is normally carried out by transistors, which often act like sophisticated electronic switches. Modern electronic systems are usually underpinned by silicon-based technology, but alternative approaches are being investigated, including devices based on carbon nanotubes³⁰. Here, the carbon nanotube (CNT) acts as an electron channel between source and drain electrodes. The current is switched ‘on’ or ‘off’ by means of a gate electrode. A variety of CNT transistors have been tested but fabrication and performance challenges remain. DNA nanotechnology could provide a valuable tool for the construction of devices of this type.

In 2010, a rectangular DNA origami tile was used to guide assembly of CNTs³¹ (Fig. 2ab). Two CNTs were attached to the tile in a cross-like formation and electrodes were fabricated for electronic characterization (Fig. 2c). Of six devices, one exhibited transistor-like

behavior. Subsequently, it was shown that an array of parallel CNTs could be formed with a similar technique³². In this case the origami substrate was a three-dimensional block that contained multiple trenches, and the spacing of the trenches enabled control over the separation of the CNTs (Fig. 2de). It was demonstrated that this strategy could be used to build CNT field-effect transistors³³ (Fig. 2f).

Via templated metallization (see earlier), DNA nanostructures can also enable fabrication of ‘interconnects’, wiring that connects different devices in a circuit. It has been shown that conducting metal-semiconductor junctions can be templated by DNA origami³⁴ and complex branched metal nanostructures can be made using DNA origami molds³⁵. Organic materials can also be used, and individual polymers can be routed in curved patterns on the surface of DNA origami tiles³⁶. Such polymers could potentially be made conducting for use in technologies that would benefit from flexible electronic circuitry, such as wearable health monitoring devices or bendable smartphones.

Future studies could use a combination of the technologies described here to produce integrated circuits with multiple components and complex wiring pathways. For a broader review of DNA-based nanoelectronics, the reader is referred to the review by Hui *et al*⁷.

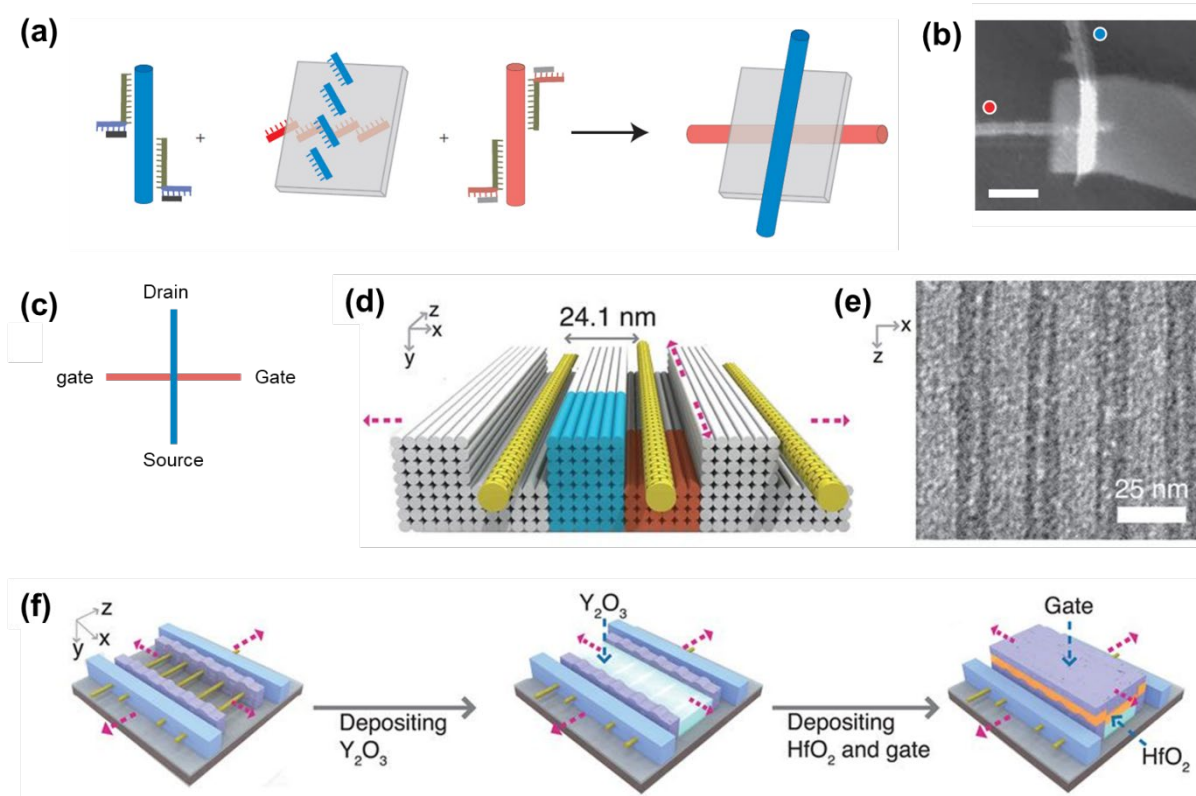


Figure 2. (a) Method for attaching carbon nanotubes site-specifically in a cross shape to a DNA origami substrate. (b) Image acquired using Atomic Force Microscopy, showing correct assembly. The scale bar is 50nm. The two nanotubes (long thin structures) have different types of DNA tags (indicated by red and blue labels) for attachment to a rectangular DNA origami tile, which itself is connected to a DNA ribbon that extends at an angle towards the bottom right of the image. (c) Sketch showing how the nanotubes are connected to electrodes in a transistor-like configuration. (d) Arranging carbon nanotubes in an array with precisely determined inter-tube separation. (e) Transmission Electron Micrograph of the structure from part (d). (f) Carbon nanotube field-effect transistors fabricated using the method of part (d)-(e). In the left-most image, the purple objects are the source and drain electrodes, carbon nanotubes are shown in yellow, and the blue blocks are metal bars. Parts (a) and (b) are Reprinted from Ref. ³¹ with permission from Springer Nature, Nature Nanotechnology, Copyright 2009. Part (d) and (e) are from Ref. ³², reprinted with permission from AAAS. Part (f) is from Ref. ³³, reprinted with permission from AAAS.

2. *Quantum computing*

One trend identified in the International Roadmap for Devices and Systems is the development of quantum computing²⁹, which is based on qubits³⁷. Unlike the ‘bits’ of conventional computers, each qubit can exist in a superposition of two states at the same time, enabling quantum computers to process information in a radically different way, sometimes much faster than a classical computer.

In order for a quantum computer to be realized, it is necessary to build structures that can support qubits, keep them stable, and manipulate them. Qubits can be realized using photons, trapped ions/atoms, or electrons. It has been suggested that it would be advantageous to develop quantum computing systems based on silicon hardware³⁸, to help with interfacing quantum computers and their classical counterparts. There are many challenges for the implementation of silicon-based quantum computers, some of which relate to the fabrication of the devices. It is conceivable that DNA nanotechnology could play a role here, providing a way to make nanoscale structures that could not be synthesized using standard top-down methods.

Some quantum information processing systems make use of Josephson junctions (Fig. 2a), consisting of two regions of superconducting material separated by a small insulating region across which electrons can tunnel. A Josephson junction is well-suited to the creation of qubits and a variety of circuit designs can be used³⁹. Interestingly, DNA nanostructures can be used to assemble three-dimensional arrays of Josephson junctions⁴⁰ (Fig. 2b). The process began with the assembly of octahedra, in which each edge consisted of a six helix DNA

origami bundle. The octahedra were assembled into a lattice before being coated with silica and niobium. In the resultant structure, superconductivity began at 3.8K. Further characterization suggested that the lattice comprised a three-dimensional array of Josephson junctions (Fig. 2c), such a structure being unattainable with conventional methods. This indicates how DNA nanotechnology could in future potentially help to address challenges involved in fabrication of quantum computing hardware, overcoming limitations of conventional nanofabrication methods. However, a great deal of work remains. Not only will it be necessary to demonstrate that DNA-templated structures can support stable qubits, but massively scaled-up production will be required.

Qubits can also be realized using organic chromophores and acceptor molecules. When the chromophore is photoexcited and transfers charge to the acceptor, this sometimes results in the creation of a 'spin qubit pair'. The chromophore and acceptor can be held in position relative to each other using a DNA scaffold, and the addition of a covalently bound radical could enable development of a three-spin system⁴¹ (Fig. 3c) . It has been noted that the use of chemistry and molecular engineering for quantum information systems is potentially a very powerful approach⁴². Considering this and the other possibilities mentioned above, there already appears to be reason to believe that DNA nanotechnology methods could have an impact in the area of quantum computing, despite the fact the latter field is still in its infancy. It may be helpful to combine DNA-scaffolded quantum information systems with DNA-templated nanophotonic structures (next section).

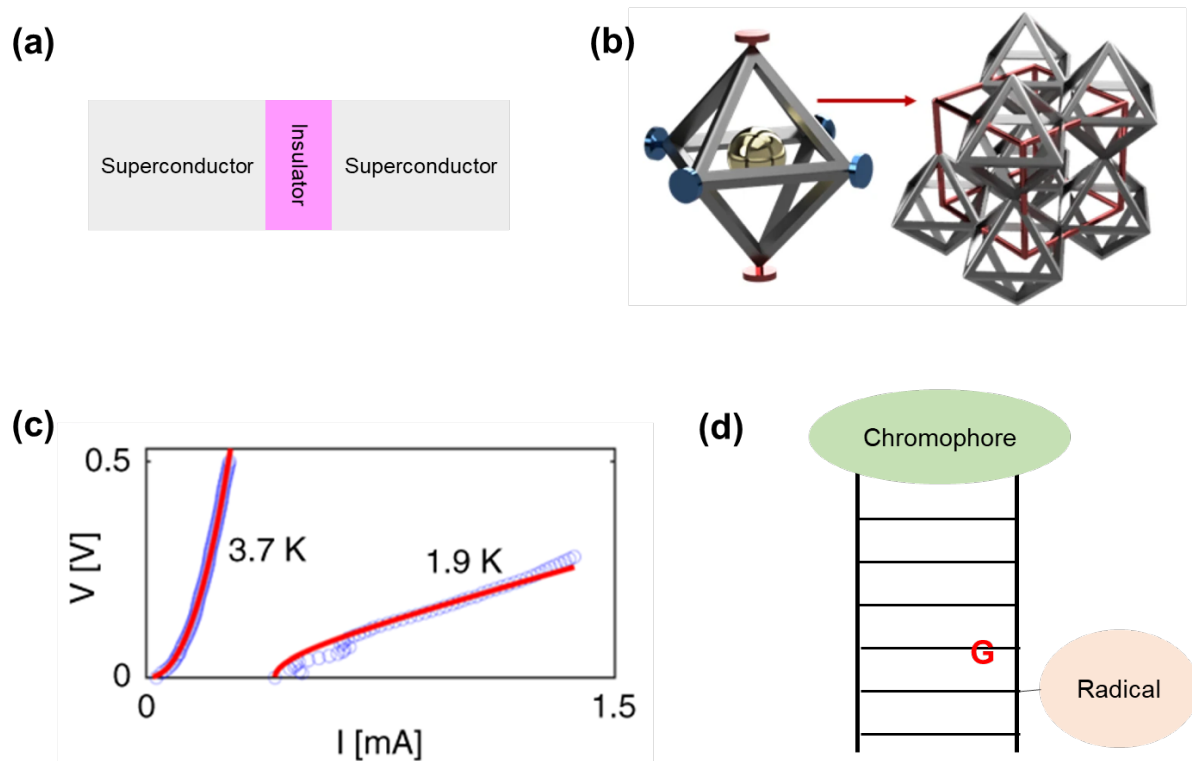


Figure 3: (a) Schematic illustration of a Josephson junction, consisting of a thin layer of insulating material sandwiched between two pieces of superconductor. (b) The assembly of DNA octahedra into a superlattice that was then coated with silica and niobium. There is a nanoparticle inside each octahedron. (c) The current-voltage characteristics of the resultant superlattice at temperatures of 3.7K (just below the superconducting transition temperature) and 1.9K. The data for 1.9K has been fitted with the I-V characteristic of a Josephson junction. (b) and (c) are reproduced from Ref. ⁴⁰ under a CC-BY license. (d) Schematic diagram of the DNA structures described in Ref. ⁴¹, where the chromophore (hole donor) covalently links the two DNA strands. As indicated, only one guanine residue is present and a radical is attached to the DNA. The resultant structure can be used to generate a three-spin system.

3. *Nanophotonics*

DNA nanotechnology has a plethora of applications in photonics^{8,43,44}, relying on nanoscale patterning and precise spatial arrangement of cargoes. Here we focus on selected examples.

The notion of artificial electromagnetic materials (AEMs) was conceived over a century ago⁴⁵; fabricating arrays of conducting objects within a nonconducting matrix can result in a composite material that achieves bespoke electromagnetic properties. The vital prerequisite for the macroscopic composite is that it possesses a periodic structure with active features of dimensions and lattice spacing smaller than the length of the electromagnetic wave (Fig. 4a). Indeed, if size of the active features is sufficiently small then these may act as an effective medium, i.e. the electromagnetic wave will experience the material as a monolithic entity. Examples of AEMs (also known as optical metamaterials) include among other examples materials with negative refractive index and photonic crystals⁴⁶. The 1940-70s saw the accelerated development of AEMs in the microwave region (wavelengths of 30 – 0.1 cm) but until recently AEMs in the optical regime (400-700 nm), also known as optical metamaterials, were unmanufacturable. However, such materials are of considerable interest as they open the door to new ways of manipulating light, providing functions such as enhanced imaging capability or invisibility cloaks.

To produce a macroscale AEM will require 100s of billions of active features, manufactured and assembled with exceptionally high fidelity and precision. The utilization of DNA nanotechnology for the fabrication of nanophotonic devices offers a number of compelling advantages, which have been demonstrated over the last decade in a number of studies, two of which amply illustrate its power; nanocavities and chiral structures.

Nanocavities are used to confine light using resonating modes at sub-wavelength scales. These have seen much use in the quantum optical studies, in particular the creation of hybrid systems with nanocavities and single emitters (fluorophores or quantum dots), as shown for example in Ref. ⁴⁷. The fabrication of such systems demands the deterministic placement of the emitters within the nanocavity, a task requiring accuracy orders of magnitude smaller than the wavelength⁴⁸. Gopinath *et al.*⁴⁹ pioneered the use of DNA structures to control the position of a dye molecule within a photonic crystal cavity (PCC); by targeting the dye to different locations on a DNA structure located within the PCC, they demonstrated tunable emission corresponding to the electric field intensity within the PCC. The same group has gone on to develop control over the relative angle between the dipole of fluorescent dyes and the polarization of the incident light, thereby governing device brightness⁵⁰.

DNA nanotechnology has also opened up avenues in study of chiral structures. In its optical sense, chirality allows a structure to differently absorb left- and right-handed circularly polarized light. Once more DNA nanotechnology's ability to self-assemble these structures has propelled the emergence of a significant body of study using such systems⁵¹, catalyzed by the marker laid down by Kuzyk *et al.*⁵²(Fig. 4b). This study used a DNA nanorod as a scaffold to attach a helical string of gold nanospheres with a designed chiroptical response (Fig. 3b). Left- and right-handed arrangements of the nanosphere were both shown to generate the characteristic bisignate circular dichroism spectra, centered at the resonant frequency of the individual nanosphere.

Overall, DNA nanotechnology has become a “go-to” solution for basic research in nanophotonics but as yet there are very few commercialization successes to celebrate. Further technical development is required to de-risk the transition away from conventional materials, particularly in the context of scaling up to larger areas and mass production. Detailed economic assessment and life cycle analysis would be of particular benefit.

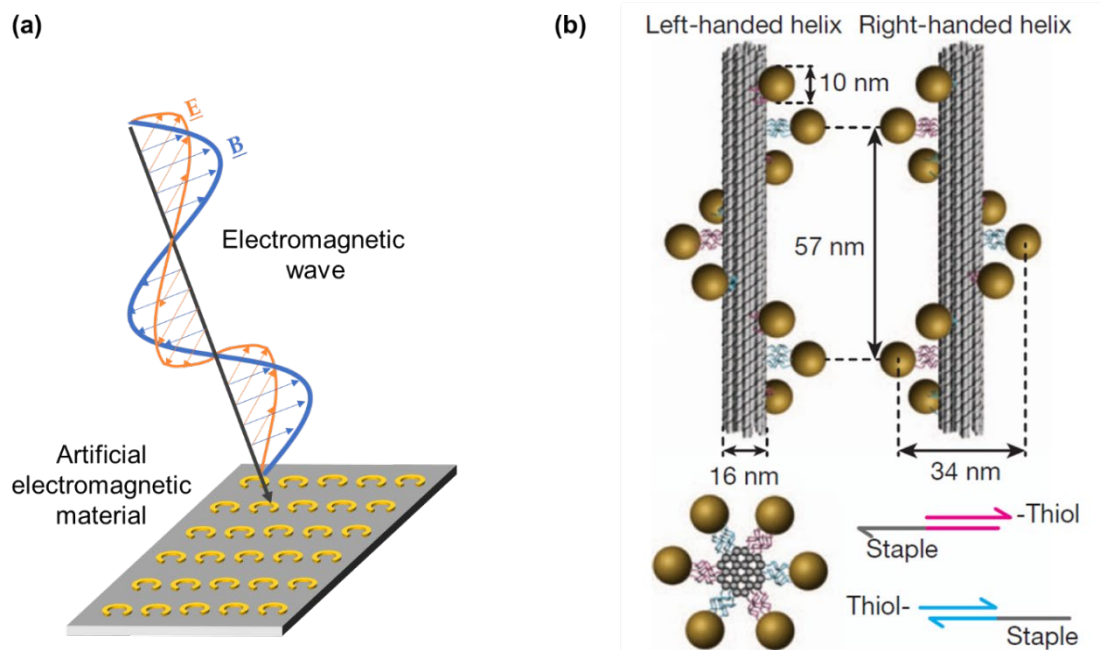


Figure 4. (a) Depiction of an artificial electromagnetic material (otherwise known as an optical metamaterial).

The periodicity and feature size are significantly smaller than the wavelength of the electromagnetic wave, which interacts with the metamaterial as if it is an effective medium with engineered electromagnetic properties.

(b) Gold nanoparticles arranged on a DNA origami bundle via thiol-modified linkers. Reprinted from Ref. ⁵² with permission from Springer Nature, Nature, Copyright 2012. The two designs have opposite chirality and this affects the way in which the structures interact with circularly polarized light, such that the circular dichroism spectrum of one exhibits a flipped sign relative to that of the other.

4. *Biobatteries*

Climate change and increasing use of electrical devices are driving research on new technologies for the energy sector. Bioengineering has the potential to make a valuable

contribution to these efforts, and the term ‘electrosynbionics’ has been coined to describe the ‘creation of engineered devices that use components derived from or inspired by biology’ for electricity generation, use and storage⁵³. This includes biophotovoltaics and biobatteries, among other technologies. Enzymatic fuel cells are a type of biological battery in which reactions catalyzed by enzymes generate a flow of electrons (Fig. 5a). In one particularly interesting example, 13 different enzymes were used and a maximum current of 6 mA cm^{-2} was achieved⁵⁴. It was suggested that this device could have an energy storage density (in terms of energy stored per kg) an order of magnitude higher than lithium-ion batteries.

DNA nanotechnology has a potential role to play in the development of the next generation of enzymatic fuel cells. As will be described shortly, a DNA-based hydrogel can be used as a medium for an enzymatic fuel cell, where a hydrogel consists of a network of linked polymers that contains a significant amount of absorbed water. Various DNA hydrogels have been reported, including one that was described as a ‘mechanical metamaterial’⁵⁵. Another technique for hydrogel formation involves structures called ‘Y-DNA’ and ‘linkers’, and this was the approach used for the DNA hydrogel biobattery⁵⁶(Fig. 5b). The Y-DNA was a three-way junction made from double-stranded DNA segments, with single-stranded sticky ends at all three termini. The linkers were duplexes with single-stranded overhangs at both ends. The enzyme glucose oxidase and mediator Fc-COOH were added to the mixture of DNA components. The resulting gel was applied to a stainless-steel mesh anode and used with an air-breathing cathode, giving rise to an enzymatic fuel cell. Upon fuel addition, the maximum power density was approximately $300 \mu\text{W cm}^{-2}$, over six and a half times the value observed in the absence of enzyme. It was later demonstrated that redox mediators could bind to the DNA, potentially provide a way to enhance electron transfer to the electrode⁵⁷. Based on

recent news stories from the researchers and funders, further work appears to be in progress⁵⁸⁻

60.

DNA hydrogels share with origami structures the potential for straightforward assembly under benign conditions, and in both cases the product poses minimal hazard, unlike more conventional devices that rely on more dangerous materials. For future development of DNA hydrogel biobatteries, it will be important to maximize energy and power density by perfecting the electron transfer pathway and choice of enzymes/substrates. The longevity and stability of the battery will need to be optimized, and the end-of-life disposal route must be confirmed.

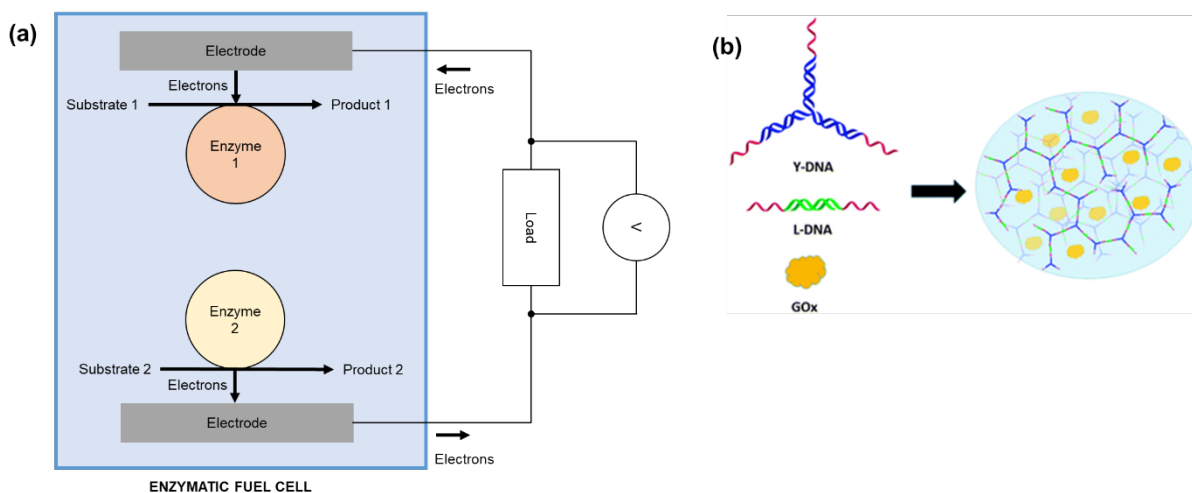


Figure 5. (a) Schematic illustration of the mechanism of an enzymatic fuel cell. The enzymes may be immobilized on the electrodes (perhaps covalently attached or trapped with polymers) or floating freely in solution. Additional redox-active compounds (not shown) may be added as mediators to enable electron transfer to the electrodes. In some implementations a semi-permeable membrane (not shown) may be present in the cell to separate the two electrodes. The reaction catalyzed by the enzymes pushes/pulls electrons into/out of the electrodes, and this drives current flow through an external resistive load, across which a voltage may be measured as shown. **(b)** Encapsulation of enzyme GOx (Glucose Oxidase, yellow splodge) in a DNA hydrogel made from L-DNA linkers and Y-DNA three-way junctions. The DNA linkers and Y-shapes shown on the left assemble into the hydrogel shown on the right, in which GOx molecules are trapped. Reproduced from Ref. ⁵⁶ with permission from the Royal Society of Chemistry permission conveyed through Copyright Clearance

Center, Inc.

Discussion & conclusion

Here, we have discussed examples of the use of DNA nanotechnology for applications in photonics and electronics. In addition to the case studies presented, it is worth noting that DNA nanostructures can be used in combination with other lithography techniques⁶¹ such as nanosphere lithography^{62,63} or top-down methods^{24,64-66}. In all the examples we considered, DNA nanotechnology offers great advantages in spatial precision and versatility, while enabling assembly under benign conditions. Despite this, these approaches have not yet been fully exploited and further development is required for the full potential to be realized, particularly in connection with scaling up to commercial production levels. One aspect of this is the preparation of the DNA itself.

For many applications, chemical synthesis of oligonucleotides would be prohibitively expensive. DNA synthesis costs continue to fall, but alternative approaches are also being explored, for example using ‘biotechnological mass production’⁶⁷. Widespread deployment of new DNA synthesis methods could make DNA nanotechnology solutions more cost-effective, as has been demonstrated in the biomedical arena by modelling the economics of DNA nanostructure-based drug delivery⁶⁸.

A second aspect of scaling up is the fidelity of assembly of nanostructures into bigger structures or arrays with a large surface area, as recently reviewed in Ref. ⁶⁹. Several research groups have made impressive advances in this area, including surface-assisted assembly⁷⁰ of tessellating origami triangles over 18.75 cm² and the realization of ‘supershapes’ using criss-cross assembly of origami ‘slats’⁷¹.

In general, translation of DNA nanotechnology research would be facilitated by a more problem-driven approach, where the design of devices is shaped by a detailed understanding of the needs of a particular target market and a focused device specification of. Coupled with effective means to reduce cost and scale up, this attitude has the potential to enable DNA nanotechnology to underpin a new generation of exciting products for photonic and electronic applications.

Conflict of interest: the authors declare no conflict of interest.

Acknowledgements

There is no applicable funding to acknowledge. (The authors are in receipt of funding from various sources – for which they are very grateful – but those funds were not used to support the preparation of the present manuscript.) For the purpose of open access, the authors have applied a CC BY public copyright license to any Author Accepted Manuscript version arising from this submission.

References

1. Chen, J. and Seeman, N.C. (1991) Synthesis from DNA of a molecule with the connectivity of a cube. *Nature* **350**: 631-633. DOI: 10.1038/350631a0
2. Seeman, N.C. and Sleiman, H.F (2018) DNA nanotechnology. *Nat. Rev. Mater.* **3**: 17068 DOI: 10.1038/natrevmats.2017.68
3. Douglas, S.M., Dietz, H., Liedl, T., Högberg, B., Graf, F. and Shih, W.M. (2009) Self-assembly of DNA into nanoscale three-dimensional shapes. *Nature* **459**: 414-418. DOI: 10.1038/nature08016
4. Rothemund, P.W.K. (2006) Folding DNA to create nanoscale shapes and patterns. *Nature* **440**: 297-302. DOI: 10.1038/nature04586
5. Dunn, K.E. (2020) The Business of DNA Nanotechnology: Commercialization of Origami and Other Technologies. *Molecules*. **25**: 377. DOI: 10.3390/molecules25020377

6. Keller, A. and Linko, V. (2020) Challenges and Perspectives of DNA Nanostructures in Biomedicine. *Angew. Chem., Int. Ed.* **59**: 15818-15833. DOI: 10.1002/anie.201916390
7. Hui, L., Bai, R., Liu, H. (2022) DNA-based nanofabrication for nanoelectronics. *Adv. Funct. Mater.* **32**: 2112331. DOI:10.1002/adfm.202112331
8. Kuzyk, A., Jungmann, R., Acuna, G.P. and Liu, N. (2018) DNA origami route for nanophotonics. *ACS Photonics.* **5**: 1151-1163
9. Integrated DNA Technologies. Oligo modifications.
<https://eu.idtdna.com/pages/products/custom-dna-rna/oligo-modifications>
10. Dunn, K.E., Trefzer, M.A., Johnson, S. and Tyrrell, A.M. (2016) Investigating the dynamics of surface-immobilised DNA nanomachines. *Sci. Rep.* **6**:29581. DOI: 10.1038/srep29581
11. Juan-Colás, J., Parkin, A., Dunn, K.E., Scullion, M.G., Krauss, T.F. and Johnson, S.D. (2016) The electrophotonic silicon biosensor. *Nat. Commun.* **7**:12769. DOI: 10.1038/ncomms12769
12. Scheckenbach, M., Bauer, J., Zähringer, J., Selback, F. and Tinnefeld, P. (2020) DNA origami nanorulers and emerging reference structures. *APL Mater.* **8**:110902. DOI: 10.1063/5.0022885
13. Bui, H., Onodera, C., Kidwell, C., Tan, Y., Graugnard, E., Kuang, W., Lee, J., Knowlton, W.B., Yurke, B. and Hughes, W.L. (2010) Programmable Periodicity of Quantum Dot Arrays with DNA Origami Nanotubes. *Nano Lett.* **10**: 3367-3372. DOI: 10.1021/nl101079u
14. Gür, F.N., Schwarz, F.W., Ye, J., Diez, S. and Schmidt, T.L. (2016) Toward Self-Assembled Plasmonic Devices: High-Yield Arrangement of Gold Nanoparticles on DNA Origami Templates. *ACS Nano.* **10**:5374-5382. DOI: 10.1021/acsnano.6b01537

15. Stephanopoulos, N. (2020) Hybrid nanostructures from the self-assembly of proteins and DNA. *Chem.* **6**: 364-405. DOI: 10.1016/j.chempr.2020.01.012
16. Fu, Y., Zeng, D., Chao, J., Jin, Y., Zhang, Z., Liu, H., Li, D., Ma, H., Huang, Q., Gothelf, K.V. *et al.* (2012) Single-Step Rapid Assembly of DNA Origami Nanostructures for Addressable Nanoscale Bioreactors. *J. Am. Chem. Soc.* **135**: 696-702 DOI: 10.1021/ja3076692
17. Fu, J., Liu, M., Liu, Y., Woodbury, N.W., and Yan, H. (2012) Interenzyme Substrate Diffusion for an Enzyme Cascade Organized on Spatially Addressable DNA Nanostructures. *J. Am. Chem. Soc.* **134**:5516–5519. DOI: 10.1021/ja300897h
18. Berger, R.M.L., Weck, J.M., Kempe, S.M., Hill, O., Liedl, T., Rädler, J.O., Monzel, C. and Heuer-Jungemann, A. (2021) Nanoscale FasL Organization on DNA Origami to Decipher Apoptosis Signal Activation in Cells. *Small.* **17**: 2101678. DOI: 10.1002/smll.202101678
19. Wang, Y., Baars, I., Fördös, F., and Högberg, B. (2021) Clustering of Death Receptor for Apoptosis Using Nanoscale Patterns of Peptides. *ACS Nano.* **15**: 9614-9626 DOI: 10.1021/acsnano.0c10104
20. Comberlato, A., Koga, M. M., Nüssing, S., Parish, I.A. and Bastings, M.M.C. (2022) Spatially Controlled Activation of Toll-like Receptor 9 with DNA-Based Nanomaterials. *Nano Lett.* **22**:2506-2513 DOI:10.1021/acs.nanolett.2c00275
21. Roller, E-M., Besteiro, L.V., Pupp, C., Khorashad, L.K., Govorov, A.O. and Liedl, T. (2017) Hotspot-mediated non-dissipative and ultrafast plasmon passage. *Nat. Phys.* **13**: 761-765. DOI: 10.1038/nphys4120

22. Biswas, A., Bayer, I.S., Biris, A.S., Wang, T., Dervishi, E., and Faupel, F. (2012) Advances in top–down and bottom–up surface nanofabrication: Techniques, applications and future prospects. *Adv. Colloid Interface Sci.* **170**: 2-27. DOI: 10.1016/j.cis.2011.11.001
23. Heuer-Jungemann, A. and Linko, V. (2021) Engineering inorganic materials with DNA nanostructures. *ACS Cent. Sci.* **7**:1969-1979 DOI: 10.1021/acscentsci.1c01272
24. Shen, J. Sun, W., Liu, D., Schaus, T & Yin, P. (2021) Three-dimensional nanolithography guided by DNA modular epitaxy. *Nat. Mater.* **20**: 683-690. DOI: 10.1038/s41563-021-00930-7
25. Tian, C., Kim, H., Sun, W., Kim, Y., Yin, P. & Liu, H. (2017) DNA Nanostructures-Mediated Molecular Imprinting Lithography. *ACS Nano.* **11**: 227-238. DOI: 10.1021/acsnano.6b04777
26. Bai, R., Yanhao D., Xu, A., Yang, H., Erickson, J.R., Hui, L., Chen, J., Xiong, F., Liu, H. (2020) DNA-based strategies for site-specific doping. *Adv. Funct. Mater.* **31**: 2005940. DOI: 10.1002/adfm.202005940
27. Ober, M.F., Baptist, A., Wassermann, L., Heuer-Jungemann, A. and Nickel, B. (2022) In situ small-angle X-ray scattering reveals strong condensation of DNA origami during silicification. *ArXiv*: 2204.07385 DOI: 10.48550/arXiv.2204.07385
28. Jia, S., Wang, J., Xie, M., Sun, J., Liu, H., Zhang, Y., Chao, J., Li, J., Wang, L., Lin, J. *et al.* (2019) Programming DNA origami patterning with non-canonical DNA-based metallization reactions. *Nat. Commun.* **10**: 5597 DOI: 10.1038/s41467-019-13507-5
29. International Roadmap Committee (2021) The International Roadmap for Devices and Systems 2021. *IEEE*. Available from: <https://irds.ieee.org/>

30. Peng, L.M., Zhang, Z. and Qiu, C. (2019) Carbon nanotube digital electronics. *Nat. Electron.* **2**: 499-505 DOI: 10.1038/s41928-019-0330-2
31. Maune, H. T., Han, S., Barish, R.D., Bockrath, M., Goddard III, W.A., Rothmund, P.W.K. and Winfree, E. (2010) Self-assembly of carbon nanotubes into two-dimensional geometries using DNA origami templates. *Nat. Nanotechnol.* **5**: 61-66 DOI: 10.1038/nnano.2009.311
32. Sun, W., Shen, J., Zhao, Z., Arellano, N., Rettner, C., Tang, J., Cao, T., Zhou, Z., Ta, T., Streit, J.K. *et al.* (2020) . Precise pitch-scaling of carbon nanotube arrays within three-dimensional DNA nanotrenches. *Science* **368**:874-877 DOI: 10.1126/science.aaz7440
33. Zhao, M., Chen, Y., Wang, K., Zhang, Z., Streit, J.K., Fagan, J.A., Tang, J., Zheng, M., Yang, C., Zhu., Z. *et al.* (2020) DNA-directed nanofabrication of high-performance carbon nanotube field-effect transistors. *Science* **368**: 878-881. DOI: 10.1126/science.aaz7435
34. Aryal, B.R., Ranasinghe, D.R., Westover, T.R., Calvopiña, D.G., Davis, R.C., Harb, J.N. and Woolley, A.T. (2020) DNA origami mediated electrically connected metal-semiconductor junctions. *Nano Res.* **13**: 1419-1426 DOI: 10.1007/s12274-020-2672-5
35. Ye, J., Aftenieva, O., Bayrak, T., Jain A., König, T.A.F., Erbe, A. and Seidel, R. (2021) Complex metal nanostructures with programmable shapes from simple DNA building blocks. *Adv. Funct. Mater.* **33**: 2100381. DOI:10.1002/adma.202100381
36. Knudsen, J.B., Liu, L., Bank Kodal, A.L., Madsen, M., Li, Q., Song, J., Woehrstein, J.B., Wickham, S.F.J., Strauss, M.T., Schueder, F., Vinther J. *et al.* (2015). Routing of individual polymers in designed patterns. *Nat. Nanotechnol.* **10**: 892-898 DOI: 10.1038/nnano.2015.190
37. Knill, E. (2010) Quantum computing. *Nature* **463**, 441-443 DOI: 10.1038/463441a

38. Gonzalez-Zalba, M. F., de Franceschi, S., Charbon, E., Meunier, T., Vinet, M. and Dzurak, A. S. (2021) Scaling silicon-based quantum computing using CMOS technology. *Nat. Electron.* **4**: 872-884 DOI: 10.1038/s41928-021-00681-y
39. Kockum, A.F. and Nori, F. (2019) Quantum Bits with Josephson Junctions, in 'Fundamentals and Frontiers of the Josephson Effect'. p703. *Springer Series in Materials Science*. Web link: https://link.springer.com/chapter/10.1007/978-3-030-20726-7_17
40. Shani, L., Michelson, A.N., Minevich, B., Flegler, Y., Stern, M., Shaulov, A., Yeshurun, Y. and Gang, O. (2020) DNA-assembled superconducting 3D nanoscale architectures. *Nat. Commun.* **11**: 5697 DOI: 10.1038/s41467-020-19439-9
41. Lorenzo, E.R., Olshansky, J.H., Abia, D.S.D., Krzyaniak, M.D., Young, R.M. and Wasielewski, M.R. (2021) Interaction of Photogenerated Spin Qubit Pairs with a Third Electron Spin in DNA Hairpins. *J. Am. Chem. Soc.* **143**: 4625-4632 DOI: 10.1021/jacs.0c12645
42. Wasielewski, M.R., Forbes, M.D.E., Frank, N.L., Kowalski, K., Scholes, G.D., Yuen-Zhou, J., Baldo, M.A., Freedman, D.E., Goldsmith, R.H., Goodson III, T., *et al.* (2020) Exploiting chemistry and molecular systems for quantum information science. *Nat. Rev. Chem* **4**: 490-504. DOI: 10.1038/s41570-020-0200-5
43. Shen, B., Kostianen, M.A. and Linko, V. (2018) DNA origami nanophotonics and plasmonics at interfaces. *Langmuir.* **34**: 14911-14920. DOI: 10.1021/acs.langmuir.8b01843
44. Pilo-Pais, M, Acuna, G.P., Tinnefeld, P. and Liedl, T. (2017) Sculpting light by arranging optical components with DNA nanostructures. *MRS Bulletin* **42**: 936-942. DOI: 10.1557/mrs.2017.278
- 45Lindell, I.V., Sihvola A.H. and Kurkijärvi, J. (1992) Karl F. Lindman: The Last Hertzian,

and a Harbinger of Electromagnetic Chirality. *IEEE Antennas and Propagation Magazine*.

34: 24-30 DOI: 10.1109/74.153530

46. Smith, D.R., Pendry, J.B. and Wiltshire, M.C.K. (2004) Metamaterials and Negative Refractive Index. *Science* **305**: 788-792. DOI: 10.1126/science.1096796

47. Gupta, S.N., Bitton, O., Neuman, T., Esteban, R., Chuntanov, L., Aizpurua, J. and Haran G. (2021) Complex plasmon-exciton dynamics revealed through quantum dot light emission in a nanocavity. *Nat. Commun.* **12**: 1310. DOI: 10.1038/s41467-021-21539-z

48. Hwang, M.S., Choi, J.H., Jeong, K.Y., Kim, K.H., Kim, H.R., So, J.P., Lee, H.C., Kim, J., Kwon, S.H. and Park, H.G. (2021) Recent advances in nanocavities and their applications. *Chem. Commun.* **57**: 4875–4885 DOI: 10.1039/D1CC01084K

49. Gopinath, A., Miyazono, E., Faraon, A. and Rothmund, P. W.K. (2016) Engineering and mapping nanocavity emission via precision placement of DNA origami. *Nature* **535**: 401–405 DOI: 10.1038/nature18287

50. Gopinath, A., Thachuk, C., Mitskovets, A., Atwater, H. A., Kirkpatrick, D., and Rothmund, P.W.K. (2021) Absolute and arbitrary orientation of single-molecule shapes. *Science* **371**: eabd6179. DOI: 10.1126/science.abd6179

51. Urban, M. J., Shen, C., Kong, X.T., Zhu, C., Govorov, A. O., Wang, Q., Hentschel, M. and Liu, N. (2019) Chiral plasmonic nanostructures enabled by bottom-up approaches. *Annu. Rev. Phys. Chem.* **70**, 275–299 DOI: 10.1146/annurev-physchem-050317-021332

52. Kuzyk, A., Schreiber, R., Fan, Z., Pardatscher, G., Roller, E. M., Högele, A., Simmel, F. C., Govorov, A. O. and Liedl, T. (2012) DNA-based self-assembly of chiral plasmonic nanostructures with tailored optical response. *Nature* **483**, 311–314. DOI: 10.1038/nature10889

53. Dunn, K.E. (2020) The emerging science of electrosynbionics. *Bioinspiration Biomimetics*. **15**: 033001 DOI: 10.1088/1748-3190/ab654f
54. Zhu, Z., Tam, T.K., Sun, F., You, C. and Zhang, Y.-H.P. (2014) A high-energy-density sugar biobattery based on a synthetic enzymatic pathway. *Nat. Commun.* **5**: 3026 DOI: 10.1038/ncomms4026
55. Lee, J.B., Peng, S., Yang, D., Roh, Y.H., Funabashi, H., Park N., Rice, E.J., Chen, L., Long, R., Wu M. *et al.* . (2012) A mechanical metamaterial made from a DNA hydrogel. *Nat Nanotechnol* **7**:816-820 DOI:10.1038/nnano.2012.211
56. Van Nguyen, K. and Minter, S. (2015) Investigating DNA hydrogels as a new biomaterial for enzyme immobilization in biobatteries. *ChemComm* **51**: 13071-13073 DOI: 10.1039/C5CC04810A
57. Van Nguyen, K., Holade Y. and Minter S. (2016) DNA Redox Hydrogels: Improving Mediated Enzymatic Bioelectrocatalysis *ACS Catal.* **6**: 2603-2607 DOI: 10.1021/acscatal.5b02699
58. <https://www.touchlight.com/news/touchlight-to-develop-biobatteries-with-potential-to-address-limitations-of-portable-power-supply/>
59. <https://www.gov.uk/government/news/dstl-scientists-develop-pioneering-bio-batteries>
60. <https://eandt.theiet.org/content/articles/2022/03/dna-based-bio-batteries-make-powerful-progress-in-lab-tests/>

61. Martynenko, I.V., Ruider, V., Dass, M., Liedl, T. and Nickels, P.C. (2021) DNA origami meets bottom-up nanopatterning. *ACS Nano*. **15**: 10769-10774. DOI: 10.1021/acsnano.1c04297
62. Haynes C.L. and Van Duyne R.P. (2001) Nanosphere Lithography: A Versatile Nanofabrication Tool for Studies of Size-Dependent Nanoparticle Optics. *J. Phys. Chem. B* **105**:5599-5611. DOI:10.1021/jp010657m
63. Shetty R.M., Brady S.R., Rothmund P.W.K., Hariadi R.F. and Gopinath A. (2021) Bench-Top Fabrication of Single-Molecule Nanoarrays by DNA Origami Placement. *ACS Nano* **15**:11441-11450 DOI: 10.1021/acsnano.1c01150
64. Jin, Z., Sun, W., Ke, Y., Shih, C., Paulus, G.L.C., Wang, Q.H., Mu, B., Yin, P. and Strano, M.S. (2013) Metallized DNA nanolithography for encoding and transferring spatial information for graphene patterning. *Nat. Commun.* **4**: 1663 DOI: 10.1038/ncomms2690
65. Piskunen, P., Shen, B., Keller, A., Toppari, J.J., Kostianen, M.A. and Linko, V. (2020) Biotemplated Lithography of Inorganic Nanostructures (BLIN) for Versatile Patterning of Functional Materials. *ACS Appl. Nano Mater.* **4**: 529-538 DOI: 10.1021/acsanm.0c02849
66. Kershner, R.J., Bozano, L.D., Micheel, C.M., Hung, A.M., Fornof, A.R., Cha, J.N., Rettner, C.T., Bersani, M., Frommer, J., Rothmund, P.W.K. *et al.* (2009) Placement and orientation of individual DNA shapes on lithographically patterned surface. *Nat. Nanotechnol.* **4**:557-561. DOI:10.1038/nnano.2009.220
67. Praetorius, F., Kick, B., Behler, K.L., Honemann, M.N., Weuster-Botz, D. and Dietz, H. (2017) Biotechnological mass production of DNA origami. *Nature* **522**: 84-87 DOI: 10.1038/nature24650

68. Coleridge, E. and Dunn, K.E. (2020) Assessing the cost-effectiveness of DNA origami nanostructures for targeted delivery of anti-cancer drugs to tumours. *Biomedical Physics & Engineering Express*. **6**: 065030 DOI: 10.1088/2057-1976/abbe73
69. Chen, Y. Sun, W., Yang, C. and Zhu, Z. (2020) Scaling up DNA self-assembly. *ACS Appl. Bio. Mater.* **3**: 2805-2815. DOI: 10.1021/acsabm.0c00035
70. Xin, Y., Shen, B., Kostiaianen, M.A., Grundmeier, G., Castro, M., Linko, V. and Keller, A. (2021) Scaling up DNA origami lattice assembly. *Chem. – Eur. J.* **27**: 8564-8571. DOI: 10.1002/chem.202100784
71. Wintersinger, C.M., Minev, D., Ershov, A., Sasaki, H.M., Gowri, G., Berungut, J.F., Corea-Dilbert, F.E., Yin, P. and Shih, W.M. (2022) Multi-micron crisscross structures from combinatorially assembled DNA-origami slats. *Biorxiv*. DOI: 10.1101/2022.01.06.47524 3