

# Ply-stacking effects on mechanical properties of Kevlar-29/banana woven mats reinforced epoxy hybrid composites

Volume 52: 1–31





© The Author(s) 2022

Article reuse guidelines:

[sagepub.com/journals-permissions](https://sagepub.com/journals-permissions)

DOI: 10.1177/15280837221128024

[journals.sagepub.com/home/jit](https://journals.sagepub.com/home/jit)

M Muralidharan<sup>1</sup>, TP Sathishkumar<sup>2</sup> , N Rajini<sup>3</sup> ,  
P Navaneethakrishan<sup>2</sup>, Sikiru Oluwarotimi Ismail<sup>4</sup>,  
K Senthilkumar<sup>5</sup>, Suchart Siengchin<sup>6</sup> , Faruq Mohammad<sup>7</sup>   
and Hamad A Al-Lohedan<sup>7</sup>

## Abstract

Development of new hybrid laminated composites of Kevlar-29 (K-29)/banana fiber (*Musa acuminata*) mats to meet future demand for fiber reinforced polymer (FRP)

<sup>1</sup>Department of Mechanical Engineering, Vel Tech High Tech Dr. Ranagarajan Dr. Sakunthala Engineering College, Chennai, India

<sup>2</sup>Department of Mechanical Engineering, Kongu Engineering College, Erode, India

<sup>3</sup>School of Automotive and Mechanical Engineering, Department of Mechanical Engineering, Kalasalingam Academy of Research and Education, Krishnankoil, India

<sup>4</sup>Center for Engineering Research, Department of Engineering, School of Physics, Engineering and Computer Science, University of Hertfordshire, Hertfordshire, UK

<sup>5</sup>Department of Mechanical Engineering, PSG Institute of Technology and Applied Research, Coimbatore, India

<sup>6</sup>Department of Materials and Production Engineering, The Sirindhorn International Thai-German Graduate School of Engineering (TGGS), King Mongkut's University of Technology North Bangkok, Bangkok, Thailand

<sup>7</sup>Department of Chemistry, College of Science, King Saud University, Riyadh, Kingdom of Saudi Arabia

## Corresponding authors:

TP Sathishkumar, Department of Mechanical Engineering, Kongu Engineering College, Perundurai, Erode 638 060, India.

Email: [tpsahish@kongu.ac.in](mailto:tpsahish@kongu.ac.in)

N Rajini, School of Automotive and Mechanical Engineering, Department of Mechanical Engineering, Kalasalingam Academy of Research and Education, Anand Nagar, Krishnankoil 626 126, India.

Email: [rajiniku@gmail.com](mailto:rajiniku@gmail.com)



Creative Commons Non Commercial CC BY-NC: This article is distributed under the terms of the Creative Commons Attribution-NonCommercial 4.0 License (<https://creativecommons.org/licenses/by-nc/4.0/>) which permits non-commercial use,

reproduction and distribution of the work without further permission provided the original work is attributed as specified on the SAGE and Open Access pages (<https://us.sagepub.com/en-us/nam/open-access-at-sage>).

composites has been investigated. The different ply-stacking sequenced Kevlar (K)/natural (N) banana reinforced epoxy polymeric hybrid composite samples were designated as KN1, KN2, KN3, KN4, KN5 and KN6, in addition to NN7 and KK8 for single or non-hybrid FRP (control) composite samples. The ply-stacking effects on mechanical properties of all the laminated composite were investigated. The maximum tensile, flexural, impact and interlaminar shear strengths (ILSS) were obtained with sample KN4, because of the stacking of its Kevlar and natural banana mats, which was K2/N4/K2 of 8 layers and different from other stacking sequences. The percentage improvements on tensile strength of sample KN4 when compared with other hybrid composite samples KN1, KN2, KN3, KN5 and KN6 were 6.3, 4.4, 3.6, 13.1 and 11.3%, respectively. While, same optimum sample KN4 recorded highest flexural strength among hybrid samples with percentage improvements of 122.19, 70.97, 31.03 and 83.68% when compared with other hybrid samples KN2, KN3, KN5 and KN6, respectively. Similar trend of results was obtained for their tensile and flexural moduli. But, both hybrid composite samples KN3 and KN4 recorded higher impact strengths of 3.0 and 2.8 J, respectively, when compared with other hybrid counterparts. The tensile and flexural strengths of sample KN4 were 147.48 and 223.69 MPa, respectively. The tensile properties of various theoretical model were compared with experimental values.

### **Keywords**

Kevlar-29/banana fibers, Ply-stacking sequences, Woven Mats, Hybrid composites, Mechanical properties, Failure modes/mechanisms

## **Introduction**

Fiber reinforced polymer (FRP) composite laminates have been widely used for automobile parts, household appliances and aircraft components.<sup>1-3</sup> The use of FRP composite laminates has been increasing significantly in several fields to meet the design and functional requirements. The synthetic FRP composites have been used in the aforementioned industries. However, they possess high manufacturing costs, non-biodegradability, and high toxicity levels, making them environmentally unfriendly and relatively unsafe for human health. For product development in the last two decades, natural fibers and their woven mats are widely used to further reduce the weight of products with ease of handling during manufacturing stage.<sup>4</sup> Different natural fibers have been combined with synthetic fibers to prepare hybrid laminated composites, which reduce the overall weight of products. Despite of many works that have been done on synthetic, natural FRP, synthetic-natural and synthetic-synthetic FRP hybrid composites for lower and higher load bearing applications,<sup>2,5-7</sup> there are still needs for further studies on synthetic-natural FRP hybrid composites.

Moving forward, the pairing effects of aramid and glass fiber fabrics reinforced with carbon fiber fabric hybrid composites did not show significant difference in their mechanical properties. The carbon fiber fabric was laminated commonly between two

laminates of glass and aramid fibers in the hybrid composite systems. Both tensile and flexural properties of the hybrid composites were obtained among other properties of carbon, aramid and glass fiber fabric reinforced composites. Fabric delamination was observed at outer surface rather than inner layer and it was observed higher with carbon/glass than carbon/aramid fiber fabrics hybrid composites.<sup>8</sup> Jute,<sup>9–11</sup> sisal,<sup>12,13</sup> flax,<sup>14–16</sup> hemp<sup>15</sup> and pineapple leaf<sup>13</sup> fibers were reinforced in short and woven mat forms of glass fiber to prepare natural/glass fibers hybrid composites. The impact properties of the hybrid composites were varied with the weight contents of their natural and glass fibers. Impact damage on the fabric laminated composites were predicted by two approaches: overall size of the impact damaged area and appearance of first matrix crack that propagated to produce delamination of the laminates. Matrix cracking, delamination, fiber-matrix debonding and fiber fracture were initiated together during impact test of all the laminated composites.<sup>9,10,12,14,17</sup> Pineapple leaf fiber (PALF)/woven glass fiber fabric reinforced polyester composite exhibited maximum tensile and flexural properties at 25% total fiber contents with 8.6% of glass fiber. Addition of glass fiber in sisal fiber hybrid composites increased the mechanical properties and produced maximum properties at 8.5% of glass fiber content. Also, alkaline treated sisal fiber in hybrid composites showed higher strength than untreated, cyanoethylation and acetylation treated fiber composites. This was attributed to the higher interfacial bonding between the fiber and matrix.<sup>13</sup>

Besides, enhancement of the compatibility between sisal/glass fibers in polypropylene (PP) hybrid composites was achieved by grafting the maleic anhydride in PP (MAPP). Hence, it improved the mechanical properties.<sup>18</sup> The addition of chalk powder in sisal/glass fiber hybrid composites gradually reduced the interfacial bonding and consequently reduced their tensile and flexural strengths.<sup>19</sup> Presence of bidirectional woven glass fabric in sisal fiber reinforced epoxy composite showed uniform tensile strength in all directions.<sup>20</sup> An increased glass fiber content in woven jute/bidirectional glass fiber woven fabric reinforced polyester composites caused a decrease in their impact energy absorption. Composite samples with thickness of 6.1 mm, 17.1% of jute fiber weight fraction and 25.2% of glass weight fraction recorded better impact properties at maximum peak load.<sup>21</sup> The post-impact damage was analyzed for 14 layers of E-glass fiber fabric with 4 layers of jute fiber fabric in hybrid composites, an increase in the post-impact energy decreased the acoustic emission stress.<sup>22</sup> Sisal-jute fiber isothallic polyester composite showed higher impact and tensile strengths than both jute-glass fiber and sisal-jute-glass fibers isothallic polyester composites.<sup>23</sup> Similar trend was observed with jute-glass fiber epoxy composites, when glass fiber bidirectional woven fabric was used as a skin material.<sup>20</sup> The impact strength of plant (jute fiber plane fabric)-glass fibers reinforced polymer hybrid composites depended on their fiber contents.<sup>24</sup> The tensile and flexural properties of synthetic fiber composites increased by decreasing the weight content of palmyra,<sup>25</sup> coir,<sup>26</sup> bamboo<sup>27</sup> and roystonearegia<sup>28</sup> fibers.

Furthermore, roselle/sisal fiber reinforced polyester hybrid composites recorded maximum tensile and flexural strengths at fiber length of 150 mm.<sup>29</sup> The sisal-oil palm fibers aligned at longitudinal direction have showed higher mechanical properties rather than transverse direction. The addition of resorcinol-hexamethylenetetramine in rubber composites improved their rubber-fiber interfacial adhesion.<sup>30</sup> The tensile strength and

hardness of sisal/oil palm fiber reinforced rubber composites were observed higher in 4% of sodium hydroxide (NaOH) treated fibers.<sup>31</sup> Sisal and coir fibers were randomly oriented in unsaturated polyester composite and it exhibited maximum tensile and flexural strengths at fibers length of 20 mm.<sup>32</sup> Alkali treated coir fiber reinforced silk fiber polyester hybrid composites improved the adhesion between coir and matrix, due to the removal of hemicellulose, moisture content from the coir fiber, and also offered better surface roughness on the coir fibers, which increased the bonding area between the fiber and matrix.<sup>33</sup> The woven jute fiber fabric has been used as core and/or skin material of oil palm empty fruit bunch fiber (OPEFB) hybrid epoxy composites, which showed higher tensile and flexural properties with layer pattern of jute-OPEFB-jute fibers.<sup>34</sup> Both tensile strength and modulus were higher for the OPEFB-jute fiber epoxy hybrid composites with relative fiber ratio of 1:4. An increase in jute fiber ratio of the hybrid composites significantly increased their tensile properties.<sup>35</sup>

In addition, snake grass/banana fiber reinforced polyester hybrid composite exhibited higher tensile and flexural properties than snake grass/coir fiber counterpart. This was attributed to the higher moisture content of the coir fiber than that of banana and snake grass fibers.<sup>36</sup> The mechanical properties of hybrid and single fiber composites were defined by laminating sequence, fiber strength, matrix strength and rule of mixture. Reduction in ultimate load caused delamination of the laminates and eventually, catastrophic broken of glass, carbon and natural fibers.<sup>37-40</sup> The 40% weight fraction of kenaf/bamboo fiber mat reinforced composites were examined with relative weight fractions of 70:30, 50:50 and 70:70 for both fibers. The composites with relative weight fraction of 50:50 showed highest flexural and impact strengths.<sup>41</sup> Glass and jute fibers fabric epoxy composites depicted higher tensile strengths of approximately 80 MPa, due to the presence of outer ply of glass fiber mats, and hardness of 80 HRL.<sup>42</sup> Jute, hemp and flax fiber fabric composites showed maximum tensile properties with jute/hemp/flax fabric stacking sequence, because of the higher strengths of both hemp and flax fiber fabrics.<sup>43</sup> Mechanical properties of glass fiber fabric and coir fiber reinforced epoxy composites were purely based on number of glass fiber fabric present in the composite systems.<sup>44</sup> Hybrid composites have showed higher mechanical properties than single fiber composites<sup>45</sup> and laminating sequence have varied the impact load of the composites.<sup>46</sup>

Based on the afore-reported studies, it was evident that work on Kevlar-29/banana (K-29/banana) fiber woven mats reinforced epoxy hybrid composite has not been investigated for a medium load bearing application. Hence, the aim of this work was to develop a new hybrid composite with K-29 and banana fiber mats for a medium load bearing application. Also, it will meet the future ever-increasing demand for FRP composites. The main objectives is to use the K-29 and banana fiber woven mats to prepare the hybrid epoxy composite laminates and their mechanical properties are studied by varying the layering sequence of the woven mats. Importantly, banana fiber mat was selected, because it is abundantly available, especially in southern part of India. The fiber mat has been traditionally used for various textile products, such as sleep and foot mats as well as window shelter, among other applications. The K-29 mat is one of the synthetic fiber mats, which is less harmful to living things, when compared with glass and carbon fibers.

Therefore, these two fibers mats were selected for the new FRP hybrid composite development. After fabrication, different experimental tests were carried out on their mechanical properties: tensile, flexural, impact and interlaminar shear strengths (ILSS) and their mechanisms of stress transverse were elucidated. Also, results obtained from their various mechanical responses were compared with that of existing similar hybrid composite materials for further improvement.


## Materials and methods

### *Kevlar-29/natural banana fiber fabric and bonding material*

Kevlar-29 fabric<sup>47,48</sup> woven mat purchased from KR fiber industry, Bangalore, India. The long Kevlar mat was cut into small pieces of 250 mm length and 200 mm width for composite preparation, as shown in [Figure 1\(a\)](#). A banana fiber woven mat was prepared by using hand-weaving machine at Sri Achu fibers, Erode, Tamil Nadu, India. The long banana fiber mat was cut into small pieces with dimension of 250 × 200 mm during composite preparation ([Figure 1\(b\)](#)). The total working width of 0.5–1.0 m was used. The number of treadles was 8. Wrap and cloth roller were 250 cm long with diameter of 100 mm. It has one beater hand-tree with two heddles. The physico-mechanical properties of the fibers and their mats are shown in [Table 1](#). The epoxy binding material with hardener was purchased from the Covai Senu Industry, Coimbatore, India and its properties are shown in [Table 2](#).

### *Preparation of hybrid composites*

The hybrid composites were prepared by using simple hand lay-up method, followed by compression molding process, with various ply-stacking sequences of Kevlar (K) and natural (N) banana fiber mats. The ply-stacking pairing sequences were designated as KN1, KN2, KN3, KN4, KN5, KN6, NN7 and KK8, as previously illustrated in [Figure 1\(c\)](#). The epoxy and hardener were mixed in ratio of 10:1. Initially, the releasing agent of liquefied polyvinylchloride (PVC) was coated on internal surfaces of mold, which aided easy removal of the composites. Both banana and Kevlar woven fabric mats were wetted in epoxy with hardener solution. According to ply-stacking sequences, the layer-by-layer wetted mats were placed on the steel mold cavity, as shown in [Figure 1\(c\)](#). Then, the closed mold was kept in a hydraulic press under pressure of 10 kg/cm<sup>2</sup> for 24 h at atmospheric temperature. During lamination on mold, the spring roller was used to roll on each lamina to remove air bubbles in the resin. Also, it ensured uniform distribution of the resin, maintained uniform thickness of the composite and avoided the wrinkle formation in each lamina. Finally, the solidified composite was taken from the mold with size of 250 × 200 × 3 mm and post cured in a hot air oven for 4 h at 80°C. The total weight fraction of the fibers was 45%, then Kevlar and banana fiber weight fractions were 33 and 17%, respectively.

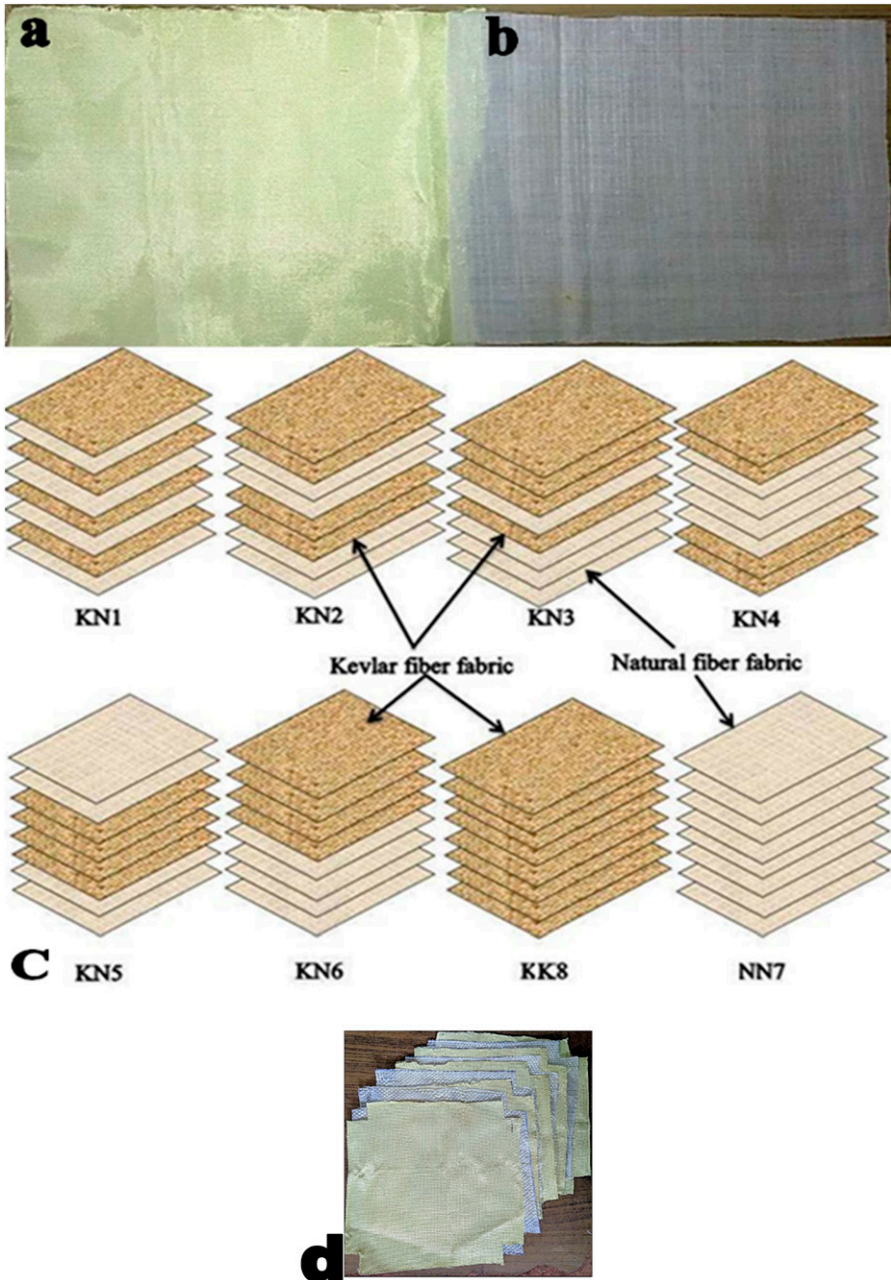

**Figure 1.** (a) Kevlar, (b) banana fiber woven mats, (c) stacking sequences for K-29/banana woven mats for hybrid samples KN1-KN6 and control or non-hybrid composite samples KK8 and NN7 and (d) Stacking of mats.

**Table 1.** Properties of the fibers and mats used.

Properties	Unit	Fiber	
		Kevlar	Banana
Tensile strength of fiber	GPa	2.8	0.4
Tensile modulus of fiber	GPa	62.0	5.5–12.6
Elongation of fiber	%	3.6	7.0–8.0
Density of fiber	g/cm <sup>3</sup>	1.44	1.50–1.60
Diameter of fiber	μm	12	155–195
Yarn Denier of mat	(g/km)	165	104
Yarn linear density of mat	(mg/cm)	1.656	0.875
Yarn count of mat	(yarns/cm)	6.7	40.0
Fabric ply thickness of mat	(mm)	0.18	0.21
Fabric weight	g/m <sup>2</sup>	305	120
Fabric types	—	Plane weaving	Plane weaving
Linear density (warp and weft direction)	Tex	132	182
Moisture content	%	0	12
Count (warp and weft direction)	Number fibers	9 × 9	1 × 1
Fiber diameter	mm	0.0012	0.150


**Table 2.** Properties of the epoxy resin used.

Properties	Unit	Range
Specific gravity at 25°C	—	1.16 ± 0.02
Density	g/cm <sup>3</sup>	1.12
Viscosity at 25°C	cps	1150 ± 450
Tensile strength	MPa	24
Tensile modulus	MPa	450
Flexural strength	MPa	32
Flexural modulus	MPa	1.25
Shrinkage	%	0.004–0.008

### Mechanical properties

Mechanical behaviors of the prepared hybrid composite samples were obtained, using various appropriate American society for testing and materials (ASTM) standards. Five identical samples were tested for each experiment, as subsequently discussed.

**Tensile test.** The tensile properties were determined in accordance with the ASTM D 638 standard, constant rectangular cross-section. The test samples were machined to obtained standard size of 165 × 13 × 3 mm. The gauge length was 50 mm. The universal tensile testing machine of DTRX-30 kN model from Deepakpoly-Plast Pvt. Ltd. was used to perform the tensile test. It has a cross head speed of 2 mm/min and a maximum load cell

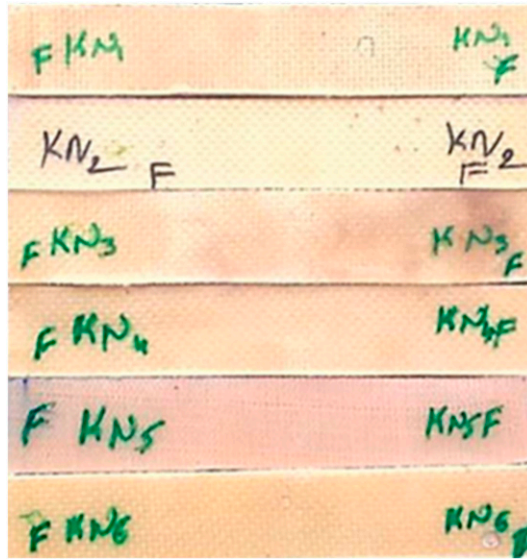

**Figure 2.** Flexural test samples of K-29/banana woven mat hybrid composites.


of 25 kN. The maximum cross head travel was allowed for a complete fracture of each sample. Mechanical properties, such as tensile strength, elastic modulus, load and elongation at break of the composites were obtained from the experiments.

**Flexural test.** Flexural properties were obtained according to the ASTM D 790 standard.<sup>13,16</sup> Sample size of  $48 \times 13 \times 3$  mm (Figure 2) was machined with span-to-depth ratio of 16:1, which was associated with high-strength reinforced composite laminates. The flexural testing machine of same DTRX-5 kN model from Deepak poly-Plast Pvt. Ltd was used to perform the flexural test. It has a cross head speed of 2 mm/min and a maximum load cell of 5 kN. The maximum cross head travel was set-up to 20 mm.

**Interlaminar shear strength test.** Short beam shear test was directly used through bending test to study the ILSS of the laminated hybrid composite beams in accordance with the ASTM D 2344 standard.<sup>49</sup> The sample size was  $15 \times 12.7 \times 3$  mm with span length-to-depth ratio of 5:1 for high-strength reinforced composite laminates. The flexural testing machine of same DTRX-5 kN model from Deepak poly-Plast Pvt. Ltd was used to perform the ILSS test. It has a crosshead speed of 1.3 mm/min and a maximum load cell of 500 N.

**Impact test.** Izod impact strength was measured according to the ASTM D 256 standard and sample size of  $64 \times 12.7 \times 3$  mm was used (Figure 3). The impact testing machine of IZOD TESTC-R model from same Deepakpoly-Plast Pvt. Ltd was used to perform the impact strength. The accuracy of the machine was 0.01 J and maximum measuring range



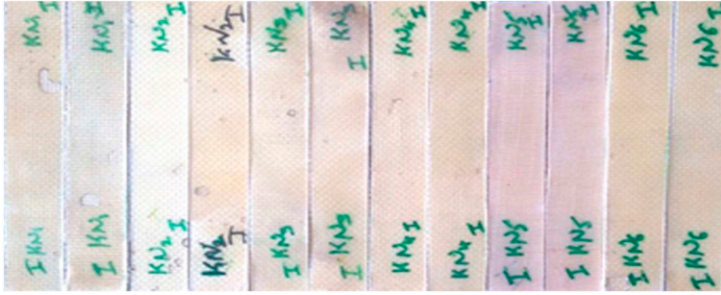

**Figure 3.** Impact test samples of K-29/banana woven mat hybrid composites.

was up to 25 J. Before testing, manually operated notch cutter was used to make the V notch on the samples for impact testing.

### Scanning electron microscopy

The microstructural failures and fractures of the composite samples were analyzed, using cross section analyze method through scanning electron microscopy (SEM), available in Tamil Nadu Agricultural University (TNAU), Tamil Nadu, India. The following specifications were used during image scanning: resolution of 3.0 nm (Acc V 15 kV and WD 8–9 mm), magnification of 50–500 $\times$ ) and electron gun accelerating voltage of 0.5–30 kV.

### Theoretical models

Parallel and series models were used to predict the tensile strengths and moduli of the composites, using different relationships. Figure 4 shows the directions of strength and modulus for various theoretical models.<sup>50</sup>

Parallel model was used to find the stress in the composite along fiber direction,<sup>50</sup> as expressed in equations (1) and (2).


$$E_C = E_{Kf}V_{Kf} + E_{Bf}V_{Bf} + E_mV_m \quad (1)$$

$$\sigma_C = \sigma_{Kf}V_{Kf} + \sigma_{Bf}V_{Bf} + \sigma_mV_m \quad (2)$$

Series model was used to determine the stress in the composite perpendicular to the fiber direction,<sup>50</sup> as presented in equations (3) and (4).

$$E_C = \frac{E_{Kf}E_{Bf}E_m}{E_{Kf}V_m + E_{Bf}V_m + E_mV_f} \quad (3)$$

$$\sigma_C = \frac{\sigma_{Kf}\sigma_{Bf}\sigma_m}{\sigma_{Kf}V_m + \sigma_{Bf}V_m + \sigma_mV_f} \quad (4)$$

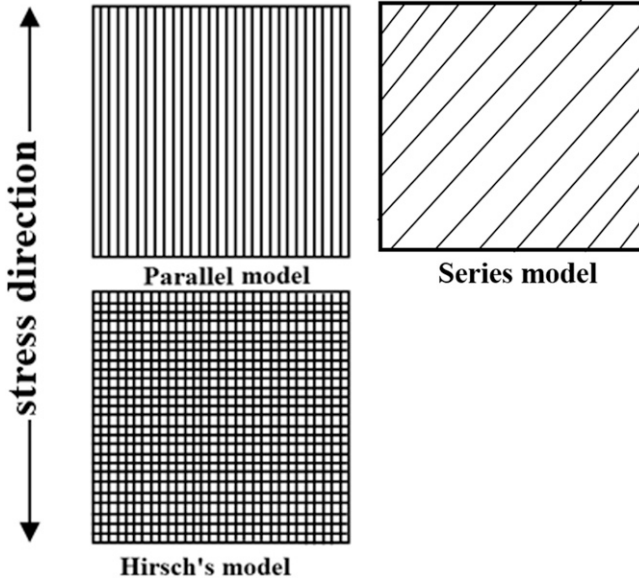

**Figure 4.** A schematic representation of various theoretical models used.

Where,  $E_c$ ,  $E_m$ ,  $E_{kf}$  and  $E_{Bf}$  represented the Young's moduli of the composites, matrix, kevlar and banana fibers, respectively.  $V_m$ ,  $V_{kf}$  and  $V_{Bf}$  denoted volume fractions of the matrix, kevlar and banana fibers, respectively. Also,  $\sigma_c$ ,  $\sigma_m$ ,  $\sigma_{kf}$  and  $\sigma_{Bf}$  were tensile strengths of the composites, matrix, kevlar and banana fibers, respectively.

Hirsch's model is a hybrid model of merged parallel and series models. It was similarly used, as presented in equations (5) and (6).

$$E_c = x(E_m V_m + E_{kf} V_{kf} + E_{Bf} V_{Bf}) + (1 - x) \frac{E_{kf} E_{Bf} E_m}{E_m V_f + E_{kf} V_m + E_{Bf} V_m} \quad (5)$$


$$\sigma_c = x(\sigma_m V_m + \sigma_{kf} V_{kf} + \sigma_{Bf} V_{Bf}) + (1 - x) \frac{\sigma_{kf} \sigma_{Bf} \sigma_m}{\sigma_m V_f + \sigma_{kf} V_m + \sigma_{Bf} V_m} \quad (6)$$

Where,  $x$  value was taken as 0.4, as an assumed factor.<sup>50</sup> This determined the stress transfer between the fiber and matrix.

## 4 Results and discussion

### *Tensile behaviors of the hybrid and control FRP composites*


The tensile test results of K-29/banana fiber mat reinforced hybrid composites are presented in Figure 5, 6 and 7. Figure 5 shows typical tensile stress-strain curves of hybrid composites and control composites. It was observed that the tensile stresses of all the

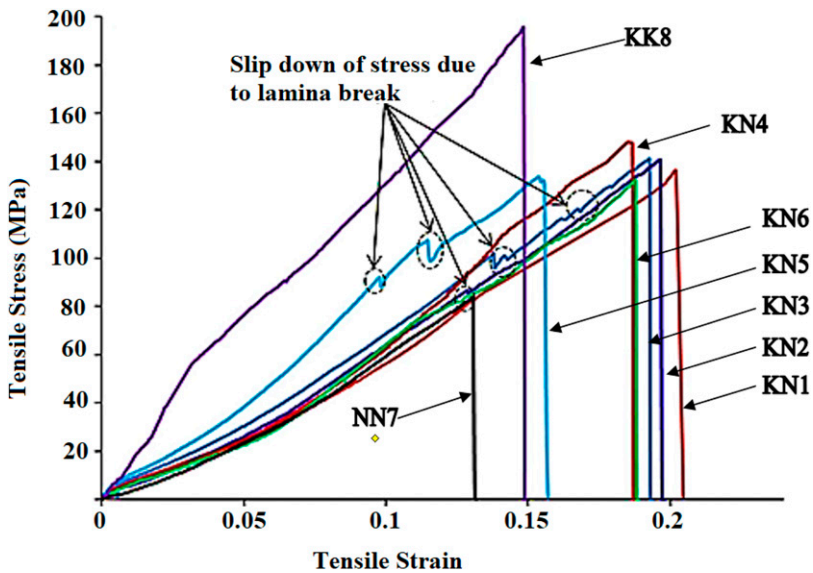

**Figure 5.** Engineering tensile stress versus tensile strain curves of the various K-29/banana woven mat hybrid and control/non-hybrid composite samples.

composites were gradually increased, and linear elastic behavior was observed for all the composites against axial tensile strain.<sup>8</sup> The stress-strain behaviors of the six hybrid composites were intermediately between that of samples NN7 and KK8, with single natural banana and synthetic Kevlar fiber mats only, respectively. Observing that the curves of hybrid composites were biased towards KK8, the tensile behaviors of sample KN4 appeared to be affected by the types of laying sequences. The curve of composite laminate sample KK8 showed a rougher and higher stress-strain behavior than the combined effect of banana and Kevlar hybrid composite laminate samples. This can be attributed to the higher toughness of Kevlar fiber (KF)<sup>8</sup> compared with banana fiber. But, the pure banana mat laminate (sample NN7) showed smooth stress-strain behaviors than the KK8, due to the lower toughness property of banana fiber. Kevlar-type hybrid composites showed more elongation than banana-type. Due to difference in mechanical properties of Kevlar and banana fibers-type, a large difference in their properties was observed from their hybrid composites. This suggested that the incorporation of banana fiber mat to KF mat in epoxy composites dominated the stress field, due to a lower strength and rigidity of banana fiber. In other words, the addition of KF mat to banana fiber mat in epoxy composites dominated the stress-strain behaviors, due to higher strength and rigidity of KF. However, addition of natural fiber (NF) with synthetic fiber showed a comparatively lower tensile strength than the pure or single synthetic fiber reinforced composites.<sup>23</sup>


Moreover, it was observed from the curves of KN2, KN3, KN5 and KN6 hybrid composite samples that the climbing stress-strain curves showed a small drop in stress at a

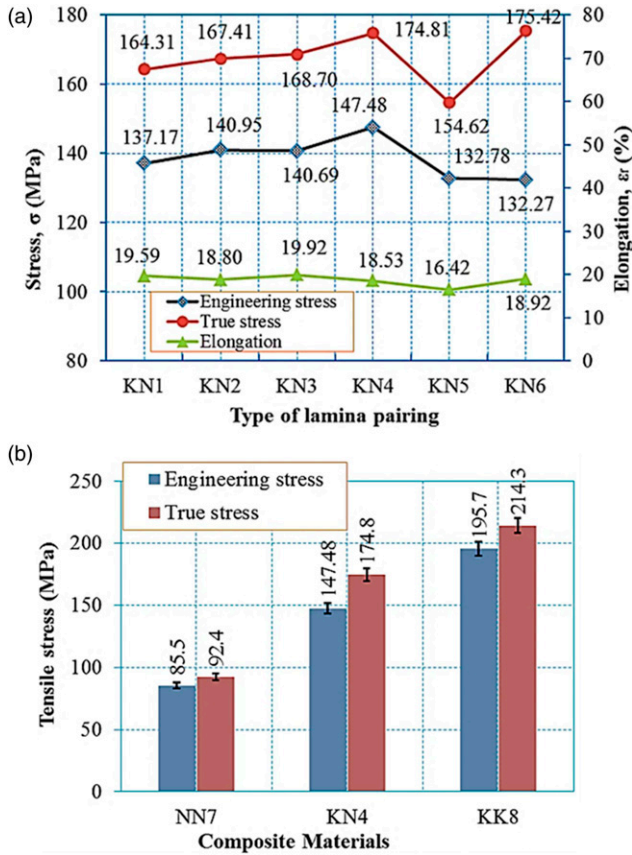

**Figure 6.** (a) Tensile properties of the various K-29/banana woven mat hybrid composites and (b) sample KN4 in comparison with control/non-hybrid composite samples HH7 and KK8.

particular strain. This was attributed to earlier failure of NF laminas during experiment. From sample KN5 laminated hybrid composite curve, the drop in stress of 91.53 MPa at 0.0964 strain and stress of 106.37 MPa at 0.1143 strain occurred at two stages. The earlier failure of the NF laminas reduced the stress carrying capability of sample KN5 composite. Ultimately, this might have reduced the tensile stress of the composite. Also, sample KN2 hybrid composite exhibited a drop-down stress of 99.35 MPa at 0.1337 strain. The stress-strain curves of KN1, KN4 and KN6 hybrid composite samples did not show any drop-down stress. This can be traced to the even distribution of stress in all the laminas. Also, the presence of higher strength laminas (fabrics) at outside of the composites improved their tensile strengths.

Furthermore, the engineering stresses of all the composites were calculated from the ratios of maximum load carried by the composites and their cross-sectional areas before testing. The true stresses were calculated from the ratio of maximum load carried by the

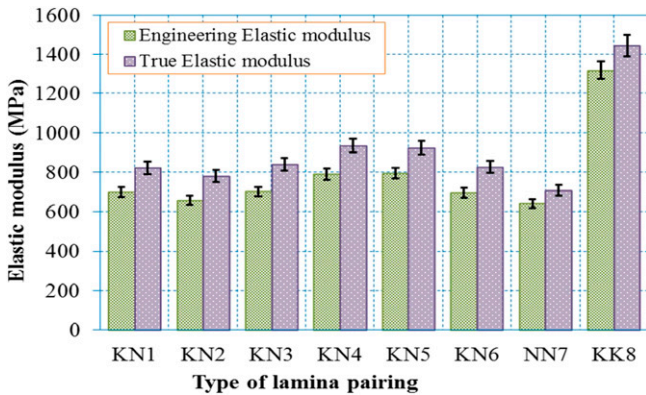

**Figure 7.** Elastic moduli of the various K-29/banana woven mat hybrid and control composite samples.

composites and their neck cross sectional areas after testing. [Figure 6\(a\)](#) illustrates the key tensile properties of K-29/banana fiber epoxy composites, calculated from their tensile test results obtained, such as engineering stress (ultimate strength), true stress, modulus of elasticity and elongations with various pairing methods. This indicated that both stresses showed maximum in sample KN4 by pairing effect of hybrid composites. The engineering stresses of samples KN1, KN2, KN3, KN4, KN5, KN6, NN7 and KK8 were 137.17, 140.95, 140.69, 147.48, 132.78, 132.27, 85.50 and 195.70 MPa, respectively. The percentage differences between the maximum engineering stresses of sample KN4 and other hybrid samples KN1, KN2, KN3, KN5 and KN6 were 6.3, 4.4, 3.6, 13.1 and 11.3%, respectively. The true stresses of samples KN1, KN2, KN3, KN4, KN5, KN6, NN7 and KK8 were 164.31, 167.41, 168.70, 174.81, 154.62, 175.42, 92.40 and 214.30 MPa, respectively. The percentage differences between the maximum true stresses of sample KN4 and other hybrid samples KN1, KN2, KN3, KN5 and KN6 were 7.5, 4.6, 4.8, 11.0 and 11.5%, respectively. [Figure 6\(b\)](#) shows that hybrid composite sample KN4 was compared with both control composite samples NN7 and KK8. This indicated that the tensile properties of hybrid composite were obtained intermediately between that of single FRP composites or control samples NN7 and KK8. Sample KN4 recorded 1.72 times higher tensile stress when compared with sample NN7 and 0.75 times lower tensile stress than sample KK8. [Figure 7](#) shows that the engineering and true tensile moduli or elastic moduli of all the hybrid composites. Importantly, it was observed that sample KN4 recorded the maximum modulus, due to the pairing effect of laminating sequence. [Table 3](#) presents the various mechanical properties of the hybrid composites in comparison with other similar hybrid composite systems. From all the results presented, the synthetic-synthetic<sup>2</sup> fibers reinforced hybrid composites recorded higher tensile and flexural properties than our present work, because the fibers possessed higher tensile strengths. Notwithstanding, K-29/banana fibers hybrid composites exhibited better mechanical properties, when compared with other similar synthetic-NFs hybrid composites.

**Table 3.** Tensile and flexural properties of the hybrid composite sample in comparison with related hybrid composite counterparts.


Composites	NF treatment	Fiber weight fraction (%)	Resin	TS (MPa)	TM (GPa)	FS (MPa)	FM (GPa)	Reference
Kevlar 29/banana	—	45	Epoxy	147.48	0.789	223.69	5.78	Present work
Carbon/aramid	—	—	Epoxy	415–450	350–435	—	—	8
Carbon/glass	—	—	Epoxy	390–445	350–390	696.00	—	8
Palf/glass	—	16.5/8.6	Polyester	72.00	—	101.25	—	16
Sisal/glass	—	16.5/8.5	Polyester	99.00	—	140.00	—	16
Sisal/glass	(5% NaOH)	16.5/8.5	Polyester	130.00	—	150.00	—	16
Sisal/glass	Cyanoethylation	16.5/8.5	Polyester	112.00	—	151.57	—	16
Sisal/glass	Acetylation	16.5/8.5	Polyester	117.00	—	145.00	—	16
Sisal/glass	—	20/10	Polypropylene	29.62	2.33	66.74	4.03	13
Sisal/glass	—	15/15	Polypropylene	31.48	2.42	68.49	4.04	18
Sisal/glass	—	10/20	Polypropylene	31.59	2.43	68.84	4.13	18
Sisal/glass	—	—	Epoxy	68.55	—	—	—	20
Sisal/glass	—	—	Polyester	176.20	—	—	—	23
Jute/glass	—	—	Polyester	229.54	—	—	—	23
Glass/jute/sisal	—	—	Polyester	200.00	—	—	—	23
Palmyra/glass	—	55	Polyester	42.65	1.515	59.19	3.54	25
Coir/glass	—	1:2	Phenolic	71.58	71.58	71.58	8.60	26
Coir/glass	NaOH	1:2	Phenolic	74.58	9.91	192.80	9.74	26
Bamboo/glass	—	30	Polypropylene	17.50	3.00	34.00	3.40	27
Bamboo/glass	MAPP	30	Polypropylene	18.50	3.25	42.00	4.50	27
Roystonearegia/glass	—	15/5	Epoxy	31.48	2.41	40.12	3.98	28
	—	10/10	Epoxy	33.42	2.52	46.44	3.99	28
	—	5/15	Epoxy	34.42	2.64	48.66	4.01	28
Sisal/silk	—	20	Polyester	18.95	—	46.18	—	32
Sisal/silk	NaOH	20	Polyester	23.61	—	54.74	—	32
Coir/silk	—	20	Polyester	15.62	—	43.74	—	33

(continued)

**Table 3.** (continued)

Composites	NF treatment	Fiber weight fraction (%)	Resin	TS (MPa)	TM (GPa)	FS (MPa)	FM (GPa)	Reference
Coir/silk	NaOH	20	Polyester	17.24	—	45.07	—	<sup>33</sup>
OPEFB/jute	—	40 (1:4)	Epoxy	37.50	3.75	57.23	3.25	<sup>34</sup>
OPEFB/jute	—	40 (4:1)	Epoxy	25.30	2.62	—	—	<sup>35</sup>
Jute/hemp	—	43	Epoxy	42.19	1.59	86.60	0.78	<sup>43</sup>
Hemp/jute	—	43	Epoxy	44.17	1.49	44.64	0.74	<sup>43</sup>
Jute/hemp/jute	—	43	Epoxy	58.59	1.88	86.60	—	<sup>43</sup>

FM: Flexural modulus; FS: Flexural strength; NF: Natural fiber; TS: Tensile strength; TM: Tensile modulus.

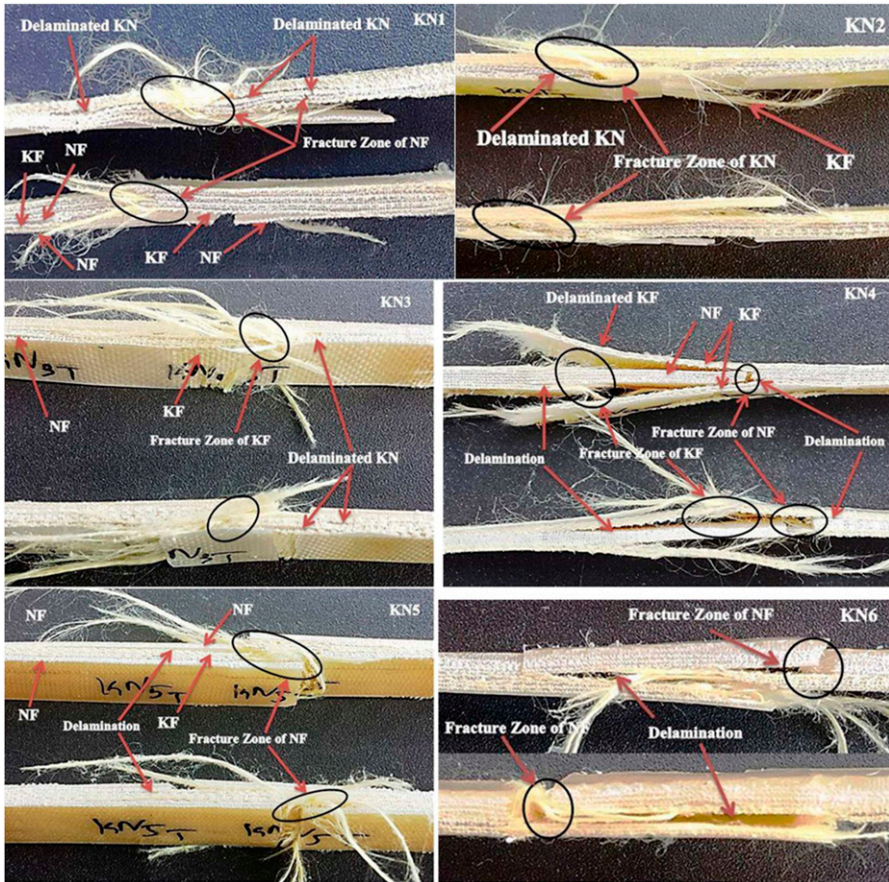


**Figure 8.** Images of the various tensile fractured hybrid composite samples.

### *Linear fracture and mechanism of tensile stress transfer*

Figure 8 depicts the macro-images of linear fracture of hybrid composites, while Figure 9 shows the schematic of contact mechanism of loading and unloading fiber surfaces subjected to a tensile load. In Figure 8, the developed linear fractures along loading direction were not uniform and occurred at same point. Observing that the perfect fracture zone of NF occurred with a group of fiber mat, delamination occurred between the different laminas.

With fiber matrix composites, it was significantly evident that the fiber carried most of the load, since applied load was continuously transmitted to the fiber before fracture.<sup>8</sup> The fracture behavior and propagation of crack that delaminated the composite laminates were different for various ply-stacking composites. Delamination of NF laminas at NF and KF laminas at KF was not uniform, because both fiber strengths and fiber-matrix interfacial




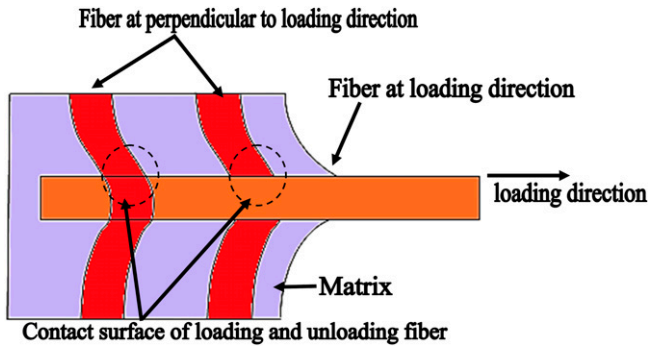

**Figure 9.** Contact mechanism of loading and unloading woven pattern fibers in matrix, subjected to the applied tensile load.

bonding areas were different. The propagation of cracks and delamination along the sample length at loading direction occurred very rapidly with hybrid composite sample KN1. It recorded longer length of delamination. Similar fracture and delamination occurred with composite samples KN2, KN3, KN5 and KN6. [Figure 8](#) shows that during experiment, loading fibers were elongated and unloading fibers were subjected to bend, due to internal surface contact between the fibers and nature of woven design. The unloading fibers resisted the deformation of loading fibers. It was evident that the unloading fibers withstood little load through their contact surfaces. The volume of load carrying and transferring between the fibers through matrix and surfaces was increased significantly. Therefore, the tensile strength and modulus were higher when compared with other hybrid composite counterparts ([Table 3](#)).


Also, [Figure 10](#) shows the internal micro-crack propagation and delamination of fiber mats in composite samples KN3 and KN4. Similar trend was concluded in the sisal/jute/glass FRP epoxy composites.<sup>23</sup> The NF pull-outs almost disappeared because the completed fracture occurred on NF mats rather than KF mats and better interfacial bonding between the NF and epoxy, the hydrophilic nature of NF, and the shear failure of NF at a single point. The KF zone showed that the fiber fracture disappeared uniformly and more fiber pull-outs seemingly occurred with random failure. This was the rationale behind delamination of KF laminas in the composite systems. Fiber breakage pattern was significantly showed on the fractured surfaces.<sup>23</sup> With sample KN4, the fracture zone of NF and KF laminas appeared at a certain region ([Figure 8](#)). Also, pairs of delamination occurred at fracture zone of NF and KF, respectively. Hence, the complete fracture occurred without fiber pull-outs at NF laminas with sample KN4 ([Figure 10](#)), fiber pull-outs and uneven fiber fracture occurred with KF laminas. It was observed that the applied load (stress) was transferred from low strength of NF lamina to higher strength laminas of KF, and it acted away from the center of the composite. The load transfer in terms of stress transfer is indicated later in [Figure 11](#). There was no delamination between the pair of similar laminas. Also, the fracture surface on the KF mat was complex and its fiber broke in a very rough cutting pattern.<sup>8</sup>

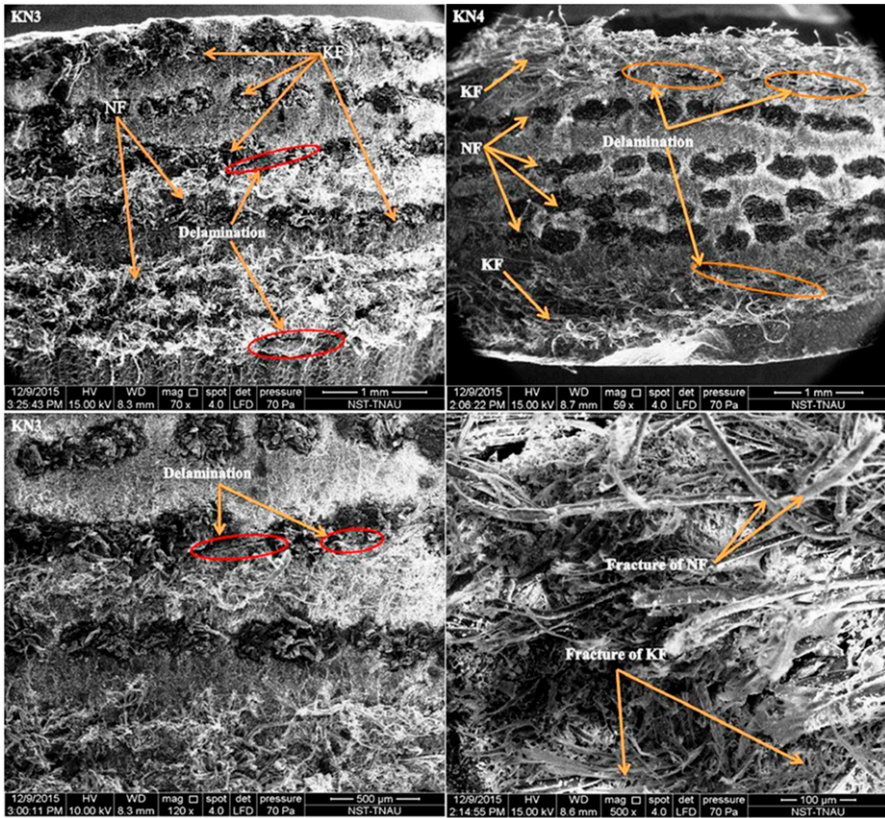

**Figure 10.** SEM images of the K-29/banana woven mat hybrid composite samples KN3 and KN4.

Figure 11 shows the mechanism of tensile stress distribution of both laminas. The low NF and high KF strength laminas were evidently indicated in the composites. The stress or load transfer from center of the sample is shown as straight line in both single FRP composite samples NN7 and KK8. This indicated uniform distribution of stress in the entire composites, because the total thickness of the composite was laminated by single fiber laminas. The indicated stress line at lower position in sample NN7 showed its lower stress distribution, and at upper position in sample KK8 depicted its higher stress distribution. Conversely, the lower and higher position lines were combined to form curved shape line (zig-zag line) in the hybrid composite samples. This established the fact that the hybrid composite samples contained two different fiber mats with various layering patterns, showing various stress distribution lines or curves, due to the strengths of the mats.

Among all the stress lines (Figure 11), stress of the hybrid composite sample KN4 started from center of the NF layers at lower position and it moved towards outward KF layers at higher position. Therefore, sample KN4 recorded more tensile strength than

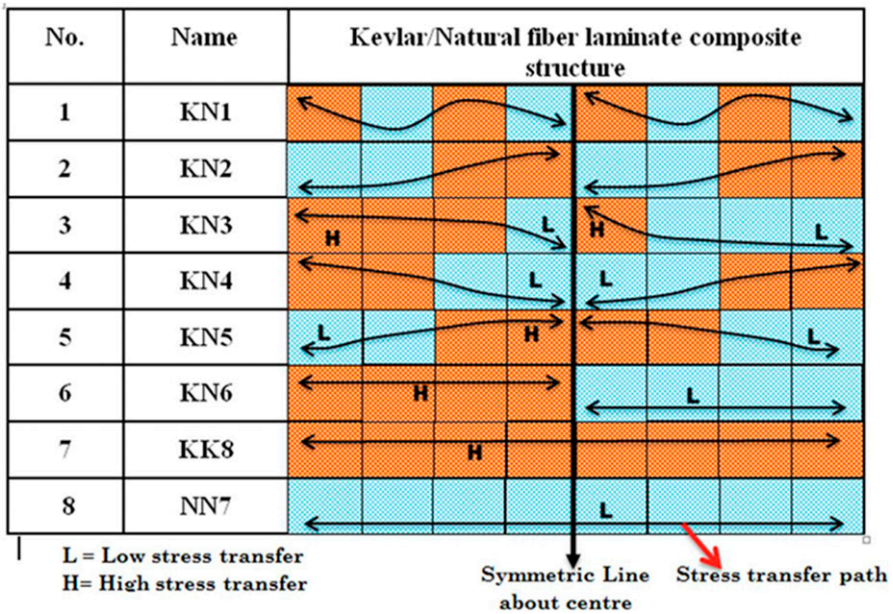


**Figure 11.** Mechanisms of tensile stress transfer path in laminated structure of K-29/banana woven mat hybrid and control composite samples (Orange and blue colors represent K-29 and banana, respectively).


other hybrid composites. Also, growth of delamination along sample length was observed to be lower when compared with other hybrid composites, because stress was distributed very quickly towards outward layers. With other hybrid composites, the stress distribution was not uniform; the stress line was showed in a zig-zag manner. Hence, the strength of hybrid composite sample KN4 showed superior tensile properties when compared with other hybrid composite counterparts.

**Flexural properties**

Flexural properties were determined from the bending capability of hybrid composite laminates. Figure 12 shows three-point bending test design to analyze the flexural properties of all the hybrid composite laminates. Figure 13 depicts the different curves obtained when flexural loads were plotted against the flexural displacements of all the hybrid composite with different ply-stacking sequences. From the results obtained, it was observed that sample KN4 laminated hybrid composite produced higher flexural load against displacement before complete fracture occurred. This can be attributed to pairing effect of higher strength of KF mat lamina at top and bottom planes (as skin laminas) of the composite, which absorbed more bending load before fracture, and lower strength of banana (NF) mat laminas at middle plane (as core laminas). In addition, sample KN4 was stronger and stiffer than all other hybrid composites. The bending fracture zone of the

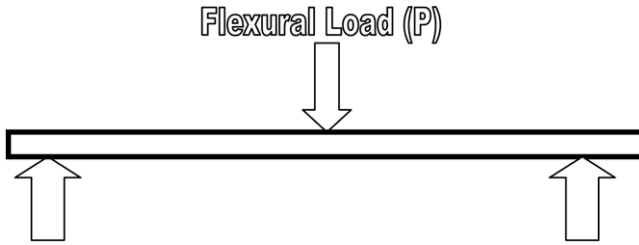


**Figure 12.** Three-point bending test set-up.

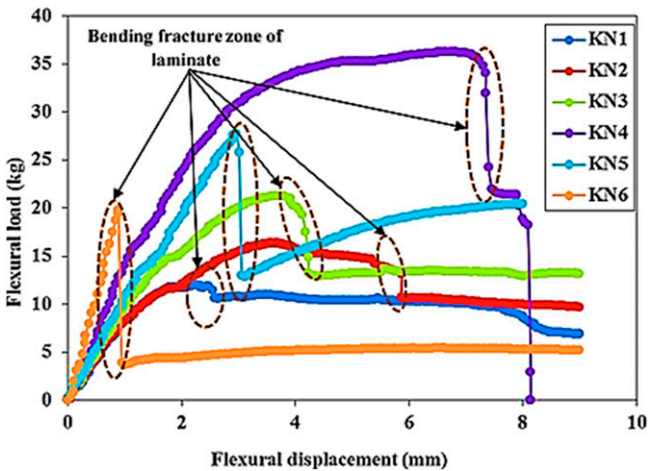

**Figure 13.** Flexural load versus displacement curves of the various K-29/banana woven mat hybrid composite samples.

laminated hybrid composite sample 4 was evident, as showed in the curves (Figure 13). After displacement of 7.52 mm, there was a complete rupture of the sample.<sup>23</sup> Hybrid composite samples KN1, KN2, KN3, KN5 and KN6 exhibited lower flexural loads and displacements, because these composites experienced preliminary bending fracture of laminate (Figure 13), when compared with sample KN4. The final fracture showed at higher displacement with lowest flexural load. This can be attributed to the stacking of lower strength laminas at skin. Also, the lower strength laminas might have completely fractured under a lower displacement and consequently, unable to carry lower flexural load.

Figure 14 shows the flexural strengths and moduli of the various hybrid and non-hybrid composites. KF/epoxy (KK8) and NF/epoxy (NN7) non-hybrid composites were compared with other hybrid composite samples. It was observed that hybrid composite sample KN4 recorded the highest flexural strength and modulus when compared with

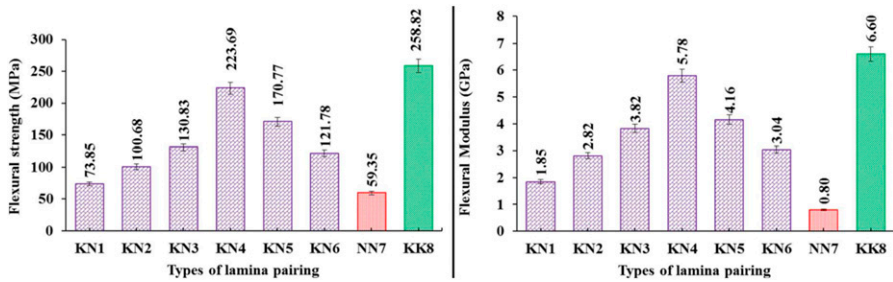


**Figure 14.** Flexural strengths and moduli of the various K-29/banana woven mat hybrid composites in comparison with control or non-hybrid composite samples.

other hybrid composites only, but non-hybrid composite sample KK8 had highest flexural properties among all the eight hybrid and non-hybrid composite samples. The maximum flexural properties of sample KK8 were greater than that of non-hybrid composite sample NN7 (Figure 14). Hybridizing Kevlar and banana fiber mats produced intermediate properties of composite samples KK8 and NN7. Additionally, the obtained flexural properties of the hybrid composite sample KN4 were very close to that of non-hybrid composite sample KK8, because stacking sequence of sample KN4 laminas contributed to its flexural properties. Hence, the outer surfaces or skins (top and bottom planes) of the composite sample KN4 possessed a pair of Kevlar laminas, which experienced higher flexural strength and modulus. This significantly showed that presence of high strength laminas at skins showed better flexural properties. However, some hybrid composite samples showed improvements in their flexural properties after altering their ply-stacking sequences. The strength and modulus percentage differences between samples KN4 and KK8 as well as KN4 and NN7 were 13.57 and 73.47%, respectively. The flexural strength differences between sample KN4 and other similar hybrid composite samples KN2, KN3, KN5 and KN6 were 122.19, 70.97, 31.03 and 83.68%, respectively.


### *Interlaminar shear strengths*

ILSS of K-29/banana fiber fabric mat hybrid composites were measured, using a short beam shear testing method, and it referred to the shear strength parallel to the plane of each laminate. The length-to-depth ratio of the beam has no effect on the shear strength. The maximum shear strength was denoted as ILSS of the composites. Based on interlaminar shear mode, the composite failed as a result of the formation of crack between the pair of laminas. Figure 15 shows the schematic of ILSS test. It was interesting to note that hybrid composite sample KN4 exhibited highest ILSS, when compared with other hybrid composites and sample NN7, as shown in Figure 16. This can be attributed to loss formation of interlaminar shear crack and more interfacial load transfer between fabrics by matrix. With hybrid composite sample KN1, Kevlar fabric was stacked under odd manner, which generated more micro-cracks between pair of different laminas (K-29/banana lamina), and the cracks reduced the shear strength between the laminas.

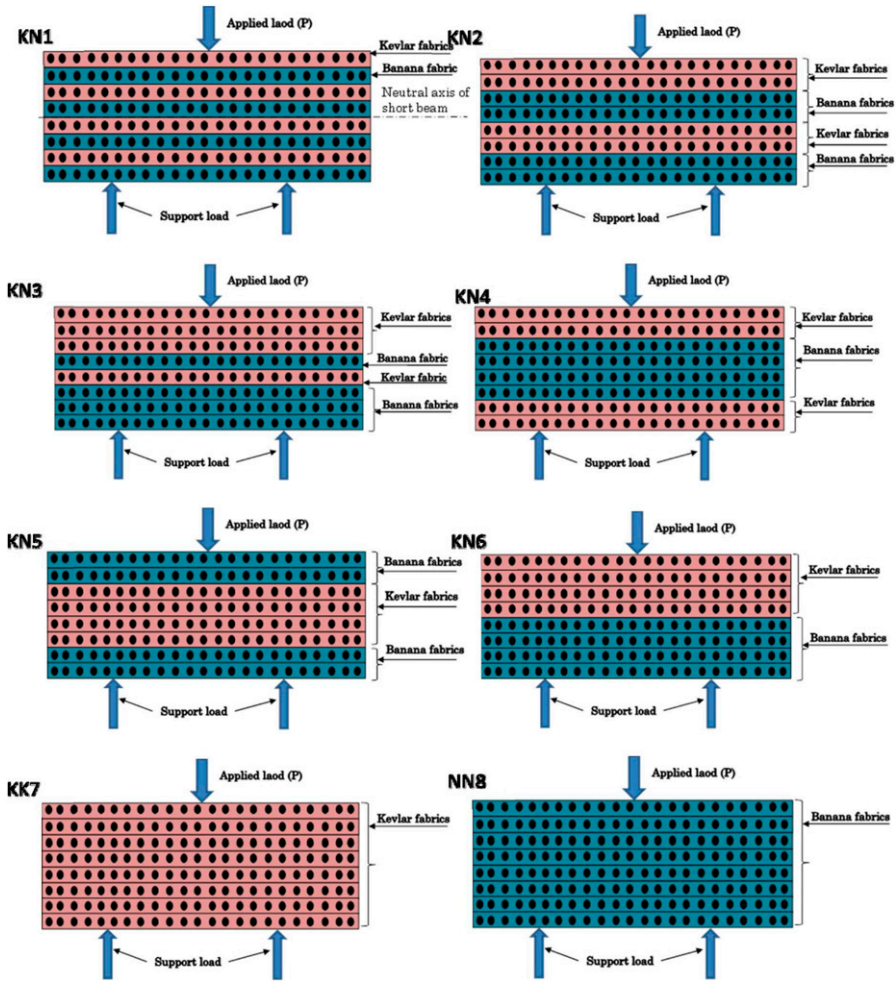

**Figure 15.** Schematic representation of the short beam shear test for ILSS.

During the experiment, the vertical downward applied load,  $P$  was acting on the K-29 and two vertical supporting loads were acting on the banana fabric. According to beam bending theory, the compressive and tensile forces were experienced by K-29 and banana fabrics, respectively. Also, the initial bending occurred on Kevlar fabrics along with banana fabrics from top to bottom and second was on banana fabric along with Kevlar fabrics from bottom to top, which were led to propagation of more cracks between pair of laminas. This might have reduced the ILSS. With hybrid composite samples KN2 and KN3, the supporting loads were acting on the pair of banana fabrics (Figure 16), which generated more cracks at the interfaces of banana laminas. The rate of crack propagate at outer laminas was very quicker than the cracks generated at middle laminas. Then,

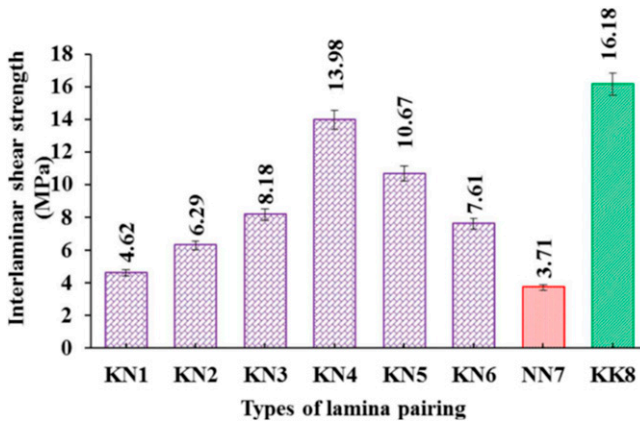


**Figure 16.** ILSS of the various K-29/banana woven mat hybrid in comparison with control or non-hybrid composite samples.

the interfacial bonding between the fabrics (laminas) and matrix decreased when laminas were shearing. This led to less ILSS. Similarly, the vertical downward and supporting loads were acting on the pair of banana fabrics of the hybrid composite sample KN5. The composite absorbed lower bending load and hence, it generated more cracks at interfacial plane, which consequently caused a lower ILSS.

In addition, applied load acted on the set of Kevlar fabrics and supporting loads acted on the set of banana fabrics in hybrid composite sample KN6 (Figure 16). The cracks generated between the banana fabrics and pair of different laminas were observed to be more during the experiment. Nevertheless, upward and downward loads acted on the Kevlar fabrics of high strength lamina in hybrid composite sample KN4, which resisted the rate of crack propagation between pair of laminas and absorbed more vertical loads. Therefore, hybrid composite sample KN4 exhibited highest ILSS among hybrid composite samples and sample NN7, because all the laminas of sample NN7 were made up of natural banana fabrics. Significantly, it was observed that ILSS of sample KN4 was very close to that of control or non-hybrid composite sample KK8, due to the pairing effect of its ply-stacking sequence. The ILSS improvements between sample KN4 and other hybrid samples KN1, KN2, KN3, KN5 and KN6 were 202.59, 122.25, 70.90, 31.02 and 83.71%, respectively.

### *Impact properties*

Impact strengths of all the various ply-stacking sequenced hybrid and non-hybrid/control composite laminate samples were obtained from drop tower impact Charpy tester. Samples NN7 and KK8 were tested for the purpose of comparison. The pendulum created impact force on the samples to absorb the impact energy. The maximum energy was determined from the potential difference between before and after tests. The impact toughness of the hybrid composite was calculated by dividing the absorbed energy by

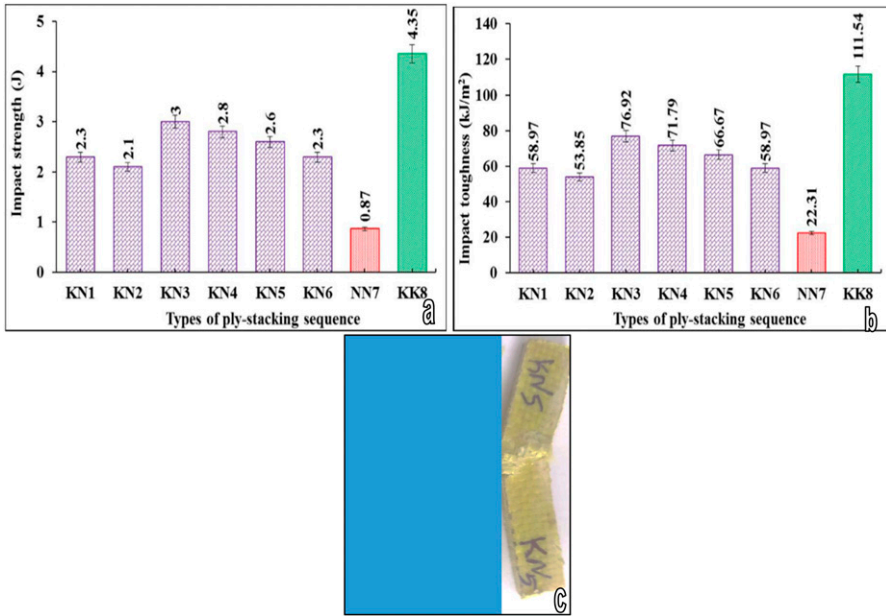

**Figure 17.** Impact strengths (a) and toughness (b) of the various K-29/banana woven mat hybrid in comparison with non-hybrid or control composite samples and (c) fracture samples.

cross section area of the composite. Figure 17 shows the impact energies or strengths and toughness of all the hybrid and non-hybrid composite laminates. It was evidently observed that by changing the ply-stacking sequence, the hybrid composites recorded different impact energy and toughness results. Samples KN3 recorded maximum impact (strength and modulus) properties, followed by sample KN4 among hybrid composite samples. While non-hybrid or control composite sample KK8 exhibited higher impact properties when compared with similar sample NN7, including other hybrid samples. This can be attributed to the presence of stronger K-29 fabrics in sample KK8, as previously juxtaposed in Table 1. Sample NN7 recorded the lowest impact properties among hybrid and non-hybrid composite systems.

More also, the impact strengths of samples KN1, KN2, KN3, KN4, KN5, KN6, NN7 and KK8 were 2.30, 2.10, 3.00, 2.80, 2.60, 2.30, 0.87 and 4.35 J, respectively. Also, the impact toughness values of samples KN1, KN2, KN3, KN4, KN5, KN6, NN7 and KK8 were 58.97, 53.85, 76.92, 71.79, 66.67, 58.97, 22.31 and 111.54 kJ/m<sup>2</sup>, respectively. Sample KN2 showed the lowest impact behaviors among the hybrid composite samples, followed by sample KN1. While, sample NN7 recorded the smallest values of impact strength and toughness among both hybrid and non-hybrid composite laminate samples. In both samples KN1 and KN2, a lamina or pair of similar laminas de-bonded quicker along with near successive pairs of different laminas. When the machine tower impacted the samples, the lower strength laminas exhibited faster failure at entire samples. This showed lower impact strength and toughness. With samples KN3, KN4 and KN5, a pairs




**Table 4.** Impact properties of the hybrid composite sample in comparison with related hybrid composite counterparts.

Composites	NF treatment	Fiber content	Resin	Impact strength	Unit	Reference
Kevlar-29/ banana	—	45	Epoxy	71.79	kJ/m <sup>2</sup>	Present work
Bamboo/glass	—	6.2/18.8	Unsat. polyester	32	kJ/m <sup>2</sup>	<sup>9</sup>
Jute/glass	—	6/8	Unsat. polyester	44	kJ/m <sup>2</sup>	<sup>10</sup>
Flax/glass	—	30/20	Polypropylene	43.2	kJ/m <sup>2</sup>	<sup>11</sup>
Sisal/glass	—	2.7/5.3	Unsat. polyester	5.76	kJ/m <sup>2</sup>	<sup>12</sup>
Palf/glass	—	16.5/8.6	Polyester	129	J/m	<sup>13</sup>
Sisal/glass	—	16.5/8.5	Polyester	149	J/m	<sup>13</sup>
Sisal/glass	5% NaOH	16.5/8.5	Polyester	169	J/m	<sup>13</sup>
Sisal/glass	Cyanoethylation	16.5/8.5	Polyester	156	J/m	<sup>13</sup>
Sisal/glass	Acetylation	16.5/8.5	Polyester	165	J/m	<sup>13</sup>
Coir/glass	—	15/30	Unsat. polyester	40	kJ/m <sup>2</sup>	<sup>14</sup>
Hemp/glass	—	30/10	Polypropylene	75	J/m	<sup>15</sup>
Flax/glass	—	16/25	Soybean oil	33.6	kJ/m	<sup>16</sup>
Sisal/glass	—	20/10	Polypropylene	16.7	kJ/m	<sup>18</sup>
Sisal/glass	—	15/15	Polypropylene	18.4	kJ/m <sup>2</sup>	<sup>18</sup>
Sisal/glass	—	10/20	Polypropylene	20	kJ/m <sup>2</sup>	<sup>18</sup>
Sisal/glass	—	—	Unsat. polyester	18	J	<sup>23</sup>
Sisal/jute	—	—	Unsat. polyester	10	J	<sup>23</sup>
Glass/jute/sisal	—	—	Unsat. polyester	12	J	<sup>23</sup>
Bamboo/glass	—	25	Unsat. polyester	32	kJ/m <sup>2</sup>	<sup>24</sup>
Coir/glass	—	45	Unsat. polyester	40	kJ/m <sup>2</sup>	<sup>24</sup>
Jute/glass	—	14	Unsat. polyester	44	kJ/m <sup>2</sup>	<sup>24</sup>
Sisal/glass	—	8	Unsat. polyester	5.76	kJ/m <sup>2</sup>	<sup>24</sup>
Flax/glass	—	50	Polypropylene	43.2	kJ/m <sup>2</sup>	<sup>24</sup>
Flax/glass	—	41	Soybean oil	33.6	kJ/m <sup>2</sup>	<sup>24</sup>
Hemp/glass	—	40	Polypropylene	75	kJ/m <sup>2</sup>	<sup>24</sup>
Palmyra/glass	—	55	Polyester	6.05	kJ/cm <sup>2</sup>	<sup>25</sup>
Basalt/glass	—	33	Epoxy	20.6	J	<sup>38</sup>

(continued)

**Table 4.** (continued)

Composites	NF treatment	Fiber content	Resin	Impact strength	Unit	Reference
Flax/carbon	—	62	Epoxy	26.8	J	40
Banana/sisal/ glass	—	39	Epoxy	12.8	J	51

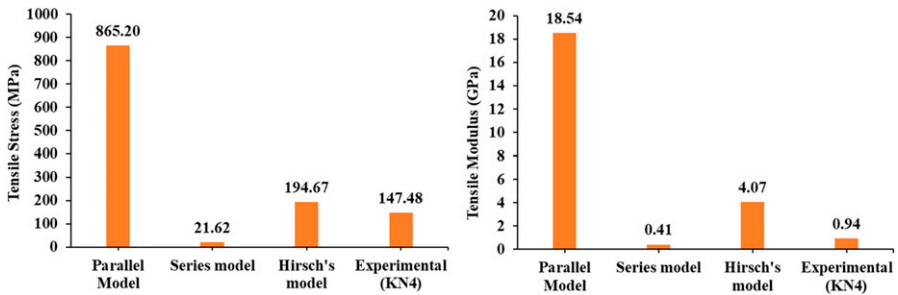**Figure 18.** Variation in theoretical model and experimental tensile properties of the hybrid composites.

of higher strength laminas and lower strength laminas were reinforced at inside and outside of the samples. These groups of laminas absorbed higher impact energy when compared with KN1, KN2 and NN7 samples, due to slowly occurred debonding damage between different laminas.

In other words, from clear comparison between non-hybrid composites samples NN7 and KK8, it was observed that Kevlar-29 fiber woven mat recorded greater impact resistance performance by absorbing more impact energy than banana counterpart. This was exhibited in monolithic composite sample KK8 with maximum impact strength and toughness of 4.35 J and 111.54 KJ/m<sup>2</sup> respectively, which were 5 times higher than that of sample NN7 with 0.87 J and 22.31 KJ/m<sup>2</sup>, respectively. Besides, considering impact damage on composite laminate as a combination effects of compressive, shear and tensile stresses at its impacted top, middle and back regions respectively, hence it was further evident from the best impact resistant hybrid composite sample KN3 system that its K3/NK/N3 design absorbed substantial compressive, shear and tensile stresses, respectively. Moreover, both samples KN4 and KN5 showed that symmetricity of their ply-stacking sequences influenced their competitive impact performances, when compared with sample KN3.

Pen ultimately, Table 4 shows the impact properties of different similar hybrid composites in comparison with the present work (sample KN4). K-29/banana fabric epoxy composites exhibited competitive and higher results than several similar hybrid composite systems. The percentage improvements between sample KN4 and other hybrid

composite samples KN1, KN2, KN3, KN5 and KN6 were 21.74, 33.33, 6.67, 7.69 and 21.74%, respectively.

## Comparison of theoretical model and experimental values

The predicted tensile stresses and moduli, using various theoretical models and experimental values are shown in [Figure 18](#). The obtained tensile stress and modulus from the parallel model were too high when compared with the experimental values obtained from sample KN4, but the values obtained from the series model were too low. This can be attributed to the higher fiber volume fraction of the hybrid composite.<sup>50</sup> Therefore, combination of parallel and series models, known as Hirsch's model, produced acceptance level of tensile properties, because it considered both transfer and longitudinal directional stresses of the hybrid composite. Therefore, this model showed a good agreement with experimental tensile properties of continuous fibers reinforced polymer hybrid composites.

## Conclusions

New K-29/banana fiber mats reinforced epoxy hybrid composite laminate samples, single/non-hybrid K-29 and banana fiber FRP counterparts have been developed, using hand lay-up and compression molding methods and the Mechanical properties were investigated. From the results obtained, the following concluding remarks were highlighted.

1. The KF mat composites exhibited highest strengths (Tensile strength: 147.48 MPa) when compared with other hybrid composite counterparts. The lower strength of banana fiber mat composites can be attributed to the lower strength of their fibers. The composites with both low and high strength fibers have moderate strength when compared with both single fiber composite samples NN7 and KK8.
2. The tensile stress-strain curves of hybrid composite were biased toward stacking sequence of laminas, indicating that the maximum tensile properties were obtained with optimum hybrid composite sample KN4. Its delamination was observed between NF and KF laminas; it was neither observed in NF lamina-NF lamina nor KF lamina-KF lamina. Therefore, the maximum tensile and flexural properties were observed with the same optimal sample KN4 when compared with other hybrid composite systems, as its stress transfer mechanism significantly showed the stress distribution. The experimental tensile stress and modulus of sample KN4 were 147.4800 MPa and 0.9428 GPa, respectively. Whereas, Hirsch's model produced 194.67 MPa and 4.10 GPa. The experimental flexural stress and modulus of sample KN4 were 223.69 MPa and 5.78 GPa, respectively.
3. Also, the maximum ILSS and impact strength were observed with same optimum hybrid composite sample KN4, with a less delamination at the interface between K-29 and banana fiber mats. This can be attributed to the greater interfacial adhesion between the fiber and matrix. The consecutive accumulation of central

banana layer resulted to a proportional increase in the mechanical properties. The experimental ILSS and impact strength of sample KN4 were 13.98 MPa and 2.80 J, respectively.

4. Hence, sample KN4 depicted better mechanical properties when compared with other hybrid composite samples and previously reported works. In other words, the tensile, flexural and impact properties of our present work were better, when compared with several existing studies on similar hybrid composites, containing natural and synthetic fibers.
5. The tensile properties obtained from Hirsch's model were in good agreement with the experimental values of the hybrid composites. This model showed a better stress transfer between the fiber and matrix.
6. The ply-stacking sequence of Kevlar/banana fiber mat was an important factor for obtaining the higher mechanical properties. The ply-stacking sequence of K2/N4/K2 exhibited higher mechanical properties than other stacking sequences. Hence, this stacking sequence was evidently more suitable for preparing the synthetic/natural fiber mat reinforced polymer hybrid composites.

### Acknowledgements

The authors sincerely appreciate the Department of Mechanical Engineering, Kongu Engineering College, Erode, Tamilnadu, India for the preparation and testing of the composite samples in their laboratories/workshops. The authors acknowledge the funding from Researchers Supporting Project (RSP-2021/355), King Saud University, Riyadh, Saudi Arabia.

### Declaration of conflicting interests

The author(s) declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

### Funding

The author(s) disclosed receipt of the following financial support for the research, authorship, and/or publication of this article: The KSU authors were financially supported by the Researchers Supporting Project (RSP-2021/355).

### Data availability statement

The raw/processed data required to reproduce these findings cannot be shared at this time as the data also forms part of an ongoing study.

### ORCID iDs

TP Sathishkumar  <https://orcid.org/0000-0001-8228-4593>

N Rajini  <https://orcid.org/0000-0002-2337-3470>

Suchart Siengchin  <https://orcid.org/0000-0002-6635-5686>

Faruq Mohammad  <https://orcid.org/0000-0002-9318-9986>

## References

1. Sathishkumar TP, Navaneethakrishnan P, Shankar S, et al. Characterization of natural fiber and composites—a review. *J Reinf Plast Compos* 2013; 32: 1457–1466.
2. Sathishkumar TP, Naveen J and Satheeshkumar S. Hybrid fiber reinforced polymer composites—a review. *J Reinf Plast Compos* 2014; 33: 454–471.
3. Sun K, Qin J, Wang Z, et al. Polyvinyl alcohol/carbon fibers composites with tunable negative permittivity behavior. *Surf Interf* 2020; 21: 100735.
4. Senthilkumar K, Ungtrakul T, Chandrasekar M, et al. Performance of sisal/hemp bio-based epoxy composites under accelerated weathering. *J Polym Environ* 2020; 29: 1–13.
5. Senthilkumar K, Saba N, Rajini N, et al. Mechanical properties evaluation of sisal fibre reinforced polymer composites: a review. *Constr Build Mater* 2018; 174: 713–729.
6. Krishnasamy S, Thiagamani SMK, Kumar CM, et al. Recent advances in thermal properties of hybrid cellulosic fiber reinforced polymer composites. *Int J Biol Macromol* 2019; 141: 1–13.
7. Atiqah A. *Characterization and interface of natural and synthetic hybrid composites*. Elsevier Ltd, 2020.
8. Song JH. Pairing effect and tensile properties of laminated high-performance hybrid composites prepared using carbon/glass and carbon/aramid fibers. *Compos B Eng* 2015; 79: 61–66.
9. Mohan R, Shridhar MK, Rao R, et al. Compressive strength of jute-glass hybrid fibre composites. *J Mater Sci Lett* 1983; 2: 99–102.
10. Varma IK, Krishnan SRA and Krishnamoorthy S. Composites of glass/modified jute fabric and unsaturated polyester resin. *Composites* 1989; 20: 383–388.
11. Kalaprasad G, Mathew G, Pavithran C, et al. Melt rheological behavior of intimately mixed short sisal–glass hybrid fiber-reinforced low-density polyethylene composites. I. Untreated fibers. *J Appl Polym Sci* 2003; 89: 432–442.
12. Pavithran C, Mukherjee PS, Brahmakumar M, et al. Impact properties of sisal-glass hybrid laminates. *J Mater Sci* 1991; 26: 455–459.
13. Mishra S, Mohanty AK, Drzal LT, et al. Studies on mechanical performance of biofibre/glass reinforced polyester hybrid composites. *Compos Sci Technol* 2003; 63: 1377–1385.
14. Joffe R, Andersons J and Wallström L. Strength and adhesion characteristics of elementary flax fibres with different surface treatments. *Compos A Appl Sci Manuf* 2003; 34: 603–612.
15. Li H and Sain MM. High stiffness natural fiber-reinforced hybrid polypropylene composites. *Polym Plast Technol Eng* 2003; 42: 853–862.
16. Morye SS and Wool RP. Mechanical properties of glass/flax hybrid composites based on a novel modified soybean oil matrix material. *Polym Compos* 2005; 26: 407–416.
17. Kumar KS, Siva I, Rajini N, et al. Tensile, impact, and vibration properties of coconut sheath/sisal hybrid composites: Effect of stacking sequence. *J Reinf Plast Compos* 2014; 33: 1802–1812. DOI: [10.1177/0731684414546782](https://doi.org/10.1177/0731684414546782).
18. Jarukumjorn K and Suppakarn N. Effect of glass fiber hybridization on properties of sisal fiber–polypropylene composites. *Compos Part B Eng* 2009; 40: 623–627.
19. Naidu VNP, Kumar MA, Reddy GR, et al. Tensile and flexural properties of sisal/glass fibre reinforced hybrid composites. *Int J Macromol Sci* 2011; 1: 19–22.

20. Ramesh M, Palanikumar K and Reddy KH. Comparative evaluation on properties of hybrid glass fiber-sisal/jute reinforced epoxy composites. *Proced Eng* 2013; 51: 745–750. DOI: [10.1016/j.proeng.2013.01.106](https://doi.org/10.1016/j.proeng.2013.01.106).
21. Ahmed KS, Vijayarangan S and Kumar A. Low velocity impact damage characterization of woven jute-glass fabric reinforced isothalic polyester hybrid composites. *J Reinf Plast Compos* 2007; 26: 959–976.
22. De Rosa IM, Santulli C, Sarasini F, et al. Post-impact damage characterization of hybrid configurations of jute/glass polyester laminates using acoustic emission and IR thermography. *Compos Sci Technol* 2009; 69: 1142–1150.
23. Ramesh M, Palanikumar K and Reddy KH. Mechanical property evaluation of sisal-jute-glass fiber reinforced polyester composites. *Compos Part B Eng* 2013; 48: 1–9. DOI: [10.1016/j.compositesb.2012.12.004](https://doi.org/10.1016/j.compositesb.2012.12.004).
24. Santulli C. Impact properties of glass/plant fibre hybrid laminates. *J Mater Sci* 2007; 42: 3699–3707.
25. Velmurugan R and Manikandan V. Mechanical properties of palmyra/glass fiber hybrid composites. *Compos Part A Appl Sci Manuf* 2007; 38: 2216–2226.
26. Kumar NM, Reddy GV, Naidu SV, et al. Mechanical properties of coir/glass fiber phenolic resin based composites. *J Reinf Plast Compos* 2009; 28: 2605–2613.
27. Thwe MM and Liao K. Effects of environmental aging on the mechanical properties of bamboo-glass fiber reinforced polymer matrix hybrid composites. *Compos Part A Appl Sci Manuf* 2002; 33: 43–52. DOI: [10.1016/S1359-835X\(01\)00071-9](https://doi.org/10.1016/S1359-835X(01)00071-9).
28. Goud G and Rao RN. Mechanical and electrical performance of *Roystonea regia*/glass fibre reinforced epoxy hybrid composites. *Bull Mater Sci* 2012; 35: 595–599.
29. Athijayamani A, Thiruchitrambalam M, Natarajan U, et al. Effect of moisture absorption on the mechanical properties of randomly oriented natural fibers/polyester hybrid composite. *Mater Sci Eng A* 2009; 517: 344–353. DOI: [10.1016/j.msea.2009.04.027](https://doi.org/10.1016/j.msea.2009.04.027).
30. Jacob M, Thomas S and Varughese KT. Mechanical properties of sisal/oil palm hybrid fiber reinforced natural rubber composites. *Compos Sci Technol* 2004; 64: 955–965. DOI: [10.1016/S0266-3538\(03\)00261-6](https://doi.org/10.1016/S0266-3538(03)00261-6).
31. John MJ, Francis B, Varughese KT, et al. Effect of chemical modification on properties of hybrid fiber biocomposites. *Compos Part A Appl Sci Manuf* 2008; 39: 352–363. DOI: [10.1016/j.compositesa.2007.10.002](https://doi.org/10.1016/j.compositesa.2007.10.002).
32. Noorunnisa KP, Mohan RM, Raghu K, et al. Tensile, flexural and compressive properties of sisal/silk hybrid composites. *J Reinf Plast Compos* 2007; 26: 1065–1070. DOI: [10.1177/0731684407079347](https://doi.org/10.1177/0731684407079347).
33. Noorunnisa KP, Ramachandra RG, Raghu K, et al. Tensile, flexural and compressive properties of coir/silk fiber-reinforced hybrid composites. *J Reinf Plast Compos* 2009; 29: 2124–2127. DOI: [10.1177/0731684409345413](https://doi.org/10.1177/0731684409345413).
34. Jawaid M, Khalil HPSA and Bakar AA. Woven hybrid composites : tensile and flexural properties of oil palm-woven jute fibres based epoxy composites. *Mater Sci Eng A* 2011; 528: 5190–5195. DOI: [10.1016/j.msea.2011.03.047](https://doi.org/10.1016/j.msea.2011.03.047).
35. Jawaid M, Abdul Khalil HPS, Hassan A, et al. Effect of jute fibre loading on tensile and dynamic mechanical properties of oil palm epoxy composites. *Compos Part B Eng* 2013; 45(1): 619–624. DOI: [10.1016/j.compositesb.2012.04.068](https://doi.org/10.1016/j.compositesb.2012.04.068).

36. Sathishkumar T, Navaneethakrishnan P, Shankar S, et al. Mechanical properties of randomly oriented snake grass fiber with banana and coir fiber-reinforced hybrid composites. *J Compos Mater* 2012; 45(18): 2181–2191. DOI: [10.1177/0021998312454903](https://doi.org/10.1177/0021998312454903).
37. Reis PNB, Ferreira JAM, Antunes F V, et al. Flexural behaviour of hybrid laminated composites. *Compos Part A Appl Sci Manuf* 2007; 38: 1612–1620.
38. Sarasini F, Tirillò J, Valente M, et al. Effect of basalt fiber hybridization on the impact behavior under low impact velocity of glass/basalt woven fabric/epoxy resin composites. *Compos Part A Appl Sci Manuf* 2013; 47: 109–123. DOI: [10.1016/j.compositesa.2012.11.021](https://doi.org/10.1016/j.compositesa.2012.11.021).
39. Valença SL, Griza S, de Oliveira VG, et al. Evaluation of the mechanical behavior of epoxy composite reinforced with Kevlar plain fabric and glass/Kevlar hybrid fabric. *Compos Part B Eng* 2015; 70: 1–8.
40. Sarasini F, Tirillò J, D’Altilia S, et al. Damage tolerance of carbon/flax hybrid composites subjected to low velocity impact. *Compos Part B Eng* 2016; 91: 144–153.
41. Ismail AS, Jawaid M, Sultan MTH, et al. Physical and mechanical properties of woven Kenaf/Bamboo fiber mat reinforced epoxy hybrid composites. *BioResources* 2019; 14: 1390–1404.
42. Tripathi P, Gupta VK, Dixit A, et al. Development and characterization of low cost jute, bagasse and glass fiber reinforced advanced hybrid epoxy composites. *AIMS Mater Sci* 2018; 5: 320–337.
43. Chaudhary V, Bajpai PK and Maheshwari S. Studies on mechanical and morphological characterization of developed jute/hemp/flax reinforced hybrid composites for structural applications. *J Nat Fibers* 2018; 15: 80–97. DOI: [10.1080/15440478.2017.1320260](https://doi.org/10.1080/15440478.2017.1320260).
44. Prajapati P, Sharma C, Rana RS, et al. Evaluation of mechanical properties of coir and glass fiber hybrid composites. *Mater Today Proc* 2018; 5: 19056–19062.
45. Dalvand A and HatamiChegini HAS. Experimental study of the effect of dynamic loading on rectangular armed panels made of self-compacting composite fiber and lattice sheets. *J Struct Eng* 2021; 8(1): 131–151.
46. Azeem M, Ya H H, Alam M A, et al. Macroscale assessment of low-velocity impact on hybrid composite laminates. *Mater Sci Technol* 2020; 5210(6): 1101–1111.
47. Talib ARA, Ramadhan AA, Rafie ASM, et al. Influence of cut-out hole on multi-layer Kevlar-29/epoxy composite laminated plates. *Mater Des* 2013; 43: 89–98.
48. Ramadhan AA, Talib ARA, Rafie ASM, et al. High velocity impact response of Kevlar-29/epoxy and 6061-T6 aluminum laminated panels. *Mater Des* 2013; 43: 307–321.
49. Fan Z, Santare MH and Advani SG. Interlaminar shear strength of glass fiber reinforced epoxy composites enhanced with multi-walled carbon nanotubes. *Compos Part A Appl Sci Manuf* 2008; 39: 540–554.
50. Kalaprasad G, Joseph K and Thomas S. Theoretical modelling of tensile properties of short sisal fibre-reinforced low-density polyethylene composites. *J Mater Sci* 1997; 32: 4261–4267.
51. Arthanarieswaran VP, Kumaravel A and Kathirselvam M. Evaluation of mechanical properties of banana and sisal fiber reinforced epoxy composites: influence of glass fiber hybridization. *Mater Des* 2014; 64: 194–202.