

# Toward Sustainable Wearable Electronic Textiles

Marzia Dulal, Shaila Afroj,\* Jaewan Ahn, Yujang Cho, Chris Carr, Il-Doo Kim,\* and Nazmul Karim\*



Cite This: <https://doi.org/10.1021/acsnano.2c07723>



Read Online


ACCESS |

Metrics & More

Article Recommendations

**ABSTRACT:** Smart wearable electronic textiles (e-textiles) that can detect and differentiate multiple stimuli, while also collecting and storing the diverse array of data signals using highly innovative, multifunctional, and intelligent garments, are of great value for personalized healthcare applications. However, material performance and sustainability, complicated and difficult e-textile fabrication methods, and their limited end-of-life processability are major challenges to wide adoption of e-textiles. In this review, we explore the potential for sustainable materials, manufacturing techniques, and their end-of-the-life processes for developing eco-friendly e-textiles. In addition, we survey the current state-of-the-art for sustainable fibers and electronic materials (i.e., conductors, semiconductors, and dielectrics) to serve as different components in wearable e-textiles and then provide an overview of environmentally friendly digital manufacturing techniques for such textiles which involve less or no water utilization, combined with a reduction in both material waste and energy consumption. Furthermore, standardized parameters for evaluating the sustainability of e-textiles are established, such as life cycle analysis, biodegradability, and recyclability. Finally, we discuss the current development trends, as well as the future research directions for wearable e-textiles which include an integrated product design approach based on the use of eco-friendly materials, the development of sustainable manufacturing processes, and an effective end-of-the-life strategy to manufacture next generation smart and sustainable wearable e-textiles that can be either recycled to value-added products or decomposed in the landfill without any negative environmental impacts.

**KEYWORDS:** wearable electronics, e-textiles, sustainability, biodegradability, recyclability, sustainable electronics, smart textiles, life cycle analysis

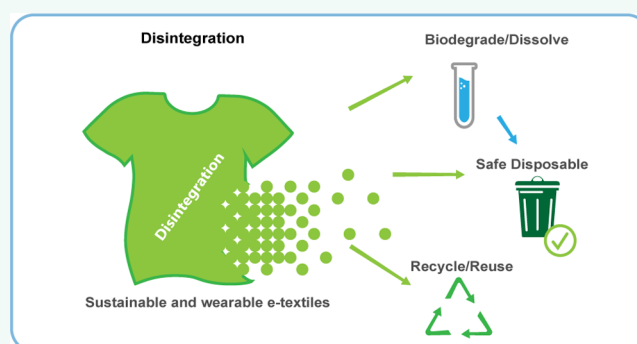

Smart wearable electronic textiles (e-textiles) are becoming increasingly attractive due to their intriguing electrical, thermal, and optical functionalities, as well as being able to collect physiological data in real-time for continuous health monitoring applications.<sup>1–4</sup> Indeed, what makes smart wearable e-textiles exciting is their potential for developing highly innovative and intelligent clothing that can function as sensors, heaters, energy generating and storage devices simultaneously.<sup>1</sup> Multifunctional wearable e-textiles that can detect and distinguish multiple different types of stimuli, while also collecting and storing a wide range of signals all using just a single device, are of high value for personalized healthcare applications.<sup>5–7</sup> However, the significant barriers for wide adoption of e-textiles are poor material performance and sustainability, complicated and time-consuming fabrication methods, numerous toxic wastes generated from manufacturing processes, and their limited end-of-life portion processability.<sup>8–11</sup>

With an estimated 92 million tonnes of textile waste produced annually,<sup>12–14</sup> the textile industry is thought to be the second largest environmental polluter behind the oil sector,<sup>15,16</sup> with an equivalent to a garbage truck full of clothing being dumped into the ground every second.<sup>17</sup> Although 95% of textiles are fully recyclable,<sup>18</sup> ~85% of all textiles are still dumped into landfills.<sup>17,19,20</sup> The incorporation of electronics into existing textiles to produce e-textiles will therefore make end-of-life processing even more complicated and challenging.<sup>10</sup> Indeed, wearable e-textiles containing nontextile components, such as electronics, batteries and

**Received:** August 3, 2022

**Accepted:** November 10, 2022

interconnections, are challenging or even impractical to disassemble. For example, current electronics can comprise of up to 57 types of components,<sup>21</sup> each of which requires specific recycling methods due to their varying physical/chemical properties. Many components are valuable, while others are hazardous heavy metals and halogenated organic compounds that can impact individual health and generate environmental risks.<sup>22,23</sup> Therefore, there is a clear unmet need for an integrated product design, the use of eco-friendly materials, the development of sustainable manufacturing processes, and an effective end-of-the-life strategy to encourage the manufacture of the next generation of smart and sustainable wearable e-textiles that can either be recycled to value-added products or decomposed in the landfill without any negative environmental impacts.

Here, we review the potential of sustainable materials and manufacturing techniques for developing eco-friendly wearable e-textiles that can either be decomposed or recycled after use. Within the discussion, we examine the nature of sustainable fibers including biosynthetic and recycled fibers, the modulation of their electrical properties using sustainable electronic materials (i.e., conductors, semiconductors, and dielectrics) to serve as different components in wearable e-textiles, and the potential for innovative manufacturing techniques that facilitate sustainable production plants based on waterless technologies and lower energy consumption. In addition, standardized parameters for evaluating the sustainability of e-textiles are established, such as life cycle analysis (LCA), biodegradability, and recyclability. Finally, the current development trends, as well as future research directions for wearable e-textiles are identified.

## SUSTAINABLE MATERIALS

**Sustainable Fiber Materials.** The major component in smart wearable e-textiles are either natural (e.g., cotton, flax) or man-made (e.g., polyester, acrylic) fibers.<sup>24</sup> Polyester is the most widely used textile fiber, comprising ~51% (~54 million tonnes) of total consumption. Cotton is the second most widely used fibers at 25% (~26 million tonnes) in global consumption.<sup>12</sup> Although cotton is a naturally produced cellulosic fiber material that is also biodegradable,<sup>25</sup> the manufacturing of conventional cotton fibers is regarded as environmentally unfriendly<sup>26</sup> and involves significant water consumption.<sup>27</sup> In general, a significant amount of water (>20,000 L/kg of fibers) is required to process cotton textiles,<sup>28</sup> which has significant environmental impacts on most cotton-based textiles producing countries such as Bangladesh, India, and China, where there is already a shortage of fresh drinking water.<sup>29</sup> Additionally, cotton fibers consume ~10% and 25% of the global pesticides and insecticides,<sup>30</sup> respectively, with a large portion<sup>31</sup> of the pesticides being discarded as runoff into rivers<sup>32</sup> or the soil,<sup>33</sup> which has become a threat to the environment and marine life.<sup>32</sup> Nevertheless, man-made cellulosic fibers (such as viscose, modal, and lyocell) could potentially play a significant role in realizing sustainable and circular fashion by becoming carbon sinks and enhancing public resilience and benefits.<sup>34,35</sup>


Polyester, the most commonly used textile fiber, is man-made and derived from nonrenewable fossil fuels. The raw materials for polyester fibers, such as polyethylene terephthalate (PET), are produced by converting crude oil into petrochemicals, during which toxins such as ethylene, propylene, butadiene, and methanol are released into the

atmosphere<sup>36</sup> and pose severe risks to human life and the ecosystem at large.<sup>37</sup> Additionally, polyester fibers are not biodegradable, and their production process is also a highly energy-intensive. For example, ~125 MJ of energy is required to produce 1 kg of polyester fiber, with a staggering CO<sub>2</sub> emission level of 14.2 kg/kg.<sup>38,39</sup> Considering the finite supply of resources on Earth, the rapidly growing global population, and the shrinkage of arable land available for cultivation, there is a clear need for an alternative approach to textile manufacturing based on sustainability.<sup>40,41</sup>

Sustainability is a multifaceted concept involving the integration of better usage of materials, reducing the overall carbon footprints, and balancing the use of renewable resources and biodegradable products with an efficient recycling/remanufacturing economy. Through this holistic approach, a global solution to fiber production, textile manufacturing, and sustainability can be achieved, and the main factors are identified in Figure 1a. The development of sustainable fibrous polymers will enable conservation of limited natural resources and provide a potential solution to the key challenges generated by plastic-based synthetic polymers. Various research strategies have been previously identified which will contribute toward developing an integrated strategy.<sup>42</sup>

Biopolymers have emerged as a latest class of sustainable and natural<sup>44</sup> alternatives to current fossil-fuel-based fibers.<sup>45</sup> “Bio-based” refers to the origin of the material which is either partly or totally bio-based. Biopolymers are derived from renewable resources, typically plants or plant-derived matter (e.g., sugar cane, cassava, corn). Note that the label “bio-based” only indicates the source of the materials and does not address implications about its end-of-life. In contrast, biodegradable plastics undergo chemical processes for their conversion into natural materials (e.g., carbon dioxide, biomass, and water) with the aid of microbes that are present in the environment. The environmental conditions must be optimal for biodegradation to occur efficiently. Though not all bio-based plastics are biodegradable, some exhibit biodegradable characteristics, together physical properties that are not dissimilar from petroleum-based plastics.

Examples of bio-based and biodegradable bioplastics include starch-derived polylactic acid (PLA), polyhydroxyalkanoates (PHA), microbe-derived polyhydroxybutyrate (PHB), and polybutylene succinate (PBS).<sup>46</sup> However, most of the current bio-based plastics are non-biodegradable, which causes waste management problems.<sup>47</sup> For instance, bio-based “drop-in” polyethylene (PE), polypropylene (PP), PET, thermoplastic polyester elastomers (TPC-ET), and bio-based polyamides (PA) are all non-biodegradable bioplastics derived from renewable natural resources.<sup>48</sup> In contrast, some fossil-fuel-based plastics such as polybutylene adipate terephthalate (PBAT) and polycaprolactone (PCL) exhibit biodegradable characteristics despite not originating from bio-based sources.<sup>49–51</sup> PBAT is fully biodegradable when composted due to the presence of butylene adipate groups. However, it should be noted that the terephthalate chain sections, which provide the material’s high stability and mechanical properties, do not degrade in marine and fresh water. In addition, while some plastics (fossil-fuel-based and non-biodegradable) may be recyclable to some extent,<sup>52</sup> after a finite number of cycles they eventually end up in the landfill as trash.<sup>53,54</sup> Therefore, the selection of the “best” sustainable fibrous materials, as listed in Figure 1b, provides an opportunity to establish a long-

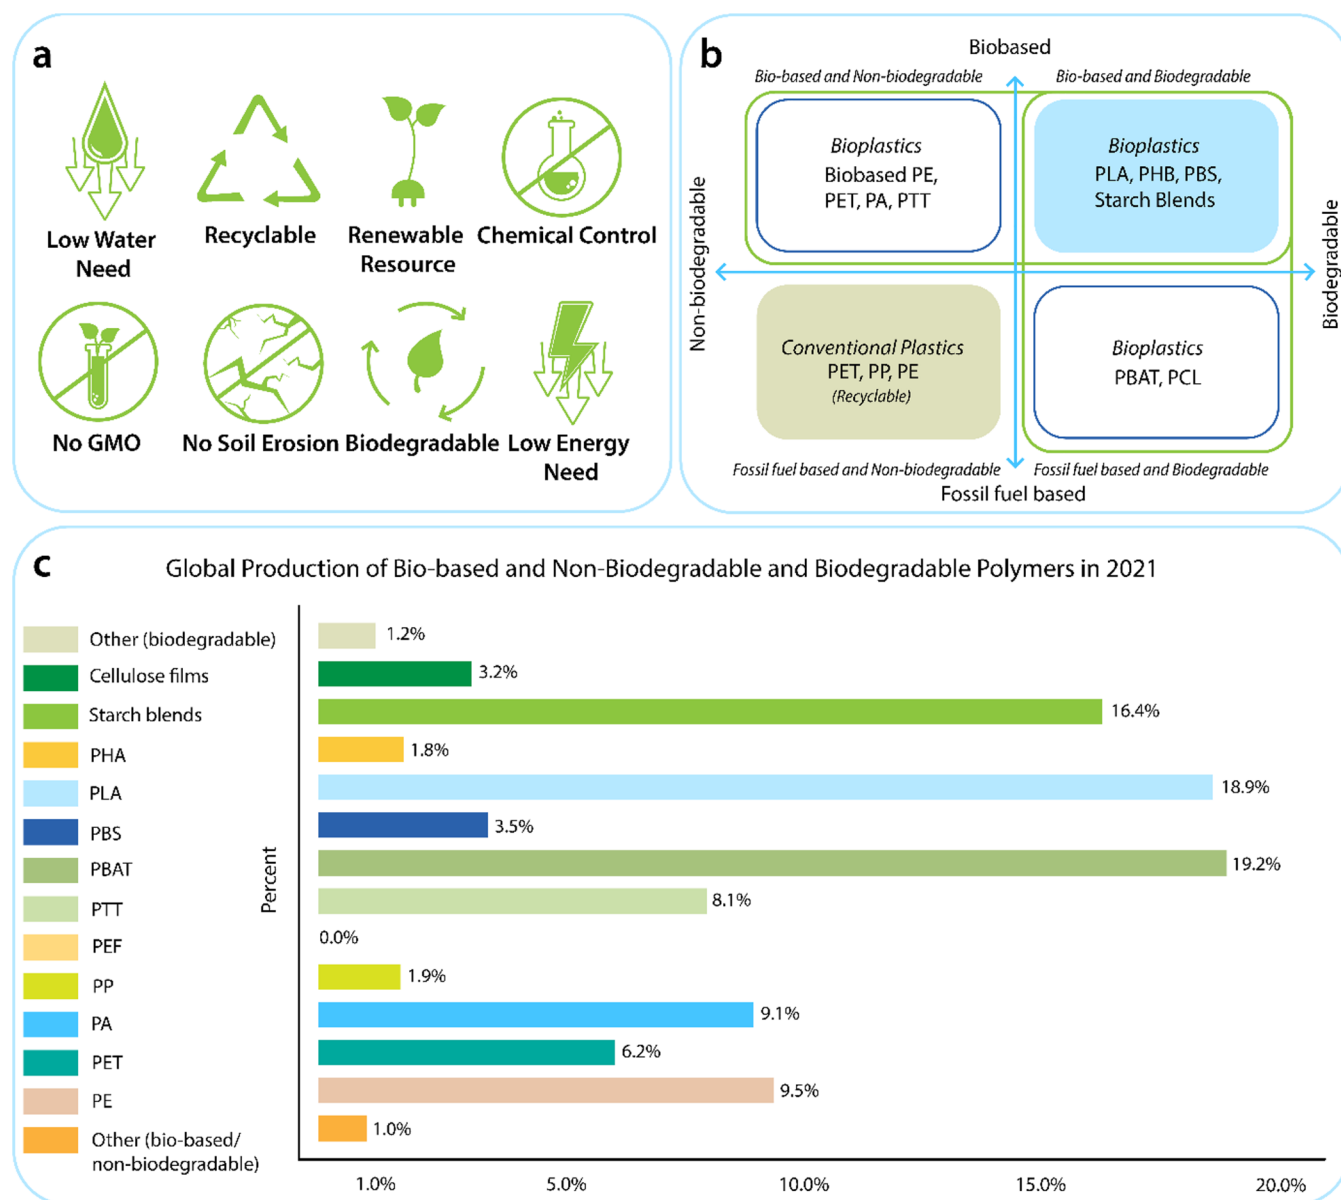

**Figure 1.** (a) Criteria for sustainable fibers. (b) Classification of plastic. (c) Global production of bio-based non-biodegradable and biodegradable polymers in 2021.<sup>43</sup>

term strategy for the design of sustainable and multifunctional wearable e-textiles but also for the betterment of the environment, society, and the global economy. Thus, plastic polymers can be classified into four groups and the global production data,<sup>43</sup> shown in Figure 1c, highlights the significant production of PBAT in 2021.

The growing concerns over environmental issues such as polymer waste, high energy wastage, greenhouse gas emission, marine plastic pollution, and other problems associated with plastic production<sup>55</sup> have focused interest in the recycling of PET not only in the plastics industry but also within the healthcare wearable electronic devices sector.<sup>56</sup> PET bottles can be recycled, with 94% of UK city councils now collecting such bottles either from the domestic home or at recycling centers.<sup>57</sup> Nowadays, the importance of recycling PET bottles through both mechanical and chemical processes has been recognized,<sup>58</sup> as well as the need to establish circular usage and improved end-of-life disposal.<sup>59</sup> PET, a semicrystalline thermo-

plastic, is the most widely used polymer for industrial applications such as textile fibers and food packaging because of its superior mechanical, chemical and barrier properties, combined with good processability,<sup>60</sup> low cost, and recyclability.<sup>61</sup> Indeed, postconsumer PET bottles have become a popular choice for recycling into useful products such as textile fibers due to their chemical stability, mechanical strength, and fluid resistance. In addition, the thermoplasticity of PET provides a high degree of malleability and ductility at relatively low temperatures to allow easy molding and shaping. Together with its high biocompatibility, recycled PET (rPET) should be attractive and advantageous for use in wearable devices. rPET, which is mainly made by mechanical<sup>62</sup> or chemical<sup>63</sup> recycling of postconsumer PET bottles,<sup>64–67</sup> is a sustainable choice for manufacturing textile fibers<sup>68</sup> and meets the criteria for recyclable sustainable fibers either fully or partially, as illustrated in Figure 2.

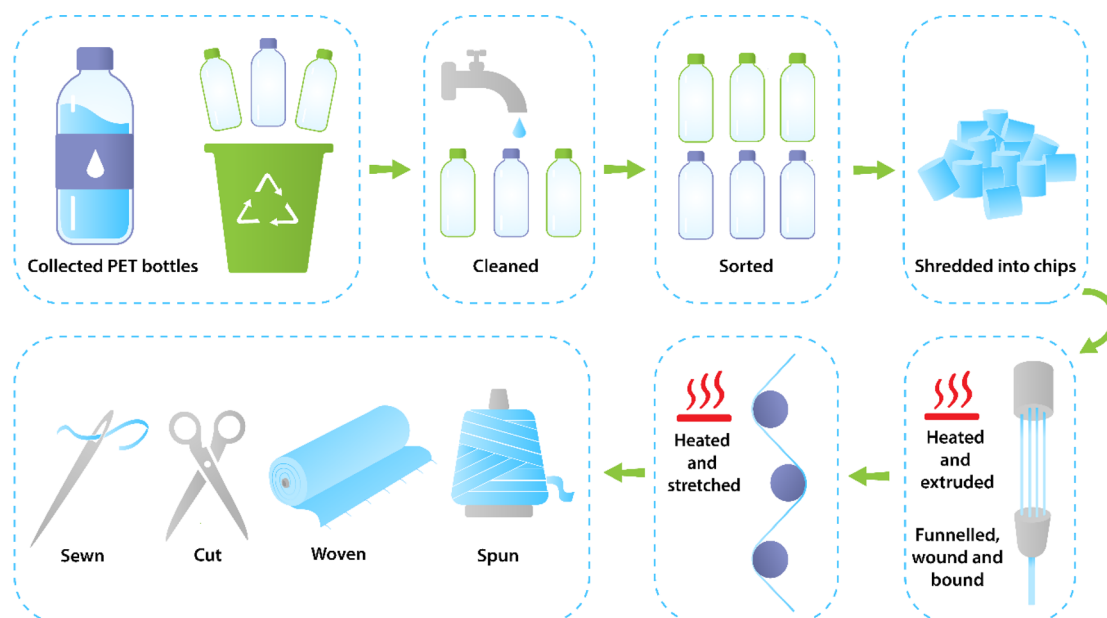


Figure 2. Process flow: from collection of PET bottles to recycling into garments.<sup>64–67</sup>

Many textile businesses have already started to move away from virgin PET to rPET-based polyester fabrics with the benefits of less environmental impact. In fact, reports have confirmed that rPET consumes  $\sim 70\%$  less energy, and the  $\text{CO}_2$  emissions are  $\sim 75\%$  lower when compared to that of virgin polyester production.<sup>69,70</sup> However, like virgin polyester, rPET-based textiles are non-biodegradable. Additionally, rPET polymers often suffer from poor mechanical performance due to the mixing of different grade polymers and subsequent thermal aging, resulting in phase separation, which adversely affects the material properties.<sup>71,72</sup> Therefore, there remains a need for improving the melt-processability of rPET to adequately facilitate recycling. The performance modification techniques for recycled thermoplastic polymers have extensively been reviewed<sup>71</sup> and include the use of additives such as compatibilizers, coupling agents, and impact modifiers. Among them, carbon nanotubes (CNTs) and graphene are of particular interest for wearable e-textile applications due to their capability in forming electronic networks coupled with their extraordinary mechanical and thermal properties. Such materials have already been used as both reinforcing agents and compatibilizers in polymer blends. Previously, we demonstrated significant improvements in mechanical and electrical properties of textiles fibers, yarns, and fabrics by adding graphene-based materials such as graphene oxide (GO), reduced graphene oxide (rGO), and graphene-based flakes,<sup>9,73–75</sup> which can be extended to recycled polymers such as rPET to enhance its performance and functionality.

Further, in a recent study, a textile-based electrode was developed for a wearable supercapacitor by incorporating rGO flakes and polypyrrole (PPy) particles onto PET fabric, thus demonstrating its potential as a suitable substrate for wearable e-textiles applications.<sup>76</sup> In another study,<sup>77,78</sup> flexible MgO barrier magnetic tunnel junctions exhibited improved performance on PET substrate. The benefit of PET is its ultraflexibility and can be shaped into tubular form without compromising the performance of embedded electronics potentially,<sup>77,79</sup> which could facilitate for the development of various lightweight and flexible wearable devices.<sup>80</sup> The enormous

potential for PET materials incorporating active conductive materials has been a focus for wearable electronics, e-textiles and e-skin in the application of strain sensors, smart clothes, health monitoring sensors, and human-machine interaction systems (Table 1). By effectively integrating the recyclability of PET with its compatibility with electronic components, PET offers many opportunities as the base substrate for wearable electronic devices.

Recently, bio-based and biodegradable polymers have emerged as latest classes of sustainable and natural<sup>44</sup> materials (Figure 1b) as alternatives to the current fossil fuel-based fibers.<sup>45</sup> The so-called “biopolymers” can degrade at a much faster rate than other conventional plastics.<sup>83</sup> In addition, biodegradable bio-based polymers decompose into carbon dioxide, water, and other naturally occurring materials, leaving no residual toxins. Therefore, biopolymers could potentially meet growing demands for environmentally sustainable materials<sup>48</sup> (Figure 1a) for fiber production.<sup>84</sup> Furthermore, such bio-based and biodegradable polymers can address the problems of resource depletion<sup>85–87</sup> and the environmental impacts of a fast-growing economy.<sup>85,88,89</sup>

Previously, bio-based polymers have been mainly derived from agricultural feedstocks such as corn, potatoes, and other carbohydrate feedstocks.<sup>90,91</sup> In addition, there have been extensive technological developments in renewable resource-based biopolymers, and their commercial applications have been studied.<sup>92,93</sup> There are several methods that have been advanced over the years to derive bio-based and biodegradable polymers.<sup>43</sup> The most commonly used production routes, Figure 3, includes<sup>81,342</sup> (a) chemical conversion of natural raw materials into reactive monomers followed by polymerization, such as the process of obtaining nylon (amino acids) from castor seeds; (b) direct extraction of biopolymers such as starch and cellulose, followed by thermopressing/molding to derive thermoplastic starch polymers (TSPs); (c) further functionalization of extracted biopolymers by processes such as acetylation, carboxymethylation, and phosphorylation to make calcium alginate (CA), carboxymethyl cellulose (CMC), and cellulose diphenyl phosphate, respectively, which are then



Table 1. Summary of PET and PLA Polymers Used and Their Performance for Wearable Electronics

type of fiber/yarn/textile substrate	type of conductor materials	integration in textiles fabrication method	performance criteria	smart wearable electronic functionality	ref
PET	Graphene Nanoplatelets (GNPs)	spray coating	gauge factor (GF):150	piezoresistive - strain sensor	113
PET substrate	conductive Ag and CNT ink	flexographic printing		printed wearable sensors	114
PET substrate	active material: gold nanoparticles	inkjet		position: facemask printed respiratory rate sensors: resistive humidity	115
PET	silver	screen		position: wrist printed temperature sensors: resistive	116
PET	CNTs and PEDOT: PSS	screen	temperature sensitivity: 0.13%/°C	position: chest-resistive	117,118
PET	polymer paste	screen	capacitive: 9 kHz/°C	capacitive sensor	119
PET	CNTs	screen		position: chest printed heart rate and SpO <sub>2</sub> sensors: ECG/3 electrodes	117,118
PEN, PET, ITO-coated glass	organic materials	blade-coating spin-coating	error: HR: 1%	position: finger HR/SpO <sub>2</sub>	120
PET substrate	GNPs		up to 65% extensibility with a gauge factor of 62.5 High sensitivity, long-term stability, reproducibility and durability.	piezoresistive strain sensor, smart clothes, touch-based flexible screens, flexible sensors, electronic skin, health monitoring, human/machine interaction system	121
polyester (PET) fibers	scaffold PU fiber	coating with GO, winding	showing GF of 10 within 1% strain and high stretchability of 280%	strain sensor	122
PET yarns	coated with intrinsically conductive polymers PEDOT encapsulated in PMMA	fabrication: in situ polymerization	interconnectivity between the PET/PEDOT monofilaments enhanced on straining, decreasing resistance resistance: ~600 Ω/cm GF: -0.76 (20% strain), 0.665 (50% strain), -0.244 (70% strain)	fiber-based strain sensors	123,124
PU core/PET wrapper fiber yarns and graphene oxide (GO)	coated with graphene	dip-coating, when strained, GO/PET winding fibers separated, contact area decreased, resistance increased	durability - withstood 1000 cycles with stable GF conductivity: ~0.15 S/m GF: 10 (1% strain), 3.7 (50% strain) response unchanged after 1000 cycles detection limit 0.2% strain response time: <100 ms reproducible signal up to 1310,000 cycles GF: ~3.2(30% strain)	health and motion monitoring detecting full range of human activities fiber-based strain sensors	122,124
PU core/PET wrapper fiber yarns	coated with metals AgNWs	dip-coating, when strained, AgNW layer cracked, resistance increased	sensed up to 50% strain strain detection limit 1%	e-skin: fiber-based strain sensors	124,125
PU core/PET wrapper fiber yarns and	coated with metals: AgNWs, silicone	dip-coating, when load applied to fiber crossover point, dielectric thickness decreased, resulting in change in capacitance	S: 0.096 kPa <sup>-1</sup> (<0.1 kPa) and 1.1 MPa <sup>-1</sup> (0.1–10 kPa) durability: 10,000 cycles extensibility: up to 30–40% dynamic sensing range up to 50 kPa detection limit of 1.5 Pa response time ~32 ms	e-skin: fiber-based pressure sensors application	124,125
PET nonwoven fabric substrate	reduced graphene oxide (RGO)	suction filtration	stability (cycle):150 (10% strain) electrothermal property (about 50 °C under a voltage of 6 V)	strain sensor:monitor human wrist movements	126,127
weft-knit polyester fabric	RGO	dip-coating	GF : 1.7 (<15% strain, x-direction), 26 (<8% strain, y-direction) sensing range (%): up to 50	strain sensor: monitor physiological activities of a human body	127,128

Table 1. continued

type of fiber/yarn/textile substrate	type of conductor materials	integration in textiles fabrication method	performance criteria	smart wearable electronic functionality	ref
polyester knitted elastic band	RGO	dip-coating	stability cycle: 500 (7.5% strain, x-direction), 500 (5% strain, y-direction) GF: 34(0–20% strain), 5 (20–50% strain) sensing range (%): 0.2–50 stability (cycle): >6000(30% strain) GF:10 (<1% strain), 3.7 (<50% strain) sensing range (%): up to 100 stability (cycle): 10,000 (30 and 50% strain)	strain sensor: monitoring of large- and small-scale human body movements	127,129
double-covered yarn (PU core fiber and polyester fibers)	RGO	dip-coating	providing reliable electroanalytical performance with high flexibility, biocompatibility, wearability, and high detection sensitivity even under different motion states	strain sensor: monitoring of a wide variety of human activities and complex robot movements	122,127
PET or polyester fiber	graphene films	wet-laid method	excellent electrical and thermal conductivities, suitable flexibility	flexible electrode for ECG monitoring	130
PET-based nonwoven material	graphite fillers			electrical devices and the potential for use in wearable devices	131
PE/PET nonwoven fabrics	graphene layer, silver nanoparticles (AgNPs)	two-step method; dipping process, magnetron sputtering	KH-560 treatment improves the interfacial adhesion between graphene and the PE/PET continuing to the enhanced the durability of the conductive composite fabrics.	wearable electronics applications	132
PET fiber surfaces	aqueous mixture of graphene oxide and AgNO <sub>3</sub>	dip-coating and subsequent reduction with hydrazine, thermal annealing (<200 °C)	graphene and AgNPs gave GPP and AGPP excellent thermal stability	improve the conductivity and durability of modified PET fabrics	133
SiO <sub>2</sub> /Si wafer/Cotton fabric/PET fabric	chemical vapor deposition (CVD)-grown graphene	collamination, wet transfer method	good durability of rGO coating on PET via a series of wash fastness and bending tests	graphene e-fabric wearable chemical sensor showed a sensitivity up to 53% for nerve chemical warfare agents (GD)	134
PET substrates	graphene type: GO films		show smooth and homogeneous morphology, The sheet resistances of graphene on PET showed values comparable to those of graphene on the wafer	sensor types: piezoresistive	135,136
PET Substrates	CVD-graphene		motion detection by wearable sensors based on graphene materials		
PET substrates	bilayer graphene		motion types: elbow bending	capacitive	136,137
three-arm stereo-complex PLA (tascPLA) substrate/dielectric layers	organic field-effect transistors (OFET)	spin-coating or dip-coating	demonstrate stable mechanical and electrical performances	piezoresistive biomaterial-based OFET, skin-like temperature sensor array	136,138 139
PP, PLA, PP/PLA composite	polydopamine (PDA)-treated and poly(3,4-ethylenedioxythiophene);poly(styrenesulfonate)	dip-coating, wet-spinning, scalable fabrication	strain sensing to monitor the tiny movement of human motion for public safety, healthcare, artificial muscles, military, space exploration, stretchable displays, sports, and consumer fitness	biodegradable, highly stretchable and wearable conductive yarn	112

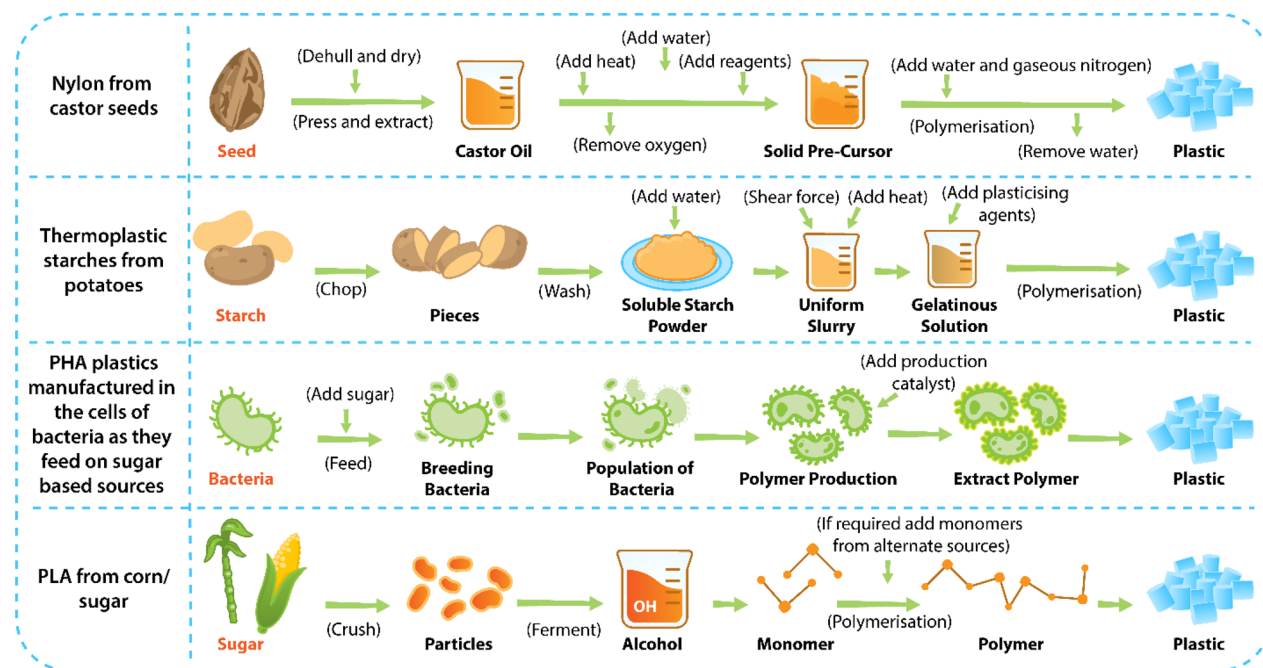


Figure 3. Different production routes for bio-based and biodegradable polymers.<sup>81,82</sup>

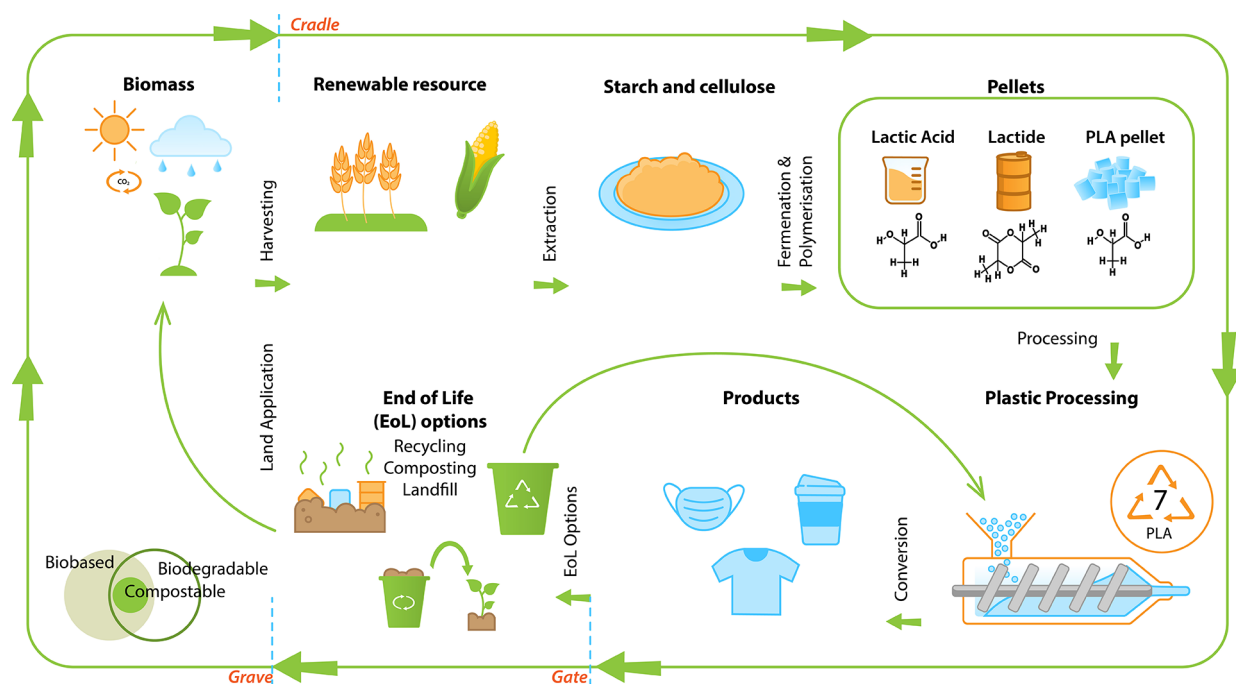


Figure 4. Life cycle of PLA from cradle to cradle.

polymerized further;<sup>94</sup> (d) hydrolysis of extracted biopolymers to sugars for the bacterial synthesis of polyesters, such as polyhydroxyalkanoates (PHA); (e) fermentation of the aforementioned biopolymer-derived sugars to lactic acids followed by their direct polycondensation or ring-opening condensation to PLA.<sup>95</sup>

According to standards developed by the Biodegradable Products Institute,<sup>96</sup> PLA is an excellent biodegradable material as well as a green bio-based polymer. However, PLA will only degrade into carbon dioxide and water within a controlled composting environment,<sup>97</sup> making it more sustainable than other types of plastics derived from fossil

fuels and any other bio-based and biodegradable polymers. PLA is one of the most prevalent pervasive bio-based polymers for scores of usages, with diverse end-of-life (EoL) options (Figure 4), including recycling, landfilling, and industrial composting.<sup>98</sup> In spite of this attractive performance and process flexibility, PLA does have some drawbacks. PLA are decomposed or sent to landfill after their useful life, due to an inadequate PLA recycling facility. PLA in this form is often considered “unidentifiable” and serves as a contaminant for the recycling of other plastics. Therefore, nonrecycled PLA products must be processed in an industrial compost environment to fully utilize its biodegradability, otherwise it

may take many hundreds of years to decompose<sup>99</sup> and may pollute the environment.

Nonetheless, by its nature, PLA possesses many desirable material properties and processing benefits.<sup>100</sup> Thermoplastic PLA has a lower melting point than other petrochemical plastics and requires less energy for conversion, making it compatible with blow-molding and melt-spinning. PLA-based fabrics can also be pigment printed and thermally cured at different conditions.<sup>101</sup> In addition, such fabrics can be inkjet-printed with UV-curable inks with good color strength and fastness properties.<sup>102</sup> The outstanding processability of PLA makes it a preferred material for 3D printing. Also, while there are some concerns over the adsorption of viruses and molds to the surface<sup>103</sup> of conventional biodegradable plastics,<sup>104</sup> PLA shows excellent antibacterial,<sup>105,106</sup> and antifungal properties. Furthermore, the PLA film also offers good air permeability,<sup>107</sup> oxygen permeability<sup>108,109</sup> and odor isolation.<sup>110</sup> All these qualities promote PLA as a highly suitable candidate for use in wearable e-textiles. In a recent study, flexible and conductive membranes with antibacterial properties have been reported, showing potential for wearable movement sensing applications.<sup>111</sup> The processability of PLA enables various form factors, such as PEDOT:PSS-coated conductive and stretchable PLA yarns could be used for detecting small movements in human motions.<sup>112</sup>

**Sustainable Electronic Materials.** Wearable e-textiles incorporate electronic components and interconnections within their fibrous network<sup>4</sup> to accomplish specialized tasks such as health monitoring. E-textiles have attracted considerable academic, military, and commercial interests because of their potential applications in defense uniforms, sportswear, and medical clothing.<sup>140–142</sup> Much research has been carried out to integrate electronics into clothing for various applications including sensors,<sup>122,143–145</sup> energy storage devices,<sup>79,146</sup> transistors,<sup>147</sup> heating textiles, electrostatic discharge clothing,<sup>148</sup> physiological monitoring,<sup>131</sup> photovoltaic devices,<sup>149,150</sup> and many other critical applications. Importantly, for the end user, the e-textiles should offer the same properties as conventional textiles, such as washability, flexibility, low weight, and robustness, to be considered as fully “wearable.” These features depend on the properties of the electronic materials as well as the fibrous materials, which may be influenced by the post-treatment and integration techniques.<sup>151</sup> Such smart e-textiles are manufactured either by printing or coating of electronic materials on the textiles surface or by incorporating such electronic materials within the fibers that construct the fabric. As a result, electronic materials and their applications in e-textiles are expected to drive the demand for promising textiles, fibers, fabrics, and processing technologies. However, even with their level of importance, there is little appreciation of how the use of electronic/conductive materials, such as gold, silver and copper, can involve large energy consumption, carbon emissions, over-consumption of natural resources and environmental pollution. Therefore, innovations in sustainable technologies are required in this sector, such as developing appropriate recycling strategies, utilizing biomaterials where possible, and discovering innovative materials. This review focuses on different electronic materials, including conductors, semiconductors, and dielectrics, identifying the challenges with their design, materials selection, and environmental impacts that must be overcome to achieve sustainability.

**Conductors.** Conductors are the most important component in e-textiles, operating the electronics and facilitating the added functionalities. Metal inks based on silver (Ag),<sup>152</sup> copper (Cu),<sup>153</sup> or gold (Au)<sup>154</sup> are right away the uttermost frequently used materials considering their high electrical conductivity ( $\sigma$ ), commonly  $\sim 10^5$  S/m.<sup>155</sup> However, such inks are neither cheap<sup>156</sup> nor environmentally friendly.<sup>156</sup> They are not biocompatible<sup>157</sup> and frequently need higher sintering temperatures,<sup>158</sup> which limited the choice of textiles substrate. Therefore, there remains a need for an inexpensive and eco-friendly conductive materials that can be sintered at lower temperature for establishing sustainable wearable e-textiles. In the section that follows, we review the characteristics of such potentially sustainable metal-based, conductive polymer-based and carbon-based materials that are electrically conductive as well as some of their prospective uses in biodegradable wearable electronics.

**Metal-Based Conductors.** Electrode materials transport electrical charge carriers across electronic or sensing devices, as well as the external circuit. Conductors with immense electrical conductivities ( $>10^{-1}$  S/cm) are required to underpin a high-performance electronic device. It is becoming extremely crucial for “green” electronics formation to use biodegradable “metallic” component materials. To maximize the performance and reliability of the integrated circuit for wearable electronics applications, an optimum metal would have high carrier mobility, low resistance, significant thermal conductivity, outstanding mechanical properties, as well as corrosion resistance. Additionally, the changes in electrical properties as the metal degrades are the most important parameters that need to be considered for biodegradable metals. A previous study reported substantial standards for the use of metals in order to improve the performance of “green” electronics, which “dissolve” once their service life has been reached. It was shown that the electrical dissolution rate (EDR) of electrodes based on magnesium (Mg), Mg alloy, and zinc (Zn) boosted into salt solutions, or even the EDRs risen to body temperature (between RT and 37 °C), ceasing to increase within 8 h upon contact with a transistor.<sup>159</sup> Conductive metals and microelements, including Mg, molybdenum (Mo), tungsten (W), iron (Fe), Zn, and their alloys,<sup>160</sup> are a fascinating category of materials for short-term healthcare applications.<sup>161</sup> Such materials have appealing electrical and mechanical properties, as well as degradability in a controlled environment.<sup>162</sup> In addition, such materials can dissolve at different rates across both deionized (DI) water and simulation model biological fluids (Hanks’ solution pH 5–8),<sup>163–165</sup> where metals move as electron donors and water as electron receivers.

One of the biggest challenges in developing wearable electronic devices is the requirement for flexibility, lightweight, thinness, safe and portable energy storage devices. To this end, we may draw inspiration from zinc ion batteries, which have demonstrated excellent potential for wearable electronics applications because of their safety, economical, and environmental friendliness.<sup>166</sup> Zn dissolution rates for aqueous system and biofluids have been reported as 1.7 nm day<sup>-1</sup> and 7.2 nm day<sup>-1</sup>, respectively. In addition, Mg has shown biodegradability and electrical conductivity as an electrode material for resistive switching memory devices based on chitosan,<sup>167</sup> with both of these materials exhibiting rapid dissolution rates. In contrast, Mo and W are favored metals for degradable medical devices with transient lifetimes, such as physiological electrical signal sensing that may stand in need forthright connection amid



Table 2. Dissolution Products, Rate, and Factor for Metal-Based Conductive Materials

metallic conductor	dissolution product/solution	dissolution rate	dissolution factor	ref
Zn, Mg, Mg alloy	Zn(OH) <sub>2</sub> , Mg(OH) <sub>2</sub>	300 nm/day	room temperature, 37 °C, ceased within 8 h with MOSFET film	157,159
Mg	PBS solution		dissolution kinetic depends on the temperature and pH	170–172
			pH increases from 7.4 to 10, temp decreases from 37 to 25 °C	
			dissolution over 2 min to 12 h	
Mo, W	H <sub>2</sub> MoO <sub>4</sub> , H <sub>2</sub> WO <sub>4</sub>	~10 <sup>-2</sup> nm/day	pH and temperature of the surrounding environment	162,168,169
Zn	Zn(OH) <sub>2</sub>	1.7 nm/day	pH and temperature of the surrounding environment	162,168,169
Zn	viofluid solution	7.2 nm/day	pH and temperature of the surrounding environment	162,168,169
Fe	Fe(OH) <sub>2</sub>		pH and temperature of the surrounding environment	

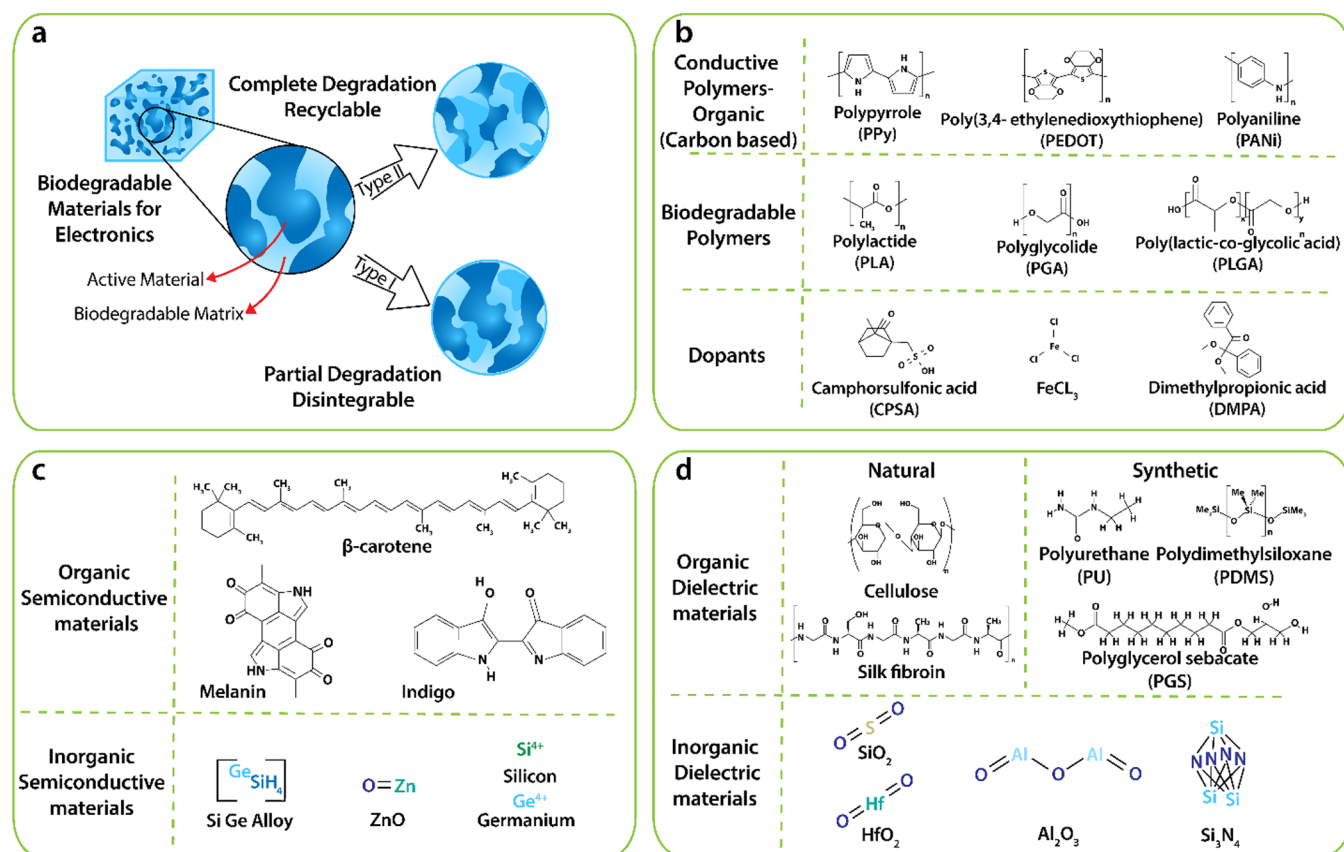


Figure 5. (a) Biodegradable materials with preferred electronic properties are made up of an active material (dark blue) dissolved within a biodegradable matrix (light blue), with biodegradable materials classified into type I and type II. Reprinted with permission from ref 185. Copyright 2018 American Chemical Society. (b) Chemical structures of biodegradable conductors. (c) Chemical structures of biodegradable semiconductor. (d) Chemical structures of dielectric fillers.

biological tissues and metal parts. They have slower and more tunable degradation characteristics, around  $\sim 10^{-2}$  nm day<sup>-1</sup>,<sup>162,168,169</sup> making them better suited for controlled-length monitoring. Thin iron films show slow degradability, despite their rapid oxidation in biological conditions to convert into the iron oxides and hydroxides, which minimizes their solubility. The prolonged decomposition of these byproducts may restrict the use of Fe-based materials in certain biodegradable health monitoring applications, particularly oral or implantable techniques, which should vanish completely once their needs are fulfilled.<sup>162</sup> In Table 2, the dissolution rate of inorganic conductive materials and their dissolution factors are summarized.

While Zn, Mg, Fe, W, and Mo have demonstrated excellent dissolution performance for many applications, including health monitoring devices, flexible electronics, energy storage, and electronic sensors, further studies will be needed to

investigate their compatibility and interactions with sustainable textile fibers for wearable e-textile applications. Additionally, suitable processes need to be established to either separate such materials from textiles or achieve complete biodegradation of both fibers and materials.

**Conductive Polymer-Based Conductors.** Conductive polymers (CP) are electrically conductive materials composed of a conjugated covalent backbone and functional groups with pseudocapacitive characteristics, together giving rise to conductive properties.<sup>173</sup> The most common conductive polymers are polypyrrole (PPy), polyaniline (PANI), polythiophene (PT), and PT derivatives such as poly(3,4-ethylene dioxythiophene) (PEDOT), which have been used satisfactorily as electrode materials (Figure 5b).<sup>174</sup> Such conductive polymers have mechanical flexibility greater than that of metal contacts, which makes them ideal for developing flexible and conformal electronics for health monitoring systems.<sup>162</sup>

Table 3. Types of Conductive Polymer Degradation<sup>a</sup>

conductive polymer	material system	dopant	conductivity	applications	ref	
type I: conductive blends	PANI gelatin nanofibers	camphorsulfonic acid (CPSA)	$2.1 \times 10^{-2}$ S/cm	scaffold for tissue engineering	185,196	
	PANI electrospun with PLCL	CPSA	$1.4 \times 10^{-2}$ S/cm	control of cell adhesion	185,197,198	
	PPy with PCLF (polycaprolactone fumarate)	anionic dopants: naphthalene-2-sulfonic acid sodium salt and dodecyl benzenesulfonic acid sodium salt	$6 \times 10^{-3}$ S/cm	nerve regeneration	185,199,200	
type II: conjugation breaking	PEDOT particles in PLLA	hyaluronic acid	$4.7 \times 10^{-3}$ S/cm	biomedical application	185,201,202	
	PPy nanoparticles in PDLILA	oxidation with FeCl <sub>3</sub>	$1 \times 10^{-3}$ S/cm	biosensors, drug-delivery systems, biomedical applications, as well as tissue engineering	185,203,204	
	PPy-coated PLGA fibers	oxidation with FeCl <sub>3</sub>	$R_s = 4.7 \times 10^5 \Omega/\text{sq}$	neuronal tissue scaffolds	185,205	
type II: conjugation breaking	PANI grafted to gelatin	CPSA	$4.5 \times 10^{-4}$ S/cm	tissue engineering	185,206,207	
	PPy-thiophene-PPy with aliphatic linkers	iodine	$10^{-4}$ S/cm	electrochemical energy storage, as well as optoelectronics	185,208,209	
	hyperbranched: AP and PCL	hydrochloric acid (HCl)	$2.4 \times 10^{-5}$ S/cm	tissue repair and bioelectronics.	185,210	
	aniline trimer with polycaprolactone	dimethylpropionic acid (DMIPA) (incorporated into backbone)	$1.2 \times 10^{-5}$ S/cm (dry)	skeletal muscle tissue engineering	185,211	
	aniline tetramer grafted to poly(ester amide)	CPSA	$4.7 \times 10^{-3}$ S/cm (in PBS)	vascular tissue engineering	185,212–214	
	aniline pentamers (AP) with PLA triblock copolymers	CPSA	$8.0 \times 10^{-6}$ S/cm	tissue engineering	185,215–217	
	quaterthiophene and alkyl chains joined by ester bonds	FeCl <sub>3</sub> and Fe (ClO <sub>4</sub> ) <sub>3</sub>	$5 \times 10^{-6}$ S/cm		185,218	

<sup>a</sup>Composites of nondegradable conductive polymers and electrically insulating degradable polymers make up type I conductors. Type II conductors are created by cleavable linkages, connecting conductive oligomers with degradable polymer segments. Dopants must achieve workable conductivity values in both case scenarios, and they need to be biocompatible.

Additionally, they have demonstrated excellent biocompatibility within biological systems.<sup>175</sup> Furthermore, the properties of conductive polymers are beneficial in wearable devices focused on on-skin sensing.<sup>176</sup> Textiles or films with conductive polymer coatings are suitable for use in various military and aviation applications, as the conductive polymer components have the combined properties of both metals and plastics. In studies,<sup>177–180</sup> efficient *in-situ* polymerization of CP precursors such as aniline and pyrrole on the textile substrates has been achieved, resulting in electrically conductive cotton and polyester-based textiles. By combining inherently conductive polymers with more mainstream fibrous polymers, the characteristic mechanical and physical properties of the textile can be produced.<sup>181,182</sup> Such polymeric combinations may better suit wearable technologies, due to their inherent mechanical stiffness, flexibility and adaptive structure with stretchable electronics.<sup>3,183,184</sup>

Although CPs are suitable for many electronics applications, conventional CPs are still nondegradable, and their sustainability needs to be improved for imparting reliable electrical conductivity while reducing comparable concentration of the nondegradable conjugated component.<sup>185</sup> One method of dealing with the deterioration of these conductive polymers would be to construct a composite structure where the conductive polymers are embedded in a biodegradable insulating matrix. Under right set of circumstances, such matrix can be degraded, and the nondegradable components are biocompatible.<sup>185,186</sup> This type of degradation is classified as type I, as illustrated in Figure 5a, with typical examples (Table 3) such as PANI, PPy, and PEDOT which have conductivities up to  $4.6 \times 10^3$  S/cm when doped with poly(styrenesulfonate) (PSS).<sup>172,187</sup> The second approach is to incorporate flexible, biodegradable and conductive polymers and nonconjugated division with the copolymer backbone format. The obtained small and conjugated components after breakdown are nontoxic, and they could further be degraded or eliminated by the atmosphere or the body's immune function. Such degradation is labeled as type II,<sup>185,186</sup> as illustrated in Figure 5a, and biodegradable polyurethane segments are typically incorporated into the copolymer backbone to achieve type II (a few examples are given in Table 3) degradation.<sup>186</sup> These biodegradable conductive polymers have recently attracted considerable attention as an evolving class of futuristic polymeric biomaterials that offer electrical conductivity, biocompatibility, and biodegradability. Conductive polymers such as PANI, PPy, PT, and biodegradable polymers such as poly(D,L-lactic acid) (PDLA) and PCL can be covalently bound together, enabling the ability to “tailor and engineer” the performance and sustainability properties of the final polymeric material. However, an ongoing challenge for organic-based conductive polymers is that the material's longevity is relatively poor, specifically the inadequate cycling performance of conductive polymers in applications such as supercapacitor electrodes<sup>173,188</sup> in wearable electronics. To overcome this technical deficiency, incorporating carbon-based materials into conductive polymers is a promising approach to enhancing their overall electrochemical performance by integrating the optimal individual properties of both components leading to better utilization and sustainability.

**Carbon-Based Conductors.** Carbon-based materials such as single wall/multiwall CNTs and graphene have been reported as good conductors for wearable electronics applications.<sup>172</sup> Due to their noticeable features, such as nanoscale diameters,

outstanding electrochemical functions, electrical conductivity, favorable physical properties and biocompatibility, CNTs and graphene can be used for fabricating electrochemical devices.<sup>189</sup> Carbon-based conductive materials (CNTs, carbon fibers, graphene, reduced graphene oxide, and pyrolytic carbon particles) are also thermally stable and have electrical conductivities (of CNTs and graphene) greater than those of the conductive polymers.<sup>190–193</sup> Furthermore, virtually any known form of applicable conductive carbons can be formed from renewables.<sup>193</sup> Therefore, the use of carbon-based conductive materials is considered to the “greener” option than metals. However, the electrical conductivity of carbon-based materials is not as significant as metals, even though CNTs are an example of the most promising materials for wearable electronics offering metallic-like and superconductive electron transport<sup>194</sup> and can be modulated under several forms of stimulation.<sup>195</sup> This functionality can help monitor various health parameters such as temperature, heart rate, and glucose levels in the blood. In addition, CNT-based e-textiles may help to record electrocardiography (ECG), electroencephalography (EEG), and electromyography (EMG) signals.

In addition to building on the initial CNTs studies, graphene inks have also been assessed within electronic components and devices integrated into smart fabric textiles. This material changes the wearable electronics textile framework with its excellent physical properties for use in electronics, sensing, catalysis, photonics, and energy storage.<sup>219</sup> Graphene's atomic thickness (0.345 nm) and outstanding electrical and mechanical properties<sup>220</sup> also offer further significant benefits, allowing deposition of exceedingly thin, soft, and conductive film on surfaces of textile fibers through inkjet printing. The strong adhesion of graphene to textile substrates, combined with the inherent environmental compatibility, makes graphene-enhanced electronics attractive for wearable applications. Moreover, incorporating carbon-based fillers further increases the host material's performances<sup>221</sup> with less material needed to deliver the same performance, thus improving sustainability. Hence, the carbon footprint required to manufacture and integrate the material into its intended application will be decreased. The use of such conductive materials in this framework can improve the sustainability of the recycled or biosynthetic polymer also by creating a more durable fiber, so fewer plastics will need to enter the landfill and, in turn, the oceans and local ecosystems.

**Semiconductors.** Semiconductors are essential to the switching mechanism of organic transistors,<sup>222</sup> and these are necessary for complicated electronic circuitry. They are usually distinguished by their charge carrier mobility ( $\mu_i$ ), that reflects how rapidly a free charge can keep moving through the substances when dragged by an electric field. Mobility and conductivity ( $\sigma$ ) are related by the following equation:

$$\sigma = e(n\mu_e + p\mu_h)$$

where  $n$  is the concentration of electrons with mobility  $\mu_e$  and  $p$  is the concentration of holes with mobility  $\mu_h$ . Mobility is normally expressed in  $\text{cm}^2/\text{V}\cdot\text{s}$  and can be calculated directly from working devices like thin-film transistors. Regular semiconductive polymers are PT (e.g., poly(3-hexylthiophene), P3HT) and donor–acceptor copolymers developed originally for organic photovoltaics (e.g., diketopyrrolopyrroles, DPP).<sup>223,224</sup>





**Table 4. Dissolution Solutions, Dissolution Factors, Electron Mobility and Hole Mobility of Biodegradable Semiconductor Materials**

biodegradable semiconductor materials	dissolved solutions	dissolution factor	electron mobility (cm <sup>2</sup> /V·s)	holes with mobility	ref
DPP			up to 0.55	up to 0.34	172,185
PDPP-PD	hydrolyzed with a catalytic amount of acid	30 days for disintegration in a buffer solution with pH 4.6		0.12	186
organic	anthraquinone derivatives		$1.2 \times 10^{-2}$		185
	$\beta$ -carotene		$4 \times 10^{-4}$		186
	natural dye Indigo		$10^{-2}$		172,185,186
Si-NMs	biofluid and aqueous solution $\text{Si} + 4\text{H}_2\text{O} \rightarrow \text{Si}(\text{OH})_4 + 2\text{H}_2$	time: 12 h, temp: 37 °C, pH: 6–14 doping level of the Si, ionic concentration, hydrolysis rate of Si NMs is around 10 nm/day in groundwater			172,240
inorganic	ZnO	produced Zn(OH) <sub>2</sub> by hydrolysis, slightly soluble ZnO (s) + 2OH <sup>-</sup> → ZnO <sub>2</sub> <sup>2-</sup> + H <sub>2</sub> O			172
	Ge	produced H <sub>2</sub> GeO <sub>3</sub> upon hydrolysis $\text{Ge} + \text{O}_2 (\text{aq}) + \text{H}_2\text{O} \rightarrow \text{H}_2\text{GeO}_3 (\text{aq})$			172

In some cases, a semiconductor-containing device can contain large quantities of hazardous elements such as mercury, chromium, arsenic, and lead (Pb), which can release toxic elements into soils and waterways when e-textile derived waste is thrown away in landfills. Additionally, the incineration of plastics used for semiconductors can lead to the discharge of volatile compounds like dioxin derivatives, polychlorinated dibenzofuran and polychlorinated biphenyls, that are classified as group I carcinogens.<sup>227,228</sup> Therefore, to reduce the intensity and influence of waste electronics, there is a significant focus on sustainable semiconductors which contain more environmentally friendly materials.

Developed in a previous study,<sup>229</sup> a *p*-phenylenediamine (PPD) polymer-based semiconductor degraded when exposed to a weak acid. The substrate was made of transparent cellulose, and the electronic components were comprised of iron rather than gold, because it is less toxic to humans and more eco-friendly. Skin-like electronics have a wide range of potential applications, including skin patches that can monitor glucose levels, blood pressure, and other vital signs. It can also act as a wearable device and can interact with ecologic detection systems that could be utilized across a vast wooded areas, sending back data on the forest “health” during the biodegradation.

For many applications, the total breakdown of polymers into their monomeric building blocks is redundant, and device disintegration is adequate to prevent obstructive and pricey recovery processes. Type I<sup>185</sup> materials are those that exhibit transient behavior, as illustrated in Figure 5a and Table 1. Like conductive polymers, blending has been used to produce semiconductors which display type I degradation. Furthermore, the notion of blending has been investigated in order to generate flexible “green” electronics, in which two conductive polymers (CPs) are blended together to overcome the flaws of the individual materials.<sup>230</sup> For type II biodegradable semiconductors, the innovative adoption of reversible imine bonds as conjugated linkages between DPP and *p*-phenylenediamine recently has been reported.<sup>185</sup> Poly(3-thiophene methyl acetate) (P3TMA), a derivative of P3HT with carboxylate substituents, was selected for blending with poly-

(tetramethylene succinate), PLA, poly(ester urea), and thermoplastic polyurethane (TPU) to enhance miscibility with more polar, biodegradable matrixes.<sup>185,231</sup> Therefore, we can expect fully degradable semiconductors, which signifies a good potential step toward the development of multifunctional materials for wearable electronic devices that can resolve earlier unconquerable obstacles and develop fit for purpose inventions.

**Organic Materials.** The development of organic-based semiconductor materials as a replacement for traditional inorganic materials is a recent research focus. Their beneficial characteristic features include solution processability, superior mechanical flexibility, simplicity of structural modification, low-temperature fabrication method, relatively low charge, and the ability to produce on a large scale.<sup>186,232</sup> Researchers have attempted to identify naturally occurring conjugated materials for use in the fabrication of semiconductors for electronic devices. Furan has shown some promise as a “building block” because of derivatives can indeed be made from natural sources,<sup>233</sup> and the establishment of furan-based semiconductive materials may represent a major leap toward green electronics. Oligofurans have widely been reviewed (with a mobility of  $10^{-2}$  cm<sup>2</sup>/V·s) as active semiconductor materials in OFET devices, and furan substructures have extensively been accounted as constituents within the backbone of conjugated materials.<sup>234</sup> Bao et al.<sup>229</sup> also designed a DPP-based polymer (polymer diketopyrrolopyrrolephenylenediamine, PDPP-PD) that recommended imine functionality into the polymer backbone to escalation biodegradability. Following that, this device demonstrated excellent hole mobility (0.12 cm<sup>2</sup>/V·s) and extremely good biodegradability. The device was reasonably stable in DI water disintegrated within 30 days immersed into a pH 4.6 buffer solution (Figure 6b).

Melanin, a conjugated biopolymer widely found in nature, provides a hybrid electronic-protonic conductivity.<sup>172,235,236</sup> The conductivity of melanin is strongly reliant on its hydration state, with a fully hydrated state having a conductivity of  $10^{-3}$  S/cm and a dehydrated state having a conductivity of  $10^{-9}$  S/cm to  $10^{-8}$  S/cm. Temperature and physical framework are

Table 5. Dielectric Constant Frequency and Applications of Dielectric Fillers<sup>172,186,213</sup>

	dielectric fillers	dielectric constant (K)	frequency	incorporation/application
inorganic	SiO <sub>2</sub>	3.9		
	Si <sub>3</sub> N <sub>4</sub>	7		gate dielectric
	Al <sub>2</sub> O <sub>3</sub>	27.57	50 Hz	dissolved in 6 months in PBS at pH 12 and 37 °C
	HfO <sub>2</sub>	25		cellulose acetate (Figure 6c)
organic	cotton	17	60–1000 Hz	
	sugar-glucose	6.35	1 kHz	
	sugar-lactose	55	1 kHz	
	DNA and its precursors			gate dielectric, cationic surfactant—hexadecyltrimethylammonium chloride (CTMAC)
	PGS poly(glycerol sebacate)			capacitive sensor
	CNTs	3198	1 kHz	CNFs (Figure 6c)

also factors that influence its conductivity.<sup>185</sup> Melanin, indigo derivative, purpurin, alizarin, PDI (pyridinediimine), and NDI (naphthalenetetracarboxylic diimide) carry a great number of C=O functionality that aids in forming intramolecular and/or intermolecular H-bonding interactions. Regardless of the absence of intramolecular conjugation in some of these molecules, the H-bonded intermolecularly connected materials provide outstanding quality for organic electronic devices, denoting good prospects as biodegradable semiconductors in future green electronics.  $\beta$ -Carotene is another noteworthy natural conjugated polymer, which make the orange color for carrots and can be used as a nontoxic semiconductive layer in organic bioelectronics.<sup>237</sup> It has been proclaimed as a p-type field-effect semiconductor with charge mobility of  $4 \times 10^{-4}$  cm<sup>2</sup>/V·s.<sup>185</sup> Solution-processed p-type  $\beta$ -carotene was employed satisfactorily as an active layer for OFETs and organic solar cells (OSCs).<sup>238</sup> As a result, much further exploration into the use of organic semiconductor materials is necessary to accomplish fully organic bioelectronics with enhanced electrical performances.

**Inorganic Materials.** Along with their own outstanding conductivity, mainstream semiconductors are primarily based on metal oxides and Si derivatives, such as various forms of Si and Si–germanium (Ge) alloys. The resulting conventional integrated circuit from such materials may not disintegrate for many hundreds of years, making them non-biodegradable materials. Nevertheless, some studies have shown that nanomembranes or nanowires of Si or Si/Ge alloy can improve biodegradability to facilitate the dissolution/decomposition process of the integrated circuits by fully decomposing within 10 days, without generating toxic byproducts.<sup>186</sup> For instance, Rogers et al.<sup>239</sup> investigated the transient form of Si by fabricating a set of functional devices, including resistors, field-effect transistors, photodetectors, and diodes, using a Si nanomembrane as the semiconductor.

Previous studies<sup>241–247</sup> have shown that mono-silicon nanomembranes (Si NMs), amorphous silicon (a-Si), germanium (Ge), polycrystalline silicon (poly-Si), silicon–germanium alloy (SiGe), zinc oxide (ZnO), and amorphous indium–gallium–zinc oxide (a-IGZO) are soluble (Table 4) in biological aqueous medium. pH, temperatures, doping levels, concentrations, and types of ions and proteins in the solution are discovered each to have a major impact upon that dissolution rates of mono-Si NMs. pH levels and rising temperatures accelerate the dissolution rate of Si NMs, whereas a high doping level ( $>10^{20}$  cm<sup>-3</sup>) significantly slows

the dissolution rate.<sup>246,247</sup> Correspondingly, the dissolution rates of poly-Si, a-Si, Ge, and SiGe are largely shaped by pH, temperature, proteins, and ion type. Such materials, for instance, dissolve faster at physiological body temperature (37 °C) than at room temperature. For poly-Si, a-Si, and single-crystal Si, dissolution rates in bovine serum at a similar pH are 30–40 times higher than those in a phosphate-buffered solution at 37 °C.<sup>245</sup> Si-NMs with coherent hydrolysis rates have found widespread application in biodegradable electronics devices such as diodes, photodetectors, and metal–oxide–semiconductor field-effect transistors (MOS-FETs).<sup>162,165,248</sup>

Zinc oxide (ZnO) has indeed received a great deal of attention in published findings as an inorganic semiconductor owing to its large and direct band gap (3.37 eV) and high exciton binding energy (60 meV).<sup>249</sup> ZnO, a piezoelectric material that is free of lead, is widely used in mechanical sensing and energy harvesting, with differing ZnO nanorod<sup>250</sup> lengths both influencing and improving the nanogenerator energy-harvesting performance. Consequently, there is potential to efficiently convert from physical movement and the environmental elements to electronic signals using this dissolvable ZnO, which could drive wearable electronic textiles for sensing, activity recognition, or surveilling to raise the quality life.

**Dielectric Materials.** Another essential building block for manufacturing wearable electronics are dielectric materials, which are necessary for facilitating capacitive functionalities. These insulating materials have the greatest impact on determining the overall properties of a component. Dielectric materials are characterized by the dielectric constant,  $K$ , defined as the ratio of the material's electric permeability to free space's electric permeability (i.e., a vacuum). The permittivity of a dielectric material comparable to that of free space is known as relative permittivity, generally denoted by  $\epsilon_r$ , the dielectric constant. The following equation connects absolute permittivity ( $\epsilon_0$ ), relative permittivity or dielectric constant ( $\epsilon_r$ ), and permittivity of a material ( $\epsilon$ ).

$$K = \epsilon_r = \epsilon/\epsilon_0$$

Whenever a voltage is applied to a capacitor, its dielectric constant determines how much energy it can store. Even if a dielectric material is exposed to an electric field, it becomes polarized, and polarization reduces the effective electric field. Because the permittivity of a material varies with frequency and temperature, the dielectric constant is administered at specific

conditions, typically at low frequencies.<sup>185,251</sup> Depending on the requirements, the target dielectric constant ( $K$ ) can be high or low, usually aiming for low dielectric losses for minimal dissipation of electromagnetic energy and high breakdown voltages for stability.<sup>185</sup>

Incorporating high- $K$  fillers into a degradable polymer matrix is a common strategy for developing biodegradable dielectrics. In addition to natural materials, such as cellulose and silk fibroin, poly(glycerol sebacate) (PGS), a synthetic biodegradable polymer, also has functional dielectric properties.<sup>252</sup> Elastic materials (e.g., PGS) are advantageous for capacitive sensing as they can resist repeated and reversible deformation better than viscoelastic alternatives because textiles materials have a very low dielectric constant.<sup>162</sup> For example, the dielectric constant for silk and polyester is 1.75 and 1.90, respectively, which are comparatively lower than those of SiO<sub>2</sub>, HfO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub> which are 3.9, 25.0, and 27.6, respectively. Textile materials generally have quite small dielectric constants because they are porous, as well as interstitial air raises the relative permittivity to be closer to unity (i.e., dielectric constant in air).<sup>253</sup> A range of dielectric fillers are detailed in Table 5 with dielectric constant, frequency, and their potential applications as sustainable materials.

Currently, the potential for wearable e-textile has gained prominence in the healthcare sector, focused on applications in sensing, communication, health monitoring and simply following up with patients. This clothing-based communication platform<sup>254</sup> requires the miniaturization of wireless devices for tracking and navigation, mobile computing and public safety. This communication is possible when the wearable antenna can transmit fast-changing signals across the textile transmission line based on the complex dielectric permittivity of the material or substrate. Incorporating sustainable dielectric materials such as SiO<sub>2</sub> or Al<sub>2</sub>O<sub>3</sub>, which have high dielectric constant, into these wearable textiles can establish a latest sustainable opportunity for developing wearable antennae (Table 5). While the variable positioning of wearable antennas on the body due to human body movements, such as standing, sitting, walking, running and during sports, may affect the transmission of electrical signals, textiles infused with dielectric materials provides an opportunity to address this issue and improve the user experience.

**Sustainable Electronic Components.** Electronic components are frequently encapsulated in discrete form with two or more running parallel leads or conductive pads. The functions of electronic components depend on the type and application of the circuits. Electronic components are projected to be soldered to a printed circuit board (PCB) to form an electronic circuit with a particular function.<sup>255,256</sup> There are two categories of electronic components: passive and active. Passive electronic components include resistors, capacitors, diodes and inductors, all of which lack gain or directionality. In contrast, integrated circuits (IC), transistors, and logic gates are examples of active electronic members that have yield or directionality.<sup>255</sup>

Wearable electronics would not be feasible without electronic components, such as electrodes, connectors and interconnectors. For example, electrodes act as a connection between the body as well as the circuit when wearable e-textiles acquire electrical or biological signals. Even when electrical signal acquisition is not required, connectors and interconnectors are necessary to create a connection with both textiles and electronics. Textile circuits are usually built on textile

substrates by printing, knitting, embroidering, or laminating. Embroidery of conductive threads into textile substrates to form electronic device is a common method for stitching patterns that designate component connection pads, circuit traces, or sensing surfaces employing computer-aided design (CAD) tools.<sup>257</sup> There are many types of textile yarns available for creating electronic connections and circuit elements, including silver-coated yarns, gold, titanium, and stainless steel, and tin threads. Conductive patterns can also be made via inkjet printing of conductive inks.<sup>258</sup> Textile circuits are generally constructed with a low-power rate and a large input impedance, which contrasts with the traditional requirement of low impedance for component interconnections. Hot press, a heat weldable electronic circuit to a textile substrate is another method for making textile circuits.<sup>259</sup> Once connected to the textiles, the circuit can be soldered like a traditional PCB. Furthermore, conductive inks and polymers could be used to print flexible conduction lines.

Fixing the circuitry to textiles uses materials such as solder, protective coatings, plastics and paints. Solder is used in circuit board assembly to melt and form a solid metal joint between the pins of electronic components and the metal landing pads on the board. Soldering, on the other hand, can produce high concentrations (>85%) of lead<sup>260</sup> as well as other toxic substances, attempting to make it hazardous to humans and the environment. To protect against these toxic materials, printed circuit boards can now be formed using green technology, which includes lead-free soldering.<sup>241</sup> It not only provides a more sustainable and environmentally friendly option but also conforms to the restriction of hazardous substances (RoHS)<sup>260</sup> legislation mandated for electronics sold in Europe.<sup>261</sup>

## SUSTAINABLE MANUFACTURING

The sustainability of wearable electronics depends on the sustainability of its individual component elements and the manufacturing process.<sup>262</sup> In other words, the textile substrates, insulators (dielectrics), conductors, and semiconductors all need to be fabricated through sustainable techniques, as well as themselves be sustainable by being recyclable and/or biodegradable. Such resource-rich products need to be designed in such a way that they do not lose their inherent value at the end of their life cycles. Additionally, sustainable production requires that the energy, water and other natural resources used to manufacture such devices are optimally utilized as much as possible. Furthermore, the disassembly of various electronic components needs to be considered to fully recycle wearable electronics at the end of their useful life.<sup>263</sup> The degree of integration of the numerous electronic components within the substrates has a direct impact on this goal. These electronic components can be embedded within the fibers or be removable. An assembly process that considers a lower level of integration with relatively low negative environmental consequences will be beneficial not just for reuse and recycling, but also for cleaning, washing, and updating rapidly changing technology, and can constructively involve the end-user throughout this process.<sup>264</sup>

There are several techniques available for incorporating electronic materials (conductors, semiconductors and dielectric) into traditional textiles, either in fiber, yarn, or fabric form.<sup>265,266</sup> In the most simple sense, the process of incorporating conductive yarns into traditional textiles can be achieved by manually sewing the conductive yarns or

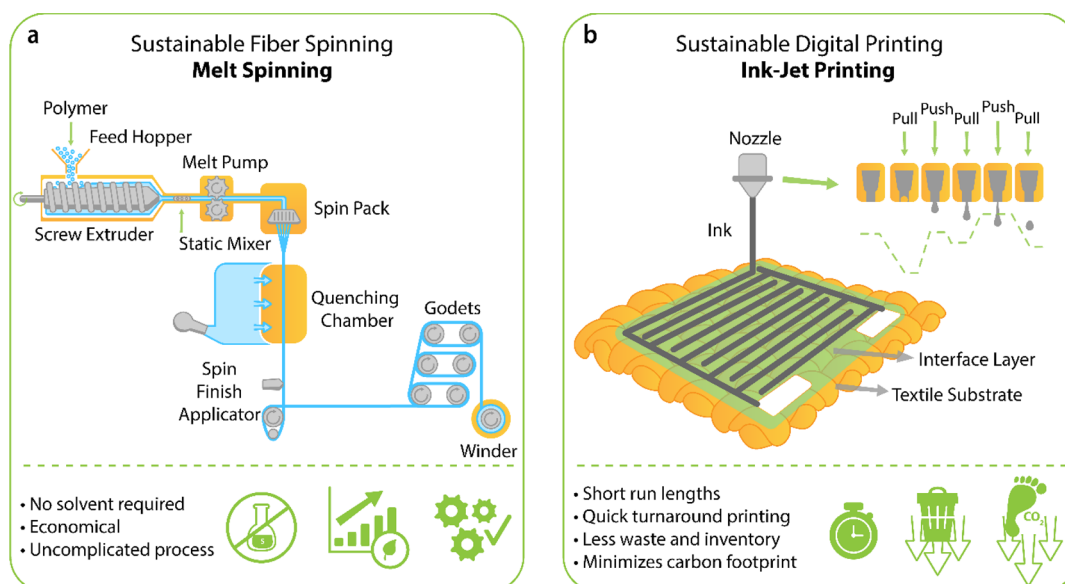


Figure 7. Sustainable manufacturing techniques: (a) fiber-spinning: melt-spinning.<sup>284</sup> (b) Digital printing: inkjet printing.

mechanically embedding in the fabric through knitting, weaving, embroidery, or braiding.<sup>4</sup> Nonconductive yarns can be coated with galvanic substances, metals, or metallic salts to make electrically conductive yarns from “pure” textile threads, enabling e-textile production.<sup>4,267</sup>

Over the past decade, it has also been evident that manufacturing techniques used to produce conventional textiles could be applied to produce e-textiles.<sup>268</sup> For example, the fabrics used for protective medical clothing are typically knitted, woven, or nonwoven. Woven fabrics are generally stronger and more durable;<sup>269,270</sup> they are less extensible, however, than knitted fabrics, which are porous but have relatively poor barrier properties. Knitting is the second most used fabric manufacturing method after weaving. Knitting is a faster and more cost-effective method of converting yarn into textiles than weaving. Furthermore, knitted fabrics typically offer improved comfort and a great choice in most sorts of apparel because of their ability for very high extensibility, up to 100%.<sup>271</sup>

Nonwoven fabric (NWF) is a low-cost textile material that can be engineered in higher value functionality in healthcare, protective clothing, filtration, and packaging. In a previous study,<sup>272</sup> graphene enhanced NWF sensors have demonstrated that they can respond to a variety of human movements, with a clear differentiation of the activities’ levels of difficulty. They can also monitor small-scale movements such as pulse and respiration. Additionally, chemical vapor deposition, sputtering, electroless plating, and conductive polymer coating are also widely accepted textile coating processes.<sup>273</sup> Several methods exist for printing conductive material on textile substrates, however they all use conductive inks containing metals such as copper (Cu), silver (Ag), and gold (Au).<sup>274</sup> Many fabrication processes and materials make the wearable e-textiles field more promising by providing exemplary performance, such as lightweight, strong mechanical properties, high conductivity, wearability and biocompatibility. Even after these benefits, electrical and mechanical performance metrics such as stability, sensitivity, and long-term use are still lacking for realizing practical wearable applications. Accordingly, there is still considerable scope for improvement in wearable e-textile

design through improved fabrication or manufacturing technology that can be cost-effective, environmentally friendly, and provide better performance. Among all the fabrication and manufacturing techniques, melt-spinning and digital inkjet printing are of particular interest due to inherent advantages such as less waste of materials, less water and energy-intensive processes, making such methods suitable for sustainable manufacturing of conductive e-textiles. Additionally, we note the potential of electrospinning, an emerging technology that has begun its transition from the laboratory-based incubation stage to commercial-scale development, for providing additional opportunities to integrate distinctive functionalities.

**Melt-Spinning.** Typically, man-made fibers are formed by “spinning” the polymer, which involves extruding the polymer in long lengths and dramatically increasing their aspect ratio, which results in the formation of polymeric fiber strands with small widths in the micron-scale or less. In dry-spinning process, polymers are dissolved in a solution that can be evaporated, whereas wet-spinning involves extruding the polymer/solvent mix into a second coagulation solvent. In contrast, melt-spinning is applied to polymers that can be effortlessly melted at a relatively low temperature. Melt-spinning is one of the simplest extrusion processes where no additional solvent is required, hence there is also no need for subsequent solvent removal. It is also considered one of the most economical and popular methods for polymer fiber manufacturing at industrial scales. The fiber-forming substance is melted just before to extrusion through the spinneret in melt-spinning and then consequently solidified by cooling into a cold-air quench duct (Figure 7a). Since no solvents are released in this process, there are no byproducts that have to be recycled. The extruded polymer cools and solidifies into continuous filaments, which is then drawn, twisted, further processed, and wound onto spools. From a wearable e-textile perspective, conductive nanomaterials such as graphene and CNTs at the fiber-spinning stage, can be integrated into the textile structure by adding straight into the polymer solution, which is later extruded together to generate conductive fibers or filament. Such a spinning method is suitable for producing the commodity fibers based on polyamide (nylon),<sup>275</sup> PET,<sup>276</sup>



and PP fibers. In addition, in melt-spinning of e-textile fibers, PE and PP melts can also directly act as initiator to produce ultrafine fibers.<sup>277</sup> Solvent-free melt-spinning, as compared to polymer-spinning in the solution phase, may present further opportunities for spinning without the danger of solvent residue in fibers, solvent evaporation into the atmosphere, or the high cost of solvent recycling. It also has the potential to have potential applications in the biomedical, tissue engineering, technical textiles, and filtration sectors.

Moreover, multicomponent melt-spinning takes advantage of capabilities not found in polymers alone, as beneficial mechanical, physical, or chemical properties of different materials can be merged in a single fiber, broadening the range of possible application domains.<sup>278,279</sup> For instance, as the two polymers (e.g., PET/PP) can influence the thinning and solidification behaviors of each material along the spinning line, both components' molecular structure development can influence each other.<sup>280</sup> Several research groups have already investigated multicomponent and multifunctional electronic fibers for wearable electronics. Kapoor et al.<sup>281</sup> presented a prototype multimodal and multifunctional sensing system constituted within a woven fabric structure with organized insulating and conductive portions. In addition, Lund et al.<sup>282</sup> asserted melt-spinning of a piezoelectric bicomponent polymer fiber for developing a force sensor. That was eventually a carbon black (CB) and high-density polyethylene (HDPE) electrically conductive compound, respectively functioning as an inner electrode and core material, with poly(vinylidene fluoride) as the electroactive component. The piezoelectric effect of the fibers was comparable to that of commercial piezoelectric polymer films. Fink et al.<sup>283</sup> developed a scalable preform drawing method for the preparation of multicomponent as well as multifunctional fibers. Multicomponent melt-spinning, which combines metals, insulators, and semiconductors within a single fiber strand, can then be used to produce single-material fibers with multifunctionality. Recognizing that traditional man-made polymer fibers may lack the geometry, compositional range, and feature sizes<sup>283,284</sup> for extra functions, the expedition of the frontier of fiber functionality, multicomponent melt-spinning could be a productive area for future fiber production for wearable e-textiles.

Therefore, it can be summarized that the development of melt-spun fiber for wearable e-textiles are inextricably linked to fields of study such as polymer synthesis and processing, functionalization, multicomponent concepts, healthcare applications, as well as "frontier" electronics. Embedding multiple functionalities into a single fiber is still a massive obstacle, but advanced materials with enhanced rheological, electrical and other properties that retain their functional features when applied through melt-spinning should be further investigated. We anticipate that a single strand of fiber will exhibit extremely developed fiber architectures, both within its cross-section and length, to demonstrate electronic functionalities within a sustainable wearable e-textile sector using sustainable materials and fabrication approaches.

**Digital Printing.** There are emerging trends around the use of manufacturing processes that are sustainable with low environmental impact. Sustainable manufacturing promotes processes that are energy/water efficient and use sustainable and recycled materials, eliminating hazardous substances wherever possible. In this regard, digital manufacturing offers many sustainability benefits, such as the minimal waste of

materials, lower energy consumption, and less use of chemicals. For manufacturing sustainable and wearable e-textiles, the digital printing technique is attractive in being low-cost and utilizes existing machines but is still evolving in the use of robust, highly conductive inks.

Inkjet printing is currently at the forefront of flexible printed electronics. It offers an attractive route to low-cost, versatile and high-resolution multilayer printing (Figure 7b) of picoliter volume functional materials on generic textile substrates with multiple functionalities, united with a cutback in material waste and water utilization. Materials offering conductive, semi-conductive and insulating properties are used in different combinations in inkjet printing, allowing the fabrication of various heterostructures ("designer devices"), which bring precisely tailored properties to have diverse functionalities and improved performance for applications. Inkjet printing of such devices will solve the reliability and manufacturing issues that current wearable devices face through the nonimpact and mask-less deposition of controlled quantities of materials in a rapid, precise, and reliable way. Inkjet printing will provide a sustainable alternative or complementary approach to the multicomponent melt-spinning of multimaterial fibers. However, the realization of fully inkjet-printed devices is extremely challenging on "rough and porous" textiles substrates with an intrinsic planar anisotropy of the general properties<sup>198</sup> and continuously changing fiber morphology due to the orientation fibers or yarns and exchange of water molecules with surroundings, respectively.

In our previous study,<sup>258</sup> all-inkjet-printed graphene-based wearable e-textiles were developed, which incorporated an organic surface pretreatment to allow printing of conductive (and potentially nonconductive and semiconductive structures) patterns via inkjet printing on rough and porous textile surfaces and reduced surface resistance by 3 orders of magnitude compared with the untreated textiles. This type of pretreatment acts as a receptor layer for water-based reduced graphene oxide (rGO)-based ink, which can then be dried at low temperatures (100 °C), lowering the risk of damaging heat-sensitive fabrics. However, the study was limited only to two-dimensional rGO-based inks with lower electrical conductivity, limiting their prospects for specific applications requiring higher electrical conductivity. In another study,<sup>285</sup> we have already shown that graphene–Ag hybrid inks could well be inkjet-printed onto pretreated cotton fabrics, allowing us to create all-inkjet-printed, highly conductive, and cost-effective wearable e-textiles. However, the study involved the application of metallic Ag, which again suffers from environmental and biocompatibility issues. Recently, research on a screen-printed, flexible and machine washable electrically conductive e-textiles platform has been carried out to store energy and monitor brain activities (i.e., through EEG).<sup>286</sup> Although screen printing is highly scalable, it suffers from poor print resolution, multistep processes for mesh preparation, and washings with material waste and water pollution.

Despite the clear potential of inkjet-printed wearable e-textiles, there have still only been a few attempts to produce wearable textiles of multimaterials via inkjet printing. Carey et al.<sup>287</sup> reported the possibility of inkjet printing of graphene/h-BN field-effect heterojunctions for wearable and textile applications. However, the reported device was neither flexible, nor washable, and not entirely fabricated from inkjet printing. The surface pretreatment was coated on fabrics, which reduced the comfort and breathability of the device and limited the



Figure 8. Environmental impact comparison among fossil-fuel-based PET, rPET, and PLA.<sup>293</sup>

print resolutions. An initial study by Kim et al.<sup>288</sup> on inkjet printing of multimaterials (metals: Ag nanoparticles, conductive polymer: PEDOT; PSS, and isolating inks: PVP) by a simple desktop inkjet printer showed promise for stretchable wearable e-textiles applications.

However, we anticipate that additional ground-breaking applications for inkjet-printed wearable e-textiles will emerge in the near future to satisfy the empirical demands for high-performance detection, data processing, computation, and display. The irresistible development of advanced inkjet printing technologies is accelerating the impact on wearable electronics textiles. For example, researchers have shown that inkjet printed material did not lose any electrical performance after more than 100 cycles.<sup>289</sup> Compared to other processing routes, inkjet printing needs no special conditions or atmospheres to create such e-textiles and offers routine reliability in diverse applications such as energy harvesting, mainstream electronic gadgets or healthcare biomedical devices.

## SUSTAINABILITY ASSESSMENT

The reasons for the growing interest in smart e-textiles and related applications can be ascribed to their great potential to establish innovative, rich as well as personalized material experiences. As such, metrics for describing e-textiles have been centered around their electronic performances and/or physical properties but less so on their sustainability. Evaluating the overall state of the e-textiles industry with sustainability aspects added to the criteria for assessment of

product success and viability, it is apparent that these “smart” effect can be obtained with less environmentally harmful materials. However, it is often the case that the “environmentally-friendly alternatives” perform much worse in comparison to typically used fossil-fuel-based and/or non-biodegradable materials. As a result, research into how materials are perceived and how they can be used interchangeably to make different user experiences is ongoing,<sup>290–292</sup> allowing manufacturers to be confident that the materials they are using are eco-friendly alternative solutions to fossil-fuel-based plastics. In this regard, a quantitative evaluation of various materials’ environmental performance over the entire wheel of life is needed alongside the existing metrics for a fair comparison of the sustainability of recently developed materials against other conventional materials for the same application. Specifically, we discuss the LCA as a vital system for selecting the best materials and processes as well as waste management techniques that promote sustainability and product quality.

**Life Cycle Analysis.** LCA enables the quantification of environmental consequences of a product, service, or material, typically allowing better-informed decisions to be made in the design of that item or the formulation of specific policies.<sup>294</sup> According to international standards, LCA is a quantitative environmental assessment method,<sup>295,296</sup> which is widely used to investigate the potential environmental consequences of operations, goods, and services from the cradle to the grave.<sup>297,298</sup> It includes the acquisition of raw materials, the manufacturing processes that lead to products, the trans-

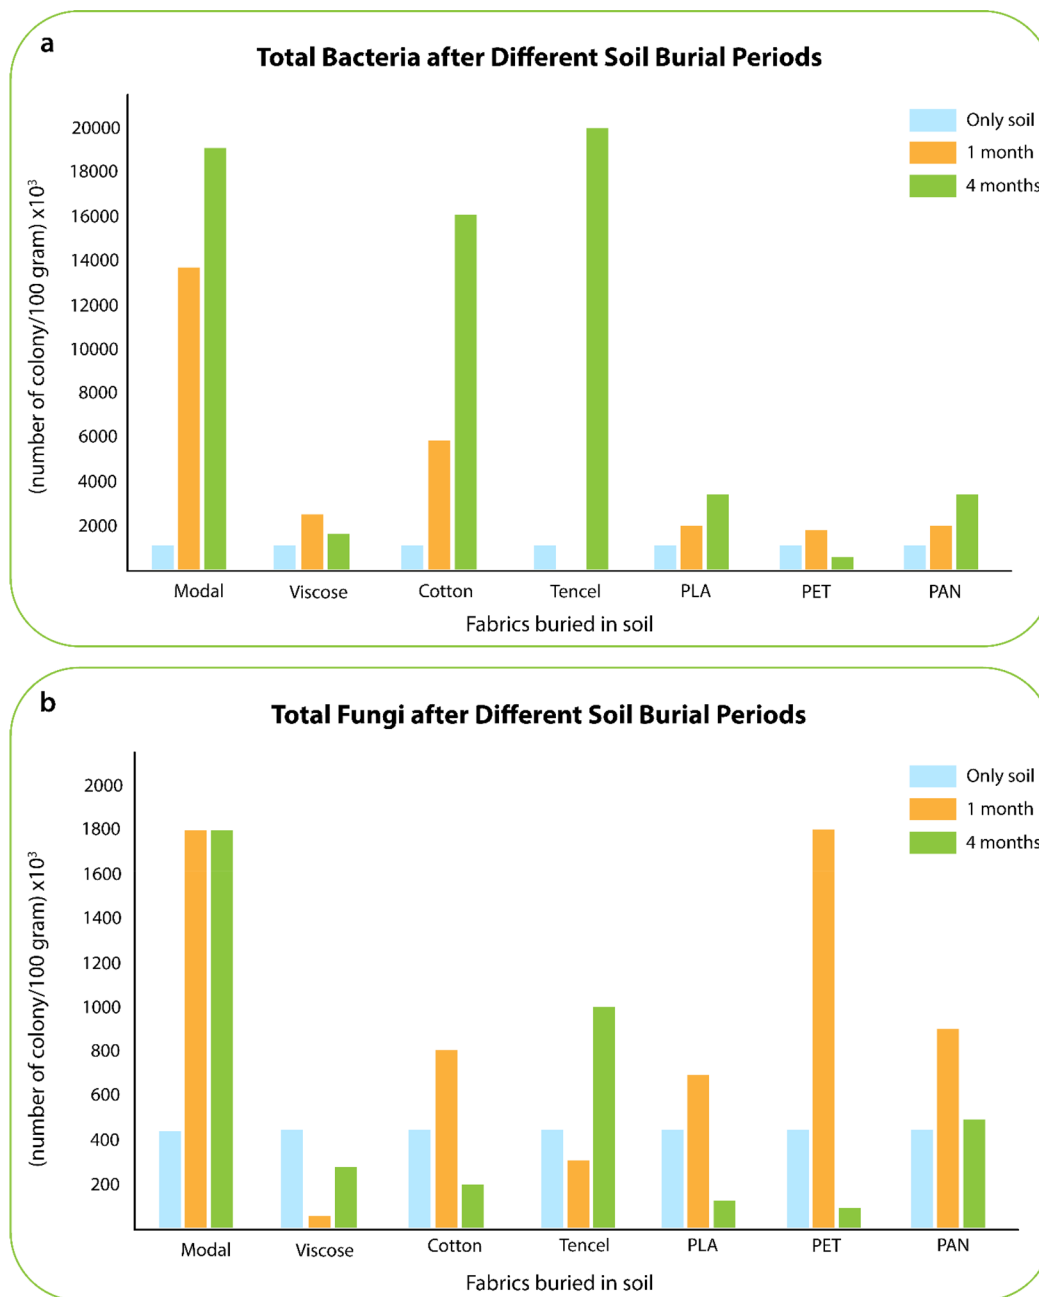


Figure 9. (a) Influence of burial interval on soil bacteria total values. (b) Influence of burial interval on soil sample total fungi values.<sup>306</sup>

portation processes, the product use phase, and the EoL stages. The impact on the environment of a product can be analyzed and contrasted with other products or possible alternative solutions using the LCA methodology. Generally, LCA evaluation starts with setting the goal and scope, followed by inventory, impact and improvement assessment. Materials and energy from the inventory stage are used in processes ranging from raw material extraction to manufacturing, distribution, transportation, use as well as maintenance, disposal, and recycling. These are then benchmarked within the framework of their impacts on factors such as global warming potential, air, water, soil pollution, ecotoxicity, and resource depletion. International standards (ISO 14040 and others) place strict control on what qualifies as an LCA and which items are permissible.<sup>294</sup>

There have been a few environmental assessment studies on products with similar characteristics to smart textiles, such as an LCA of a printed antenna<sup>299</sup> and an environmental LCA of a prospective nanosilver T-shirt.<sup>300</sup> LCAs of traditional textile products<sup>301,302</sup> based on cotton, polyester (PET), nylon, acrylic, and elastane without smart functionality are readily available, but so far, no LCA studies of smart textile products have been established. As a result, despite extensive research on LCAs of individual materials, it is not possible to draw conclusions about future LCA results of smart textile products, as the impact of the combination of textile and electronic materials in one product is still unknown. For instance, in a study,<sup>297</sup> two promising sustainable alternatives to PET plastics, 100% rPET and bio-based plastics based on PLA, were analyzed as a potential fiber base material for wearable e-textiles. The comparison of environmental impact among

fossil-fuel-based PET, rPET, and PLA on different parameters, such as climate change and toxicity, is illustrated in Figure 8. Both recycled and bio-based plastics are frequently criticized because of their limited environmental benefits compared to fossil-fuel-based plastics. Nevertheless, they are now a sustainable choice of consideration as promising alternatives to conventional fossil-fuel-based plastics. rPET offers essential ecological benefits compared to traditional fossil-fuel-based PET during the manufacturing and end-of-life management stages. Additionally, PLA shows clear environmental advantages over PET, irrespective of freshwater eutrophication and human toxicity. Hence, a lifecycle perspective on the consequences of design choices, material selection and manufacturing techniques can now guide the implementation of sustainable manufacturing.

**Biodegradability.** The capability of a substance to decompose after interactions with biological elements is known as biodegradability. The conditions of the environment, including matrix composition and temperature, will also influence the rate at which a product will breakdown/decompose.<sup>303</sup> During biodegradation, numerous microorganisms such as fungi, bacteria, worms, as well as many other species attack the materials,<sup>304</sup> for instance, during soil burial tests.<sup>305</sup> Therefore, many studies examined the total bacteria and fungi in soil samples to ascertain the biodegradation behavior patterns of textile materials.<sup>306</sup> Unmodified natural fabrics such as cotton, hemp, linen or bamboo will often decompose more quickly than synthetic textiles.<sup>307</sup> Due to their structure, synthetic fabrics like nylon, acrylic and Lycra will naturally take more time to biodegrade.<sup>308</sup> Sular and Devrim<sup>306</sup> concluded in their study that a 4 month burial interval is sufficient for assessing the biodegradation behavior of cellulosic fibers, while periods longer than 4 months are required to properly assess the biodegradation behavior of synthetic fibers (Figure 9). The biodegradability of textiles is altered according to the chemistry added/used during the manufacture of the material or the product lifecycle (regardless of whether the material started as a natural or synthetic fiber).<sup>307</sup> In addition, not all natural materials may be defined as “sustainable” due to the nature of the techniques used by researchers for assessing biopolymer biodegradation evaluations such as CO<sub>2</sub> generation, molecular weight decrease, residual weight analysis or weight loss measurement, and mathematical modeling.<sup>309,310</sup> Biodegradation of bio-based and biodegradable polymer PLA under composting conditions involves two pathways, that is, hydrolytic degradation followed by biodegradation (microbial assimilation).<sup>311</sup> The abiotic degradation<sup>310</sup> process of PLA-based biocomposites at composting temperatures is rarely discussed.

Besides bio-based and biodegradable fiber materials PLA, we have discussed type I conductive polymers in previous sections, which can be partially disintegrated, and type II conductive polymers, which can be dissolved aided dopants. However, for a product to breakdown and decompose fully into the surrounding environment, both disintegration and biodegradation must occur. Disintegration is the physical process of material breakdown. In contrast, biodegradability is the breakdown of the product back into fundamental components such as water, biomass, and gas through a chemical reaction. During biodegradability testing, the evolution of CO<sub>2</sub> or O<sub>2</sub> is measured to determine the rate of biodegradation. Establishing how a product or material disintegrates and biodegrades is achievable through testing.<sup>312</sup> The standard test methods for

determining the anaerobic biodegradation of plastic materials under accelerated landfill conditions and simulated laboratory conditions, respectively, are ASTM D5526 and ASTM D5511.<sup>313</sup> ISO 20200:2015 disintegration testing can evaluate materials for their propensity to disintegrate in a compost environment. ISO 20136 Biodegradability testing will evaluate whether the product can completely break down to a state that mimics the natural environment. This type of testing measures the capability of a product to be degraded by microorganisms, where a measure of CO<sub>2</sub> produced is used to assess the extent of biodegradation.<sup>306,314</sup>

**Recyclability.** Recyclability is the capability of a product to be reused at the end of its multiple lifetimes to reduce waste, pollution, and resource use. Recycling, on the other hand, is the process of converting waste materials into reusable materials and byproduct objects, for recycling to be economical, there must be an ample supply of the homogeneous material, a supply chain to collect and process those materials and a market-driven demand. When considering recycling products in general, fundamental factors need to be checked, such as whether the recycled material is cheaper to use than the primary virgin material. First, we must establish whether using recycled materials instead of virgin materials to make a product can save energy. Then, we should confirm if the recycled material needs to be free of contamination and whether this material can economically meet the same quality and performance standards.

One report found that only 9% of all plastics are recycled,<sup>315</sup> where only plastic PET and HDPE bottles and containers meet the minimal legal standards to be labeled as recyclable. Other materials typically end up in landfills or incinerators, polluting the environment.<sup>316</sup> An important feature of PET is that it has a well-established recycling process and can be recycled several times as rPET. Its excellent physical properties enable the manufacture of lightweight containers, which reduces the use of natural resources. Plastic is collected, cleaned, and remade into products during the recycling process. As the reuse and recycling of plastics reduce carbon emissions by at least 24%, rPET can be considered a more sustainable alternative to PET (Table 6). Postconsumer PET bottles or rPET can be mechanically recycled into sheets, films, and fibers that are used for sacking, insulations strapping packaging, and floor coverings.<sup>317</sup> It is also possible to recover feedstock materials from PET or generate fresh materials through chemical recycling, which can then be reused as fiber materials in wearable e-textiles. Acids, methanol, glycols, ammonia, and amines are used in the chemical recycling of PET, each chemical treatment (hydrolysis, methanolysis, glycolysis, ammonolysis, and aminolysis, respectively) having its individual relative merits.<sup>318,319</sup> For sustainable development, chemical recycling is the simplest route to obtaining the raw materials from which PET is initially created. The ultimate goal of chemical recycling of PET is to increase monomer yield while reducing reaction time and conducting the chemical reaction under mild conditions.<sup>320</sup> Ongoing R&D has brought about significant improvements in the chemical recycling processes.<sup>321</sup> ISO 15270:2008 directs the progress of standards and guidelines for the recycling and recovery of plastic waste.<sup>322</sup> The standard specifies the various options for recovering plastic waste from pre- and postconsumer sources.

In the long term, the recycling of nonrenewable materials, like postconsumer PET bottles, may decrease environmental pollution and protect natural ecosystems, but it is important



Table 6. Sustainability Profile of Fibrous Polymers Used Fiber in Wearable E-Textiles

polymers	raw materials	biodegradability	composting	recyclability	energy consumption	carbon footprint	environmentally friendly
rPET	postconsumer PET bottles	nonbiodegradable	noncompostable	can be recycled several times from PET which stands as rPET	35 MJ/kg <sup>3,24</sup>	0.45 kg CO <sub>2</sub> equivalent per kilogram of rPET <sup>3,24</sup>	rPET reduces energy consumption 79% and greenhouse gas emissions 67%
PLA	100% renewable source/bio-based: corn	biodegradable by microorganism	industrial-scale composting needed which is not enough in facilities, i.e., conditionally compostable	other plastic in resin identification, sometimes recyclable; but not in bulk scale	58.9 MJ/kg <sup>325</sup>	500 g CO <sub>2</sub> /kg <sup>325</sup>	production uses 65% less energy than conventional virgin plastics; bioplastics are safe as food packaging materials, though they are not microwavable


we ensure that *every* recycling operation and *every* material is sustainable and beneficial for our environment. Recycling is a prolonged and circular process, so it is vital to understand the dynamics of the evolving process. With climate change being a global concern, reducing greenhouse indicator gas emissions is key in securing environmental sustainability and ensuring the future of the world's economy and ecology.<sup>323</sup> If recycling can use less energy to make the final product than the primary usage of virgin materials, then the energy generation costs are similarly reduced. Thus, the optimized supply chain leads to less pollution, lower cost, reduced environmental damage, and thus better environmental sustainability. Further, by redirecting from landfill and minimizing the discharge of incineration gases such as carbon dioxide, carbon monoxide, and other toxic gases,<sup>323</sup> we can directly influence global warming and climate change. Therefore, recycling is a vital component of sustainability in consideration of the global environment.

## FUTURE DIRECTIONS AND OUTLOOK

Many fibers, such as cotton and silk, are biodegradable. However, their processing is increasingly unattractive and appears to be unsustainable. The use of alternative biodegradable and recycled materials again cannot safeguard against all hazards for making a sustainable wearable e-textile and may not be able to achieve the target mechanical and electrical properties alone. Fabrication techniques, end-of-life management of electronic components and materials, working environment, duration of exposure, type of associated hazards, atmospheric conditions and many other factors are related to selecting appropriate materials and techniques for sustainability.

First, considering the available "sustainable" fibers that offer bio-based, biodegradability and recyclability, materials such as PLA, rPET, and rPP may fulfill the sustainability criteria outlined in Figure 1b. Moreover, there have also been significant progress in the further development of sustainable biopolymer fibers modified with graphene or other conductive 2D materials. This modification enhances the mechanical and electrical properties of the fibers, facilitating their use in wearable electronics. This advancement represents only one of several recently reported functional materials that could be used for e-textiles, each one outperforming the previous in any given aspect. Even with this rapid development, there remains a challenge in directly comparing the performances of one type of electronic fibers/yarns/fabrics with another absence of consistent technical and testing standards. At present, the characterization system used in the evaluation of biodegradability parameters for electronic fibers/yarns/fabrics are inconsistent across different reports, making it difficult to establish a balanced comparison between different samples and processes. Further, in recognizing that the study of electronic fibers/yarns/fabrics is interdisciplinary by nature, joint cooperation by scientists across the disciplines will become increasingly necessary to establish environmentally conscious, factually consistent and simple evaluation standards. By doing so, we will increase the potential for commercializing electronic fibers/yarns/fabrics as well as incorporating them in flexible and wearable electronic textiles for immediate uses in the fields of human health monitoring and various other smart devices.


Second, the development of environmentally friendly fabrication methods for e-textiles requires actively assessing and minimizing the environmental consequences of the manufacturing, usage as well as recycling of e-textiles.<sup>293</sup>

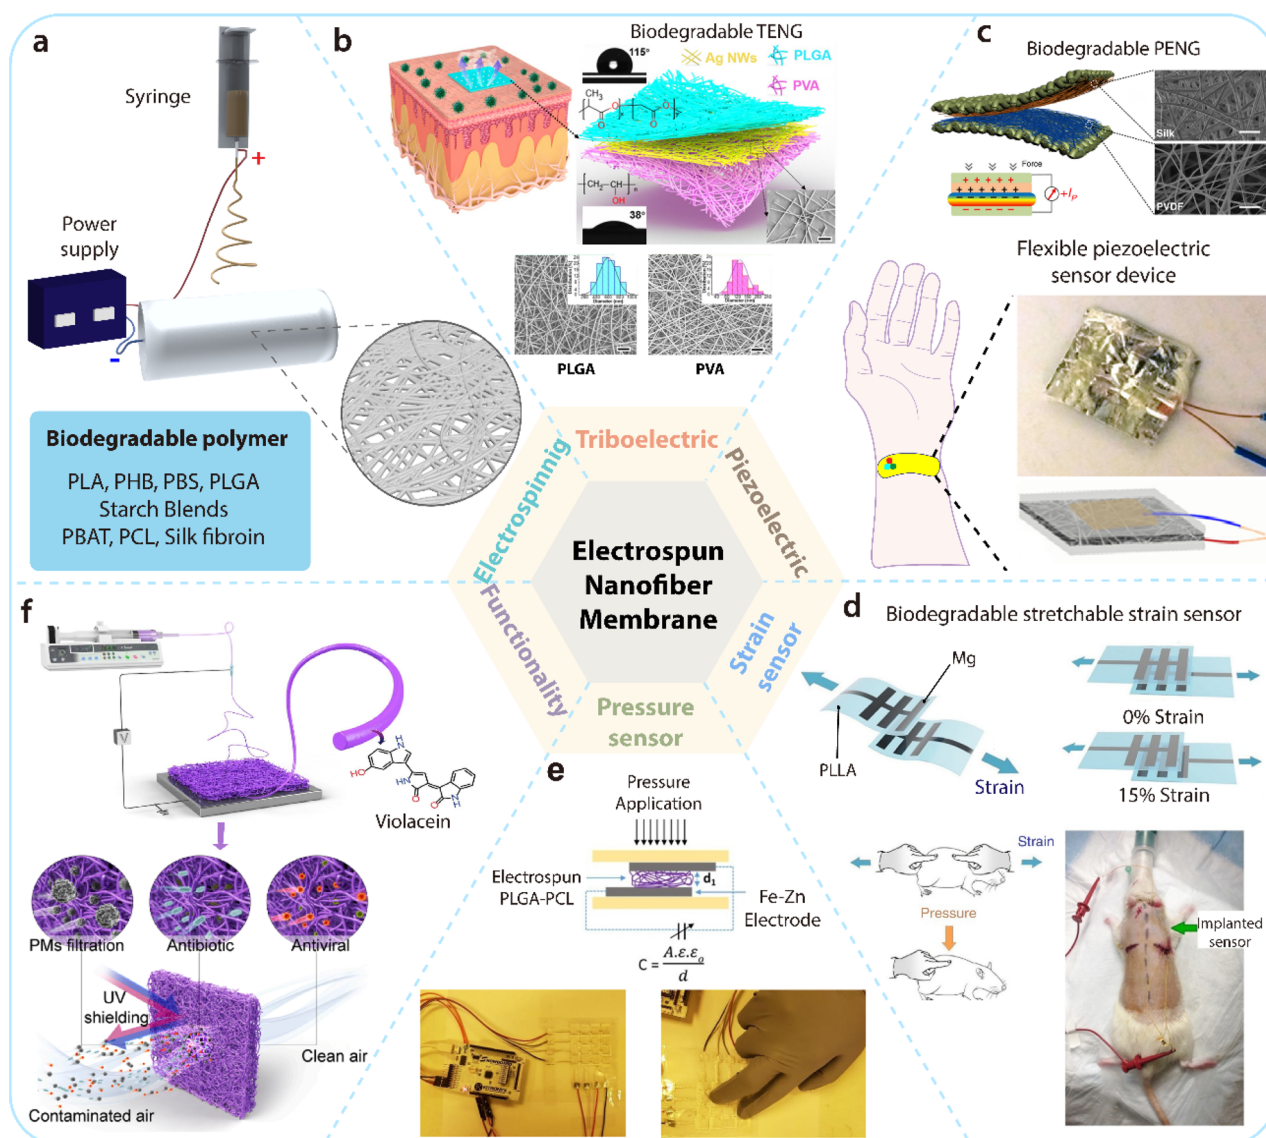

**Figure 10.** Applications of electrospun nanofiber membranes. (a) Electrospun nanofiber membrane using various biodegradable polymers. (b) Schematic illustration of the 3D network structure of the all-nanofiber TENG-based e-skin and the application scenario for the e-skin can be quickly and conformally bonded to the epidermis and is porous, biodegradable, and antimicrobial.<sup>326</sup> (c) Schematic illustration of an all-fiber hybrid triboelectric nanogenerator comprises electrodes (conductive fabric) and a triboelectric pair made of electrospun silk and PVDF nanofibers and schematic illustration of flexible sensor assembling and recording of radial artery pulse signals of a candidate. Reprinted with permission from ref 327. Copyright 2020 American Chemical Society. (d) Schematic illustration of biodegradable strain sensor. Strain sensing: When strain is applied, the two thin-film comb electrodes move about one another, causing the capacitance to change. As the strain on tendons in real life is less than 10%, the strain detecting range of 0 to 15% was chosen. Reprinted with permission from ref 332. Copyright 2018 Springer Nature. (e) Schematic illustration of a highly sensitive biodegradable pressure sensor and a commercially available pressure mapping platform coupled to a 4 by 4 array produced using a dielectric membrane and application of pressure. Reprinted with permission from ref 331. Copyright 2019 Elsevier. (f) Schematic illustration of the fabrication and properties of violacein-embedded nanofiber filter. Reprinted with permission from ref 328. Copyright 2022 Elsevier.

Producing textiles with robust mechanical, thermal, electrical and antimicrobial properties are achievable, but longevity requires alternative approaches focused on avoiding over-consumption of materials and using less harmful solvents, via inkjet printing and melt-spinning methods, respectively. To achieve a robust manufacturing technology, we need to devise simple solutions to solve the issues with inkjet nozzle clogging for a durable printing method and the improved longevity with all sorts of inks is required. Another eco-friendly direction is to reduce the number of polymer materials used in the manufacturing of e-textiles. In this regard, we may consider

the use of electrospinning as a viable alternative technique to fabricate biodegradable polymeric nanofiber membranes for use in flexible/wearable electronics applications (Figure 10). Based on their structural merits of high surface area, ease of manufacturing, and design flexibility, electrospun biodegradable membranes have shown to be promising for providing higher functionalities than conventional melt-spinning and inkjet processes.<sup>326,327,329,330</sup> One of the most studied materials are biodegradable polymers with triboelectric and piezoelectric properties, which induce the redistribution of charges in a controllable manner depending on how the

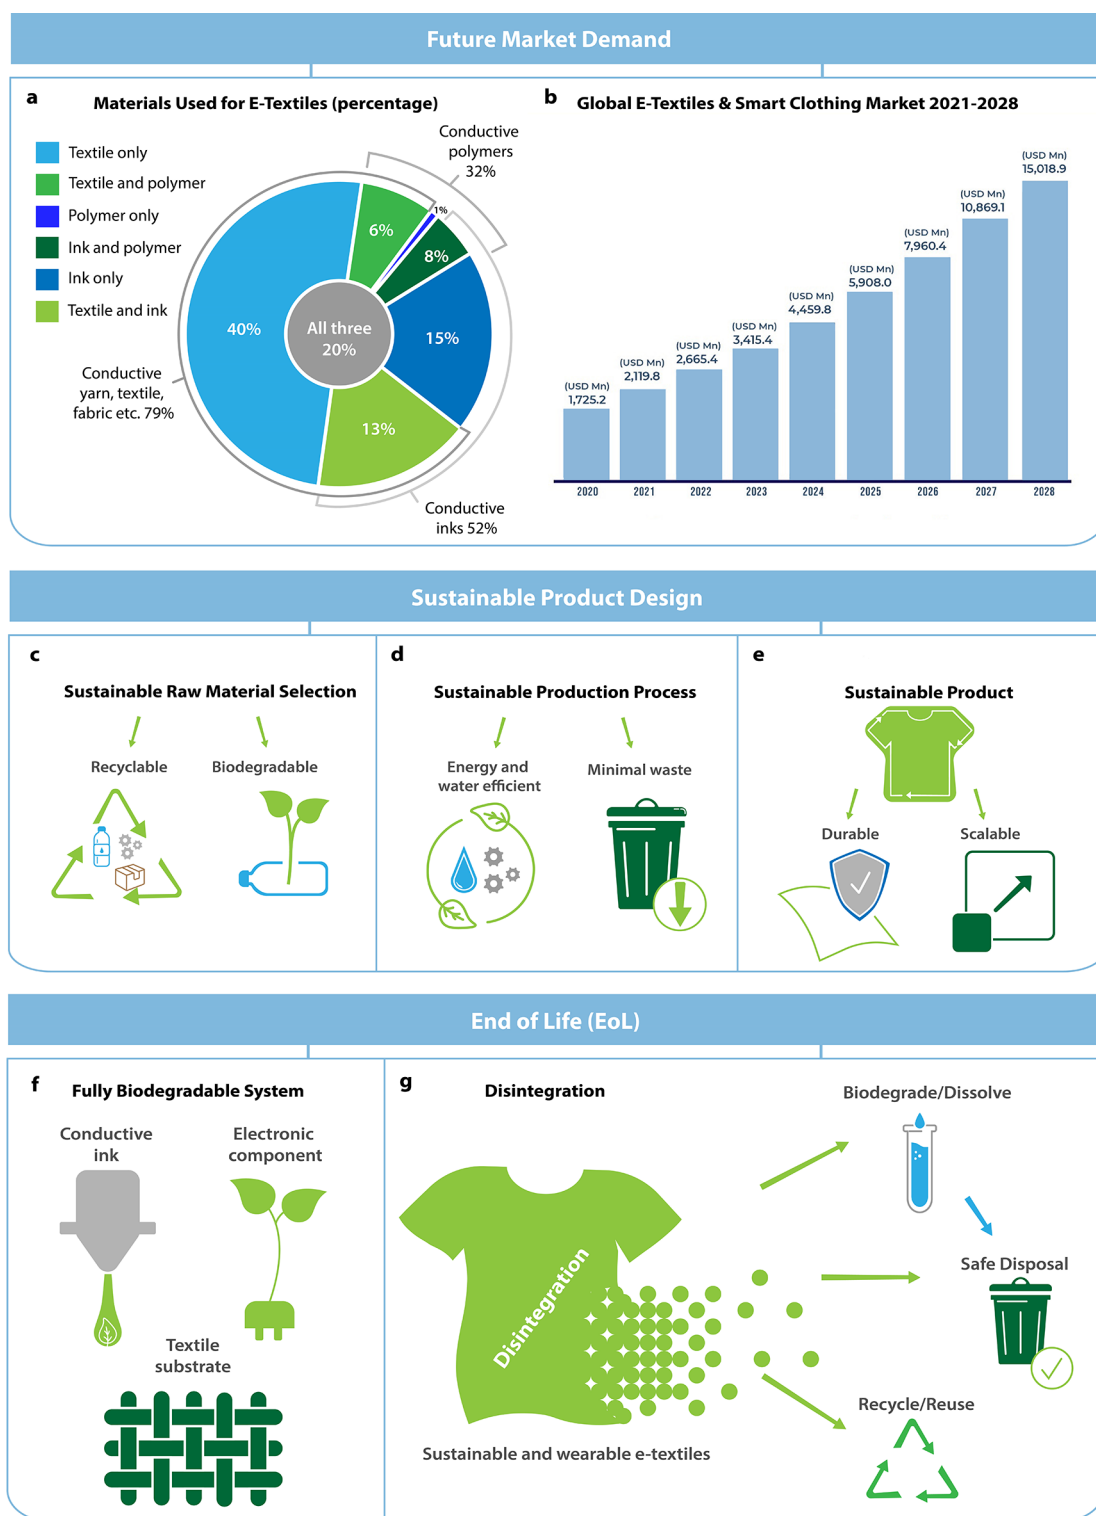

**Figure 11.** Toward environmental sustainability of wearable e-textiles. Future market demand: (a) Materials used for e-textile players 2019–2029,<sup>339,340</sup> (b) global e-textiles and smart clothing market 2021–2028.<sup>341,342</sup> Sustainable product design: (c) Sustainable raw materials selection, (d) sustainable production process, (e) sustainable product. End of life (EoL): (f) fully biodegradable system, (g) disintegration.

membrane is mechanically deformed. There are several examples in the literature that demonstrate the successful electrospinning synthesis of biodegradable tribo-/piezoelectric polymers, such as poly(lactic-co-glycolic acid) (PLGA) as well as silk fibroin, which could be used in energy harvesting and sensing applications.<sup>326,327,329,330</sup> In fact, electrospun biodegradable membranes have also been utilized as the essential

component in “electronic skin” devices, which are biocompatible sensor arrays that detect changes in multiple physicochemical parameters for providing on-site health monitoring and diagnostics.<sup>331–333</sup> Moreover, electrospinning supports the incorporation of functional molecules in the nanofiber membrane itself, which is beneficial for wearable textiles because it provides additional functionality.<sup>328,334</sup> A recent



report by Lee et al. synthesized nanofiber membranes functionalized with violacein, a naturally occurring violet-colored pigment, by electrospinning a polymer solution containing the violacein molecules.<sup>328,334</sup> As a result, in addition to the membrane's ability to filter out particulate matter (PM), the violacein-embedded membrane showed antibacterial and antiviral properties as well as UV-shielding performance. Though this polymer is not strictly biodegradable, we highlight this case study as an example of the versatility of electrospinning in adding desired functionalities to fiber membranes. Altogether, these examples demonstrate the versatility of electrospinning as a facile approach to incorporate various functionalities into the nanofiber membrane and therefore need to be considered in the design of future e-textiles.

Similarly, manufacturers should ensure that diverse data paths, parallel lines, and fool proof circuit design are used, wearable e-textiles still focus on the minimal use of materials, such as nanomaterials. Graphene has the potential to enhance the performance of different materials and alleviate their carbon footprint. Recently, it has been reported that washable, durable, and flexible graphene-based wearable e-textiles are highly scalable, cost-effective, and potentially more environmentally friendly than existing metals-based technologies.<sup>1,258,335,336</sup> Additionally, graphene and other 2D materials have sparked considerable interest in flexible and wearable electronics applications because of their electrical, mechanical<sup>73,337</sup> and other performance properties. Those very attributes may be employed in heterostructures and furthermore.<sup>338</sup> As more of a result, integrated graphene-based wearable e-textiles may be capable of dealing with both sustainability and current technical challenges associated with various applications, such as activity monitoring, early detection of highly transmissible diseases, and securing the health and well-being of frontline workers.

Moreover, fiber-based wearable electronic devices integrated into garments can offer comfort, breathability, lightweight, flexibility, and extensibility. They are engineered platforms interfacing and linking the environment, electronic devices and the human body. It also provides current possibilities for incorporating sustainable materials into energy storage devices, activity monitoring, disassembling wearable textile circuits for durability, and more extended usage, by setting up electronic hardware on the textile surface quickly and in a removable way. The quality, disposability, wearability, repairability, functionality, technological and aesthetic obsolescence will improve wearable e-textiles. Designing a sustainable wearable requires the integration of materials design, comfort, durability, recyclability and efficient removal of nonrecyclable electrical elements to enable a simple, cost-effective circularity. It is critically important to develop efficient technologies to make sustainable, breathable, flexible, and large-scale electronic fibers while guaranteeing that the performances of the electronics meet the demands of commercial application potentials of sustainable wearable e-textiles.

At present, researchers are producing at the laboratory scale sustainable electronic fibers and mainly weaving into electronic textiles by hand. Developing innovative and efficient machine fabrication technologies to form wearable e-textiles to promote large-scale fabrication is vital. In addition to this challenge, integrating multifunctions into wearable e-textiles is one of the significant challenges due to the conflict between different functions. In addition to the processes discussed above,

including sensing, energy harvesting, and energy storage, the integration of fiber/textile-based circuits, information acquisition components, personal data security functions, and computing units has been little explored.

Lastly, the user must have sufficient information to care for the textile at home with minimal environmental impact. As wearable electronics combined with textiles (e-textiles) move from the bespoke maker into production and the mass market, issues concerning the laundering, disposal and waste electronics will increasingly arise. The sustainability of e-textiles, therefore, is determined at the start of the design process. We must consider several questions, such as whether the e-textile can be disassembled and recycled with ease, whether the e-textile can be repaired in a simple manner and whether the e-textile incorporates the necessary circuitry to support off-site software updates over wireless communications. Even though different alternatives have been reported to improve the performance of wearable e-textiles, such as the introduction of more sustainable conductive materials or the design of device structures, a balance between their electrical and mechanical properties has not been achieved. Furthermore, the cycling stability and washability of electronic fibers/textiles must be improved in order to advance energy harvesting, utilization, and storage.

By addressing these challenges in the early stage development of mass production wearable e-textiles, we can expect to minimize the negative environmental impacts. Not only are these efforts beneficial at the current stage, where the e-textiles technology remains limited to highly specialized applications, but they are also expected to expedite its transition from the laboratory to the marketplace as mass commodity. Amidst this e-textile evolution, researchers will no doubt attempt to take advantage of high-performance and multifunctional materials by incorporating varying amounts of functional materials, including not only graphene and other 2D materials but also eco-friendly functional fillers, within a fibrous, bio-based, biodegradable, and recyclable textile framework.<sup>343</sup> In achieving this, we must deliver a sustainable, safe environment with associated social and economic benefits over the entire product life cycle. Thus, "3R" rules of environmental sustainability,<sup>344</sup> i.e., "reduce, reuse, and recycle," can be achieved by extracting raw materials up to the final disposal.

In summary, the market for smart wearable electronics offers great potential for sustainable materials and it is anticipated that like traditional commodity materials, wearable textiles with distinctive forms and functionalities will become a part of all of our lives in the future. They will not simply meet the requirements of everyday wear, but they will also serve the arising fields of personalized healthcare and human-machine interface, which will revolutionize our way of life. Even though some optimistic advancements have been made in certain areas, many diverse challenges remain. We believe that the continuous endeavors of researchers from different fields will further improve sustainable, wearable electronic textile design, functionality and performance, thus promoting the development of sustainable materials and manufacturing techniques toward a viable commercial future (Figure 11).

## AUTHOR INFORMATION

### Corresponding Authors

Shaile Afroj – Centre for Print Research (CFPR), University of the West of England, Bristol BS16 1QY, United Kingdom;



orcid.org/0000-0002-0469-261X; Email: shaila.afroj@uwe.ac.uk

**Il-Doo Kim** – Department of Materials Science and Engineering, Korea Advanced Institute of Science and Technology (KAIST), Daejeon 34141, Republic of Korea; orcid.org/0000-0002-9970-2218; Email: idkim@kaist.ac.kr

**Nazmul Karim** – Centre for Print Research (CFPR), University of the West of England, Bristol BS16 1QY, United Kingdom; orcid.org/0000-0002-4426-8995; Email: nazmul.karim@uwe.ac.uk

## Authors

**Marzia Dulal** – Centre for Print Research (CFPR), University of the West of England, Bristol BS16 1QY, United Kingdom

**Jaewan Ahn** – Department of Materials Science and Engineering, Korea Advanced Institute of Science and Technology (KAIST), Daejeon 34141, Republic of Korea; orcid.org/0000-0002-0136-8427

**Yujang Cho** – Department of Materials Science and Engineering, Korea Advanced Institute of Science and Technology (KAIST), Daejeon 34141, Republic of Korea

**Chris Carr** – Clothworkers' Centre for Textile Materials Innovation for Healthcare, School of Design, University of Leeds, Leeds LS2 9JT, United Kingdom

Complete contact information is available at: <https://pubs.acs.org/10.1021/acsnano.2c07723>

## Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

The authors gratefully acknowledge funding from Commonwealth Scholarship Commission (CSC) U.K. for a Ph.D. scholarship for Marzia Dulal, and UKRI Research England the Expanding Excellence in England (E3) grant. The authors also acknowledge scientific illustration support from Natalie Corner.

## VOCABULARY

**Wearable electronics**, electronic devices that are continuously worn by an individual, much like garments, to provide intelligent assistance that enhances memory, intellect, originality, interaction, and physiological senses; **Electronic textiles**, also known as e-textiles, are fabrics that can be embedded with electronic components such as batteries, lights, sensors, and microcontrollers; **Smart textiles**, materials and structures that sense and respond to environmental conditions or stimuli such as thermal, mechanical, electrical, chemical, magnetic, or other sources; **Sustainability**, the ability to cause little or no environmental damage and thus to sustain for a long time; **Biodegradability**, the ability of living organisms to degrade organic materials biologically to base substances such as water, carbon dioxide, methane, basic elements, and biomass; **Composting**, a man-made process in which biodegradation occurs under specific conditions; **Recycling**, the transformation of waste materials into reusable materials and objects

## REFERENCES

(1) Afroj, S.; Tan, S.; Abdelkader, A. M.; Novoselov, K. S.; Karim, N. Highly Conductive, Scalable, and Machine Washable Graphene-Based

E-Textiles for Multifunctional Wearable Electronic Applications. *Adv. Funct. Mater.* **2020**, *30*, 2000293.

(2) Wu, Y.; Michael, S. S.; Carmichael, T. B. Wearable E-Textiles Using a Textile-Centric Design Approach. *Acc. Chem. Res.* **2021**, *54*, 4051–4064.

(3) Ismar, E.; Kurşun Bahadır, S.; Kalaoglu, F.; Koncar, V. Futuristic Clothes: Electronic Textiles and Wearable Technologies. *Global Challenges* **2020**, *4*, 1900092.

(4) Stoppa, M.; Chiolerio, A. Wearable Electronics and Smart Textiles: A Critical Review. *Sensors (Basel)* **2014**, *14*, 11957–11992.

(5) Lian, Y.; Yu, H.; Wang, M.; Yang, X.; Li, Z.; Yang, F.; Wang, Y.; Tai, H.; Liao, Y.; Wu, J.; Wang, X.; Jiang, Y.; Tao, G. A Multifunctional Wearable E-Textile via Integrated Nanowire-coated Fabrics. *J. Mater. Chem. C* **2020**, *8*, 8399–8409.

(6) Li, Y.; Chen, W.; Lu, L. Wearable and Biodegradable Sensors for Human Health Monitoring. *ACS Appl. Bio Mater.* **2021**, *4*, 122–139.

(7) Hozumi, S.; Honda, S.; Arie, T.; Akita, S.; Takei, K. Multimodal Wearable Sensor Sheet for Health-Related Chemical and Physical Monitoring. *ACS Sens.* **2021**, *6*, 1918–1924.

(8) Shi, J.; Liu, S.; Zhang, L.; Yang, B.; Shu, L.; Yang, Y.; Ren, M.; Wang, Y.; Chen, J.; Chen, W.; Chai, Y.; Tao, X. Smart Textile-Integrated Microelectronic Systems for Wearable Applications. *Adv. Mater.* **2020**, *32*, 1901958.

(9) Karim, N.; Afroj, S.; Leech, D.; Abdelkader, A. M. Flexible and Wearable Graphene-Based E-Textiles. In *Oxide Electronics*; Ray, A., Ed.; Wiley Online Library: Hoboken, NJ, 1998; pp 565–566 and 21–49 (2021); DOI: 10.1002/9781119529538.ch2.

(10) Gurova, O.; Merritt, T. R.; Papachristos, E.; Vaajakari, J. Sustainable Solutions for Wearable Technologies: Mapping the Product Development Life Cycle. *Sustainability* **2020**, *12*, 8444.

(11) Chen, G.; Xiao, X.; Zhao, X.; Tat, T.; Bick, M.; Chen, J. Electronic Textiles for Wearable Point-of-Care Systems. *Chem. Rev.* **2022**, *122*, 3259–3291.

(12) Niinimäki, K.; Peters, G.; Dahlbo, H.; Perry, P.; Rissanen, T.; Gwilt, A. The Environmental Price of Fast Fashion. *Nat. Rev. Earth Environ.* **2020**, *1*, 189–200.

(13) Echeverria, C. A.; Handoko, W.; Pahlevani, F.; Sahajwalla, V. Cascading Use of Textile Waste for the Advancement of Fibre Reinforced Composites for Building Applications. *J. Cleaner Prod.* **2019**, *208*, 1524–1536.

(14) Chen, X.; Memon, H. A.; Wang, Y.; Marriam, I.; Tebyetekerwa, M. Circular Economy and Sustainability of the Clothing and Textile Industry. *Mater. Circular Econ.* **2021**, *3*, 12.

(15) Cole, M. A.; Elliott, R. J. R.; Shimamoto, K. Industrial Characteristics, Environmental Regulations and Air Pollution: An Analysis of the UK Manufacturing Sector. *J. Environ. Econ. Manage.* **2005**, *50*, 121–143.

(16) Nahalkova Tesarova, E.; Křížanová, A. The Impact of COVID-19 on Sustainability and Changing Consumer Behavior in the Textile Industry: Is It Significant? *Management dynamics in the knowledge economy* **2022**, *10*, 95–105.

(17) Lawton, G. Can Fashion Really Go Green? *New Sci.* **2022**, *254*, 38–45.

(18) Brown, R. Road Runner. *The Environmental Crisis Caused by Textile Waste*; <https://www.roadrunnerwm.com/blog/textile-waste-environmental-crisis> (accessed May 8, 2022).

(19) Weber, S.; Lyles, J.; Young, S. B. Fashion Interest as a Driver for Consumer Textile Waste Management: Reuse, Recycle or Disposal. *Int. J. Consum. Stud.* **2017**, *41*, 207–215.

(20) Gupta, R.; Kushwaha, A.; Dave, D.; Mahanta, N. R. Waste Management in Fashion and Textile Industry: Recent Advances and Trends, Life-Cycle Assessment, and Circular Economy. In *Emerging Trends to Approaching Zero Waste*; Hussain, C. M., Singh, S., Goswami, L., Eds.; Elsevier: Amsterdam, 2022; pp 215–242.

(21) Kaya, M. Current WEEE recycling solutions. In *Waste Electrical and Electronic Equipment Recycling*; Vegliò, F., Birloaga, I., Eds.; Woodhead Publishing: Cambridge, UK, 2018; pp 33–93.

(22) Williams, E. Environmental Effects of Information and Communications Technologies. *Nature* **2011**, *479*, 354–358.

- (23) Köhler, A.; Erdmann, L. Expected Environmental Impacts of Pervasive Computing. *Hum. Ecol. Risk Assess.* **2004**, *10*, 831–852.
- (24) Weng, W.; Chen, P.; He, S.; Sun, X.; Peng, H. Smart Electronic Textiles. *Angew. Chem., Int. Ed. Engl.* **2016**, *55*, 6140–6169.
- (25) Mohsin, M.; Rasheed, A.; Farooq, A.; Ashraf, M.; Shah, A. Environment Friendly Finishing of Sulphur, Vat, Direct and Reactive Dyed Cotton Fabric. *J. Cleaner Prod.* **2013**, *53*, 341–347.
- (26) Wakelyn, P.; Chaudhry, M. Organic Cotton: Production Practices and Post-harvest Considerations. *Sustainable Textiles*; Elsevier: Amsterdam, 2009; pp 231–301.
- (27) Raja, A. S. M.; Arputharaj, A.; Saxena, S.; Patil, P. G. Water Requirement and Sustainability of Textile Processing Industries. In *Water in Textiles and Fashion*; Muthu, S. S., Ed.; Woodhead Publishing: Cambridge, UK, 2019; pp 155–173.
- (28) Basit, A.; Latif, W.; Ashraf, M.; Rehman, A.; Iqbal, K.; Maqsood, H. S.; Jabbar, A.; Baig, S. A. Comparison of Mechanical and Thermal Comfort Properties of Tencel Blended with Regenerated Fibers and Cotton Woven Fabrics. *Autex Res. J.* **2019**, *19*, 80–85.
- (29) Chowdhury, N. T. Water Management in Bangladesh: An Analytical Review. *Water Policy* **2010**, *12*, 32–51.
- (30) Amutha, K. Environmental Impacts of Denim. In *Sustainability in Denim*; Muthu, S. S., Ed.; Woodhead Publishing: Cambridge, UK, 2017; pp 27–48; DOI: 10.1016/B978-0-08-102043-2.00002-2.
- (31) Damalas, C. A.; Telidis, G. K.; Thanos, S. D. Assessing Farmers' Practices on Disposal of Pesticide Waste After Use. *Sci. Total Environ.* **2008**, *390*, 341–345.
- (32) Wilson, C.; Tisdell, C. Why Farmers Continue to Use Pesticides Despite Environmental, Health and Sustainability Costs. *Ecol. Econ.* **2001**, *39*, 449–462.
- (33) Nannipieri, P.; Bollag, J. M. Use of Enzymes to Detoxify Pesticide-Contaminated Soils and Waters. *J. Environ. Qual.* **1991**, *20*, 510–517.
- (34) Hjelt, M.; Sepponen, S.; Moisio, M.; Nurmi, J.; McKinnon, D.; Baxter, J.; Whalen, K.; Gíslason, S. *Low-Carbon Circular Transition in the Nordics: Part II Potential Impacts of Circular Economy in Selected Areas*; Nordisk Ministerråd: Copenhagen, 2022; p 115.
- (35) Kamble, Z.; Behera, B. K. Upcycling Textile Wastes: Challenges and Innovations. *Text. Prog.* **2021**, *53*, 65–122.
- (36) Serrano-Ruiz, J. C.; Luque, R.; Sepúlveda-Escribano, A. Transformations of Biomass-derived Platform Molecules: From High Added-Value Chemicals to Fuels via Aqueous-Phase Processing. *Chem. Soc. Rev.* **2011**, *40*, 5266–5281.
- (37) Jaiswal, K. K.; Dutta, S.; Banerjee, I.; Pohrmen, C. B.; Singh, R. K.; Das, H. T.; Dubey, S.; Kumar, V. Impact of Aquatic Microplastics and Nanoplastics Pollution on Ecological Systems and Sustainable Remediation Strategies of Biodegradation and Photodegradation. *Sci. Total Environ.* **2022**, *806*, 151358.
- (38) CFDA. *Polyester*; <https://cfda.com/resources/materials/detail/polyester> (accessed June 10, 2022).
- (39) Jnr, E. B.-A.; Amisah, E. K. Maximising Ghana's Oil Resource to Boost Polyester Fibre Production in Ghana. *Fash. Tex. Rev.* **2021**, *1*, 15–30.
- (40) Kaye, L. *Triple Pundit. The Rise of Sustainable Fibers in the Fashion Industry*; <https://www.triplepundit.com/story/2015/rise-sustainable-fibers-fashion-industry/58051> (accessed April 16, 2022).
- (41) Ariaprene. *Sustainable Fabrics: 5 Reasons Why You Have to Choose Eco Friendly Fabric*; <https://ariaprene.com/blog/sustainable-fabrics-5-reasons-why-you-have-to-choose-eco-friendly-fabric/> (accessed May 20, 2022).
- (42) Hong, M.; Chen, E. Y. X. Future Directions for Sustainable Polymers. *Trends in Chemistry* **2019**, *1*, 148–151.
- (43) European Bioplastics. *Bioplastics Market Data*; [https://www.european-bioplastics.org/market/#iLightbox\[gallery\\_image\\_1\]/2](https://www.european-bioplastics.org/market/#iLightbox[gallery_image_1]/2) (accessed May 25, 2022).
- (44) Thangavelu, K.; Subramani, K. B. Sustainable Biopolymer Fibers-Production, Properties and Applications. *Sustainable Fibres for Fashion Industry*; Springer: New York, 2016; pp 109–140.
- (45) Hottle, T. A.; Bilec, M. M.; Landis, A. E. Biopolymer Production and End of Life Comparisons Using Life Cycle Assessment. *Resour. Conserv. Recycl.* **2017**, *122*, 295–306.
- (46) Riggi, E.; Santagata, G.; Malinconico, M. Bio-based and Biodegradable Plastics for Use in Crop Production. *Recent Pat. Food, Nutr. Agric.* **2011**, *3*, 49–63.
- (47) Rahman, M. H.; Bhoi, P. R. An Overview of Non-Biodegradable Bioplastics. *J. Cleaner Prod.* **2021**, *294*, 126218.
- (48) Coppola, G.; Gaudio, M. T.; Lopresto, C. G.; Calabro, V.; Curcio, S.; Chakraborty, S. Bioplastic from Renewable Biomass: A Facile Solution for A Greener Environment. *Earth Syst. Environ.* **2021**, *5*, 231–251.
- (49) Ferreira, F. V.; Cividanes, L. S.; Gouveia, R. F.; Lona, L. M. An Overview on Properties and Applications of Poly (Butylene Adipate-Co-Terephthalate)-PBAT Based Composites. *Polym. Sci. Eng.* **2019**, *59*, E7–E15.
- (50) Jiang, L.; Zhang, J. Biodegradable and Biobased Polymers. *Applied Plastics Engineering Handbook*; Elsevier: Amsterdam, 2017; pp 127–143.
- (51) Jian, J.; Xiangbin, Z.; Xianbo, H. An Overview on Synthesis, Properties and Applications of Poly (Butylene-Adipate-Co-Terephthalate)-PBAT. *Adv. Ind. Eng. Polym. Res.* **2020**, *3*, 19–26.
- (52) Zimmermann, W. Biocatalytic Recycling of Polyethylene Terephthalate Plastic. *Philos. Trans. R. Soc., A* **2020**, *378*, 20190273.
- (53) Croxatto Vega, G.; Gross, A.; Birkved, M. The Impacts of Plastic Products on Air Pollution - A Simulation Study for Advanced Life Cycle Inventories of Plastics Covering Secondary Microplastic Production. *Sustain. Prod. Consum.* **2021**, *28*, 848–865.
- (54) Finnveden, G.; Albertsson, A.-C.; Berendson, J.; Eriksson, E.; Höglund, L. O.; Karlsson, S.; Sundqvist, J.-O. Solid Waste Treatment within the Framework of Life-Cycle Assessment. *J. Cleaner Prod.* **1995**, *3*, 189–199.
- (55) Shams, M.; Alam, I.; Mahbub, M. S. Plastic pollution during COVID-19: Plastic Waste Directives and its Long-Term Impact on the Environment. *Environ. Adv.* **2021**, *5*, 100119.
- (56) Iqbal, S. M. A.; Mahgoub, I.; Du, E.; Leavitt, M. A.; Asghar, W. Advances in Healthcare Wearable Devices. *Flexible Electron.* **2021**, *5*, 9.
- (57) Know Your Plastic: Seven Plastics for Seven Recycling Possibilities. CODA2017; <https://www.coda-plastics.co.uk/blog/know-your-plastic-seven-plastics-for-seven-recycling-possibilities> (accessed June 25, 2022).
- (58) Khoonkari, M.; Haghighi, A. H.; Sefidbakht, Y.; Shekoohi, K.; Ghaderian, A. Chemical Recycling of PET Wastes with Different Catalysts. *Int. J. Polym. Sci.* **2015**, *2015*, 124524.
- (59) Sarda, P.; Hanan, J. C.; Lawrence, J. G.; Allahkarami, M. Sustainability Performance of Polyethylene Terephthalate, Clarifying Challenges and Opportunities. *J. Polym. Sci.* **2022**, *60*, 7–31.
- (60) Lepoittevin, B.; Roger, P. Poly(Ethylene Terephthalate). *Handbook of Engineering and Speciality Thermoplastics: Polyethers and Polyesters*; Wiley Online Library: Hoboken, NJ, 2011; Vol. 3, pp 97–126, DOI: 10.1002/9781118104729.ch4.
- (61) Koshti, R.; Mehta, L.; Samarth, N. Biological recycling of polyethylene terephthalate: a mini-review. *J. Polym. Environ.* **2018**, *26*, 3520–3529.
- (62) Valerio, O.; Muthuraj, R.; Codou, A. Strategies for Polymer to Polymer Recycling from Waste: Current Trends and Opportunities for Improving the Circular Economy of Polymers in South America. *Curr. Opin. Green Sustainable Chem.* **2020**, *25*, 100381.
- (63) Kakoria, A.; Chandel, S. S.; Sinha-Ray, S. Novel Supersonically Solution Blown Nanofibers from Waste PET Bottle for PM0.1–2 Filtration: from Waste to Pollution Mitigation. *Polymer* **2021**, *234*, 124260.
- (64) Foolmaun, R. K.; Ramjeeawon, T. Comparative Life Cycle Assessment and Social Life Cycle Assessment of Used Polyethylene Terephthalate (PET) Bottles in Mauritius. *Int. J. Life Cycle Assess.* **2013**, *18*, 155–171.
- (65) Foolmaun, R. K.; Ramjeeawon, T. Life Cycle Sustainability Assessments (LCSA) of Four Disposal Scenarios for Used Poly-



- ethylene Terephthalate (PET) Bottles in Mauritius. *Environ. Dev. Sustain.* **2013**, *15*, 783–806.
- (66) Zhang, R.; Ma, X.; Shen, X.; Zhai, Y.; Zhang, T.; Ji, C.; Hong, J. PET Bottles Recycling in China: An LCA Coupled with LCC Case Study of Blanket Production Made of Waste PET Bottles. *J. Environ. Manage.* **2020**, *260*, 110062.
- (67) Wu, H. Enhancements of sustainable plastics manufacturing through the proposed technologies of materials recycling and collection. *Sustainable Mater. Technol.* **2022**, *31*, No. e00376.
- (68) Majumdar, A.; Shukla, S.; Singh, A. A.; Arora, S. Circular Fashion: Properties Of Fabrics Made from Mechanically Recycled Poly-Ethylene Terephthalate (PET) Bottles. *Resour., Conserv. Recycl.* **2020**, *161*, 104915.
- (69) Ecofera. *The Top 5 Benefits of rPET Fabric*; <https://ecofera.com/blogs/news/the-top-5-benefits-of-rpet-fabric> (accessed July 12, 2022).
- (70) Fuchs, L.; Dyllick, T. Circular Economy Approaches for the Apparel Industry. Master's Thesis, Universität St. Gallen, Switzerland, 2016.
- (71) Ghosh, A. Performance Modifying Techniques for Recycled Thermoplastics. *Resour., Conserv. Recycl.* **2021**, *175*, 105887.
- (72) Joo, E.; Oh, J.-E. Challenges Facing Recycled Polyester. *Textile World*; <https://www.textileworld.com/textile-world/features/2019/07/challenges-facing-recycled-polyester/> (accessed July 22, 2022).
- (73) Islam, M. H.; Islam, M. R.; Dulal, M.; Afroj, S.; Karim, N. The Effect of Surface Treatments and Graphene-Based Modifications on Mechanical Properties of Natural Jute Fiber Composites: A Review. *iScience* **2022**, *25*, 103597.
- (74) Karim, N.; Sarker, F.; Afroj, S.; Zhang, M.; Potluri, P.; Novoselov, K. S. Sustainable and Multifunctional Composites of Graphene-Based Natural Jute Fibers. *Adv. Sustainable Syst.* **2021**, *5*, 2000228.
- (75) Afroj, S.; Islam, M.; Karim, N. *Multifunctional Graphene-Based Wearable E-Textiles*; International Conference on the Challenges, Opportunities, Innovations and Applications in Electronics Textiles, Southampton, UK (Virtual), 4.11.2020; MDPI, Switzerland, 2021; p 68; DOI: 10.3390/proceedings2021068011.
- (76) Barakzehi, M.; Montazer, M.; Sharif, F.; Norby, T.; Chatzitzakis, A. A Textile-Based Wearable Supercapacitor Using Reduced Graphene Oxide/Polypyrrole Composite. *Electrochim. Acta* **2019**, *305*, 187–196.
- (77) 'Smart' Plastic Brings Flexible, Wearable Electronic Devices One Step Closer. *Plastic Today*; <https://www.plasticstoday.com/materials/smart-plastic-brings-flexible-wearable-electronic-devices-one-step-closer> (accessed July 22, 2022).
- (78) Loong, L. M.; Lee, W.; Qiu, X.; Yang, P.; Kawai, H.; Saeys, M.; Ahn, J.-H.; Yang, H. Flexible MgO Barrier Magnetic Tunnel Junctions. *Adv. Mater.* **2016**, *28*, 4983–4990.
- (79) Abdelkader, A. M.; Karim, N.; Vallés, C.; Afroj, S.; Novoselov, K. S.; Yeates, S. G. Ultraflexible and Robust Graphene Supercapacitors Printed on Textiles for Wearable Electronics Applications. *2D Mater.* **2017**, *4*, 035016.
- (80) Uddin, M. A.; Afroj, S.; Hasan, T.; Carr, C.; Novoselov, K. S.; Karim, N. Environmental Impacts of Personal Protective Clothing Used to Combat COVID-19. *Adv. Sustainable Syst.* **2022**, *6*, 2100176.
- (81) Halonen, N.; Pálvolgyi, P. S.; Bassani, A.; Fiorentini, C.; Nair, R.; Spigno, G.; Kordas, K. Bio-Based Smart Materials for Food Packaging and Sensors – A Review. *Front. Mater.* **2020**, DOI: 10.3389/fmats.2020.00082.
- (82) Dent, A. Bioplastics & Biopolymers; Are They Really Biodegradable? *Dieline*; [https://thedieline.com/blog/2018/10/15/bioplastics--biopolymers-are-they-really-biodegradable?](https://thedieline.com/blog/2018/10/15/bioplastics--biopolymers-are-they-really-biodegradable/) (accessed June 10, 2022).
- (83) Weinstein, J. E.; Dekle, J. L.; Leads, R. R.; Hunter, R. A. Degradation of Bio-Based and Biodegradable Plastics in A Salt Marsh Habitat: Another Potential Source of Microplastics in Coastal Waters. *Mar. Pollut. Bull.* **2020**, *160*, 111518.
- (84) Shafqat, A.; Tahir, A.; Mahmood, A.; Tabinda, A. B.; Yasar, A.; Pugazhendhi, A. A Review on Environmental Significance Carbon Foot Prints of Starch Based Bio-Plastic: A Substitute of Conventional Plastics. *Biocatal. Agric. Biotechnol.* **2020**, *27*, 101540.
- (85) Ingrao, C.; Tricase, C.; Cholewa-Wójcik, A.; Kawecka, A.; Rana, R.; Siracusa, V. Polylactic Acid Trays for Fresh-Food Packaging: A Carbon Footprint Assessment. *Sci. Total Environ.* **2015**, *537*, 385–398.
- (86) Saba, N.; Jawaid, M.; Sultan, M.; Alothman, O. Y. Green Biocomposites for Structural Applications. *Green Biocomposites*; Springer: New York, 2017; pp 1–27.
- (87) Stolberg, T. Applicability of Bio-Based Polymer Packaging in the Meal Kit Context-A Case Study with HelloFresh. Master's Thesis, Lund University, Sweden, 2019; <https://lup.lub.lu.se/luur/download?func=downloadFile&recordId=8988743&fileId=8988756>.
- (88) Koller, M.; Salerno, A.; Dias, M.; Reiterer, A.; Brauneegg, G. Modern Biotechnological Polymer Synthesis: A Review. *Food Technol. Biotechnol.* **2010**, *48*, 255–269.
- (89) Shen, L.; Haufe, J.; Patel, M. K. Product Overview and Market Projection of Emerging Bio-Based Plastics PRO-BIP 2009. *Report for European polysaccharide network of excellence (EPNOE) and European bioplastics* **2009**, *243*, 1–245.
- (90) Babu, R. P.; O'Connor, K.; Seeram, R. Current Progress on Bio-Based Polymers and Their Future Trends. *Prog. Biomater.* **2013**, *2*, 1–16.
- (91) Raj, T.; Chandrasekhar, K.; Naresh Kumar, A.; Kim, S.-H. Lignocellulosic Biomass as Renewable Feedstock for Biodegradable and Recyclable Plastics Production: A Sustainable Approach. *Renewable Sustainable Energy Rev.* **2022**, *158*, 112130.
- (92) Kumar, S.; Krishnan, S.; Samal, S. K.; Mohanty, S.; Nayak, S. K. Itaconic Acid Used As A Versatile Building Block for the Synthesis of Renewable Resource-Based Resins and Polyesters for Future Prospective: A Review. *Polym. Int.* **2017**, *66*, 1349–1363.
- (93) Lunt, J. Large-Scale Production, Properties and Commercial Applications of Polylactic Acid Polymers. *Polym. Degrad. Stab.* **1998**, *59*, 145–152.
- (94) Šešlija, S.; Nešić, A.; Škorić, M. L.; Krušić, M. K.; Santagata, G.; Malinconico, M. *Pectin/Carboxymethylcellulose Films As A Potential Food Packaging Material*; Macromolecular Symposia, Wiley Online Library: Hoboken, NJ, 2018; p 1600163.
- (95) Avérous, L. Chapter 21 - Polylactic Acid: Synthesis, Properties and Applications. In *Monomers, Polymers and Composites from Renewable Resources*; Belgacem, M. N., Gandini, A., Eds.; Elsevier: Amsterdam, 2008; pp 433–450.
- (96) Greene, J. Biodegradation of Compostable Plastics in Green Yard-Waste Compost Environment. *J. Polym. Environ.* **2007**, *15*, 269–273.
- (97) Mitchell, M.; Link, R.; Danyluk, C.; Erickson, R.; Burrows, S.; Auras, R. Industrial Composting of Poly(Lactic Acid) Bottles. *J. Test. Eval.* **2010**, *38*, 102685.
- (98) Rezvani Ghomi, E.; Khosravi, F.; Saedi Ardahaei, A.; Dai, Y.; Neisiany, R. E.; Foroughi, F.; Wu, M.; Das, O.; Ramakrishna, S. The Life Cycle Assessment for Polylactic Acid (PLA) to Make it a Low-Carbon Material. *Polymers.* **2021**, *13*, 1854.
- (99) Is PLA Biodegradable and Compostable? *Radius*; <https://madebyradius.com/blogs/good-to-know/is-pla-biodegradable-and-compostable> (accessed May 16, 2022).
- (100) Turco, R.; Ortega-Toro, R.; Tesser, R.; Mallardo, S.; Collazo-Bigliardi, S.; Chiralt Boix, A.; Malinconico, M.; Ripa, M.; Di Serio, M.; Santagata, G. Poly (Lactic Acid)/Thermoplastic Starch Films: Effect of Cardoon Seed Epoxidized Oil on their Chemicophysical, Mechanical, and Barrier Properties. *Coatings* **2019**, *9*, 574.
- (101) Karim, M. N.; Rigout, M.; Yeates, S. G.; Carr, C. Surface Chemical Analysis of the Effect of Curing Conditions on the Properties of Thermally-Cured Pigment Printed Poly (Lactic Acid) Fabrics. *Dyes Pigm.* **2014**, *103*, 168–174.
- (102) Karim, M. N.; Afroj, S.; Rigout, M.; Yeates, S. G.; Carr, C. Towards UV-curable Inkjet Printing of Biodegradable Poly (Lactic Acid) Fabrics. *J. Mater. Sci.* **2015**, *50*, 4576–4585.

- (103) Griffin, M.; Naderi, N.; Kalaskar, D. M.; Malins, E.; Becer, R.; Thornton, C. A.; Whitaker, I. S.; Mosahebi, A.; Butler, P. E. M.; Seifalian, A. M. Evaluation of Sterilisation Techniques for Regenerative Medicine Scaffolds Fabricated with Polyurethane Nonbiodegradable and Bioabsorbable Nanocomposite Materials. *Int. J. Biomater.* **2018**, *2018*, 6565783.
- (104) Shibata, M.; Oyamada, S.; Kobayashi, S.-i.; Yaginuma, D. Mechanical Properties and Biodegradability of Green Composites Based on Biodegradable Polyesters and Lyocell Fabric. *J. Appl. Polym. Sci.* **2004**, *92*, 3857–3863.
- (105) Zhong, Y.; Godwin, P.; Jin, Y.; Xiao, H. Biodegradable Polymers and Green-Based Antimicrobial Packaging Materials: A Mini-Review. *Adv. Ind. Eng. Polym. Res.* **2020**, *3*, 27–35.
- (106) Chen, C.-H.; Yao, Y.-Y.; Tang, H.-C.; Lin, T.-Y.; Chen, Dave W.; Cheng, K.-W. Long-Term Antibacterial Performances of Biodegradable Polylactic Acid Materials with Direct Absorption of Antibiotic Agents. *RSC Adv.* **2018**, *8*, 16223–16231.
- (107) Gao, D.; Zhao, R.; Yang, X.; Chen, F.; Ning, X. Bicomponent PLA Nanofiber Nonwovens as Highly Efficient Filtration Media for Particulate Pollutants and Pathogens. *Membr.* **2021**, *11*, 819.
- (108) Auras, R.; Harte, B.; Selke, S. An Overview of Polylactides as Packaging Materials. *Macromol. Biosci.* **2004**, *4*, 835–84.
- (109) Yu, Z.; Ji, Y.; Bourg, V.; Bilgen, M.; Meredith, J. C. Chitin- and Cellulose-Based Sustainable Barrier Materials: A Review. *Emergent Mater.* **2020**, *3*, 919–936.
- (110) Lavermicocca, P.; Valerio, F.; Visconti, A. Antifungal Activity of Phenylactic Acid against Molds Isolated from Bakery Products. *Appl. Environ. Microbiol.* **2003**, *69*, 634–640.
- (111) Gan, L.; Geng, A.; Wu, Y.; Wang, L.; Fang, X.; Xu, L.; Mei, C. Antibacterial, Flexible, and Conductive Membrane Based on MWCNTs/Ag Coated Electro-Spun PLA Nanofibrous Scaffolds as Wearable Fabric for Body Motion Sensing. *Polymers* **2020**, *12*, 120.
- (112) Islam, G. M. N.; Collie, S.; Qasim, M.; Ali, M. A. Highly Stretchable and Flexible Melt Spun Thermoplastic Conductive Yarns for Smart Textiles. *Nanomaterials* **2020**, *10*, 2324.
- (113) Hempel, M.; Nezich, D.; Kong, J.; Hofmann, M. A Novel Class of Strain Gauges Based on Layered Percolative Films of 2D Materials. *Nano Lett.* **2012**, *12*, 5714–5718.
- (114) Al-Halhouli, A. a.; Albagdady, A.; Alawadi, J. F.; Abeeleh, M. A. Monitoring Symptoms of Infectious Diseases: Perspectives for Printed Wearable Sensors. *Micromachines* **2021**, *12*, 620.
- (115) Su, C.-H.; Chiu, H.-L.; Chen, Y.-C.; Yesilmen, M.; Schulz, F.; Ketelsen, B.; Vossmeier, T.; Liao, Y.-C. Highly Responsive PEG/Gold Nanoparticle Thin-Film Humidity Sensor via Inkjet Printing Technology. *Langmuir* **2019**, *35*, 3256–3264.
- (116) Deflection Temperature Testing of Plastics. *Matweb*; <http://www.matweb.com/p/deflection-temperature.aspx> (accessed June 16, 2022).
- (117) Yamamoto, Y.; Yamamoto, D.; Takada, M.; Naito, H.; Arie, T.; Akita, S.; Takei, K. Efficient Skin Temperature Sensor and Stable Gel-Less Sticky ECG Sensor for a Wearable Flexible Healthcare Patch. *Adv. Healthcare Mater.* **2017**, *6*, 1700495.
- (118) Yamamoto, D.; Nakata, S.; Kanao, K.; Arie, T.; Akita, S.; Takei, K. All-Printed, Planar-Type Multi-Functional Wearable Flexible Patch Integrated with Acceleration, Temperature, and ECG Sensors, 2017 IEEE 30th International Conference on Micro Electro Mechanical Systems (MEMS), 22–26 Jan. 2017; pp 239–242.
- (119) Voutilainen, J.; Happonen, T.; Häkkinen, J.; Fabritius, T. All Silk-Screen Printed Polymer-Based Remotely Readable Temperature Sensor. *IEEE Sens. J.* **2015**, *15*, 723–733.
- (120) Lochner, C. M.; Khan, Y.; Pierre, A.; Arias, A. C. All-Organic Optoelectronic Sensor for Pulse Oximetry. *Nat. Commun.* **2014**, *5*, 5745.
- (121) Baloda, S.; Ansari, Z. A.; Singh, S.; Gupta, N. Development and Analysis of Graphene Nanoplatelets (GNPs)-Based Flexible Strain Sensor for Health Monitoring Applications. *IEEE Sens. J.* **2020**, *20*, 13302–13309.
- (122) Cheng, Y.; Wang, R.; Sun, J.; Gao, L. A Stretchable and Highly Sensitive Graphene-Based Fiber for Sensing Tensile Strain, Bending, and Torsion. *Adv. Mater.* **2015**, *27*, 7365–7371.
- (123) Eom, J.; Jaisutti, R.; Lee, H.; Lee, W.; Heo, J.-S.; Lee, J.-Y.; Park, S. K.; Kim, Y.-H. Highly Sensitive Textile Strain Sensors and Wireless User-Interface Devices Using All-Polymeric Conducting Fibers. *ACS Appl. Mater. Interfaces* **2017**, *9*, 10190–10197.
- (124) Chatterjee, K.; Tabor, J.; Ghosh, T. K. Electrically Conductive Coatings for Fiber-Based E-Textiles. *Fibers* **2019**, *7*, 51.
- (125) Cheng, Y.; Wang, R.; Zhai, H.; Sun, J. Stretchable Electronic Skin Based on Silver Nanowire Composite Fiber Electrodes for Sensing Pressure, Proximity, and Multidirectional Strain. *Nanoscale* **2017**, *9*, 3834–3842.
- (126) Wang, D.; Li, D.; Zhao, M.; Xu, Y.; Wei, Q. Multifunctional Wearable Smart Device Based on Conductive Reduced Graphene Oxide/Polyester Fabric. *Appl. Surf. Sci.* **2018**, *454*, 218–226.
- (127) Yu, R.; Zhu, C.; Wan, J.; Li, Y.; Hong, X. Review of Graphene-Based Textile Strain Sensors, with Emphasis on Structure Activity Relationship. *Polymers* **2021**, *13*, 151.
- (128) Yang, Z.; Pang, Y.; Han, X.-l.; Yang, Y.; Ling, J.; Jian, M.; Zhang, Y.; Yang, Y.; Ren, T.-L. Graphene Textile Strain Sensor with Negative Resistance Variation for Human Motion Detection. *ACS Nano* **2018**, *12*, 9134–9141.
- (129) Reddy, K. R.; Gandla, S.; Gupta, D. Highly Sensitive, Rugged, and Wearable Fabric Strain Sensor Based on Graphene Clad Polyester Knitted Elastic Band for Human Motion Monitoring. *Adv. Mater. Interfaces* **2019**, *6*, 1900409.
- (130) Cao, X.; Halder, A.; Tang, Y.; Hou, C.; Wang, H.; Duus, J. Ø.; Chi, Q. Engineering Two-Dimensional Layered Nanomaterials for Wearable Biomedical Sensors and Power Devices. *Mater. Chem. Front.* **2018**, *2*, 1944–1986.
- (131) Sun, K. C.; Ali, M.; Anjum, A. S.; Noh, J. W.; Sahito, I. A.; Jeong, S. H. Facile Preparation of a Wet-Laid Based Graphite Nanoplate and Polyethylene Terephthalate Staple Fiber Composite for Textile-Structured Rollable Electronics. *J. Electron. Mater.* **2021**, *50*, 5433–5441.
- (132) Zhuo, T.; Chen, Z.; Xin, B.; Xu, Y.; Song, Y.; He, S.; Wang, S. Surface Modification of PE/PET by Two-Step Method with Graphene and Silver Nanoparticles for Enhanced Electrical Conductivity. *J. Ind. Text.* **2022**, *0*, 8246–8266.
- (133) Babaahmadi, V.; Montazer, M.; Gao, W. Low Temperature Welding of Graphene on PET with Silver Nanoparticles Producing Higher Durable Electro-Conductive Fabric. *Carbon* **2017**, *118*, 443–451.
- (134) Jin, Y.; Ka, D.; Jang, S.; Heo, D.; Seo, J.; Jung, H.; Jeong, K.; Lee, S. Fabrication of Graphene Based Durable Intelligent Personal Protective Clothing for Conventional and Non-Conventional Chemical Threats. *Nanomaterials* **2021**, *11*, 940.
- (135) Tang, D.; Wang, Q.; Wang, Z.; Liu, Q.; Zhang, B.; He, D.; Wu, Z.; Mu, S. Highly Sensitive Wearable Sensor Based on a Flexible Multi-Layer Graphene Film Antenna. *Sci. Bull.* **2018**, *63*, 574–579.
- (136) Xie, J.; Chen, Q.; Shen, H.; Li, G. Review-Wearable Graphene Devices for Sensing. *J. Electrochem. Soc.* **2020**, *167*, 037541.
- (137) Kang, M.; Kim, J.; Jang, B.; Chae, Y.; Kim, J.-H.; Ahn, J.-H. Graphene-Based Three-Dimensional Capacitive Touch Sensor for Wearable Electronics. *ACS Nano* **2017**, *11*, 7950–7957.
- (138) Lee, Y.; Kim, J.; Jang, B.; Kim, S.; Sharma, B. K.; Kim, J.-H.; Ahn, J.-H. Graphene-Based Stretchable/Wearable Self-Powered Touch Sensor. *Nano Energy* **2019**, *62*, 259–267.
- (139) Wu, X.; Ma, Y.; Zhang, G.; Chu, Y.; Du, J.; Zhang, Y.; Li, Z.; Duan, Y.; Fan, Z.; Huang, J. Thermally Stable, Biocompatible, and Flexible Organic Field-Effect Transistors and their Application in Temperature Sensing Arrays for Artificial Skin. *Adv. Funct. Mater.* **2015**, *25*, 2138–2146.
- (140) Jost, K.; Dion, G.; Gogotsi, Y. Textile Energy Storage in Perspective. *J. Mater. Chem. A* **2014**, *2*, 10776–10787.
- (141) Wang, Z. L.; Wu, W. Nanotechnology-Enabled Energy Harvesting for Self-Powered Micro-/Nanosystems. *Angew. Chem., Int. Ed.* **2012**, *51*, 11700–11721.



- (142) Zeng, W.; Shu, L.; Li, Q.; Chen, S.; Wang, F.; Tao, X.-M. Fiber-Based Wearable Electronics: A Review of Materials, Fabrication, Devices, and Applications. *Adv. Mater.* **2014**, *26*, 5310–5336.
- (143) Wang, Y.; Wang, L.; Yang, T.; Li, X.; Zang, X.; Zhu, M.; Wang, K.; Wu, D.; Zhu, H. Wearable and Highly Sensitive Graphene Strain Sensors for Human Motion Monitoring. *Adv. Funct. Mater.* **2014**, *24*, 4666–4670.
- (144) Park, J. J.; Hyun, W. J.; Mun, S. C.; Park, Y. T.; Park, O. O. Highly Stretchable and Wearable Graphene Strain Sensors with Controllable Sensitivity for Human Motion Monitoring. *ACS Appl. Mater. Interfaces* **2015**, *7*, 6317–24.
- (145) Boland, C. S.; Khan, U.; Backes, C.; O'Neill, A.; McCauley, J.; Duane, S.; Shanker, R.; Liu, Y.; Jurewicz, I.; Dalton, A. B.; Coleman, J. N. Sensitive, High-Strain, High-Rate Bodily Motion Sensors Based on Graphene–Rubber Composites. *ACS Nano* **2014**, *8*, 8819–8830.
- (146) Liu, L.; Yu, Y.; Yan, C.; Li, K.; Zheng, Z. Wearable Energy-Dense and Power-Dense Supercapacitor Yarns Enabled by Scalable Graphene–Metallic Textile Composite Electrodes. *Nat. Commun.* **2015**, *6*, 7260.
- (147) Yoo, T.-H.; Sang, B.-I.; Hwang, D. K. One-Dimensional Ingazno Field-Effect Transistor on a Polyimide Wire Substrate for an Electronic Textile. *J. Korean Phys. Soc.* **2016**, *68*, 599–603.
- (148) Mattila, H. Yarn to Fabric: Intelligent Fabrics in Textiles and Fashion. *Materials Design and Technology*; Woodhead: Cambridge, UK, 2015; pp 355–376.
- (149) Yang, Z. High Performance Fiber-Shaped Solar Cells. *Pure Appl. Chem.* **2016**, *88*, 113–117.
- (150) Zhang, N.; Chen, J.; Huang, Y.; Guo, W.; Yang, J.; Du, J.; Fan, X.; Tao, C. A Wearable All-Solid Photovoltaic Textile. *Adv. Mater.* **2016**, *28*, 263–269.
- (151) Tseghai, G. B.; Malengier, B.; Fante, K. A.; Nigusse, A. B.; Van Langenhove, L. Integration of Conductive Materials with Textile Structures, an Overview. *Sensors (Basel)* **2020**, *20*, 6910.
- (152) Bayram, Y.; Zhou, Y.; Shim, B. S.; Xu, S.; Zhu, J.; Kotov, N. A.; Volakis, J. L. E-Textile Conductors and Polymer Composites for Conformal Lightweight Antennas. *IEEE Trans. Antennas Propag.* **2010**, *58*, 2732–2736.
- (153) Han, J.-W.; Meyyappan, M. Copper Oxide Resistive Switching Memory for E-Textile. *AIP Adv.* **2011**, *1*, 032162.
- (154) Schwarz-Pfeiffer, A.; Hakuzimana, J.; Kaczynska, A.; Banaszczyk, J.; Westbroek, P.; McAdams, E.; Moody, G.; Chronis, I.; Priniotakis, G.; Mey, G.; Tseles, D.; Van Langenhove, L. Gold Coated Para-Aramid Yarns Through Electroless Deposition. *Surf. Coat. Technol.* **2010**, *204*, 1412–1418.
- (155) Jeong, S.; Woo, K.; Kim, D.; Lim, S.; Kim, J. S.; Shin, H.; Xia, Y.; Moon, J. Controlling the Thickness of the Surface Oxide Layer on Cu Nanoparticles for the Fabrication of Conductive Structures by Ink-Jet Printing. *Adv. Funct. Mater.* **2008**, *18*, 679–686.
- (156) Xu, L.; Yang, G.; Jing, H.; Wei, J.; Han, Y. Ag-Graphene Hybrid Conductive Ink for Writing Electronics. *Nanotechnology* **2014**, *25*, 055201.
- (157) Irimia-Vladu, M.; Glowacki, E. D.; Voss, G.; Bauer, S.; Sariciftci, N. S. Green and Biodegradable Electronics. *Mater. Today* **2012**, *15*, 340–346.
- (158) Kamyshny, A.; Magdassi, S. Conductive Nanomaterials for Printed Electronics. *Small* **2014**, *10*, 3515–3535.
- (159) Jung, Y. H.; Zhang, H.; Gong, S.; Ma, Z. High-Performance Green Semiconductor Devices: Materials, Designs, and Fabrication. *Semicond. Sci. Technol.* **2017**, *32*, 3002.
- (160) Venezuela, J.; Dargusch, M. S. The Influence of Alloying and Fabrication Techniques on the Mechanical Properties, Biodegradability and Biocompatibility of Zinc: A Comprehensive Review. *Acta Biomater.* **2019**, *87*, 1–40.
- (161) Hermawan, H. Updates on the Research and Development of Absorbable Metals for Biomedical Applications. *Prog. Biomater.* **2018**, *7*, 93–110.
- (162) Hosseini, E. S.; Dervin, S.; Ganguly, P.; Dahiya, R. Biodegradable Materials for Sustainable Health Monitoring Devices. *ACS Appl. Bio Mater.* **2021**, *4*, 163–194.
- (163) Li, R.; Liu, Q.; Gui, J.; Gu, D.; Hu, H. Indoor Relocalization in Challenging Environments with Dual-Stream Convolutional Neural Networks. *IEEE Trans. Autom. Sci. Eng.* **2018**, *15*, 651–662.
- (164) Singh, R.; Bathaei, M. J.; Istif, E.; Beker, L. A Review of Bioresorbable Implantable Medical Devices: Materials, Fabrication, and Implementation. *Adv. Healthcare Mater.* **2020**, *9*, 2000790.
- (165) Yu, X.; Shou, W.; Mahajan, B. K.; Huang, X.; Pan, H. Materials, Processes, and Facile Manufacturing for Bioresorbable Electronics: A Review. *Adv. Mater.* **2018**, *30*, 1707624.
- (166) Xu, Y.; Xu, X.; Guo, M.; Zhang, G.; Wang, Y. Research Progresses and Challenges of Flexible Zinc Battery. *Front. Chem.* **2022**, *10*, 827563–827563.
- (167) Hosseini, N. R.; Lee, J.-S. Biocompatible and Flexible Chitosan-Based Resistive Switching Memory with Magnesium Electrodes. *Adv. Funct. Mater.* **2015**, *25*, 5586–5592.
- (168) La Mattina, A. A.; Mariani, S.; Barillaro, G. Bioresorbable Materials on the Rise: From Electronic Components and Physical Sensors to In Vivo Monitoring Systems. *Adv. Sci.* **2020**, *7*, 1902872.
- (169) Yin, L.; Cheng, H.; Mao, S.; Haasch, R.; Liu, Y.; Xie, X.; Hwang, S.-W.; Jain, H.; Kang, S.-K.; Su, Y.; Li, R.; Huang, Y.; Rogers, J. A. Dissolvable Metals for Transient Electronics. *Adv. Funct. Mater.* **2014**, *24*, 645–658.
- (170) Zhang, J.; Li, H.; Wang, W.; Huang, H.; Pei, J.; Qu, H.; Yuan, G.; Li, Y. The Degradation and Transport Mechanism of a Mg-Nd-Zn-Zr Stent in Rabbit Common Carotid Artery: A 20-Month Study. *Acta Biomater.* **2018**, *69*, 372–384.
- (171) Nocera, A. D.; Comín, R.; Salvatierra, N. A.; Cid, M. P. Development of 3D Printed Fibrillar Collagen Scaffold for Tissue Engineering. *Biomed. Microdevices* **2018**, *20*, 26.
- (172) Morsada, Z.; Hossain, M. M.; Islam, M. T.; Mobin, M. A.; Saha, S. Recent Progress in Biodegradable and Bioresorbable Materials: from Passive Implants to Active Electronics. *Appl. Mater. Today* **2021**, *25*, 101257.
- (173) Park, S.-J.; Son, Y.-R.; Heo, Y.-J. Prospective Synthesis Approaches to Emerging Materials for Supercapacitor. *Emerging Materials for Energy Conversion*; Elsevier: Amsterdam, 2018; pp 185–208.
- (174) Li, R.; Wang, L.; Yin, L. Materials and Devices for Biodegradable and Soft Biomedical Electronics. *Materials* **2018**, *11*, 2108.
- (175) Balint, R.; Cassidy, N. J.; Cartmell, S. H. Conductive polymers: Towards a Smart Biomaterial for Tissue Engineering. *Acta Biomater.* **2014**, *10*, 2341–2353.
- (176) Mokhtar, S.; Alvarez de Eulate, E.; Yamada, M.; Prow, T.; Evans, D. Conducting Polymers in Wearable Devices. *Med. Devices Sens.* **2020**, *4*, e10160.
- (177) Oh, K. W.; Hong, K. H.; Kim, S. H. Electrically Conductive Textiles by *In Situ* Polymerization of Aniline. *J. Appl. Polym. Sci.* **1999**, *74*, 2094–2101.
- (178) Zhang, Y.; Dong, A.; Wang, Q.; Fan, X.; Cavaco-Paulo, A.; Zhang, Y. Conductive Cotton Prepared by Polyaniline *In Situ* Polymerization Using Laccase. *Appl. Biochem. Biotechnol.* **2014**, *174*, 820–831.
- (179) Patil, A. J.; Deogaonkar, S. C. A Novel Method of *In Situ* Chemical Polymerization of Polyaniline for Synthesis of Electrically Conductive Cotton Fabrics. *Text. Res. J.* **2012**, *82*, 1517–1530.
- (180) Lin, T.; Wang, L.; Wang, X.; Kaynak, A. Polymerising Pyrrole on Polyester Textiles and Controlling the Conductivity through Coating Thickness. *Thin Solid Films* **2005**, *479*, 77–82.
- (181) Harlin, A.; Ferenets, M. Introduction to Conductive Materials. In *Intelligent Textiles and Clothing*; Mattila, H. R., Ed.; Woodhead Publishing: Sawston, Cambridge, 2006; pp 217–238.
- (182) Ismar, E.; Sarac, A. S. Facile Synthesis of Poly[1-P (Tolylsulfonyl) Pyrrole] via Ce (IV)-Pyrrole Redox Initiating System and Polyacrylonitrile Blended Nanofibers. *Polym. Adv. Technol.* **2018**, *29*, 2440–2448.
- (183) Liu, Y.; Pharr, M.; Salvatore, G. A. Lab-on-Skin: A Review of Flexible and Stretchable Electronics for Wearable Health Monitoring. *ACS Nano* **2017**, *11*, 9614–9635.

- (184) Kaltenbrunner, M.; Sekitani, T.; Reeder, J.; Yokota, T.; Kuribara, K.; Tokuhara, T.; Drack, M.; Schwödiauer, R.; Graz, I.; Bauer-Gogonea, S.; Bauer, S.; Someya, T. An Ultra-Lightweight Design for Imperceptible Plastic Electronics. *Nature* **2013**, *499*, 458–463.
- (185) Feig, V. R.; Tran, H.; Bao, Z. Biodegradable Polymeric Materials in Degradable Electronic Devices. *ACS Cent. Sci.* **2018**, *4*, 337–348.
- (186) Li, W.; Liu, Q.; Zhang, Y.; Li, C. a.; He, Z.; Choy, W. C. H.; Low, P. J.; Sonar, P.; Kyaw, A. K. K. Biodegradable Materials and Green Processing for Green Electronics. *Adv. Mater.* **2020**, *32*, 2001591.
- (187) Worfolk, B. J.; Andrews, S. C.; Park, S.; Reinspach, J.; Liu, N.; Toney, M. F.; Mannsfeld, S. C. B.; Bao, Z. Ultrahigh Electrical Conductivity in Solution-Sheared Polymeric Transparent Films. *Proc. Natl. Acad. Sci. U. S. A.* **2015**, *112*, 14138.
- (188) Islam, M. R.; Afroj, S.; Novoselov, K. S.; Karim, N. Smart Electronic Textile-Based Wearable Supercapacitors. *Adv. Science* **2022**, 2203856.
- (189) Kandasamy, S. K.; Kandasamy, K. Recent Advances in Electrochemical Performances of Graphene Composite (Graphene-Polyaniline/Polypyrrole/Activated Carbon/Carbon Nanotube) Electrode Materials for Supercapacitor: A Review. *J. Inorg. Organomet. Polym. Mater.* **2018**, *28*, 559–584.
- (190) Stepien, L.; Roch, A.; Tkachov, R.; Leupolt, B.; Han, L.; van Ngo, N.; Leyens, C. Thermal Operating Window for PEDOT:PSS Films and Its Related Thermoelectric Properties. *Synth. Met.* **2017**, *225*, 49–54.
- (191) Oh, J. Y.; Kim, S.; Baik, H.-K.; Jeong, U. Conducting Polymer Dough for Deformable Electronics. *Adv. Mater.* **2016**, *28*, 4455–4461.
- (192) Wang, Y.; Zhu, C.; Pfattner, R.; Yan, H.; Jin, L.; Chen, S.; Molina-Lopez, F.; Lissel, F.; Liu, J.; Rabiah, N. I.; Chen, Z.; Chung, J. W.; Linder, C.; Toney, M. F.; Murmann, B.; Bao, Z. A Highly Stretchable, Transparent, and Conductive Polymer. *Sci. Adv.* **2017**, *3*, No. e1602076.
- (193) Bozó, É.; Ervasti, H.; Halonen, N.; Shokouh, S. H. H.; Tolvanen, J.; Pitkänen, O.; Järvinen, T.; Pálvölgyi, P. S.; Szamosvölgyi, A.; Sági, A.; Konya, Z.; Zacccone, M.; Montalbano, L.; De Brauer, L.; Nair, R.; Martínez-Nogués, V.; San Vicente Laurent, L.; Dietrich, T.; Fernández de Castro, L.; Kordas, K. Bioplastics and Carbon-Based Sustainable Materials, Components, and Devices: Toward Green Electronics. *ACS Appl. Mater. Interfaces* **2021**, *13*, 49301–49312.
- (194) Wang, J. Carbon-Nanotube Based Electrochemical Biosensors: A Review. *Electroanalysis* **2005**, *17*, 7–14.
- (195) Tan, S.; Islam, M. R.; Li, H.; Fernando, A.; Afroj, S.; Karim, N. Highly Scalable, Sensitive and Ultraflexible Graphene-Based Wearable E-Textiles Sensor for Bio-Signal Detection. *Adv. Sensor Res.* **2022**, DOI: 10.1002/adsr.202200010.
- (196) Li, M.; Guo, Y.; Wei, Y.; MacDiarmid, A. G.; Lelkes, P. I. Electrospinning Polyaniline-Contained Gelatin Nanofibers for Tissue Engineering Applications. *Biomaterials* **2006**, *27*, 2705–2715.
- (197) Bhang, S. H.; Jeong, S. I.; Lee, T.-J.; Jun, I.; Lee, Y. B.; Kim, B.-S.; Shin, H. Electroactive Electrospun Polyaniline/Poly[(L-lactide)-co-( $\epsilon$ -caprolactone)] Fibers for Control of Neural Cell Function. *Macromol. Biosci.* **2012**, *12*, 402–411.
- (198) Jeong, S. I.; Jun, I. D.; Choi, M. J.; Nho, Y. C.; Lee, Y. M.; Shin, H. Development of Electroactive and Elastic Nanofibers that Contain Polyaniline and Poly(L-lactide-co- $\epsilon$ -caprolactone) for the Control of Cell Adhesion. *Macromol. Biosci.* **2008**, *8*, 627–637.
- (199) Runge, M. B.; Dadsetan, M.; Baltrusaitis, J.; Knight, A. M.; Ruesink, T.; Lazcano, E. A.; Lu, L.; Windebank, A. J.; Yaszemski, M. J. The Development of Electrically Conductive Polycaprolactone Fumarate-Polypyrrole Composite Materials for Nerve Regeneration. *Biomaterials* **2010**, *31*, 5916–5926.
- (200) Runge, M. B.; Dadsetan, M.; Baltrusaitis, J.; Ruesink, T.; Lu, L.; Windebank, A. J.; Yaszemski, M. J. Development of Electrically Conductive Oligo(polyethylene glycol) Fumarate-Polypyrrole Hydrogels for Nerve Regeneration. *Biomacromolecules* **2010**, *11*, 2845–2853.
- (201) Wang, S.; Guan, S.; Wang, J.; Liu, H.; Liu, T.; Ma, X.; Cui, Z. Fabrication and Characterization of Conductive Poly(3,4-Ethylenedioxythiophene) Doped with Hyaluronic Acid/Poly(L-Lactic Acid) Composite Film for Biomedical Application. *J. Biosci. Bioeng.* **2017**, *123*, 116–125.
- (202) Winters, C.; Zamboni, F.; Beaucamp, A.; Culebras, M.; Collins, M. N. Synthesis of Conductive Polymeric Nanoparticles with Hyaluronic Acid Based Bioactive Stabilizers for Biomedical Applications. *Mater. Today Chem.* **2022**, *25*, 100969.
- (203) Kaur, G.; Adhikari, R.; Cass, P.; Bown, M.; Gunatillake, P. Electrically Conductive Polymers and Composites for Biomedical Applications. *RSC Adv.* **2015**, *5*, 37553–37567.
- (204) Shi, G.; Rouabhia, M.; Wang, Z.; Dao, L. H.; Zhang, Z. A Novel Electrically Conductive and Biodegradable Composite Made of Polypyrrole Nanoparticles and Polylactide. *Biomaterials* **2004**, *25*, 2477–2488.
- (205) Lee, J. Y.; Bashur, C. A.; Goldstein, A. S.; Schmidt, C. E. Polypyrrole-Coated Electrospun PLGA Nanofibers for Neural Tissue Applications. *Biomaterials* **2009**, *30*, 4325–4335.
- (206) Molino, B. Z.; Fukuda, J.; Molino, P. J.; Wallace, G. G. Redox Polymers for Tissue Engineering. *Front. in Med. Technol.* **2021**, *3*, 666973.
- (207) Li, L.; Ge, J.; Guo, B.; Ma, P. X. In Situ Forming Biodegradable Electroactive Hydrogels. *Polym. Chem.* **2014**, *5*, 2880–2890.
- (208) Lohse, M. S.; Bein, T. Covalent Organic Frameworks: Structures, Synthesis, and Applications. *Adv. Funct. Mater.* **2018**, *28*, 1705553.
- (209) Rivers, T. J.; Hudson, T. W.; Schmidt, C. E. Synthesis of a Novel, Biodegradable Electrically Conducting Polymer for Biomedical Applications. *Adv. Funct. Mater.* **2002**, *12*, 33–37.
- (210) Guo, B.; Finne-Wistrand, A.; Albertsson, A.-C. Enhanced Electrical Conductivity by Macromolecular Architecture: Hyperbranched Electroactive and Degradable Block Copolymers Based on Poly( $\epsilon$ -caprolactone) and Aniline Pentamer. *Macromolecules* **2010**, *43*, 4472–4480.
- (211) Xu, C.; Huang, Y.; Yezpez, G.; Wei, Z.; Liu, F.; Bugarin, A.; Tang, L.; Hong, Y. Development of Dopant-Free Conductive Bioelastomers. *Sci. Rep.* **2016**, *6*, 34451.
- (212) Karimi, P.; Rizkalla, A. S.; Mequanint, K. Versatile Biodegradable Poly(Ester Amide)s Derived from  $\alpha$ -Amino Acids for Vascular Tissue Engineering. *Materials* **2010**, *3*, 2346–2368.
- (213) Tropp, J.; Rivnay, J. Design of Biodegradable and Biocompatible Conjugated Polymers for Bioelectronics. *J. Mater. Chem. C* **2021**, *9*, 13543–13556.
- (214) Cui, H.; Liu, Y.; Deng, M.; Pang, X.; Zhang, P.; Wang, X.; Chen, X.; Wei, Y. Synthesis of Biodegradable and Electroactive Tetraaniline Grafted Poly(Ester Amide) Copolymers For Bone Tissue Engineering. *Biomacromolecules* **2012**, *13*, 2881–9.
- (215) Huang, L.; Zhuang, X.; Hu, J.; Lang, L.; Zhang, P.; Wang, Y.; Chen, X.; Wei, Y.; Jing, X. Synthesis of Biodegradable and Electroactive Multiblock Polylactide and Aniline Pentamer Copolymer for Tissue Engineering Applications. *Biomacromolecules* **2008**, *9*, 850–858.
- (216) Chiong, J. A.; Tran, H.; Lin, Y.; Zheng, Y.; Bao, Z. Integrating Emerging Polymer Chemistries for the Advancement of Recyclable, Biodegradable, and Biocompatible Electronics. *Adv. Sci.* **2021**, *8*, 2101233.
- (217) Huang, L.; Hu, J.; Lang, L.; Wang, X.; Zhang, P.; Jing, X.; Wang, X.; Chen, X.; Lelkes, P. I.; Macdiarmid, A. G.; Wei, Y. Synthesis and Characterization of Electroactive and Biodegradable ABA Block Copolymer of Polylactide and Aniline Pentamer. *Biomaterials* **2007**, *28*, 1741–51.
- (218) Guimard, N. K.; Sessler, J. L.; Schmidt, C. E. Towards a Biocompatible, Biodegradable Copolymer Incorporating Electroactive Oligothiophene Units. *Macromolecules* **2009**, *42*, 502–511.
- (219) Ren, J. Environmentally-Friendly Graphene Textiles Could Enable Wearable Electronics. *PHYS.ORG*; <https://phys.org/news/>

2016-11-environmentally-friendly-graphene-textiles-enable-wearable.html (accessed July 12, 2022).

(220) Fuente, J. D. L. Graphene Structure. *Graphenea*; <https://www.graphenea.com/pages/graphene-properties#.Ypie9HbMK3A> (accessed July 15, 2022).

(221) Al Sheheri, S. Z.; Al-Amshany, Z. M.; Al Sulami, Q. A.; Tashkandi, N. Y.; Hussein, M. A.; El-Shishtawy, R. M. The Preparation of Carbon Nanofillers and Their Role on the Performance of Variable Polymer Nanocomposites. *Des. Monomers Polym.* **2019**, *22*, 8–53.

(222) Facchetti, A. Semiconductors for Organic Transistors. *Mater. Today* **2007**, *10*, 28–37.

(223) Qiao, Y.; Guo, Y.; Yu, C.; Zhang, F.; Xu, W.; Liu, Y.; Zhu, D. Diketopyrrolopyrrole-Containing Quinoidal Small Molecules for High-Performance, Air-Stable, and Solution-Processable n-Channel Organic Field-Effect Transistors. *J. Am. Chem. Soc.* **2012**, *134*, 4084–4087.

(224) Chen, H.; Guo, Y.; Yu, G.; Zhao, Y.; Zhang, J.; Gao, D.; Liu, H.; Liu, Y. Highly  $\pi$ -Extended Copolymers with Diketopyrrolopyrrole Moieties for High-Performance Field-Effect Transistors. *Adv. Mater.* **2012**, *24*, 4618–4622.

(225) Gelmi, A.; Ljunggren, M. K.; Rafat, M.; Jager, E. W. H. Influence of Conductive Polymer Doping on the Viability of Cardiac Progenitor Cells. *J. Mater. Chem. B* **2014**, *2*, 3860–3867.

(226) Liu, T.; Xie, D.; Xu, J.; Pan, C. Structure and Doping Optimization of IDT-Based Copolymers for Thermoelectrics. *Polymers* **2020**, *12*, 1463.

(227) Puangprasert, S.; Prueksasit, T. Health Risk Assessment of Airborne Cd, Cu, Ni and Pb for Electronic Waste Dismantling Workers in Buriram Province, Thailand. *J. Environ. Management* **2019**, *252*, 109601.

(228) Guo, J.; Luo, X.; Tan, S.; Ogunseitan, O. A.; Xu, Z. Thermal Degradation and Pollutant Emission from Waste Printed Circuit Boards Mounted with Electronic Components. *J. Hazard Mater.* **2020**, *382*, 121038.

(229) Lei, T.; Guan, M.; Liu, J.; Lin, H. C.; Pfaltner, R.; Shaw, L.; McGuire, A. F.; Huang, T. C.; Shao, L.; Cheng, K. T.; Tok, J. B.; Bao, Z. Biocompatible and Totally Disintegrable Semiconducting Polymer for Ultrathin and Ultralightweight Transient Electronics. *Proc. Natl. Acad. Sci. U S A* **2017**, *114*, 5107–5112.

(230) Wang, M.; Baek, P.; Akbarinejad, A.; Barker, D.; Travas-Sejdic, J. Conjugated Polymers and Composites for Stretchable Organic Electronics. *J. Mater. Chem. C* **2019**, *7*, 5534–5552.

(231) Pérez Madrigal, M. M.; Giannotti, M. I.; Oncins, G.; Franco, L.; Armelin, E.; Puiggali, J.; Sanz, F.; del Valle, L. J.; Alemán, C. Bioactive Nanomembranes of Semiconductor Polythiophene and Thermoplastic Polyurethane: Thermal, Nanostructural and Nano-mechanical Properties. *Polym. Chem.* **2013**, *4*, 568–583.

(232) Jin, S. H.; Kang, S.-K.; Cho, I.-T.; Han, S. Y.; Chung, H. U.; Lee, D. J.; Shin, J.; Baek, G. W.; Kim, T.-i.; Lee, J.-H.; Rogers, J. A. Water-Soluble Thin Film Transistors and Circuits Based on Amorphous Indium–Gallium–Zinc Oxide. *ACS Appl. Mater. Interfaces* **2015**, *7*, 8268–8274.

(233) Kaur, M.; Lee, D. H.; Yang, D. S.; Um, H. A.; Cho, M. J.; Kang, J. S.; Choi, D. H. Diketopyrrolopyrrole-Bitellurophene Containing a Conjugated Polymer and Its High Performance Thin-Film Transistor Sensor for Bromine Detection. *Chem. Commun.* **2014**, *50*, 14394–14396.

(234) Zou, X.; Cui, S.; Li, J.; Wei, X.; Zheng, M. Diketopyrrolopyrrole Based Organic Semiconductor Materials for Field-Effect Transistors. *Front. Chem.* **2021**, *9*, 671294–671294.

(235) Madkhali, N.; Alqahtani, H. R.; Alterary, S.; Albrithen, H. A.; Laref, A.; Hassib, A. Characterization and Electrochemical Deposition of Natural Melanin Thin Films. *Arabian J. Chem.* **2020**, *13*, 4987–4993.

(236) Vahidzadeh, E.; Kalra, A. P.; Shankar, K. Melanin-Based Electronics: from Proton Conductors to Photovoltaics and Beyond. *Biosens. Bioelectron.* **2018**, *122*, 127–139.

(237) Hopkins, J.; Travaglini, L.; Lauto, A.; Cramer, T.; Fraboni, B.; Seidel, J.; Mawad, D. Photoactive Organic Substrates for Cell Stimulation: Progress and Perspectives. *Adv. Mater. Technol.* **2019**, *4*, (238) Pradhan, S.; Brooks, A. K.; Yadavalli, V. K. Nature-Derived Materials for the Fabrication of Functional Biodevices. *Mater. Today Bio.* **2020**, *7*, 100065.

(239) Rogers, J. A.; Lagally, M. G.; Nuzzo, R. G. Synthesis, Assembly and Applications of Semiconductor Nanomembranes. *Nature* **2011**, *477*, 45–53.

(240) Sarkar, A.; Lee, Y.; Ahn, J.-H. Si Nanomembranes: Material Properties and Applications. *Nano Research* **2021**, *14*, 3010–3032.

(241) Li, R.; Wang, L.; Kong, D.; Yin, L. Recent Progress on Biodegradable Materials and Transient Electronics. *Bioact. Mater.* **2018**, *3*, 322–333.

(242) Hwang, S.-W.; Tao, H.; Kim, D.-H.; Cheng, H.; Song, J.-K.; Rill, E.; Brenckle, M. A.; Panilaitis, B.; Won, S. M.; Kim, Y.-S.; Song, Y. M.; Yu, K. J.; Ameen, A.; Li, R.; Su, Y.; Yang, M.; Kaplan, D. L.; Zakin, M. R.; Slepian, M. J.; Huang, Y.; Omenetto, F. G.; Rogers, J. A. A Physically Transient Form of Silicon Electronics. *Science* **2012**, *337*, 1640–1644.

(243) Yin, L.; Farimani, A. B.; Min, K.; Vishal, N.; Lam, J.; Lee, Y. K.; Aluru, N. R.; Rogers, J. A. Mechanisms for Hydrolysis of Silicon Nanomembranes as Used in Bioresorbable Electronics. *Adv. Mater.* **2015**, *27*, 1857–1864.

(244) Dagdeviren, C.; Hwang, S.-W.; Su, Y.; Kim, S.; Cheng, H.; Gur, O.; Haney, R.; Omenetto, F. G.; Huang, Y.; Rogers, J. A. Transient, Biocompatible Electronics and Energy Harvesters Based on ZnO. *Small* **2013**, *9*, 3398–3404.

(245) Kang, S.-K.; Park, G.; Kim, K.; Hwang, S.-W.; Cheng, H.; Shin, J.; Chung, S.; Kim, M.; Yin, L.; Lee, J. C.; Lee, K.-M.; Rogers, J. A. Dissolution Chemistry and Biocompatibility of Silicon- and Germanium-Based Semiconductors for Transient Electronics. *ACS Appl. Mater. Interfaces* **2015**, *7*, 9297–9305.

(246) Hwang, S.-W.; Park, G.; Cheng, H.; Song, J.-K.; Kang, S.-K.; Yin, L.; Kim, J.-H.; Omenetto, F. G.; Huang, Y.; Lee, K.-M.; Rogers, J. A. 25th Anniversary Article: Materials for High-Performance Biodegradable Semiconductor Devices. *Adv. Mater.* **2014**, *26*, 1992–2000.

(247) Hwang, S.-W.; Park, G.; Edwards, C.; Corbin, E. A.; Kang, S.-K.; Cheng, H.; Song, J.-K.; Kim, J.-H.; Yu, S.; Ng, J.; Lee, J. E.; Kim, J.; Yee, C.; Bhaduri, B.; Su, Y.; Omenetto, F. G.; Huang, Y.; Bashir, R.; Goddard, L.; Popescu, G.; Lee, K.-M.; Rogers, J. A. Dissolution Chemistry and Biocompatibility of Single-Crystalline Silicon Nanomembranes and Associated Materials for Transient Electronics. *ACS Nano* **2014**, *8*, 5843–5851.

(248) Li, H.; Li, J.; Jiao, X.; Li, K.; Sun, Y.; Zhou, W.; Shen, Y.; Qian, J.; Chang, A.; Wang, J.; Zhu, H. Characterization of the Biosynthetic Pathway of Nucleotide Sugar Precursor UDP-Glucose During Sphingan WL Gum Production in *Sphingomonas* Sp. WG. *J. Biotechnol.* **2019**, *302*, 1–9.

(249) Choi, Y.; Koo, J.; Rogers, J. A. Inorganic Materials for Transient Electronics in Biomedical Applications. *MRS Bull.* **2020**, *45*, 103–112.

(250) He, Q.; Li, X.; Zhang, J.; Zhang, H.; Briscoe, J. P–N junction-based ZnO Wearable Textile Nanogenerator for Biomechanical Energy Harvesting. *Nano Energy* **2021**, *85*, 105938.

(251) Dielectric Constant and its Effects on the Properties of a Capacitor. *Passive Components*; <https://passive-components.eu/the-dielectric-constant-and-its-effects-on-the-properties-of-a-capacitor/#:~:text=Materials%20with%20high%20dielectric%20constants,materials%20have%20high%20electric%20susceptibility> (accessed June 5, 2022).

(252) Cao, Y.; Urich, K. E. Biodegradable and Biocompatible Polymers for Electronic Applications: A Review. *J. Bioact. Compat. Polym.* **2019**, *34*, 3–15.

(253) Salvado, R.; Loss, C.; Gonçalves, R.; Pinho, P. Textile Materials for the Design of Wearable Antennas: A Survey. *Sensors (Basel)* **2012**, *12*, 15841–15857.



- (254) Yadav, A.; Singh, V. K.; Chaudhary, M.; Mohan, H. A Review on Wearable Textile Antenna. *J. Tel. Switch. Sys. Net.* **2015**, *2*, 37–41.
- (255) Das, S. Electronic Components, Parts and Their Function. *Electronics and You*; <http://www.electronicandyou.com/blog/electronic-components-parts-and-their-function.html> (accessed July 5, 2022).
- (256) Perdignes Sánchez, F.; Quero Reboul, J. M. Printed Circuit Boards: The Layers' Functions for Electronic and Biomedical Engineering. *Micromachines* **2022**, *13*, 460.
- (257) Kallmayer, C.; Simon, E. *Large Area Sensor Integration in Textiles*; International Multi-Conference on Systems, Signals & Devices, IEEE, 2012; pp 1–5.
- (258) Karim, N.; Afroj, S.; Malandraki, A.; Butterworth, S.; Beach, C.; Rigout, M.; Novoselov, K. S.; Casson, A. J.; Yeates, S. G. All Inkjet-Printed Graphene-Based Conductive Patterns for Wearable E-Textile Applications. *J. Mater. Chem. C* **2017**, *5*, 11640–11648.
- (259) Cameron, M. H. The Walkaide® Functional Electrical Stimulation System-A Novel Therapeutic Approach for Foot Drop in Central Nervous System Disorders. *Eur. Neurol. Rev.* **2010**, *5*, 18–20.
- (260) Menon, S.; George, E.; Osterman, M.; Pecht, M. High Lead Solder (Over 85%) Solder in the Electronics Industry: RoHS Exemptions and Alternatives. *J. Mater. Sci.: Mater. Electron.* **2015**, *26*, 4021–4030.
- (261) Nnorom, I. C.; Osibanjo, O. Overview of Electronic Waste (E-Waste) Management Practices and Legislations, and their Poor Applications in the Developing Countries. *Resour., Conserv. Recycl.* **2008**, *52*, 843–858.
- (262) Ossevoort, S. Improving the sustainability of smart textiles. *Multidisciplinary know-how for smart-textiles developers*; Elsevier: Amsterdam, 2013; pp 399–419.
- (263) Tseng, M.-L.; Chiu, A. S. F.; Tan, R. R.; Siriban-Manalang, A. B. Sustainable Consumption and Production for Asia: Sustainability through Green Design and Practice. *J. Clean. Prod.* **2013**, *40*, 1–5.
- (264) Timmins, M. Environmental and Waste Issues Concerning the Production of Smart Clothes and Wearable Technology. *Smart Clothes and Wearable Technology*; Elsevier: Amsterdam, 2009; pp 319–331.
- (265) Zhang, Y.; Wang, H.; Lu, H.; Li, S.; Zhang, Y. Electronic Fibers and Textiles: Recent Progress and Perspective. *iScience* **2021**, *24*, 102716.
- (266) Baeg, K.-J.; Lee, J. Flexible Electronic Systems on Plastic Substrates and Textiles for Smart Wearable Technologies. *Adv. Mater. Technol.* **2020**, *5*, 2000071.
- (267) Koc, U.; Yurdabak Karaca, G.; Uygun Oksuz, A.; Oksuz, L. RF Sputtered Electrochromic Wool Textile in Different Liquid Media. *J. Mater. Sci.: Mater. Electron.* **2017**, *28*, 8725–8732.
- (268) Heo, J. S.; Eom, J.; Kim, Y.-H.; Park, S. K. Recent Progress of Textile-Based Wearable Electronics: A Comprehensive Review of Materials, Devices, and Applications. *Small* **2018**, *14*, 1703034.
- (269) Hatch, K. L. *Textile Science*; West Publishing: St. Paul, MN, 1993.
- (270) Karim, N.; Afroj, S.; Lloyd, K.; Oaten, L. C.; Andreeva, D. V.; Carr, C.; Farmery, A. D.; Kim, I.-D.; Novoselov, K. S. Sustainable Personal Protective Clothing for Healthcare Applications: A Review. *ACS Nano* **2020**, *14*, 12313–12340.
- (271) Miao, M.; Xin, J. H. *Engineering of High-Performance Textiles*; Woodhead Publishing: Cambridge, UK, 2017.
- (272) Du, D.; Li, P.; Ouyang, J. Graphene Coated Nonwoven Fabrics as Wearable Sensors. *J. Mater. Chem. C* **2016**, *4* (15), 3224–3230.
- (273) Ojstršek, A.; Plohl, O.; Gorgieva, S.; Kurečić, M.; Jančić, U.; Hribernik, S.; Fakin, D. Metallisation of Textiles and Protection of Conductive Layers: An Overview of Application Techniques. *Sensors* **2021**, *21*, 3508.
- (274) Wang, D.; Zhang, Y.; Lu, X.; Ma, Z.; Xie, C.; Zheng, Z. Chemical Formation of Soft Metal Electrodes for Flexible and Wearable Electronics. *Chem. Soc. Rev.* **2018**, *47*, 4611–4641.
- (275) Bankar, V. G.; Spruiell, J. E.; White, J. L. Melt Spinning of Nylon 6: Structure Development and Mechanical Properties of as-spun Filaments. *J. Appl. Polym. Sci.* **1977**, *21*, 2341–2358.
- (276) Chen, G. Y.; Cuculo, J. A.; Tucker, P. A. Effects of Spinning Conditions on Morphology and Properties of Polyethylene Terephthalate Fibers Spun at High Speeds. *J. Appl. Polym. Sci.* **1997**, *44*, 447–458.
- (277) Zhang, L.-H.; Duan, X.-P.; Xu, Y.; Yu, M.; Ning, X.; Zhao, Y.; Long, Y.-Z. Recent Advances in Melt Electrospinning. *RSC Adv.* **2016**, *6*, 53400–53414.
- (278) Fei, B. 2 - High-performance fibers for textiles. In *Engineering of High-Performance Textiles*; Miao, M., Xin, J. H., Eds.; Woodhead Publishing: Cambridge, UK, 2018; pp 27–58.
- (279) Hufenus, R.; Affolter, C.; Camenzind, M.; Reifler, F. A. Design and Characterization of a Bicomponent Melt-Spun Fiber Optimized for Artificial Turf Applications. *Macromol. Mater. Eng.* **2013**, *298*, 653–663.
- (280) Kikutani, T.; Arikawa, S.; Takaku, A.; Okui, N. Fiber Structure Formation in High-Speed Melt Spinning of Sheath-Core Type Bicomponent Fibers. *Sen-i Gakkaishi* **1995**, *51*, 408–415.
- (281) Kapoor, A.; McKnight, M.; Chatterjee, K.; Agcayazi, T.; Kausche, H.; Bozkurt, A.; Ghosh, T. K. Toward Fully Manufacturable, Fiber Assembly-Based Concurrent Multimodal and Multifunctional Sensors for E-Textiles. *Adv. Mater. Technol.* **2019**, *4*, 1800281.
- (282) Lund, A.; Jonasson, C.; Johansson, C.; Haagensen, D.; Hagström, B. Piezoelectric Polymeric Bicomponent Fibers Produced by Melt Spinning. *J. Appl. Polym. Sci.* **2012**, *126*, 490–500.
- (283) Loke, G.; Yan, W.; Khudiyev, T.; Noel, G.; Fink, Y. Recent Progress and Perspectives of Thermally Drawn Multimaterial Fiber Electronics. *Adv. Mater.* **2020**, *32*, 1904911.
- (284) Hufenus, R.; Yan, Y.; Dauner, M.; Kikutani, T. Melt-Spun Fibers for Textile Applications. *Materials* **2020**, *13*, 4298.
- (285) Karim, N.; Afroj, S.; Tan, S.; Novoselov, K. S.; Yeates, S. G. All Inkjet-Printed Graphene-Silver Composite Ink on Textiles for Highly Conductive Wearable Electronics Applications. *Sci. Rep.* **2019**, *9*, 8035.
- (286) Islam, M. R.; Afroj, S.; Beach, C.; Islam, M. H.; Parraman, C.; Abdelkader, A.; Casson, A. J.; Novoselov, K. S.; Karim, N. Fully Printed and Multifunctional Graphene-Based Wearable E-Textiles for Personalized Healthcare Applications. *iScience* **2022**, *25*, 103945.
- (287) Carey, T.; Cacovich, S.; Divitini, G.; Ren, J.; Mansouri, A.; Kim, J. M.; Wang, C.; Ducati, C.; Sordan, R.; Torrisi, F. Fully Inkjet-Printed Two-Dimensional Material Field-Effect Heterojunctions for Wearable and Textile Electronics. *Nat. Commun.* **2017**, *8*, 1202.
- (288) Kim, I.; Ju, B.; Zhou, Y.; Li, B. M.; Jur, J. S. Microstructures in All-Inkjet-Printed Textile Capacitors with Bilayer Interfaces of Polymer Dielectrics and Metal–Organic Decomposition Silver Electrodes. *ACS Appl. Mater. Interfaces* **2021**, *13*, 24081–24094.
- (289) Researchers Show New Strategy For Making E-Textiles With Inkjet Printing. *drupa*; <https://blog.drupa.com/en/e-textiles-inkjet-printing/> (accessed July 29, 2022).
- (290) Karana, E. Characterization of 'Natural' and 'High-Quality'-materials to Improve Perception of Bio-Plastics. *J. Cleaner Prod.* **2012**, *37*, 316–325.
- (291) Karana, E.; Nijkamp, N. Fiberness, Reflectiveness and Roughness in the Characterization of Natural and High Quality Materials. *J. Cleaner Prod.* **2014**, *68*, 252–260.
- (292) van der Velden, N. M.; Kuusk, K.; Köhler, A. R. Life Cycle Assessment and Eco-Design of Smart Textiles: The Importance of Material Selection Demonstrated through E-Textile Product Redesign. *Mater. Des.* **2015**, *84*, 313–324.
- (293) Veske, P.; Kuusk, K.; Toeters, M.; Scholz, B. *Environmental Sustainability of E-Textile Products Approached by Makers and Manufacturers*, Textile Intersections, 13.09.2019; Loughborough University: London, 2019; ; pp 12–19, DOI: 10.17028/rd.lboro.o.9724664.v1.
- (294) Life Cycle Analysis (LCA) - A Complete Guide to LCAs. *British Plastics Federation*; <https://www.bpf.co.uk/sustainable-manufacturing/life-cycle-analysis-lca>.



aspx#A%20word%20on%20LCA%20International%20Standards (accessed June 28, 2022).

(295) ISO. *Environmental Management: Life Cycle Assessment; Principles And Framework*; <https://www.iso.org/standard/37456.html> (accessed June 28, 2022).

(296) Luo, Y.; Song, K.; Ding, X.; Wu, X. Environmental Sustainability of Textiles and Apparel: A Review of Evaluation Methods. *Environ. Impact Assess. Rev.* **2021**, *86*, 106497.

(297) Guinee, J. B. Handbook on Life Cycle Assessment Operational Guide to the ISO Standards. *International Journal of Life Cycle Assessment* **2002**, *7*, 311.

(298) Schau, E. M.; Traverso, M.; Lehmann, A.; Finkbeiner, M. Life Cycle Costing in Sustainability Assessment—A Case Study of Remanufactured Alternators. *Sustainability* **2011**, *3*, 2268–2288.

(299) Kanth, R. K.; Wan, Q.; Kumar, H.; Liljeberg, P.; Zheng, L.; Tenhunen, H. Life Cycle Assessment of Printed Antenna: Comparative Analysis and Environmental Impacts Evaluation; *Proceedings of the 2011 IEEE International Symposium on Sustainable Systems and Technology*, IEEE, 2011; p 1.

(300) Walser, T.; Demou, E.; Lang, D. J.; Hellweg, S. Prospective Environmental Life Cycle Assessment of Nanosilver T-Shirts. *Environ. Sci. Technol.* **2011**, *45*, 4570–4578.

(301) van der Velden, N. M.; Patel, M. K.; Vogtländer, J. G. LCA Benchmarking Study on Textiles Made of Cotton, Polyester, Nylon, Acryl, or Elastane. *Int. J. LCA* **2014**, *19*, 331–356.

(302) Laursen, S. E.; Hansen, J.; Knudsen, H. H.; Wenzel, H.; Larsen, H. F.; Kristensen, F. *MEDIPTX-Environmental Assessment of Textiles*; Danish Environmental Protection Agency, 2007.

(303) Chamas, A.; Moon, H.; Zheng, J.; Qiu, Y.; Tabassum, T.; Jang, J. H.; Abu-Omar, M.; Scott, S. L.; Suh, S. Degradation Rates of Plastics in the Environment. *ACS Sustainable Chem. Eng.* **2020**, *8*, 3494–3511.

(304) Mohanan, N.; Montazer, Z.; Sharma, P. K.; Levin, D. B. Microbial and Enzymatic Degradation of Synthetic Plastics. *Front. Microbiol.* **2020**, *11*, 580709–580709.

(305) Vasile, C.; Pamfil, D.; Răpă, M.; Darie-Niță, R. N.; Mitelut, A. C.; Popa, E. E.; Popescu, P. A.; Draghici, M. C.; Popa, M. E. Study of the Soil Burial Degradation of Some PLA/CS Biocomposites. *Composites, Part B* **2018**, *142*, 251–262.

(306) Sular, V.; Devrim, G. Biodegradation Behaviour of Different Textile Fibres: Visual, Morphological, Structural Properties and Soil Analyses. *Fibres Text. East. Eur.* **2019**, *27*, 100–111.

(307) Biodegradability Testing – undertaking the correct testing methods. *euofins*; <https://www.blcleathertech.com/news/biodegradability-testing-undertaking-the-correct-testing-methods> (accessed July 16, 2022).

(308) Janaway, R. C. The Decomposition of Materials Associated with Buried Cadavers. *Soil Analysis in Forensic Taphonomy*; CRC Press: Boca Raton, FL, 2008; pp 165–214.

(309) Han, X.; Pan, J. A Model for Simultaneous Crystallisation and Biodegradation of Biodegradable Polymers. *Biomaterials* **2009**, *30*, 423–430.

(310) Kalita, N. K.; Damare, N. A.; Hazarika, D.; Bhagabati, P.; Kalamdhad, A.; Katiyar, V. Biodegradation and Characterization Study of Compostable PLA Bioplastic Containing Algae Biomass as Potential Degradation Accelerator. *Environ. Challenges* **2021**, *3*, 100067.

(311) Kalita, N. K.; Nagar, M. K.; Mudenu, C.; Kalamdhad, A.; Katiyar, V. Biodegradation of Modified Poly(Lactic Acid) Based Biocomposite Films Under Thermophilic Composting Conditions. *Polym. Test.* **2019**, *76*, 522–536.

(312) Kyrikou, I.; Briassoulis, D. Biodegradation of Agricultural Plastic Films: A Critical Review. *J. Polym. Environ.* **2007**, *15*, 125–150.

(313) Reep, C. A Primer Biodegradability Testing Methods. *OH&S*; <https://ohsonline.com/Articles/2020/08/01/A-Primer-Biodegradability-Testing-Methods.aspx> (accessed June 20, 2022).

(314) Starnecker, A.; Menner, M. Assessment of Biodegradability of Plastics under Simulated Composting Conditions in a Laboratory Test System. *Int. Biodeterior. Biodegrad.* **1996**, *37*, 85–92.

(315) Parker, L. Here's How Much Plastic Trash is Littering the Earth. *National Geographic*; <https://www.nationalgeographic.com/science/article/plastic-produced-recycling-waste-ocean-trash-debris-environment> (accessed June 18, 2022).

(316) d'Ambrières, W. Plastics Recycling Worldwide: Current Overview and Desirable Changes. *Field Actions Sci. Rep.* **2019**, *12*–21.

(317) Sharma, V.; Singh, G. Chemical Degradation of PET: Waste with Different Catalysts. *J. Pharmacogn. Phytochem.* **2019**, *8*, 386–388.

(318) Damayanti; Wu, H.-S. Strategic Possibility Routes of Recycled PET. *Polymers* **2021**, *13* (9), 1475.

(319) Achilias, D.; Karayannidis, G. The Chemical Recycling of PET in the Framework of Sustainable Development. *Water, Air, & Soil Pollution: Focus* **2004**, *4*, 385–396.

(320) Al-Sabagh, A. M.; Yehia, F. Z.; Eshaq, G.; Rabie, A. M.; ElMetwally, A. E. Greener Routes for Recycling of Polyethylene Terephthalate. *Egypt. J. Pet.* **2016**, *25*, 53–64.

(321) Bartolome, L.; Imran, M.; Cho, B.; Al-Masry, W.; Kim, D. Recent Developments in the Chemical Recycling of PET. *Intech Open* **2012**, DOI: 10.5772/33800.

(322) Akhras, M. H.; Fischer, J. Sampling Scheme Conception for Pretreated Polyolefin Waste Based on a Review of the Available Standard Procedures. *Polymers* **2022**, *14*, 3450.

(323) Owusu, P. A.; Asumadu-Sarkodie, S. A Review of Renewable Energy Sources, Sustainability Issues and Climate Change Mitigation. *Cogent Eng.* **2016**, *3*, 1167990.

(324) Ilie, A. G.; Jurconi, A. The Implications of a Mandatory rPET Content in the Soft Drinks Plastic Bottles from an Industry-Retail-Consumer Relations Perspective. *New Trends in Sustainable Business and Consumption* **2019**, 821.

(325) Morão, A.; de Bie, F. Life Cycle Impact Assessment of Poly(lactic Acid) (PLA) Produced from Sugarcane in Thailand. *J. Polym. Environ.* **2019**, *27*, 2523–2539.

(326) Peng, X.; Dong, K.; Ye, C.; Jiang, Y.; Zhai, S.; Cheng, R.; Liu, D.; Gao, X.; Wang, J.; Wang, Z. L. A Breathable, Biodegradable, Antibacterial, and Self-Powered Electronics Skin Based on All-Nanofiber Triboelectric Nanogenerators. *Sci. Adv.* **2020**, DOI: 10.1126/sciadv.aba9624.

(327) Moghadam, B. H.; Hasanzadeh, M.; Simchi, A. Self-Powered Wearable Piezoelectric Sensors Based on Polymer Nanofiber–Metal–Organic Framework Nanoparticle Composites for Arterial Pulse Monitoring. *ACS Appl. Nano Mater.* **2020**, *3*, 8742–8752.

(328) Lee, J.; Bae, J.; Youn, D.-Y.; Ahn, J.; Hwang, W.-T.; Bae, H.; Bae, P. K.; Kim, I.-D. Violacein-Embedded Nanofiber Filters with Antiviral and Antibacterial Activities. *Chem. Eng. J.* **2022**, *444*, 136460.

(329) Le, T. T.; Curry, E. J.; Vinikoor, T.; Das, R.; Liu, Y.; Sheets, D.; Tran, K. T. M.; Hawxhurst, C. J.; Stevens, J. F.; Hancock, J. N.; Bilal, O. R.; Shor, L. M.; Nguyen, T. D. Piezoelectric Nanofiber Membrane for Reusable, Stable, and Highly Functional Face Mask Filter with Long-Term Biodegradability. *Adv. Funct. Mater.* **2022**, *32*, 2113040.

(330) Sun, N.; Wang, G.-G.; Zhao, H.-X.; Cai, Y.-W.; Li, J.-Z.; Li, G.-Z.; Zhang, X.-N.; Wang, B.-L.; Han, J.-C.; Wang, Y.; Yang, Y. Waterproof, Breathable and Washable Triboelectric Nanogenerator Based on Electrospun Nanofiber Films for Wearable Electronics. *Nano Energy* **2021**, *90*, 106639.

(331) Khalid, M. A. U.; Ali, M.; Soomro, A. M.; Kim, S. W.; Kim, H. B.; Lee, B.-G.; Choi, K. H. A Highly Sensitive Biodegradable Pressure Sensor Based on Nanofibrous Dielectric. *Sens. Actuators, A* **2019**, *294*, 140–147.

(332) Boutry, C. M.; Kaizawa, Y.; Schroeder, B. C.; Chortos, A.; Legrand, A.; Wang, Z.; Chang, J.; Fox, P.; Bao, Z. A Stretchable and Biodegradable Strain and Pressure Sensor for Orthopaedic Application. *Nat. Electron.* **2018**, *1*, 314–321.

(333) Yang, Z.; Huang, T.; Cao, P.; Cui, Y.; Nie, J.; Chen, T.; Yang, H.; Wang, F.; Sun, L. Carbonized Silk Nanofibers in Biodegradable, Flexible Temperature Sensors for Extracellular Environments. *ACS Appl. Mater. Interfaces* **2022**, *14*, 18110–18119.

(334) Sofi, H. S.; Ashraf, R.; Khan, A. H.; Beigh, M. A.; Majeed, S.; Sheikh, F. A. Reconstructing Nanofibers from Natural Polymers Using

Surface Functionalization Approaches for Applications in Tissue Engineering, Drug Delivery and Biosensing Devices. *Mater. Sci. Eng., C* **2019**, *94*, 1102–1124.

(335) Karim, N.; Afroj, S.; Tan, S.; He, P.; Fernando, A.; Carr, C.; Novoselov, K. S. Scalable Production of Graphene-Based Wearable E-Textiles. *ACS Nano* **2017**, *11*, 12266–12275.

(336) Afroj, S.; Karim, N.; Wang, Z.; Tan, S.; He, P.; Holwill, M.; Ghazaryan, D.; Fernando, A.; Novoselov, K. S. Engineering Graphene Flakes for Wearable Textile Sensors via Highly Scalable and Ultrafast Yarn Dyeing Technique. *ACS Nano* **2019**, *13*, 3847–3857.

(337) Islam, M. H.; Afroj, S.; Uddin, M. A.; Andreeva, D. V.; Novoselov, K. S.; Karim, N. Graphene and CNT-Based Smart Fiber-Reinforced Composites: A Review. *Adv. Funct. Mater.* **2022**, *32*, 2205723.

(338) Novoselov, K. S.; Mishchenko, A.; Carvalho, A.; Neto, A. H. C. 2D Materials and van der Waals Heterostructures. *Science* **2016**, *353*, aac9439.

(339) Hayward, J.E-Textiles 2019–2029: Technologies, Markets and Players. *A Comprehensive Review of Materials, Processes, Components, Products and Markets*; <https://www.idtechex.com>, 2019 (accessed March 1, 2020).

(340) Yang, K.; Isaia, B.; Brown, L. J. E.; Beeby, S. E-Textiles for Healthy Ageing. *Sensors* **2019**, *19*, 4463.

(341) E-Textiles & Smart Clothing Market Surpass \$15,018.9 Mn by 2028 | CAGR 32.3% Says Acumen Research and Consulting. *Globe Newswire*; <https://www.globenewswire.com/news-release/2021/12/09/2349113/0/en/E-Textiles-Smart-Clothing-Market-Surpass-15-018-9-Mn-by-2028-CAGR-32-3-Says-Acumen-Research-and-Consulting.html> (accessed June 26, 2022).

(342) Meena, J. S.; Choi, S. B.; Jung, S.-B.; Kim, J.-W. Recent Progress of  $Ti_3C_2T_x$ -Based Mxenes for Fabrication of Multifunctional Smart Textiles. *Appl. Mater. Today* **2022**, *29*, 101612.

(343) Maiti, S.; Islam, M. R.; Uddin, M. A.; Afroj, S.; Eichhorn, S. J.; Karim, N. Sustainable Fiber-Reinforced Composites: A Review. *Adv. Sustainable Syst.* **2022**, 2200258.

(344) Habib, M. A.; Bao, Y.; Nabi, N.; Dulal, M.; Asha, A. A.; Islam, M. Impact of Strategic Orientations on the Implementation of Green Supply Chain Management Practices and Sustainable Firm Performance. *Sustainability* **2021**, *13*, 340.