

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

**Room-Temperature Quantum Coherence and Rabi Oscillations in Vanadyl Phthalocyanine: Toward Multifunctional Molecular Spin Qubits**

**This is a pre print version of the following article:**

*Original Citation:*

*Availability:*

This version is available <http://hdl.handle.net/2318/1610465> since 2016-11-09T10:07:50Z

*Published version:*

DOI:10.1021/jacs.5b13408

*Terms of use:*

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

This is the author's final version of the contribution published as:

Atzori, Matteo; Tesi, Lorenzo; Morra, Elena; Chiesa, Mario; Sorace, Lorenzo; Sessoli, Roberta. Room-Temperature Quantum Coherence and Rabi Oscillations in Vanadyl Phthalocyanine: Toward Multifunctional Molecular Spin Qubits. JOURNAL OF THE AMERICAN CHEMICAL SOCIETY. 138 (7) pp: 2154-2157.  
DOI: 10.1021/jacs.5b13408

The publisher's version is available at:

<http://pubs.acs.org/doi/pdf/10.1021/jacs.5b13408>

When citing, please refer to the published version.

Link to this full text:

<http://hdl.handle.net/>

# Room Temperature Quantum Coherence and Rabi Oscillations in Vanadyl Phthalocyanine: Toward Multifunctional Molecular Spin Qubits

Matteo Atzori,<sup>†</sup> Lorenzo Tesi,<sup>†</sup> Elena Morra,<sup>‡</sup> Mario Chiesa,<sup>‡</sup> Lorenzo Sorace,<sup>†</sup> and Roberta Sessoli<sup>\*,†</sup>

<sup>†</sup> Dipartimento di Chimica “Ugo Schiff” & INSTM RU, Università degli Studi di Firenze, Via della Lastruccia 3, I50019 Sesto Fiorentino (Firenze), Italy.

<sup>‡</sup> Dipartimento di Chimica & NIS Centre, Università di Torino, Via P. Giuria 7, I10125 Torino, Italy.

*Supporting Information Placeholder*

---

**ABSTRACT:** Here we report the investigation of the magnetic relaxation and the quantum coherence of vanadyl phthalocyanine, VOPc, a multifunctional and easy-processable potential molecular spin qubit. VOPc in its pure form (**1**) and its crystalline dispersions in the isostructural diamagnetic host TiOPc in different stoichiometric ratios, namely VOPc:TiOPc 1:10 (**2**) and 1:1000 (**3**), were investigated via an emerging multitechnique approach based on the combination of alternate current (AC) susceptometry, continuous wave (CW) and pulsed electron paramagnetic resonance (EPR) spectroscopy. AC susceptibility measurements revealed a linear increase of the relaxation rate with temperature up to 20 K, as expected for a direct mechanism, but  $\tau$  remains slow over a very wide range of applied static field values (up to ca. 5 T). Pulsed EPR spectroscopy experiments on **3** revealed quantum coherence up to room temperature with  $T_m$  ca. 1  $\mu$ s at 300 K, representing the highest value obtained to date for molecular electronic spin qubits. Rabi oscillations are observed in this nuclear spin-active environment (<sup>1</sup>H and <sup>14</sup>N nuclei) at room temperature also for **2**, indicating an outstanding robustness of the quantum coherence in this molecular semiconductor exploitable in spintronic devices.

---

In the development of spin-based information technology magnetic molecules represent particularly versatile building blocks as they can serve for the realization of both “static” and “dynamic” components of a potential quantum computer.<sup>1</sup> While single-molecule magnets (SMMs) show magnetic bistability resulting from magnetic anisotropy and large spin,<sup>2</sup> molecules with lower spin values can be exploited in quantum computation as quantum bits, or qubits.<sup>3</sup> A qubit is a two states quantum-mechanical system able to be placed in a state of coherent superposition of these levels. Physical realizations of qubits can be found in superconductive circuits, trapped ions, photons, *etc.*<sup>4</sup> Nuclear and electronic spins are also interesting because they can be prepared in a superposition of spin states by pulsed magnetic resonance techniques. The most investigated electronic spin systems are nitrogen-

vacancy pairs in diamonds<sup>5</sup> or defects in silicon<sup>6</sup> or silicon carbide.<sup>7</sup> Polynuclear metal complexes,<sup>8</sup> in particular ferromagnetic rings,<sup>3</sup> have been also investigated for the possibility to use synthetic chemistry to obtain multi-bit systems.<sup>9</sup> Only recently, molecular spin systems have become really competitive. The realization of a qubit requires, in fact, the accomplishment of stringent and antithetic requirements known as Di Vincenzo criteria.<sup>10</sup> If molecules are better suited to satisfy some of them, like addressing and control of qubits entanglement, the short lifetime of the quantum superposition of states,  $T_m$ , has up to now posed some limitations in their use as qubits. Recently promising results have been obtained on simple  $S = 1/2$  complexes.<sup>11</sup> Remarkably, mononuclear V<sup>IV</sup> complexes with nuclear spin-free ligands like dithiolenes,<sup>12</sup> when dispersed in nuclear spin-free solvents like CS<sub>2</sub>, can attain, at low temperature,  $T_m$  of the order of the millisecond,<sup>13</sup> a value comparable to those observed for vacancies in extended lattices. Their use at room temperature is however hampered by the rapid decrease, on increasing the temperature, of the spin-lattice relaxation time,  $T_1$ , which acts as a limiting factor for  $T_m$ .

In a recent investigation we have shown that AC susceptibility can flank pulsed EPR techniques to identify species that show slow spin-lattice relaxation as potential spin qubits.<sup>14</sup> A vanadyl complex with  $\beta$ -diketonate ligands has revealed remarkable  $T_m$  despite the proton rich ligands, and, more interestingly, a long  $T_1$  over a wide range of temperature and applied magnetic fields.

Keeping in mind the growing interest to address single molecules on surfaces exploiting their electric conductance, we focused our attention on vanadyl phthalocyanine, VOPc. This system exhibits the expected electronic and structural features to behave as a molecular spin qubit combined with other technologically relevant physical properties, such as extrinsic semiconductivity<sup>15</sup> and the ability of being deposited on different surfaces in oriented dispositions,<sup>16</sup> fundamental requisites for a suitable processability and incorporation of these materials in real devices. The high stability of the diamagnetic analogue, titanyl phthalocyanine, TiOPc, allows the preparation of crystalline materials with different percentage of paramagnetic component diluted in the diamag-

netic host leading to two important advantages: *i*) reduce the interactions between electronic magnetic moments, that significantly increases the  $T_2$  relaxation time<sup>17</sup> and *ii*) extend the investigation up to room temperature, avoiding the melting of frozen solutions. We have thus investigated the magnetic relaxation and the quantum coherence of VOPc in its pure form (**1**) and its crystalline dispersions in the isostructural diamagnetic host TiOPc in different molar ratios, 1:10 (**2**) and 1:1000 (**3**), through a multitechnique approach based on the combination of AC susceptometry, and CW and pulsed EPR spectroscopies.

VOPc is a non-planar metal-phthalocyanine in which the vanadyl ion  $\text{VO}^{2+}$ , coordinated by four nitrogen donor atoms of the dianionic phthalocyaninato ligand, points out of the plane of the ligand. The coordination geometry around the pentacoordinated  $\text{V}^{\text{IV}}$  ion is a distorted square pyramid with the metal slightly above the basal plane (0.575(1) Å).<sup>18</sup> The apical position is occupied by an oxo ligand which forms a double bond with the  $\text{V}^{\text{IV}}$  ion having a V=O distance of 1.580(3) Å, whereas the V–N bond lengths are in the 2.008(7)–2.034(7) Å range (Figure 1).

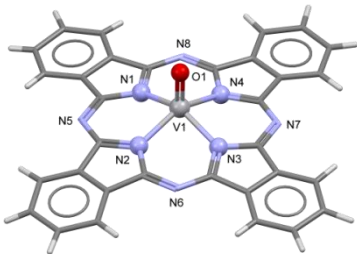


Figure 1. Molecular structure of VOPc with principal atoms labelling scheme and coordination geometry of the  $\text{V}^{\text{IV}}$  ion highlighted.

The presence of such short V=O bond distance is responsible for a  $d$ -orbitals splitting that leaves the  $d_{xy}$  orbital lowest in energy and well separated from the other orbitals, making this molecule a perfect two levels potential molecular qubit. VOPc and its diamagnetic analogue TiOPc exhibit a rich polymorphism and crystallize in more than four different structural phases showing slight different crystal packings (Type I–IV polymorphs).<sup>19</sup> Type II was selected because  $\pi$ – $\pi$  stacked supramolecular dimers are absent in the crystal structure and is the preferred one for VOPc (Figure S1). Moreover, TiOPc can be conveniently converted in this structural phase by dissolution in a 1:4 mixture of  $\text{CF}_3\text{COOH}:\text{CH}_2\text{Cl}_2$  and successive precipitation in *iso*-propanol (see SI).<sup>19</sup> Powder X-ray diffraction analyses performed on polycrystalline samples show structural phase homogeneity for all the investigated samples and a good agreement between experimental and simulated patterns (Figure S2).

Compounds **1** and **2** were investigated by AC susceptometry in order to get deeper insights on their magnetization dynamics. The thermal variation of the magnetic susceptibility in a zero static magnetic field reveals no imaginary component of the susceptibility ( $\chi''$ ) in the whole investigated  $T$  range (1.9–40 K). When a small static magnetic field ( $> 40$  mT) is applied, slow magnetic relaxation is observed with appearance of a peak in the imaginary component of the susceptibility and a concomitant decrease of the real part ( $\chi'$ ) (Figures S3–S10). Both **1** and **2** under a static magnetic field

( $B$ ) of 0.2 T show slow relaxation of the entire magnetization, so that this field, and a higher one (1 T), were selected to investigate the  $T$  dependence of the relaxation time ( $\tau$ ). The frequency dependence of  $\chi''$  are well reproduced with the Debye model (Figures S3–S10) and the extracted values of  $\tau$  as a function of  $T$  for the two selected fields are reported in Figure 2a.

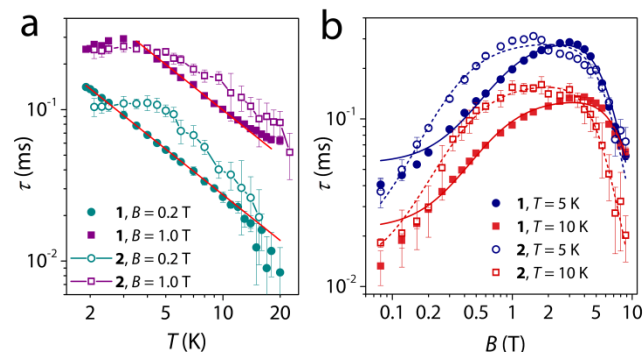


Figure 2. (a)  $T$  and (b)  $B$  dependence of  $\tau$  extracted from AC susceptibility measurements on **1** and **2** at different applied static magnetic field values and temperatures (see legends). Solid and dashed lines are the best-fits of the models.

Figure 2a shows that **1** exhibits up to 20 K a  $\tau$  dependence typical of the direct mechanism of relaxation in absence of phonon-bottleneck effects.<sup>20</sup> The field dependence of  $\tau$  in this  $T$  range (Figure 2b) shows an increase up to ca. 3 T while the rapid decrease expected for the direct mechanism is only visible above 5 T. The non-monotonous behavior is due to two antagonist effects of the magnetic field. An isolated  $S = \frac{1}{2}$  spin in zero field should not be able to relax due to time-reversal symmetry, but spin-spin and spin-nuclei interactions promote a rapid relaxation. The latter mechanisms are suppressed when the magnetic field splits the energy of the doublet, similarly to the phenomenon of resonant quantum tunneling in SMMs.<sup>2</sup> On the other hand, the larger is the energy separation of the doublet the more efficient is the spin-phonon direct mechanism providing  $\tau^{-1} \propto B^4$ . In general, fields weaker than 1 T are sufficient to accelerate the relaxation.<sup>21</sup> The two mechanisms can be taken into account in a phenomenological model described by the following equation:<sup>22</sup>

$$\tau^{-1} = cB^4 + d \frac{e(f+B^2)}{ef+B^2} \quad (1)$$

The first term considers the typical field dependence of a direct process while in the second term,  $d$  represents the zero-field relaxation rate,  $e$  is a parameter related to the concentration, and  $f$  is a parameter proportional to the square of the internal field generated by neighboring spins. The best-fit parameters are reported in Table S1. It is interesting to notice that  $f$  decreases significantly passing from **1** to **2**, in agreement with the reduction upon dilution of the internal field. The increase of the zero field relaxation rate, which is not expected, appears however as an artifact of the poor reproduction of the low field data, as testified by the large errors. As a result,  $\tau$  increases much faster in moderate field in **2**, indicating that both spin-spin and hyperfine interactions are active in promoting relaxation in weak applied fields. A comparison with a recent report on the compound  $\text{VO}(\text{dpm})_2$  ( $\text{dpm}^-$  is the anion of dipivaloylmethane)<sup>14</sup> shows, in both cases, a remarkable wide field range where  $\tau$  remains

long, suggesting that the vanadyl moiety strongly reduces the efficiency of spin-phonon coupling. We can notice that  $\tau$  is in general shorter for VOPc and the maximum is observed at higher fields, in agreement with the presence of the nitrogen nuclear spins directly coordinated to  $V^{IV}$  contributes to the spin relaxation, as recently shown for a  $Co^{II}$  pseudo  $S = 1/2$  spin system.<sup>23</sup> This could also be responsible of the low temperature saturation of  $\tau$ , not detected in  $VO(dpm)_2$ .

The CW-EPR X-band spectra of compounds **1-3** at 300 K and 5 K are reported in Figure S11. **1** shows a broad spectrum very likely due to the presence of an extensive network of intermolecular interactions between paramagnetic molecules.<sup>18</sup> The 1:10 crystalline dispersion of VOPc in TiOPc (**2**) dramatically changes the EPR spectrum, which reveals already at room temperature the expected hyperfine splitting due to the coupling with the nuclear spin of  $^{51}V$  ( $I = 7/2$ , natural abundance: 99.75%). By lowering the concentration of the paramagnetic component to 1:1000 (**3**), the superhyperfine spectral features due to the further coupling with the nuclear spins ( $I = 1$ ) of the chelating  $^{14}N$  nuclei become visible (Figure 3a).<sup>24</sup> As far as the position of the resonance lines are concerned, no significant variations are observed between **2** and **3**, thus confirming that VOPc retains the same molecular geometry and environment (Figure S11).

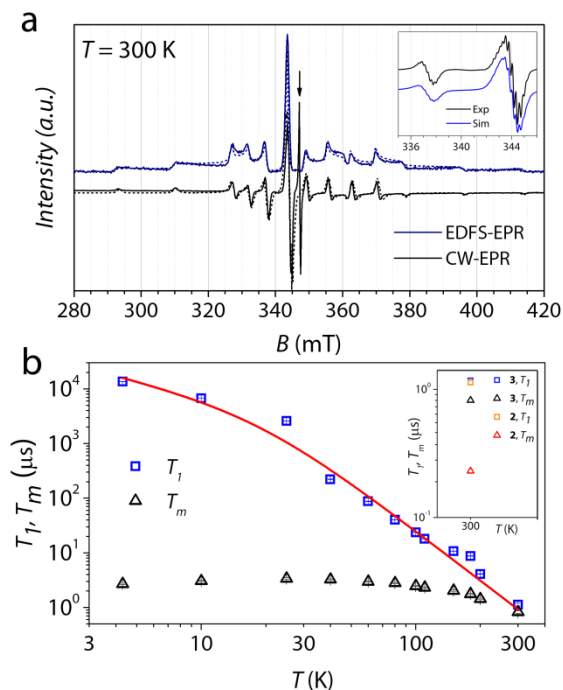


Figure 3. (a) EDfs- and CW-EPR X-band spectra for **3**. Short-dashed lines are the best-simulations. Inset shows the CW superhyperfine spectral feature of **3**. The arrow indicates the signal of the organic radical. (b)  $T$  dependence of  $T_1$  and  $T_m$  relaxation times for **3**. The solid line is the best-fit of the model. Inset shows the room temperature data for **2** and **3**.

Good spectral simulations<sup>25</sup> (Figure 3a and S12) were performed on the basis of the spin Hamiltonian:

$$\mathcal{H} = \hat{I}_V \cdot V A \cdot \hat{S} + N A \sum_{i=1}^4 \hat{I}_{N_i} \cdot \hat{S} + \mu_B \hat{S} \cdot g \cdot B \quad (2)$$

which provides as best-fit parameters the values reported in Table S2. In the EPR spectrum of **3** an additional very narrow signal exhibiting the typical features of an organic radical ( $g = 2.00$ ) is present (Figure 3a and S12). This signal, also

observed in the TiOPc matrix before and after purification (Figure S13), was assigned to the reduced species,  $TiOPc^{\cdot-}$ .<sup>26</sup> Double integration of the spectrum allowed to estimate the amount of this species as one order of magnitude less concentrate than VOPc, viz. 0.01% of the entire diamagnetic TiOPc. The quantities of  $TiOPc^{\cdot-}$  observed in **3** and in the TiOPc diamagnetic matrix were of the same order of magnitude, thus confirming that this species is not generated as a result of the doping process.

X-band echo-detected field-swept (EDfs) EPR spectra for **3** were recorded by using a standard Hahn echo sequence (Figure 3a and S14). As evidenced by the presence of a spin-echo, we can anticipate that quantum coherence is expected for this compound. Moreover the spin Hamiltonian parameters obtained through the CW spectrum simulation allow to provide good simulations of the EDfs spectra as well, thus indicating that the entire VOPc is experiencing the detected coherence. Inversion recovery experiments were performed in the 4.3-300 K  $T$  range to investigate the  $T$  dependence of  $T_1$  for **3** since the amount of paramagnetic component was too low for an investigation through AC susceptometry. The resulting saturation recovery traces were fitted with a standard stretched monoexponential equation (see S1) and the extracted  $T_1$  values are reported in Figure 3b.  $T_1$  decreases very slowly from the maximum value of ca. 14 ms at 4.3 K to 0.22 ms at 40 K in a way that is qualitatively similar to what observed for **1-2** through AC susceptometry. At higher temperature a higher slope is observed, reaching the value of 1.1  $\mu$ s at room temperature. The entire curve has been simulated assuming the contribution of a direct and a Raman-like process (see S1), dominating at low and high  $T$ , respectively. Best-fit values gives a very low Raman-like exponent  $n$  of ca. 3 as already observed in closely related systems,<sup>11b,14,27</sup> and attributed to the involvement of both optical and acoustic phonons in the relaxation.

To investigate the quantum coherence in details and to quantify the phase memory time,  $T_m$ , of VOPc in the doped material **3** as a function of  $T$ , echo decay experiments were performed at the so-called powder-like line field (345 mT). Remarkably, echo decay traces (Figure 4a) were detected up to room temperature.

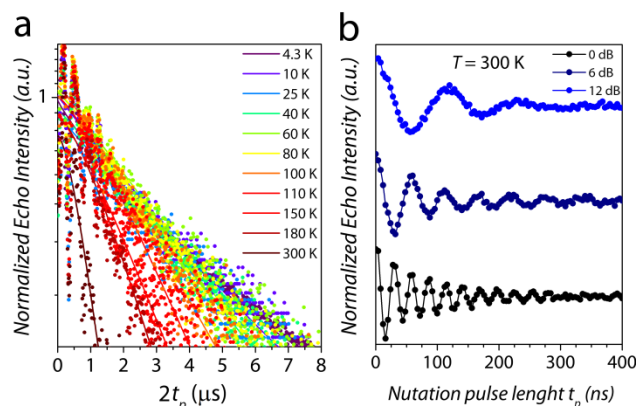


Figure 4. (a) Echo decay traces for **3** at different  $T$  (see legend). Solid lines are the best-fits (see S1). (b) Rabi oscillations recorded for **3** at 300 K for different microwave attenuations.

The thermal variation of  $T_m$  shows an almost temperature independent behavior in the 4.3-150 K range, with values within the 2.04-3.41  $\mu$ s range, only slightly higher than those

observed for CuPc diluted in pure phthalocyanine,<sup>11a</sup> then it slowly decreases as the temperature increases reaching a still remarkable value of 0.83  $\mu\text{s}$  at room temperature (Figure 3b). To date a comparable value of  $T_m$  at room temperature was obtained in a less concentrated (0.001%) dispersion of [(Ph)<sub>4</sub>P]<sub>2</sub>[Cu(mnt)<sub>2</sub>] (mnt = maleonitriledithiolate) in the Ni<sup>II</sup> isostructural diamagnetic host.<sup>11b</sup> Furthermore, **3** shows a higher value of  $T_m$  even if four out of five coordinating atoms are N atoms and the ligand presents several H atoms on its periphery. Preliminary results obtained on **2** revealed that  $T_1$  and  $T_m$  are not suppressed by the high concentration of VOPc, assuming really remarkable values of 1.1  $\mu\text{s}$  ( $T_1$ ) and 0.23  $\mu\text{s}$  ( $T_m$ ) at room temperature (Figure 3b and S15).

To prove that such coherence times allow to perform coherent spin manipulations *i.e.* place the spins in any arbitrary superposition of states, nutation experiments were performed at different microwave powers at 4.3 and 300 K. Remarkably, Rabi oscillations were clearly observed at room temperature for both **2** and **3**, with the expected linear dependence of the Rabi frequency,  $\Omega_R$ , as a function of the  $B_1$  relative intensity (Figure 4b and S16-S18). To the best of our knowledge, this is the first report of Rabi oscillations detected at room temperature in a molecular spin system. Even more remarkable is their observation in a concentrated sample, indicating a particular robustness of quantum coherence in this vanadyl-based systems.

In conclusion, VOPc in its crystalline dispersion in TiOPc represents one of the few examples of potential molecular qubit showing room temperature quantum coherence. The combination of these features with its high thermal stability and high processability makes these materials extremely appealing as they can be used as paramagnetic semiconductors in spintronics devices. It is also known that VOPc molecules retain their paramagnetism when in direct contact with metallic surfaces thanks to the protected nature of the  $d_{xy}$  magnetic orbital.<sup>16</sup> Depending on the nature of the substrate (*e.g.* Si(111), Ag(111)) VOPc orients with the O pointing towards the substrate or towards the vacuum.<sup>16</sup> This further widens the interest in this system for the detection of single-molecule quantum coherence by scanning tunneling microscopy.

## ASSOCIATED CONTENT

### Supporting Information

Additional Figures, Tables, Equations and Experimental details as mentioned in the text. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## AUTHOR INFORMATION

### Corresponding Author

roberta.sessoli@unifi.it

### Notes

The authors declare no competing financial interests.



## ACKNOWLEDGMENT

European Research Council (ERC) through AdG MolNanoMaS (267746), Italian MIUR through the project Futuro in Ricerca 2012 (RBF12RPD1), and Fondazione Ente Cassa di Risparmio di Firenze are acknowledged for financial support.

## REFERENCES

- (1) Leuenerberger, M. N.; Loss, D., *Nature* **2001**, *410*, 789–793.
- (2) Gatteschi, D.; Sessoli, R.; Villain, J., *Molecular nanomagnets*. Oxford University Press: Oxford, UK, **2006**.
- (3) Ardavan, A.; Rival, O.; Morton, J. J. L.; Blundell, S. J.; Tyryshkin, A. M.; Timco, G. A.; Winpenny, R. E. P., *Phys. Rev. Lett.* **2007**, *98* (5), 057201.
- (4) Le Bellac, M., *A short introduction to quantum information and quantum computation*. Cambridge University Press: Cambridge, **2006**.
- (5) (a) Takahashi, S.; Hanson, R.; van Tol, J.; Sherwin, M. S.; Awschalom, D. D., *Phys. Rev. Lett.* **2008**, *101*, 047601; (b) Balasubramanian, G.; Neumann, P.; Twitchen, D.; Markham, M.; Kolesov, R.; Mizuochi, N.; Isoya, J.; Achard, J.; Beck, J.; Tissler, J.; Jacques, V.; Hemmer, P. R.; Jelezko, F.; Wrachtrup, J., *Nature Mater.* **2009**, *8*, 383–387.
- (6) Pla, J. J.; Tan, K. Y.; Dehollain, J. P.; Lim, W. H.; Morton, J. J. L.; Jamieson, D. N.; Dzurak, A. S.; Morello, A., *Nature* **2012**, *489*, 541–545.
- (7) Tyryshkin, A. M.; Tojo, S.; Morton, J. J. L.; Riemann, H.; Abrosimov, N. V.; Becker, P.; Pohl, H.-J.; Schenkel, T.; Thewalt, M. L. W.; Itoh, K. M.; Lyon, S. A., *Nature Mater.* **2012**, *11*, 143–147.
- (8) (a) Aguila, D.; Barrios, L. A.; Velasco, V.; Roubeau, O.; Repolles, A.; Alonso, P. J.; Sese, J.; Teat, S. J.; Luis, F.; Aromi, G., *J. Am. Chem. Soc.* **2014**, *136*, 14215–14222; (b) Takahashi, S.; Tupitsyn, I. S.; van Tol, J.; Beedle, C. C.; Hendrickson, D. N.; Stamp, P. C. E., *Nature* **2011**, *476*, 76–79; (c) Troiani, F.; Affronte, M., *Chem. Soc. Rev.* **2011**, *40*, 3119–3129.
- (9) (a) Aromi, G.; Aguila, D.; Gamez, P.; Luis, F.; Roubeau, O., *Chem. Soc. Rev.* **2012**, *41*, 537–546; (b) Ardavan, A.; Bowen, A. M.; Fernandez, A.; Fielding, A. J.; Kaminski, D.; Moro, F.; Muryn, C. A.; Wise, M. D.; Ruggi, A.; McInnes, E. J. L.; Severin, K.; Timco, G. A.; Timmel, C. R.; Tuna, F.; Whitehead, G. F. S.; Winpenny, R. E. P., *Ardavan, Arzhang* **2015**, *1*, 15012.
- (10) DiVincenzo, D. P., *Fortschritte der Physik* **2000**, *48*, 771–783.
- (11) (a) Warner, M.; Din, S.; Tupitsyn, I. S.; Morley, G. W.; Stoneham, A. M.; Gardener, J. A.; Wu, Z.; Fisher, A. J.; Heutz, S.; Kay, C. W. M.; Aeppli, G., *Nature* **2013**, *503*, 504–508; (b) Bader, K.; Dengler, D.; Lenz, S.; Endeward, B.; Jiang, S.-D.; Neugebauer, P.; van Slageren, J., *Nature Comm.* **2014**, *5*, 5304.
- (12) Zadrozny, J. M.; Niklas, J.; Poluektov, O. G.; Freedman, D. E., *J. Am. Chem. Soc.* **2014**, *136*, 15841–15844.
- (13) Zadrozny, J. M.; Niklas, J.; Poluektov, O. G.; Freedman, D. E., *ACS Cent. Sci.* **2015**, *10.1021/acscentsci.5b00338*.
- (14) Tesi, L.; Lucaccini, E.; Cimatti, I.; Perfetti, M.; Mannini, M.; Atzori, M.; Morra, E.; Chiesa, M.; Caneschi, A.; Sorace, L.; Sessoli, R., *Chem. Sci.* **2015**, *10.1039/C5SC04295J*.
- (15) Zhang, Y.; Learmonth, T.; Wang, S.; Matsuura, A. Y.; Downes, J.; Plucinski, L.; Bernardis, S.; O'Donnell, C.; Smith, K. E., *J. Mat. Chem.* **2007**, *17*, 1276–1283.
- (16) Eguchi, K.; Takagi, Y.; Nakagawa, T.; Yokoyama, T., *J. Phys. Chem. C* **2013**, *117*, 22843–22851.
- (17) Abragam, A.; Bleaney, B., *Electron Paramagnetic Resonance of Transition Ions*. Dover: New York, **1986**.
- (18) Ziolo, R. F.; Griffiths, C. H.; Troup, J. M., *J. Chem. Soc., Dalton Trans.* **1980**, *11*, 2300–2302.
- (19) J. M. Duff; J. D. Mayo; C.-K. Hsiao; A.-M. Hor; T. L. Bluhm; G. K. Hamer; Kazmaier, P. M., *U.S. Patent* **1992**, *5,166,339*.
- (20) Shrivastava, K. N., *Physica status solidi (b)* **1983**, *117*, 437–458.
- (21) Soeteman, J.; van Duyneveldt, A. J.; Pouw, C. L. M.; Breur, W., *Physica* **1973**, *66*, 63–69.
- (22) De Vroomen, A. C.; Lijphart, E. E.; Prins, D. Y. H.; Marks, J.; Poullis, N. J., *Physica* **1972**, *61*, 241–249.
- (23) Gómez-Coca, S.; Urtizberea, A.; Cremades, E.; Alonso, P. J.; Camón, A.; Ruiz, E.; Luis, F., *Nature Comm.* **2014**, *5*, 4300.
- (24) Sato, M.; Kwan, T., *J. Chem. Phys.* **1969**, *50*, 558–559.
- (25) Stoll, S.; Schweiger, A., *J. Magn. Reson.* **2006**, *178*, 42–55.
- (26) Guzy, C. M.; Raynor, J. B.; Stodulski, L. P.; Symons, M. C. R., *J. Chem. Soc. A*, **1969**, 997–1001.
- (27) Du, J.-L.; Eaton, G. R.; Eaton, S. S., *J. Magn. Reson., Ser A* **1996**, *119*, 240–246.

## SYNOPSIS TOC

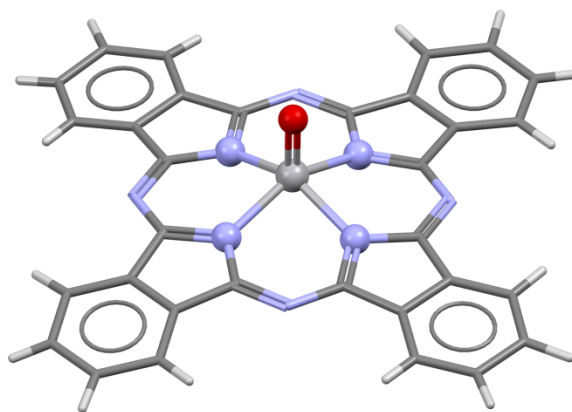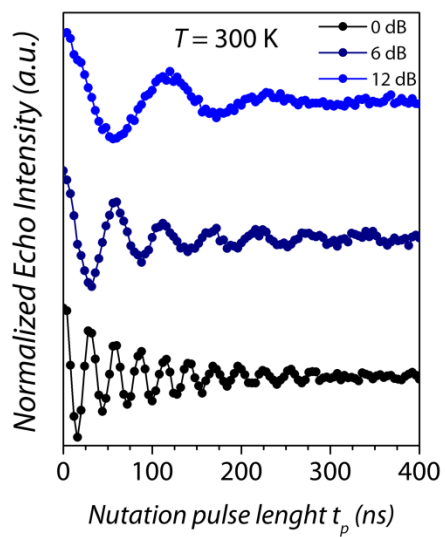

### Vanadyl Phthalocyanine