

UvA-DARE (Digital Academic Repository)

Regulating C₂H₂/CO₂ adsorption selectivity by electronic-state manipulation of iron in metal-organic frameworks

Chen, C.X.; Pham, T.; Tan, K.; Krishna, R.; Lan, P.C.; Wang, L.; Chen, S.; Al-Enizi, A.M.; Nafady, A.; Forrest, K.A.; Wang, H.; Wang, S.; Shan, C.; Zhang, L.; Su, C.Y.; Ma, S.

DOI

[10.1016/j.xcrp.2022.100977](https://doi.org/10.1016/j.xcrp.2022.100977)

Publication date

2022

Document Version

Final published version

Published in

Cell Reports Physical Science

License

CC BY-NC-ND

[Link to publication](#)

Citation for published version (APA):

Chen, C. X., Pham, T., Tan, K., Krishna, R., Lan, P. C., Wang, L., Chen, S., Al-Enizi, A. M., Nafady, A., Forrest, K. A., Wang, H., Wang, S., Shan, C., Zhang, L., Su, C. Y., & Ma, S. (2022). Regulating C₂H₂/CO₂ adsorption selectivity by electronic-state manipulation of iron in metal-organic frameworks. *Cell Reports Physical Science*, 3(8), [100977]. <https://doi.org/10.1016/j.xcrp.2022.100977>

General rights

It is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), other than for strictly personal, individual use, unless the work is under an open content license (like Creative Commons).


Disclaimer/Complaints regulations

If you believe that digital publication of certain material infringes any of your rights or (privacy) interests, please let the Library know, stating your reasons. In case of a legitimate complaint, the Library will make the material inaccessible and/or remove it from the website. Please Ask the Library: <https://uba.uva.nl/en/contact>, or a letter to: Library of the University of Amsterdam, Secretariat, Singel 425, 1012 WP Amsterdam, The Netherlands. You will be contacted as soon as possible.

UvA-DARE is a service provided by the library of the University of Amsterdam (<https://dare.uva.nl>)

Article

Regulating C₂H₂/CO₂ adsorption selectivity by electronic-state manipulation of iron in metal-organic frameworks

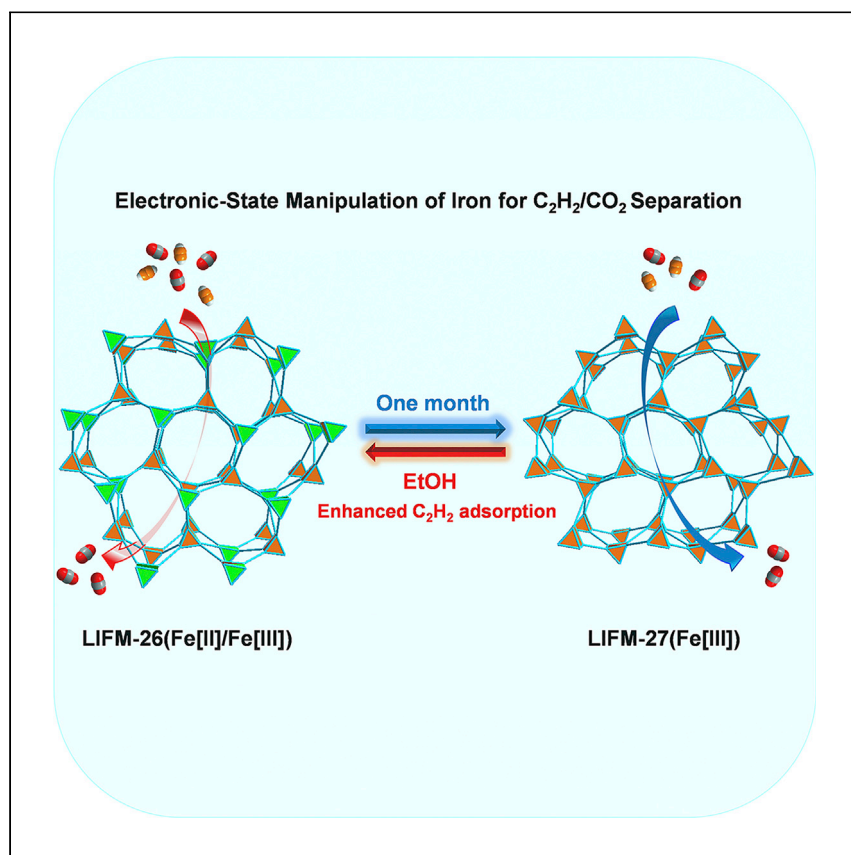

Chen et al. report a metal electronic-state manipulation strategy to construct a pair of isostructural and interconvertible Fe-MOFs featuring open Fe centers with different electron densities for efficient C₂H₂/CO₂ separation. They show that the presence of Fe[III] centers with a medium-spin-state trail plays a crucial role in the enhanced C₂H₂ selective adsorption.

Cheng-Xia Chen, Tony Pham,
Kui Tan, ..., Lei Zhang,
Cheng-Yong Su, Shengqian Ma

cesscy@mail.sysu.edu.cn (C.-Y.S.)
Shengqian.Ma@unt.edu (S.M.)

Highlights

The electronic state of Fe can be purposely tuned to regulate C₂H₂/CO₂ separation

Increasing electron density of Fe centers results in enhanced C₂H₂ adsorption

The interconvertible nature deepens understanding of structure-property relationship

Distinct adsorption mechanism is unveiled through *in situ* FTIR and molecular simulation

Article

Regulating C₂H₂/CO₂ adsorption selectivity by electronic-state manipulation of iron in metal-organic frameworks

Cheng-Xia Chen,^{1,2} Tony Pham,³ Kui Tan,⁴ Rajamani Krishna,⁶ Pui Ching Lan,² Longfei Wang,¹ Songbo Chen,⁷ Abdullah M. Al-Enizi,⁸ Ayman Nafady,⁸ Katherine A. Forrest,³ Haiping Wang,² Sicheng Wang,² Chuan Shan,³ Lei Zhang,⁵ Cheng-Yong Su,^{1,9,*} and Shengqian Ma^{2,9,*}

SUMMARY

The separation of C₂H₂ from C₂H₂/CO₂ mixture is of great importance, yet highly challenging in the petrochemical industry due to their similar physicochemical properties. While open-metal sites (OMSs) in metal-organic frameworks (MOFs) are known to possess high affinity toward C₂H₂, its selective adsorption performance regulated by the electronic state of the same OMSs remains unexplored. Here, we report a metal electronic-state manipulation approach to construct a pair of isostructural Fe-MOFs, namely LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) with different Fe[II] or Fe[III] oxidation states on the Fe centers, which display mixed-valent Fe[II]/Fe[III] centers in the former and sole Fe[III] centers in the latter. Remarkably, LIFM-26(Fe[II]/Fe[III]) shows significantly enhanced C₂H₂ uptake capacity than LIFM-27(Fe[III]), attested by adsorption isotherms and IAST calculations, as well as simulated and experimental breakthrough experiments. Furthermore, *in situ* infrared (IR) and molecular calculations unveil that the presence of Fe[II] in LIFM-26(Fe[II]/Fe[III]) results in stronger Fe[II]-C₂H₂ interactions than Fe[III]-C₂H₂, which plays a key role in the C₂H₂/CO₂ separation.

INTRODUCTION

Industrial chemical separations account for 10%–15% of the global energy consumption, which corresponds to half of the United States's industrial energy use.¹ Among them, acetylene (C₂H₂) purification represents an energy- and cost-intensive process.² As one of the most widely used feedstocks in the petroleum industry, C₂H₂ is mainly produced by the combustion of methane or thermal cracking of petroleum, with CO₂ as the major byproduct.³ Therefore, separating CO₂ from C₂H₂/CO₂ gas mixture is of great importance. Presently, the industrial separation of CO₂ from C₂H₂ is usually implemented through solvent extraction and cryogenic distillation, leading to intensive costs and energy penalties due to their similar physicochemical properties (molecular sizes and shapes: 3.32 × 3.34 × 5.70 Å³ for C₂H₂, 3.18 × 3.33 × 5.36 Å³ for CO₂; boiling points: 189.3 and 194.7 K for C₂H₂ and CO₂, respectively).^{4,5} As a result, adsorptive separation based on porous solid materials has drawn much attention owing to the advantage of dramatically reducing the energy and cost consumption.^{6–10}

Owing to their structural diversity, designable pore size, high pore volume, and tunable functionalities, metal-organic frameworks (MOFs) have shown great

¹MOE Laboratory of Bioinorganic and Synthetic Chemistry, Lehn Institute of Functional Materials, School of Chemistry, Sun Yat-Sen University, Guangzhou 510275, China

²Department of Chemistry, University of North Texas, Denton, TX 76201, USA

³Department of Chemistry, University of South Florida, Tampa, FL 33620, USA

⁴Department of Materials Science & Engineering, University of Texas at Dallas, Richardson, TX 75080, USA

⁵College of Materials Science and Engineering, Fujian University of Technology, Fuzhou 350118, China

⁶Van't Hoff Institute for Molecular Sciences, University of Amsterdam, 1098 Amsterdam, the Netherlands

⁷School of Physical Science and Technology, Lanzhou University, Lanzhou 730000, China


⁸Department of Chemistry, College of Science, King Saud University, Riyadh 11451, Saudi Arabia

⁹Lead contact

*Correspondence:
cesscy@mail.sysu.edu.cn (C.-Y.S.),
Shengqian.Ma@unt.edu (S.M.)

<https://doi.org/10.1016/j.xcrp.2022.100977>



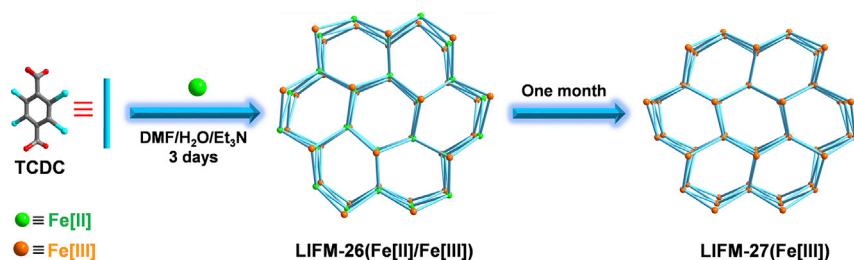

Scheme 1. Schematic synthetic route of Fe-MOF isostructures with different ratios of Fe[II] and Fe[III] centers through a metal electronic-state manipulation strategy

potentials in gas adsorption and separation involving C₂H₂/CO₂, C₂H₄/C₂H₆, C₃H₆/C₃H₈, N₂/O₂, CO/H₂, and CO/N₂.^{8–15} However, it is still challenging to rationally design MOFs for C₂H₂/CO₂ separation due to their similar dynamic sizes and volatility. Tremendous efforts have been devoted to developing highly effective MOF adsorbents, suggesting that the introduction of open-metal sites (OMSs) into suitable pore space is most likely to be competent for this task.^{16–24} The suitable pore space (appropriate pore size, high pore volume, and polar pore surface) can render the framework with a high C₂H₂ adsorption working capacity and facilitates adsorption dynamics.^{25–30} In addition, the OMSs with exposed partial positive charges not only behave as Lewis-acid-accepting electrons from the electron lone pair orbital of C₂H₂ but also function as a π -bond back donor providing electrons to C₂H₂ (delocalizing d electrons to the antibonding π^* orbitals of C₂H₂), thus resulting in preferential adsorption toward C₂H₂ over CO₂.^{26,31–33} However, it is extremely difficult to combine exposed positive charges and strong π back donors into a single material. Actually, most MOFs with OMSs present weak π -bond back donation due to their electron-poor metal centers, and only a few MOFs featuring exposed electron-rich metal centers are found to be suitable for π -bond back donation.^{32,34–36}

In order to functionalize MOFs with electron-rich OMSs for highly selective C₂H₂ adsorption, it is anticipated that the manipulation of the mixed-valent electronic states of exposed metal centers in a suitable MOF pore space is an effective yet challenging strategy. The introduction of an appropriate low-valent metal center can impart enhanced π back donation, thereby facilitating the preferential C₂H₂ adsorption over CO₂, while the presence of a high-valent metal center can allow for facile desorption of C₂H₂ due to the moderate metal-adsorbate interactions. Herein, we report a pair of isostructural Fe-MOFs, namely LIFM-26(Fe[II]/Fe[III])³⁷ and LIFM-27(Fe[III]) (LIFM stands for Lehn Institute of Functional Materials) that possess pore spaces constructed from the same perchlorinated ligand (2,3,5,6-tetrachloride terephthalic acid [TCDC]) (Scheme S1) and oxidation-state variant Fe[II]/Fe[III] centers (Scheme 1). Both structures feature coordinately unsaturated Fe centers, in which the ratios of Fe[II] and Fe[III] can be purposely tuned through an *in situ* redox process (Scheme 1), endowing the isostructural Fe-MOFs with distinct C₂H₂ selective adsorption performance. It is worth noting that LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) are interconvertible as the isostructures of (Fe[II]/Fe[III])₃O(TFBDC)₃ (TFBDC = 2,3,5,6-tetrafluorobenzene-1,4-dicarboxylate),³⁸ providing ideal examples for studying the inherent relationship between the metal electronic-state and adsorption performance. Compared with LIFM-27(Fe[III]), the increased electron density in LIFM-26(Fe[II]/Fe[III]) affords much higher C₂H₂ uptake capacity and superior C₂H₂ selectivity over CO₂ in the low-pressure region, due to the stronger Fe[II]-adsorbate interactions than Fe[III]-C₂H₂, which illustrates that manipulation of the electronic-state of OMSs can lead to enhanced preferential C₂H₂ adsorption.

Moreover, the combined studies of ideal adsorbed solution theory (IAST) calculations, simulated/experimental dynamic breakthrough experiments, molecular simulations, and *in situ* infrared (IR) analysis well confirm that the exposed Fe[II] center with a strong π back-donation character plays a crucial role in the enhanced C₂H₂/CO₂ separation.

RESULTS AND DISCUSSION

Synthesis and structure determination

LIFM-26(Fe[II]/Fe[III]) was synthesized according to our previously reported method with a slight modification.³⁷ The slow diffusion of triethylamine vapor into a mixture of *N,N*-dimethylformamide (DMF) and water dissolving TCDC ligand and FeCl₂ for 3 days afforded LIFM-26(Fe[II]/Fe[III]) crystals, during which Fe[II] was partially oxidized into Fe[III]. In comparison, LIFM-27(Fe[III]) was obtained by extending the vapor diffusion time to 1 month, during which Fe[II] was completely oxidized into Fe[III] (Scheme 1). Notably, LIFM-27(Fe[III]) can be transformed back to LIFM-26(Fe[II]/Fe[III]) via soaking the samples in ethanol solution for 3 days at 75°C (denoted as LIFM-27(Fe[III])-EtOH; Figure S10), showing solvent-dependent redox property. Single-crystal X-ray diffraction (SCXRD) analyses reveal that LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) crystallize in the *P*-3 and *P*21/*n* space groups, respectively (Table S1). Both of them possess the same acs net topology as (Fe[II]/Fe[III])₃O(TFBDC)₃, which is constructed from perfluorinated ligand TFBDC and FeCl₂ (Figure 1). Compared with (Fe[II]/Fe[III])₃O(TFBDC)₃, the Fe₃O clusters in LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) are twisted without the C₃ axis of symmetry perpendicular to the Fe₃O plane due to the large steric hindrance of chlorine atoms. The Fe-(μ_3 -O)-Fe angles in LIFM-26(Fe[II]/Fe[III]) are 115.8°, 120.9°, and 123.3°, while those in LIFM-27(Fe[III]) are 118.4°, 118.8°, and 122.8°. In these three structures, every Fe₃O cluster connects six ligands, whereas every ligand links two independent Fe₃O clusters, thus forming a three-dimensional (3D) framework containing 1D channels (Figures 1C–1E). Notably, (Fe[II]/Fe[III])₃O(TFBDC)₃ presents one type of round channel along the *c* axis with an aperture size of ca. 13.2 Å (Figures 1C and 1F), while LIFM-26(Fe[II]/Fe[III]) features two types of different channels functionalized by chlorine atoms along the *c* axis, i.e., one round channel with an aperture size of ca. 9.0 Å and one elliptic channel with a pore size of ca. 8.2 × 11.5 Å² (Figures 1D, 1G, and S1). As for LIFM-27(Fe[III]), there is one type of elliptic channel decorated by chlorine atoms along the *c* axis with a pore size of about 7.5 × 9.7 Å² (Figures 1E, 1H, and S2). Additionally, all three frameworks present one type of tetrahedral cage (diameter ca. 7.0 Å) constructed from six ligands and five Fe₃O clusters (Figure 1I).

In order to probe the oxidation and spin states of Fe centers, ⁵⁷Fe Mössbauer spectroscopic experiments were carried out for LIFM-26(Fe[II]/Fe[III]), LIFM-27(Fe[III]), and LIFM-27(Fe[III])-EtOH (Figures 2 and S3–S5; Table S2). The spectra of LIFM-26(Fe[II]/Fe[III]) can be fitted by one type of doublet and one type of singlet, revealing two kinds of Fe species with adsorption area ratios of 47.65% and 52.35%, corresponding to the amounts of Fe[II] and Fe[III] centers (0.9:1.0) (Figure 2A, D1 line). For comparison, only one type of fitting doublet in LIFM-27(Fe[III]) was observed, confirming the existence of sole Fe[III] species (Figure 2B). LIFM-27(Fe[III])-EtOH also shows two kinds of Fe species similar to LIFM-26(Fe[II]/Fe[III]) yet with different adsorption area ratios, implying a variation of Fe[II] and Fe[III] species (Fe[II]:Fe[III] = 0.5:1.0; Figure S5). As shown in Figure 2A, the D2 line can readily be assigned to high-spin Fe[III] species in LIFM-26(Fe[II]/Fe[III]) with isomer shift δ = 0.78 mm/s,³⁴ while the D3 line can be assigned to medium-spin Fe[II] species with isomer shift δ = 0.31 mm/s and quadrupole splitting value

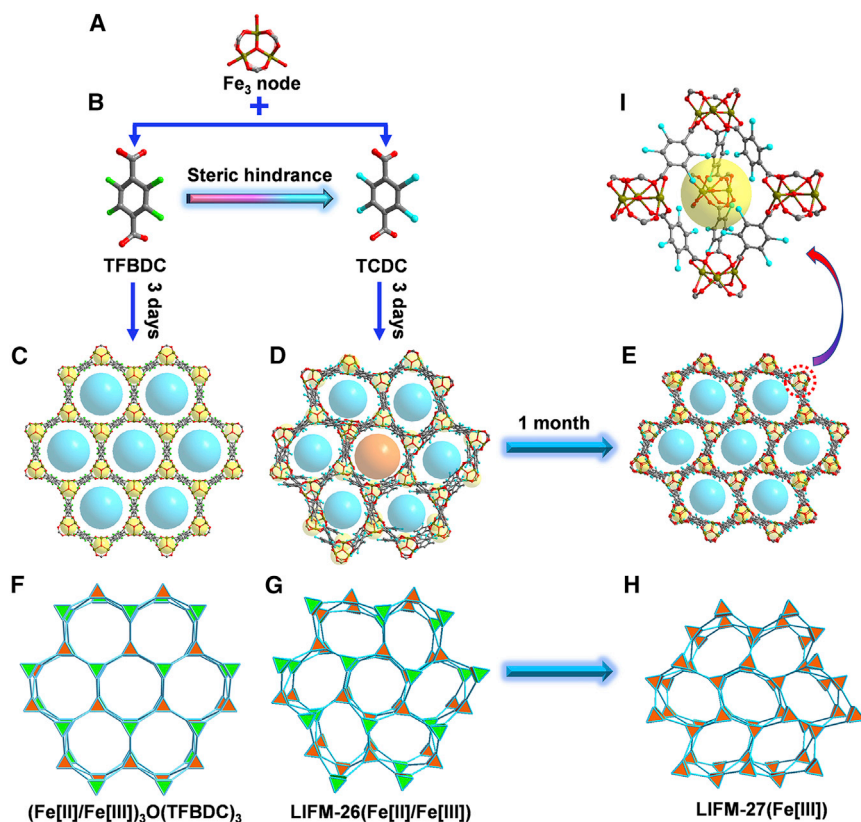


Figure 1. The schematic construction route of the 3D-MOFs

(A) Trimeric Fe₃O cluster.

(B) TFBDC and TCDC ligands.

(C–E) The 3D structures of (C) (Fe[II]/Fe[III])₃O(TFBDC)₃, (D) LIFM-26(Fe[II]/Fe[III]), and (E) LIFM-27(Fe[III]).

(F–H) The corresponding network topologies of (F) (Fe[II]/Fe[III])₃O(TFBDC)₃, (G) LIFM-26(Fe[II]/Fe[III]), and (H) LIFM-27(Fe[III]).

(I) The tetrahedral cage in three isostructural MOFs.

$\Delta E_{\text{O}} = 0.56 \text{ mm/s}$,³⁴ suggesting the existence of a strong π back donation in LIFM-26(Fe[II]/Fe[III]). For LIFM-27(Fe[III]), the Mössbauer spectra reveal only one type of high-spin Fe[III] species with isomer shift $\delta = 0.44 \text{ mm/s}$.

Purity and porosity

Powder X-ray diffraction (PXRD) patterns were conducted to confirm the phase purity of the as-synthesized samples (Figures S8, S9, and S11), and the scanning electron microscope (SEM) images unveil similar crystal morphology (Figure S7). Thermal gravimetric analyses (TGAs) indicate comparable thermal stability of two isostructural MOFs up to 250°C (Figure S6). In contrast to (Fe[II]/Fe[III])₃O(TFBDC)₃ (Figure S11), both LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) retain good crystallinity after activation under high vacuum, indicative of their good framework robustness (Figures S8 and S9). N₂ sorption isotherms at 77 K were collected to evaluate the permanent porosity of all three samples. As shown in Figure 3A, LIFM-26(Fe[II]/Fe[III]) (356 cm³ g⁻¹) and LIFM-27(Fe[III]) (310 cm³ g⁻¹) show much higher N₂ uptakes than (Fe[II]/Fe[III])₃O(TFBDC)₃ (17 cm³ g⁻¹) due to loss of its crystallinity after activation (Figure S11). Both LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) show typical type I adsorption isotherms with the Brunauer-Emmett-Teller (BET) surface areas of 1,403 and 1,174 m² g⁻¹, respectively, and the total pore volumes are 0.55 and 0.48 cm³ g⁻¹, respectively (Figures S12–S14; Table S3). The pore sizes of

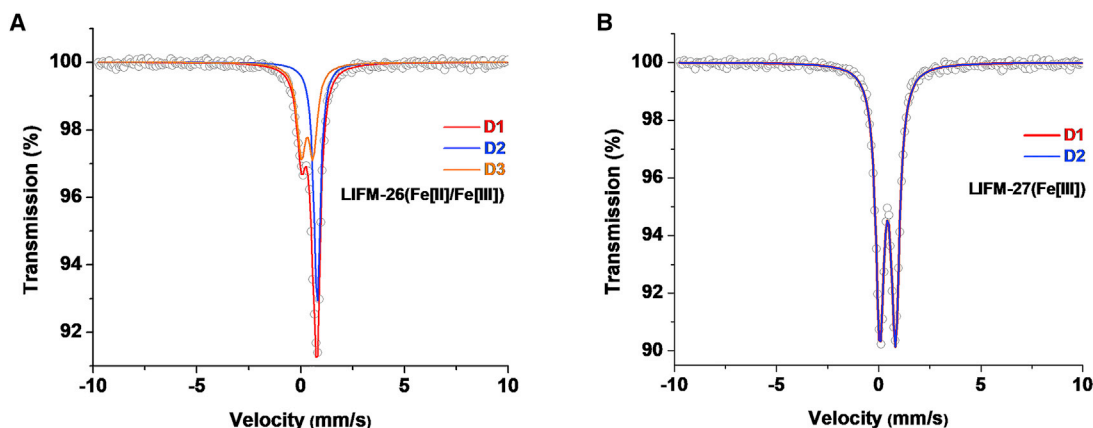


Figure 2. The ^{57}Fe Mössbauer Spectroscopy collected at 298 K

(A) LIFM-26(Fe[II]/Fe[III]).

(B) LIFM-27(Fe[III]).

LIFM-26(Fe[II]/Fe[III]) are calculated to be 6.8, 8.0, and 10.1 Å by density functional theory (DFT) analysis, while those of LIFM-27(Fe[III]) are 6.8 and 8.0 Å (Figure S15), matching well with the corresponding structural analyses. Additionally, we also evaluated the porosity of LIFM-27(Fe[III])-EtOH, which exhibits the BET surface area and pore volumes of 1,330 $\text{m}^2 \text{g}^{-1}$ and 0.53 $\text{cm}^3 \text{g}^{-1}$, falling between those of LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) (Figure S16; Table S4).

Adsorption studies

The suitable pore structures of two isostructural Fe-MOFs as described above, including appropriate pore size and high pore volume as well as polar pore surface, are anticipated to facilitate C_2H_2 adsorption. To examine the effectiveness of the variant electronic state of OMSs on the adsorption performance, we selected C_2H_2 as a model gas molecule for evaluation. The C_2H_2 adsorption isotherms of both MOFs were measured at 273, 285, and 298 K, respectively (Figures 3B, 3C, S17, S19–S21, and S23–S24). Evidently, LIFM-26(Fe[II]/Fe[III]) showed much higher C_2H_2 uptake capacity (181 and 131 $\text{cm}^3 \text{g}^{-1}$ at 273 and 298 K, 1 bar, respectively) than LIFM-27(Fe[III]) (128 and 97 $\text{cm}^3 \text{g}^{-1}$ at 273 and 298 K, 1 bar, respectively), suggesting that Fe[II] center with higher electron density for stronger π back donation in LIFM-26(Fe[II]/Fe[III]) can effectively improve its adsorption behavior. Specifically, LIFM-26(Fe[II]/Fe[III]) (17.0 $\text{cm}^3 \text{g}^{-1}$) can take up more than four times of C_2H_2 than LIFM-27(Fe[III]) (4.2 $\text{cm}^3 \text{g}^{-1}$) at low pressure (3.4 mbar) (Figure 3D). Moreover, the C_2H_2 uptake capacity of LIFM-26(Fe[II]/Fe[III]) is much higher than that of $(\text{Fe[III]/Fe[III]})_3\text{O}(\text{TFBDC})_3$ (Figures 3B and S25), and is also higher than many other known MOFs like Zn-MOF-74 (122 $\text{cm}^3 \text{g}^{-1}$),³¹ UTSA-74a (104 $\text{cm}^3 \text{g}^{-1}$),³³ and PCP-33 (122 $\text{cm}^3 \text{g}^{-1}$),³⁹ but is lower than some MOFs like FJI-H8-R series (174–229 $\text{cm}^3 \text{g}^{-1}$),^{17,24} MIL-160 (191 $\text{cm}^3 \text{g}^{-1}$),⁴⁰ SIFSIX-Cu-TPA (185 $\text{cm}^3 \text{g}^{-1}$),⁴¹ and FJU-90a (180 $\text{cm}^3 \text{g}^{-1}$) (Table S5).⁴² To further confirm the effect of low-valent Fe(II) center, the C_2H_2 adsorption of LIFM-27(Fe[III])-EtOH, in which the amount of Fe[II] center is less than the prototypical LIFM-26(Fe[II]/Fe[III]), was measured at 298 K. As expected, the C_2H_2 uptake by LIFM-27(Fe[III])-EtOH was lower than LIFM-26(Fe[II]/Fe[III]) but higher than LIFM-27(Fe[III]) (Figures S30–S32). Additionally, the CO_2 adsorption isotherms were performed on both Fe-MOFs. LIFM-26(Fe[II]/Fe[III]) can take up 80 $\text{cm}^3 \text{g}^{-1}$ CO_2 at 298 K and 1 bar, while the uptake capacity of LIFM-27(Fe[III]) is 51 $\text{cm}^3 \text{g}^{-1}$ under the same condition (Figures 3B, 3C, S18, and S22). These

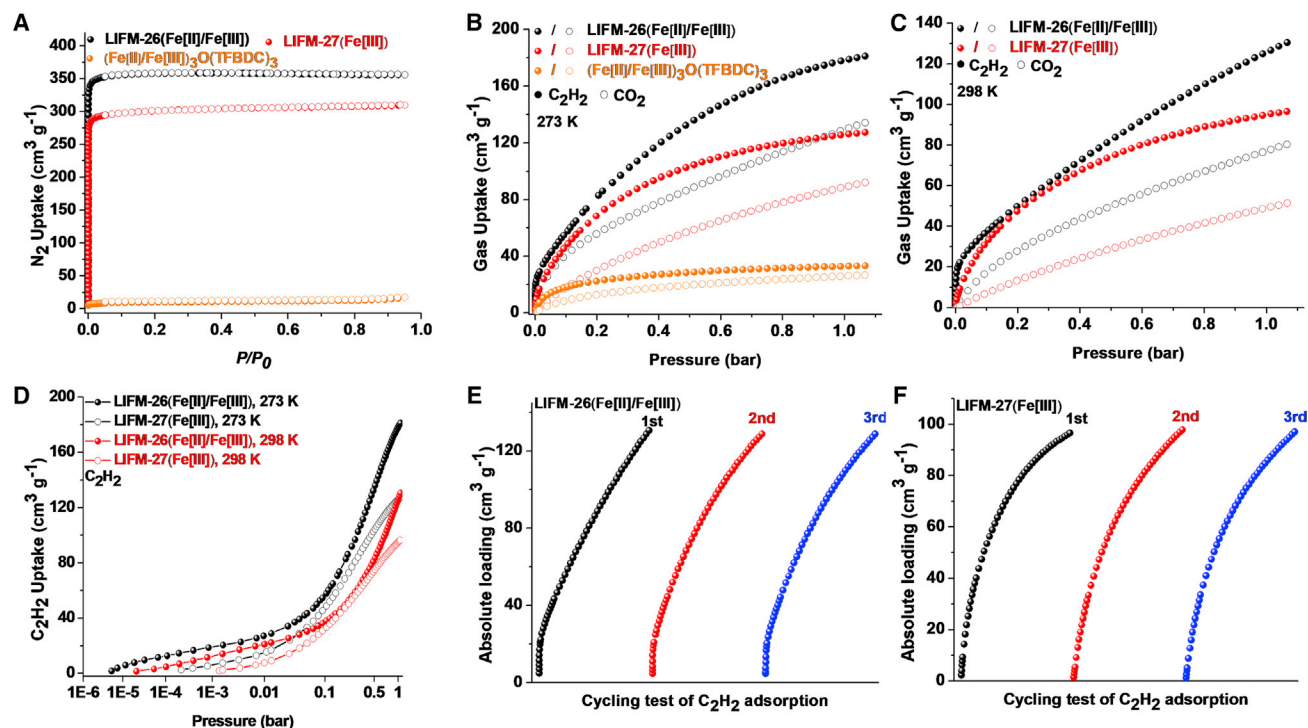


Figure 3. Gas adsorption properties of the three MOFs

(A) The N_2 adsorption of all the three MOFs at 77 K.

(B and C) The C_2H_2 and CO_2 adsorption isotherms at (B) 273 and (C) 298 K.

(D) The C_2H_2 adsorption isotherms.

(E and F) The repetitive C_2H_2 adsorption isotherms of (E) LIFM-26(Fe[II]/Fe[III]) and (F) LIFM-27(Fe[III]).

results indicate that the gas adsorption performance of the two isostructural Fe-MOFs can be finely tuned by regulating the electron state of OMSs. Furthermore, the continuous C_2H_2 and CO_2 adsorption isotherms on both Fe-MOFs were carefully performed, verifying their excellent reusability (Figures 3E, 3F, and S26–S29).

The isosteric heat (Q_{st}) of C_2H_2 and CO_2 on both MOFs were calculated using the Clausius-Clapeyron equation based on their adsorption isotherms at three different temperatures (Figures S17, S18, S21, S22, and S33–S36). For C_2H_2 , LIFM-26(Fe[II]/Fe[III]) displays higher isosteric heat (53.8 kJ mol^{-1}) than LIFM-27(Fe[III]) (44.6 kJ mol^{-1}) at near-zero coverage corresponding to the interactions between gas and Fe center, which further confirms the electronic effect of the open Fe[II] centers (Figures S37 and S38). Afterward, the subsequent gradual decrease in isosteric heat for C_2H_2 on both MOFs along with increased C_2H_2 loading amount indicate the adsorption saturation of Fe centers. Notably, the moderate Q_{st} value of C_2H_2 in LIFM-26(Fe[II]/Fe[III]) is lower than some other reported MOFs with OMSs, such as ATC-Cu (79.1 kJ mol^{-1}),¹⁶ Cu@UiO-66(COOH)₂ (74.5 kJ mol^{-1}),⁴³ ZJU-74a (65.0 kJ mol^{-1}),⁴⁴ and NKMOF-1-Ni (60.3 kJ mol^{-1}),⁴⁵ implying the sufficient adsorption reversibility of the adsorbent owing to the presence of Fe(III) center. For CO_2 , both MOFs present comparable isosteric heats, giving values of 37.8 (LIFM-26(Fe[II]/Fe[III])) and 35.8 kJ mol^{-1} (LIFM-27(Fe[III])) at near-zero coverage (Figures S37 and S38). The higher Q_{st} value of C_2H_2 than CO_2 suggests a promising potential of C_2H_2 purification from C_2H_2/CO_2 gas mixture.

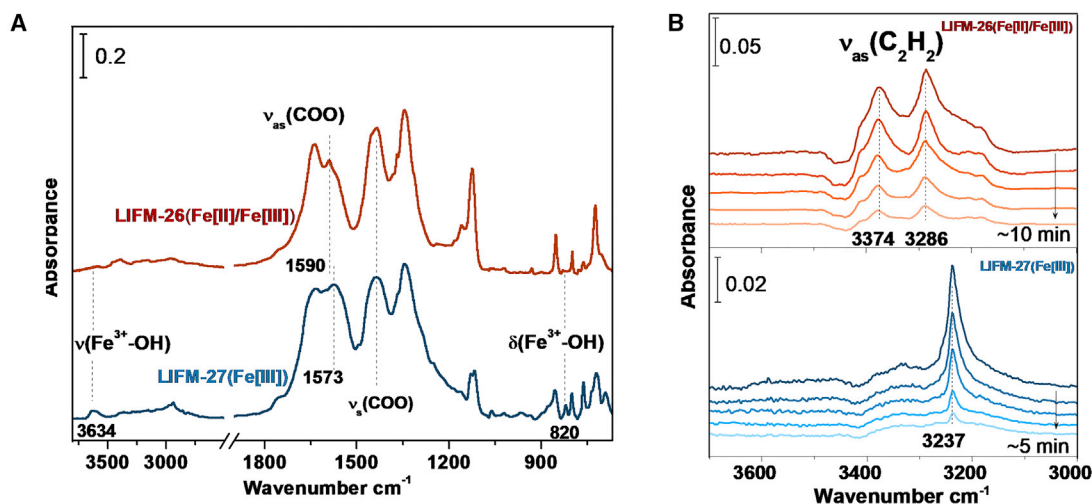


Figure 4. *In situ* IR spectra of LIFM-26(Fe(II)/Fe(III)) and LIFM-27(Fe(III)) before and after C₂H₂ loading

(A) IR spectra of activated LIFM-26(Fe(II)/Fe(III)) (top) and LIFM-27(Fe(III)) (bottom) samples, referenced to pure KBr pellet in vacuum (<20 mTorr base pressure).

(B) Difference spectra showing the asymmetric stretching band ν_{as} of adsorbed C₂H₂ in LIFM-26(Fe(II)/Fe(III)) (top) and LIFM-27(Fe(III)) (bottom) samples upon loading at the pressure of ~1 bar (top spectrum in each panel) and subsequent evacuation of gas phase under vacuum for ~10 and ~5 min, respectively. Each is referenced to the spectrum of activated sample.

Adsorption mechanism

To probe the binding interaction of C₂H₂ with the frameworks, *in situ* IR spectroscopy measurements were performed. The samples of LIFM-26(Fe(II)/Fe(III)) and LIFM-27(Fe(III)) were first heated under vacuum to remove trapped solvents and then cooled to room temperature to collect IR spectra of activated samples, as presented in Figure 4A. The spectra of two samples are dominated by the vibrational bands associated with the organic linker (Figure S44), which exhibit general similarities. A noticeable difference is that the LIFM-27(Fe(III)) sample shows extra two bands at ~3,634 and 820 cm⁻¹, which are absent in LIFM-26(Fe(II)/Fe(III)). Based on the well-established studies on Fe-based MOFs containing a hydroxyl group,^{46,47} these two bands are attributed to the stretching and deformation modes of OH⁻, which terminates one Fe(III) of the trimeric Fe(III)₃O cluster for charge balance. In the neutrally charged (Fe(II)/Fe(III))₃O cluster of the LIFM-26(Fe(II)/Fe(III)) sample, no extra OH⁻ is needed. In addition, careful examination of spectra at 1,600–1,500 cm⁻¹ reveals that carboxylate asymmetric stretching band $\nu_{\text{as}}(\text{COO})$ in LIFM-26(Fe(II)/Fe(III)) occurs at a higher frequency (1,590 cm⁻¹) than that in the LIFM-27(Fe(III)) sample, leading to a larger separation $\Delta\nu$ between $\nu_{\text{as}}(\text{COO})$ and $\nu_{\text{s}}(\text{COO})$.⁴⁸ This is as expected since the inequivalence of the two C–O bonds connected with Fe(II) and Fe(III), respectively, would further split $\Delta\nu$.^{49,50} Gas adsorption measurement was then conducted on these activated samples by loading C₂H₂ at ~1 bar for ~10 min to ensure adsorption saturation, which was followed by subsequent desorption via pumping the samples under vacuum. The adsorbed C₂H₂ is clearly observed in different IR spectra (Figure 4B), which demonstrate the characteristic stretching band $\nu_{\text{as}}(\text{C}_2\text{H}_2)$ of adsorbed C₂H₂ at 3,400–3,200 cm⁻¹. A marked difference is noted for both the position and shape of the $\nu_{\text{as}}(\text{C}_2\text{H}_2)$ band between in LIFM-26(Fe(II)/Fe(III)) and LIFM-27(Fe(III)). LIFM-27(Fe(III)) displays only a single band located at 3,237 cm⁻¹, which corresponds to C₂H₂ adsorbed at the primary exposed Fe(III) sites, as identified by molecular simulations (Figures 5B and S46; vide infra). In comparison, LIFM-26(Fe(II)/Fe(III)) shows two distinct bands appearing at higher frequencies of 3,374 and 3,286 cm⁻¹, pointing to two types of C₂H₂

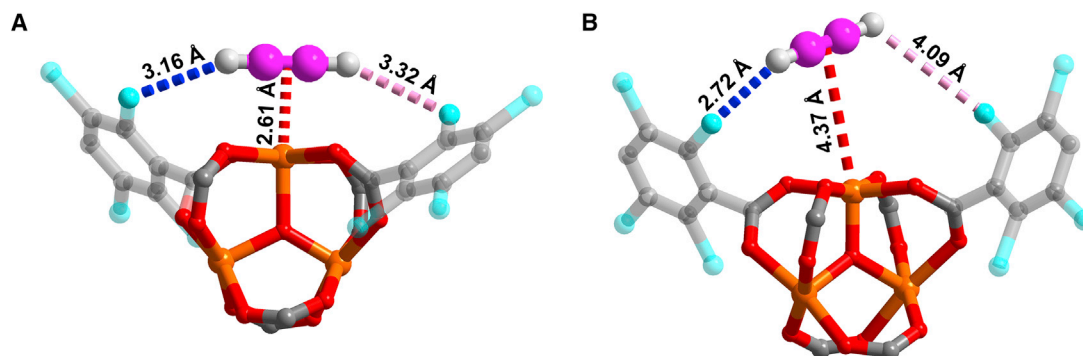


Figure 5. Preferential binding sites

(A and B) The preferential C_2H_2 binding sites in (A) LIFM-26(Fe[II]/Fe[III]) and (B) LIFM-27(Fe[III]).

adsorbed on Fe[II] and Fe[III] sites, respectively. It is noteworthy that the $3,374\text{ cm}^{-1}$ band undergoes an upward shift (blue shift) with respect to the value of the gas phase C_2H_2 ($3,287\text{ cm}^{-1}$).⁵¹ Such a shift to the higher wavenumber strongly suggests that π back donation occurs between Fe[II] cations and C_2H_2 in LIFM-26(Fe[II]/Fe[III]),⁵² which weakens the C–C bond but stiffens the C–H bond,⁵³ thus resulting in a raise of C–H stretching frequency. The broadening and asymmetric line shape of the $\nu_{as}(C_2H_2)$ bands in LIFM-26(Fe[II]/Fe[III]) indicate vibrational dynamic coupling between adsorbed C_2H_2 molecules, which could account for the occurrence of the Fe[III]-bound C_2H_2 band at a higher frequency of $3,286\text{ cm}^{-1}$ in LIFM-26(Fe[II]/Fe[III]) compared with that in LIFM-27(Fe[III]) ($3,237\text{ cm}^{-1}$).⁵⁴

To get further insight into the adsorption mechanism with regard to the mixed-valent Fe[II]/Fe[III] centers, we implemented molecular simulations. For LIFM-26(Fe[II]/Fe[III]), C_2H_2 is mainly located in the channel surrounded by one open Fe[II] center and two chlorine atoms, in which the strong $Fe\cdots C\equiv C$ (2.61 \AA) and weak $C-Cl\cdots H$ interactions (3.16 and 3.22 \AA) occur between C_2H_2 and the framework, suggesting strong C_2H_2 binding affinity (Figures 5A and S45), whereas the C_2H_2 binding site in LIFM-27(Fe[III]) is located in the elliptic channel surrounded by one open Fe[III] center and two chlorine atoms with weak $Fe\cdots C\equiv C$ (4.37 \AA) and $C-Cl\cdots H$ interactions (2.72 and 4.09 \AA), indicating weaker C_2H_2 binding affinity compared with LIFM-26(Fe[II]/Fe[III]) (Figures 5B and S46). The calculated C_2H_2 binding energy for LIFM-26(Fe[II]/Fe[III]) is 49.7 kJ mol^{-1} , which is higher than LIFM-27(Fe[III]) (45.6 kJ mol^{-1}) (Table S6), manifesting the stronger interaction between C_2H_2 and LIFM-26(Fe[II]/Fe[III]). In comparison, both LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) present weaker interactions toward CO_2 . The observed CO_2 binding site in LIFM-26(Fe[II]/Fe[III]) is mainly the $Fe\cdots O-C$ interaction with a distance of 2.13 \AA , which is similar to that of LIFM-27(Fe[III]) ($Fe\cdots O-C$ distance is 2.17 \AA) (Figures S47–S49). The CO_2 binding energy for LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) are calculated to be 38.5 and 37.6 kJ mol^{-1} , respectively (Table S6), which are weaker than those of C_2H_2 , confirming the feasible C_2H_2/CO_2 -separation performance.

IAST adsorption selectivity and dynamic breakthrough

To evaluate the C_2H_2/CO_2 -separation ability, the IAST⁵⁵ calculation was conducted on the basis of the composition of a 50:50 C_2H_2/CO_2 mixture (Figures S39–S42). As shown in Figures 6A and S43, LIFM-26(Fe[II]/Fe[III]) gives much higher C_2H_2/CO_2 selectivity (56.1 at 0.01 bar) than LIFM-27(Fe[III]) (14.3 at 0.01 bar) under low pressure, which can be attributed to the stronger Fe[II]– C_2H_2 binding affinity as a result

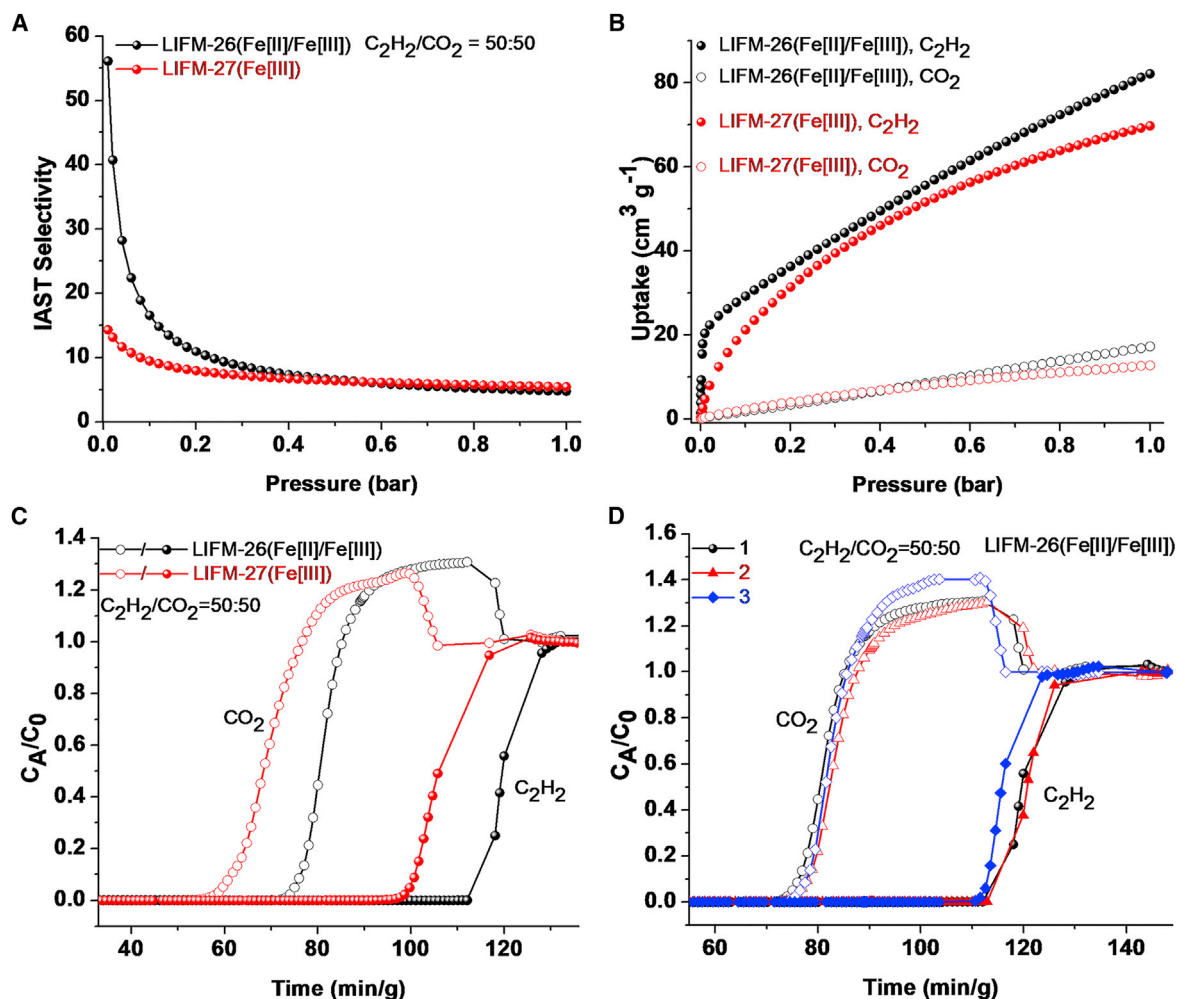


Figure 6. IAST calculated selectivity and dynamic breakthrough

(A) IAST adsorption selectivity of C₂H₂/CO₂ (v/v, 50:50) at 298 K.

(B) IAST calculated C₂H₂ and CO₂ uptake capacity for equimolar C₂H₂/CO₂ mixtures.

(C) The experimental dynamic breakthrough measurements of LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) for C₂H₂/CO₂ mixture at 298 K and 1 bar.

(D) The cycling dynamic breakthrough measurements of LIFM-26(Fe[II]/Fe[III]) for C₂H₂/CO₂ mixture at 298 K and 1 bar.

of the increased electron density at the Fe[II] center. Subsequently, the C₂H₂/CO₂ selectivity for both MOFs gradually decreases as a function of the increased pressure due to the adsorption saturation of the Fe centers. The final C₂H₂/CO₂ selectivities for LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) are 4.8 and 5.5 at 298 K and 1 bar, respectively, which are comparable with many reported MOFs, such as SIFSIX-Cu-TPA (5.3),⁴¹ SNNU-45 (4.5),⁵⁶ TIFSIX-2-Cu-i (6.5),²⁸ FJU-90 (4.3),⁴² UTSA-222 (4.0),⁵⁷ JNU-1 (3.6),¹⁸ and Zn-MOF-74 (2.8).³¹ Additionally, the C₂H₂ uptake capacity was calculated based on the IAST method. Compared with LIFM-27(Fe[III]) (4.7 cm³ g⁻¹ at 0.01 bar), LIFM-26(Fe[II]/Fe[III]) exhibits enhanced C₂H₂-capture performance, especially at low pressure (20.4 cm³ g⁻¹ at 0.01 bar) (Figure 6B). More importantly, the C₂H₂ uptake capacity for both MOFs is remarkably higher than their CO₂ adsorption, implying potential C₂H₂-separation ability from C₂H₂/CO₂ mixture (Figure 6B).

Prompted by the outstanding C₂H₂ uptake capacity and C₂H₂/CO₂ adsorption selectivity, the simulated transient breakthrough experiments were carried out

according to the documented methodology.⁵⁸ For both LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]), CO₂ elutes first, and then C₂H₂ breaks through after some time, demonstrating the adequate capacity for the demanding C₂H₂/CO₂ separation (Figures S52 and S53). The C₂H₂ capture productivity calculated on the basis of the simulated breakthrough curves gives rise to the values of 88.9 (LIFM-26(Fe[II]/Fe[III])) and 76.6 (LIFM-27(Fe[III])) cm³ g⁻¹, unveiling the better C₂H₂/CO₂-separation performance of LIFM-26(Fe[II]/Fe[III]). It is noticeable that the C₂H₂ productivity for LIFM-26(Fe[II]/Fe[III]) is slightly lower than FJU-90 (114.2 cm³ g⁻¹)⁴² yet higher than other reported MOFs including FJU-22a (83.1 cm³ g⁻¹),⁵⁹ ZUL-60a (80.6 cm³ g⁻¹),⁶⁰ UTSA-74a (79.7 cm³ g⁻¹),³³ Zn-MOF-74 (76.6 cm³ g⁻¹),³¹ and PCP-33 (75.7 cm³ g⁻¹).³⁹

To further assess the practical C₂H₂/CO₂-separation performance by both LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]), dynamic fixed-bed breakthrough experiments were conducted through a stainless-steel column under ambient condition, in which the equimolar C₂H₂/CO₂ mixture flowed over the packed column with a flow rate of 1.0 mL min⁻¹. As depicted in Figure 6C, both Fe-MOFs present excellent C₂H₂-separation performance from C₂H₂/CO₂ mixture. For LIFM-26(Fe[II]/Fe[III]), CO₂ undoubtedly elutes first and then quickly reaches a pure grade without detectable C₂H₂, while C₂H₂ remains in the packed column for a remarkable time until it is saturated in LIFM-26(Fe[II]/Fe[III]). As expected, LIFM-27(Fe[III]) exhibits similar C₂H₂/CO₂ dynamic breakthrough behavior but with a shorter C₂H₂ breakthrough time. Based on the experimental breakthrough curves, LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) present comparable C₂H₂/CO₂ selectivity with values of 1.6 and 1.7, respectively. The calculated C₂H₂-capture productivity for LIFM-26(Fe[II]/Fe[III]) based on the experimental breakthrough curve is estimated to be 60.0 cm³ g⁻¹, whereas the value for LIFM-27(Fe[III]) is 53.7 cm³ g⁻¹. In principle, ideal adsorbents should present good recyclability in practical industrial applications. Therefore, the continuous dynamic breakthrough experiments were performed under the above conditions. The results indicate that both Fe-MOFs maintain almost the same retaining time and capture productivity in three continuous C₂H₂/CO₂ dynamic breakthrough experiments (Figures 6D, S50, and S51), demonstrating their good reusability. The PXRD patterns after the repetitive experiments also confirm the crystallinity is retained well (Figures S54 and S55). Taken together, these results clearly demonstrate that the Fe-MOFs have successfully achieved a combination of high C₂H₂ uptake capacity, moderate-high C₂H₂/CO₂ selectivity, and sufficient reversibility by rationally regulating the electronic state of the open-metal centers.

In summary, a metal electronic-state manipulation strategy has been successfully applied to constructing a pair of microporous isostructural Fe-MOFs featuring open Fe centers with different electron densities for efficient C₂H₂/CO₂ separation. Notably, the isostructural LIFM-26(Fe[II]/Fe[III]) and LIFM-27(Fe[III]) can be interconverted, and the electronic state of Fe centers can be finely tuned by simply changing the oxidation conditions depending on the solvents and reaction time, thus facilitating understanding of the inherent relationship between the metal electronic state and C₂H₂ selective adsorption. Compared with LIFM-27(Fe[III]), LIFM-26(Fe[II]/Fe[III]) presents remarkably higher C₂H₂ uptake capacity while retaining moderate-high C₂H₂/CO₂ selectivity, which is well supported by the simulated and experimental dynamic breakthrough experiments. *In situ* IR and molecular calculations manifest that LIFM-26(Fe[II]/Fe[III]) exhibits enhanced binding affinity toward C₂H₂ than LIFM-27(Fe[III]) due to the increased electron density at the metal site, resulting in a stronger π back donation. Significantly, this work provides an effective guideline to realize the challenging C₂H₂/CO₂ separation by rationally manipulating the electronic state of OMSs in MOF pore spaces.

MATERIALS AND METHODS

See the [supplemental experimental procedures](#) for full details of synthesis, characterization, modeling and analysis, and adsorption and breakthrough measurements.

EXPERIMENTAL PROCEDURES

Resource availability

Lead contact

Further information and requests for resources should be directed to and will be fulfilled by the lead contact, Cheng-Yong Su (cesscy@mail.sysu.edu.cn), and Sheng-qian Ma (shengqian.ma@unt.edu).

Materials availability

All materials generated in this study are available from the [lead contact](#) without restriction.

Data and code availability

The X-ray crystallographic coordinates for LIFM-27(Fe[III]) have been deposited at the Cambridge Crystallographic Data Centre (CCDC) under CCDC: 2114493. These data can be obtained free of charge from the CCDC via http://www.ccdc.cam.ac.uk/data_request/cif. All other data are available from the [lead contact](#) upon request.

SUPPLEMENTAL INFORMATION

Supplemental information can be found online at <https://doi.org/10.1016/j.xcrp.2022.100977>.

ACKNOWLEDGMENTS

This work was supported by NSFC (21821003, 21890380, and 22001271), the Chinese Postdoctoral Science Foundation (2017M622866), the International Postdoctoral Exchange Fellowship Program (20180055), and FRF for the Central Universities (20lgpy79). The authors also extend their appreciation to the Robert A. Welch Foundation (B-0027) and Researchers Supporting Program (RSP-2022/55) at King Saud University, Riyadh, Saudi Arabia, for partial support of this work. T.P. and K.A.F. acknowledge the use of services provided by Research Computing at the University of South Florida. The IR spectroscopic work was supported by the US Department of Energy, Office of Science, Basic Energy Sciences, under award no. DE-SC0019902.

AUTHOR CONTRIBUTIONS

Conceptualization, C.-X.C., C.-Y.S., and S.M.; methodology, C.-X.C.; investigation, C.-X.C.; theoretical calculation, T.P. and K.A.F.; *in situ* IR measurements, K.T.; simulated transient breakthrough, R.K.; Mössbauer spectra, S.C. and L.W.; writing – original draft, C.-X.C.; writing – review & editing, C.-X.C., H.W., S.M., and C.-Y.S.; funding acquisition, C.-X.C., C.-Y.S., and S.M.; all authors analyzed and discussed the data and contributed to writing the paper.

DECLARATION OF INTERESTS

The authors declare no competing interests.

Received: April 14, 2022

Revised: June 3, 2022

Accepted: June 17, 2022

Published: July 20, 2022

REFERENCES

- Sholl, D.S., and Lively, R.P. (2016). Seven chemical separations to change the world. *Nature* 532, 435–437. <https://doi.org/10.1038/532435a>.
- Guo, C.J., Shen, D., and Bülow, M. (2001). 18-O-3-Kinetic separation of binary mixtures of carbon dioxide and C₂ hydrocarbons on modified LTA-type zeolites. In *Studies in Surface Science and Catalysis*, A. Galarneau, F. Fajula, F. Di Renzo, and J. Védrine, eds. (Elsevier), p. 144.
- Pässler, P., Hefner, W., Buckl, K., Meiness, H., Meiswinkel, A., Wernicke, H.-J., Ebersberg, G., Müller, R., Bässler, J., Behringer, H., and Mayer, D. (2011). In *Ullmann's Encyclopedia of Industrial Chemistry*, B. Elvers, ed. (Wiley-VCH).
- Duan, X., Cai, J., Yu, J., Wu, C., Cui, Y., Yang, Y., and Qian, G. (2013). Three-dimensional copper (II) metal-organic framework with open metal sites and anthracene nucleus for highly selective C₂H₂/CH₄ and C₂H₂/CO₂ gas separation at room temperature. *Microporous Mesoporous Mater.* 181, 99–104. <https://doi.org/10.1016/j.micromeso.2013.07.019>.
- Reid, C.R., and Thomas, K.M. (2001). Adsorption kinetics and size exclusion properties of probe molecules for the selective porosity in a carbon molecular sieve used for air separation. *J. Phys. Chem. B* 105, 10619–10629. <https://doi.org/10.1021/jp0108263>.
- Adil, K., Belmabkhout, Y., Pillai, R.S., Cadiau, A., Bhatt, P.M., Assen, A.H., Maurin, G., and Eddaoudi, M. (2017). Gas/vapour separation using ultra-microporous metal-organic frameworks: insights into the structure/separation relationship. *Chem. Soc. Rev.* 46, 3402–3430. <https://doi.org/10.1039/c7cs00153c>.
- Shekha, O., Chernikova, V., Belmabkhout, Y., and Eddaoudi, M. (2018). Metal-organic framework membranes: from fabrication to gas separation. *Crystals* 8, 412. <https://doi.org/10.3390/cryst8110412>.
- Yang, L., Qian, S., Wang, X., Cui, X., Chen, B., and Xing, H. (2020). Energy-efficient separation alternatives: metal-organic frameworks and membranes for hydrocarbon separation. *Chem. Soc. Rev.* 49, 5359–5406. <https://doi.org/10.1039/c9cs00756c>.
- Li, J., Bhatt, P.M., Li, J., Eddaoudi, M., and Liu, Y. (2020). Recent progress on microfine design of metal-organic frameworks: structure regulation and gas sorption and separation. *Adv. Mater.* 32, 2002563. <https://doi.org/10.1002/adma.202002563>.
- Wang, H., Liu, Y., and Li, J. (2020). Designer metal-organic frameworks for size-exclusion-based hydrocarbon separations: progress and challenges. *Adv. Mater.* 32, 2002603. <https://doi.org/10.1002/adma.202002603>.
- Lin, R.-B., Xiang, S., Zhou, W., and Chen, B. (2020). Microporous metal-organic framework materials for gas separation. *Chem* 6, 337–363. <https://doi.org/10.1016/j.chempr.2019.10.012>.
- Hua, G.F., Xie, X.J., Lu, W., and Li, D. (2020). Optimizing supramolecular interactions in metal-organic frameworks for C₂ separation. *Dalton Trans.* 49, 15548–15559. <https://doi.org/10.1039/d0dt03013a>.
- Cui, W.G., Hu, T.L., and Bu, X.H. (2020). Metal-organic framework materials for the separation and purification of light hydrocarbons. *Adv. Mater.* 32, 1806445. <https://doi.org/10.1002/adma.201806445>.
- Oktawiec, J., Jiang, H.Z.H., Vitillo, J.G., Reed, D.A., Darago, L.E., Trump, B.A., Bernales, V., Li, H., Colwell, K.A., Furukawa, H., et al. (2020). Negative cooperativity upon hydrogen bond-stabilized O₂ adsorption in a redox-active metal-organic framework. *Nat. Commun.* 11, 3087. <https://doi.org/10.1038/s41467-020-16897-z>.
- Reed, D.A., Xiao, D.J., Gonzalez, M.I., Darago, L.E., Herm, Z.R., Grandjean, F., and Long, J.R. (2016). Reversible CO scavenging via adsorbate-dependent spin state transitions in an iron(II)-Triazolate metal-organic framework. *J. Am. Chem. Soc.* 138, 5594–5602. <https://doi.org/10.1021/jacs.6b00248>.
- Niu, Z., Cui, X., Pham, T., Verma, G., Lan, P.C., Shan, C., Xing, H., Forrest, K.A., Suepaul, S., Space, B., et al. (2021). A MOF-based ultra-strong acetylene nano-trap for highly efficient C₂H₂/CO₂ separation. *Angew. Chem. Int. Ed.* 60, 5283–5288. <https://doi.org/10.1002/anie.202016225>.
- Di, Z., Liu, C., Pang, J., Chen, C., Hu, F., Yuan, D., Wu, M., and Hong, M. (2021). Cage-like porous materials with simultaneous high C₂H₂ storage and excellent C₂H₂/CO₂ separation performance. *Angew. Chem. Int. Ed.* 60, 10828–10832. <https://doi.org/10.1002/anie.202101907>.
- Zeng, H., Xie, M., Huang, Y.L., Zhao, Y., Xie, X.J., Bai, J.P., Wan, M.Y., Krishna, R., Lu, W., and Li, D. (2019). Induced fit of C₂H₂ in a flexible MOF through cooperative action of open metal sites. *Angew. Chem. Int. Ed.* 58, 8515–8519. <https://doi.org/10.1002/anie.201904160>.
- Fischer, M., Hoffmann, F., and Fröba, M. (2010). New microporous materials for acetylene storage and C₂H₂/CO₂ separation: insights from molecular simulations. *ChemPhysChem* 11, 2220–2229. <https://doi.org/10.1002/cphc.201000126>.
- Xu, H., He, Y., Zhang, Z., Xiang, S., Cai, J., Cui, Y., Yang, Y., Qian, G., and Chen, B. (2013). A microporous metal-organic framework with both open metal and Lewis basic pyridyl sites for highly selective C₂H₂/CH₄ and C₂H₂/CO₂ gas separation at room temperature. *J. Mater. Chem.* 1, 77–81. <https://doi.org/10.1039/c2ta00155a>.
- Ji, Y., Ding, L., Cheng, Y., Zhou, H., Yang, S., Li, F., and Li, Y. (2017). Understanding the effect of ligands on C₂H₂ storage and C₂H₂/CH₄, C₂H₂/CO₂ separation in metal-organic frameworks with open Cu(II) sites. *J. Phys. Chem. C* 121, 24104–24113.
- Moreau, F., da Silva, I., Al Smail, N.H., Easun, T.L., Savage, M., Godfrey, H.G.W., Parker, S.F., Manuel, P., Yang, S., and Schröder, M. (2017). Unravelling exceptional acetylene and carbon dioxide adsorption within a tetra-amide functionalized metal-organic framework. *Nat. Commun.* 8, 14085. <https://doi.org/10.1038/ncomms14085>.
- Chen, S., Behera, N., Yang, C., Dong, Q., Zheng, B., Li, Y., Tang, Q., Wang, Z., Wang, Y., and Duan, J. (2020). A chemically stable nanoporous coordination polymer with fixed and free Cu²⁺ ions for boosted C₂H₂/CO₂ separation. *Nano Res.* 14, 546–553. <https://doi.org/10.1007/s12274-020-2935-1>.
- Pang, J., Jiang, F., Wu, M., Liu, C., Su, K., Lu, W., Yuan, D., and Hong, M. (2015). A porous metal-organic framework with ultrahigh acetylene uptake capacity under ambient conditions. *Nat. Commun.* 6, 7575. <https://doi.org/10.1038/ncomms8575>.
- Lin, R.-B., Li, L., Wu, H., Arman, H., Li, B., Lin, R.-G., Zhou, W., and Chen, B. (2017). Optimized separation of acetylene from carbon dioxide and ethylene in a microporous material. *Material. J. Am. Chem. Soc.* 139, 8022–8028. <https://doi.org/10.1021/jacs.7b03850>.
- Bloch, E.D., Queen, W.L., Krishna, R., Zadrozny, J.M., Brown, C.M., and Long, J.R. (2012). Hydrocarbon separations in a metal-organic framework with open iron(II) coordination sites. *Science* 335, 1606–1610. <https://doi.org/10.1126/science.1217544>.
- Zhang, J.-P., and Chen, X.-M. (2009). Optimized acetylene/carbon dioxide sorption in a dynamic porous crystal. *J. Am. Chem. Soc.* 131, 5516–5521. <https://doi.org/10.1021/ja8089872>.
- Chen, K.-J., Scott, H.S., Madden, D.G., Pham, T., Kumar, A., Bajpai, A., Lusi, M., Forrest, K.A., Space, B., Perry, J.J., and Zaworotko, M.J. (2016). Benchmark C₂H₂/CO₂ and CO₂/C₂H₂ separation by two closely related hybrid ultramicroporous materials. *Chem* 1, 753–765. <https://doi.org/10.1016/j.chempr.2016.10.009>.
- Cui, X., Chen, K., Xing, H., Yang, Q., Krishna, R., Bao, Z., Wu, H., Zhou, W., Dong, X., Han, Y., et al. (2016). Pore chemistry and size control in hybrid porous materials for acetylene capture from ethylene. *Science* 353, 141–144. <https://doi.org/10.1126/science.aaf2458>.
- Fan, W., Yuan, S., Wang, W., Feng, L., Liu, X., Zhang, X., Wang, X., Kang, Z., Dai, F., Yuan, D., et al. (2020). Optimizing multivariate metal-organic frameworks for efficient C₂H₂/CO₂ separation. *J. Am. Chem. Soc.* 142, 8728–8737. <https://doi.org/10.1021/jacs.0c00805>.
- Xiang, S., Zhou, W., Zhang, Z., Green, M.A., Liu, Y., and Chen, B. (2010). Open metal sites within isostructural metal-organic frameworks for differential recognition of acetylene and extraordinarily high acetylene storage capacity at room temperature. *Angew. Chem. Int. Ed.* 49, 4615–4618. <https://doi.org/10.1002/anie.201000094>.
- Yoon, J.W., Lee, J.S., Lee, S., Cho, K.H., Hwang, Y.K., Daturi, M., Jun, C.H., Krishna, R., and Chang, J.S. (2015). Adsorptive separation of acetylene from light hydrocarbons by mesoporous iron trimesate MIL-100(Fe). *Chem. Eur. J.* 21, 18431–18438. <https://doi.org/10.1002/chem.201502893>.
- Luo, F., Yan, C., Dang, L., Krishna, R., Zhou, W., Wu, H., Dong, X., Han, Y., Hu, T.L., O'Keefe, M., et al. (2021). A metal-organic framework with open metal sites and anthracene nucleus for highly selective C₂H₂/CH₄ and C₂H₂/CO₂ gas separation at room temperature. *Microporous Mesoporous Mater.* 303, 110000. <https://doi.org/10.1016/j.micromeso.2021.110000>.

- M., et al. (2016). UTSA-74: a MOF-74 isomer with two accessible binding sites per metal center for highly selective gas separation. *J. Am. Chem. Soc.* 138, 5678–5684. <https://doi.org/10.1021/jacs.6b02030>.
34. Yoon, J.W., Seo, Y.K., Hwang, Y.K., Chang, J.S., Leclerc, H., Wuttke, S., Bazin, P., Vimont, A., Daturi, M., Bloch, E., et al. (2010). Controlled reducibility of a metal-organic framework with coordinatively unsaturated sites for preferential gas sorption. *Angew. Chem. Int. Ed.* 49, 5949–5952. <https://doi.org/10.1002/anie.201001230>.
35. Bachman, J.E., Kapelewski, M.T., Reed, D.A., Gonzalez, M.I., and Long, J.R. (2017). $M_2(m\text{-dobdc})$ ($M = \text{Mn, Fe, Co, Ni}$) metal-organic frameworks as highly selective, high-capacity adsorbents for olefin/paraffin separations. *J. Am. Chem. Soc.* 139, 15363–15370. <https://doi.org/10.1021/jacs.7b06397>.
36. Luna-Triguero, A., Vicent-Luna, J.M., Madero-Castro, R.M., Gómez-Alvarez, P., and Calero, S. (2019). Acetylene storage and separation using metal-organic frameworks with open metal sites. *ACS Appl. Mater. Interfaces* 11, 31499–31507. <https://doi.org/10.1021/acsami.9b09010>.
37. Chen, C.X., Zheng, S.P., Wei, Z.W., Cao, C.C., Wang, H.P., Wang, D.W., Jiang, J.J., Fenske, D.T., and Su, C.Y. (2017). A robust metal-organic framework combining open metal sites and polar groups for methane purification and CO_2 /fluorocarbon capture. *Chem. Eur. J.* 23, 4060–4064. <https://doi.org/10.1002/chem.201606038>.
38. Yoon, J.H., Choi, S.B., Oh, Y.J., Seo, M.J., Jhon, Y.H., Lee, T.-B., Kim, D., Choi, S.H., and Kim, J. (2007). A porous mixed-valent iron MOF exhibiting the acs net: synthesis, characterization and sorption behavior of $\text{Fe}_3\text{O}(\text{F}_4\text{BDC})_3(\text{H}_2\text{O})_3 \cdot (\text{DMF})_{3.5}$. *Catal. Today* 120, 324–329. <https://doi.org/10.1016/j.cattod.2006.09.003>.
39. Duan, J., Jin, W., and Krishna, R. (2015). Natural gas purification using a porous coordination polymer with water and chemical stability. *Inorg. Chem.* 54, 4279–4284. <https://doi.org/10.1021/ic5030058>.
40. Ye, Y., Xian, S., Cui, H., Tan, K., Gong, L., Liang, B., Pham, T., Pandey, H., Krishna, R., Lan, P.C., et al. (2022). Metal-organic framework based hydrogen-bonding nanotrap for efficient acetylene storage and separation. *J. Am. Chem. Soc.* 144, 1681–1689. <https://doi.org/10.1021/jacs.1c10620>.
41. Li, H., Liu, C., Chen, C., Di, Z., Yuan, D., Pang, J., Wei, W., Wu, M., and Hong, M. (2021). An unprecedented pillar-cage fluorinated hybrid porous framework with highly efficient acetylene storage and separation. *Angew. Chem. Int. Ed.* 60, 7547–7552. <https://doi.org/10.1002/anie.202013988>.
42. Ye, Y., Ma, Z., Lin, R.B., Krishna, R., Zhou, W., Lin, Q., Zhang, Z., Xiang, S., and Chen, B. (2019). Pore space partition within a metal-organic framework for highly efficient $\text{C}_2\text{H}_2/\text{CO}_2$ separation. *J. Am. Chem. Soc.* 141, 4130–4136. <https://doi.org/10.1021/jacs.9b00232>.
43. Zhang, L., Jiang, K., Yang, L., Li, L., Hu, E., Yang, L., Shao, K., Xing, H., Yang, Y., Cui, Y., et al. (2021). Benchmark $\text{C}_2\text{H}_2/\text{CO}_2$ separation in an ultramicroporous metal-organic framework via copper(I)-alkynyl chemistry. *Angew. Chem. Int. Ed.* 60, 15995–16002. <https://doi.org/10.1002/anie.202102810>.
44. Pei, J., Shao, K., Wang, J.X., Wen, H.M., Yang, Y., Cui, Y., Krishna, R., Li, B., and Qian, G. (2020). A chemically stable hofmann-type metal-organic framework with sandwich-like binding sites for benchmark acetylene capture. *Adv. Mater.* 32, 1908275. <https://doi.org/10.1002/adma.201908275>.
45. Peng, Y.-L., Pham, T., Li, P., Wang, T., Chen, Y., Chen, K.-J., Forrest, K.A., Space, B., Cheng, P., Zaworotko, M.J., and Zhang, Z. (2018). Robust ultramicroporous metal-organic frameworks with Benchmark Affinity for Acetylene. *Angew. Chem. Int. Ed.* 57, 10971–10975. <https://doi.org/10.1002/anie.201806732>.
46. Xiao, D.J., Bloch, E.D., Mason, J.A., Queen, W.L., Hudson, M.R., Planas, N., Borycz, J., Dzubak, A.L., Verma, P., Lee, K., et al. (2014). Oxidation of ethane to ethanol by N_2O in a metal-organic framework with coordinatively unsaturated iron(II) sites. *Nat. Chem.* 6, 590–595. <https://doi.org/10.1038/nchem.1956>.
47. Devic, T., Horcajada, P., Serre, C., Salles, F., Maurin, G., Moulin, B., Heurtaux, D., Clet, G., Vimont, A., Grenèche, J.M., et al. (2010). Functionalization in flexible porous solids: effects on the pore opening and the Host–Guest interactions. *J. Am. Chem. Soc.* 132, 1127–1136. <https://doi.org/10.1021/ja9092715>.
48. Deacon, G.B., and Phillips, R.J. (1980). Relationships between the carbon-oxygen stretching frequencies of carboxylate complexes and the type of carboxylate coordination. *Coord. Chem. Rev.* 33, 227–250. [https://doi.org/10.1016/s0010-8545\(00\)80455-5](https://doi.org/10.1016/s0010-8545(00)80455-5).
49. Nakamoto, K. (2009). *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Sixth edition* (Wiley & Sons, Inc.).
50. Colthup, N.B., Daly, L.H., and Wiberley, S.E. (1990). *Introduction to Infrared and Raman Spectroscopy, Third edition* (Academic Press).
51. Kumar, N., Mukherjee, S., Harvey-Reid, N.C., Bezrukov, A.A., Tan, K., Martins, V., Vandichel, M., Pham, T., van Wyk, L.M., Oyekan, K., et al. (2021). Breaking the trade-off between selectivity and adsorption capacity for gas separation. *Chem* 7, 3085–3098. <https://doi.org/10.1016/j.chempr.2021.07.007>.
52. Citek, C., Oyala, P.H., and Peters, J.C. (2019). Mononuclear Fe(I) and Fe(II) acetylene adducts and their reductive protonation to terminal Fe(IV) and Fe(V) carbynes. *J. Am. Chem. Soc.* 141, 15211–15221. <https://doi.org/10.1021/jacs.9b06987>.
53. Lamberti, C., Zecchina, A., Groppo, E., and Bordiga, S. (2010). Probing the surfaces of heterogeneous catalysts by in situ IR spectroscopy. *Chem. Soc. Rev.* 39, 4951. <https://doi.org/10.1039/c0cs00117a>.
54. Tobin, R.G. (1987). Vibrational linewidths of adsorbed molecules: experimental considerations and results. *Surf. Sci.* 183, 226–250. [https://doi.org/10.1016/s0039-6028\(87\)80347-3](https://doi.org/10.1016/s0039-6028(87)80347-3).
55. Myers, A.L., and Prausnitz, J.M. (1965). Thermodynamics of mixed-gas adsorption. *AIChE J.* 11, 121–127. <https://doi.org/10.1002/aic.690110125>.
56. Li, Y.P., Wang, Y., Xue, Y.Y., Li, H.P., Zhai, Q.G., Li, S.N., Jiang, Y.C., Hu, M.C., and Bu, X. (2019). Ultramicroporous building units as a path to Bi-microporous metal-organic frameworks with high acetylene storage and separation performance. *Angew. Chem. Int. Ed.* 58, 13590–13595. <https://doi.org/10.1002/anie.201908378>.
57. Ma, J.X., Guo, J., Wang, H., Li, B., Yang, T., and Chen, B. (2017). Microporous lanthanide metal-organic framework constructed from lanthanide metalligand for selective separation of $\text{C}_2\text{H}_2/\text{CO}_2$ and $\text{C}_2\text{H}_2/\text{CH}_4$ at room temperature. *Inorg. Chem.* 56, 7145–7150. <https://doi.org/10.1021/acs.inorgchem.7b00762>.
58. Krishna, R. (2017). Screening metal-organic frameworks for mixture separations in fixed-bed adsorbents using a combined selectivity/capacity metric. *RSC Adv.* 7, 35724–35737. <https://doi.org/10.1039/c7ra07363a>.
59. Yao, Z., Zhang, Z., Liu, L., Li, Z., Zhou, W., Zhao, Y., Han, Y., Chen, B., Krishna, R., and Xiang, S. (2016). Extraordinary separation of acetylene-containing mixtures with microporous metal-organic frameworks with open O donor sites and tunable robustness through control of the helical chain secondary building units. *Chem. Eur. J.* 22, 5676–5683. <https://doi.org/10.1002/chem.201505107>.
60. Duan, X., Zhang, Q., Cai, J., Yang, Y., Cui, Y., He, Y., Wu, C., Krishna, R., Chen, B., and Qian, G. (2014). A new metal-organic framework with potential for adsorptive separation of methane from carbon dioxide, acetylene, ethylene, and ethane established by simulated breakthrough experiments. *J. Mater. Chem.* 2, 2628. <https://doi.org/10.1039/c3ta14454b>.