





ARTICLE

DOI: 10.1038/s41467-018-06174-5

OPEN

Control of coordinatively unsaturated Zr sites in ZrO₂ for efficient C–H bond activation

Yaoyuan Zhang^{1,2}, Yun Zhao ¹, Tatiana Otroshchenko¹, Henrik Lund ¹, Marga-Martina Pohl¹, Uwe Rodemerck¹, David Linke ¹, Haijun Jiao¹, Guiyuan Jiang² & Evgenii V. Kondratenko ¹

Due to the complexity of heterogeneous catalysts, identification of active sites and the ways for their experimental design are not inherently straightforward but important for tailored catalyst preparation. The present study reveals the active sites for efficient C–H bond activation in C₁–C₄ alkanes over ZrO₂ free of any metals or metal oxides usually catalysing this reaction. Quantum chemical calculations suggest that two Zr cations located at an oxygen vacancy are responsible for the homolytic C–H bond dissociation. This pathway differs from that reported for other metal oxides used for alkane activation, where metal cation and neighbouring lattice oxygen form the active site. The concentration of anion vacancies in ZrO₂ can be controlled through adjusting the crystallite size. Accordingly designed ZrO₂ shows industrially relevant activity and durability in non-oxidative propane dehydrogenation and performs superior to state-of-the-art catalysts possessing Pt, CrO_x, GaO_x or VO_x species.

¹Leibniz-Institut für Katalyse e.V. an der Universität Rostock, Albert-Einstein-Straße 29a, Rostock 18059, Germany. ²State Key Laboratory of Heavy Oil Processing, China University of Petroleum Beijing, Beijing 102249, China. These authors contributed equally: Yaoyuan Zhang, Yun Zhao. Correspondence and requests for materials should be addressed to G.J. (email: jiangy@cup.edu.cn) or to E.V.K. (email: evgenii.kondratenko@catalysis.de)

The ability of scientists to elaborate and apply fundamental principles for rational design of heterogeneous catalysts is decisive for the global sustainable development and the environment protection applications. One possible way in this direction is to identify the active sites or key atomic structures^{1,2} and, for the most part, to use this knowledge for catalyst design and preparation. For example, owing to the well-defined structure (size and/or shape) and composition of nanoparticles of metals or metal oxides, they are successfully used for the development of supported catalysts with controlled properties^{3–8}. Modifying structure of bulk metal oxides at a nanoscale level also has striking effects on their physico-chemical and catalytic properties^{9–13}. The present study elucidates at molecular level the effects of nanostructure of bare ZrO₂ on the activity and selectivity in the non-oxidative dehydrogenation of ethane, propane or iso-butane to the corresponding olefins.

In comparison with oil-based cracking technologies, which provide a major part of C₂–C₄ olefins for the chemical industry, ethane steam cracking and the dehydrogenation of propane or iso-butane are more environmentally friendly processes because they are based on natural/shale gas containing significantly less impurities than the oil-based feedstock. In addition, the dehydrogenation of propane (PDH) has been developed to close the gap between the demand and supply of propene^{14,15}. This olefin is second to ethene as an important building block of the chemical industry with an annual production of about 80 million metric tons¹⁵. Contribution of PDH technology to the overall propene production will grow because new plants are under construction¹⁶. There are, however, flaws related to the commercial catalysts with supported CrO_x or Pt species^{14,15}. According to the U.S. Occupational Safety and Health Administration¹⁷, workplace exposure to Cr(VI) may cause various health effects. A key drawback of Pt-based catalysts is their cost and deactivation triggered by sintering of Pt species. To re-disperse platinum, the catalysts are treated by ecologically harmful Cl₂ or Cl-containing compounds¹⁵. Recently, we developed eco-friendly and cost-efficient catalysts on the basis of ZrO₂, which had, however, to be promoted with metal oxides and contain supported Ru or Rh NP to show high activity in the non-oxidative dehydrogenation of propane, n-butane or iso-butane^{18–20}. Coordinatively unsaturated Zr (Zr_{cus}) and neighbouring lattice oxygen were suggested to participate in the dehydrogenation reaction. Yet, the promoter used to purposefully create Zr_{cus} sites either increased or decreased the activity hence proving the limitations of this classical approach for tailored catalyst design.

Here, we describe how nanostructuring of ZrO₂ crystallites enables the identification of the nature of active sites for efficient C–H bond activation and the control of their concentration without the usage of any dopant or supported species. Acid–base, redox and electrical conductivity properties of ZrO₂ can also be controlled through crystallite size. A structural model of the active site is established owing to our multi-disciplinary approach combining density functional theory (DFT) calculations with a number of complementary experimental methods including catalytic tests. The active site consists of two Zr cations located at an oxygen vacancy, which homolytically break the C–H bond in alkanes. The kind of this site differs from that previously suggested by some of us for doped ZrO₂-based catalysts^{18,19} and by other researchers for different metal oxides used for PDH^{21–23}, where metal cation and neighbouring lattice oxygen were assumed to form the active site. Bare ZrO₂ designed especially to maximize the concentration of the active sites shows industrially relevant performance in comparison with commercial-like catalysts containing CrO_x or Pt species and other alternative state-of-the-art catalysts.

Results

Controlling activity and selectivity of ZrO₂. The scientific background for our study was the fact that the relative ratio of coordinatively unsaturated sites on the surface of metal oxides to their regular counterparts depends on the size of crystallites²⁴. To check the influence of the nanostructure of bare ZrO₂ for C–H bond activation in lower alkanes, we synthesized about 40 ZrO₂ samples (Supplementary Table 1). Powder X-ray diffraction (XRD) analysis proved that they are mainly composed of the monoclinic phase (Supplementary Fig. 1) but differed in the average size of crystallites determined from the (111) and (111) XRD reflexes. As seen in Fig. 1a, the rate of propene formation in PDH decreased by a factor of up to 70 with an increase in the size from 7 to 45 nm. There were no such strong differences between the catalysts in terms of the rate of propene formation if non-catalytic propane dehydrogenation played a significant role. The latter process is actually not relevant under the reaction conditions applied as proven by separate tests¹⁹ without catalysts.

It is also worth mentioning that for ZrO₂ samples calcined at temperatures below 550 °C, the size of crystallites was determined after performing the PDH reaction (Supplementary Table 2). In addition to the crystallite size, long-range order of lattice oxygen and zirconium cations within at least a few nanometres in the crystal lattice of ZrO₂ should be relevant for achieving high PDH activity. This conclusion is based on the fact that XRD-amorphous ZrO₂ showed very low activity (Fig. 1a). The obtained relationship between the rate of propene formation and the size of crystallites is also valid when the rate is calculated with respect to catalyst surface area (Supplementary Fig. 2a). Thus, a simple effect of the crystallite size on the surface area and accordingly on the activity can be excluded, as the rate related to catalyst surface area increases with the area (Supplementary Fig. 2b–c).

No effect of the area would be visible if this catalyst property determined the activity exclusively. Moreover, although amorphous ZrO₂ samples (ZrO₂_24 and ZrO₂_26 in Supplementary Table 1) possess the highest surface area, they showed the lowest activity. The PDH activity of ZrO₂ is governed by the number of the active sites, which depends on the size of crystallites. A further experimental support for the importance of the latter catalyst property for PDH is the fact that apparent activation energy of propene formation depends on the size. The energy increases from about 140 to 300 kJ mol^{–1} with an increase in the size from 9 to 43 nm (Supplementary Fig. 3). This effect is related to the kind of catalytically active sites as will be demonstrated below when taking further catalytic and characterization studies as well as DFT calculations into account.

The activity–size relationship in Fig. 1a can be explained by an increase in the concentration of the catalytically active Zr_{cus} sites with a decrease in crystallite size. To validate the importance of such sites for propene formation, catalytic tests were performed with ZrO₂ treated with either H₂ or CO at 550 °C before testing in PDH at the same temperature. The idea was to create additional Zr_{cus} sites through removal of lattice oxygen from ZrO₂ in form of H₂O or CO₂. The rate of propene formation increased by a factor of 2 after 6 h on H₂ stream in comparison with the non-treated sample (Fig. 1c).

When CO was used as a reducing agent, a seven-time increase in the rate of propene formation was achieved after only 30 min treatment. Such distinctive effects of the reducing agents on the increase in the rate are related to their ability to remove lattice oxygen from ZrO₂ as proven by temperature-programmed reduction (TPR) tests with H₂ or CO (Supplementary Fig. 5). Our DFT calculations also predict that oxygen vacancies are easier formed through removal of lattice oxygen by CO than by H₂ (Supplementary Table 3). The relevance of the so-generated surface defects for propene formation is further supported by the

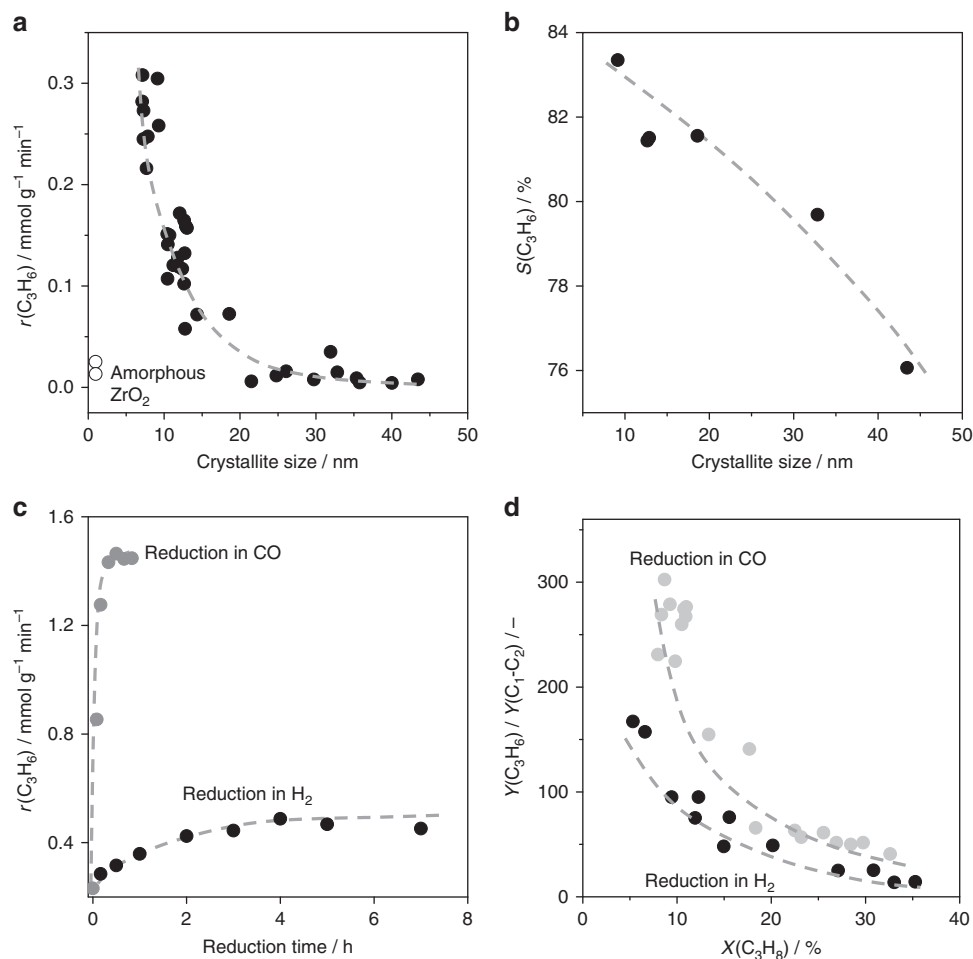


Fig. 1 Catalytic property in PDH. **a** The rate of propene formation ($r(\text{C}_3\text{H}_6)$) versus the size of crystallites of differently prepared ZrO_2 (Supplementary Table 1). **b** An integral selectivity to propene ($S(\text{C}_3\text{H}_6)$) calculated from the number of C_3H_8 moles converted and C_3H_6 moles formed within 1 h on C_3H_8 stream (Supplementary Fig. 4 and Supplementary Equation 2) over ZrO_2 with different crystallite sizes. **c** $r(\text{C}_3\text{H}_6)$ over ZrO_2 after reduction in H_2 or CO. **d** The effect of catalyst treatment by CO or H_2 on the ratio of yields of propene to cracking products ($Y(\text{C}_3\text{H}_6)/Y(\text{C}_1\text{-C}_2)$). ZrO_2 with the highest $S(\text{C}_3\text{H}_6)$ in **b** was used in **c** and **d**. All these tests were performed at 550 °C using a feed containing 40 vol% C_3H_8 in N_2

higher ratio of the yield of propene ($Y(\text{C}_3\text{H}_6)$) to that of cracking products ($Y(\text{C}_1\text{-C}_2)$) in a broad range of propane conversion obtained over the CO-treated catalyst in comparison to its H_2 -treated counterpart (Fig. 1d). This result suggests that propene and cracking products are formed on different sites.

The use of ZrO_2 composed of small crystallites is also beneficial for propene selectivity, which increased with a decrease in the crystallite size (Fig. 1b). Such positive effect holds over a broad range of propane conversion (Supplementary Fig. 6). An insight into the formation and the kind of carbon deposits, which are the main undesired reaction product, was derived from the operando UV-vis analysis upon PDH over three ZrO_2 samples with 9.1, 13.0 or 43.4 nm crystallites. The obtained UV-vis spectra expressed as the relative Kubelka–Munk function ($F(R_{\text{rel}})$) in Eq. (2) after different times on propane stream are shown in Fig. 2a–c. $F(R_{\text{rel}})$ increased across the entire range of the UV-vis spectrum with rising time on propane stream. This increase must have occurred due to the deposition of coke species because the UV-vis spectra of H_2 -treated catalysts differ strongly (Supplementary Fig. 7). Absorption bands with the maxima at about 300, 420, 600 and 750 nm can be tentatively identified in the spectra of ZrO_2 under PDH conditions. The latter two signals can be ascribed to polyaromatic graphitic species as previously suggested for PDH over a Cr-containing catalyst²⁵. Temporal changes of the

intensity of these bands under PDH conditions follow the same trend thus suggesting that they belong to the same carbon-containing species (Fig. 2d–f). The bands with the maxima in UV range (at 300 and 420 nm) should originate from low-condensed aromatic species, which differ from polyaromatic graphitic species also absorbing light above 500 nm. Different carbon-containing species are formed with different rates as seen in Fig. 2d–f showing temporal changes in the intensity of the corresponding bands with rising time of propane stream. When analysing the UV-vis spectra in Fig. 2a–c, it becomes obvious that the relative ratio of the intensity of absorption bands at 300 and 420 nm to that of the bands at higher wavelengths depends on the size of ZrO_2 crystallites. The larger the size, the higher the fraction of polyaromatic graphitic species (absorption bands above 500 nm) is expected. In addition, there is an induction period before the UV-vis spectra start to change under the PDH conditions (Supplementary Fig. 8). Such delay may indicate that some coke precursors (seeds) must be initially formed before coke formation can proceed. Importantly, the duration of this induction period increased with a decrease in the size of ZrO_2 crystallites (Supplementary Fig. 8).

On the basis of the above discussion, the effect of the size of ZrO_2 crystallites on coke formation can be explained as follows. From a mechanistic point of view, adsorbed propene molecules

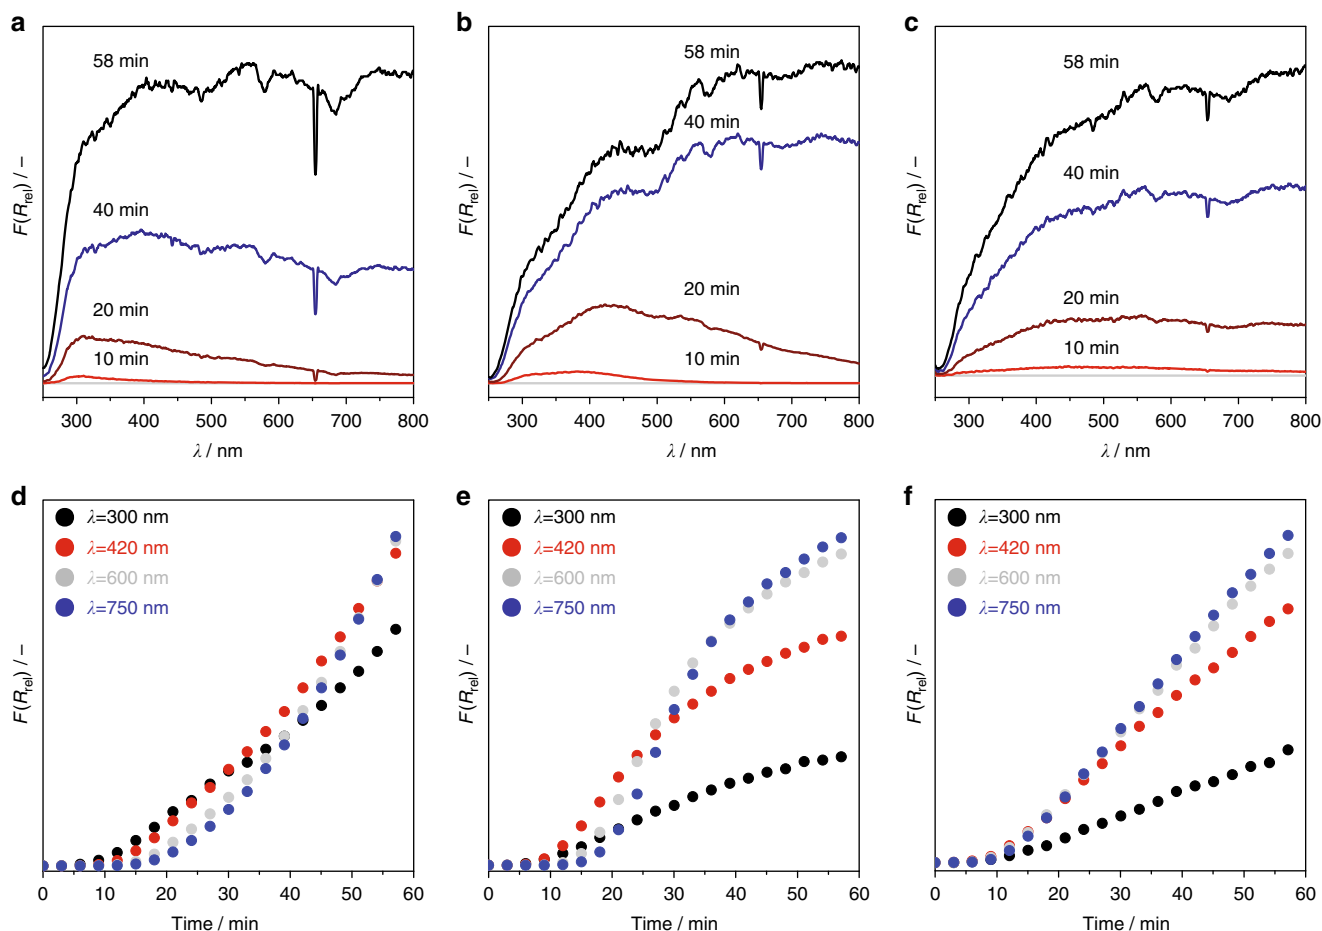


Fig. 2 Coke formation in PDH. The UV-vis spectra of ZrO_2 with **a** 9.1, **b** 13.0 or **c** 43.4 nm crystallites after different times on PDH stream. **d-f** Temporal evolution of Kubelka-Munk function at 300 (black circle), 420 (red circle), 600 (light grey circle) and 750 nm (blue circle) under PDH conditions. PDH was performed at 550 °C using a feed containing 40 vol% C_3H_8 in N_2

interact with each other to initially form small aromatic structures followed by further oligomerization and condensation to large graphitic structures¹⁵. It is reasonable to suggest that propene molecules adsorbed horizontally to catalyst surface can recombine owing to their spatial location. Such adsorption should be more favourable for Zr sites located on flat ZrO_2 surfaces in comparison to those located on corners or edges. Upon increasing the size of crystallites, the fraction of the former species will decrease and thus will result in a higher rate of carbon deposition. Exactly this trend was observed experimentally. Further experimental and theoretical studies are, however, required to clarify the size effect on coke formation.

We turn our discussion back to catalyst activity to answer two important questions. Can ZrO_2 activate C–H bond in other alkanes? Is the size–activity relationship valid for PDH only? To this end, we performed catalytic tests with iso-butane, ethane and methane with the latter possessing the highest C–H bond strength among alkanes. Due to the thermodynamic constraints, methane activation was investigated at 800 °C, while the tests with other alkanes were carried out at 550 °C, where PDH was also performed. Ethylene was the only product observed in the tests with methane. It is, however, worth mentioning that due to the low CH_4 conversion of only 0.015%, it was difficult to precisely conclude if other products were also formed. Therefore, we do not discuss product selectivity in CH_4 conversion tests. On the basis of previous studies on the oxidative coupling of methane²⁶ and non-oxidative methane conversion to ethylene²⁷, CH_3 radical is suggested to be formed through breaking the C–H bond in

CH_4 . Two such radicals recombine to C_2H_6 followed by its dehydrogenation to C_2H_4 . ZrO_2 is actually able to catalyse the latter reaction (Fig. 3a).

As seen in Fig. 3a, the feed alkanes can be ordered in terms of the rate of olefin formation as follows $CH_4 < C_2H_6 < C_3H_8 < iso-C_4H_{10}$. This activity order actually correlates with the strength of the weakest C–H bond in these alkanes. The corresponding values of the weakest C–H bond in these alkanes are 439.3, 420.5, 410.5 and 400.4 $kJ\ mol^{-1}$. Regardless of the size of ZrO_2 crystallites, the activity order did not change, while the dehydrogenation rate of C_2H_6 , C_3H_8 and $iso-C_4H_{10}$ increased with a decrease in the size (Fig. 3b). CH_4 conversion tests with ZrO_2 materials differing in the size of their crystallites were not performed because this alkane requires too high temperature, where different structural changes in ZrO_2 will occur.

Benchmarking and demonstrating catalyst durability. To demonstrate the potential of ZrO_2 for PDH from an applied viewpoint, we determined the space time yield of propene (STY (C_3H_6)) over the best performing catalyst from Fig. 1b at different temperatures and propane conversion above 25%. The selectivity to propene was above 85%. Carbon deposits were the main side product with the selectivity of about 10%. Although they are not desired, such deposits indirectly contribute to minimizing overall costs in the course of CATOFIN process through using the heat released upon their combustion during catalyst regeneration phase for the endothermic PDH reaction¹⁴. Figure 4a shows a

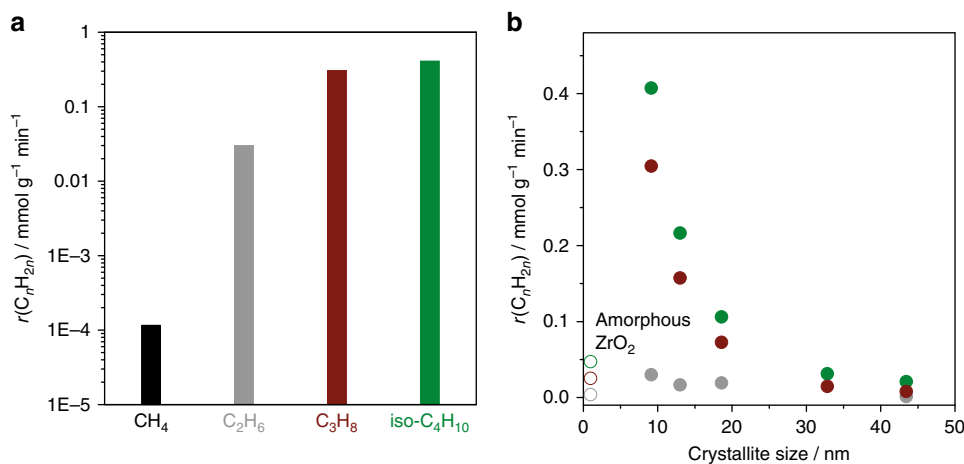


Fig. 3 Catalytic activity for C-H bond breaking. The rate of olefin formation ($r(C_nH_{2n})$), i.e. C_2H_4 , C_2H_4 , C_3H_6 and iso- C_4H_8 from CH_4 (black), C_2H_6 (grey), C_3H_8 (dark red) and iso- C_4H_{10} (green), respectively, **a** versus feed alkane over ZrO_2 with the highest $S(C_3H_6)$ in Fig. 1b or **b** versus the size of ZrO_2 crystallites. The rate values obtained over amorphous ZrO_2 in **b** are shown with open symbols. All these tests were performed using a feed containing 40 vol% alkane in N_2 at 550 °C for C_2H_6 (grey bar in **a** and grey circle in **b**), C_3H_8 (dark red bar in **a** and dark red circles in **b**), and iso- C_4H_{10} (green bar in **a** and green circle in **b**) or at 800 °C for CH_4 (black bar in **a**)

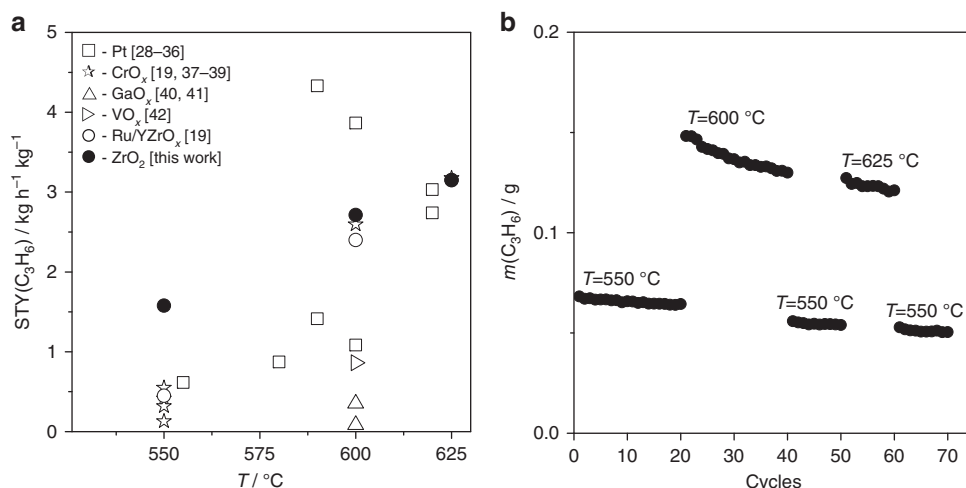


Fig. 4 Comparison with literature data and durability. **a** Space time yield of propene ($STY(C_3H_6)$) obtained over ZrO_2 and the most active catalysts from previous studies²⁸⁻⁴² (Supplementary Table 3). The data at propane conversion above 25% were considered. **b** The amount of propene ($m(C_3H_6)$) formed within each 30 min PDH cycle in a series of 70 PDH/regeneration cycles at 550, 600 and 625 °C with WHSV of 1.57, 6.28 and 9.42 h^{-1} , respectively. ZrO_2 is the catalyst with the highest $S(C_3H_6)$ in Fig. 1b

comparison of the present $STY(C_3H_6)$ values with those obtained over state-of-the-art catalysts²⁸⁻⁴² (Supplementary Table 4). All traditional catalysts with supported species of different metal oxides including chromium are less active than ZrO_2 . The latter also showed higher activity in comparison with doped ZrO_2 -based catalysts possessing supported Ru. Even in comparison with highly active but expensive Pt-based catalysts, ZrO_2 proved its outstanding PDH activity.

Further practical relevance of ZrO_2 was demonstrated over about 13 days on stream in a series of 70 PDH/regeneration cycles at 550, 600 and 625 °C. No reductive treatment was performed before PDH cycles because the catalyst can generate Zr_{cus} sites in situ through removal of lattice oxygen by propane/propene. The yield of propene within one PDH cycle initially increased and then decreased with rising time on stream at 550 °C but continuously decreased at higher temperatures (Supplementary Fig. 9). The increase is related to the formation of Zr_{cus} sites, while the decrease is due to catalyst deactivation caused by

formation of carbon deposits, which could be removed upon oxidative catalyst regeneration as proven by stable catalyst performance within first 20 cycles at 550 °C (Fig. 4b).

When performing PDH at higher temperatures, the catalyst was less durable but showed high productivity. Such change of catalyst durability is due to increasing the size of crystallites caused by temperature-induced sintering process (Supplementary Fig. 10). Owing to small changes in the size, the catalyst was still active and durable at 550 °C (last 10 cycles in Fig. 4b) after the preceding PDH tests at 600 and 625 °C. Propene selectivity was about 90% (Supplementary Fig. 11).

Role of ZrO_2 nanostructure for formation of oxygen defects. High-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) was applied to characterize crystal morphology as a function of the size of crystallites. Figure 5a-c shows representative HAADF-STEM images of two crystalline

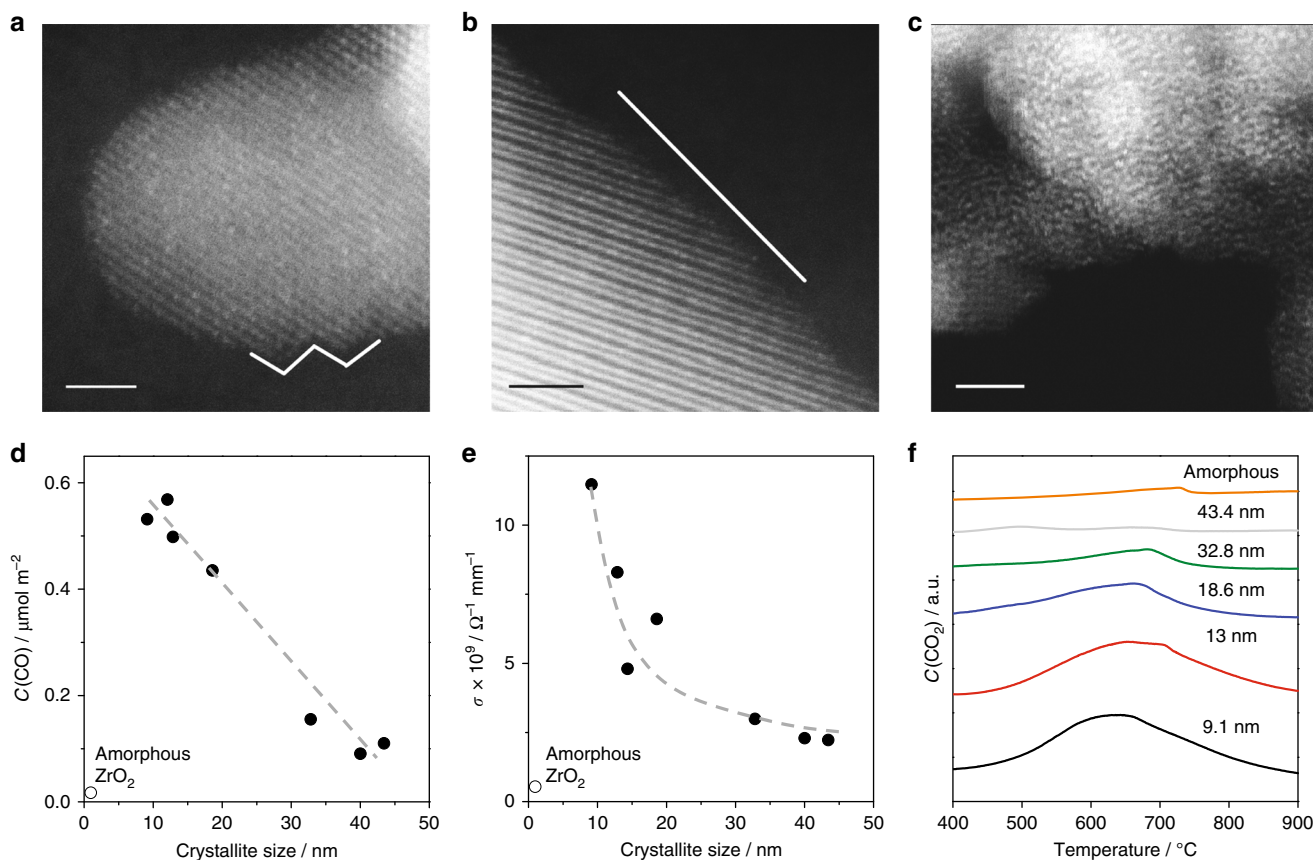


Fig. 5 Morphology, acidic, conductivity and redox properties. HAADF-STEM images of ZrO_2 with crystallites of **a** 9.1 nm, **b** 43.4 nm or **c** amorphous ZrO_2 . **d** Surface-normalized concentration of CO ($C(\text{CO})$) determined from the amount of CO desorbed in CO-TPD. **e** Electrical conductivity at 550 °C in air. **f** Concentration of CO_2 ($C(\text{CO}_2)$) detected upon CO-TPR. Scale bars: 2 nm

samples with crystallites of 9.1 or 43.4 nm and one amorphous sample. Further representative images are given in Supplementary Fig. 12. There are significant differences between the samples in the structure of the surface depending on the crystallite size. Zigzag edges were seen in some images of the sample with 9.1 nm crystallites (Fig. 5a) and indicate the presence of a large number of corner atoms. Such surface defects should be coordinatively unsaturated zirconium and/or oxygen ions. They were not observed in the sample with 43.4 nm crystallites. Nearly perfect lattice planes with no corner atoms are typical for this sample (Fig. 5b), while no lattice planes are visible for the XRD-amorphous sample (Fig. 5c).

The HAADF-STEM technique can provide only limited quantitative information about the concentration and distribution of defect sites. In this regard, we applied surface-sensitive temperature-programmed desorption (TPD) of probe molecules differing in their Lewis basicity strength. For minimizing the effect of Brønsted sites on adsorption/desorption properties of ZrO_2 ²⁰, all TPD tests were carried out with the samples treated at 550 °C to remove acidic OH groups before adsorbing probe molecules.

CO naturally adsorbing on the Zr_{cus} sites (Lewis acidic sites) desorbed between 250 and 450 °C (Supplementary Fig. 13). The surface-normalized concentration of sites for CO adsorption was established to increase with a decrease in the size of crystallites (Fig. 5d), while the temperature of maximal rate of CO desorption was not affected (Supplementary Fig. 13). The lowest amount was detected for amorphous ZrO_2 . A similar effect of the crystallite size on the concentration of adsorption sites for NH_3

and C_3H_6 was also obtained when these compounds were used as probe molecules for titrating Lewis acidic sites (Supplementary Fig. 14). Regardless of the probe molecule the rate of alkene formation from C_2H_6 , C_3H_8 and iso- C_4H_{10} rose with an increase in the concentration of the accordingly determined Lewis acidic sites (Supplementary Fig. 15). Thus, the TPD results suggest that nanostructure is vital for the stabilization/formation of surface Lewis acidic defects.

We also applied electrical conductivity tests at 550 °C for semi-quantitative analysis of the number of bulk anion vacancies, which are responsible for oxygen-ionic conductivity in ZrO_2 -based materials⁴³ and direct indicators for the presence of Zr_{cus} sites. To check the contribution of electronic conduction, we analysed the effect of oxygen partial pressure on overall conductivity. Regardless of the size of crystallites, the conductivity decreased by only a factor of less than 2, which is lower than 21 as expected for a pure p-conductor upon reducing the pressure from 20 kPa to about 10^{-4} kPa (Supplementary Table 5). This result proves that all tested ZrO_2 samples mainly possess ionic conductivity. As seen in Fig. 5e the conductivity increased with a decrease in the size of crystallites. Such relationship is due to the higher concentration of anion vacancies or/and higher diffusivity of O^{2-} in the samples with smaller crystallite size. It is worth mentioning that the conductivity of amorphous ZrO_2 was very low (Fig. 5e). Thus, an optimal size of ZrO_2 crystallites is required to achieve the highest conductivity.

The crystallite size is also decisive for the formation of anion vacancies as proven by TPR tests with CO (Fig. 5f). The smaller the size, the higher the amount of lattice oxygen was removed in

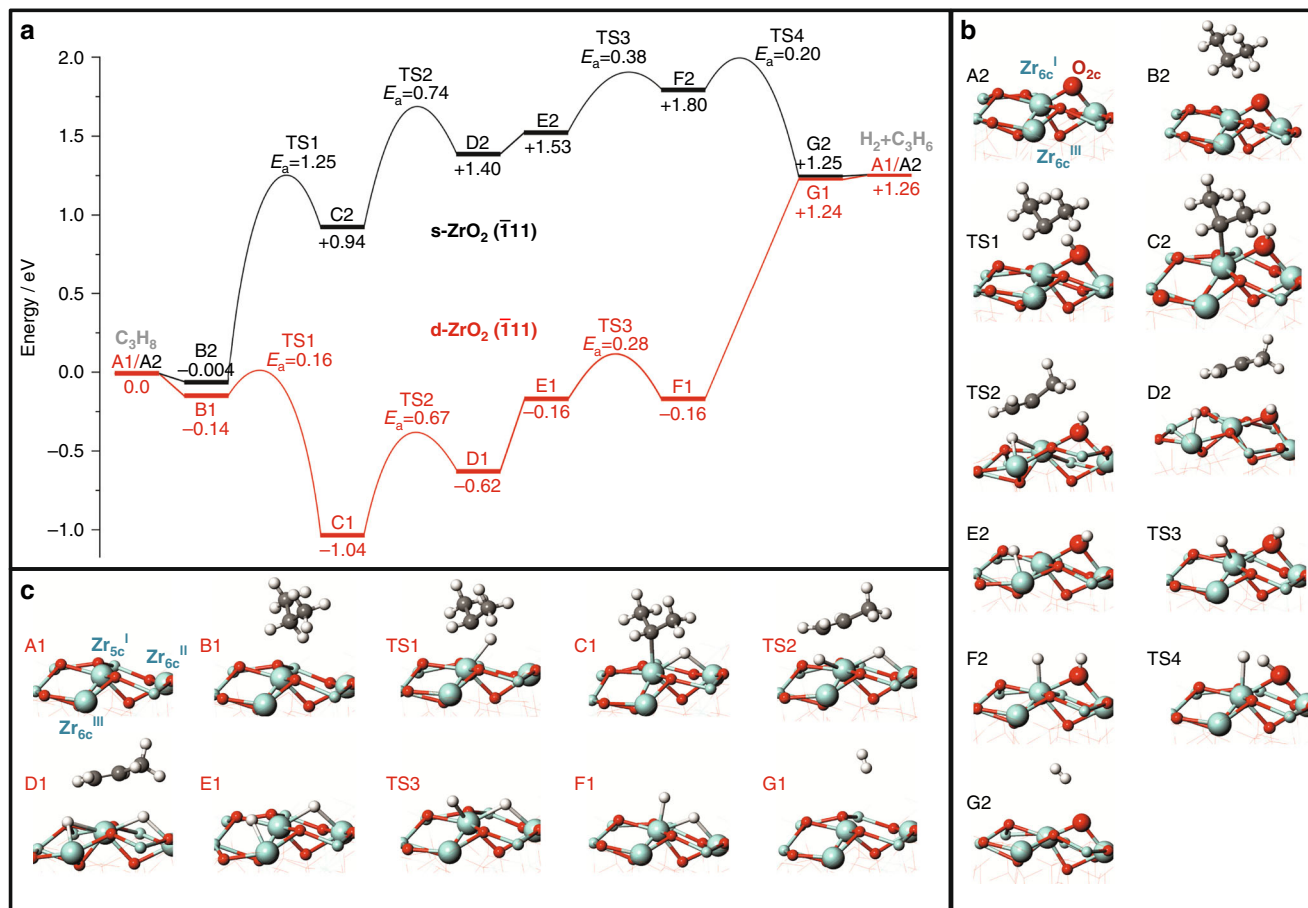


Fig. 6 Mechanism of PDH. **a** The calculated energy profiles along the pathways of propane dehydrogenation to propene and the optimized structures of intermediates and transition states (TS) on **b** s-ZrO₂($\bar{1}\bar{1}\bar{1}$) and **c** d-ZrO₂($\bar{1}\bar{1}\bar{1}$) surfaces (Cyan, grey, red and white symbols stand for Zr, C, O and H, respectively)

form of CO₂. This result is in agreement with previous DFT calculations predicting that the energy for the formation of an oxygen vacancy in ZrO₂ lowers for nanoscale particles⁴⁴. However, amorphous ZrO₂ produced very low amount of CO₂ from CO (Fig. 5f). Thus, there should be a minimal size of crystallites, below which the removal of lattice oxygen from ZrO₂ will be hindered.

Molecular level details on C₃H₈ dehydrogenation over ZrO₂.

With the purpose to derive molecular insights into the kind of the catalytically active sites for propane dehydrogenation to propene over monoclinic ZrO₂, we performed DFT calculations. The focus was put on the role of Zr_{cus} sites. As the ($\bar{1}\bar{1}\bar{1}$) facet represents the most stable surface plane of monoclinic ZrO₂^{45–47}, it was used as the basis for computing stoichiometric (s-ZrO₂($\bar{1}\bar{1}\bar{1}$)) and oxygen-defective (d-ZrO₂($\bar{1}\bar{1}\bar{1}$)) surfaces. Computational details are given in Supplementary Fig. 16, Supplementary Table 3 and Supplementary Table 6. Although the energies for activating C₃H₈ at the methylene or methyl C–H bond to yield *iso*-C₃H₇ or *n*-C₃H₇ are close (Supplementary Table 7), subtraction of a second hydrogen to yield propene is kinetically more favourable for the *iso*-C₃H₇ fragment. This result is in agreement with previous DFT calculations of PDH over other metal oxides^{21–23}. Therefore, the first step of propane activation in our calculations was cleavage of the methylene C–H bond. The full potential energy surfaces of the most preferred routes on both surfaces are shown in Fig. 6, while the Gibbs free energy profiles are given in

Supplementary Fig. 17. This figure shows that the apparent free energy barrier for propane dehydrogenation over the d-ZrO₂($\bar{1}\bar{1}\bar{1}$) facet is 1.66 eV lower than that over the s-ZrO₂($\bar{1}\bar{1}\bar{1}$) facet (2.52 vs. 4.18 eV) thus indicating that the dehydrogenation reaction is kinetically more favoured over the d-ZrO₂($\bar{1}\bar{1}\bar{1}$) facet than over the s-ZrO₂($\bar{1}\bar{1}\bar{1}$) facet.

Methylene C–H bond activation in propane: To identify the active sites and the modes of methylene C–H bond dissociation on the s-ZrO₂($\bar{1}\bar{1}\bar{1}$) surface, we computed this route on a centre consisting either of one Zr site and one O site or two O sites. For the sake of completeness, six- and seven-fold coordinated Zr cations (Zr_{6c}^I, Zr_{7c}^{II}, Zr_{6c}^{III} and Zr_{6c}^{IV}) as well as twofold and threefold coordinated oxygen anions (O_{2c}, O_{3c}^I, O_{3c}^{II}, O_{3c}^{III} and O_{3c}^{IV}) were considered (Supplementary Fig. 16). A Zr–O pair was found to be the most favourable centre to break the methylene C–H bond through a heterolytic route (Supplementary Fig. 18 and Supplementary Table 7). The Zr_{6c}^I–O_{2c} site should possess the highest reactivity because of the formation of the most stable Zr_{6c}^I–*iso*-C₃H₇ and O_{2c}–H intermediates owing to the stronger basicity of O_{2c} in comparison with O_{3c}. This step is endothermic by 0.94 eV and has an activation barrier of 1.25 eV (Fig. 6).

In contrast to s-ZrO₂($\bar{1}\bar{1}\bar{1}$), methylene C–H bond cleavage over d-ZrO₂($\bar{1}\bar{1}\bar{1}$) is a homolytic process without involving lattice oxygen. This reaction should occur on two adjacent Zr cations, *i. e.* Zr_{5c}^I and Zr_{6c}^{II} ([Zr_{5c}^I, Zr_{6c}^{II}]-O_v) or Zr_{5c}^I and Zr_{6c}^{III} ([Zr_{5c}^I, Zr_{6c}^{III}]-O_v), and is exothermic by 1.04 or 0.55 eV (Fig. 6 and Supplementary Table 8). The Zr_{5c}^I and Zr_{6c}^{II} cations are located at an anion vacancy (O_v), while Zr_{6c}^{III} is a regular surface site.

The formed *iso*-C₃H₇ fragment is bound to the Zr_{5c}^I site, while the H atom is located in a bridged position between Zr_{5c}^I and Zr_{6c}^{II} or between Zr_{5c}^I and Zr_{6c}^{III}. On the basis of the activation barrier (0.16 vs. 0.73 eV) for breaking the methylene C–H bond (Supplementary Fig. 19), the [Zr_{5c}^I, Zr_{6c}^{II}]-O_v site should be more reactive than the [Zr_{5c}^I, Zr_{6c}^{III}]-O_v site. With respect to the Zr_{6c}^I-O_{2c} site on the *s*-ZrO₂($\bar{1}11$) surface, the activation barrier for this reaction pathway decreases by 1.09 eV in the presence of oxygen vacancy (Fig. 6) thus strongly facilitating propane activation.

To check the importance of oxygen defects for activation of methane, which is the most inert alkane, we computed breaking C–H bond over the *s*-ZrO₂($\bar{1}11$) and *d*-ZrO₂($\bar{1}11$) surfaces. Similarly to propane activation, Zr_{6c}^I-O_{2c} and [Zr_{5c}^I, Zr_{6c}^{II}]-O_v should be the corresponding active sites. The presence of oxygen defect was established to be essential for breaking the C–H bond in CH₄, too. The activation barrier on the Zr_{6c}^I-O_{2c} site is 1.14 eV but is only 0.10 eV on the [Zr_{5c}^I, Zr_{6c}^{II}]-O_v site. Moreover, CH₄ activation on the latter centre is exothermic by 1.06 eV.

C₃H₆ and H₂ formation: After having identified the first step of propane activation over *s*-ZrO₂($\bar{1}11$), we examined transformation routes of the Zr_{6c}^I-*iso*-C₃H₇ and H-O_{2c} intermediates. The most thermodynamically and kinetically preferred way for Zr_{6c}^I-*iso*-C₃H₇ conversion is the cleavage of the methyl C–H bond at the Zr_{6c}^{III} site (Supplementary Fig. 20). It is an endothermic process (0.46 eV) and has an activation barrier of 0.74 eV (C2 to D2 in Fig. 6), which is 0.51 eV lower than that for the activation of the first methylene C–H bond in propane. The so-formed propene adsorbs weakly (0.13 eV) at the Zr_{6c}^I site, while the co-generated H fragment is bound to the neighbouring Zr_{6c}^{III} site (Fig. 6).

When one H atom is subtracted from the methyl group of Zr_{5c}^I-*iso*-C₃H₇ stabilized on the *d*-ZrO₂($\bar{1}11$) surface (Fig. 6 and Supplementary Fig. 21), weakly adsorbed propene (0.46 eV) is formed (TS2, Fig. 6). The remaining H atom is bound to the Zr_{5c}^I and Zr_{6c}^{III} cations. This process is endothermic by 0.42 eV and has an activation barrier of 0.67 eV, which is slightly lower than that (0.74 eV) required for the activation of Zr_{6c}^I-*iso*-C₃H₇ over the stoichiometric surface. In addition to the mechanism and the kinetics of propene formation, the presence of anion vacancies also affects H₂ formation (Fig. 6). This process on the *s*-ZrO₂($\bar{1}11$) surface has an effective activation barrier of 0.47 eV and is exothermic by 0.28 eV, while the formation of H₂ on the *d*-ZrO₂($\bar{1}11$) surface is endothermic by 1.40 eV (H₂ dissociation is barrierless).

Discussion

The work presented here explains at molecular level the importance of oxygen defects on the surface of ZrO₂ for efficient C–H bond activation in C₁–C₄ alkanes. Owing to the presence of such defects, this typically non-reducible metal oxide showed unexpectedly high activity in the non-oxidative propane dehydrogenation to propene and outperformed the state-of-the-art catalysts possessing supported metal oxides or platinum. Its unique performance is related to the presence of surface coordinatively unsaturated Zr cations (Zr_{cus}) located at anion vacancies in the lattice of ZrO₂. Our DFT calculations predict that Zr_{cus} sites open an alternative pathway of propene and hydrogen formation with a lower activation barrier in comparison with non-defect ZrO₂. Two Zr_{cus} sites directly participate in homolytic C–H bond activation, while lattice oxygen and zirconium cation are required for this process on the stoichiometric surface of ZrO₂. Although the concentration of Zr_{cus} can be adjusted in a controlled manner through the size of ZrO₂ crystallites, further

improvements are expected when the coordination number of zirconium cations, their location on certain facets and/or the shape of crystallites can also be tuned. Our approach presented herein can be extended to other bulk oxides of non-reducible metals and offers the opportunity for tailoring their acid–base and redox properties as well as electrical conductivity for specific applications.

Methods

Catalyst preparation. ZrO₂ samples were prepared by hydrothermal, precipitation, sol-gel, hard-template methods or simple decomposition of different zirconium salts. The used chemicals and selected physico-chemical properties of the synthesized materials are given in Supplementary Table 1. Further preparation details are provided in Supplementary Note 1.

Catalyst characterization. XRD powder patterns were recorded on a Panalytical X'Pert diffractometer equipped with a Xcelerator detector, automatic divergence slits and Cu tube (ka1/a2 radiation, 40 kV, 40 mA, $\lambda = 0.015406$ nm, 0.0154443 nm). Cu beta-radiation was excluded by using nickel filter foil. The measurements were performed in 0.0167° steps and 25 s of data collecting time per step. Peak positions and profile were fitted with Pseudo-Voigt function using the HighScore Plus software package (Panalytical). The PDF-2 database of the International Centre of Diffraction Data (ICDD) was used for phase identification. The integral breadth method using the Scherrer equation under the assumption of spherically shaped crystallites was applied for calculating crystallite size from the ($\bar{1}11$) and (111) reflection peak and the average values are reported. The K parameter was set to 1.0747. The adjustment of the used diffractometer is weekly checked according to the Si (111) reflection peak at 28.433°. The deviation of the peak position is within the standard deviation (0.004°). We have also measured XRD of five randomly taken probes of ZrO₂ with an estimated crystallite size of 9.1 nm, which is one of the lowest values. The size of crystallites was determined with an error of 0.02 nm. Thus, the error in determining the size of crystallites is below 1%.

Transmission electron microscopy measurements were carried out at 200 kV with an aberration-corrected JEM-ARM200F (JEOL, Corrector: CEOS). The aberration-corrected STEM imaging (High-Angle Annular Dark Field) was performed with a spot size of approximately 0.1 nm, a convergence angle of 30–36° and collection semi-angle of 90–170 mrad.

Acid–base, redox and electrical properties of selected samples were determined from temperature-programmed desorption tests using CO, NH₃ or C₃H₆ as probe molecules, temperature-programmed reduction tests with H₂ or CO and electrical conductivity measurements respectively. Technical details of these tests are given in Supplementary Note 2.

In situ UV-vis tests were performed at 550 °C in an in-house developed set-up equipped with an AVASPEC fibre optical spectrometer (Avantes), a DH-2000 deuterium-halogen light source and a CCD array detector. A high-temperature reflection UV-vis probe consisting of six radiating optical fibres and one reading fibre was threaded through the furnace to face quartz reactor walls at the position where catalysts were held⁴⁸. A feed containing 40 vol% C₃H₈ in N₂ was used in these tests. Initial propane conversion was about 10%.

For analysing carbon deposition during PDH, we defined relative reflectance (R_{rel}) as given in Eq. (1) as the ratio of the reflectance of the catalysts with coke deposits (R_{DH}) to the fully oxidized ones (R_{O_2}). From this reflectance, we calculated the relative Kubelka–Munk function $F(R_{rel})$ according to Eq. (2).

$$R_{rel} = \frac{R_{DH}}{R_{O_2}} \quad (1)$$

$$F(R_{rel}) = \frac{(1 - R_{rel})^2}{2 \times R_{rel}} \quad (2)$$

Catalytic tests. Catalytic tests with C₂H₆, C₃H₈ and *iso*-C₄H₁₀ were performed at 1 bar between 550 and 625 °C using an in-house developed set-up consisting of 15 continuous-flow fixed-bed quartz tubular (length and inner diameter are 465 and 4 mm, respectively) reactors operating in parallel. Tests with CH₄ were carried out at 800 °C in an in-house developed set-up consisting of six continuous-flow fixed-bed quartz tubular (length and inner diameter are 330 and 4 mm respectively) reactors operating in parallel. Depending on specific purposes, catalytic tests were performed with oxidized (treated in air at the reaction temperature) or reduced (treated in either CO/N₂ = 57/43 or H₂/N₂ = 57/43 at the reaction temperature) catalysts. Feeds containing 40 vol% C₂H₆, 40 vol% C₃H₈, 40 vol% *iso*-C₄H₁₀ or 40 vol% CH₄ in N₂ were used. The feed components and the reaction products were analysed by an on-line gas chromatograph (Agilent 6890) equipped with PLOT/Q (for CO₂), AL/S (for hydrocarbons) and Molsieve 5 (for H₂, O₂, N₂ and CO) columns as well as flame ionization and thermal conductivity detectors.

Further details about catalytic tests as well as formulae for calculating various catalyst characteristics are provided in Supplementary Note 3.

DFT calculations. Spin-polarized and periodic density functional theory (DFT) calculations were carried out by using the Vienna ab initio simulation package (VASP)^{49,50}. Exchange and correlation were treated within the Perdew–Burke–Ernzerhof generalized gradient approximation (GGA-PBE)⁵¹. To obtain accurate energies with errors of less than 1 meV per atom, a cut-off energy of 400 eV was used. Geometry optimization was converged until forces acting on atoms were lower than 0.02 eV/Å, whereas the energy threshold defining self-consistency of the electron density was set to 10^{-4} eV. The climbing image nudged elastic band (CI-NEB) method with eight images was applied for finding transition states and minimum energy paths of all reactions⁵². The final transition state structures were refined by using the quasi-Newton algorithm until the Hellman–Feynman forces on each ion were lower than 0.02 eV/Å. The normal mode frequency analysis was performed to validate the optimized transition states and each authentic transition state has only one imaginary frequency along the reaction coordinates. The resulted zero-point vibrational energies (ZPE) from the frequency analysis are included in our energetic comparison and discussion. For the optimization of the bulk structure, the lattice parameters of the monoclinic ZrO_2 ($m\text{-ZrO}_2$) phase were determined by minimizing the total energy of the unit cell by using a conjugated gradient algorithm to relax the ions. A $7 \times 7 \times 7$ Monkhorst–Pack k point grid was used for sampling the Brillouin zone⁵³. Additional details are provided in Supplementary Methods. In addition, we also tested the corrections of Hubbard term (PBE + U) and dispersion (DFT + D3). These new data are now presented in Supplementary Fig. 22 and Supplementary Fig. 23.

Data availability

The authors declare that the data supporting the findings of this study are available within the paper and its supplementary information. Further information is also available from the corresponding authors upon reasonable request.

Received: 21 March 2018 Accepted: 23 August 2018

Published online: 18 September 2018

References

- Nørskov, J. K., Bligaard, T., Rossmeisl, J. & Christensen, C. H. Towards the computational design of solid catalysts. *Nat. Chem.* **1**, 37 (2009).
- Buurmans, I. L. C. & Weckhuysen, B. M. Heterogeneities of individual catalyst particles in space and time as monitored by spectroscopy. *Nat. Chem.* **4**, 873 (2012).
- Zaera, F. Nanostructured materials for applications in heterogeneous catalysis. *Chem. Soc. Rev.* **42**, 2746–2762 (2013).
- Munnik, P., de Jongh, P. E. & de Jong, K. P. Recent developments in the synthesis of supported catalysts. *Chem. Rev.* **115**, 6687–6718 (2015).
- Zečević, J., Vanbutsele, G., de Jong, K. P. & Martens, J. A. Nanoscale intimacy in bifunctional catalysts for selective conversion of hydrocarbons. *Nature* **528**, 245–248 (2015).
- Jagadeesh, R. V. et al. MOF-derived cobalt nanoparticles catalyze a general synthesis of amines. *Science* **358**, 326–332 (2017).
- Shan, J. et al. Mild oxidation of methane to methanol or acetic acid on supported isolated rhodium catalysts. *Nature* **551**, 605–608 (2017).
- Marcinkowski, M. D. et al. Pt/Cu single-atom alloys as coke-resistant catalysts for efficient C–H activation. *Nat. Chem.* **10**, 325–332 (2018).
- Wu, H. B., Chen, J. S., Hng, H. H. & Lou, X. W. Nanostructured metal oxide-based materials as advanced anodes for lithium-ion batteries. *Nanoscale* **4**, 2526–2542 (2012).
- Mahato, R. N. et al. Ultrahigh magnetoresistance at room temperature in molecular wires. *Science* **341**, 257–260 (2013).
- Zhang, Z. et al. Ultrathin inorganic molecular nanowire based on polyoxometalates. *Nat. Commun.* **6**, 1–9 (2015).
- Zhang, Z. et al. Acidic ultrafine tungsten oxide molecular wires for cellulosic biomass conversion. *Angew. Chem. Int. Ed.* **55**, 10234–10238 (2016).
- Trovarelli, A. & Llorca, J. Ceria catalysts at nanoscale: how do crystal shapes shape catalysis? *ACS Catal.* **7**, 4716–4735 (2017).
- Vora, B. V. Development of dehydrogenation catalysts and processes. *Top. Catal.* **55**, 1297–1308 (2012).
- Sattler, J. J. H. B., Ruiz-Martinez, J., Santillan-Jimenez, E. & Weckhuysen, B. M. Catalytic dehydrogenation of light alkanes on metals and metal oxides. *Chem. Rev.* **114**, 10613–10653 (2014).
- Boswell, C. On-purpose technologies ready to fill propylene gap. <https://www.ics.com/resources/news/2012/04/16/9549968/on-purpose-technologies-ready-to-fill-propylene-gap/> (2012).
- Occupational Safety and Health Administration. Hexavalent chromium. <https://www.osha.gov/SLTC/hexavalentchromium/index.html> (accessed 2 Sept 2018).
- Otroshchenko, T. et al. ZrO_2 -based alternatives to conventional propane dehydrogenation catalysts: active sites, design and performance. *Angew. Chem. Int. Ed.* **54**, 15880–15883 (2015).
- Otroshchenko, T. et al. ZrO_2 -based unconventional catalysts for non-oxidative propane dehydrogenation: factors determining catalytic activity. *J. Catal.* **348**, 282–290 (2017).
- Otroshchenko, T. P. et al. Non-oxidative dehydrogenation of propane, n-butane, and isobutane over bulk ZrO_2 -based catalysts: effect of dopant on the active site and pathways of product formation. *Catal. Sci. Tech.* **7**, 4499–4510 (2017).
- Liu, Y., Li, Z.-H., Lu, J. & Fan, K.-N. Periodic density functional theory study of propane dehydrogenation over perfect $\text{Ga}_2\text{O}_3(100)$ surface. *J. Phys. Chem. C* **112**, 20382–20392 (2008).
- Fu, H. et al. Periodic density functional theory study of propane oxidative dehydrogenation over $\text{V}_2\text{O}_5(001)$ surface. *J. Am. Chem. Soc.* **128**, 11114–11123 (2006).
- Rozanska, X., Fortrie, R. & Sauer, J. Size-dependent catalytic activity of supported vanadium oxide species: oxidative dehydrogenation of propane. *J. Am. Chem. Soc.* **136**, 7751–7761 (2014).
- Rodriguez, J. A. & Fernández-García, M. *Synthesis, Properties, and Applications of Oxide Nanomaterials*. (John Wiley & Sons, Hoboken, NJ, 2007).
- Nijhuis, T. A., Tinnemans, S. J., Visser, T. & Weckhuysen, B. M. Towards real-time spectroscopic process control for the dehydrogenation of propane over supported chromium oxide catalysts. *Chem. Eng. Sci.* **59**, 5487–5489 (2004).
- Kondratenko, E. V. & Baerns, M. *Handbook of Heterogeneous Catalysis* 2nd Edn, 3010–3023 (Wiley-VCH, Weinheim, 2008).
- Guo, X. et al. Direct, nonoxidative conversion of methane to ethylene, aromatics, and hydrogen. *Science* **344**, 616–619 (2014).
- Sattler, J. J. H. B. et al. Platinum-promoted $\gamma\text{-Al}_2\text{O}_3$ as highly active, selective, and stable catalyst for the dehydrogenation of propane. *Angew. Chem. Int. Ed.* **53**, 9251–9256 (2014).
- De Cola, P. L., Gläser, R. & Weitkamp, J. Non-oxidative propane dehydrogenation over Pt–Zn-containing zeolites. *Appl. Catal. A* **306**, 85–97 (2006).
- Xiong, H. et al. Thermally stable and regenerable platinum–tin clusters for propane dehydrogenation prepared by atom trapping on ceria. *Angew. Chem. Int. Ed.* **56**, 8986–8991 (2017).
- Li, J. et al. Size effect of TS-1 supports on the catalytic performance of PtSn/TS-1 catalysts for propane dehydrogenation. *J. Catal.* **352**, 361–370 (2017).
- Pham, H. N., Sattler, J. J. H. B., Weckhuysen, B. M. & Datye, A. K. Role of Sn in the regeneration of Pt/ $\gamma\text{-Al}_2\text{O}_3$ light alkane dehydrogenation catalysts. *ACS Catal.* **6**, 2257–2264 (2016).
- Im, J. & Choi, M. Physicochemical stabilization of Pt against sintering for a dehydrogenation catalyst with high activity, selectivity, and durability. *ACS Catal.* **6**, 2819–2826 (2016).
- Shi, L. et al. Al_2O_3 nanosheets rich in pentacoordinate Al^{3+} ions stabilize Pt–Sn clusters for propane dehydrogenation. *Angew. Chem., Int. Ed.* **54**, 13994–13998 (2015).
- Zhu, H. et al. Sn surface-enriched Pt–Sn bimetallic nanoparticles as a selective and stable catalyst for propane dehydrogenation. *J. Catal.* **320**, 52–62 (2014).
- Jiang, F. et al. Propane dehydrogenation over Pt/TiO₂–Al₂O₃ catalysts. *ACS Catal.* **5**, 438–447 (2015).
- Alcántara-Rodríguez, M., Rodríguez-Castellón, E. & Jiménez-López, A. Propane dehydrogenation on mixed Ga/Cr oxide pillared zirconium phosphate materials. *Langmuir* **15**, 1115–1120 (1999).
- Zhang, X., Yue, Y. & Gao, Z. Chromium oxide supported on mesoporous SBA-15 as propane dehydrogenation and oxidative dehydrogenation catalysts. *Catal. Lett.* **83**, 19–25 (2002).
- Michorczyk, P., Pietrzyk, P. & Ogonowski, J. Preparation and characterization of SBA-1–supported chromium oxide catalysts for CO₂ assisted dehydrogenation of propane. *Micro. Mesopor. Mater.* **161**, 56–66 (2012).
- Michorczyk, P. & Ogonowski, J. Dehydrogenation of propane to propene over gallium oxide in the presence of CO₂. *Appl. Catal. A* **251**, 425–433 (2003).
- Xu, B. J. et al. Support effect in dehydrogenation of propane in the presence of CO₂ over supported gallium oxide catalysts. *J. Catal.* **239**, 470–477 (2006).
- Liu, G. et al. Nature of the active sites of VO_x/Al₂O₃ catalysts for propane dehydrogenation. *ACS Catal.* **6**, 5207–5214 (2016).
- Etsell, T. H. & Flengas, S. N. Electrical properties of solid oxide electrolytes. *Chem. Rev.* **70**, 339–376 (1970).
- Ruiz Puigdollers, A., Schlexer, P., Tosoni, S. & Pacchioni, G. Increasing oxide reducibility: the role of metal/oxide interfaces in the formation of oxygen vacancies. *ACS Catal.* **7**, 6493–6513 (2017).
- Christensen, A. & Carter, E. A. First-principles study of the surfaces of zirconia. *Phys. Rev. B* **58**, 8050–8064 (1998).

46. Piskorz, W. et al. Periodic DFT and atomistic thermodynamic modeling of the surface hydration equilibria and morphology of monoclinic ZrO_2 nanocrystals. *J. Phys. Chem. C* **115**, 24274–24286 (2011).
47. Kouva, S., Honkal, K., Lefferts, L. & Kanervo, J. Review: monoclinic zirconia, its surface sites and their interaction with carbon monoxide. *Catal. Sci. Tech.* **5**, 3473–3490 (2015).
48. Kondratenko, E. V. Using time-resolved methods to monitor and understand catalytic oxidation reactions. *Catal. Today* **157**, 16–23 (2010).
49. Kresse, G. & Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **6**, 15–50 (1996).
50. Kresse, G. & Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186 (1996).
51. Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).
52. Henkelman, G., Uberuaga, B. P. & Jónsson, H. A climbing image nudged elastic band method for finding saddle points and minimum energy paths. *J. Chem. Phys.* **113**, 9901–9904 (2000).
53. Monkhorst, H. J. & Pack, J. D. Special points for Brillouin-zone integrations. *Phys. Rev. B* **13**, 5188–5192 (1976).

Acknowledgements

Financial support by Deutsche Forschungsgemeinschaft (KO 2261/8-1, JI 210/1-1), the National Natural Science Foundation of China (Grants 91645108, U1162117), Science Foundation of China University of Petroleum, Beijing (C201604) and the State of Mecklenburg-Vorpommern are gratefully acknowledged. Ya.Z. acknowledges support from the China Scholarship Council.

Author contributions

E.V.K. conceived and coordinated all stages of this research. All authors participated in planning, discussing and interpreting the experimental and theoretical data as well as in

writing and revising the manuscript. Various catalytic and characterization experiments as well as DFT calculations were performed by Ya.Z., Yu.Z., T.O., H.L., M.-M.P. and H.J., who also evaluated the data obtained.

Additional information

Supplementary Information accompanies this paper at <https://doi.org/10.1038/s41467-018-06174-5>.

Competing interests: The authors declare no competing interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2018