

Characterization of polyether-poly(methyl methacrylate)-lithium perchlorate blend electrolytes

Paula C. Barbosa¹, Luísa C. Rodrigues¹, M. Manuela Silva^{1*}, Michael J. Smith¹, Prudência B. Valente², A. Gonçalves², E. Fortunato²

1. *Centro de Química, Universidade do Minho, Gualtar, 4710-057 Braga, Portugal*

2. *Centro de Investigação de Materiais, Universidade Nova de Lisboa, Campus da FCT, 2829-516 Caparica, Portugal*
*nini@quimica.uminho.pt

Abstract

Solid polymer electrolytes (SPEs) systems based on interpenetrating blends of poly(ethylene oxide-co-propylene oxide) and poly(methyl methacrylate) host matrices, with lithium perchlorate as guest salt, were prepared. These electrolytes were presented as free-standing films, and their thermal and electrochemical properties were characterized by conductivity and electrochemical stability measurements.

The properties of the interpenetrating blends of poly(ethylene oxide-co-propylene oxide) and poly(methyl methacrylate) host matrices as the electrolyte component of a solid-state electrochromic device are reported and the results obtained suggest that this electrolyte provides an encouraging performance in this application. The most conducting electrolyte composition of this SPE system is the formulation designated as SPE2-0PC ($5.01 \times 10^{-4} \text{ S cm}^{-1}$ at about 57°C). The lowest decomposition temperature was registered with the SPE6-15PC composition (233°C). The average transmittance in the visible region of the spectrum was above 41% for all the samples analyzed. After coloration the device assembled with 71 wt% PC presented an average transmittance of 15.71% and an optical density at 550nm of 0.61.

Keywords: Polymer Electrolytes, Electrochromic devices, Tungsten Oxide

INTRODUCTION

Poly(ethylene oxide) complexed with inorganic salts were first reported as a novel sub-class of solid electrolytes by Fenton, Parker and Wright.^[1] Since 1973 these materials have been the object of intense study as solid electrolyte components that may form the basis of future all-solid-state lithium batteries.^[2, 3] There are however significant problems to overcome. In practical devices, the ionic conduction of the electrolyte component must be raised from values of $10^{-7} - 10^{-6} \text{ S cm}^{-1}$ typical of first-generation SPEs, to values approaching $10^{-3} \text{ S cm}^{-1}$ at room temperature.^[3] While this value is accessible to “gel” type polymer electrolytes^[3], this conductivity performance has not been achieved by “dry” polymer electrolyte systems like PEO. Unlike dry polymer electrolytes, gel polymer electrolyte formulations contain components such as propylene carbonate or ethylene carbonate that are included as additives to enhance ionic conduction. While these liquids in the gel systems certainly increase ion conduction, they also decrease the mechanical stability of the polymer and contribute to the formation of an unstable passivation layer at the lithium/polymer electrolyte interface.^[3]

Various strategies for improving ionic conduction in polymer electrolytes have been reported, including using polysiloxane and polyphosphazene host matrices with backbone structures and side chains incorporating oxyethylene oligomers.^[4-7] New generation electrolytes have been developed incorporating suitable fillers, novel guest compounds or plasticizing components.^[8-15]

Electrochromic windows represent one of the most promising applications of SPEs^[16-18] where these materials simultaneously function as the ion-conducting layer, sealing surface and adhesive. In this class of electrochemical device the demands placed

on the conductivity of the electrolyte are not so high because instantaneous color change is not essential in normal device operation.

In this study we report the preparation of solid polymer electrolytes and characterization by measurements of ionic conductivity, differential scanning calorimetry, thermogravimetry and scanning electron microscopy of several different SPEs based on interpenetrating p(EO-PO)/pMMA blends doped with lithium perchlorate and produced by co-deposition from THF. The performance of these SPEs was tested on small-scale solid-state electrochromic windows.

EXPERIMENTAL

SPE films preparation

Polymer electrolytes were prepared by combining appropriate amounts of poly(ethylene oxide-co-propylene oxide), p(EO-PO) (supplied by Zeon Corporation Inc.) and poly(methyl methacrylate), pMMA (120,000 g mol⁻¹, Aldrich) with a propylene carbonate (PC) (Aldrich) plasticizer and known quantities of LiClO₄ as guest salt. All electrolytes were prepared by solvent casting from THF (Aldrich, anhydrous 99.9%). Homogeneous solutions of p(EO-PO), pMMA, PC and lithium perchlorate were prepared by stirring known masses of electrolyte components in THF for a period of at least 48 hours within a dry argon-filled preparative glovebox. The resulting homogeneous viscous solutions were decanted into rings seated on glass plates and the solvent was removed slowly in an isolated chamber within the preparative glovebox. The atmosphere of this chamber was recirculated through a column of molecular sieves to effect a slow evaporation of the casting solvent and form free-standing films. These electrolyte films were subjected to a final drying procedure in which the temperature was raised from 30°C to 60°C over a period of 3 days. During this period the tube oven

was periodically evacuated and purged with dry argon. Solid polymer electrolyte compositions were prepared with the compositions indicated in Table 1.

Transparent conductive oxide (TCO)

Indium doped zinc oxide films (IZO) were deposited on glass substrates by rf (13.56 MHz) magnetron sputtering using a ceramic oxide target $\text{In}_2\text{O}_3:\text{ZnO}$ (92:8 wt%; 5 cm diameter, Super Conductor Materials, Suffern, NY, USA) with a purity of 99.99%. Sputtering was carried out at room temperature, with an argon flow of 20 sccm and an oxygen flow of 0.4 sccm. During sputtering the deposition pressure (argon and oxygen) was held constant at a value of 0.15 Pa. The distance between the substrate and the target was 10 cm and the rf power was maintained at 100 W.

Electrochromic Material

Tungsten oxide films with thickness of about 300 nm were deposited on transparent conductive oxide coated glass substrates by rf magnetron sputtering using a WO_3 ceramic oxide target from Super Conductor Materials with a purity of 99.99%. Sputtering was carried out at room temperature, under an argon and oxygen atmosphere with a constant deposition pressure of 2.6 Pa. The distance between the substrate and the target was 10 cm and the rf power was maintained at 200 W.

Electrochromic device structure

Solid-state electrochromic devices were constructed using a four layer sandwich structure with the following configuration: glass/IZO/ WO_3 /polymer electrolyte/IZO/glass. The layers of active material were deposited by rf magnetron sputtering using appropriate targets. Device assembly with electrolytes was carried out by direct application of a small volume of the electrolyte, (10%) p(EO-PO) / (39%)

pMMA / (40%) PC / (11%) LiClO₄, to the surface of a glass plate onto which a IZO/WO₃ coating had been previously deposited. Typical thicknesses of these layers were 170 nm for IZO and 400 nm for WO₃. A second glass plate with a IZO coating was placed on top of the electrolyte gel sample and the two plates were pressed together to spread the electrolyte in a thin film between the electrochromic surfaces. In this manner a surface with an area of approximately 2 cm² was formed. The entire assembly procedure described was carried out under atmospheric conditions.

Measurements

2.4.1. DSC and TGA measurements

Polymer electrolyte sections were removed from cast films and subjected to thermal analysis under a flowing argon atmosphere between 25 and 350 °C at a heating rate of 5 °C min⁻¹ using a Mettler DSC 821e instrument. All samples were presented for analysis in 40 µL aluminium cans with perforated lids to permit the release and removal of the decomposition products. Samples for thermogravimetric studies were prepared in a similar manner, transferred to open platinum crucibles and analyzed using a Rheometric Scientific TG 1000 thermobalance operating under a flowing argon atmosphere. A heating rate of 10 °C min⁻¹ was used to analyze all the electrolyte samples.

2.4.2. Impedance spectroscopy

Total ionic conductivities of electrolyte samples were determined using a constant volume support equipped with gold blocking electrodes and located within a Buchi TO 50 oven. The sample temperature was evaluated by means of a type K thermocouple placed close to the electrolyte film and impedance measurements were

carried out at frequencies between 65 kHz and 500 mHz with a Solartron 1250 FRA and 1286 ECI, over a temperature range from 20 to 90 °C. Measurements of conductivity were effected during heating cycles. The reproducibility of recorded conductivities was confirmed by comparing the results obtained for a sample subjected to two heating-cooling-heating cycles. This procedure demonstrated the correct operation of the support and the mechanical stability of the samples.

2.4.3 Optical properties

The optical transmittance measurements were performed with a Shimadzu UV/VIS 3100PC double beam spectrophotometer in the wavelength range from 380 to 800 nm. The thickness of sample films was measured using a surface profilometer (Dektak 3D from Solan Tech).

2.4.4. Scanning electron microscopy (SEM)

X-ray diffraction experiments were carried out using a Bruker-AXS D8 Discover diffractometer in θ - 2θ geometry using Cu $K\alpha_{1,2}$ lines collimated with a Gobel mirror, a divergent slit of $0.6 \times 10 \text{ mm}^2$ and a Ni filter. The data was collected from 10° to 80° with a detector slit of $0.2 \times 10 \text{ mm}^2$, a step size of 0.04° and an acquisition time of 0.8 s per step.

RESULTS AND DISCUSSION

Thermal behaviour of electrolytes

The DSC thermograms of electrolyte samples represented in Figure 1 confirm that compositions with high p(EO-PO) content (SPE1-0PC, SPE3-9PC, SPE5-15PC, SPE7-25PC) show broad melting peaks with onsets at about 30 °C. This can be attributed to

the fusion of the crystalline phase of the p(EO-PO) component which is generally complete by about 45 °C. The introduction of substantial quantities of the pMMA and PC components in the network effectively suppressed crystallization of the (EO-PO) components of the electrolytes.

The thermal stability of the electrolyte formulations is influenced by the polymer components, the presence of stabilizing additives and the guest salt concentration. Electrolytes with high pMMA content show a marked tendency to undergo partial decomposition at temperatures close to 200°C. The lowest decomposition temperature observed is found with the SPE2-0PC composition (186°C), a value considered acceptable for most foreseeable applications under normal operating conditions. The thermal stability of electrolytes apparently improves with an increase in p(EO-PO) and PC content. Samples with substantial quantities of the p(EO-PO) component show a major exothermic peak at temperatures between about 250 and 325 °C while electrolyte formulations with less p(EO-PO) and more pMMA tend to decompose at slightly higher temperatures.

The evolution of the glass transition temperatures of the electrolyte samples is illustrated in Figure 2. The addition of the plasticizing component results in a slight decrease of T_g values. For electrolyte compositions with 15 and 25 wt% of PC the onset of the T_g is shifted to lower temperatures. Electrolyte samples, SPE1-0PC and SPE3-9PC, clearly show two glass transitions, denoted T_{g1} and T_{g2} , indicating the coexistence of two distinct polymer phases.

Ionic conductivity of electrolytes

Ionic conductivity is an important performance parameter in the development of p(EO-PO)/pMMA/LiClO₄ electrolyte systems for use as multi-functional components in electrochromic devices, such as smart windows.

The results of conductivity studies of the electrolyte compositions are illustrated in Figure 3 and confirm that the lowest conductivity was registered with compositions rich in p(EO-PO) and without plasticizing additive. A significant improvement was observed as a result of the addition of pMMA and/or a plasticizing additive. Encouraging levels of ionic conductivity were found, particularly at temperatures close to ambient, at compositions with higher concentrations of pMMA and plasticizer. The most conducting electrolyte of this SPE system is the SPE2-0PC composition ($5.01 \times 10^{-4} \text{ S cm}^{-1}$ at about $57 \text{ }^\circ\text{C}$), however electrolytes with moderate plasticizer content also show appropriate levels of conductivity and the use of electrolytes with a lower T_g may be expected to improve sealing/adhesive functions and electrode/electrolyte interfacial contact. In optical devices or displays these aspects of electrolyte behavior may become just as relevant as high ionic conductivity.

Scanning electron microscopy (SEM)

The microphase structure adopted by a blend, and its microscopic appearance, is largely determined by the miscibility of the components. The morphology of the SPE3-9PC polymer electrolyte was studied by scanning electron microscopy (SEM). Some typical examples of the SEM micrographs are presented in Fig. 4 and 5. The polymer membranes were obtained by evaporating the solvent from the casting solution. In this process, the pore morphology of the polymer membrane is determined by the nature of the solvent, evaporation rate and environmental humidity. The evaporation rate of solvents and the pore size and number can be controlled by adjusting the relative volatility of the casting solvents employed, as reported by Huang and Wunder.^[19]

Blending p(EO-PO) with pMMA and lithium salt changes the surface morphology from rough to smooth and a reduction of wrinkle is also observed in Fig.4.

After an appropriate amount of pMMA was incorporated into the p(EO-PO) -LiClO₄ electrolyte matrix, a further significant improvement in surface morphology is apparent. This may be related to a reduction of crystallinity in the pEO component as a result of blending with Li salt and pMMA. This interpretation is consistent with DSC results.

Analysis of Figures 4 and 5 suggests that electrolyte sample SPE3-9PC includes spherulites, symmetric arrays of lamellar crystals immersed in the amorphous material.^[3] The formation of these spherulites is directly related to the synthetic procedure used to prepare polymer electrolytes (the nature of the solvent, the rate of solvent removal, etc). Figure 5 also shows that this electrolyte composition is of high density and low porosity.

Optical Properties

Polymer electrolyte films prepared for application in optical devices must meet various pre-requisites. One of these is that the film must exhibit high optical transmission. If this condition is not fulfilled the electrolyte will reduce the color contrast of the device.^[20]

Figure 6 illustrates the optical transmittance in the wavelength range 400-800 nm for the prototype electrochromic assembly. Various electrolyte configurations were employed as ionic conducting layers in devices. The objective of this study was to evaluate the influence of the wt% of PC on the performance of the electrochromic device. Coloring and bleaching voltages of 4 V and -4 V respectively were applied for 20 s intervals. Table 2 summarizes the average transmittance and the optical density exhibited by devices. The transmittance in the visible region of the spectrum was above 41% for all the samples analyzed. After coloration the device assembled with 71 wt%

PC presented a transmittance of 15.71% and an optical density at 550nm of 0.61. Figure 7 illustrates the optical density at 550 nm for all electrochromic devices.

Figure 8 demonstrates the transparency of the electrolytes produced and shows a prototype solid-state electrochromic device in the coloured state. Prototype electrochromic devices were constructed using a four layer sandwich structure with the following configuration: glass/IZO/ WO_3 /polymer electrolyte/IZO/glass. The active layer of the assembled device changed from almost transparent to a blue colour associated with WO_3 reduction and simultaneous Li^+ insertion as a result of the application of a positive voltage. Inversion of the applied voltage resulted in WO_3 oxidation and the device returned to its initial state. Cycling tests were performed on all the electrochromic cells, and each cell was cycled (bleached-colored-bleached) 25 times.

CONCLUSIONS

The preliminary results obtained with combined p(EO-PO) with pMMA host matrices and lithium perchlorate are promising. These electrolytes showed good mechanical and electrochemical properties that were improved with the addition of a plasticizer, propylene carbonate. The pMMA and p(EO-PO) blend network was found to reduce the tendency of the electrolyte to adsorb moisture and provide good adhesion to a glass substrate. The results obtained with prototype electrochromic devices based on this SPE formulation were encouraging and suggest that polymer electrolytes with these components may, with further development, find application in commercial optical devices.

ACKNOWLEDGEMENTS

The authors are pleased to acknowledge the support provided by the University of Minho and the Fundação para a Ciência e a Tecnologia (contracts POCI/QUI/59856/2004, POCTI/SFA/3/686) for laboratory equipment, research staff grants (contracts SFRH/BD/22707/2005 and SFRH/BD/38616/2007) and travel funds (PCB).

REFERENCES

- [1] D.E. Fenton, J.M. Parker, P.V. Wright, *Polymer* **1973**; *14*, 589.
- [2] P.G. Bruce (Ed.), *Solid-state electrochemistry*, Cambridge University Press, Cambridge, **1995**.
- [3] F.M. Gray, *Polymer Electrolytes*, RSC Materials Monographs, The Royal Society of Chemistry, Cambridge, **1997**.
- [4] P.M. Blonsky, D.F. Shriver, P.E. Austin and H.R. Allcock, *J. Am. Chem. Soc.* **1984**; *106*, 6854.
- [5] J.R. MacCallum and C.A. Vincent, Editors, *Polymer Electrolytes Reviews*, London: Elsevier Applied Science. **1987**, Ch.1, pp.1-22.
- [6] C.J. Nelson, W.D. Coggio, H.R. Allcock, *Chem. Mater.* **1991**; *3*, 117.
- [7] H.R. Allcock, S.E. Kuharcik, C.S. Reed, M.E. Napierala, *Macromolecules* **1996**; *29*, 3384.
- [8] S. Vorrey, D. Teeters, *Electrochim. Acta* **2003**; *48*, 2137.
- [9] M.M. Silva, S.C. Barros, M.J. Smith and J.R. MacCallum, *J. Power Sources* **2002**; *111*, 52.
- [10] Armand, M., Gorecki, W., Andreani, R. in *Second International Meeting on Polymer Electrolytes* (ed. Scrosati, B.), Elsevier, London, **1989**, 91–96.
- [11] D. Benrabah, D. Baril, J.Y. Sanchez and M. Armand, *J. Chem. Soc., Faraday Trans* **1993**; *89*, 355.
- [12] K. Xu, S.S. Zhang, T.R. Jow, W. Xu and C.A. Angell, *Electrochem. Solid State Lett.* **2002**; *5*, A26.

- [13] M. Schmidt, U. Heider, A. Kuehner, R. Oesten, M. Jungnitz, N. Ignatev and P. Sartori, *J. Power Sources* **2001**; 97–98, 557.
- [14] J.S. Gnanaraj, M.D. Levi, Y. Gofer and D. Aurbach, *J. Electrochem. Soc.* **2003**; 150, 445.
- [15] F. Kita, H. Sakata, S. Sinomoto, A. Kawakami, H. Kamizori, T. Sonoda, H. Nagashima, J. Nie, N.V. Pavlenko and Y. L. Yagupolskii, *Journal of Power Sources* **2000**; 90, 27.
- [16] M.-A. de Paoli, A. Berlin, A. Geri, G. C. Miceli, W.A. Gazotti, *Adv. Mater.* **1998**; 10, 1522.
- [17] M.-A. de Paoli, A.F. Nogueira, D.A. Machado, Claudia Longo, *Electrochimica Acta* **2001**; 46, 4243.
- [18] C.O. Avellaneda, D.F. Vieira, A.Al-Kahlout, S. Heusing, E.R. Leite, A. Pawlicka, M.A. Aegerter, *Solar Energy Materials and Solar Cells* **2008**; 92, 228.
- [19] H. Huang and S. L. Wunder, *Journal Power Sources* **2001**; 97-98, 649.
- [20] M-H. Cui, Jun-Shi Guo, H-Q. Xie, Z-H. Wu, S-C. Qiu, *Journal of Applied Polymer Science* **1997**; 65, 1739.

Table 1 – Electrolyte compositions based on p(EO-PO), pMMA, PC and LiClO₄.

| (wt%) p(EO-PO) | (wt%) pMMA | (wt%) PC | (wt%) LiClO ₄ | Sample |
|----------------|------------|----------|--------------------------|-----------|
| 80 | 9 | 0 | 11 | SPE1-0PC |
| 9 | 80 | 0 | 11 | SPE2-0PC |
| 62 | 18 | 9 | 11 | SPE3-9PC |
| 18 | 62 | 9 | 11 | SPE4-9PC |
| 59 | 15 | 15 | 11 | SPE5-15PC |
| 15 | 59 | 15 | 11 | SPE6-15PC |
| 54 | 10 | 25 | 11 | SPE7-25PC |
| 10 | 54 | 25 | 11 | SPE8-25PC |

Table 2 - Average transmittance and optical density exhibited by electrochromic devices.

| (wt%) PC | Transmittance in bleached state (%) | Transmittance in colored state (%) | Optical density (550 nm) |
|-----------------|--------------------------------------------|-------------------------------------------|---------------------------------|
| 0 | 54.19 | 16.57 | 0.49 |
| 9 | 52.59 | 24.21 | 0.34 |
| 15 | 47.09 | 17.88 | 0.35 |
| 20 | 41.49 | 16.96 | 0.36 |
| 40 | 61.59 | 19.58 | 0.46 |
| 71 | 73.44 | 15.71 | 0.61 |

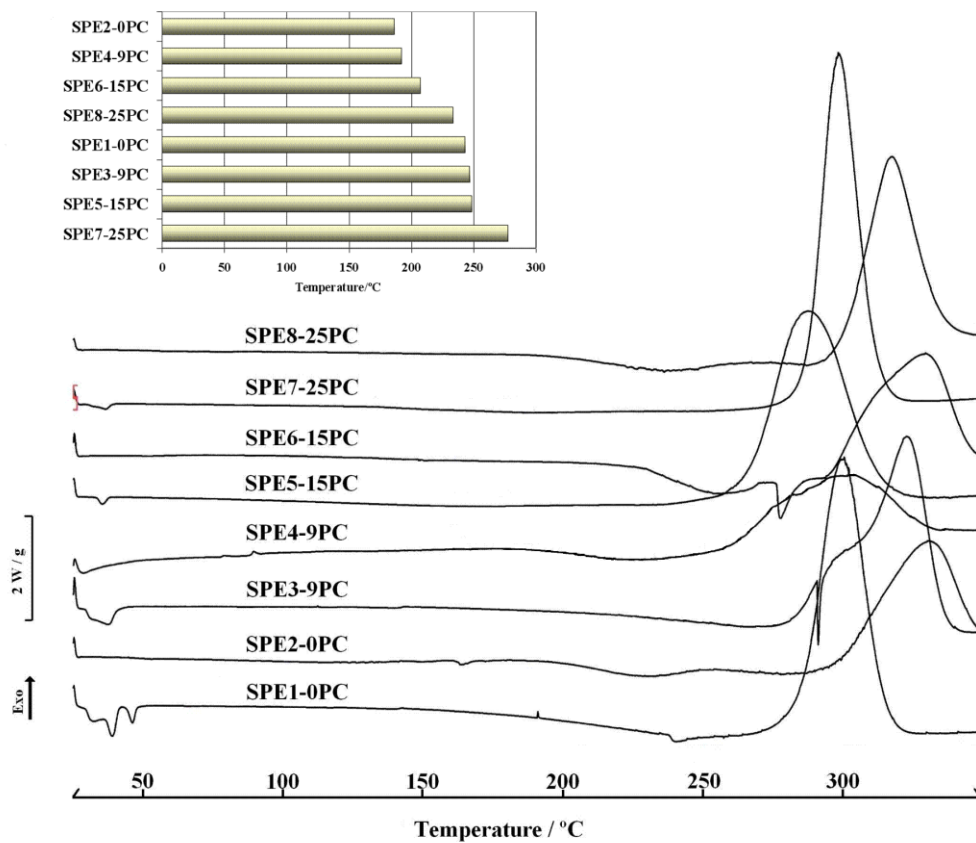


Figure 1. DSC thermograms of p(EO-PO)/pMMA/LiClO₄ electrolytes.

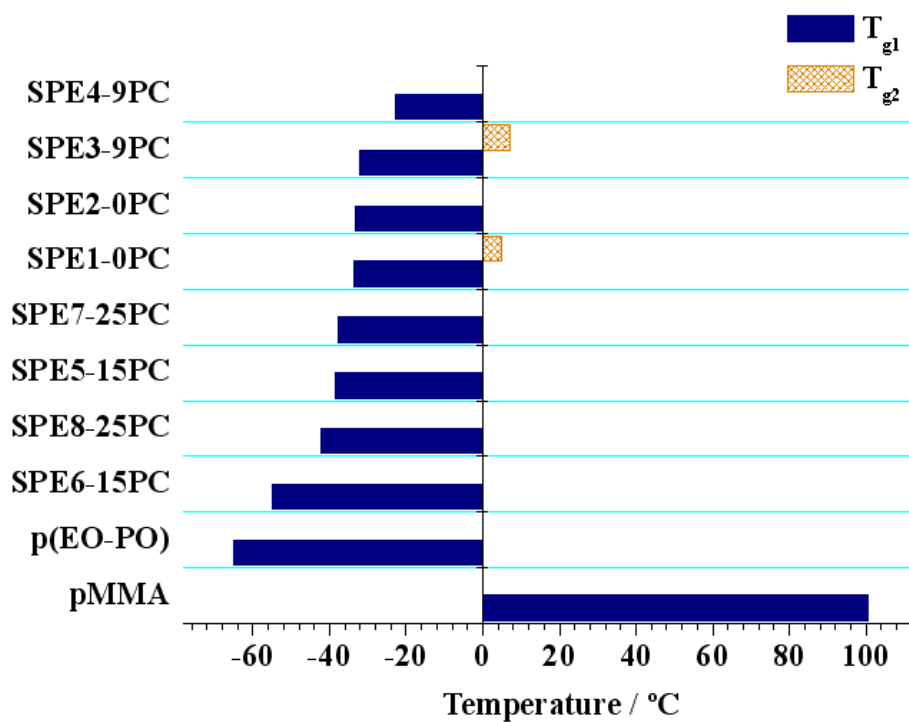


Figure 2. T_g of p(EO-PO)/pMMA/LiClO₄ electrolytes.

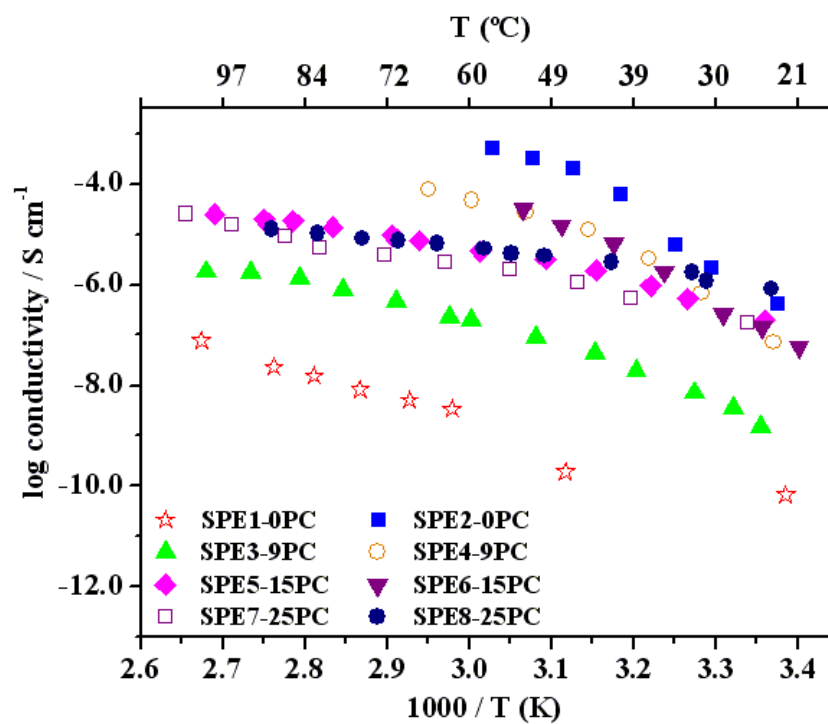


Figure 3. Variation of conductivity of p(EO-PO)/pMMA/LiClO₄ electrolytes with temperature.

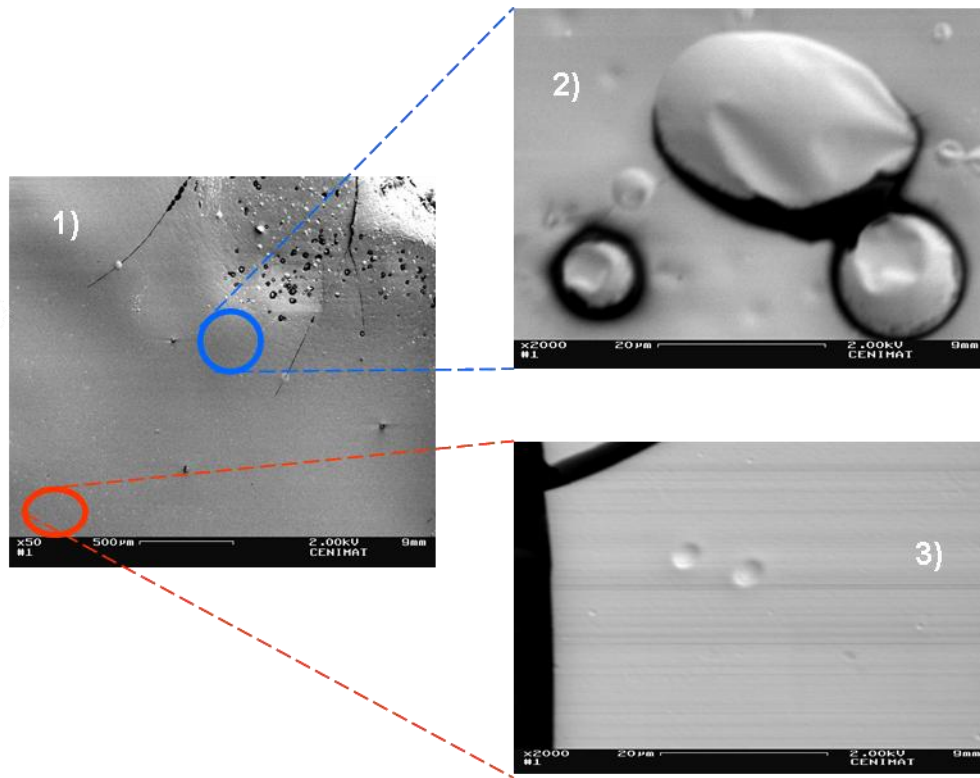


Figure 4. Selected SEM photographs of morphology of upper surface of SPE3-9PC (x50) (1) and two magnifications (x2000) of the areas identified as (2) and (3).

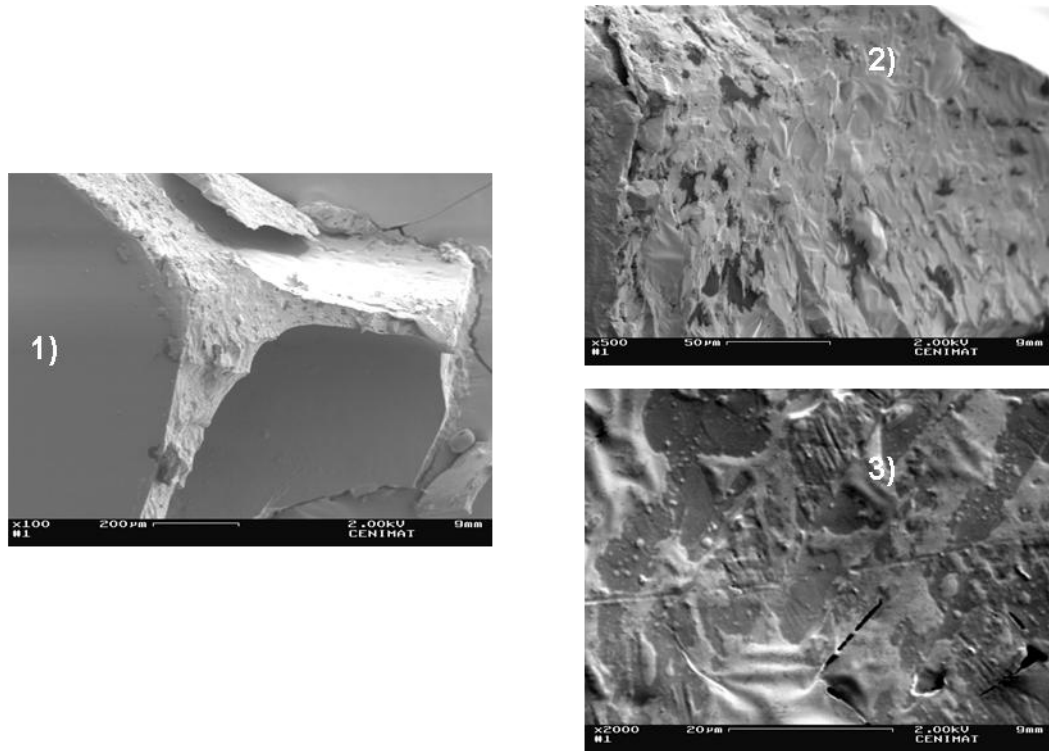


Figure 5. Scanning electron microscope (SEM) images of SPE3-9PC, cross-sectional view, (x100) (1) and two images at different locations of the observed area (x500) (2) and (x2000) (3).

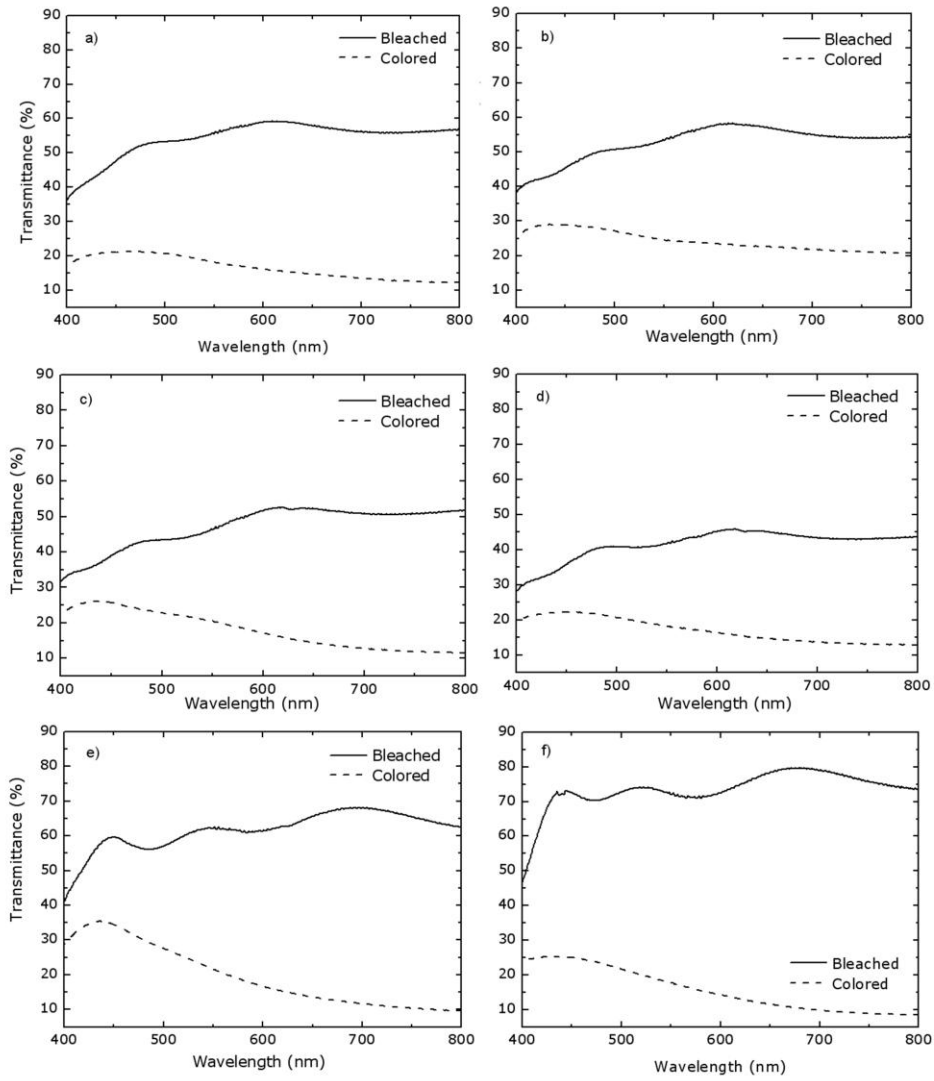


Figure 6. Optical transmittance as a function of wavelength for the electrochromic device assembly in bleached and colored states using (a) 0 wt% PC; (b) 9 wt % PC; (c) 15 wt % PC; (d) 20 wt % PC; (e) 40 wt % PC; (f) 71 wt % PC.

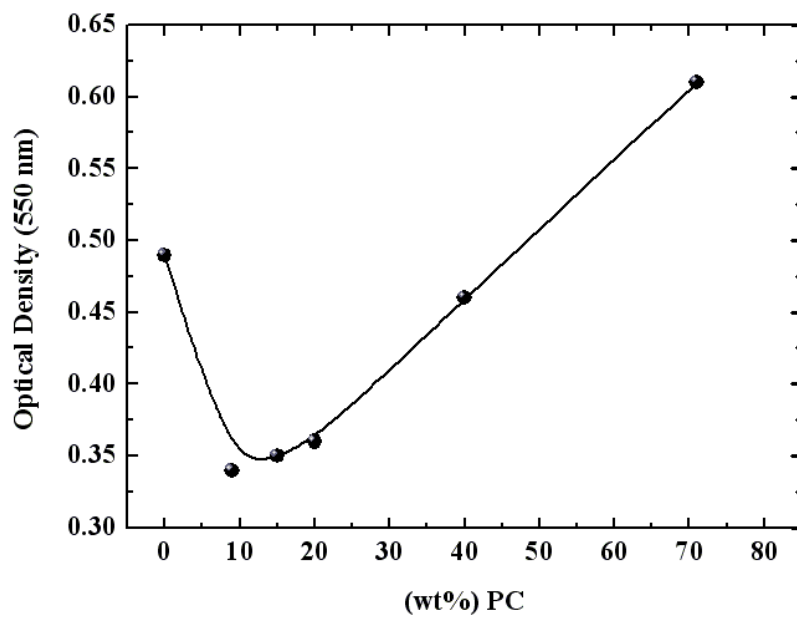


Figure 7. Optical density versus wt% PC.

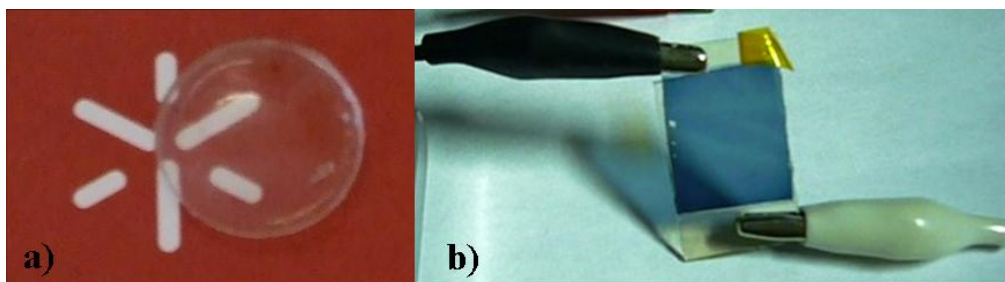


Figure 8. a) p(EO-PO)/pMMA/PC/LiClO₄ electrolyte; b) Prototype electrochromic device based on (10%) p(EO-PO) / (39%) pMMA / (40%) PC / (11%) LiClO₄ electrolyte, in the colored state.