

Online Research @ Cardiff

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <https://orca.cardiff.ac.uk/id/eprint/158240/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Pan, Z., Dibert, K. R., Zhang, J., Barry, Peter, Anderson, A. J., Bender, A. N., Benson, B. A., Cecil, T., Chang, C. L., Gualtieri, R., Li, J., Lisovenko, M., Novosad, V., Rouble, M., Wang, G. and Yefremenko, V. 2023. Noise optimization for MKIDs with different design geometries and material selections. IEEE Transactions on Applied Superconductivity 33 (5) 10.1109/TASC.2023.3250167 file

Publishers page: <http://dx.doi.org/10.1109/TASC.2023.3250167>
<<http://dx.doi.org/10.1109/TASC.2023.3250167>>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies.

See

<http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



Noise Optimization for MKIDs with Different Design Geometries and Material Selections

Z. Pan¹, K. R. Dibert^{2,3}, J. Zhang¹, P. S. Barry^{4,1}, A. J. Anderson^{2,3,5}, A. N. Bender¹, B. A. Benson^{2,3,5}, T. Cecil¹, C. L. Chang^{1,2,3}, R. Gualtieri¹, J. Li¹, M. Lisovenko¹, V. Novosad¹, M. Rouble⁶, G. Wang¹, and V. Yefremenko¹,

¹Argonne National Laboratory, 9700 South Cass Avenue., Argonne, IL, 60439, USA

²Dept. of Astronomy & Astrophysics, U. Chicago, 5640 South Ellis Avenue, Chicago, IL, 60637, USA

³Kavli Institute for Cosmological Physics, U. Chicago, 5640 South Ellis Avenue, Chicago, IL, 60637, USA

⁴School of Physics and Astronomy, Cardiff University, Cardiff CF24 3YB, UK

⁵Fermi National Accelerator Laboratory, MS209, P.O. Box 500, Batavia, IL, 60510, USA

⁶Department of Physics, McGill University, 3600 Rue University, Montreal, Quebec H3A 2T8, Canada

Abstract—The separation and optimization of noise components is critical to microwave-kinetic inductance detector (MKID) development. We analyze the effect of several changes to the lumped-element inductor and interdigitated capacitor geometry on the noise performance of a series of MKIDs intended for millimeter-wavelength experiments. We extract the contributions from two-level system noise in the dielectric layer, the generation-recombination noise intrinsic to the superconducting thin-film, and system white noise from each detector noise power spectrum and characterize how these noise components depend on detector geometry, material, and measurement conditions such as driving power and temperature. We observe a reduction in the amplitude of two-level system noise with both an elevated sample temperature and an increased gap between the fingers within the interdigitated capacitors for both aluminum and niobium detectors. We also verify the expected reduction of the generation-recombination noise and associated quasiparticle lifetime with reduced inductor volume. This study also iterates over different materials, including aluminum, niobium, and aluminum manganese, and compares the results with an underlying physical model.

Index Terms—Two-level system (TLS), noise, microwave kinetic inductance detectors (MKIDs), generation-recombination noise, optimization.

I. INTRODUCTION

Future mm-wave experiments require ever-increasing detector counts to achieve the necessary sensitivity to pursue ambitious science cases. Microwave kinetic inductance detectors (MKIDs) are well suited to large-format detector arrays, including photometer arrays [1], [2], [3] and on-chip filter-bank spectrometers [4], [5], [6], [7]. To achieve photon-limited sensitivity for each detector, it is necessary to understand each component of detector noise, including two-level system (TLS) noise, shot noise from the generation and recombination (GR) of quasiparticles, and amplifier noise.

TLS noise is caused by the coupling of a resonator to a thin amorphous solid dielectric layer, where two-level tunneling states are thought to exist based on a phenomenological model [8]. When atoms tunnel between two states, the resulting dipole can couple to the electric field of the resonator, causing excessive noise with a characteristic spectral

shape proportional to $f^{-1/2}$, where f is the frequency of the noise. Though a full microscopic understanding of TLS noise is yet to be established, previous studies have shown that the TLS amplitude in MKIDs can be altered by changing the capacitor geometry [9], and through substrate surface treatments prior to the deposition of the metal films [10]. The generation-recombination noise of an MKID is caused by the continual breaking and reforming of Cooper pairs within the inductor. From the perspective of the resonator, the GR noise is also dependent on inductor geometry and should decrease with reduced inductor volume [11]. The amplifier noise can be minimized by operating the amplifiers just below MKID bifurcation power, or by using amplifiers with lower noise-equivalent temperatures.

In this paper, we fit detector noise power spectra to extract the TLS noise, the GR noise, and the amplifier white noise for a series of detector designs with different inductor volumes and interdigitated capacitor (IDC) geometries. We repeat this analysis with different detector materials, including niobium, aluminum, and manganese-doped aluminum (AlMn) with a lower superconducting transition temperature T_c than aluminum. The goal of this exercise is to identify a set of geometric and material parameters that enable the tuning of detector noise to achieve the requirements of a given an experiment. This has immediate application both to our current efforts toward the development of SPT-3G+ [12] and to future missions with more stringent noise requirements such as an NEP at the level of $10^{-20} \text{W} / \sqrt{\text{Hz}}$.

II. DEVICE DESIGN AND FABRICATION

The MKID design used for this study is based on the prototype design for SPT-3G+ [12]. We then modify component geometries and detector materials to explore their impact on detector noise. Figure 1 shows a photo of 1×0.5 inch device used for this study. The microstrip feedline is capacitively coupled to five pixels, each composed of two MKIDs aligned to orthogonal polarization optical modes. Operating as detectors, these resonators are intended to couple to radiation via

a feedhorn, which drives the design of the resonator inductor to double as an efficient photon absorber. Each inductor is coupled to an IDC whose geometry sets the unique resonant frequency of each resonator on the device. Three types of devices were fabricated, each designed to test one change to device geometry. These include: A) a device with varying inductor volumes for all five pixels to explore the impact on the GR noise, B) a device with a varying gap width between IDC lines or equivalently varying IDC filling factor, and C) a device with varying IDC tine width as well as the gap between tines. See Fig. 2 for the design geometries of A), B), and C). The devices are fabricated via a single-layer metal deposition on a high-resistivity silicon substrate. The resonator geometry is defined via optical photolithography and a wet etch. The silicon wafers are prepared with a buffered-HF etch to remove the native oxide layer prior to metal deposition. Each six-inch wafer contains all of the geometric design variations, so that the film material remains as consistent as possible across all device types.


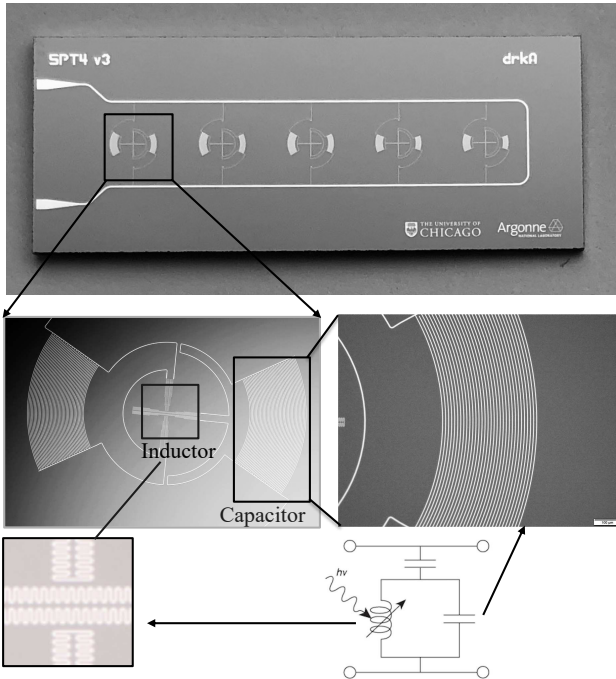



Fig. 1. Microscope images of the type (A) chip described in the text with different inductor volumes. Each pixel contains two detectors with two inductors oriented in orthogonal directions and two associated capacitors to form the resonators. The inductors are meandered metal lines, and the capacitors utilize the interdigitated design. The capacitors have curved tines that allow higher packing density in the final detector array. Bottom right diagram is from [13].

III. NOISE MEASUREMENT AND MODELING


Detector noise timestreams were measured with a homodyne single-tone setup consisting of a microwave signal generator, quadrature demodulator, signal splitter, attenuators, and a 200 kHz commercial ADC. Measurements were taken over a temperature range spanning $\sim 8 - 300$ mK, and the

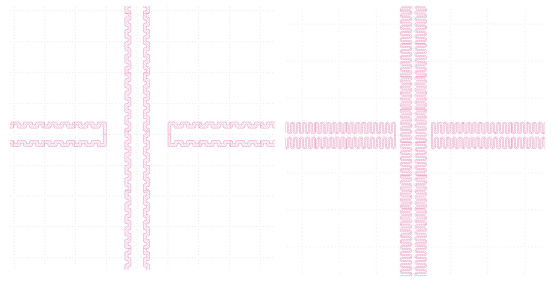

(A) Varying inductor volume. Left: $173 \mu\text{m}^3$, right: $460 \mu\text{m}^3$

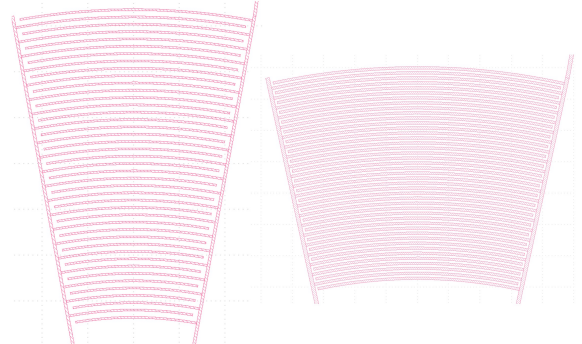

(B) Varying capacitor tine gap. Left: $12 \mu\text{m}$, right: $4 \mu\text{m}$

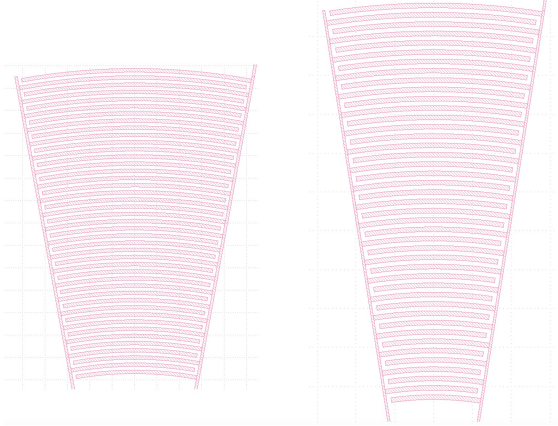

(C) Varying capacitor tine gap and width. Left: $8 \mu\text{m}$, right: $12 \mu\text{m}$

Fig. 2. Detector geometry variations. Here subfigures A), B), and C) correspond to designs A), B), and C) discussed in the text.

microwave signal was amplified using amplifiers at both 4 K and room temperature.

We report the noise power spectral densities (PSDs) calculated using the local-gradient procedure in [14] and we have verified the consistency of this method with the phase-shift method described in the same reference. Figure 3 shows example noise measurements for one detector taken at a microwave power on the feedline of -110 dBm. At 8 mK, we observe in the noise PSD a clear $1/\sqrt{f}$ slope associated with TLS noise that decays with increasing device temperature. Around 1000 Hz, we observe a rolloff in the PSD that is related to the quasiparticle lifetime. The frequency of this rolloff shifts to a higher frequency as the operating temperature increases, as expected [15]. The noise beyond 20 KHz is dominated by the white noise level of the cryogenic amplifier.

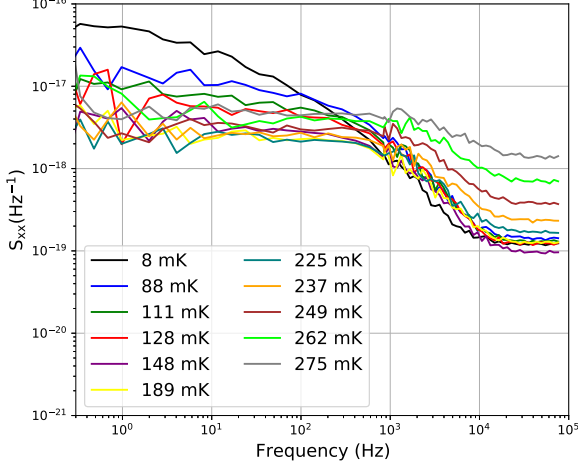


Fig. 3. Sample fractional frequency shift noise PSD for a resonator. The $1/\sqrt{f}$ feature at lower stage temperature corresponds to TLS noise and decreases as we increase the operating temperature. The flat white noise level in the mid-frequency range corresponds to the generation and recombination of quasiparticles. The white noise floor above the GR rolloff at a few kHz is mostly system noise dominated by amplifier noise.

Each noise PSD is fit with the following model [16]:

$$S_{xx}(f) = \left(\frac{A + Bf^{-n}}{1 + (2\pi f\tau)^2} + C \right), \quad (1)$$

where S_{xx} is the frequency noise PSD, A is the GR noise component, Bf^{-n} is the $1/\sqrt{f}$ noise (mostly dominated by TLS in our system), τ is the quasiparticle lifetime, and C is the system white noise level.

To break the degeneracy of parameters, we note that the GR noise level A does not depend on temperature [11]. Thus, we can fit for A using high-temperature data where the TLS component is suppressed, and then fit for B in low-temperature data using a model with fixed A . We found that our low-temperature data is consistent with $n \sim 0.5$ and therefore fixed $n = 0.5$ to better expose the geometry dependence of parameter B . The quasiparticle lifetime, τ , and the system white noise level, C , are not degenerate with other parameters since they correspond to distinct features: the rolloff and the flat region at high frequency ($\sim 10^5$ Hz).


Some of the AIMn detectors were found to have a non-negligible resonator ring-down time $\tau_{res} = Q/\pi f_0$, where Q is the resonator quality factor, and f_0 is the resonant frequency. Since the ring-down time is assumed to be negligible in Eq. (1), we re-introduced the rolloff term $1 + (2\pi f\tau_{res})^2$ to the denominator of Eq. (1) for AIMn detectors with τ_{res} from independent measure of Q and f_0 [11]. The AIMn resonators also have low bifurcation power [17], which in some cases was only slightly above the system white noise floor. As a result, we collected limited data for a fraction of AIMn resonators within a small range of stage temperature and bias powers relative to the datasets taken for other materials. For a robust extraction of the fit parameters, we fit multiple noise curves taken for the same resonator at different temperatures and powers simultaneously.

IV. GENERATION-RECOMBINATION NOISE OPTIMIZATION


The generation-recombination noise contribution to the quasiparticle fluctuation PSD is expected to follow:

$$S_N(f) = \frac{4N_{qp}\tau}{1 + (2\pi f\tau)^2}, \quad (2)$$

where N_{qp} is the number of quasiparticles. The numerator of this expression should scale with detector volume V_L since $N_{qp} = n_{qp}V_L$, where n_{qp} is the quasiparticle number density. We seek to demonstrate the dependence of the numerator on inductor volume.

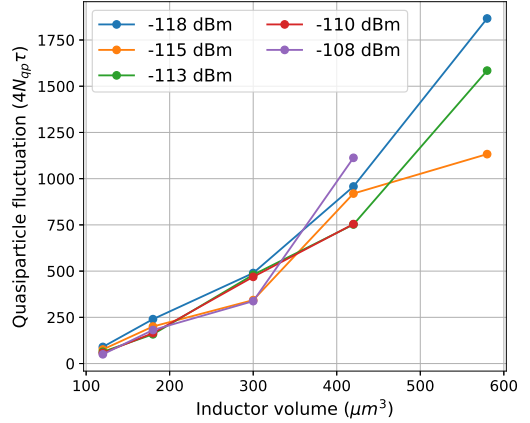

(a) X-polarization detectors, aluminum, type A

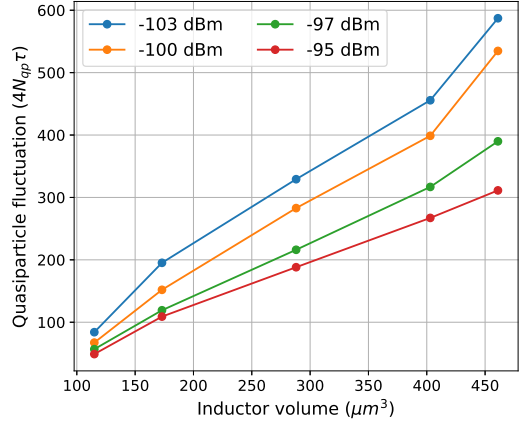

(b) Y-polarization detectors, aluminum, type A

Fig. 4. Quasiparticle number fluctuation PSD vs. inductor volume for X and Y polarizations. We separate X and Y due to different inductor geometries.

We fit the noise PSDs of aluminum detectors with varying inductor volume (Type A from Section II), and extracted the GR noise level (A in Eq. (1)). This parameter theoretically has dependence $A = 4N_{qp}\tau(dx/dN_{qp})^2$, where $x = df/f$. To isolate the linear dependence of $4N_{qp}\tau$ on inductor volume, we divide out the dx/dN_{qp} term by recognizing that

$$\frac{dx}{dN_{qp}} = \frac{dx}{dT} \frac{dT}{dN_{qp}} = \frac{1}{V_L} \frac{dx}{dT} \frac{dT}{dn_{qp}}, \quad (3)$$

and making use of expression for quasiparticle number density:

$$n_{qp} = 2N_0 \sqrt{2\pi k_B T \Delta} \exp(-\Delta/k_B T), \quad (4)$$

where N_0 is the single spin density of states at the Fermi level ($1.72 \times 10^{10} \mu\text{m}^{-3} eV^{-1}$ for aluminum), k_B is the Boltzmann constant, and $\Delta = 1.76k_B T_c$ is the energy gap for aluminum. Fig. 4 shows $4N_{qp}\tau$ as a function of inductor volume for the aluminum devices. We grouped the detectors by polarization alignment, as the inductor geometry differs slightly between polarization. This figure shows that the GRN noise scales as expected with inductor volume. The difference between X and Y may be the different inductor geometries (Fig. 2A).

V. TWO-LEVEL SYSTEM NOISE OPTIMIZATION

We fit noise PSDs for aluminum detectors of varying IDC tine gap width (Type B from II) and IDC tine width (Type C from II) to extract the TLS amplitude (B from Equation 1).

Fig. 5a shows a clear decrease in TLS amplitude as the IDC tines are spaced further apart. With a larger gap between the IDC tines, the electric field is smaller, resulting in weaker coupling to the dipole states in the amorphous solid.

Coupling of the field to the TLS is expected to cause a shift in both quadratures of the dielectric response function [18]. We can measure the quantity $F\delta$ by fitting resonant frequency vs. temperature to a TLS model [19]. Here F is the filling factor, which defines the fraction of the power coupled through the dielectric, and δ is the loss for the dielectrics. We measured the TLS loss for the resonators and plotted the fit B values vs. $F\delta$ in Fig. 5b, where a clear correlation is observed. We repeated these measurements for niobium resonators with detector type C and found a similar positive correlation between B and $F\delta$ in Fig. 5c.

To minimize TLS noise, we should reduce the filling factor in dielectrics or surface states. While intuitive ways such as changing capacitor gap size exist, a more systematic way for this optimization is through simulations such as HFSS. We can simulate the filling factors for potential TLS locations such as dielectrics, surface oxide layers, or interface layers and study their correlation with the observed TLS noise levels.


There are additional external parameters for tuning the TLS noise, such as the driving power and the operating temperature. The phenomenological TLS model predicts the dependence on power and temperature as

$$S_{xx} \propto P^{-1/2} f^{-1/2} T^\beta \tanh(hf_0/2k_B T), \quad (5)$$


where P is the power, f is the frequency, β is an empirically derived exponent ($\beta \sim -0.14$ reported in [20]), and f_0 is the resonant frequency. Our measured TLS noise levels parametrized by B agree with the model in Eq. (5) and decrease as a function of power or temperature (Fig. 6). To reduce TLS noise, we can operate at a high bias power just below the onset of bifurcation [21], and raise the stage temperature ensuring that the white noise level and resonator quality factor are not degraded.

VI. QUASIPARTICLE LIFETIME


The quasiparticle lifetime is another parameter we can fit from the S_{xx} rolloff frequency. The recombination time is summarized in [22]:

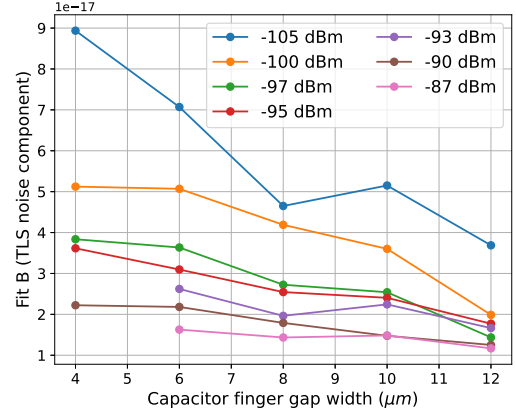

(a) Fit B vs. capacitor finger gap, aluminum, type B

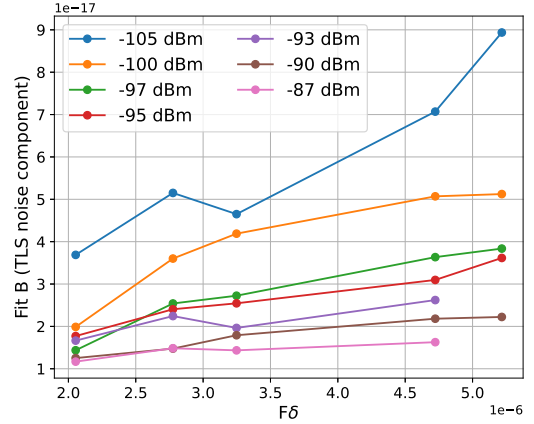

(b) Fit B vs. $F\delta$, aluminum, type B

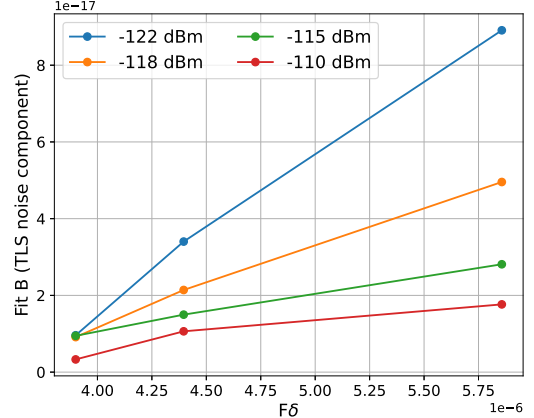

(c) Fit B vs. $F\delta$, niobium, type B

Fig. 5. TLS noise's dependence on capacitor finger gap width and $F\delta$. (a) and (b) are for aluminum, and (c) is for niobium.

$$\tau_R = \frac{\tau_0}{\sqrt{\pi}} \left(\frac{k_B T_c}{2\Delta} \right)^{5/2} \sqrt{\frac{T_c}{T}} e^{\Delta/k_B T} = \frac{\tau_0}{n_{qp}} \frac{N_0 (k_B T_c)^3}{2\Delta^2}, \quad (6)$$

where τ_0 is a material-dependent characteristic electron-phonon interaction time. Note that one recombination is associated with the disappearance of two quasiparticles so that

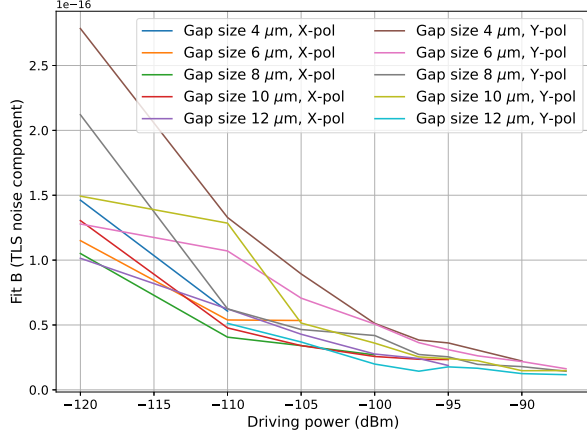
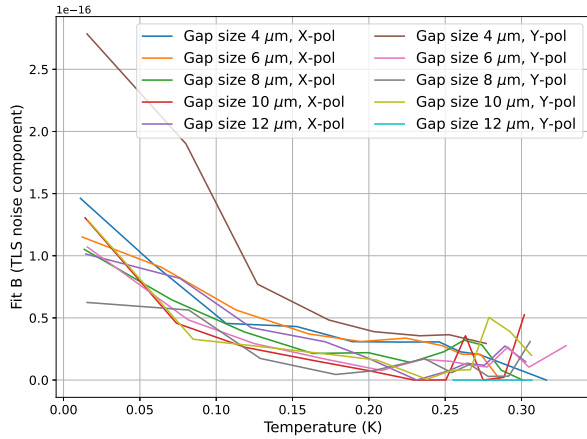
(a) Fit B vs. driving power, aluminum, type B(b) Fit B vs. operating temperature, aluminum, type B

Fig. 6. TLS noise's dependence on driving power and temperature. We have included ten detectors in each plot for five different gap sizes and two polarizations. The design is type (B) in Fig. 2.

$\Gamma_R^* = 2\Gamma_R F_\omega^{-1}$ [23], where Γ_R is the recombination rate, Γ_R^* is the time constant for a small quasiparticle perturbation to decay (quantity measured experimentally), and F_ω is the phonon trapping factor that accounts for pair breaking by emitted phonon from the recombination. If we neglect phonon trapping, $\Gamma_R^* = 2\Gamma_R$, and the resulting measured quasiparticle lifetime $\tau = \tau_R/2$, where τ_R is defined in Eq. (6). We plot the dependence of the quasiparticle lifetime as a function of temperature in Fig. 7 and then fit it to the model in Eq. (6) with the factor of two correction using temperatures above 0.24 K. The fit value for τ_0 is $0.2 \pm 0.1 \mu\text{s}$, which is of the same order of magnitude as for previous measurements [22], [24] but somewhat smaller. [25] found impurities can change quasiparticle recombination time, which could mean there are impurities in our aluminum. Another uncertainty comes from T_c and Δ . We found the τ_0 in the model fit sensitive to the preset T_c and Δ values, and that using $T_c = 1.2 \text{ K}$ and $\Delta = 1.76 k_B T_c$ gives $\tau_0 = 0.6 \mu\text{s}$ for the fit. The current $T_c = 1.37 \text{ K}$ we used for this analysis is from fitting f vs. T to a Mattis-Bardeen model [26] and may not be very accurate. Also, $\Delta = 1.76 k_B T_c$ may not be accurate for a thin film, and we neglected phonon trapping. We note these

uncertainties for our τ_0 result. The quasiparticle lifetime below $\sim 0.2 \text{ K}$ is limited by other relaxation mechanisms, such as nonequilibrium quasiparticle excitations [27], [28].

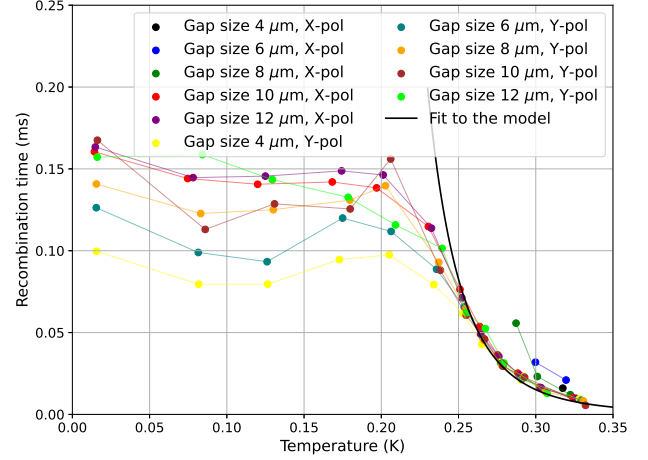


Fig. 7. Quasiparticle lifetime vs. operating temperature. We have included ten detectors in each plot for five different gap sizes and two polarizations. Plotted is for aluminum type (B) in Fig. 2. We fit data above 0.24 K to the model in Eq. 6 with the correction.

VII. ALMN NOISE RESULTS

The AlMn samples we used are the same as the ones reported in [17]. We can reach a lower T_c than pure aluminum by doping aluminum with manganese, and baking provides yet another knob to tune their T_c . Low- T_c MKIDs are interesting for spectrometers because they open up below 100 GHz for a few redshifted CO lines and are also useful for MKID-based dark matter searches that require higher sensitivity. The aluminum and AlMn films were sputtered using high-purity aluminum and Mn doped aluminum with 1050 ppm (parts per million) and 1150 ppm doping levels, respectively. The superconducting transition temperatures for the aluminum sample, 1050 ppm AlMn, and 1150 ppm AlMn are 1.37 K, 0.73 K, and 0.61 K, respectively. The 1050 ppm sample subsequently went through a baking process at 180 °C for 10 minutes, which shifted its T_c from 0.73 K pre-baking to 0.78 K after baking. Our goals with the AlMn samples are to understand the dependence of GR noise level and quasiparticle lifetime on the doping and baking conditions.

The measured noise PSDs for the AlMn resonators are similar to those for the aluminum resonators shown in Fig. 3, but the PSD curves are noisier especially in the low frequency region below about 1 kHz. Since the GR noise level A , in the temperature and bias power range where we took data, is independent of temperature or bias power, we fit the set of PSD curves for an AlMn resonator simultaneously with a single parameter A , while the τ_{res} corrections were applied independently to each noise curve. The quasiparticle lifetime for each noise curve, τ , was also obtained from this global fit. The GR noise level can in principle be expressed in quasiparticle number fluctuations, $4N_{qp}\tau$, by factoring out dx/dN_{qp} from A . However, we did not do this for the AlMn resonators because N_0 for AlMn was not known to us.

Fig. 8 shows the GR noise level A in fractional frequency shift for different doping and baking configurations. We observe an increase in GR noise with increasing Mn doping levels, and we find that baking makes the GR noise slightly worse for the 1050 ppm AlMn resonators. Clearly, these observations are still limited by statistics because of the limited dataset.

We plot the fitted quasiparticle lifetime τ as a function of the reduced temperature T/T_c in Fig. 9. All samples show saturated τ when $T/T_c < 0.1$, but their rolloff start at different reduced temperatures. Doped aluminum with impurities can be analyzed with more complex theories developed by Zittartz, Bringer, and Müller-Hartmann [29], or Kaiser [30]. Barends et al. [25] obtained some qualitative conclusions applying these models but did not model their data quantitatively. τ for AlMn in Fig. 9 show wider scatter compared with the Al resonators shown in Fig. 7. This is because the AlMn resonators have lower bifurcation power than pure aluminum, which required a reduction in the bias power for the measurement and consequently increased the noise.

We can draw qualitative conclusions from the τ vs. T/T_c dependence shown in Fig. 9. In the same figure, the modeled quasiparticle lifetime $\tau = \tau_R/2$ using Eq. (6) are also shown. τ_0 's are chosen that the theoretical curves match the corresponding roll-off edges visually. Assuming all samples are BCS superconductors, the samples doped with manganese have τ_0 about an order of magnitude smaller than pure aluminum. This reduction in τ_0 is not unexpected through its dependence on impurities [31]. We realize that the BCS modeling may not fully apply here: O'Neil et al. [32] demonstrated that the density of states of AlMn remains BCS-like, but additional sub-gap states and gap edge smearing are also present.

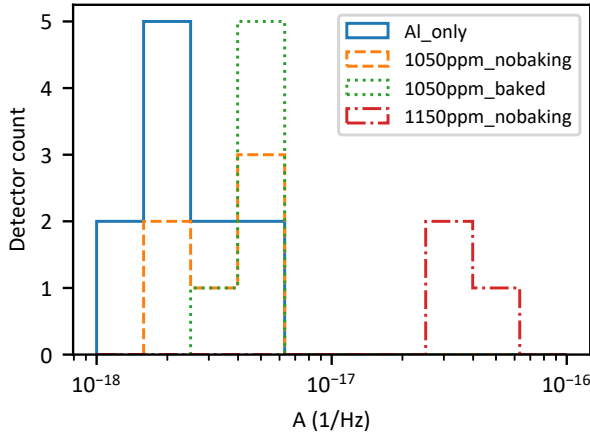


Fig. 8. Histograms of the GR noise level A in S_{xx} for pure aluminum and AlMn with different Mn concentrations.

Finally, we use the GR noise level A to constrain τ_0 and N_0 . With Eq. (4) and Eq. (6), we can decompose the dependence of A into:

$$A = 4N_{qp}\tau \left(dx/dN_{qp}\right)^2 = \frac{\tau_0}{N_0} \frac{2}{V_L} \left(\frac{dx}{d\rho}\right)^2 \frac{(k_B T_c)^3}{2\Delta^2}, \quad (7)$$

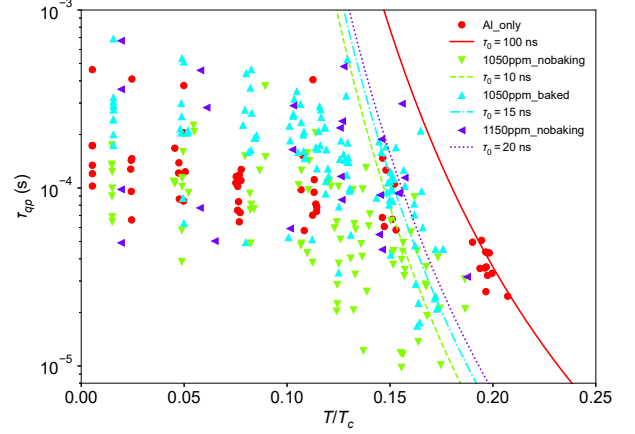


Fig. 9. Quasiparticle lifetime vs. reduced temperature T/T_c for pure aluminum and AlMn with different Mn concentrations. We have added model curves using Eq. (6) with the samples' measured T_c . The τ_0 values for the model are chosen such that the curves follow the falling edges at higher temperatures. The data is too noisy for a good fit, but we can still tell τ_0 for AlMn is an order of magnitude smaller than pure aluminum if we assume a BCS description.

where $\rho = n_{qp}/N_0 = 2\sqrt{2\pi k_B \Delta} \exp(-\Delta/k_B T)$. We can put constraints on τ_0/N_0 using Eq. (7) since all other terms can be measured or are known from the design. The resulting histograms for τ_0/N_0 are summarized in Fig. 10. The τ_0/N_0 values for pure aluminum are about two orders of magnitude larger than those for AlMn, indicating that the density of states N_0 for AlMn is higher than that for aluminum since the τ_0 's only differ by one order of magnitude. [33] reported a calculation of local density of states for Al with impurities. One caveat is that we have assumed all the samples are BCS-like.

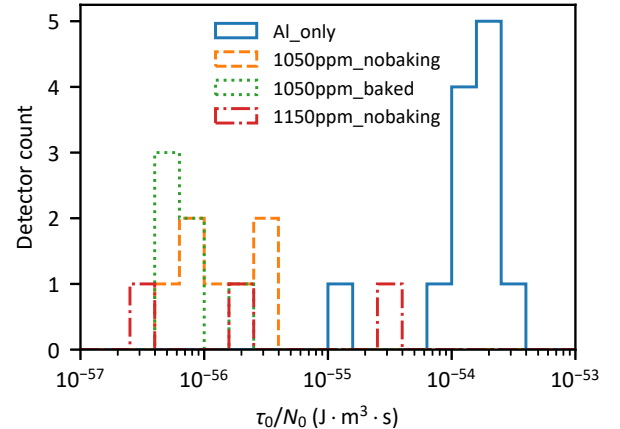


Fig. 10. τ_0/N_0 histograms for pure aluminum and AlMn with different Mn concentrations.

VIII. CONCLUSIONS

In this paper, we explored and validated a few directions to control the noise components of MKIDs. For aluminum detectors, we were able to tune the GR noise by changing

the inductor volume of our detectors and observed a linear dependence between the quasiparticle fluctuation noise and inductor volume. We can reduce the TLS noise using three methods: 1) lowering the capacitor filling factor, 2) raising the operating temperature, and 3) increasing the driving power. We compared the temperature and power dependence of TLS with models and correlated the TLS noise with $F\delta$ measured using a TLS dielectric loss model. We did the TLS study for both niobium and aluminum resonators. We also explored the noise components' dependence on manganese doping with AlMn detectors. We found manganese doping increases the GR noise level. Assuming a BCS description, we observed that AlMn samples prefer a lower τ_0 and a higher N_0 than aluminum samples. The noise for our samples can be controlled below the photon noise limit for ground-based photometer applications (e.g., SPT3G+). However, we need more thorough optimization for space applications or spectrometers with narrower bands that require lower noise. This study provides a few directions for future noise optimization.

IX. ACKNOWLEDGEMENTS

Work at Argonne, including the use of the Center for Nanoscale Materials, an Office of Science user facility, was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, and Office of High Energy Physics, under Contract No. DE-AC02-06CH11357. Zhaodi Pan is supported by ANL under the award LDRD-2021-0186. Maclean Rouble acknowledges funding from the Natural Sciences and Engineering Research Council of Canada and Canadian Institute for Advanced Research.

REFERENCES

- [1] M. Calvo, A. Benoît, A. Catalano, J. Goupy, A. Monfardini, N. Ponthieu, E. Barria, G. Bres, M. Grollier, G. Garde *et al.*, “The nika2 instrument, a dual-band kilopixel kid array for millimetric astronomy,” *Journal of Low Temperature Physics*, vol. 184, no. 3, pp. 816–823, 2016.
- [2] T. L. Brien, P. A. Ade, P. S. Barry, E. Castillo-Domínguez, D. Ferrusca, T. Gascard, V. Gómez, P. C. Hargrave, A. L. Hornsby, D. Hughes *et al.*, “Muscat: the mexico-uk sub-millimetre camera for astronomy,” in *Millimeter, Submillimeter, and Far-Infrared Detectors and Instrumentation for Astronomy IX*, vol. 10708. SPIE, 2018, pp. 67–75.
- [3] G. W. Wilson, S. Abi-Saad, P. Ade, I. Aretxaga, J. Austermann, Y. Ban, J. Bardin, J. Beall, M. Berthoud, S. Bryan *et al.*, “The toltec camera: an overview of the instrument and in-lab testing results,” *Millimeter, Submillimeter, and Far-Infrared Detectors and Instrumentation for Astronomy X*, vol. 11453, p. 1145302, 2020.
- [4] E. Shirokoff, P. S. Barry, C. M. Bradford, G. Chattopadhyay, P. Day, S. Doyle, S. Hailey-Dunsheath, M. I. Hollister, A. Kovács, C. McKeeney *et al.*, “Mkid development for superspec: an on-chip, mm-wave, filter-bank spectrometer,” in *Millimeter, Submillimeter, and Far-Infrared Detectors and Instrumentation for Astronomy VI*, vol. 8452. SPIE, 2012, pp. 209–219.
- [5] A. Endo, J. Baselmans, P. van der Werf, B. Knoors, S. Javadzadeh, S. Yates, D. Thoen, L. Ferrari, A. Baryshev, Y. Lankwarden *et al.*, “Development of deshima: a redshift machine based on a superconducting on-chip filterbank,” in *Millimeter, Submillimeter, and Far-Infrared Detectors and Instrumentation for Astronomy VI*, vol. 8452. SPIE, 2012, pp. 253–267.
- [6] P. Barry, A. Anderson, B. Benson, J. Carlstrom, T. Cecil, C. Chang, M. Dobbs, M. Hollister, K. Karkare, G. Keating *et al.*, “Design of spt-slim focal plane; a spectroscopic imaging array for the south pole telescope,” *arXiv preprint arXiv:2111.04633*, 2021.
- [7] M. Mirzaei, E. M. Barrentine, B. T. Bulcha, G. Cataldo, J. A. Connors, N. Ehsan, T. M. Essinger-Hileman, L. A. Hess, J. W. Mugge-Durum, O. Noroozian *et al.*, “ μ -spec spectrometers for the exclaim instrument,” in *Millimeter, Submillimeter, and Far-Infrared Detectors and Instrumentation for Astronomy X*, vol. 11453. SPIE, 2020, pp. 128–139.
- [8] W. A. Phillips, “Tunneling states in amorphous solids,” *Journal of low temperature physics*, vol. 7, no. 3, pp. 351–360, 1972.
- [9] O. Noroozian, J. Gao, J. Zmuidzinas, H. G. LeDuc, and B. A. Mazin, “Two-level system noise reduction for microwave kinetic inductance detectors,” in *AIP Conference Proceedings*, vol. 1185, no. 1. American Institute of Physics, 2009, pp. 148–151.
- [10] J. Verjaaw, A. Potočnik, M. Mongillo, R. Acharya, F. Mohiyaddin, G. Simion, A. Pacco, T. Ivanov, D. Wan, A. Vanleenhove *et al.*, “Investigation of microwave loss induced by oxide regrowth in high-q niobium resonators,” *Physical Review Applied*, vol. 16, no. 1, p. 014018, 2021.
- [11] P. De Visser, J. Baselmans, P. Diener, S. Yates, A. Endo, and T. Klapwijk, “Number fluctuations of sparse quasiparticles in a superconductor,” *Physical review letters*, vol. 106, no. 16, p. 167004, 2011.
- [12] K. Dibert, P. Barry, Z. Pan, A. Anderson, B. Benson, C. Chang, K. Karkare, J. Li, T. Natoli, M. Rouble *et al.*, “Development of mkids for measurement of the cosmic microwave background with the south pole telescope,” *Journal of Low Temperature Physics*, pp. 1–9, 2022.
- [13] P. K. Day, H. G. LeDuc, B. A. Mazin, A. Vayonakis, and J. Zmuidzinas, “A broadband superconducting detector suitable for use in large arrays,” *Nature*, vol. 425, no. 6960, pp. 817–821, 2003.
- [14] P. Barry, “On the development of superspec: a fully integrated on-chip spectrometer for far-infrared astronomy,” Ph.D. dissertation, Cardiff University, 2014.
- [15] P. De Visser, J. Baselmans, P. Diener, S. Yates, A. Endo, and T. Klapwijk, “Generation-recombination noise: The fundamental sensitivity limit for kinetic inductance detectors,” *Journal of Low Temperature Physics*, vol. 167, no. 3, pp. 335–340, 2012.
- [16] R. McGeehan, P. Barry, E. Shirokoff, C. Bradford, G. Che, J. Glenn, S. Gordon, S. Hailey-Dunsheath, M. Hollister, A. Kovács *et al.*, “Low-temperature noise performance of superspec and other developments on the path to deployment,” *Journal of Low Temperature Physics*, vol. 193, no. 5, pp. 1024–1032, 2018.
- [17] M. Lisovenko, Z. Pan, P. Barry, T. Cecil, C. Chang, J. Hood, J. Li, V. Novosad, G. Wang, and V. Yefremenko, “Characterization of the superconducting microwave properties of aluminum manganese,” *Journal of Low Temperature Physics*, pp. 1–7, 2022.
- [18] D. P. Pappas, M. R. Vissers, D. S. Wisbey, J. S. Kline, and J. Gao, “Two level system loss in superconducting microwave resonators,” *IEEE Transactions on Applied Superconductivity*, vol. 21, no. 3, pp. 871–874, 2011.
- [19] J. Zmuidzinas, “Superconducting microresonators: Physics and applications,” *Annu. Rev. Condens. Matter Phys.*, vol. 3, no. 1, pp. 169–214, 2012.
- [20] S. Kumar, J. Gao, J. Zmuidzinas, B. A. Mazin, H. G. LeDuc, and P. K. Day, “Temperature dependence of the frequency and noise of superconducting coplanar waveguide resonators,” *Applied Physics Letters*, vol. 92, no. 12, p. 123503, 2008.
- [21] L. Swenson, P. Day, B. Eom, H. Leduc, N. Llombart, C. McKeeney, O. Noroozian, and J. Zmuidzinas, “Operation of a titanium nitride superconducting microresonator detector in the nonlinear regime,” *Journal of Applied Physics*, vol. 113, no. 10, p. 104501, 2013.
- [22] S. B. Kaplan, C. Chi, D. Langenberg, J.-J. Chang, S. Jafarey, and D. Scalapino, “Quasiparticle and phonon lifetimes in superconductors,” *Physical Review B*, vol. 14, no. 11, p. 4854, 1976.
- [23] C. Wilson and D. Prober, “Quasiparticle number fluctuations in superconductors,” *Physical Review B*, vol. 69, no. 9, p. 094524, 2004.
- [24] C. Wilson, L. Frunzio, and D. Prober, “Time-resolved measurements of thermodynamic fluctuations of the particle number in a nondegenerate fermi gas,” *Physical review letters*, vol. 87, no. 6, p. 067004, 2001.
- [25] R. Barends, S. Van Vliet, J. Baselmans, S. Yates, J. Gao, and T. Klapwijk, “Enhancement of quasiparticle recombination in ta and al superconductors by implantation of magnetic and nonmagnetic atoms,” *Physical Review B*, vol. 79, no. 2, p. 020509, 2009.
- [26] J. Gao, J. Zmuidzinas, A. Vayonakis, P. Day, B. Mazin, and H. Leduc, “Equivalence of the effects on the complex conductivity of superconductor due to temperature change and external pair breaking,” *Journal of Low Temperature Physics*, vol. 151, no. 1, pp. 557–563, 2008.
- [27] J. M. Martinis, M. Ansmann, and J. Aumentado, “Energy decay in superconducting josephson-junction qubits from nonequilibrium quasiparticle excitations,” *Physical review letters*, vol. 103, no. 9, p. 097002, 2009.
- [28] G. Catelani, J. Koch, L. Frunzio, R. Schoelkopf, M. H. Devoret, and L. Glazman, “Quasiparticle relaxation of superconducting qubits in the presence of flux,” *Physical review letters*, vol. 106, no. 7, p. 077002, 2011.

- [29] J. Zittartz, A. Bringer, and E. Müller-Hartmann, "Impurity bands in superconductors with magnetic impurities," *Solid State Communications*, vol. 10, no. 6, pp. 513–516, 1972.
- [30] A. Kaiser, "Effect of non-magnetic localized states in superconducting alloys," *Journal of Physics C: Solid State Physics*, vol. 3, no. 2, p. 410, 1970.
- [31] J. Rammer and A. Schmid, "Destruction of phase coherence by electron-phonon interactions in disordered conductors," *Physical Review B*, vol. 34, no. 2, p. 1352, 1986.
- [32] G. C. O'Neil, D. R. Schmidt, N. A. Tomlin, and J. N. Ullom, "Quasi-particle density of states measurements in clean superconducting almn alloys," *Journal of Applied Physics*, vol. 107, no. 9, p. 093903, 2010.
- [33] J. Deutz, P. Dederichs, and R. Zeller, "Local density of states of impurities in al," *Journal of Physics F: Metal Physics*, vol. 11, no. 9, p. 1787, 1981.