



LJMU Research Online

Omoregie, AI, Muda, K, Ong, DEL, Ojuri, OO, Bin Bakri, MK, Rahman, MR, Basri, HF and Ling, YE

Soil bio-cementation treatment strategies: state-of-the-art review

<http://researchonline.ljmu.ac.uk/id/eprint/19942/>

Article

Citation (please note it is advisable to refer to the publisher's version if you intend to cite from this work)

Omoregie, AI, Muda, K, Ong, DEL, Ojuri, OO, Bin Bakri, MK, Rahman, MR, Basri, HF and Ling, YE (2023) Soil bio-cementation treatment strategies: state-of-the-art review. Geotechnical Research. pp. 1-25.

LJMU has developed **LJMU Research Online** for users to access the research output of the University more effectively. Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Users may download and/or print one copy of any article(s) in LJMU Research Online to facilitate their private study or for non-commercial research. You may not engage in further distribution of the material or use it for any profit-making activities or any commercial gain.

The version presented here may differ from the published version or from the version of the record. Please see the repository URL above for details on accessing the published version and note that access may require a subscription.

For more information please contact researchonline@ljmu.ac.uk

<http://researchonline.ljmu.ac.uk/>

Cite this article

Omoregie AI, Muda K, Ong DEL et al.
Soil bio-cementation treatment strategies: state-of-the-art review.
Geotechnical Research,
<https://doi.org/10.1680/jgere.22.00051>

Review Paper

Paper 2200051
Received 31/08/2022; Accepted 26/01/2023

Published with permission by the ICE under the
CC-BY 4.0 license.
(<http://creativecommons.org/licenses/by/4.0/>)

Soil bio-cementation treatment strategies: state-of-the-art review

1 Armstrong Ighodalo Omoregie PhD

Postdoctoral Researcher, Department of Water and Environmental Engineering, School of Civil Engineering, Faculty of Engineering, Universiti Teknologi Malaysia, Johor Bahru, Malaysia (Orcid:0000-0002-6356-9638) (corresponding author: adaloomoregie@gmail.com)

2 Khalida Muda PhD

Professor, Department of Water and Environmental Engineering, School of Civil Engineering, Faculty of Engineering, Universiti Teknologi Malaysia, Johor Bahru, Malaysia (Orcid:0000-0001-7285-7044)

3 Dominic Ek Leong Ong PhD

Associate Professor, School of Engineering and Built Environment, Griffith University, Brisbane, Australia (Orcid:0000-0001-8604-8176)

4 Oluwapelumi Olumide Ojuri PhD

Senior Lecturer, Built Environment and Sustainable Technologies Research Institute, Liverpool John Moores University, Liverpool, UK (Orcid:0000-0003-2543-2304)

5 Muhammad Khusairy Bin Bakri PhD

Postdoctoral Research Associate, Composites Materials and Engineering Center, Washington State University, Pullman, WA, USA (Orcid:0000-0003-1971-2350)

6 Md. Rezaur Rahman PhD

Senior Lecturer, Department of Chemical Engineering and Energy Sustainability, Faculty of Engineering, Universiti Malaysia Sarawak, Kota Samarahan, Malaysia (Orcid:0000-0002-7151-0687)

7 Hazlami Fikri Basri PhD

Senior Lecturer, Department of Water and Environmental Engineering, School of Civil Engineering, Faculty of Engineering, Universiti Teknologi Malaysia, Johor Bahru, Malaysia (Orcid:0000-0002-3398-1832)

8 Yong Ee Ling PhD

Senior Lecturer, Department of Water and Environmental Engineering, School of Civil Engineering, Faculty of Engineering, Universiti Teknologi Malaysia, Johor Bahru, Malaysia (Orcid:0000-0003-4367-3988)



Bio-cementation is a new sustainable approach that has gained popularity due to its low energy and carbon dioxide footprint compared with those of existing technologies for geotechnical and geoenvironmental engineering applications. Bio-cementation is a soil improvement technique that involves binding the pore space of soil particles with calcium carbonate minerals by microbially induced carbonate precipitation (MICP) and filling the soil pore space. The purpose of this paper is to present the current state of the art and a comprehensive discussion on the development of bio-cementation for soil improvement/reinforcement. Premixing, injection, immersing and surface percolation are identified as four distinct bio-cementation treatment techniques. Furthermore, scholars have reported employing ureolytic bacteria such as *Sporosarcina pasteurii*, *Bacillus sphaericus* and *Lysinibacillus sphaericus* isolated from corals, limestone caves, soils, waste materials, seawater and other sources to accomplish effective bio-cementation. Some of the major issues (bacterial cultivation costs and ammonium production) that impede its industrial potential and promising remedial techniques are also discussed. This state-of-the-art review also discusses the benefits and drawbacks of bio-cementation compared with traditional approaches. The significance of enzyme-induced carbonate precipitation as a soil bio-cementation alternative to MICP is also highlighted. Finally, the sustainable procedure, bio-cementation principles and future implications are discussed.

Keywords: biomineralisation/circular economy/ground improvement/microstructure/soil stabilisation/sustainable development

Introduction

The bio-cementation process occurs at ambient temperature, is low energy and has a minimal carbon dioxide (CO₂) footprint ('carbon footprint') compared with conventional cement

manufacturing (Ivanov *et al.*, 2015; Myhr *et al.*, 2019). Instead of using pyro-processing technology to produce cementitious building materials, bio-cementation is an alternative method for improving soil engineering properties by using microorganisms

and their products (e.g. enzymes and biominerals) (Omoregie *et al.*, 2016). Geological conditions often impact the design of infrastructure projects such as tunnelling (Choo and Ong, 2020; Peerun *et al.*, 2020), road construction (Sun *et al.*, 2021; Zhalehjoon *et al.*, 2018), subgrade stabilisation (Liu *et al.*, 2022; Luis *et al.*, 2019) and ground improvement (Fatehi *et al.*, 2021; Omoregie *et al.*, 2017). Globally, the building and construction sector consumes a large amount of global energy and continues to contribute to climate change through its greenhouse gas (GHG) emissions. Therefore, it is important to focus on developing environmentally friendly materials and processes. Additionally, urbanisation and infrastructure development have generated a lot of environmental waste and pollution (Ojuri *et al.*, 2022).

Sustainable options for manufacturing construction materials are a top priority due to the need to reduce GHG emissions and the air pollution associated with cement production (Farajnia *et al.*, 2022). The construction industry needs a built environment with fewer cement-based materials and more environmentally friendly and innovative construction technologies (Mirkouei *et al.*, 2017; Scrivener *et al.*, 2018). If appropriate environmental actions are not taken, the construction industry will contribute significantly to GHG emissions, resource depletion and landfill overflow. In recent decades, the use of cement alternatives such as bio-cementation for soil improvement has increased due to the need for net-zero carbon dioxide emission construction practice (Kahani *et al.*, 2020). As a result, researchers from various disciplines, such as biotechnology, chemical engineering, geoscience, environmental engineering and civil engineering, are increasingly using bio-cementation for soil improvement and other important applications. The bio-cementation treatment technique uses microbially induced carbonate precipitation (MICP) to produce calcium carbonate (CaCO_3) to increase the strength and rigidity of granular soil. It also can be applied at a large scale (Figure 1). The bio-cementation process significantly improves the interface shear strength of geo-structures, according to assessment trials, with an interface efficiency factor of at least 2 and up to 7. Friction piles, earth-retaining structures, strengthened slopes and embankments may benefit from this eco-friendly soil improvement technique (Mortazavi *et al.*, 2021).

The efficiency of calcium carbonate precipitation is primarily determined by factors such as biological (enzymatic activity), chemical (cementation ingredients and concentration) and physical factors (soil nature) (Omoregie *et al.*, 2021). While bio-cementation technology is becoming more popular, several factors still need to be standardised to optimise bacterial activity and allow real-time implementation of the method in a variety of planned operations (Hadi *et al.*, 2022). In addition, while there have been many publications on the use of ureolytic bacteria in calcium carbonate precipitation, the appropriate nutrients required to promote microbial activity and high biomass production (Lapierre *et al.*, 2020) and specific MICP conditions that help target desired calcium carbonate polymorphs during bio-cementation are yet to be established (Mokhtar *et al.*, 2021). To



Figure 1. A sandbox (10 m^3) was subjected to bio-cementation treatment. (a) Front view of the treated soil mass after an outdoor trial treatment; (b) rear view of the treated soil mass

be feasible and practical at the field level, certain conditions are necessary. Another key issue to consider is bio-cementation life-cycle assessment (LCA), which is used to evaluate the environmental impact of any product. LCA quantifies and assesses the inputs and outputs that affect the environmental performance of a product, process or activity throughout its life cycle (Le *et al.*, 2019). Therefore, LCA supports a more sustainable planning process and practice. Al-Gheethi *et al.* (2022) recently conducted a comparative study of the health of raw materials and their environmental impact on bio-cementation. Al-Gheethi *et al.* (2022) reported that calcium acetate ($\text{Ca}(\text{CH}_3\text{COO})_2$) (the calcium source required for calcium carbonate precipitation) contributes nearly 60% to ozone layer depletion, while urea ($\text{CO}(\text{NH}_2)_2$) (which is a substrate for catalysing urease production and calcium carbonate precipitation) and molasses (a nutrient source for bacterial cultivation) contribute 38% and 13% to marine eutrophication, respectively. However, it would be helpful to know the health and environmental impact of calcium chloride (CaCl_2) and yeast extract, which are the commonly used reagents in bio-cementation.

During the bio-cementation process, the extracellular polymeric substances (EPSs) released by bacterial cells increase the calcium carbonate that fills the sand pores and improves sand solidification. The EPSs bind the soil particles together, creating a more stable and cohesive soil structure. The microstructure of bio-cemented soil is characterised by the presence of EPSs, which form a network of filaments and strands throughout the soil (Figure 2). This network helps bind the soil particles together and improves the mechanical strength and stability of the soil. The

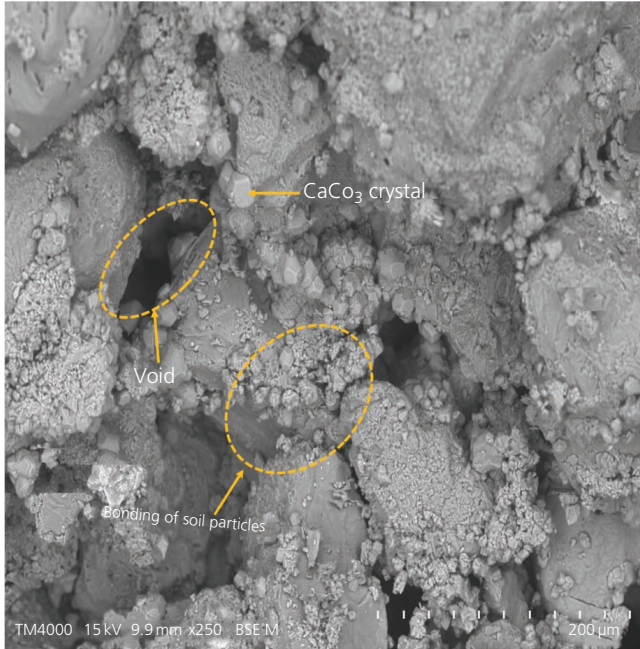


Figure 2. Scanning electron microscopic image showing calcium carbonate formations in a soil specimen and interparticle contact bonding after soil bio-cementation treatment

engineering properties such as reduced hydraulic conductivity, reduced porosity, better shear strength and improved stiffness and unconfined compressive strength (UCS) (Gomez *et al.*, 2018).

The improvement of soil engineering properties by calcium carbonate crystal precipitation with the attendant low GHG production demonstrates that soil bio-cementation is an environmentally advantageous strategy that should be considered in the present construction era (Charpe *et al.*, 2019). As a result, researchers are exploring the use of inorganic cementitious materials during MICP to cement loose soil particles during various treatment phases (Yu and Rong, 2022). Researchers are also seeking appropriate reagents to ensure that adequate cementitious materials are precipitated for effective soil reinforcement. Xiang *et al.* (2022) recently suggested that calcium acetate should be used in future bio-cementation studies because it reduces ammonia (NH₃) emissions by 54% compared with standard bio-cementation that uses calcium chloride as a calcium source, resulting in a cleaner bio-cement production method. They also observed that the unit prices of these two chemicals are comparable (US\$5.3/kg for calcium chloride and US\$5.5/kg for calcium acetate) (Xiang *et al.*, 2022).

MICP process is typically carried out with active bacterial cells after being grown in a suitable medium. Once the bacterial culture has been prepared, its ability to produce urease is determined before the bacteria are mixed with the cementation solution and applied to the soil (Figure 3). The biomineral precipitates formed in the solution or soil columns can act as a binding agent. The MICP process for bio-cementation can result in improved soil

Bio-cementation is generally effective in improving the stability and strength of sandy and silty soil. The efficiency of bio-cementation in enhancing the qualities of clayey soil and loamy soil, on the other hand, varies depending on the kind and condition of the soil and the individual microorganisms used. Furthermore, factors such as the pH and moisture content of the soil and the presence of additional soil additives or contaminants may influence the efficiency of bio-cementation. However, a growing body of research in the literature investigates the utility of bio-cementation for clayey and loamy soils. Overall, bio-

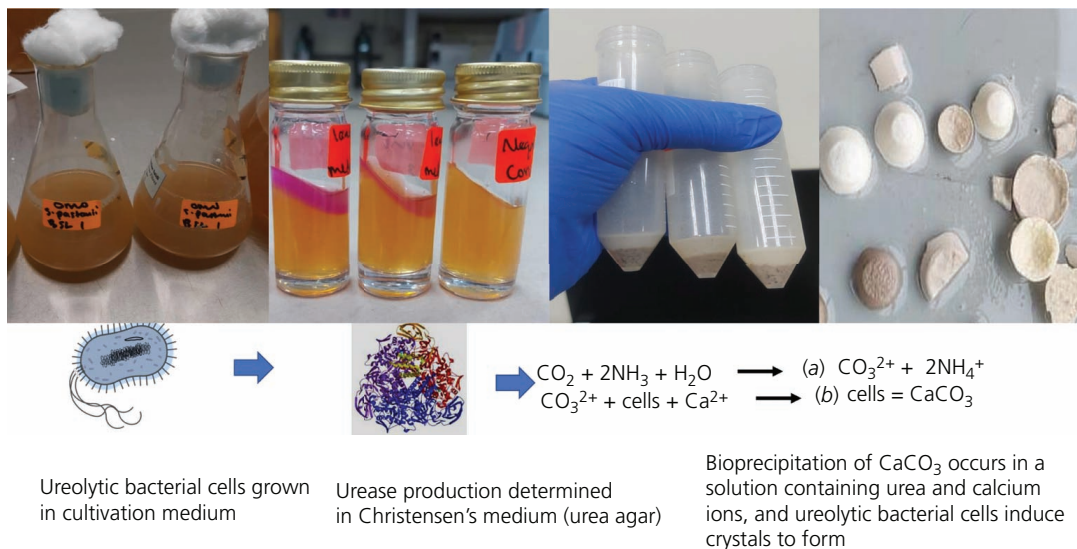


Figure 3. Simplified illustrative process of MICP



cementation can be a useful strategy for improving the quality of clayey soils. However, further research is needed to understand fully its benefits and limitations in various soil types and situations.

Many scholars have addressed important parameters that influence bio-cementation treatment and the MICP mechanism, including its potential treatment procedures, ureolytic bacteria, various biological pathways for acquiring calcium carbonate precipitates, optimal soil improvement conditions and some environmental challenges faced by this technology (Achal *et al.*, 2015; Al-Salloum *et al.*, 2017; Arias *et al.*, 2017a; De Muynck *et al.*, 2010; Omoregie *et al.*, 2021; Osinubi *et al.*, 2020; Tang *et al.*, 2020). This state-of-the-art review provides a comprehensive overview of bio-cementation technology for soil fixation and improvement, including a thorough examination of the mechanism of urease-mediated calcium carbonate mineralisation and various bio-cementation soil improvement treatment methods. It also covers methods for reducing the cost of the growth medium for large-scale bacterial production, environmental safety concerns with bio-cementation and durability issues with MICP performance. The review also outlines potential MICP applications.

Bioprecipitation of calcium carbonate through the ureolysis-driven MICP process

Among the various MICP methods/techniques (e.g. photosynthesis, ureolysis (urea hydrolysis), sulfate reduction, ammonification and denitrification (nitrate reduction)), ureolysis appears to be the simplest pathway for microorganisms to exploit their environmental conditions and aid carbonate precipitation (Al-Salloum *et al.*, 2017). When suitable ureolytic bacterial cells such as *Sporosarcina pasteurii* (also known as *S. pasteurii*) are supplied with urea and a calcium source (e.g. calcium chloride) in a solution, several biogeochemical reactions occur. During the ureolysis process, urease (Enzyme Commission number: 3.5.1.5) produced by the bacterial cells breaks down urea into ammonia and carbamate acid (NH_2COOH), which instantaneously hydrolyses to form ammonia and carbonic acid (H_2CO_3) as shown in Equations I and II (Shougrakpam and Trivedi, 2021; Svane *et al.*, 2020). This reaction is followed by ammonia, resulting in the formation of ammonium (2NH_4^+) and hydroxide (2OH^-) ions (Hadi *et al.*, 2022) (Equation III). Carbonic acid forms a bicarbonate (HCO_3^-) ion in the aqueous solution, as shown in Equation IV (Stocks-Fischer *et al.*, 1999). The production of hydroxide ions increases the pH level of the solution. These occurrences cause a shift in bicarbonate equilibrium and subsequently form carbonate (CO_3^{2-}) ions (Equation V) (Gomez *et al.*, 2018). It is carbonic anhydrase (Enzyme Commission number: 4.2.1.1) rather than the urease enzyme that converts carbonic acid to carbonate ions (Omoregie *et al.*, 2022a). The negatively charged cell walls of ureolytic microorganisms attract the positively charged calcium (Ca^{2+}) ions (i.e. calcium chloride) to their cell surface, thus allowing the formation of a nucleation site and the precipitation of calcium carbonate. The calcium ions present in the solution then react with carbonate ions to produce

calcium carbonate crystals, leading to bio-cementation (Equation VI) (Mujah *et al.*, 2017).



Ureolytic microorganisms are widely distributed and have been isolated from many sources, as shown in Table 1. These microbes, sourced from various places such as caves, soils, corals and seawater, serve as microbial agents for MICP applications. Urease activity is determined by measuring the relative conductivity changes in a solution containing urea (1.0–1.5 M) and bacterial cultures at room temperature. One unit of urease activity is defined as the amount of enzyme that catalyses the breakdown of 1 mM urea per minute (Omoregie *et al.*, 2022a). These ureolytic microorganisms can treat beach erosion caused by wave scouring due to climate change, improve soil fixation and solidification and sequester harmful heavy metals, among other applications. The ureolytic microbial species necessary for the MICP process are mostly non-pathogenic, making them easy to cultivate and implement. This has made the MICP process recognised as a green engineering practice for various applications (e.g. surface stabilisation, dust control, coastal and monumental protection, soil liquefaction mitigation and erosion control) (Gowthaman *et al.*, 2022). The ureolysis-driven MICP process speeds up the rate of bio-cementation, allowing calcium carbonate precipitation to occur within a relatively short period.

The crystalline structure of calcium carbonate formed by ureolytic bacterial species results in polymorphs such as calcite, vaterite and aragonite. The process begins with the formation of amorphous calcium carbonate, which plays a crucial role in biomineralisation (Enyedi *et al.*, 2020). The formation of other calcium carbonate polymorphs follows this. The result of calcium carbonate crystallisation can be influenced by various biological factors (e.g. bacterial strain and cell concentration), chemical factors (e.g. cementation reagents and purity level) and environmental factors (e.g. pH and temperature). Calcite is the most thermodynamically stable calcium carbonate polymorph under normal conditions and provides the best results for bio-

Table 1. List of ureolytic microorganisms isolated from various sources for MICP applications

Ureolytic microorganism	Sampling location	Urease activity	Calcium carbonate crystalline phase	Reference
<i>Citrobacter freundii</i> and <i>Pseudomonas azotoformans</i>	Soils from Beni Suef City, Egypt	45.5 and 54.9 U/ml	Calcite and aragonite	Abdel-Aleem <i>et al.</i> (2019)
<i>Bacillus</i> sp. CR2	Mine tailing soil from Urumqi, Xinjiang, China	389–432 U/ml	Aragonite and vaterite	Achal and Pan (2014)
<i>Brevundimonas</i> sp.	Soil from a mining site in Fengxian, China	Nil	Vaterite	Ali <i>et al.</i> (2022)
<i>Rhodococcus erythropolis</i> TN24F strain	Water and sediment from San Pedro de Atacama, northern Chile	Nil	Monohydrocalcite, struvite and halite	Arias <i>et al.</i> (2017b)
<i>Staphylococcus edaphicus</i>	Peatland soils from Hokkaido, Japan	Nil	Calcite	Chen <i>et al.</i> (2021)
<i>Sporosarcina soli</i> , <i>S. siberinis</i> , <i>S. pasteurii</i> and <i>Pseudogracilibacillus auburnensis</i>	Soil from the Brahmaputra riverbank in Guwahati, Assam, India	3–9.7 mM urea hydrolysed/ min/OD ₆₀₀	Calcite	Dubey <i>et al.</i> (2021)
<i>Lysinibacillus</i> sp.	Saline soil from a paddy field in Surin, Thailand	Nil	Calcite or aragonite	Ekprasert <i>et al.</i> (2020)
<i>Stenotrophomonas maltophilia</i> , <i>Bacillus simplex</i> and <i>Rhodococcus degradans</i>	Water samples from Baradla cave, Hungary	Nil	Amorphous calcium carbonate and calcite	Enyedi <i>et al.</i> (2020)
<i>Alkalibacterium iburiense</i> EE1 strain	Sandy soils from coastal regions in Egypt	20 mmol urea hydrolysed/min	Calcite	Ezzat and Ewida (2021)
<i>Penicillium chrysogenum</i> CS1 strain	Cement sludge, China	42.8 U/ml	Calcite	Fang <i>et al.</i> (2018)
<i>Bacillus</i> sp. AF1 strain	Desert soils from Yazd and Isfahan Provinces of Iran	Nil	Calcite	Farajnia <i>et al.</i> (2022)
<i>Psychrobacillus</i> sp.	Expressway slope soil from Hokkaido, Japan	0.10 and 0.41 U/ml	Calcite	Gowthaman <i>et al.</i> (2019)
<i>Sporosarcina siberiensis</i>	Sediment and water from the Altiplano of northern Chile	5.0 and 5.5 mM hydrolysed urea/min	Calcite	Marín <i>et al.</i> (2021)
<i>S. pasteurii</i> strains	Limestone cave, Sarawak, Malaysia	24.66–39.21 mM urea hydrolysed/ min/OD ₆₀₀	Nil	Omeregje <i>et al.</i> (2017)
<i>Pseudomonas</i> sp.	Activated sludge from the Xi'an wastewater-treatment plant, China	Nil	Nil	Wang <i>et al.</i> (2021a)
<i>Aneurinibacillus tyrosinisolvans</i>	Gold-smelting plant in Baotou, inner Mongolia Autonomous Region, China	Nil	Calcite	Wang <i>et al.</i> (2021b)
<i>Variovorax boronicumulans</i> and <i>Stenotrophomonas rhizophila</i>	Mine calcareous soils, Iran	1.65 and 0.85/ml	Nil	Jalilvand <i>et al.</i> (2020)
<i>Lysinibacillus</i> sp. WH strain	Saline soil from a paddy field in Surin Province, Thailand	Nil	Calcite	Ditta <i>et al.</i> (2022)
<i>Lysinibacillus boronitolerans</i> YS11 and <i>Bacillus</i> sp. AK13 strains	Soil from Seongbukche, South Korea	Nil	Nil	Lee and Park (2019)
<i>Bacillus</i> sp.	Soil from Magu Town, Guizhou Province, China	0.83 mmol/min/OD ₆₀₀	Nil	Zhao <i>et al.</i> (2017)
<i>Bacillus thuringiensis</i>	Deep-sea sediment from Barren Island coast, India	554.03 U/ml	Calcite	Rangamaran and Shanmugam (2019)
<i>Aspergillus sydowii</i> and <i>Bacillus</i> sp. DB-6 strains	Coal samples from Tai'an City, Shandong Province, China	0.31–3.24 mM urea hydrolysed/min	Vaterite and calcite	Fan <i>et al.</i> (2020)
<i>Acinetobacter guillouiae</i> and <i>Staphylococcus caprae</i>	Soil and coal from Pinglu District, Shuozhou City, Shanxi Province, China	7.44–7.63 mM urea hydrolysed/min	Vaterite	Song <i>et al.</i> (2021)
<i>S. pasteurii</i> , <i>Atopostipes suicloacalis</i> and <i>Pseudomonas caeni</i> strains	Carbide sludge from the acetylene production industry in Singapore	3–6 U/ml	Calcite	Yang <i>et al.</i> (2022)
<i>Bacillus muralis</i> , <i>B. lentus</i> , <i>B. simplex</i> , <i>B. firmus</i> and <i>B. licheniformis</i>	Alkaline soil, Nigeria	Nil	Nil	Šovljanski <i>et al.</i> (2022)

Note: OD₆₀₀, optical density measured at a wavelength of 600 nm; U, units

cementation. Amorphous calcium carbonate is the least stable calcium carbonate polymorph, but it can quickly transform into crystalline calcium carbonate minerals under certain conditions

(Enyedi *et al.*, 2020). While many test tube experiments have shown the formation of vaterite or aragonite crystal states, MICP studies in soil columns typically result in calcite crystal formation.

Many ureolytic bacterial species, including *Helicobacter pylori* and *Streptococcus salivarius*, rely on urease to adapt to their environment. For example, *S. salivarius* produces urease by using salivary urea as a nitrogen source while avoiding acid stress (Chen *et al.*, 2000). Microbial urease is encoded by the urease gene cluster *UreABCEFGD*, which is critical for ureolysis (Debowski *et al.*, 2017). The *ureC*, *ureB* and *ureA* genes encode the subunits that make up the apoenzyme, while the *ureEFGD* genes code for auxiliary proteins (Zhou *et al.*, 2019). It has been observed that these seven genes, which are involved in urease assembly and activation, are present in the genome of ureolytic microorganisms (i.e. *S. pasteurii*) as a gene cluster (Svane *et al.*, 2020). Urease enzymatic activity is activated only when nickel (Ni) is introduced into the active regions of the accessory proteins. Additional ancillary proteins, including *ureD*, *ureF*, *ureG* and *ureE*, are essential for creating catalytically active urease and enabling proper folding and assembly (Farrugia *et al.*, 2013). Furthermore, other genes encode nickel permeases (e.g. *ureH* or *ureJ*) or urea transporters (Veaudor *et al.*, 2019). Due to the variety of supplementary roles, there are several urease gene clusters, each with its function.

During biofilm formation, urease genes are heavily transcribed (Debowski *et al.*, 2017). It is important to understand the metabolic actions of these urease genes, as they can be used to improve urease efficiency in the biomineralisation process in the future. The ureolytic activity performance for calcium carbonate precipitation can be boosted by adding supplementary nickel and urease transporter genes (Hoffmann *et al.*, 2021). The more strongly this metabolic activity changes supersaturation conditions, the more likely precipitation will occur. Alterations to the composition of urease genes significantly affect the urease activity and calcite precipitation ability of microbial cells (Hoffmann *et al.*, 2021). The crystal structure of urease exhibits a pair of non-equivalent nickel atoms, with about 3.5 Å between Ni1 and Ni2 (Yu *et al.*, 2022). The nickel atom is connected to two histidine residues in the protein, and one carbamylated lysine binds the two nickel atoms. Water molecules at both ends converge to form a spherical shape, with Ni1 producing a distorted tetragonal pyramid structure and Ni2 making an asymmetric octahedral structure (Yu *et al.*, 2022). Therefore, these two nickel atoms play distinctive roles in the ureolysis reaction.

Optimising and regulating MICP through genetic engineering will provide valuable knowledge. In addition to metabolism, the surfaces of bacteria also play a role in mineral precipitation (Hoffmann *et al.*, 2021). Functional groups such as carboxyl and phosphate groups control surface charge. Teichoic acids, which have many phosphate groups in their backbone and hence have a negative charge, represent a significant portion of the surface charge in Gram-positive bacteria (Brown *et al.*, 2013). The microbial surface charge of ureolytic microorganisms plays a critical role in forming calcium carbonate (Gat *et al.*, 2014). It was reported that *S. pasteurii* has a zeta potential of 67 mV, while some non-calcium carbonate-precipitating bacteria (i.e. *Bacillus*

subtilis and *Escherichia coli*) have a range of potentials between 26 and 41 mV (Gat *et al.*, 2014). This means that *S. pasteurii* has a higher negative surface charge than these non-mineralising bacteria. *S. pasteurii* has a substantially higher negative surface charge than other non-mineralising bacteria, even without urea, which suggests that it has more negative functional groups on its surface. Furthermore, it is also essential for their digestive activity and the generation of soil bubbles. Bio-cementation is also considered a consolidation technique that improves soil strength by converting the soil from fully saturated condition to partially saturated. It may also help bind more metal ions, such as calcium ions, in the same ionic environment (Ma *et al.*, 2020). Biofilms, which extend beyond the immediate cell surface, create an extracellular environment that may facilitate precipitation by trapping ions and providing favourable functional groups for the crystal nucleation (Hoffmann *et al.*, 2021).

Bio-cementation treatment strategies

Submerged treatment method

The submerged treatment method, also known as immersing or soaking (Figure 4), has previously been proposed for in situ soil improvement of submerged or undersea sediments (Cheng and Cord-Ruwisch, 2012). Some researchers have suggested that to immerse soil samples fully in MICP treatment solution, a flexible geotextile mould may be necessary for sample processing (Zhao *et al.*, 2014b). However, most studies on soil bio-cementation use syringes, test tubes or cubic or cylindrical columns as mould specimens. There is no evidence to suggest that this procedure is equivalent to the treatment of submerged or undersea sediments. This submerged treatment method seems more suitable for bio-concrete production or crack repairs, as calcium carbonate precipitates often from within and on the outer part of soil columns (Khan *et al.*, 2021; Manzur *et al.*, 2017, 2019).

In a study, soil columns were immersed in a mechanically powered tank reactor containing 85 ml of *S. pasteurii* and cementation solution (Zhao *et al.*, 2014a). The bacterial cells had an optical density (OD) of 0.3–1.5. According to the soil MICP test by Zhao *et al.* (2014a), cementation precipitates dispersed from higher- to lower-concentration locations in the analysed soil specimens. The researchers also obtained UCS values ranging from 1.76 to 2.04 MPa, indicating that this treatment strategy stabilises soil. Zhao *et al.* (2014a) also showed that treating soil specimens prepared in a full-contact flexible geotextile mould resulted in a significantly more uniform bio-cemented soil sample and the development of homogeneous calcium carbonate residues inside the soil particles. Therefore, this method can help prevent the formation of common bio-clogs during MICP treatments.

Wen *et al.* (2019) used a full-contact flexible mould developed by Zhao *et al.* (2014a) as a column for their soil specimen (200 g/m²). The full-contact flexible mould had an opening size of 0.15 mm, a water flow rate of 34 mm/s and a thickness of 1.5 mm. The study by Wen *et al.* (2019) aimed to determine the

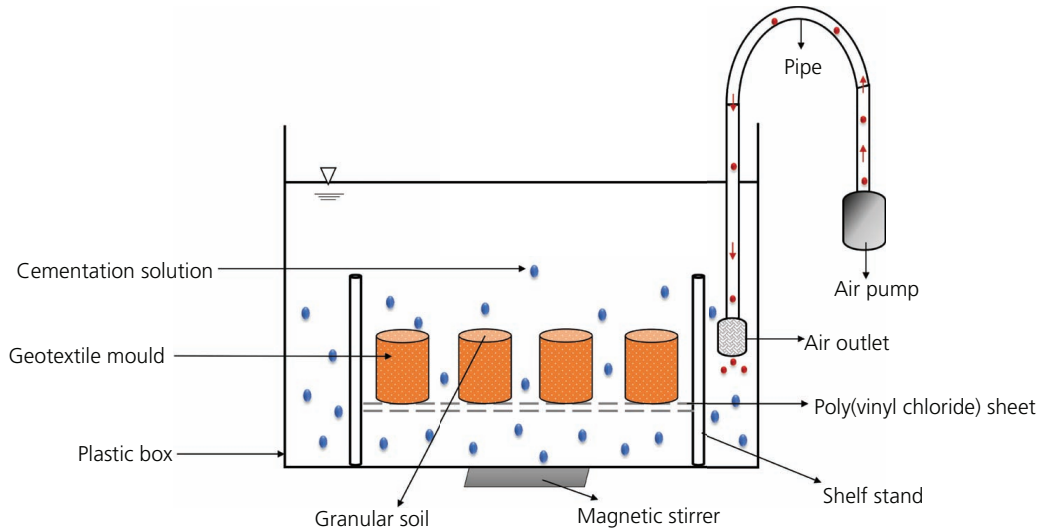


Figure 4. Illustrative diagram of soil bio-cementation using the submerged treatment method. This illustration was adapted from previous studies by Zhao *et al.* (2014a) and Liu *et al.* (2021)

effectiveness of the submerged treatment method and various concentrations of cementation solution on the mechanical properties of soil. Wen *et al.* (2019) found that soil bio-cementation could be significantly improved under specific concentrations of cementation (i.e. 0.25–0.75 M) with repeated treatments, with a UCS of 6400 kPa, which was higher than the values obtained by Zhao *et al.* (2014a). Gao *et al.* (2019) studied the mechanical behaviour of soil at various cementation levels and relative densities. The sand specimens were housed in cylindrical moulds (100 mm height and 50 mm diameter) with bottom covers. *S. pasteurii* procured from the China General Microbiological Culture Collection Center (CGMCC), designated strain CGMCC 1.3687, was cultivated for 24 h to achieve urease activity ranging from 6.66 to 11.10 mM urea hydrolysed/min. This study used cementation components of identical molarity (0.5 mol/l) of urea and calcium chloride (according to stoichiometry). Before adding and uniformly compacting dry sand, the treatment liquid (100 ml) containing a 1:1 volume ratio of bacterial culture and cementation solution was placed in the mould. The treatment was maintained for 3 days, and the researchers found that MICP treatment was effective, significantly improving soil strength and reducing deformation. The triaxial test also showed improved MICP treatment performance at various relative density levels.

Surface percolation treatment method

The second method of soil bio-cementation is termed ‘surface percolation treatment’ or ‘spraying’, shown in Figure 5. It allows the entry of cementation fluid and bacterial cultures to penetrate the soil matrix. It is used with simple pouring or spraying procedures with the help of gravitational flow and capillarity (Cheng and Shahin, 2016). Percolating the treatment fluid through free-draining soil resulted in similar or improved uniformity of

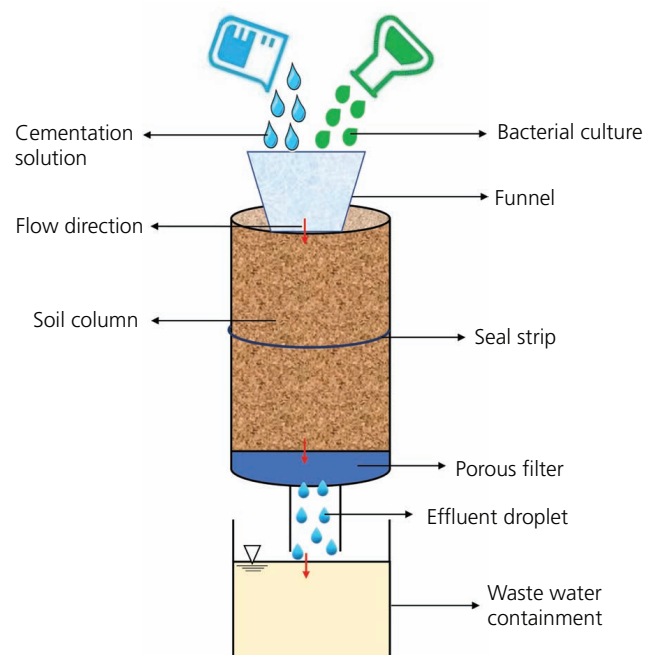


Figure 5. Illustrative diagram of soil bio-cementation through the surface percolation treatment method. This illustration was adapted from MICP experiments performed by Omoregie *et al.* (2019) and Hoang *et al.* (2020)

cementation distribution within the soil matrix compared with soil specimens subjected to the pressure injection treatment method (Ghasemi and Montoya, 2020; Montoya *et al.*, 2013; Omoregie *et al.*, 2019). The treatment is typically performed from the surface region of the granular soil. The main advantage of using this treatment method for soil solidification is its simplicity.

Introducing the cementation solution and bacterial culture does not require heavy machinery due to the easy flow movement of the fluid (Mujah *et al.*, 2017).

This method is an inexpensive, simple and practical soil bio-cementation treatment (Omeregic *et al.*, 2017). However, surface percolation is not often selected for soil bio-cementation, requiring treatment at a metre-scale depth. MICP treatment through surface percolation has increasingly been employed for erosion mitigation and stabilisation of sandy slopes under unsaturated conditions (Kou *et al.*, 2021). Because of its ease of administration onto the soil body and ability to cement soil surfaces successfully, some researchers have adopted this technique for soil bio-cementation.

Furthermore, this method creates a more manageable treatment environment for an injection scheme (i.e. arrays of injection and extraction wells) (Montoya *et al.*, 2013). Cheng and Cord-Ruwisch (2012) were among the first to study the productive potential of surface percolation for soil bio-cementation. Their research compared surface percolation with submerged treatment methods. Cheng and Cord-Ruwisch (2012) revealed that alternating *Lysinibacillus sphaericus* cultures or the cementation solution (i.e. equimolar concentrations of 1 M for calcium chloride and urea) might complete the bio-cementation process in the soil column (1 m). Their obtained UCS and calcium carbonate content resulting from the soil column subjected to surface percolation treatment were 390 kPa and 0.12 g/cm³, respectively. In contrast, UCS and calcium carbonate content findings from samples subjected to the submerged treatment method were 340 kPa and 0.14 g/cm³, respectively.

Ghasemi and Montoya (2020) discovered that the maximum calcium carbonate precipitation was concentrated in the upper 5 cm depth and decreased with depth. However, measured values for the mass reached 1% at a depth of 18–20 cm, despite the decrease in concentration with depth. Also, the maximum mass (5–5.5%) of calcium carbonate was concentrated at the surface region, which was not surprising for MICP treatment with the surface percolation method. Ghasemi and Montoya (2020) also acknowledged that industrial-grade chemicals for MICP treatment made this method a cost-effective and viable replacement for traditional soil stabilisation methods. Omeregic *et al.* (2019) investigated technical-grade cultivation media and cementation ingredients to replace standard laboratory-grade ones for MICP application. They found that the cost of this treatment method when using technical-grade cementation solutions (0.25–1.0 M) ranged from US\$0.07/l to US\$0.26/l, while that when using analytical-grade reagents ranged from US\$3.33/l to US\$13.29/l. Despite the significant cost difference (47- to 51-fold), results from the MICP tests showed comparable outcomes for surface strength (11 448.00 ± 69.00 to 4826.00 kPa) and calcium carbonate content (5.56 ± 1.15 to 33.24 ± 0.59%). Karimian *et al.* (2021) studied the impact of the surface percolation treatment technique on sand strength improvement and microstructure.

Karimian *et al.* (2021) procured ureolytic bacteria from the Persian Type Culture Collection (PTCC). *S. pasteurii* strain PTCC 1645 and cementation solution (100 ml) were used to percolate a mould tubing (internal diameter of 5 cm, length of 10 cm) with gravity at a flow rate of about 3 l/h. The MICP treatment was repeated for 10 days, and the results showed that the strength (18–324.47 kPa) of the treated soil depended on the location of the crystal formation, the particle binding site and calcium carbonate contents (3.0–12.6%). They obtained heterogeneous measurements of UCS and calcium carbonate contents along specimen lengths, while the calcium carbonate contents were less variable in the horizontal direction.

Pressure injection treatment method

The pressure injection treatment method is also referred to as the flushing or injection treatment method (Figure 6). There are two types of pressure injection treatment methods: stop-flow pressure injection and continuous-flow pressure injection. The stop-flow approach is more effective than continuous-flow pressure injection because it achieves more homogeneity of calcium carbonate generation throughout the depth of the soil columns (Barkouki *et al.*, 2011). Because it necessitates the injection of a significant volume of treatment fluids, this technique is best suited for large-scale, field-scale MICP investigations (Gomez *et al.*, 2016).

Due to the efficient transmission of cementation fluid, the injection technique can readily be applied to firm soil layers at greater depths. Martinez *et al.* (2013) studied 50 cm long sand columns using peristaltic pumps to maintain one-direction flow conditions. They observed non-uniform calcium carbonate distribution along the treated soil column, which is common with this treatment method. Martinez *et al.* (2013) discovered that most of the calcium carbonate content was generated around the injection zone, impeding the cementation process in the deeper part of the column. Treatment fluids are supplied under pressure to guarantee that the solutions are dispersed into the soil columns at controlled flow rates. To achieve successful fluid fixation and spatial distribution of calcium carbonate content within soil columns, injection procedures, chemical concentration, bacterial biomass concentration, injection flow rates and pH levels must be optimised. Harkes *et al.* (2010) previously reported the use of a two-phase pressure injection procedure (i.e. injection of bacterial culture followed by injection of the cementation solution) earlier developed by Whiffin (2004) to promote bacterial cell retention and spatial distribution of calcium carbonate during the treatment process.

Harkes *et al.* (2010) injected a culture of diluted ureolytic bacterial cells with an OD of 2.88 and urease activity of 3.1 mS/min into a soil column. The column was positioned vertically, followed by the introduction of the fixation fluid (bacterial cells) for absorption within the soil grain. The cementation solution was injected at a flow rate of 200 ml/h. However, Harkes *et al.* (2010) could not provide information on UCS results and the actual distribution of cementation flow at the end of their study.

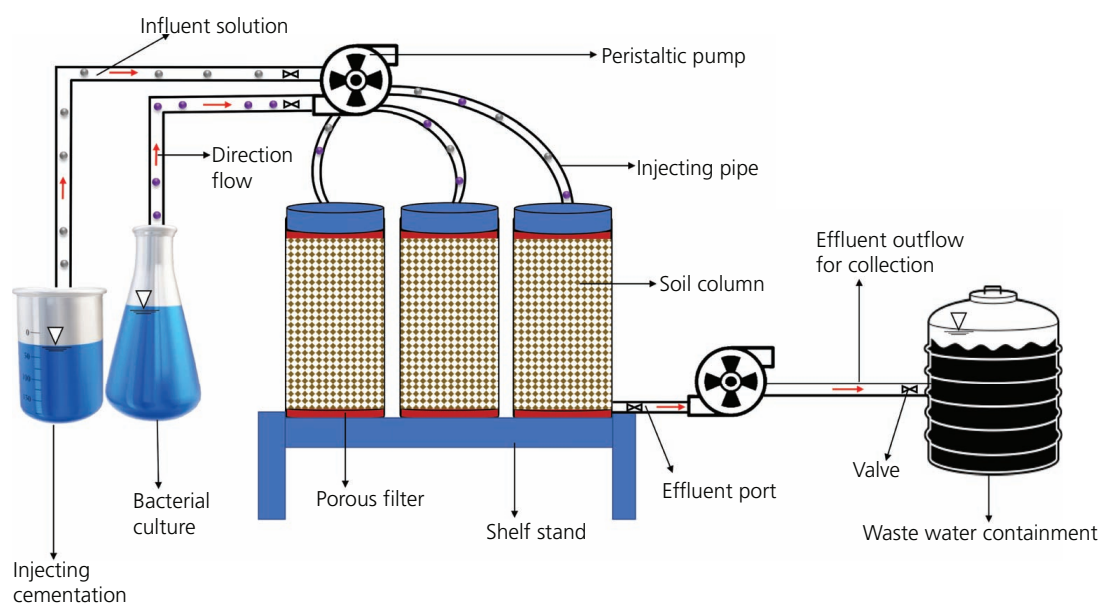


Figure 6. Schematic illustration of soil bio-cementation using the injection treatment method. This diagram was adapted from Gomez *et al.* (2018)

However, analysis from the effluent samples indicated that bacterial activities and ammonium production occurred throughout the columns. This suggested the distribution of the cementation fluid in the entire soil column. As a result, many scholars adopted sequential phases of MICP injection treatment to promote soil solidification. Harkes *et al.* (2010) further discussed the demerit of using diluted bacterial cells in a saline solution. They suggested that this might cause osmotic shock to the bacterial cells, requiring a greater volume of bacterial cultures to be acquired and injected for sufficient urease activity. It might also lead to undesired fluid fixation and bacterial cells being washed out during treatment.

Kakelar *et al.* (2016) described a pressure injection treatment approach that used a sequential batch mode (multistep injection). The scientists injected bacterial cells (OD of 2.5) and calcium chloride solution (0.05 M) into a coarse sandy soil column at a flow rate of 200 ml/h. Three injection cycles lasted 24 h to increase flocculation and bacterial retention. Kakelar *et al.* (2016) demonstrated that, in contrast to the standard treatment injection approach, the multistep injection strategy reduced the required volume for soil treatment by half and assisted in avoiding bacterial cell washout during MICP treatment. They reported a consistent calcium carbonate distribution and a UCS of 525 kPa at the end of the trial. Sharma *et al.* (2021) evaluated the durability of biotreated sand under 0–20 freeze–thaw (F-T) cycles on the shear strength and shear modulus of Narmada River sand. This MICP evaluation was conducted in non-sterile and uncontrolled environmental settings, similar to those in the study by Omoregie *et al.* (2020). Sharma *et al.* (2021) studied the effect of cultivation medium (non-autoclaved and autoclaved) and cementation solution on the MICP

performance. These cultures were injected into soil columns with two cycles (12 and 24 h) to treat alluvial Narmada River sand placed in a poly(vinyl chloride) mould. The non-sterile cementation solution was injected into the mould using different pore volumes (i.e. 1.0, 0.75 and 0.5), and this was repeated for 18 days. Sharma *et al.* (2021) found that the treatment of sand specimens with *S. pasteurii* resulted in a 31% higher strength than the treatment with *L. sphaericus*. Higher shear strength and calcium carbonate precipitation were achieved after the MICP 12 h treatment cycle and 1 pore volume injection of the treatment solution.

Premixing treatment method

Soil bio-cementation by the premixing treatment method requires the mechanical mixture of soil with bacterial stock and chemical solutions before being placed in a mould specimen (Cheng *et al.*, 2017). The premixing of bacteria or cementation reagents with soil to improve the bio-cementation process may not be practical underneath infrastructure. However, this method is applicable when deep mixing is used, which may enhance the viability of the cells (Irfan *et al.*, 2019). Premixing can be used when the improved soil is used as a backfill around engineered structures or in any other situation where engineered fill is needed. It has been suggested that the premixing treatment method may lead to the development of pseudo-strength during premixing, complicate the stress history of soil and result in undesired uncertainties during mechanical testing. Premixing soil with bacterial cultures and cementation solutions before performing other treatment methods can improve the MICP process (Cheng *et al.*, 2017). For example, adding a calcium chloride solution to soil allows the solution to act as a flocculant and initiate the coagulation of bacterial cells before subsequent MICP treatments (Al-Thawadi, 2008).

Premixing bacterial cells with soil could improve the UCS of treated soil by three- to fourfold.

Cheng and Shahin (2016) presented a method for promoting cementation distribution across the soil column during the MICP process. Cheng and Shahin (2016) suggested preparing a bio-slurry by introducing a precise amount (molarity) of urea and calcium ions into glassware containing a ureolytic bacterial culture, followed by 12 h of stirring (600 revolutions/min) to generate the needed precipitate. Later, before injecting the cementation solution, the soil was premixed with the fluid. According to Cheng and Shahin (2016), simply using bio-slurry for soil treatment without adding cementation solution or bacterial culture failed to produce bio-cementation because it lacked the requisite bonding force to solidify soil particles. However, by adding cementation solution to soil premixed with bio-slurry it resulted in an even distribution of cementation within the tested soil column and a UCS of 1 MPa.

Chen *et al.* (2021) investigated the viability of using bamboo fibre in conjunction with the MICP procedure to improve peat soil solidification. Chen *et al.* (2021) isolated native ureolytic bacteria (*Staphylococcus edaphicus*) from peat soil samples and used them in their subsequent MICP experiments. A cementation solution column was filled with the bacteria culture (15 ml) and 150 g of peat soil. Before curing for 7 days, different concentrations of cementation components (1–3 mol/l) were poured into the column. The scientists discovered that a concentration of 1 mol/l resulted in successful bio-cementation, whereas a higher concentration resulted in weak bio-cementation. Chen *et al.* (2021) further tested the effect of oven-dried bamboo fibres on peat soil at various ratios (5 and 10–50%). They reported that adding 5 and 10% bamboo fibre to peat soil before bio-cementation treatment had no significant impact. On the other hand, the incorporation of 50% bamboo fibre increased the strength of the treated peat soil by 40 times. The work of Chen *et al.* (2021) suggested that MICP treatment of peat soil would require a lower concentration of cementation ingredients and a high bamboo fibre content. Safdar *et al.* (2021) evaluated the effectiveness of upgrading peat soils in the East Anglia railway network. They combined peat soil with bacterial cultures (*Bacillus licheniformis*) before placing it in a cylindrical mould. Then, they added cementation solutions with varying amounts of urea and calcium chloride. Safdar *et al.* (2021) reported that MICP-treated soil with 0.5 or 0.75 M cementation solutions produced higher UCS results than those treated with 1 M. However, the scientists also stated that premixing bacteria with soil to increase soil bio-cementation might be impractical under existing infrastructure unless deep mixing would be performed. This might reduce bacterial cell viability due to stress from the industrial mixing process.

Major issues affecting bio-cementation

Lowering the growth medium cost for ureolytic bacterial cultivation

Bio-cementation for field-scale treatment is expensive, and this cost should be decreased drastically. For diverse MICP

experiments, most researchers employ commercially viable reagents (Omoriegbe *et al.*, 2021). The high cost of analytical-grade growing media is a financial concern that will continue to impact bio-cementation until it is addressed. The cost of ureolytic bacterial culture nutrients accounts for roughly 60% of the entire cost of the MICP process and will rise as the application is scaled up (Yoosathaporn *et al.*, 2016). For bacterial cultivation, the in situ MICP technique requires a large volume of growth ingredients (Lapierre *et al.*, 2020). It can be carried out in reactors for bioaugmentation of the MICP process or biostimulation of native ureolytic microbial communities (El Enshasy *et al.*, 2020). For large-scale bacterial production, it is necessary to find an inexpensive substrate that supports a good level of urease activity (Cuzman *et al.*, 2015). Many ways (e.g. growth nutrient alternatives and cementation chemical reagent replacements) have been intensively researched to lower the cost of MICP procedures for field-scale application. The focus of this review is on growth nutrition options. In recent years, many researchers have investigated a way to replace expensive laboratory-grade culture materials with acceptable alternatives that are practical for MICP application.

Kahani *et al.* (2020) studied the possibility of replacing conventional growth media (peptone) with alternative nutrient sources (corn steep liquor, whey, commercial yeast extract and soy flour). Since peptone provides vital carbon and nitrogen sources for microbial growth and enzyme activity, Kahani *et al.* (2020) used various analytical-grade peptone-based medium sources instead of alternative substrates. Yang *et al.* (2020) suggested a novel method for enriching ureolytic bacteria in large-scale production under non-sterile conditions for MICP field use. The scientists suggested using waste activated sludge to save up to 30% on bacterial cultivation costs. Yang *et al.* (2020) also gave a breakdown of expenses in their MICP work, revealing that just 5% of the budget was spent on bacterial sources and transportation, while materials (60%) and sterilisation (30%) were more expensive. Hong *et al.* (2021) later investigated the use of perilla meal, rice bran, sesame meal, soybean meal, soybean pulp and wheat bran as inexpensive nutrition sources for MICP. *Bacillus miscanthi* strain AK13 (previously isolated from the rhizospheres of *Miscanthus sacchariflorus*, Republic of Korea) was cultivated in these substrates and compared with a laboratory-grade Difco sporulation medium. Hong *et al.* (2021) reported that sesame meal had the highest spore amount, while perilla meal and rice bran recorded the lowest spore formation compared with the control medium. However, they also reported that while sesame meal medium was preferred to enhance high spore formation, it failed to propagate bacterial cells efficiently.

Meng *et al.* (2021) investigated the use of kitchen waste to cultivate ureolytic bacteria purchased from the American Type Culture Collection (ATCC). *S. pasteurii* (designated as strain ATCC 11859) was used for wind erosion control of desert soil through MICP. Meng *et al.* (2021) compared the performance of kitchen waste medium with those of yeast extract medium,

nutrient broth medium and tryptic soy broth medium. Meng *et al.* (2021) observed that bacterial cultivation using kitchen waste resulted in the precipitation of vaterite (a polymorph of calcium carbonate). Their research also revealed that kitchen waste (0.375 g/l) was less expensive (less than US\$1) than traditional media (US\$1–5). Since kitchen trash can be easily sourced globally at no or little cost from residential houses, retail regions and manufacturing and food sectors, it can serve as an alternative nutrition source for cultivating ureolytic bacteria, particularly on a large scale. Babakhani *et al.* (2021) demonstrated that incorporating 10% (v/v) corn steep liquor in a medium containing yeast extract, ammonium chloride (NH₄Cl) and urea (but not sterile) could cultivate *S. pasteurii* (designated as strain ATCC 11859TM). Their bio-cementation test also achieved a UCS of 811 kPa. These experiments showed that agricultural waste effluent could be an alternative medium to reduce bacterial production costs for field-scale MICP application.

Ammonium production during the ureolysis process

Waste management and pollution control are frequently overlooked during or after soil bio-cementation. However, depending on the calcium source utilised for calcium carbonate precipitation, careful attention is required to avoid undesired generation of ammonium ions. Soil acidification occurs when a substantial amount of ammonium is abruptly emitted into the environment. Ammonium is a positively charged ion produced by the reaction between ammonia and a hydrogen proton (Nvs and Saranya, 2020). After soil bio-cementation, what remains in soils may be volatilised into toxic gas and ammonia when it dissolves in water and causes severe nitrogen pollution. However, when ammonium concentrations surpass the capacity to detoxify, this results in harmful health effects on living species such as people and animals (Gowthaman *et al.*, 2022). If MICP effluents are not treated in soils, they may contaminate groundwater and water bodies (e.g. lakes and rivers) through run-off. High aqueous ammonia levels in surface water promote harmful algal blooms, deplete dissolved oxygen and result in aquatic toxicity (the process is referred to as eutrophication) (Gowthaman *et al.*, 2022). The MICP effluent can be pumped out in an extraction well, but there will still be the possibility of leaking effluents that will permeate into the soil and contaminate the groundwater (Ashraf *et al.*, 2021; Shanahan, 2016). This issue was previously encountered in a 10 m³ sandbox bio-cementation treatment trial. The unexpected leakage polluted the soil and damaged some existing plants/trees (Figure 7). Several recent studies explore reducing the number of products formed during bio-cementation treatment (Gowthaman *et al.*, 2022; Lee *et al.*, 2019; San Pablo *et al.*, 2020; Wang *et al.*, 2021a). However, the experiments performed so far have been bench-scaled. The Occupational Safety Health Administration of the USA recommends a permissible exposure limit of 35 mg/m³ for ammonium concentrations (Ivanov *et al.*, 2019). Also, the maximum allowable amounts of total ammonium for aquatic life have been reported to be 17 and 1.9 mg/l for acute and chronic exposure, respectively (Huff *et al.*, 2013).



Figure 7. Leakage of ammonium-rich effluent in a 10 m³ sandbox during an outdoor bio-cementation treatment

According to the reaction stoichiometry (shown in Equations I–VI), the ammonium concentration is twice that of the urea concentration. Moreover, previous studies indicated that during soil bio-cementation treatment, ammonia production occurred within 50–500 mmol/l (Lee *et al.*, 2019; Martinez *et al.*, 2013). The first author of the present study measured the concentration of ammoniacal nitrogen in MICP effluent solution, which was higher than the acceptable value (1300 mg/l) by the Occupational Safety Health Administration of the USA. This implied that an efficient post-MICP treatment process was imperative for the ammonium remover/remediation. Furthermore, to treat the MICP effluent successfully, it is critical to characterise physiochemical properties properly. These include ammoniacal nitrogen concentration, nitrate concentration, nitrite concentration, dissolved oxygen level, total suspended solids and volatile suspended solids, turbidity and pH level.

It seems simplistic and a little hyperbolic to say that the ammonium concentration is critical during soil bio-cementation without considering other conditions. In addition, various factors affect this (ammonium concentration) during the bio-cementation treatment process, including whether shallow or profound soil improvement is being carried out, whether bio-cementation is applied under saturated or unsaturated conditions and whether there is a receiving body of water for ammonium-impacted water. Therefore, a fate and transport analysis is required to determine how critical the ammonium production rate is during soil bio-cementation. Researchers have recently recommended using a new method, called the microbially induced struvite precipitation (MISP) process, to reduce/prevent ammonium production. MISP converts the ammonium produced into struvite, which could be further used as a fertiliser (Yu *et al.*, 2021). Gowthaman *et al.* (2022) showed that combining rinsing techniques and struvite precipitation could help minimise the environmental impact of MICP effluent. The applied rinsing solution removed around 99%

of ammonium from the sand and achieved 90% removal in the MICP effluent through precipitation as struvite. Gowthaman *et al.* (2022) were able to treat ammonium waste water through the struvite precipitation technique. However, it requires high contents of magnesium and phosphate. Yu *et al.* (2021) compared the total masses of ammonium in effluent samples after soil treatments using MICP and MISP methods. They found that the ammonium content from MICP was twice that obtained from the MISP soil sample. They suggested that MISP reduces 75% of the ammonia produced during their soil bio-cementation test. Thus, this method may be an appropriate approach to improving soil without harming the environment.

Ashraf *et al.* (2021) developed an MICP model by employing the response surface method to optimise the current MICP treatment process. They argued that manipulating the cementation solution could optimise the urea content for the MICP process and minimise the high production of unwanted ammonium ions. By reducing the urea substrate, which is the main instigator of urease production and contributor to ammonia development, researchers could more efficiently conduct soil treatment through the MICP process. The model by Ashraf *et al.* (2021) showed that using 75% less urea than the typical treatment process made it possible to achieve the desired UCS result for the treated sand columns. However, findings by Ashraf *et al.* (2021) did not elaborate on how ammonium by-products can be reduced without reducing carbonate formation. It seems stoichiometrically impossible to use a balanced cementation solution for ammonium reduction. Hence, even if the model may have suggested ammonium can be reduced if 75% less urea is employed, it does not seem feasible for actual MICP application. Ammonium and carbonate will be released as urea is used for MICP, irrespective of its concentration (or amount). Almajed *et al.* (2018) suggested potentially reusing/recycling bio-cementation waste water as a urease source to reduce soil treatment during ureolysis. However, they noticed no precipitation occurred when effluents from the previous treatment process were reused for bio-cementation. Almajed *et al.* (2018) suggested that this was due to the absence of urease denaturation, which might have been affected by the high ionic strength (Almajed *et al.*, 2018). While the opinion/suggestion of reusing effluent may be promising, it still would not resolve the ammonium pollution/production issue during soil bio-cementation. Other studies have recommended optimising the urea usage rate to minimise high ammonium production, but they encourage the need to consider the recovery of the ammonium content (Hu *et al.*, 2021a; Zeng *et al.*, 2021).

Ammonium might be collected using a biofiltration system or sustainable cleaning agents to produce fertiliser, generating financial benefit. According to the research, MICP can potentially use saline or marine water for bio-cementation. It has the potential to be a low-cost nutrition source for MICP applications. Peng *et al.* (2022) researched on the influence of a marine environment and different calcium sources on coral sand strengthening. According to the study, the pH values differed between freshwater

and marine habitats. The real calcium carbonate generation, according to the findings from Peng *et al.* (2022), is 20% lower than the theoretical figure described in the literature. Also, calcium carbonate precipitation was lower in the seawater environment than in the freshwater environment, thus having a minor impact on the calcium chloride group. Also, the most acidic substance for calcium sources was ammonium chloride, followed by ammonium nitrate, while ammonium acetate was neutral (Peng *et al.*, 2022). Also, Fu *et al.* (2022) cultivated *S. pasteurii* in a seawater medium to determine its adaptability in the marine microenvironment. Peng *et al.* (2022) observed that the bacterium required a more extended period to grow in a seawater medium compared with that in a freshwater medium. However, the ureolytic bacterium was able to induce calcium carbonate precipitates effectively to fill cracks and reduce permeability in the samples.

Durability of bio-cemented soil

Subjecting uncemented soil bodies to MICP can improve the properties of the soil. Durability refers to the ability of a material to last for an extended period without obvious deterioration (Coronado *et al.*, 2015). Long-lasting materials can benefit the environment by conserving resources, reducing waste and minimising the environmental impact of maintenance and replacement. Based on the binding nature of MICP and the pore size, porosity and particle size distribution of bio-cemented soil, a soil matrix treated by MICP will have greater durability. However, these engineering characteristics can be damaged by external environmental influences. Therefore, it is important to assess the durability and sustainability of bio-cemented soil. The durability of MICP-treated soil is not yet well understood, as there are few scientific publications on the topic. Future research should focus on the long-term exposure of MICP-treated soil to various atmospheric and climatic conditions to increase understanding of the level of tolerance of bio-cemented soil to long-term uncontrolled climate conditions. Weak soils are often encountered during the construction of foundations, formation levels and subgrades for new roads and infrastructure. Before soil stabilisation treatment is implemented, these weak soils have low mechanical strength. MICP-treated (stabilised) soils last longer in engineering performance than untreated weak soils because they have greater strength and stability. Durability is the property of a geotechnical material that reflects its performance under wetting–drying (W-D) and F-T cycles. W-D and F-T cycles are used in the laboratory to simulate exposure to adverse environmental and weather conditions for stabilised and treated soils. Previous studies have shown that the strength and stability of MICP-treated aggregates are greatly influenced by the calcium carbonate formed within the voids (Gowthaman *et al.*, 2021). Moreover, it has been found that crystallised calcite clusters at particle contacts facilitate cementation between soil particles, serving as the primary source of strength and stability. However, the cementation level also significantly impacts the durability of MICP-treated soil. The higher the cementation level, the lower the loss of mass and UCS, which enhances the durability or long-term

performance of the treatment. In a related study, F-T tests revealed that MICP-treated slope soils are durable in the face of F-T-induced erosion (Gowthaman *et al.*, 2020).

Farajnia *et al.* (2022) examined the use of ureolytic bacteria to manufacture bio-cemented bricks. Their study on soil solidification resulted in a compressive strength of 3000 kPa. Water absorption percentage and the W-D cycle tests could determine the durability of soil bio-cementation after treatment. These qualities could drastically affect the mechanical properties of construction materials (Farajnia *et al.*, 2022). The data by Farajnia *et al.* (2022) showed an increased mass-loss rate in the initial cycle of the W-D cycle tests. In addition, there were visible changes in the soil specimens. Sharma and Satyam (2021) investigated the synergistic impact of bacteria-mixed cultures (*S. pasteurii* and *Bacillus sphaericus*) on soil bio-cementation. After treatment, they also examined the W-D resistance of poorly graded liquefiable sand since this property should be determined before bio-cementation is implemented in the field. Sharma and Satyam (2021) exposed the treated specimen to 0–20 W-D cycle tests and stored it in an uncontrolled temperature environment from 0 to 6 months. This was a comprehensive test and a suitable way of evaluating the potential durability of bio-cementation. Sharma and Satyam (2021) reported that the hybrid cultures had a better impact on the treated soil when compared with individual bacterial strains. Interestingly, Sharma and Satyam (2021) reported increased compressive strength (up to three times) after subjecting the soils to a 6-month curing period in a non-temperature-controlled environment.

Sun *et al.* (2022) combined addition of polyacrylamide (PAM) with bio-cementation treatment of loess soils and studied the effect of F-T cycles on the durability of MICP-treated soils. Sun *et al.* (2022) placed bio-cemented soil specimens in a refrigerator (−20°C) for 12 h and then defrosted the samples for another 12 h at the same temperature (−20°C), which was one F-T cycle. The PAM addition enhanced the soil shear force resistance. The stable precipitation of calcium carbonate resulted in the highest surface strength, indicating optimum erosion control and which was achieved using 1.5 g/l PAM while the soil was exposed to 40 min of rainfall. Increasing the number of F-T cycles up to 12 rounds for MICP–PAM-treated soil resulted in less weathering of the treated sand (Sun *et al.*, 2022). The cementation effect on loess particles was weakened by F-T exposure, with fractures appearing on the surface of MICP–PAM-treated samples. However, adding PAM to the MICP-treated soils helped improve their durability and stability. Sharma *et al.* (2021) studied the durability of bio-cemented soil under F-T cycles since not much attention has been given on this aspect. They showed that the reduction in compressive strength was not significantly less (5–10%, in the order of magnitude of the strength loss) after five and ten F-T cycles of the bio-cemented specimens, irrespective of treatment conditions. Sharma *et al.* (2021) demonstrated that with a calcite content of 9–12% of the soil samples, the influence of ten F-T cycles did not affect the overall performance of bio-cementation.

The bio-cemented specimens retained about 90% of their shear strength. However, after 15 and 20 F-T cycle tests, the compressive strength of the treated poorly graded liquefiable sand decreased to 31–35%. The mechanical characteristics of calcareous rocks and sandstone materials have also been considerably deteriorated by the W-D process in several studies. Because the reactions of MICP-treated soils (cemented by calcium carbonate) were generally comparable with those of natural carbonate and sandstone sediments, the treated samples were more likely to deteriorate when repeatedly exposed to the cyclic W-D process (Velardo *et al.*, 2022). The W-D treatment technique altered the microstructure of soil aggregates and lowered both shear strength and compressibility. The most commonly observed degradation mechanisms for sedimentary materials include fracture energy reduction and corrosive chemical activity.

When exposed to a cementation solution, ureolytic bacteria can immediately induce calcium carbonate precipitation. Temperature, nutrition, pH, salinity and concentration or supply of urea/calcium ions are various factors that can alter the biochemical characteristics and survivability/lifetime of these ureolytic microorganisms. Also, microbial endospores can allow them to live in harsh environments. Some researchers have demonstrated that ureolytic bacterial cells can survive up to 20 days while retaining cell viability or enzyme function (Erdmann *et al.*, 2022; Peng and Liu, 2019). However, future researchers will be able to investigate the effect of long-term hunger on the ability to produce calcium carbonate or enzyme activity for an extended period. This information will be valuable for determining the durability of bio-cementation. There is no clear understanding of the MICP treatment, which involves either a periodic/repeated injection of bacterial cells or a one-time introduction. Nonetheless, research has shown that, regardless of whether microorganisms are introduced on a regular or sporadic basis, both approaches can promote soil fixation or calcification.

Sustainability process and principle of soil bio-cementation

It is pertinent to assess proactively the cost and environmental benefits and identify the potential consequences of bio-cementation as an emerging technology. A complete life-cycle sustainability assessment (LCSA) identifies the capital costs and environmental and social impacts and benefits of all parts of a given process or product from the cradle to the grave or cradle to cradle. Martin *et al.* (2020) used LCSA to compare alternative processes/products for bio-cementation. The production of urea was pointed out as the flashpoint for energy consumption. Non-fat milk powder and urea were identified as the flashpoint for carbon dioxide equivalent emissions. The release of ammonium by-products due to the hydrolysis of urea was identified as the flashpoint for eutrophication potential. The LCA was conducted to compare conventional soil stabilisation using Portland cement (PC) with bio-cementation through enzyme-induced carbonate precipitation (EICP) in terms of environmental impacts in a related study. EICP is gaining lots of attention due to its

suitability for MICP applications without the need to culture ureolytic microorganisms (Hu *et al.*, 2021a). MICP requires active microbial cells, while EICP employs purified urease from various plants such as jack bean (*Canavalia ensiformis*), potato (*Solanum tuberosum*), soya bean (*Glycine max*), pumpkin (*Cucurbita maxima*) and watermelon (*Citrullus vulgaris*) (Dilrukshi and Kawasaki, 2019; Imran *et al.*, 2021).

The use of commercially available pure urease from agricultural sources is an excellent alternative to MICP for urease activity and calcium carbonate precipitation (Hu *et al.*, 2021b). Furthermore, EICP technology strongly depends on the interaction of urease, urea and calcium transport during the bio-cementation treatment. EICP has been tried on different soil types (silty sands, clayey sand and silt) (Arab *et al.*, 2021; Yuan *et al.*, 2020). Chandra and Ravi (2021) recently showed that a urease concentration of 8 kU/l could hydrolyse practically all of a urea–calcium chloride solution at 0.5 mol/l, resulting in a higher amount of calcium carbonate precipitated as it approached the 100% precipitation level. An LCA study on EICP bio-cemented soil revealed that the bio-cementation treatment process has nearly 90% less abiotic depletion and 3% less global warming potential than PC in soil stabilisation. However, due to by-products of the hydrolysis process, EICP in soil stabilisation has higher acidification and eutrophication potentials than PC. The research suggested that EICP is potentially a better environmental option, in terms of carbon footprint, at a lower compressive strength of the treated soils (Alotaibi *et al.*, 2022).

The reliance on chemicals and nutrients and ammonium waste production for the bio-cementation process suggests that environmental implications must be addressed, particularly when establishing this technology as a sustainable building process alternative for industrial applications. The principal/significant bio-cementation components are calcium, urea and the growth medium. If bio-cementation becomes an ecologically sustainable construction technology, reusing its effluent (by-products) or naturally existing materials must be adopted (Porter *et al.*, 2021). Using recycled wastes (palm oil mill effluents and organic manure) as a naturally occurring source of nutrients for microbial growth and cementation reagents rather than commercial reagents will enhance the sustainability of bio-cementation practice (Omeregie *et al.*, 2022b). Another factor that affects the principle of bio-cementation as a sustainable practice is researchers' continuous use of urea for calcium carbonate precipitation. Many researchers often suggest that bio-cementation by MICP is a sustainable, low-energy, low-carbon-footprint soil stabilisation/reinforcement method. However, the literature does not support this frequently stated assertion.

Some research groups have argued that the carbon footprint of bio-cemented soil may exceed that of PC-stabilised soil due to the embodied energy in urea (which is generated from natural gas) (DeJong *et al.*, 2010; Lee *et al.*, 2019; van Paassen, 2009; van

Paassen *et al.*, 2009; Whiffin, 2004). On the other hand, urea should be omitted due to its large carbon footprint, such as carbon dioxide (total emissions of 0.133 million tonnes carbon dioxide equivalent (MtCO₂e) per year); the energy required for its production; and its eutrophication potential (Porter *et al.*, 2021). Another recent report stated that urea production for fertilisers directly emits 438.5 ± 37.1 MtCO₂e, while transportation emits 29.8 ± 4.0 MtCO₂e, and carbon dioxide liberation from urea usage is 86.0 ± 39.1 MtCO₂e (Menegat *et al.*, 2022). Thus, a shift towards available resources rich in urea could reduce environmental costs and promote bio-cementation sustainability. Hence, animal urine waste (i.e. from cows) will serve as an excellent source of urea and has recently been reported as a suitable alternative to synthetic urea soil improvement (Comadran-Casas *et al.*, 2022). Additionally, crushed silicate rocks, or dolerite (4 mm), a byproduct of the quarry sector and alternative source of calcium to calcium chloride, have recently been described (Casas *et al.*, 2020). Therefore, researchers should explore alternative bio-cementation components: crushed fish or chicken bones, clamshells and blood cockle shells as calcium sources; horse urine and leachate as urea sources; and agricultural waste water (i.e. from sugarcane bagasse and animal farmlands) as nutrient sources.

Advantages and disadvantages of the bio-cementation treatment approach

Bio-cementation is driven by naturally occurring mechanisms to precipitate carbonate minerals for potential activities and applications. The benefit of bio-cementation is that the building material can be induced by the metabolic activities of ureolytic bacteria, which are abundant and quickly recovered/isolated. Developing bio-mediated processes for soil improvement has several advantages over current techniques. These are discussed around the sustainability triple-bottom-line (economic, social and environmental) framework, also known as profit, people and the planet.

Advantages of bio-cementation

Considering the economic perspective, an advantage of bio-cementation is that the cementitious material can be naturally induced by the metabolic activities of ureolytic microorganisms, which are ubiquitous and quickly recovered/isolated. This reduces the economic burden of the energy-intensive processing of traditional cementitious materials. Although the initial production cost of bio-cementation may be prohibitive, it requires low-cost maintenance practices (Achal *et al.*, 2010). Additional advantages of bio-cementation technology include controlled treatment/monitoring, adaptive duration/flexible deployment in confined subsurface/retrofit construction and penetration into fine soils. Moreover, several papers have shown that high-purity media or chemicals are not entirely needed to obtain desirable calcium carbonate precipitates. Hence, low-grade reagents and industrial-waste materials can significantly lower bio-cement production costs, particularly in real-world use (Liu *et al.*, 2019; Meng *et al.*,

2021; Pakbaz *et al.*, 2020; Wei *et al.*, 2022). Both reduced construction costs with the use of natural materials and the reduced infrastructure maintenance cost due to the enhancement of self-repair characteristics in bio-cemented soils underscore economic advantages and improved sustainability in congruence with the UN Sustainable Development Goals (SDGs). Bio-cementation technology addresses environmental challenges within the UN SDGs (goals 9, 12 and 13) that include industry, innovation and infrastructure; responsible consumption and production; and climate action, respectively.

The socio-economic benefits of bio-cementation are becoming unveiled with the increasing capacity for prosperity in local communities through the new bio-based and circular economy concept derived from the bioeconomy vision (Lange *et al.*, 2021). This entails unlocking the full potential of all types of sustainability by transforming bio-based improved soil and biomass into value-added brownfields and products. An example is the biologically hardened concrete masonry units that do not require thermal hardening and thus could yield a significant reduction in embodied carbon dioxide in structures, given that concrete production makes up 5% of overall global carbon dioxide emissions (Iezzi *et al.*, 2019). Notably, a bio-based product portfolio comprises a broad spectrum of value-added products that address societal and consumer needs. Given the increasing scarcity of suitable land for development, an important factor in circular land management is the reduction of both greenfield consumption and brownfield production. This can be achieved by maintaining land in productive use as far as possible and, where it falls out of use, making sure its transition to new land use is as rapid as possible. Land usage could be for built redevelopment including creating urban green space, to lessen the scarcity of land (Bardos *et al.*, 2016). Brownfield site remediation through a bio-cementation process fosters sustainable site remediation and restoration of the biodiversity of the ecosystem. Thus, the critical interdependencies necessary for socioecological health can be re-established (De Garine-Wichatitsky *et al.*, 2021). Bio-cementation has also successfully shown its ability to preserve, protect and restore historical monuments without causing any damage to existing bodies/structures (Snigdha and Latkar, 2020).

Concerning the environment, bio-cementation can immobilise heavy metals. The calcium carbonate from MICP can co-precipitate with heavy metal ions in tailings sand, preventing the heavy metals from diffusing into the surrounding environment (Kang *et al.*, 2022). It may also be used to sequester (biomineralise) radionuclides and metal contaminants (e.g. strontium and cadmium) in groundwater, a significant problem at some US Department of Energy sites. Biomineralising metal contaminants by stimulating native denitrifying bacteria may provide a more sustainable means of remediating groundwater impacted by radionuclides and metal contaminants than hydrolytic ureolysis (Kim *et al.*, 2021). Another advantage of bio-cementation over previous technologies is that it requires only a

modest calcium source. Calcium chloride is a required chemical reagent for bio-cement precipitation, whereas other conventional processes necessitate chemical stabilisers such as lime. It was recently shown that to achieve the same compressive strength (700 kPa after 28 days of curing), the conventional cement injection amount should be 2.5 times more than that in the MICP approach (Naeimi and Haddad, 2021). MICP technology has been successfully/effectively tested on sandy soil. Other types of soils from various locations worldwide have also been tested (peat soil, silty soil, calcareous soil and lateritic soil). While the MICP process for soil stabilisation has been rigorously studied on sand, new findings on the potential of MICP on expansive soil (i.e. soft clay) enhancement have been increasing lately (Ouyang *et al.*, 2022; Xiao *et al.*, 2020).

Disadvantages of bio-cementation

Some disadvantages associated with bio-cementation include the formation of desiccation cracks, leading to an increase in hydraulic conductivity in clayey soils; non-uniform permeation of bio-grout/bio-cementation solution in highly heterogeneous soils/field-scale applications with diverse climatic conditions; ammonium removal during ureolytic MICP; and the regulatory mechanisms of crystal morphology (Jiang *et al.*, 2022). Bio-cementation has successfully shown its ability to preserve, protect and restore historical monuments without causing any damage to existing bodies/structures (Snigdha and Latkar, 2020). The limitations regarding the field application of bio-cementation include the high cost of chemical-grade reagents and cost-prohibitive laboratory-grade cultivation media, as well as issues with ammonium production as a by-product, non-uniformity of precipitation and slow and complex environmental factors. Additionally, there are challenges with transporting healthy ureolytic bacteria in large quantities to the site and optimising the treatment process given site-specific conditions, as well as the need for monitoring the treated soil during treatment and periodically throughout the service life of the system. Finally, bio-cementation cannot be used to treat soils with no sand or fine content, and the calcite precipitate may degrade during loading (DeJong *et al.*, 2010; Dubey *et al.*, 2021; Snigdha and Latkar, 2020). It has also been noted that utilising a more significant concentration of cementation chemicals results in greater strength but may cause the environment to become saltier, affecting some bacterial development (Umar *et al.*, 2016). Another disadvantage of bio-cementation is the need for costly microbiological nutrient supplies to maintain pure bacterial culture. Another drawback of bio-cementation technology is the need for a very alkaline environment for the growth of ureolytic bacteria and the MICP process (Marín *et al.*, 2021). Several studies have shown that exogenous ureolytic bacteria can be isolated from extreme environments such as limestone caves (Omoriegbe *et al.*, 2017). However, their biomass and performances are hindered when exposed to harsh environmental conditions. Hence, it has been suggested to stimulate indigenous/native ureolytic microorganisms to achieve this feat or explore microbial consortia since they have shown higher resilience to harsh environments than pure bacterial cultures (Gowthaman *et al.*, 2018, 2020; Marín *et al.*, 2021).

Some recent directions of MICP applications

Soil erosion control

Aside from soil stabilisation/improvement, erosion management using the MICP technology constitutes a major global application. The adoption of MICP technology can significantly improve soil erosion resistance. Crystals are formed, filling the pores and binding to the particles of weathered soil, allowing for effective cementation and bridging (Wang *et al.*, 2021b). Xiao *et al.* (2022a) employed an artificial rainfall system to simulate the erosion of model slopes caused by rainfall. After MICP treatment, erosion on slopes with uniformity coefficients of 4.7 and 9.7 was significantly reduced, with total soil loss reduced by 64.8 and 84.4% (relative to the total mass of sand on slopes), respectively, compared with those of untreated slopes (Xiao *et al.*, 2022a). Dubey *et al.* (2021) recently investigated the ability of Brahmaputra riverbank native ureolytic bacterial communities in erosion control due to its significant socio-economic impacts. Dubey *et al.* (2021) reported that for the soil strength test, the distribution of needle penetration resistance was non-uniform. However, producing ammonium during MICP treatment may cause environmental issues to the river ecology and geoenvironment for field application. If MICP is used at riverbanks, ammonium contents may be diluted to an insignificant level and possibly be treated by the presence of flora and fauna (Dubey *et al.*, 2021). Kou *et al.* (2021) recently studied the potential of MICP in coastal erosion control/prevention. They tested the model-scale mechanism of erosion of sandy slopes under laboratory conditions. Also, the thickness of the crust following surface percolation and its penetrating resistance were studied. Kou *et al.* (2021) reported that the water retention capacity of an MICP-treated sandy slope is crucial under surface percolation and thoroughly drained circumstances. A three-dimensional (3D) printing method can be adopted to improve further the homogeneity of consolidated soil samples suitable for erosion control (Nething *et al.*, 2020). Studies have shown that this method has the potential to generate resource-efficient sustainable construction components. However, it was noted that the practical use of the 3D printing process is restricted due to the size restriction of the print bed and the requirement of several print bed enclosures (Nething *et al.*, 2020). Nonetheless, a recent study (Erdmann *et al.*, 2022) demonstrated that the printing nozzle (150–250 μm) that is applied under varied pressure levels (0.69–2.76 bar) could significantly improve the homogeneity of the soil column. This will further support the implementation of MICP technology for erosion control.

Improvement of the road soil base

There are currently no large-scale instances of MICP use for road construction or a geotechnical purpose, such as bio-cementation as soil improvement for a road pavement layer. Chu and Wen (2015) were the first to demonstrate the utility of MICP for road repair. Their brief research demonstrated that fine limestones and maize cobs might be used as low-cost alternative raw cementation materials to produce the soluble calcium required for field-scale

MICP trials. Following the success of laboratory-scale trials, bio-grouting (on-site soil strengthening) has been investigated, which includes pumping biological fluid into the soil (Porter *et al.*, 2018). A laboratory-scale trial on the performance of MICP in reinforcing road bases reconstituted with calcareous or silica sands was successful. This study used the surface percolation approach to create four testing models at two cementation levels. A series of tests for the California bearing ratio (CBR) and UCS were also carried out to investigate the strength of biotreated samples at the model and element scales. CBR is the most important criterion for analysing subgrade soil strength and improving the engineering features of road construction pavement layer materials (Nezhad *et al.*, 2021; Tan *et al.*, 2021). *S. pasteurii* was cultured in a nutrient solution consisting of 24 mg/l nickel (II) chloride hexahydrate ($\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$), 12 mg/l manganese (II) chloride monohydrate ($\text{MnCl}_2 \cdot \text{H}_2\text{O}$), 10 g/l ammonium chloride and 20 g/l soya peptone extract (Porter *et al.*, 2018). The nutrition solution was created at a pH of 9 since the bacterial strain was more active in an alkaline environment. Bacteria were grown in a shaking incubator at a velocity of 200 revolutions/min and a constant temperature of 30°C. After 24 h of incubation, bacteria were extracted from the supernatant in a 0.9% sodium chloride (NaCl) solution and centrifuged at 5000g at 4°C. The cementation solution, which comprised 0.5 mol/l calcium chloride and 0.5 mol/l urea, acted as a sufficient reactant during the cementation process. This study used one-phase MICP treatment with the surface percolation approach to stabilise the sand models (Porter *et al.*, 2018). The one-phase cementation solution was first prepared; then, the bacterial solution was combined with the cementation solution. The mixed solution was then created in a volume equivalent to 1.1 pore volume of the sand sample and equally splattered on the sample surface, penetrating the sand matrix under gravity. The researchers discovered that bio-cementation might have reinforced cement-stabilised sand and road base materials. The CBR value of the high-treatment sample reached 75%, demonstrating high strength and performance for stabilised road bases. Furthermore, when the MICP technique was used with the cement-road base material, the UCS increased by 35–50%.

Porter *et al.* (2018) established that bio-cementation would considerably enhance road building by reducing the use of cement-based materials in road bases, improving environmental sustainability. Recently, Xiao *et al.* (2022b) were inspired to investigate the efficacy of bio-cementation as a stand-alone stabilising method and as a supplement to cement-stabilised road base materials. They concluded that the low bearing capacity of the pavement or road base frequently resulted in tyre tracks and cracking. Xiao *et al.* (2022b) investigated bio-cementation strength and reinforcing effectiveness using four biotreated road base models. Xiao *et al.* (2022b) noted that the increment and decrease in soil strength correlated with the penetration depth after treatment. Due to the differences in void ratios, the overall strength of the biotreated calcareous sand specimens was higher than that of the biotreated silica sand specimens at the model scale.

Yang *et al.* (2022) suggested that clogging in the upper layer of the base might have influenced this outcome. Successful laboratory-scale trials reviewed are on the performance of MICP in reinforcing road bases reconstituted with calcareous or silica sands. This investigation prepared four testing models by using the surface percolation method at two cementation levels.

Remediation of soils contaminated with heavy metals

Heavy metal contamination of natural surroundings through industrialisation has become a widespread environmental problem (Eltarahony *et al.*, 2021). Many sewage and solid wastes containing heavy metals are discharged into the environment due to poor waste treatment in industrial activities. Because these heavy metals cannot be destroyed, they will continue accumulating in the environment. Furthermore, these heavy metals penetrate food chains, endangering the health of animals, plants and humans. Contamination from these sources exposes the environment and human health to heavy metal pollution (e.g. lead (Pb) and mercury (Hg)). In addition, their non-degradable nature keeps them in food chains to likely cause harm to the entire ecosystem. Previous researchers showed that urease-producing microorganisms could catalyse the hydrolysis of a urea substrate into carbonate ions and other subsequent biochemical reactions/products under suitable conditions. This metabolic process can immobilise metal ions (i.e. lead and mercury) to form precipitates. This sequestration process limits heavy metal migration and decreases heavy metal toxicity in the environment. Carbonate sediments are typically generated when microbial metabolites interact with calcium ions. The bacterial cells (being negatively charged) react with cations (heavy metals) during heavy metal remediation through the MICP process (Tamayo-Figueroa *et al.*, 2019). These toxic metal ions have ionic radii that allow integration into the calcium carbonate crystal by calcium ion substitution (Ali *et al.*, 2022).

Eltarahony *et al.* (2021) reported using *Metschnikowia pulcherrima* and *Raoultella planticola* to remediate lead and mercury. Their results indicated about 95% removal of these heavy metals after 48 h of MICP treatment. It was achieved with urease activities of 884 and 639 U/ml for *M. pulcherrima* and *R. planticola*, respectively. This bioremediation method enables stable heavy metal detoxification and sequestration (Eltarahony *et al.*, 2021). *Aneurinibacillus tyrosinisolvans* was employed by Wang *et al.* (2021b) to degrade cyanide in tailings. This deadly chemical (cyanide) is a hazardous waste. Wang *et al.* (2021b) used the ureolytic strain to break down cyanide (88–95%) before solidifying it in block form using the bio-cementation procedure. MICP sequesters these compounds within precipitated calcium carbonate, causing cyanide metal to convert into a benign form. The MICP sequestration procedure was chosen to ensure that this heavy metal does not leach into the environment. Wang *et al.* (2021b) demonstrated that their innovative method, a clean disposal approach for heavy metals, could be helpful to researchers interested in mine backfill and other sectors. Wang *et al.* (2021b) reported a novel approach for seeding crystal and

ureolytic bacterial cultures to remove fluoride from groundwater. They were able to remediate 70% of the fluoride content after 14 treatment cycles by utilising the MICP technique, with a residual fluoride concentration of 0.96 mg/l in their tested sample. Wang *et al.* (2021a) proposed that MICP might be employed as a more environmentally friendly and cost-effective alternative defluorination approach to present technologies (i.e. adsorption, membrane filtration and ion exchange). Another low-cost approach studied by Chiwetalu *et al.* (2020) demonstrated the remedial ability of corn steep liquor on lead-contaminated soil. This study indicated that the extraction of lead by the plant system increased with increased lead concentration in the soil and extent of vegetation attained by the crop. Therefore, soil enhancement approaches such as bio-cementation are explored when the natural soil does not meet construction engineering standards. For example, if the soil is too weak to support a structure on a shallow foundation, there are two alternatives: deep foundations or soil remediation combined with a shallow foundation. The presence of xenobiotic (artificial) substances causes soil contamination, soil pollution or land pollution due to land deterioration (Chiwetalu *et al.*, 2020).

Mitigation of soil liquefaction

Soil liquefaction is a condition during which soil loses shear strength and suffers significant deformation relatively quickly. Desaturation is a technique that continues to gain popularity for preventing sand liquefaction because of its cost-effectiveness (Jia and Jian, 2014). Microbial denitrification is a nitrogen reduction reaction mediated through the MICP process by denitrifying bacteria (He *et al.*, 2016). This approach is a new method of mitigating soil liquefaction. During the microbial denitrification treatment process, gas bubbles in soils are gradually removed under both upflow and downflow circumstances, and the degree of saturation increases from 89 to 100% within 96 h (He *et al.*, 2016). This further helps improve the soil significantly, ensuring the distress shifts from a stress–strain to a strain-hardening mode. MICP is also beneficial for granular soils subjected to liquefaction. A two-stage process is employed to reduce earthquake-related liquefaction through MICP: ureolysis and denitrification. This is because ureolytic microorganisms can stimulate denitrifying bacteria. This allows the desaturation of soil through the generation of nitrogenous and carbon dioxide gases (O'Donnell *et al.*, 2017). During soil desaturation to prevent liquefaction through MICP, the gas is generated and collected at the top of the soil column but with a low/moderate pore pressure. In contrast, carbonate precipitation proceeds mainly at the bottom near the substrate intake, which helps stabilise the soil (Pham *et al.*, 2018).

Recent work was performed to comprehend better the impact of calcium carbonate bio-cementation on the liquefaction behaviour of loose sands. During their inquiry into inducing remediating soil liquefaction, Pham *et al.* (2018) discovered bio-cementation subjected to shear wave velocity measurement (0–100 m/s) drastically increased the number of treatment cycles required.

Pham *et al.* (2018) highlighted that despite the significant increment (tenfold) in their data, there was a slight improvement in strain build-up before and after initial triggering. More work on soil mitigation liquefaction through MICP can help to understand better the behaviour of weakly bio-cemented soils subjected to earthquake-induced undrained cyclic loads (Lee *et al.*, 2020). Another study on ground improvement through MICP by denitrification revealed that the substrate solution had an optimum carbon–nitrogen ratio of 16, confirming that merging nitrate reduction and calcium carbonate precipitation results in effective conversion. According to sand column tests, the volume and distribution of the gas phase are largely dependent on the stress conditions (Pham *et al.*, 2018). Future investigations are needed to enhance the knowledge on and potential of MICP for the prevention/mitigation of soil liquefaction.

Future considerations

When soil bio-cementation is accepted for commercial or practical application in the future, the existing substantial obstacles (environmental issues, durability over time and bacterial cultivation cost) highlighted in this research should be given more consideration. The cost of large-scale cultivation of ureolytic bacteria will increase the production cost of the MICP process. This is due to the scarcity of inexpensive or easily obtained growth media. A large-scale reactor would also be required to scale-up microbial cultures. Future researchers may be able to investigate how easily modifiable and inexpensive reactors can be improved for easy application and long-term development of ureolytic bacteria. Furthermore, incorporating physiological factors to maintain/observe optimal and sustainable microbial products could ensure that the commercial application and cost competitiveness of MICP technology are not jeopardised.

Biostimulation of native ureolytic bacteria is another technique that should be supported. Bio-cementation is accomplished through a biostimulation process that necessitates activating indigenous microbial activity for calcium carbonate deposition, which binds sand particles together. The calcium carbonate bioaugmentation technique produces precipitates and is used in most of standard bio-cementation research. After being cultured in shake flasks or reactors, exogenous ureolytic bacteria are added to the sandy or silt soil columns for treatment. However, the biostimulation method for soil bio-cementation has received little attention in the literature. Many factors must be considered during bio-cementation treatment for the bioaugmentation approach, including bacterial strain cultivation and inoculation; unbalancing the natural ecosystem (presence of indigenous microorganisms); survivability of exogenous bacteria; mass oxygen transfer; spatial variations; relatively long time required for bacterial permeation, higher cultivation costs and special precautions needed when mixing; and environmental considerations. As a result, adopting the bioaugmentation approach to accomplish bio-cementation raises several concerns. Researchers stimulated indigenous microorganisms capable of producing a significant amount of calcite precipitate for soil enhancement to solve bioaugmentation

issues. The biostimulation method necessitates the stimulation of soil-dwelling natural microorganisms. Just nutrients and cementation reagents are required to produce calcium carbonate deposition in the soil. Also, detailed/robust, scalable culture experiments must be undertaken in the laboratory- and pilot-scale settings before these alternative nutrients are deployed in field-scale trials to ensure the economic or commercial feasibility of MICP.

Inadequate understanding of the post-MICP process or post-bio-cementation treatment of soil and waste water has resulted in a considerable negative impact on this field. For example, no existing study in the literature has conducted a detailed examination of the bio-cementation effluent to determine/identify correctly its physiochemical or biochemical features. As a result, scientists frequently prefer to evaluate the ammonium level of waste water before and after treatment. However, to treat waste water sustainably, researchers should complete the effluent evaluation. Researchers are becoming more interested in the durability of bio-cemented soil. While recent data indicate that climate change may not impact the overall compressive strength of bio-cemented soil, additional research is needed. Researchers should investigate how harsh or rapidly shifting climate changes affect bio-cementation. When testing the influence of bio-cementation durability through time, it is also necessary to evaluate the effect of various ureolytic microorganisms. These conditions should be accomplished under uncontrollable external conditions so that MICP can be practically sustainable. The significant parameters utilised to test the durability of bio-cemented soil are W-D and F-T cycles. Finally, in addition to exposing bio-cemented soil to various temperatures and rainfall amounts, obtaining more information regarding climate variables such as wind, humidity and snow would be helpful.

Conclusions

This state-of-the-art review comprehensively discusses the present bio-cementation treatment strategies used for soil stabilisation. The concluding remarks of this paper are summarised as follows.

- An assessment of ureolytic bacteria bio-cementation methods indicates that changes in urease gene composition considerably alter the urease activity of microbial cells and calcite precipitation capacity, emphasising the need to increase and regulate MICP through genetic engineering and biofilms.
- The pressure injection treatment method is the most desired field-scale approach among scholars due to its adaptability and the capacity to deliver a high volume of treatment solutions into deep soil regions while allowing solution recirculation.
- By substituting alternative materials for laboratory-grade culture media and high-purity chemical reagents, MICP approaches for field-scale deployment can minimise total costs. For example, maize steep liquor and low-grade yeast extract can be employed as alternate nutrition sources to standard bacterial growth media. Eggshells, urine and

technical-grade chemicals (urea, calcium chloride), on the other hand, can be used as reagents instead of the more expensive standard chemicals. Furthermore, some of these alternative materials are inexpensive and simple to obtain.

- MISP is a novel bio-cementation technology with the potential to reduce/prevent the creation of ammonium and thereby minimise this critical environmental concern. MISP converts the ammonium produced into struvite, which can be used as fertiliser. The emission of ammonia into the environment or water bodies must be avoided in future bio-cementation technology.
- Optimising the urea utilisation rate to reduce high ammonium production or recovering ammonium contents through the use of a biofiltration system or scrubbing agents will increase economic sustainability through fertiliser manufacturing and financial income generation.
- Despite these upcoming issues, bio-cementation remains a feasible alternative for future use. Furthermore, considerable development by scholars in recent years has proven that bio-cementation practice is currently focusing on heavy metal sequestration from polluted soil and waste water, wave-scouring action erosion treatment and road-based soil improvement.

Acknowledgement

The authors gratefully acknowledge Universiti Teknologi Malaysia for the funding (05E84) supporting the production of this review paper.

REFERENCES

- Abdel-Aleem H, Dishisha T, Saafan A, AbouKhadra AA and Gaber Y (2019) Biocementation of soil by calcite/aragonite precipitation using *Pseudomonas azotoformans* and *Citrobacter freundii* derived enzymes. *RSC Advances* **9**(31): 17601–17611, <https://doi.org/10.1039/C9RA02247C>.
- Achal V and Pan X (2014) Influence of calcium sources on microbially induced calcium carbonate precipitation by *Bacillus* sp. CR2. *Applied Biochemistry and Biotechnology* **173**(1): 307–317, <https://doi.org/10.1007/s12010-014-0842-1>.
- Achal V, Mukherjee A and Reddy MS (2010) Biocalcification by *Sporosarcina pasteurii* using corn steep liquor as the nutrient source. *Industrial Biotechnology* **6**(3): 170–174, <https://doi.org/10.1089/ind.2010.6.170>.
- Achal V, Mukherjee A, Kumari D and Zhang Q (2015) Biomineralization for sustainable construction – a review of processes and applications. *Earth-science Reviews* **148**: 1–17, <https://doi.org/10.1016/j.earscirev.2015.05.008>.
- Al-Gheethi AA, Memon ZA, Balasbaneh AT *et al.* (2022) Critical analysis for life cycle assessment of bio-cementitious materials production and sustainable solutions. *Sustainability* **14**(3): article 1920, <https://doi.org/10.3390/su14031920>.
- Al-Salloum Y, Hadi S, Abbas H, Almusallam T and Moslem MA (2017) Bio-induction and bioremediation of cementitious composites using microbial mineral precipitation – a review. *Construction and Building Materials* **154**: 857–876, <https://doi.org/10.1016/j.conbuildmat.2017.07.203>.
- Al-Thawadi SM (2008) *High Strength In-situ Biocementation of Soil by Calcite Precipitating Locally Isolated Ureolytic Bacteria*. PhD thesis, Murdoch University, Perth, Australia.
- Ali A, Li M, Su J *et al.* (2022) *Brevundimonas diminuta* isolated from mines polluted soil immobilized cadmium (Cd²⁺) and zinc (Zn²⁺) through calcium carbonate precipitation: microscopic and spectroscopic investigations. *Science of the Total Environment* **813**: article 152668, <https://doi.org/10.1016/j.scitotenv.2021.152668>.
- Almajed A, Khodadadi Tirkolaei H and Kavazanjian E Jr (2018) Baseline investigation on enzyme-induced calcium carbonate precipitation. *Journal of Geotechnical and Geoenvironmental Engineering* **144**(11): 04018081, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001973](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001973).
- Alotaibi E, Arab MG, Abdallah M, Nassif N and Omar M (2022) Life cycle assessment of biocemented sands using enzyme induced carbonate precipitation (EICP) for soil stabilization applications. *Scientific Reports* **12**: article 6032, <https://doi.org/10.1038/s41598-022-09723-7>.
- Arab MG, Rohy H, Zeiada W, Almajed A and Omar M (2021) One-phase EICP biotreatment of sand exposed to various environmental conditions. *Journal of Materials in Civil Engineering* **33**(3): 04020489, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003596](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003596).
- Arias D, Cisternas LA and Rivas M (2017a) Biomineralization mediated by ureolytic bacteria applied to water treatment: a review. *Crystals* **7**(11): article 345, <https://doi.org/10.3390/cryst7110345>.
- Arias D, Cisternas LA and Rivas M (2017b) Biomineralization of calcium and magnesium crystals from seawater by halotolerant bacteria isolated from Atacama Salar (Chile). *Desalination* **405**: 1–9, <https://doi.org/10.1016/j.desal.2016.11.027>.
- Ashraf MS, Shah MUH, Bokhari A and Hasan M (2021) Less is more: optimising the biocementation of coastal sands by reducing influent urea through response surface method. *Journal of Cleaner Production* **315**: article 128208, <https://doi.org/10.1016/j.jclepro.2021.128208>.
- Babakhani S, Fahmi A, Katebi H *et al.* (2021) Non-sterile corn steep liquor a novel, cost effective and powerful culture media for *Sporosarcina pasteurii* cultivation for sand improvement. *Journal of Applied Microbiology* **130**(4): 1232–1244, <https://doi.org/10.1111/jam.14866>.
- Bardos RP, Jones S, Stephenson I *et al.* (2016) Optimising value from the soft re-use of brownfield sites. *Science of the Total Environment* **563**: 769–782, <https://doi.org/10.1016/j.scitotenv.2015.12.002>.
- Barkouki TH, Martinez BC, Mortensen BM *et al.* (2011) Forward and inverse bio-geochemical modeling of microbially induced calcite precipitation in half-meter column experiments. *Transport in Porous Media* **90**(1): 23–39, <https://doi.org/10.1007/s11242-011-9804-z>.
- Brown S, Santa Maria JP and Walker S (2013) Wall teichoic acids of gram-positive bacteria. *Annual Review of Microbiology* **67**(1): 313–336, <https://doi.org/10.1146/annurev-micro-092412-155620>.
- Casas CC, Graf A, Brüggemann N, Schaschke CJ and Jorat ME (2020) Dolerite fines used as a calcium source for microbially induced calcite precipitation reduce the environmental carbon cost in sandy soil. *Frontiers in Microbiology* **11**: article 2181, <https://doi.org/10.3389/fmicb.2020.557119>.
- Chandra A and Ravi K (2021) Application of enzyme-induced carbonate precipitation (EICP) to improve the shear strength of different type of soils. In *Problematic Soils and Geoenvironmental Concerns: Proceedings of IGC 2018* (Latha Gali M and Raghuveer Rao P (eds)). Springer, Singapore, pp. 617–632.
- Charpe AU, Latkar MV and Chakrabarti T (2019) Biocementation: an eco-friendly approach to strengthen concrete. *Proceedings of the Institution of Civil Engineers – Engineering Sustainability* **172**(8): 438–449.
- Chen YY, Weaver CA and Burne RA (2000) Dual functions of *Streptococcus salivarius* urease. *Journal of Bacteriology* **182**(16): 4667–4669, <https://doi.org/10.1680/jensu.18.00019>.
- Chen M, Gowthaman S, Nakashima K and Kawasaki S (2021) Evaluating mechanical strength of peat soil treated by fiber incorporated biocementation. *International Journal of GEOMATE* **20**(78): 121–127.

- Cheng L and Cord-Ruwisch R (2012) In situ soil cementation with ureolytic bacteria by surface percolation. *Ecological Engineering* **42**: 64–72, <https://doi.org/10.1016/j.ecoleng.2012.01.013>.
- Cheng L and Shahin MA (2016) Urease active bioslurry: a novel soil improvement approach based on microbially induced carbonate precipitation. *Canadian Geotechnical Journal* **53**(9): 1376–1385, <https://doi.org/10.1139/cgj-2015-0635>.
- Cheng L, Shahin MA and Mujah D (2017) Influence of key environmental conditions on microbially induced cementation for soil stabilization. *Journal of Geotechnical and Geoenvironmental Engineering* **143**(1): 04016083, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001586](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001586).
- Chiwetalu UJ, Mbajjorgu CC and Ogbuagu NJ (2020) Remedial ability of maize (*Zea-Mays*) on lead contamination under potted condition and non-potted field soil condition. *Journal of Bioresources and Bioproducts* **5**(1): 51–59, <https://doi.org/10.1016/j.jobab.2020.03.006>.
- Choo CS and Ong DEL (2020) Assessment of non-linear rock strength parameters for the estimation of pipe-jacking forces. Part 2. Numerical modeling. *Engineering Geology* **265**: article 105405, <https://doi.org/10.1016/j.enggeo.2019.105405>.
- Chu J and Wen Z (2015) *Proof of Concept: Biocement for Road Repair*. Institute for Transportation, Iowa State University, Ames, IA, USA, InTrans Project Report 129.
- Comadran-Casas C, Schaschke CJ, Akunna JC and Jorat ME (2022) Cow urine as a source of nutrients for microbial-induced calcite precipitation in sandy soil. *Journal of Environmental Management* **304**: article 114307, <https://doi.org/10.1016/j.jenvman.2021.114307>.
- Coronado M, Blanco T, Quijorna N, Alonso-Santurde R and Andrés A (2015) Types of waste, properties and durability of toxic waste-based fired masonry bricks. In *Eco-Efficient Masonry Bricks and Blocks* (Pacheco-Torgal F, Lourenço PB, Labrincha JA, Kumar S and Chindaprasit P (eds)). Woodhead Publishing, Oxford, UK, pp. 129–188.
- Cuzman OA, Richter K, Wittig L and Tiano P (2015) Alternative nutrient sources for biotechnological use of *Sporosarcina pasteurii*. *World Journal of Microbiology and Biotechnology* **31**(6): 897–906, <https://doi.org/10.1007/s11274-015-1844-z>.
- De Garine-Wichatitsky M, Binot A, Ward J *et al.* (2021) ‘Health in’ and ‘health of’ social–ecological systems: a practical framework for the management of healthy and resilient agricultural and natural ecosystems. *Frontiers in Public Health* **8**: article 616328, <https://doi.org/10.3389/fpubh.2020.616328>.
- De Muynck W, De Belie N and Verstraete W (2010) Microbial carbonate precipitation in construction materials: a review. *Ecological Engineering* **36**(2): 118–136, <https://doi.org/10.1016/j.ecoleng.2009.02.006>.
- Debowski AW, Walton SM, Chua EG *et al.* (2017) *Helicobacter pylori* gene silencing in vivo demonstrates urease is essential for chronic infection. *PLOS Pathogens* **13**(6): article e1006464, <https://doi.org/10.1371/journal.ppat.1006464>.
- DeJong JT, Mortensen BM, Martinez BC and Nelson DC (2010) Bio-mediated soil improvement. *Ecological Engineering* **36**(2): 197–210, <https://doi.org/10.1016/j.ecoleng.2008.12.029>.
- Dilrukshi RAN and Kawasaki S (2019) Effect of plant-derived urease-induced carbonate formation on the strength enhancement of sandy soil. In *Ecological Wisdom Inspired Restoration Engineering* (Achal V and Mukherjee A (eds)). Springer, Singapore, pp. 93–108.
- Ditta ZM, Tanapongpisit N, Saenrang W *et al.* (2022) Bio-strengthening of cementitious composites from incinerated sugarcane filter cake by a calcifying bacterium *Lysinibacillus* sp. WH. *Scientific Reports* **12**: article 7026, <https://doi.org/10.1038/s41598-022-11330-5>.
- Dubey AA, Ravi K, Mukherjee A *et al.* (2021) Biocementation mediated by native microbes from Brahmaputra riverbank for mitigation of soil erodibility. *Scientific Reports* **11**: article 15250, <https://doi.org/10.1038/s41598-021-94614-6>.
- Ekprasert J, Fongkaew I, Chainakun P, Kamngam R and Boonsuan W (2020) Investigating mechanical properties and biocement application of CaCO₃ precipitated by a newly-isolated *Lysinibacillus* sp. WH using artificial neural networks. *Scientific Reports* **10**: article 16137, <https://doi.org/10.1038/s41598-020-73217-7>.
- Eltarahony M, Kamal A, Zaki S and Abd-El-Haleem D (2021) Heavy metals bioremediation and water softening using ureolytic strains *Metschnikowia pulcherrima* and *Raoultella planticola*. *Journal of Chemical Technology and Biotechnology* **96**(11): 3152–3165, <https://doi.org/10.1002/jctb.6868>.
- El Enshasy H, Dailin DJ, Malek RA *et al.* (2020) Biocement: a novel approach in the restoration of construction materials. In *Microbial Biotechnology Approaches to Monuments of Cultural Heritage* (Yadav AN, Rastegari AA, Gupta VK and Yadav N (eds)). Springer, Singapore, pp. 177–198.
- Eneyedi NT, Makk J, Kótai L *et al.* (2020) Cave bacteria-induced amorphous calcium carbonate formation. *Scientific Reports* **10**: article 8696, <https://doi.org/10.1038/s41598-020-65667-w>.
- Erdmann N, Kästner F, de Payrebrune K and Strieth D (2022) *Sporosarcina pasteurii* can be used to print a layer of calcium carbonate. *Engineering in Life Sciences* **22**(12): 760–768, <https://doi.org/10.1002/elsc.202100074>.
- Ezzat SM and Ewida AYI (2021) Smart soil grouting using innovative urease-producing bacteria and low cost materials. *Journal of Applied Microbiology* **131**(5): 2294–2307, <https://doi.org/10.1111/jam.15117>.
- Fan Y, Hu X, Zhao Y *et al.* (2020) Urease producing microorganisms for coal dust suppression isolated from coal: characterization and comparative study. *Advanced Powder Technology* **31**(9): 4095–4106, <https://doi.org/10.1016/j.apt.2020.08.014>.
- Fang C, Kumari D, Zhu X and Achal V (2018) Role of fungal-mediated mineralization in biocementation of sand and its improved compressive strength. *International Biodeterioration & Biodegradation* **133**: 216–220, <https://doi.org/10.1016/j.ibiod.2018.07.013>.
- Farajnia A, Shafaat A, Farajnia S, Sartipipour M and Khodadadi Tirkolaei H (2022) The efficiency of ureolytic bacteria isolated from historical adobe structures in the production of bio-bricks. *Construction and Building Materials* **317**: article 125868, <https://doi.org/10.1016/j.conbuildmat.2021.125868>.
- Farrugia MA, Macomber L and Hausinger RP (2013) Biosynthesis of the urease metallocenter. *Journal of Biological Chemistry* **288**(19): 13178–13185, <https://doi.org/10.1074/jbc.R112.446526>.
- Fatehi H, Ong DEL, Yu J and Chang I (2021) Biopolymers as green binders for soil improvement in geotechnical applications: a review. *Geosciences* **11**(7): article 291, <https://doi.org/10.3390/geosciences11070291>.
- Fu Q, Wu Y, Liu S, Lu L and Wang J (2022) The adaptability of *Sporosarcina pasteurii* in marine environments and the feasibility of its application in mortar crack repair. *Construction and Building Materials* **332**: article 127371, <https://doi.org/10.1016/j.conbuildmat.2022.127371>.
- Gao Y, Hang L, He J and Chu J (2019) Mechanical behaviour of biocemented sands at various treatment levels and relative densities. *Acta Geotechnica* **14**(3): 697–707, <https://doi.org/10.1007/s11440-018-0729-3>.
- Gat D, Tsesarsky M, Shamir D and Ronen Z (2014) Accelerated microbial-induced CaCO₃ precipitation in a defined coculture of ureolytic and non-ureolytic bacteria. *Biogeosciences* **11**(10): 2561–2569, <https://doi.org/10.5194/bg-11-2561-2014>.
- Ghasemi P and Montoya BM (2020) Field application of the microbially induced calcium carbonate precipitation on a coastal sandy slope. In *Geo-Congress 2020: Biogeotechnics* (Kavazanjian E, Hambleton JP, Makhnenko R and Budge AS (eds)). American Society of Civil Engineers, Reston, VA, USA, Geotechnical Special Publication 320, pp. 141–149.

- Gomez MG, Anderson CM, Graddy CMR et al. (2016) Large-scale comparison of bioaugmentation and biostimulation approaches for biocementation of sands. *Journal of Geotechnical and Geoenvironmental Engineering* **143**(5): 04016124, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001640](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001640).
- Gomez MG, Graddy CMR, Dejong JT, Nelson DC and Tsesarsky M (2018) Stimulation of native microorganisms for biocementation in samples recovered from field-scale treatment depths. *Journal of Geotechnical and Geoenvironmental Engineering* **144**(1): 04017098, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001804](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001804).
- Gowthaman S, Mitsuyama S, Nakashima K, Komatsu M and Kawasaki S (2018) Bio-inspired stabilization of embankment soil mediating *Psychrobacillus* sp. and low-grade chemicals: preliminary laboratory investigation. In *Proceedings of the Eighth International Conference on Geotechnique, Construction Materials and Environment (GEOMATE 2018)* (Shiau J, Hossain Z, Huat BBK, Anggraini V and Shiau J (eds)). Geomate International Society, Mie, Japan, pp. 163–168.
- Gowthaman S, Mitsuyama S, Nakashima K, Komatsu M and Kawasaki S (2019) Biogeotechnical approach for slope soil stabilization using locally isolated bacteria and inexpensive low-grade chemicals: a feasibility study on Hokkaido expressway soil, Japan. *Soils and Foundations* **59**(2): 484–499, <https://doi.org/10.1016/j.sandf.2018.12.010>.
- Gowthaman S, Nakashima K and Kawasaki S (2020) Freeze–thaw durability and shear responses of cemented slope soil treated by microbial induced carbonate precipitation. *Soils and Foundations* **60**(4): 840–855, <https://doi.org/10.1016/j.sandf.2020.05.012>.
- Gowthaman S, Nakashima K and Kawasaki S (2021) Durability analysis of bio-cemented slope soil under the exposure of acid rain. *Journal of Soils and Sediments* **21**(8): 2831–2844, <https://doi.org/10.1007/s11368-021-02997-w>.
- Gowthaman S, Mohsenzadeh A, Nakashima K and Kawasaki S (2022) Removal of ammonium by-products from the effluent of bio-cementation system through struvite precipitation. *Materials Today: Proceedings* **61**(2): 243–249, <https://doi.org/10.1016/j.matpr.2021.09.013>.
- Hadi S, Abbas H, Almajed A, Binyahya A and Al-Salloom Y (2022) Biocementation by *Sporosarcina pasteurii* ATCC6453 under simulated conditions in sand columns. *Journal of Materials Research and Technology* **18**: 4375–4384, <https://doi.org/10.1016/j.jmrt.2022.04.105>.
- Harkes MP, van Paassen LA, Booster JL, Whiffin VS and van Loosdrecht MCM (2010) Fixation and distribution of bacterial activity in sand to induce carbonate precipitation for ground reinforcement. *Ecological Engineering* **36**(2): 112–117, <https://doi.org/10.1016/j.ecoleng.2009.01.004>.
- He J, Chu J, Wu S and Peng J (2016) Mitigation of soil liquefaction using microbially induced desaturation. *Journal of Zhejiang University – SCIENCE A* **17**(7): 577–588, <https://doi.org/10.1631/jzus.A1600241>.
- Hoang T, Allenman J, Cetin B and Choi SG (2020) Engineering properties of biocementation coarse- and fine-grained sand catalyzed by bacterial cells and bacterial enzyme. *Journal of Materials in Civil Engineering* **32**(4): 04020030, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003083](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003083).
- Hoffmann TD, Paine K and Gebhard S (2021) Genetic optimisation of bacteria-induced calcite precipitation in *Bacillus subtilis*. *Microbial Cell Factories* **20**(1): article 214, <https://doi.org/10.1186/s12934-021-01704-1>.
- Hong M, Jang I, Son Y, Yi C and Park W (2021) Agricultural by-products and oyster shell as alternative nutrient sources for microbial sealing of early age cracks in mortar. *AMB Express* **11**(1): article 11, <https://doi.org/10.1186/s13568-020-01166-5>.
- Hu L, Wang H, Xu P and Zhang Y (2021a) Biomineralization of hypersaline produced water using microbially induced calcite precipitation. *Water Research* **190**: article 116753, <https://doi.org/10.1016/j.watres.2020.116753>.
- Hu W, Cheng WC, Wen S and Yuan K (2021b) Revealing the enhancement and degradation mechanisms affecting the performance of carbonate precipitation in EICP process. *Frontiers in Bioengineering and Biotechnology* **9**: article 750258, <https://doi.org/10.3389/fbioe.2021.750258>.
- Huff L, Delos C, Gallagher K and Beaman J (2013) *Aquatic Life Ambient Water Quality Criteria for Ammonia – Freshwater*. US Environmental Protection Agency, Washington, DC, USA.
- Iezzi B, Brady R, Sardag S, Eu B and Skerlos S (2019) Growing bricks: assessing biocement for lower embodied carbon structures. *Procedia CIRP* **80**: 470–475, <https://doi.org/10.1016/j.procir.2019.01.061>.
- Imran A, Nakashima K, Evelpidou N and Kawasaki S (2021) Improvement of using crude extract urease from watermelon seeds for biocementation technology. *International Journal of GEOMATE* **20**(78): 142–147, <https://doi.org/10.21660/2021.78.GX180>.
- Irfan MF, Hossain SMZ, Khalid H et al. (2019) Optimization of bio-cement production from cement kiln dust using microalgae. *Biotechnology Reports* **23**: article e00356, <https://doi.org/10.1016/j.btre.2019.e00356>.
- Ivanov V, Chu J and Stabnikov V (2015) Basics of construction microbial biotechnology. In *Biotechnologies and Biomimetics for Civil Engineering* (Pacheco Torgal F, Labrincha J, Diamanti M, Yu CP and Lee H (eds)). Springer, Cham, Switzerland, pp. 21–56.
- Ivanov V, Stabnikov V, Stabnikova O and Kawasaki S (2019) Environmental safety and biosafety in construction biotechnology. *World Journal of Microbiology and Biotechnology* **35**(2): article 26, <https://doi.org/10.1007/s11274-019-2598-9>.
- Jalilvand N, Akhgar A, Alikhani HA, Rahmani HA and Rejali F (2020) Removal of heavy metals zinc, lead, and cadmium by biomineralization of urease-producing bacteria isolated from Iranian mine calcareous soils. *Journal of Soil Science and Plant Nutrition* **20**(1): 206–219, <https://doi.org/10.1007/s42729-019-00121-z>.
- Jia H and Jian C (2014) Undrained responses of microbially desaturated sand under monotonic loading. *Journal of Geotechnical and Geoenvironmental Engineering* **140**(5): 04014003, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001082](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001082).
- Jiang NJ, Wang YJ, Chu J et al. (2022) Bio-mediated soil improvement: an introspection into processes, materials, characterization and applications. *Soil Use and Management* **38**(1): 68–93, <https://doi.org/10.1111/sum.12736>.
- Kahani M, Kalantary F, Soudi MR, Pakdel L and Aghaalizadeh S (2020) Optimization of cost effective culture medium for *Sporosarcina pasteurii* as biocementing agent using response surface methodology: up cycling dairy waste and seawater. *Journal of Cleaner Production* **253**: article 120022, <https://doi.org/10.1016/j.jclepro.2020.120022>.
- Kakelar MM, Ebrahimi S and Hosseini M (2016) Improvement in soil grouting by biocementation through injection method. *Asia-Pacific Journal of Chemical Engineering* **11**(6): 930–938, <https://doi.org/10.1002/apj.2027>.
- Kang B, Zha F, Deng W et al. (2022) Biocementation of pyrite tailings using microbially induced calcite carbonate precipitation. *Molecules* **27**(11): article 3608, <https://doi.org/10.3390/molecules27113608>.
- Karimian A, Hassanlourad M and Karimi GR (2021) Insight into the properties of surface percolated biocemented sand. *Geomicrobiology Journal* **38**(2): 138–149, <https://doi.org/10.1080/01490451.2020.1818147>.
- Khan MBE, Shen L and Dias-da-Costa D (2021) Self-healing behaviour of bio-concrete in submerged and tidal marine environments. *Construction and Building Materials* **277**: article 122332, <https://doi.org/10.1016/j.conbuildmat.2021.122332>.
- Kim Y, Kwon S and Roh Y (2021) Corrigendum: effect of divalent cations (Cu, Zn, Pb, Cd, and Sr) on microbially induced calcium carbonate precipitation and mineralogical properties. *Frontiers in Microbiology* **12**: article 721478, <https://doi.org/10.3389/fmicb.2021.721478>.
- Kou HL, Wu C, Jang BA and Wang D (2021) Spatial distribution of CaCO₃ in biocemented sandy slope using surface percolation. *Journal of*

- Materials in Civil Engineering* **33(6)**: 06021004, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003729](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003729).
- Lange L, Connor KO, Arason S *et al.* (2021) Developing a sustainable and circular bio-based economy in EU: by partnering across sectors, upscaling and using new knowledge faster, and for the benefit of climate, environment & biodiversity, and people & business. *Frontiers in Bioengineering and Biotechnology* **8**: article 619066, <https://doi.org/10.3389/fbioe.2020.619066>.
- Lapierre FM, Schmid J, Ederer B *et al.* (2020) Revealing nutritional requirements of MICP-relevant *Sporosarcina pasteurii* DSM33 for growth improvement in chemically defined and complex media. *Scientific Reports* **10**: article 22448, <https://doi.org/10.1038/s41598-020-79904-9>.
- Le ABD, Whyte A and Biswas WK (2019) Carbon footprint and embodied energy assessment of roof-covering materials. *Clean Technologies and Environmental Policy* **21(10)**: 1913–1923, <https://doi.org/10.1007/s10098-018-1629-9>.
- Lee YS and Park W (2019) Enhanced calcium carbonate-biofilm complex formation by alkali-generating *Lysinibacillus boronitolerans* YS11 and alkaliphilic *Bacillus* sp. AK13. *AMB Express* **9(1)**: article 49, <https://doi.org/10.1186/s13568-019-0773-x>.
- Lee M, Kolbus CM, Yezep AD and Gomez MG (2019) Investigating ammonium by-product removal following stimulated ureolytic microbially-induced calcite precipitation. In *Geo-Congress 2019: Soil Improvement* (Meehan CL, Kumar S, Pando MA and Coe JT (eds)). American Society of Civil Engineers, Reston, VA, USA, Geotechnical Special Publication 309, pp. 260–272.
- Lee M, Gomez MG, El Kortbawi M and Ziotopoulou K (2020) Examining the liquefaction resistance of lightly cemented sands using microbially induced calcite precipitation (MICP). In *Geo-Congress 2020: Biogeotechnics* (Kavazanjian E, Hambleton JP, Makhnenko R and Budge AS (eds)). American Society of Civil Engineers, Reston, VA, USA, Geotechnical Special Publication 320, pp. 53–64.
- Liu Z, Howe J, Wang X, Liang X and Runge T (2019) Use of dry dairy manure pellets as nutrient source for tomato (*Solanum lycopersicum* var. *cerasiforme*) growth in soilless media. *Sustainability* **11(3)**: article 811, <https://doi.org/10.3390/su11030811>.
- Liu S, Wen K, Amini F and Li L (2021) Investigation of nonwoven geotextiles for full contact flexible mould used in preparation of MICP-treated geomaterial. *International Journal of Geosynthetics and Ground Engineering* **6(2)**: article 14, <https://doi.org/10.1007/s40891-020-00197-z>.
- Liu Y, Ong DEL, Oh E, Liu Z and Hughes R (2022) Sustainable cementitious blends for strength enhancement of dredged mud in Queensland, Australia. *Geotechnical Research* **9(2)**: 65–82, <https://doi.org/10.1680/jgere.21.00046>.
- Luis A, Deng L, Shao L and Li H (2019) Triaxial behaviour and image analysis of Edmonton clay treated with cement and fly ash. *Construction and Building Materials* **197**: 208–219, <https://doi.org/10.1016/j.conbuildmat.2018.11.222>.
- Ma L, Pang AP, Luo Y, Lu X and Lin F (2020) Beneficial factors for biomineralization by ureolytic bacterium *Sporosarcina pasteurii*. *Microbial Cell Factories* **19(1)**: article 12, <https://doi.org/10.1186/s12934-020-1281-z>.
- Manzur T, Rahman F, Afroz S, Huq RS and Efaz IH (2017) Potential of a microbiologically induced calcite precipitation process for durability enhancement of masonry aggregate concrete. *Journal of Materials in Civil Engineering* **29(5)**: 04016290, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0001799](https://doi.org/10.1061/(ASCE)MT.1943-5533.0001799).
- Manzur T, Shams Huq R, Hasan Efaz I *et al.* (2019) Performance enhancement of brick aggregate concrete using microbiologically induced calcite precipitation. *Case Studies in Construction Materials* **11**: article e00248, <https://doi.org/10.1016/j.cscm.2019.e00248>.
- Marin S, Cabestrero O, Demergasso C *et al.* (2021) An indigenous bacterium with enhanced performance of microbially-induced Ca-carbonate biomineralization under extreme alkaline conditions for concrete and soil-improvement industries. *Acta Biomaterialia* **120**: 304–317, <https://doi.org/10.1016/j.actbio.2020.11.016>.
- Martin KK, Khodadadi TH, Chester M and Kavazanjian E (2020) Hotspot life cycle assessment for environmental impacts of EICP for ground improvement. In *Geo-Congress 2020: Biogeotechnics* (Kavazanjian E, Hambleton JP, Makhnenko R and Budge AS (eds)). American Society of Civil Engineers, Reston, VA, USA, Geotechnical Special Publication 320, pp. 321–329.
- Martinez BC, DeJong JT, Ginn TR *et al.* (2013) Experimental optimization of microbial-induced carbonate precipitation for soil improvement. *Journal of Geotechnical and Geoenvironmental Engineering* **139(4)**: 587–598, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0000787](https://doi.org/10.1061/(ASCE)GT.1943-5606.0000787).
- Menegat S, Ledo A and Tirado R (2022) Greenhouse gas emissions from global production and use of nitrogen synthetic fertilisers in agriculture. *Scientific Reports* **12**: article 14490, <https://doi.org/10.1038/s41598-022-18773-w>.
- Meng H, Shu S, Gao Y, He J and Wan Y (2021) Kitchen waste for *Sporosarcina pasteurii* cultivation and its application in wind erosion control of desert soil via microbially induced carbonate precipitation. *Acta Geotechnica* **16(12)**: 4045–4059, <https://doi.org/10.1007/s11440-021-01334-2>.
- Mirkouei A, Haapala KR, Sessions J and Murthy GS (2017) A mixed biomass-based energy supply chain for enhancing economic and environmental sustainability benefits: a multi-criteria decision making framework. *Applied Energy* **206**: 1088–1101, <https://doi.org/10.1016/j.apenergy.2017.09.001>.
- Mokhtar N, Megat Johari MA, Tajarudin HA, Al-Gheethi AA and Algaifi HA (2021) A sustainable enhancement of bio-cement using immobilised *Bacillus sphaericus*: optimization, microstructural properties, and techno-economic analysis for a cleaner production of bio-cementitious mortars. *Journal of Cleaner Production* **318**: article 128470, <https://doi.org/10.1016/j.jclepro.2021.128470>.
- Montoya BM, DeJong JT and Boulanger RW (2013) Dynamic response of liquefiable sand improved by microbial-induced calcite precipitation. *Géotechnique* **63(4)**: 302–312, <https://doi.org/10.1680/geot.SIP13.P.019>.
- Mortazavi BH, Kariminia T, Shahbodagh B, Rowshanzamir MA and Khoshghalb A (2021) Application of bio-cementation to enhance shear strength parameters of soil–steel interface. *Construction and Building Materials* **294**: article 123470, <https://doi.org/10.1016/j.conbuildmat.2021.123470>.
- Mujah D, Shahin MA and Cheng L (2017) State-of-the-art review of biocementation by microbially induced calcite precipitation (MICP) for soil stabilization. *Geomicrobiology Journal* **34(6)**: 524–537, <https://doi.org/10.1080/01490451.2016.1225866>.
- Myhr A, Røyne F, Brandtsegg AS *et al.* (2019) Towards a low CO₂ emission building material employing bacterial metabolism (2/2): prospects for global warming potential reduction in the concrete industry. *PLOS One* **14(4)**: article e0208643, <https://doi.org/10.1371/journal.pone.0208643>.
- Naemi M and Haddad A (2021) Environmental impacts of chemical and microbial grouting. *Environmental Science and Pollution Research* **27(2)**: 2264–2272, <https://doi.org/10.1007/s11356-019-06614-9>.
- Nething C, Smirnova M, Gröning JAD *et al.* (2020) A method for 3D printing bio-cemented spatial structures using sand and urease active calcium carbonate powder. *Materials and Design* **195**: article 109032, <https://doi.org/10.1016/j.matdes.2020.109032>.
- Nezhad MG, Tabarsa A and Latifi N (2021) Effect of natural and synthetic fibers reinforcement on California bearing ratio and tensile strength of clay. *Journal of Rock Mechanics and Geotechnical Engineering* **13(3)**: 626–642.
- Nvs B and Saranya PL (2020) Water pollutants monitoring based on Internet of things. In *Inorganic Pollutants in Water* (Devi P, Singh P

- and Kansal SK (eds)). Elsevier, Amsterdam, the Netherlands, pp. 371–397.
- O'Donnell ST, Rittmann BE and Kavazanjian E Jr (2017) MIDP: liquefaction mitigation via microbial denitrification as a two-stage process. I: Desaturation. *Journal of Geotechnical and Geoenvironmental Engineering* **143**(12): 04017094, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0001818](https://doi.org/10.1061/(ASCE)GT.1943-5606.0001818).
- Ojuri OO, Osagie PO, Oluymi-Ayibiwu BD *et al.* (2022) Eco-friendly stabilization of highway lateritic soil with cow bone powder admixed lime and plastic granules reinforcement. *Cleaner Waste Systems* **2**: article 100012, <https://doi.org/10.1016/j.clwas.2022.100012>.
- Omeregje AI, Senian N, Li PY and Ngu LH (2016) Ureolytic bacteria isolated from Sarawak limestone caves show high urease enzyme activity comparable to that of *Sporosarcina pasteurii* (DSM 33). *Malaysian Journal of Microbiology* **12**(6): 463–470.
- Omeregje AI, Khoshdelnezamiha G, Senian N, Ong DEL and Nissom PM (2017) Experimental optimisation of various cultural conditions on urease activity for isolated *Sporosarcina pasteurii* strains and evaluation of their biocement potentials. *Ecological Engineering* **109**: 65–75, <https://doi.org/10.1016/j.ecoleng.2017.09.012>.
- Omeregje AI, Palombo EA, Ong DEL and Nissom PM (2019) Biocementation of sand by *Sporosarcina pasteurii* strain and technical-grade cementation reagents through surface percolation treatment method. *Construction and Building Materials* **228**: article 116828, <https://doi.org/10.1016/j.conbuildmat.2019.116828>.
- Omeregje AI, Palombo EA, Ong DEL and Nissom PM (2020) A feasible scale-up production of *Sporosarcina pasteurii* using custom-built stirred tank reactor for in-situ soil biocementation. *Biocatalysis and Agricultural Biotechnology* **24**: article 101544, <https://doi.org/10.1016/j.bcab.2020.101544>.
- Omeregje AI, Palombo EA and Nissom PM (2021) Bioprecipitation of calcium carbonate mediated by ureolysis: a review. *Environmental Engineering Research* **26**(6): 200370–200379, <https://doi.org/10.4491/eeer.2020.379>.
- Omeregje AI, Muda K, Bakri MKB *et al.* (2022a) Calcium carbonate bioprecipitation mediated by ureolytic bacteria grown in pelletized organic manure medium. *Biomass Conversion and Biorefinery*, <https://doi.org/10.1007/s13399-022-03239-w>.
- Omeregje AI, Muda K and Ngu LH (2022b) Dairy manure pellets and palm oil mill effluent as alternative nutrient sources in cultivating *Sporosarcina pasteurii* for calcium carbonate bioprecipitation. *Letters in Applied Microbiology* **74**(5): 671–683, <https://doi.org/10.1111/lam.13652>.
- Osinubi KJ, Eberemu AO, Ijimdiya TS *et al.* (2020) Review of the use of microorganisms in geotechnical engineering applications. *SN Applied Sciences* **2**(2): article 207, <https://doi.org/10.1007/s42452-020-1974-2>.
- Ouyang Q, Xiao H, Li Z *et al.* (2022) Experimental study on the influence of microbial content on engineering characteristics of improved expansive soil. *Frontiers in Earth Science* **10**: article 863357, <https://doi.org/10.3389/feart.2022.863357>.
- Pakbaz MS, Ghezlbash GR and Afzal A (2020) Sugarcane molasses: a cheap carbon source for calcite production in different class of soils using stimulation of indigenous urease-producing bacteria. *Geomicrobiology Journal* **37**(3): 213–229, <https://doi.org/10.1080/01490451.2019.1691684>.
- Peerun MI, Ong DEL, Choo CS and Cheng WC (2020) Effect of interparticle behavior on the development of soil arching in soil–structure interaction. *Tunnelling and Underground Space Technology* **106**: article 103610, <https://doi.org/10.1016/j.tust.2020.103610>.
- Peng J and Liu Z (2019) Influence of temperature on microbially induced calcium carbonate precipitation for soil treatment. *PLOS One* **14**(6): article e0218396, <https://doi.org/10.1371/journal.pone.0218396>.
- Peng J, Cao T, He J, Dai D and Tian Y (2022) Improvement of coral sand with MICP using various calcium sources in sea water environment. *Frontiers in Physics* **82**: article 825409, <https://doi.org/10.3389/fphy.2022.825409>.
- Pham VP, Nakano A, Van Der Star WRL, Heimovaara TJ and Van Paassen LA (2018) Applying MICP by denitrification in soils: a process analysis. *Environmental Geotechnics* **5**(2): 79–93, <https://doi.org/10.1680/jenge.15.00078>.
- Porter H, Dharmi NK and Mukherjee A (2018) Sustainable road bases with microbial precipitation. *Proceedings of the Institution of Civil Engineers – Construction Materials* **171**(3): 95–108, <https://doi.org/10.1680/jcoma.16.00075>.
- Porter H, Mukherjee A, Tuladhar R and Dharmi NK (2021) Life cycle assessment of biocement: an emerging sustainable solution? *Sustainability* **13**(4): article 13878, <https://doi.org/10.3390/su132413878>.
- Rangamaran VR and Shanmugam VK (2019) Biocalcification by piezotolerant *Bacillus* sp. NIOTVJ5 isolated from deep sea sediment and its influence on the strength of concrete specimens. *Marine Biotechnology* **21**(2): 161–170, <https://doi.org/10.1007/s10126-018-9867-8>.
- Safdar MU, Mavroulidou M, Gunn MJ *et al.* (2021) Innovative methods of ground improvement for railway embankment peat fens foundation soil. *Géotechnique* **71**(11): 985–998, <https://doi.org/10.1680/jgeot.19.SiP.030>.
- San Pablo AC, Lee M, Graddy MC *et al.* (2020) Meter-scale biocementation experiments to advance process control and reduce impacts: examining spatial control, ammonium by-product removal, and chemical reductions. *Journal of Geotechnical and Geoenvironmental Engineering* **146**(11): 04020125, [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0002377](https://doi.org/10.1061/(ASCE)GT.1943-5606.0002377).
- Scrivener KL, John VM and Gartner EM (2018) Eco-efficient cements: potential economically viable solutions for a low-CO₂ cement-based materials industry. *Cement and Concrete Research* **114**: 2–26, <https://doi.org/10.1016/j.cemconres.2018.03.015>.
- Shanahan CD (2016) *Improving the Resiliency of Coastal Sand Dunes Using Microbial Induced Calcite Precipitation*. MSc thesis, North Carolina State University, Raleigh, NC, USA.
- Sharma M and Satyam N (2021) Strength and durability of biocemented sands: wetting–drying cycles, ageing effects, and liquefaction resistance. *Geoderma* **402**: article 115359, <https://doi.org/10.1016/j.geoderma.2021.115359>.
- Sharma M, Satyam N and Reddy KR (2021) Effect of freeze–thaw cycles on engineering properties of biocemented sand under different treatment conditions. *Engineering Geology* **284**: article 106022, <https://doi.org/10.1016/j.enggeo.2021.106022>.
- Shougrakpam S and Trivedi A (2021) Harnessing microbially induced calcite precipitates to use in improving the engineering properties of loose sandy soils. *Sādhanā* **46**(1): article 41, <https://doi.org/10.1007/s12046-021-01563-x>.
- Snigdha PB and Latkar VM (2020) Microbially induced calcium carbonate precipitation in construction materials. *Journal of Materials in Civil Engineering* **32**(5): 03120001, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003141](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003141).
- Song C, Zhao Y, Cheng W *et al.* (2021) Preparation of microbial dust suppressant and its application in coal dust suppression. *Advanced Powder Technology* **32**(12): 4509–4521, <https://doi.org/10.1016/j.apt.2021.10.001>.
- Šovljanski O, Pezo L, Grahovac J *et al.* (2022) Best-performing *Bacillus* strains for microbially induced CaCO₃ precipitation: screening of relative influence of operational and environmental factors. *Journal of Biotechnology* **350**: 31–41, <https://doi.org/10.1016/j.jbiotec.2022.04.002>.

- Stocks-Fischer S, Galinat JK and Bang SS (1999) Microbiological precipitation of CaCO_3 . *Soil Biology and Biochemistry* **31(11)**: 1563–1571, [https://doi.org/10.1016/S0038-0717\(99\)00082-6](https://doi.org/10.1016/S0038-0717(99)00082-6).
- Sun J, Oh E and Ong DE (2021) Influence of degree of saturation (DOS) on dynamic behavior of unbound granular materials. *Geosciences* **11(2)**: article 89, <https://doi.org/10.3390/geosciences11020089>.
- Sun X, Miao L, Chen R, Wang H and Xia J (2022) Surface rainfall erosion resistance and freeze–thaw durability of bio-cemented and polymer-modified loess slopes. *Journal of Environmental Management* **301**: article 113883, <https://doi.org/10.1016/j.jenvman.2021.113883>.
- Swane S, Sigurdarson JJ, Finkenwirth F, Eitinger T and Karring H (2020) Inhibition of urease activity by different compounds provides insight into the modulation and association of bacterial nickel import and ureolysis. *Scientific Reports* **10(1)**: article 8503, <https://doi.org/10.1038/s41598-020-65107-9>.
- Tamayo-Figueroa DP, Castillo E and Brandão PFB (2019) Metal and metalloid immobilization by microbiologically induced carbonates precipitation. *World Journal of Microbiology and Biotechnology* **35(4)**: article 58, <https://doi.org/10.1007/s11274-019-2626-9>.
- Tan T, Huat BBK, Anggraini V, Shukla SK and Nahazanan H (2021) Strength behavior of fly ash-stabilized soil reinforced with coir fibers in alkaline environment. *Journal of Natural Fibers* **18(11)**: 1556–1569, <https://doi.org/10.1080/15440478.2019.1691701>.
- Tang CS, Yin LY, Jiang NJ *et al.* (2020) Factors affecting the performance of microbial-induced carbonate precipitation (MICP) treated soil: a review. *Environmental Earth Sciences* **79(5)**: article 94, <https://doi.org/10.1007/s12665-020-8840-9>.
- Umar M, Kassim KA and Ping Chiet KT (2016) Biological process of soil improvement in civil engineering: a review. *Journal of Rock Mechanics and Geotechnical Engineering* **8(5)**: 767–774, <https://doi.org/10.1016/j.jrmge.2016.02.004>.
- van Paassen L (2009) *BiogROUT: Ground Improvement by Microbially Induced Carbonate Precipitation*. PhD thesis, Delft University of Technology, Delft, the Netherlands.
- van Paassen LA, Harkes MP, Van Zwieten GA *et al.* (2009) Scale up of BioGrout: a biological ground reinforcement method. In *Proceedings of the 17th International Conference on Soil Mechanics and Geotechnical Engineering: The Academia and Practice of Geotechnical Engineering* (Hamza M, Shahien M and El-Mossallamy Y (eds)). IOS Press, Amsterdam, the Netherlands, pp. 2328–2333.
- Veaudor T, Cassier-Chauvat C and Chauvat F (2019) Genomics of urea transport and catabolism in cyanobacteria: biotechnological implications. *Frontiers in Microbiology* **10**: article 2052, <https://doi.org/10.3389/fmicb.2019.02052>.
- Velardo P, Sáez del Bosque IF, Sánchez de Rojas MI, De Belie N and Medina C (2022) Durability of concrete bearing polymer-treated mixed recycled aggregate. *Construction and Building Materials* **315**: article 125781, <https://doi.org/10.1016/j.conbuildmat.2021.125781>.
- Wang C, Ren J, Qiao X and Habib M (2021a) Ammonium removal efficiency of biochar-based heterotrophic nitrifying bacteria immobilization body in water solution. *Environmental Engineering Research* **26(1)**: 190450–190451, <https://doi.org/10.4491/eer.2019.451>.
- Wang W, Duan Y, Wu Y *et al.* (2021b) Harmless treatment of cyanide tailings by a bifunctional strain JK-1 based on biodegradation and biomineralization. *Journal of Cleaner Production* **313**: article 127757, <https://doi.org/10.1016/j.jclepro.2021.127757>.
- Wei T, Li H, Yashir N *et al.* (2022) Effects of urease-producing bacteria and eggshell on physiological characteristics and Cd accumulation of pakchoi (*Brassica chinensis* L.) plants. *Environmental Science and Pollution Research* **29(42)**: 2924–2935, <https://doi.org/10.1007/s11356-022-20344-5>.
- Wen K, Li Y, Liu S, Bu C and Li L (2019) Development of an improved immersing method to enhance microbial induced calcite precipitation treated sandy soil through multiple treatments in low cementation media concentration. *Geotechnical and Geological Engineering* **37(2)**: 1015–1027, <https://doi.org/10.1007/s10706-018-0669-6>.
- Whiffin VS (2004) *Microbial CaCO_3 Precipitation for the Production of Biocement*. PhD thesis, Murdoch University, Perth, Australia.
- Xiang J, Qiu J, Wang Y and Gu X (2022) Calcium acetate as calcium source used to biocement for improving performance and reducing ammonia emission. *Journal of Cleaner Production* **348**: article 131286, <https://doi.org/10.1016/j.jclepro.2022.131286>.
- Xiao JZ, Wei YQ, Cai H *et al.* (2020) Microbial-induced carbonate precipitation for strengthening soft clay. *Advances in Materials Science and Engineering* **2020**: article 8140724, <https://doi.org/10.1155/2020/8140724>.
- Xiao Y, Ma G, Wu H, Lu H and Zaman M (2022a) Rainfall-induced erosion of biocemented graded slopes. *International Journal of Geomechanics* **22(1)**: 04021256, [https://doi.org/10.1061/\(ASCE\)GM.1943-5622.0002239](https://doi.org/10.1061/(ASCE)GM.1943-5622.0002239).
- Xiao Y, Xiao W, Ma G *et al.* (2022b) Mechanical performance of biotreated sandy road bases. *Journal of Performance of Constructed Facilities* **36(1)**: article 04021111, [https://doi.org/10.1061/\(ASCE\)CF.1943-5509.0001671](https://doi.org/10.1061/(ASCE)CF.1943-5509.0001671).
- Yang Y, Chu J, Cao B, Liu H and Cheng L (2020) Biocementation of soil using non-sterile enriched urease-producing bacteria from activated sludge. *Journal of Cleaner Production* **262**: article 121315, <https://doi.org/10.1016/j.jclepro.2020.121315>.
- Yang Y, Chu J, Cheng L and Liu H (2022) Utilization of carbide sludge and urine for sustainable biocement production. *Journal of Environmental Chemical Engineering* **10(3)**: article 107443, <https://doi.org/10.1016/j.jece.2022.107443>.
- Yoosathaporn S, Tiangburanatham P, Bovonsombut S, Chaipanich A and Pathom-aree W (2016) A cost effective cultivation medium for biocalcification of *Bacillus pasteurii* KCTC 3558 and its effect on cement cubes properties. *Microbiological Research* **186–187**: 132–138, <https://doi.org/10.1016/j.micres.2016.03.010>.
- Yu X and Rong H (2022) Seawater based MICP cements two/one-phase cemented sand blocks. *Applied Ocean Research* **118**: article 102972, <https://doi.org/10.1016/j.apor.2021.102972>.
- Yu X, Chu J, Yang Y and Qian C (2021) Reduction of ammonia production in the biocementation process for sand using a new biocement. *Journal of Cleaner Production* **286**: article 124928, <https://doi.org/10.1016/j.jclepro.2020.124928>.
- Yu X, Wang Z and Wang J (2022) Mechanical properties of bio-cementation materials in pre-precipitation mixing process. *Environmental Science and Pollution Research* **29(1)**: 1314–1323, <https://doi.org/10.1007/s11356-021-15750-0>.
- Yuan H, Ren G, Liu K, Zheng W and Zhao Z (2020) Experimental study of EICP combined with organic materials for silt improvement in the yellow river flood area. *Applied Sciences* **10(21)**: article 7678, <https://doi.org/10.3390/app10217678>.
- Zeng Y, Chen Z, Du Y *et al.* (2021) Microbiologically induced calcite precipitation technology for mineralizing lead and cadmium in landfill leachate. *Journal of Environmental Management* **296**: article 113199, <https://doi.org/10.1016/j.jenvman.2021.113199>.
- Zhalehjoon N, Tolooiyan A, Mackay R and Bodin D (2018) The effect of instrumentation on the determination of the resilient modulus of unbound granular materials using advanced repeated load triaxial testing. *Transportation Geotechnics* **14**: 190–201, <https://doi.org/10.1016/j.trgeo.2018.01.003>.
- Zhao Q, Li L, Li C *et al.* (2014a) A full contact flexible mold for preparing samples based on microbial-induced calcite precipitation technology. *Geotechnical Testing Journal* **37(5)**: 917–921, <https://doi.org/10.1520/GTJ20130090>.
- Zhao Q, Li L, Li C *et al.* (2014b) Factors affecting improvement of engineering properties of MICP-treated soil catalyzed by bacteria and urease. *Journal of Materials in Civil Engineering* **26(12)**: 04014094, [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0001013](https://doi.org/10.1061/(ASCE)MT.1943-5533.0001013).

Zhao Y, Yao J, Yuan Z *et al.* (2017) Bioremediation of Cd by strain GZ-22 isolated from mine soil based on biosorption and microbially induced carbonate precipitation. *Environmental Science and Pollution Research* **24**(1): 372–380, <https://doi.org/10.1007/s11356-016-7810-y>.

Zhou C, Bhinderwala F, Lehman MK *et al.* (2019) Urease is an essential component of the acid response network of *Staphylococcus aureus* and is required for a persistent murine kidney infection. *PLOS Pathogens* **15**(1): article e1007538, <https://doi.org/10.1371/journal.ppat.1007538>.

How can you contribute?

To discuss this paper, please submit up to 500 words to the editor at journals@ice.org.uk. Your contribution will be forwarded to the author(s) for a reply and, if considered appropriate by the editorial board, it will be published as a discussion in a future issue of the journal.