

PAPER

Symmetric dynamic behaviour of a superconducting proximity array with respect to field reversal

To cite this article: M Lankhorst and N Poccia 2017 *J. Phys.: Condens. Matter* **29** 024003

View the [article online](#) for updates and enhancements.

Related content

- [Proximity coupling in superconductor-graphene heterostructures](#)
Gil-Ho Lee and Hu-Jong Lee
- [Proximity-induced superconductivity in bismuth nanostripes](#)
Soraya Sangiao, Laura Casado, Luis Morellón et al.
- [Coulomb interaction effects on the Majorana states in quantum wires](#)
A Manolescu, D C Marinescu and T D Stanescu



IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

Symmetric dynamic behaviour of a superconducting proximity array with respect to field reversal

M Lankhorst¹ and N Poccia^{1,2,3}

¹ MESA+ Institute for Nanotechnology, University of Twente, 7500 AE Enschede, The Netherlands

² NEST Istituto Nanoscienze-CNR, Scuola Normale Superiore, Pisa, Italy

E-mail: n.poccia@utwente.nl

Received 31 July 2016, revised 21 September 2016

Accepted for publication 26 September 2016

Published 14 November 2016



Abstract

As the complexity of strongly correlated systems and high temperature superconductors increases, so does also the essential complexity of defects found in these materials and the complexity of the supercurrent pathways. It can be therefore convenient to realize a solid-state system with regular supercurrent pathways and without the disguising effects of disorder in order to capture the essential characteristics of a collective dynamics. Using a square array of superconducting islands placed on a normal metal, we observe a state in which magnetic field-induced vortices are frozen in the dimples of the egg crate potential by their strong repulsion interaction. In this system a dynamic vortex Mott insulator transition has been previously observed. In this work, we will show the symmetric dynamic behaviour with respect to field reversal and we will compare it with the asymmetric behaviour observed at the dynamic vortex Mott transition.

Keywords: superconductivity, vortex, critical dynamics, supercurrent pathways, Mott physics

(Some figures may appear in colour only in the online journal)

1. Introduction

In spatially inhomogeneous systems carriers create complex spatial pathways and their band-structure becomes more difficult to connect with the physical properties of the material [1, 2]. High temperature superconductors belong to this latter class of materials where a non-Fermi liquid is observed [3].

Most of the manifestations of non-Fermi liquid behaviour occurs in material with a very high degree of inhomogeneity which is quite difficult to control [4, 5]. Although disorder and inhomogeneities in strongly correlated electron systems could be considered an annoyance, it seems on the other hand that

they are unavoidable as shown in several experiments with atomic scale resolution [6–10].

In prototypical cuprate superconductors, x-ray images have considered that correlated disorder could be actually beneficial [11, 12]. It has been experimentally observed that nanostructures of the quenched disorder within the spacer layer are anti-correlated with the charge density puddles accompanied by local lattice distortions of the active layer [13–15] [17] [18]. Moreover, the tuning of the superconducting properties in the active layers is inseparably given by the properties of the spacer layers that can also be controlled through a continuous light illumination [16]. As a result of the tuning, an optimal mix of anti-correlated fractal nanostructures between the active and the spacer layer has been suggested to determine an optimal spatial pathways for supercurrents [14, 18].

However, the morphology of these spatial pathways of supercurrents and their collective behaviour is considered an open problem [19]. In superconducting networks the superconducting critical temperature is dependent on the geometrical

³ This article belongs to the [special issue: Emerging Leaders](#), which features invited work from the best early-career researchers working within the scope of *Journal of Physics: Condensed Matter*. This project is part of the *Journal of Physics series'* 50th anniversary celebrations in 2017. Nicola Poccia was selected by the Editorial Board of *Journal of Physics: Condensed Matter* as an Emerging Leader.

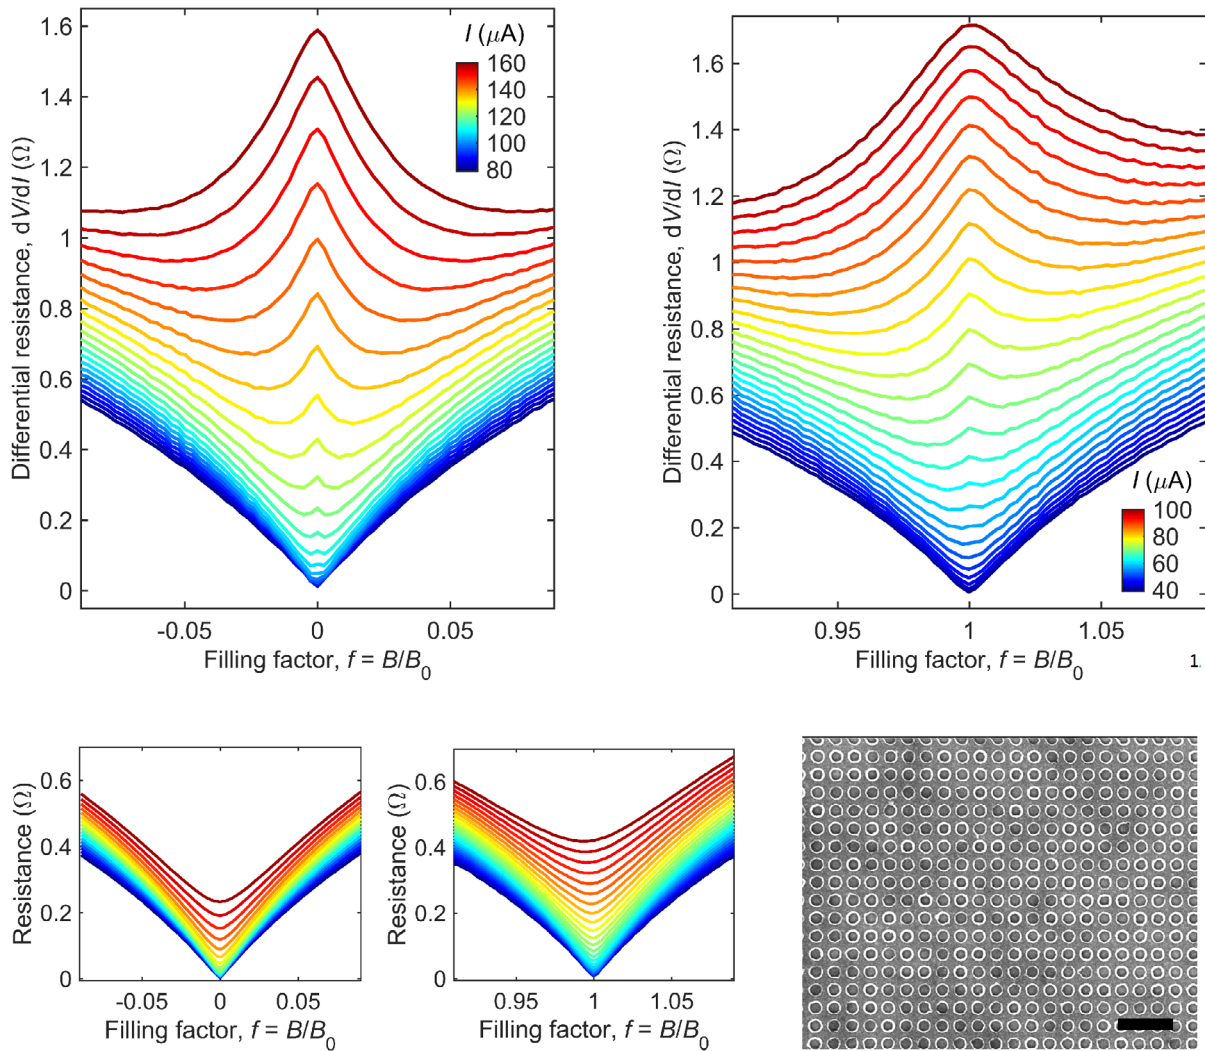


Figure 1. Comparison of the critical behavior around $f = 0$ and $f = 1$. The upper left panel shows the differential resistance, dV/dI , around $f = 0$. The lower left panel shows the corresponding resistance around $f = 0$. The upper right panel shows the differential resistance, dV/dI , around $f = 1$. The lower center panel shows the corresponding resistance around $f = 1$. The color bar shows the external current, and the resistance panels have the same current range as their respective dV/dI panel. The lower right panel shows the SEM image of a portion of the superconducting proximity array. The scale bar is $1 \mu\text{m}$.

parameters of the network [20–23]. The relevance of the geometry for the spatial pathways of supercurrents is shown by a recent experiment on an artificial man-made superconducting proximity array where supercurrents can flow in regular and well controlled pathways [24]. In this array of superconducting islands, the supercurrent pathways form vortices that are trapped between the islands in the areas of weaker proximity-induced superconductivity. Since the Feynman pathways interpretation of quantum mechanics [25] and of continuous quantum phase transitions [26], this system can be mapped to a Mott insulating state that forms when the particle concentration matches the density of the regular potential minima [27]. Via the vortex-particle mapping, in fact, the vortices sitting at the sites between the islands take the role of electrons in an electronic Mott insulator. With the application of an electric field, a collective dynamic phase transition between a vortex-Mott-insulator and a vortex-metal is observed [24].

In this weakly coupled superconducting proximity array, a classical critical dynamics of the vortex lattices is observed. We will show the transition upon magnetic field reversal, discussing the symmetrical aspects in comparison with its asymmetric counterpart observed at integer fillings of the vortex lattice.

2. Experimental method

A square array of 270-by-270 Nb islands was grown on a 40 nm thin layer of gold on top of a Si substrate. The gold layer was fabricated with photolithography and DC sputtering. The Nb islands were fabricated with e-beam lithography and DC sputtering. The islands have a diameter of 180 nm and the array has a lattice constant of 250 nm. A four-point probe measurement was done to obtain the voltage and differential resistance as a function of a transverse magnetic field. The

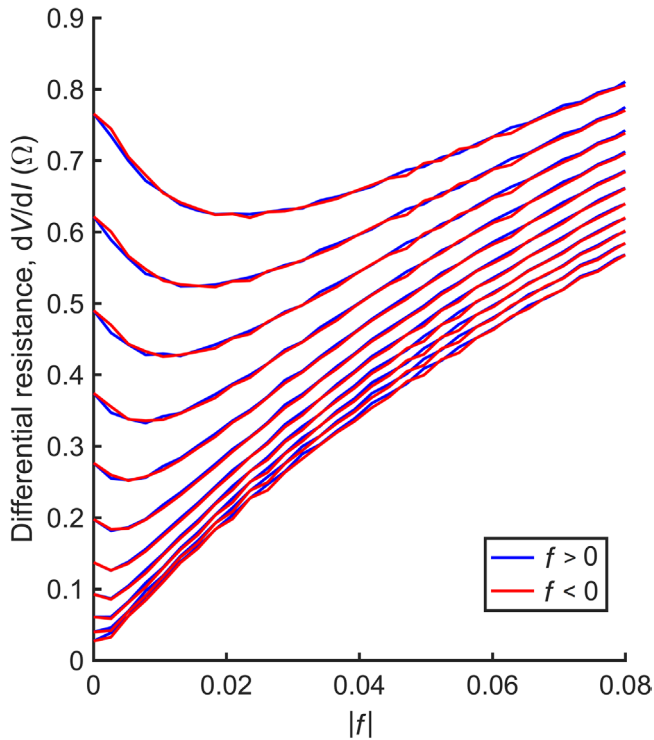


Figure 2. Symmetric dynamic behaviour with respect to field reversal. The same differential resistance around $f = 0$ as in figure 1, but now as a function of $|f|$ instead of f . The curves for negative f and positive f fall on top of each other, showing that around $f = 0$, the differential resistance is symmetric upon mirroring the magnetic field about the critical point. This is in contrast to the data around $f = 1$, where this mirror symmetry clearly does not hold.

transport measurements were done in a liquid helium bath cryostat at 4.14 K.

3. Results and discussion

Vortices occur in superconductors because the phase of the superconducting order parameter around a closed loop can pick up an integer times 2π . In contrast to Abrikosov vortices, where this loop encircles a normal core, the loop contains the weak links between the superconducting islands. If one forms a closed path between four such links along the Josephson junctions, the sum of the phase difference picked up in the junctions must add up to an integer times 2π . This integer counts the number of Josephson vortices.

The number of Josephson vortices in the square array is proportional to the perpendicular external magnetic field. The magnetic field at which the number of vortices matches the traps in our square array is $B_0 = \Phi_0/a^2$, with $\Phi_0 = \pi\hbar/e$ being the magnetic flux quantum [28]. The vortex filling fraction is defined as $f = B/B_0$. This means that $f = 1$ corresponds to one vortex per lattice cell. The vortices repel each other, and in the ground state the vortices form a periodic pattern. If the filling factor is a rational value p/q , the ground state vortex configuration is a q by q superlattice. The ground state energy versus f is described by the Harper equation [29]. The minima in the magnetoresistance as described in [24] are

resulting from a Hofstadter-type energy spectrum [30]. In this experiment, we apply an external current and measure the regime where a finite voltage is measured, so phase slips occur and the Josephson vortices are not stationary.

Figure 1 shows a scanning electron microscopy image (SEM) of the superconducting array of Nb islands, the measurements done around $f = 0$ and $f = 1$ for comparison upon the application of a current. The resistances corresponding to the differential resistance, dV/dI are shown. The resistance around $f = 0$ and $f = 1$ show pronounced dips indicating strong pinning at rational f . The minima remains even at the currents where dV/dI shows profound maxima. The vortex phase pinned around $f = 1$ is a vortex Mott insulator [31], and the transition is a dynamic vortex Mott transition [24].

In this superconducting proximity array the dip to peak reversal for $f = 0$ occurs in the range of 80 to 160 μA . Visual inspection of the shape of this current driven transition shows a symmetry around the magnetic field reversal. The nature of this symmetry is further shown in figure 2. Here the two side of the transition are plotted one on the top of each other. The superposition shows the symmetric behaviour. Around $f = 1$, this mirror symmetry around $f = f_c$ is clearly broken. In the analogy with the electronic Mott insulator proposed in [24], the asymmetry is explained by noting that the $f < 1$ regime corresponds to a hole doped Mott insulator, while the $f > 1$ regime corresponds to an electron doped, which need not have the same physical behaviour.

In conclusion, we have showed the differential resistance in a superconducting proximity array and compared its symmetric behaviour at $f = 0$ with the dynamic vortex Mott insulator to metal transition, observed at $f = 1$. Further experimental and theoretical investigations are under way to determine the origin of this difference and its implication for the strongly correlated electronic systems.

Acknowledgments

The work was supported by the Dutch FOM and NWO foundations and the Italian Ministry for Education and Research.

References

- [1] Dagotto E 2005 Complexity in strongly correlated electronic systems *Science* **309** 257–62
- [2] Shengelaya A and Muller K A 2015 The intrinsic heterogeneity of superconductivity in the cuprates *Europhys. Lett.* **109** 27001
- [3] Keimer B, Kivelson S A, Norman M R, Uchida S and Zaanen J 2015 From quantum matter to high-temperature superconductivity in copper oxides *Nature* **518** 179–86
- [4] Phillips J C, Saxena A and Bishop A R 2003 Pseudogaps, dopants, and strong disorder in cuprate high-temperature superconductors *Rep. Prog. Phys.* **66** 2111–82
- [5] Kresin V, Ovchinnikov Y and Wolf S 2006 Inhomogeneous superconductivity and the pseudogap state of novel superconductors *Phys. Rep.* **431** 231–59
- [6] Maska M M 2007 Inhomogeneity-induced enhancement of the pairing interaction in cuprate superconductors *Phys. Rev. Lett.* **99** 147006

- [7] Slezak J A *et al* 2008 Imaging the impact on cuprate superconductivity of varying the interatomic distances within individual crystal unit cells *Proc. Natl Acad. Sci.* **105** 3203–8
- [8] Wise W D *et al* 2009 Imaging nanoscale fermi-surface variations in an inhomogeneous superconductor *Nat. Phys.* **5** 213–6
- [9] Zeljkovic I *et al* 2012 Imaging the impact of single oxygen atoms on superconducting $\text{Bi}_{2+y}\text{Sr}_{2-y}\text{CaCu}_2\text{O}_{8+x}$ *Science* **337** 320–3
- [10] Zeljkovic I *et al* 2014 Nanoscale interplay of strain and doping in a high-temperature superconductor *Nano Lett.* **14** 6749–53
- [11] Zaanen J 2010 High-temperature superconductivity: the benefit of fractal dirt *Nature* **466** 825–7
- [12] Littlewood P B 2011 Superconductivity: an x-ray oxygen regulator *Nat. Mater.* **10** 726–7
- [13] Fratini M *et al* 2010 Scale-free structural organization of oxygen interstitials in $\text{La}_2\text{CuO}_{4+y}$ *Nature* **466** 841–4
- [14] Poccia N *et al* 2012 Optimum inhomogeneity of local lattice distortions in $\text{La}_2\text{CuO}_{4+y}$ *Proc. Natl Acad. Sci.* **109** 15685–90
- [15] Poccia N, Ricci A and Bianconi A 2011 Fractal structure favoring superconductivity at high temperatures in a stack of membranes near a strain quantum critical point *J. Supercond. Novel Magn.* **24** 1195–200
- [16] Poccia N *et al* 2011 Evolution and control of oxygen order in a cuprate superconductor *Nat. Mater.* **10** 733–6
- [17] Poccia N, Ricci A, Campi G, Caporale A S and Bianconi A 2013 Competing striped structures in $\text{La}_2\text{CuO}_{4+y}$ *J. Supercond. Novel Magn.* **26** 2703–8
- [18] Campi G *et al* 2015 Inhomogeneity of charge-density-wave order and quenched disorder in a high- T_c superconductor *Nature* **525** 359–62
- [19] Carlson E W 2015 Condensed-matter physics: charge topology in superconductors *Nature* **525** 329–30
- [20] Tinkham M, Abraham D W and Lobb C J 1983 Periodic flux dependence of the resistive transition in two-dimensional superconducting arrays *Phys. Rev. B* **28** 6578–81
- [21] Baturina T I, Tsaplin Yu A, Plotnikov A E and Baklanov M R 2005 Anomalous behavior near T_c and synchronization of Andreev reflection in two-dimensional arrays of SNS junctions *JETP Lett.* **81** 10–4
- [22] Eley S, Gopalakrishnan S, Goldbart P M and Mason N 2011 Approaching zero-temperature metallic states in mesoscopic superconductor-normal-superconductor arrays *Nat. Phys.* **8** 59–62
- [23] Bianconi G 2013 Superconductor-insulator transition in a network of 2d percolation clusters *Europhys. Lett.* **101** 26003
- [24] Poccia N *et al* 2015 Critical behavior at a dynamic vortex insulator-to-metal transition *Science* **349** 1202–5
- [25] Feynman R P 1972 *Statistical Mechanics* (New York: Benjamin)
- [26] Sondhi S L, Girvin S M, Carini J P and Shahar D 1997 Continuous quantum phase transitions *Rev. Mod. Phys.* **69** 315–33
- [27] Nelson D R and Vinokur V M 1993 Boson localization and correlated pinning of superconducting vortex arrays *Phys. Rev. B* **48** 13060–97
- [28] Baturina T I *et al* 2011 Nanopattern-stimulated superconductor-insulator transition in thin TiN films *Europhys. Lett.* **93** 47002
- [29] Harper P G 1955 Single band motion of conduction electrons in a uniform magnetic field *Proc. Phys. Soc. A* **68** 874–8
- [30] Hofstadter D R 1976 Energy levels and wave functions of bloch electrons in rational and irrational magnetic fields *Phys. Rev. B* **14** 2239–49
- [31] Goldberg S *et al* 2009 Mott insulator phases and first-order melting in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ crystals with periodic surface holes *Phys. Rev. B* **79** 064523