


# Effect of environmental conditions on the durability of polycarbonate for the protection of cultural heritage sites

Journal of Applied Biomaterials &  
Functional Materials  
October-December: 1–6  
© The Author(s) 2019  
Article reuse guidelines:  
sagepub.com/journals-permissions  
DOI: 10.1177/2280800019881626  
journals.sagepub.com/home/jbf  


Laura Ascione<sup>1,2</sup>, Maria Chiara Mistretta<sup>1,2</sup>, Maria Pia Pedferri<sup>3,4</sup>  and Francesco Paolo La Mantia<sup>1,2</sup>

## Abstract

Polycarbonate is a good material for covering and protecting cultural heritage sites because of its durability, mechanical properties, and transparency. However, polycarbonate degrades under environmental weathering with a significant decrease of physical and mechanical properties and loss of transparency. In this work, the contemporary presence of ultraviolet irradiation and different temperature and moisture conditions have been taken into account to study the environmental degradation of this polymer with regard to its mechanical and optical properties. The photo-oxidation reactions cause a decrease in the molecular weight and the formation of many oxygenated species. The hydrolytic scission, instead, gives rise to a remarkable reduction in the molecular weight. These two different degradation mechanisms do not seem interconnected because at the lowest degradation temperature and high humidity levels, the reduction of the molecular weight is more pronounced than that observed at the highest temperature but at a lower humidity level. Transparency decreases with the degradative processes, but even after severe degradation the loss of transparency is only about 10%. The yellowness index increases during the first stages of degradation, which has been attributed to the fast formation of carbonyl groups due to photo-oxidation.

## Keywords

Cultural heritage, durability, environmental weathering, polycarbonate

Date received: 19 June 2019; revised: 3 August 2019; accepted: 9 September 2019

## Introduction

Polycarbonate (PC) is an amorphous and transparent polymer that is often used to preserve, consolidate, and protect cultural heritage sites thanks to its durability, physical, mechanical, and optical properties. PC also finds application in building and construction as a lighter and tougher substitute for glass or metal in roofing and glazing because it shows high transparency, good electrical properties, light weight, exceptional toughness, and dimensional stability over a wide range of temperatures.<sup>1</sup> Like other polymers, PC undergoes deep processes of degradation due to the variations of temperature, stress, and, in particular, humidity and ultraviolet (UV) irradiation. The final results of degradation due to environmental weathering are discoloration, embrittlement, loss of toughness, and transparency.<sup>2–4</sup>

Photo-degradation is the main cause of the loss of PC's properties. The photo-degradation of this polymer has been widely studied in the literature<sup>5–15</sup> and involves two different mechanisms: photo-Fries reaction and photo-oxidation.

<sup>1</sup>Department of Engineering, University of Palermo, Palermo, Italy

<sup>2</sup>INSTM, National Interuniversity Consortium of Materials Science and Technology, UdR Palermo, Palermo, Italy

<sup>3</sup>Department of Chemistry, Materials and Chemical Engineering "Giulio Natta", Politecnico di Milano, Milan, Italy

<sup>4</sup>INSTM, National Interuniversity Consortium of Materials Science and Technology, UdR Politecnico di Milano, Italy

### Corresponding author:

Francesco Paolo La Mantia, University of Palermo, Department of Engineering, Viale delle Scienze, Ed. 6, Palermo, Sicilia, 90128, Italy.  
Email: francescopaolo.lamantia@unipa.it



Creative Commons Non Commercial CC BY-NC: This article is distributed under the terms of the Creative Commons

Attribution-NonCommercial 4.0 License (<http://www.creativecommons.org/licenses/by-nc/4.0/>) which permits non-commercial use, reproduction and distribution of the work without further permission provided the original work is attributed as specified on the SAGE and Open Access pages (<https://us.sagepub.com/en-us/nam/open-access-at-sage>).

**Table 1.** Sample codes and conditions of weathering.

Sample code	UV irradiation (h)	T irradiation (°C)	Condensation, (h)	T condensation (°C)	RH, %
70 RH100	–	–	12	70	100
50UV RH100	8	50	4	35	100
50UV	12	50	0	–	0
70UV RH40	8	70	4	55	40

RH: relative humidity; UV: ultraviolet.

The photo-Fries mechanism is due to wavelengths below 310 nm with the scission of the carbonate linkage. This involves the formation of two primary free radicals<sup>7</sup> that can rearrange and crosslink. The molecules produced during photo-Fries reactions can also undergo photo-oxidation, creating other products of lower molecular weight.<sup>10</sup> The photo-oxidation mechanism proceeds through three different routes: side chain oxidation, ring oxidation, and ring attack. This mechanism produces chain scission, a decrease in molecular weight, and the formation of oxygenated groups.<sup>16</sup>

Another important cause of the decrease of the mechanical properties of PC is due to moisture that, when linked to high temperatures (>70°C), leads to the hydrolysis of PC and causes the breakdown of the polymer, reducing its molecular weight.<sup>3, 17–22</sup> Finally, the formation of carbonyl groups can give rise to some yellowness in the polymer, which is important in applications such as covering cultural heritage sites. Indeed, some polymers, particularly PC, are used as material for both modern artworks and protective shields for cultural heritage sites.<sup>23–28</sup>

The main objective of this work is to evaluate the durability of PC in covering and protecting cultural heritage sites, studying its mechanical and optical properties after UV irradiation in the presence of different amounts of humidity at different temperatures.

## Materials and methods

The material used in this work was a sample of PC with a viscosimetric molecular weight (M<sub>v</sub>) of about 21,000 Da.

For the photo-oxidation tests, sheets of PC samples were prepared by compression molding at T = 280°C, P ~ 250 bar, time = 4 min in a Carver Laboratory press after drying the pellets overnight under a vacuum at 120°C.

The sheets were exposed to accelerated weathering in a Q-UV chamber (Q-Labs Corp., USA) containing eight UVB lamps for times of up to 1000 h, except for sample 50UVRH100, which, after 528 h, was completely degraded. The weathering tests were carried out under different combinations of exposure cycle parameters (time, temperature, and relative humidity (RH)). In particular, as shown in Table 1, the weathering was carried out by continuously irradiating the samples or alternating two steps: UV exposure (8 h) followed by condensation (4 h). Some

tests were also carried out by keeping some samples in an oven at T = 70°C at an RH of 100%.

The weathering conditions and the sample codes are shown in Table 1.

The intrinsic viscosity [ $\eta$ ] was measured by an iVisc Capillary Viscometer LMV 830 (Lauda Proline PV 15, Lauda-Königshofen, Germany) instrument equipped with a Ubbelohde capillary viscometer (K = 0.005) in an oil bath at 25°C.

To prepare the solution at a concentration of 0.2 wt %, each material was dissolved in tetrahydrofuran (THF) by stirring at room temperature for 1 h. Flow time measurements were performed in triplicate for each sample until the standard deviation was below 0.5 s.

The intrinsic viscosity values were calculated according to the Solomon-Ciuta equation (1):<sup>29</sup>

$$[\eta] = \frac{\sqrt{2}}{c} \cdot \sqrt{\eta_{sp} - l m \eta_{rel}} \quad (1)$$


where  $c$  is the concentration of the polymer solution and [ $\eta$ ],  $\eta_{sp}$  and  $\eta_{rel}$  are intrinsic, specific, and relative viscosity, respectively. The solution viscosity of each sample was obtained by averaging five flow measurements. The M<sub>v</sub> was calculated using the Mark–Houwink equation (Equation (2)):

$$[\eta] = K M_v^a \quad (2)$$

The parameter values of the Mark-Houwink constants,  $a$  and  $K$ , depend on the specific polymer solvent system. For PC-THF (25°C),  $K = 4.90 \times 10^{-4}$  and  $a = 0.670$ .<sup>30</sup>

Stress-strain curves were measured using a universal testing machine model 3365 (Instron). The elastic modulus was measured at a speed of 1 mm/min until the deformation was 10%. Then, the crosshead speed was increased to 100 mm/min until the specimen broke. The values of elastic modulus (E), tensile strength (TS), and elongation at break (EB) were calculated as the average of 10 tests.

Fourier Transform Infrared Spectroscopy Attenuated Total Reflectance (FT-IR ATR) spectra were obtained with a Perkin-Elmer (USA) Spectrum One spectrometer, using Spectrum software. The spectra were obtained through

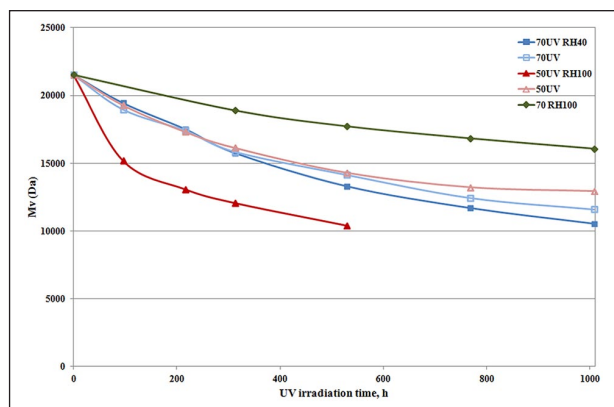

**Figure 1.** Viscosimetric molecular weight (Mv) as a function of the irradiation time. For the sample kept in the oven, the time is that spent in the oven.

16 scans with a  $4\text{ cm}^{-1}$  resolution. Measurements were obtained from the average of triplicate samples. The ATR spectra were normalized using the peak located at  $1013\text{ cm}^{-1}$  due to the aromatic CH in-plane bend.<sup>11</sup> To monitor the oxidation during the tests, the band centered at about  $1713\text{ cm}^{-1}$ , due to the aliphatic chain acids, was measured.<sup>15,22</sup>


Light transmission and haze were measured by using a spectrophotometer UV-VIS JASCO model V-650. The haze was measured according to EN 2155-5, with the yellowness index (YI) according to ASTM E313.

## Results and discussion


The Mv of the PC sample is reported as a function of the irradiation time in Figure 1. Because the weathering conditions are different, the total exposure time is, of course, different between the different tests. In particular, for the test with a condensation step, the value of the total exposure time is the irradiation time multiplied by 1.5.

The molecular weight decreases with irradiation time and with increasing temperature, but this reduction is much more pronounced in the presence of a high level of humidity over the same the irradiation time. The more pronounced reduction of the molecular weight is observed for aging carried out at the lowest temperature and at the highest level of humidity. This can be interpreted by considering that, at these temperatures, the presence of water can give rise to hydrolytic chain scission magnifying the effect of the photo-oxidation. Confirmation of this behavior is given by the values reported in the same figure for the sample kept in the oven at  $T = 70^\circ\text{C}$ ,  $\text{RH} = 100\%$  without irradiation. Indeed, Mv decreases with increasing time, but the decrease is very small with respect to that measured in the same conditions of temperature and humidity but without irradiation.

The ATR spectra of samples photo-oxidized after 528 h, Figure 2, show a broad peak at  $3200\text{ cm}^{-1}$  that indicates the presence of bonded hydroxyl (e.g. in carboxylic acids).

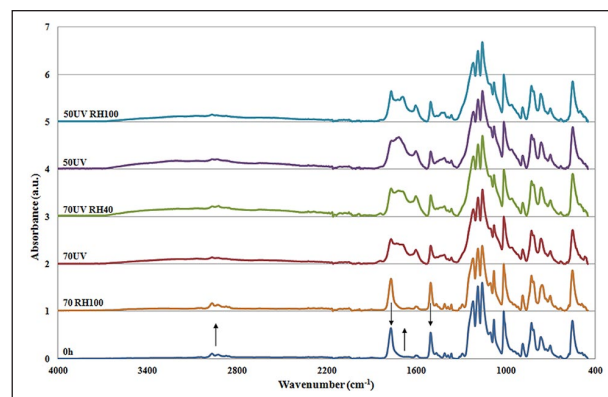

**Figure 2.** ATR spectra of virgin polycarbonate (PC) and after 528 h of irradiation.

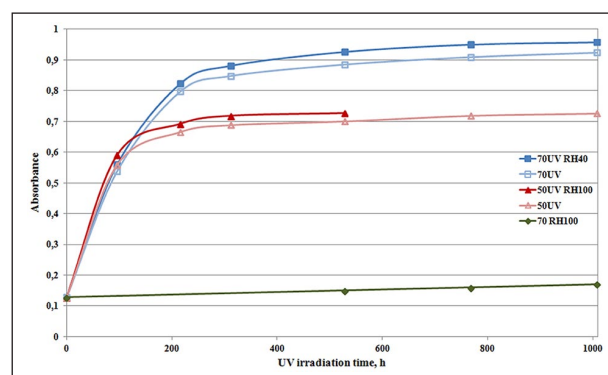


**Figure 3.** Height of the peak at  $1713\text{ cm}^{-1}$  as a function of the irradiation time.


Broad peaks at  $2600\text{--}2900\text{ cm}^{-1}$  were formed, masking the absorption of aromatic species. At the same time, the absorption in the carbonyl region ( $1500\text{--}1760\text{ cm}^{-1}$ ) increased with new peaks formed at  $1434$ ,  $1602$ ,  $1690$ , and  $1713\text{ cm}^{-1}$  related to alcohol and acid bonds. This is evidence of the formation of a range of photo-oxidation products, with substituted phenols, aromatic esters, aromatic aldehydes, heteroaromatic structures, carboxylic acids, and aliphatic esters absorbing in this region.<sup>8</sup> The peaks related to the oxidized species increase along with the temperature, but the oxidation does not seem influenced by the presence of the humidity and, indeed, the largest rise of the carbonyl and hydroxyl groups occur at the highest temperature and the curves at the same temperature and different relative humidity are similar, although the presence of humidity slightly increased the oxidation. No oxidation is shown by the sample aged without UV irradiation.

This is better put in evidence in Figure 3, where the peaks at  $1713\text{ cm}^{-1}$ , considered by Rivaton and Gijssman<sup>15,22</sup> as aliphatic chain acids, have been reported as a function of the irradiation time.

As the oxidation of PC can give rise to different oxidation species, in Figures 4 and 5 the area under the ATR curve

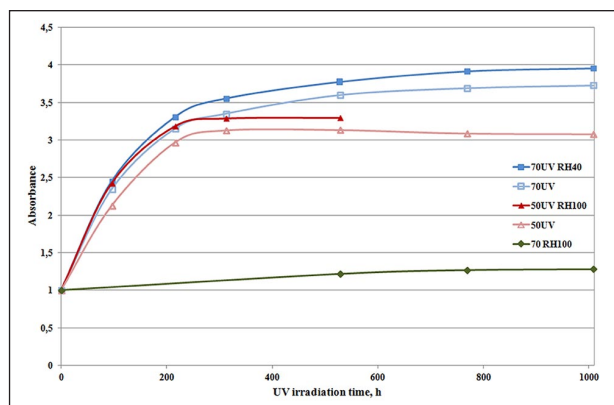

**Figure 4.** Normalized area of the peak in the region 1860–1500  $\text{cm}^{-1}$  as a function of the irradiation time.

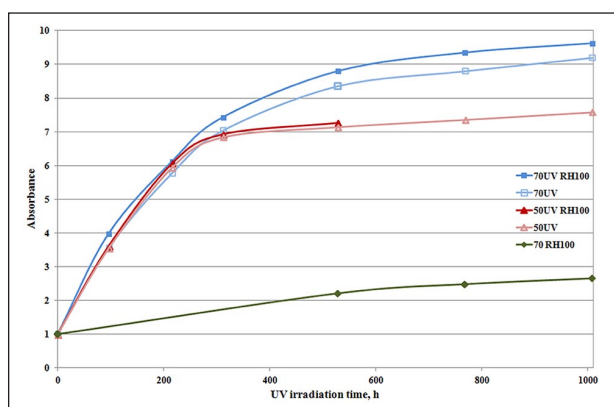


**Figure 5.** Normalized area of the peak in the region 3700–2400  $\text{cm}^{-1}$  as a function of the irradiation time.


between 1860–1500  $\text{cm}^{-1}$  and in the range 3700–2400  $\text{cm}^{-1}$  region are reported as a function of the irradiation time. In these spectra, the area was normalized with respect to the unit value given to the sample at zero time. All the oxidation species follow the same trend: they depend mainly on temperature, they increase alongside temperature, and they do not seem to depend on the level of humidity.

All the previous results seem to be in contradiction as the molecular weight is strongly dependent on the presence of humidity whereas the oxidation is dependent only on temperature. The photo-oxidation is certainly responsible for both the oxidation and reduction of molecular weight, whereas hydrolytic chain scission is responsible only for the decrease in molecular weight. It is then possible to argue that the two mechanisms, namely photo-oxidation and hydrolytic chain scission, are superimposable and seem to act separately without any significant or with very small interactions.

The degradation has a deep effect on the mechanical properties that can change dramatically during photo-oxidation. In Figures 6 and 7 TS and EB are reported as a function of the irradiation time.

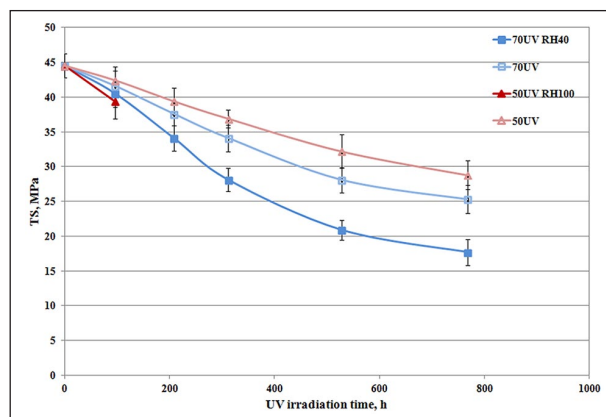

**Figure 6.** Tensile strength as a function of the ultraviolet (UV) irradiation time.

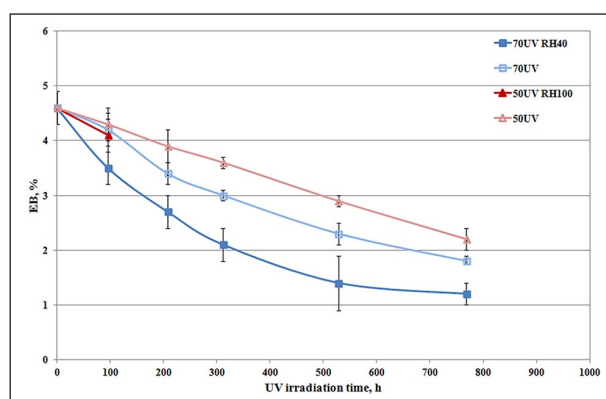

**Figure 7.** Elongation at break as a function of the ultraviolet (UV) irradiation time.

The tensile test of sample 50UVRH100 had a weathering time of 96 h because the specimens were too fragile for the mechanical tests of larger weathering times.

Due to the reduction of the molecular weight, the tensile strength decreases with the UV irradiation time. The reduction is more pronounced for the samples irradiated at a higher temperature and humidity.

The behavior is similar for the elongation at break, Figure 7. The PC becomes more fragile due to the reduction of molecular weight and, in particular, to the change of chemical structure of the polymer with the photo-oxidation, which causes a photo-oxidative damage localized within a few microns on the surface<sup>31</sup> with the creation of a “defect gradient” along the thickness that acts as a stress concentrator during the mechanical tests and causes the failure of the sample.<sup>32</sup>

Due to PC's use in covering cultural heritage sites, its optical properties take on a very important role. In particular, the light transmitted, the haze, and the YI can change with molecular differences undergone during photo-oxidation. These changes can worsen the usability and view of the cultural heritage sites protected by these sheets. In Table

**Table 2.** TLT, haze, and YI of PC samples.

	TLT, %	HAZE, %	YI
PC	89.36	81.78	0.17
50UV RH100	82.52	78.83	17.28
50UV	82.63	77.51	16.43
70UV RH40	81.36	76.18	19.89

PC: polycarbonate; TLT: total light transmission; YI: yellowness index.

2 the values of total light transmission (TLT), haze, and YI are reported. The TLT decreases then the transparency decreases with increasing severity of the photo-oxidative degradation and for the more degraded sheet it is about 10% lower than that measured for the virgin samples.

The YI remarkably increases even for the less-degraded samples. This is due to the formation of carbonyl groups that, as evident in Figure 3, increase immediately in a very short time and then become almost flat with a final value not too different between the different photo-oxidized samples.<sup>8</sup>

## Conclusions

PC is a good material for covering and protecting cultural heritage sites because of its durability, mechanical properties, and transparency. However, the contemporary action of UV irradiation, temperature, and humidity can cause dramatic degradation that gives rise to the loss of mechanical properties and transparency. In this work, the contemporary presence of UV irradiation, temperature, and humidity have been taken into account to study the environmental degradation of this polymer with regard to the properties that are important for this scope. The photo-oxidation reactions give rise to a decrease in molecular weight and the formation of many oxygenated species. The hydrolytic scission gives rise to a remarkable reduction in molecular weight. The two different degradation mechanisms do not seem to have any interaction. In particular, at the lowest degradation temperature and high humidity levels, the reduction of the molecular weight is more pronounced than that observed at the highest temperature but at lower humidity level. Considering the reduction of the molecular weight, the humidity seems to play a more important role than UV irradiation in the adopted experimental conditions. On the contrary, the UV radiation plays a more important role in the formation of oxygenated species that are not made because of the humidity level. The transparency decreases with the degradative processes but even after severe degradation, the loss of transparency is only about 10%. The YI increases during the first stages of degradation, which has been attributed to the fast formation of carbonyl groups due to photo-oxidation.

## Acknowledgements

The authors would like to thank Dr. Marco Cascone and Ing. Augusto Balloni of AGRIPLAST for the optical measurements.

## Declaration of Conflicting Interests

The author(s) declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

## Funding

The author(s) disclosed receipt of the following financial support for the research, authorship, and/or publication of this article: This work was supported by MIUR, PRIN 2015WBEP3H “Monitoraggio, Consolidamento, Conservazione e Protezione di Beni Culturali”.

## ORCID iD

MariaPia Peddeferrì  <https://orcid.org/0000-0001-9206-4869>

## References

1. Tjandraatmadja GF, Burn LS and Jollands MJ. The effects of ultraviolet radiation on polycarbonate glazing, 1999, Conference Material. Conference Name: Durability of building materials and components 8: Service life and asset management: Proceedings of the Eighth International Conference on Durability of Building Materials and Components.
2. Sherman ES, Ram A and Kenig S. Tensile failure of weathered polycarbonate. *Polym Eng Sci* 1982; 22: 457–465.
3. Ram A, Zilber O and Kenig S. Residual stresses and toughness of polycarbonate exposed to environmental conditions. *Polym Eng Sci* 1985; 25: 577–581.
4. Ram A, Zilber O and Kenig S. Life expectation of polycarbonate. *Polym Eng Sci* 1985; 25: 535–540.
5. Andradý AL, Searle ND and Crewdson LFE. Wavelength sensitivity of unstabilized and UV stabilized polycarbonate to solar simulated radiation. *Polym Degrad Stab* 1992; 35: 235–247.
6. Factor A. Mechanisms of thermal and photodegradation of bisphenol A polycarbonate. *Adv Chem Series (Polymer Durability)* 1996; 249: 59–76.
7. Rivaton A. Recent advances in bisphenol A polycarbonate photodegradation. *Polym Degrad Stab* 1995; 49: 163–179.
8. Tjandraatmadja GF, Burn LS and Jollands MC. Evaluation of commercial polycarbonate optical properties after QUV-A radiation: The role of humidity in photodegradation. *Polym Degrad Stab* 2002; 78: 435–448.
9. Diepens M and Gijsman P. Influence of light intensity on the photodegradation of bisphenol A polycarbonate. *Polym Degrad Stab* 2009; 94: 34–38.
10. Clark DT and Munro HS. Surface aspects of the photodegradation of bisphenol A polycarbonate in oxygen and nitrogen atmospheres as revealed by esca. *Polym Degrad Stab* 1982; 4: 441–457.
11. Diepens M and Gijsman P. Photodegradation of bisphenol A polycarbonate. *Polym Degrad Stab* 2007; 92: 397–406.
12. Pryde CA. Weathering of polycarbonate: A survey of variables involved. *Polymer Preprints* 1984; 25: 52–53.

13. Diepens M and Gijsman P. Photodegradation of bisphenol A polycarbonate with different types of stabilizers. *Polym Degrad Stab* 2010; 95: 811–817.
14. Diepens M and Gijsman P. Photostabilizing of bisphenol A polycarbonate by using UV: Absorbers and self-protective block copolymers based on resorcinol polyarylate blocks. *Polym Degrad Stab* 2009; 94: 1808–1813.
15. Diepens M and Gijsman P. Outdoor and accelerated weathering studies of bisphenol A polycarbonate. *Polym Degrad Stab* 2011; 96: 649–652.
16. Factor A, Ligon WV and May RJ. The role of oxygen in the photoaging of bisphenol A polycarbonate. 2. GC/GC/high-resolution MS analysis of Florida weathered polycarbonate. *Macromol* 1987; 20: 2461–2468.
17. Gardner RJ and Martin JR. Humid aging of plastics: Effects of molecular weight on the chemical properties and fracture morphology of polycarbonate. *J App Polym Sci* 1979; 24: 1269–1280.
18. Clark DT and Munro HS. Surface and bulk aspects of the natural and artificial photo-ageing of bisphenol A polycarbonate as revealed by esca and difference UV spectroscopy. *Polym Degrad Stab* 1984; 8: 195–211.
19. Ito E and Kobayashi Y. Changes in physical properties of polycarbonate by absorbed water. *J Applied Polym Sci* 1978; 22: 1143–1149.
20. Pryde CA. Photoaging of polycarbonate: effects of selected variables on degradation pathways. *ACS Symposium Series No 280 Polym Degrad Stab* 1985; 329–351.
21. Factor A and Chu ML. The role of oxygen in the photo-ageing of bisphenol-A polycarbonate. *Polym Degrad Stab* 1980; 2: 203–223.
22. Rivaton A, Sallet D and Lamaire J. The photo-chemistry of bisphenol-A polycarbonate reconsidered: Part 3-influence of water on polycarbonate photochemistry. *Polym Degrad Stab* 1986; 14: 23–40.
23. Saviello D, Toniolo L, Goidanich S, et al. Non-invasive identification of plastic materials in museum collections with portable FTIR reflectance spectroscopy: Reference database and practical applications. *Microchemical J* 2016; 124: 868–877.
24. Rychlý J, Matisová-Rychlá L and Csomorová K. Degradation of plastics from the ResinKit as a model for the selection of polymers for artworks. Assessment by nonisothermal thermogravimetric analysis and chemiluminometry. *Polym Degrad Stab* 2014; 102: 105–111.
25. Šuštar V, Kolar J, Lusa L, et al. Identification of historical polymers using Near-Infrared Spectroscopy. *Polym Degrad Stab* 2014; 107: 341–347.
26. Curran K, Možir A, Underhill M, et al. Cross-infection effect of polymers of historic and heritage significance on the degradation of a cellulose reference test material. *Polym Degrad Stab* 2014; 107: 294–306.
27. Saron C, Felisberti MI, Zulli F, et al. Influence of diazo pigment on polycarbonate photodegradation. *J App Polym Sci* 2008; 107: 1071–1079.
28. Manfredi M, Barberis E and Marengo E. Prediction and classification of the degradation state of plastic materials used in modern and contemporary art. *Appl Phys A* 2017; 123:35.
29. Abdel-Azim A-AA, Atta AM, Farahat MS, et al. Determination of intrinsic viscosity of polymeric compounds through a single specific viscosity measurement. *Polym* 1998; 39: 6827–6833.
30. [www.ampolymer.com/Mark-Houwink.html](http://www.ampolymer.com/Mark-Houwink.html).
31. Blais P, Carlsson DJ and Wiles DM. Surface changes during polypropylene photo-oxidation: A study by infrared spectroscopy and electron microscopy. *J Polym Sci A1*, 10, 1077 (1972).
32. La Mantia FP. Natural weathering of low density polyethylene-III. *Eur Polym J* 1984; 20: 993–995.