


Accepted Manuscript

The interaction of peptides and proteins with nanostructures surfaces: a challenge for nanoscience

Giorgia Brancolini, Luca Bellucci, Maria Celeste Maschio, Rosa Di Felice, Stefano Corni

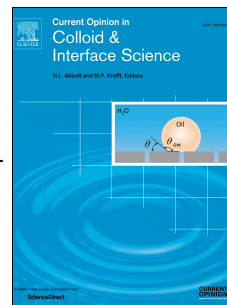

PII: S1359-0294(18)30094-3

DOI: <https://doi.org/10.1016/j.cocis.2018.12.003>

Reference: COCIS 1241

To appear in: *Current Opinion in Colloid & Interface Science*

Received Date: 10 October 2018

Revised Date: 3 December 2018

Accepted Date: 5 December 2018

Please cite this article as: Brancolini G, Bellucci L, Maschio MC, Di Felice R, Corni S, The interaction of peptides and proteins with nanostructures surfaces: a challenge for nanoscience, *Current Opinion in Colloid & Interface Science*, <https://doi.org/10.1016/j.cocis.2018.12.003>.

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

The interaction of peptides and proteins with nanostructures surfaces: a challenge for nanoscience

Giorgia Brancolini* · Luca Bellucci ·
Maria Celeste Maschio · Rosa Di Felice ·
Stefano Corni

the date of receipt and acceptance should be inserted later

Abstract The impact of nanotechnologies in biomedicine and biotechnology is becoming more and more evident. It imposes practical challenges, for instance raising specific issues on the biocompatibility of nanostructures.

Nanoparticles are characterized by a high surface-to-volume ratio, which makes them reactive to foreign species. Thus, when proteins or peptides approach an inorganic nanoparticle, as well as a flat surface, they are likely to interact with the substrate to some extent. This interaction is crucial for applications in drug delivery, imaging, diagnostics, implants and other medical devices. Specifically, gold nanoparticles are highly versatile and particularly appealing. It is widely accepted that the surfaces of nanoparticles adsorb proteins either transiently in the soft *corona* layer or permanently in the hard *corona* layer. As a consequence, the protein structure and/or function may undergo profound adjustments or remain conserved. Detailing the interaction of different inorganic substrates with proteins and peptides at the atomic level, and designing ways to control the interaction, is the key for biomedical applications of nanoparticles, both from a fundamental viewpoint and for practical implementations.

Giorgia Brancolini · Maria Celeste Maschio · Rosa Di Felice · Stefano Corni
CNR Institute of Nanoscience, via G. Campi 213/A, 41125 Modena, Italy
Tel.: +39-059-2055333; Fax: +39-059-374794; E-mail: giorgia.brancolini@nano.cnr.it

Luca Bellucci
CNR Institute of Nanoscience NEST-SNS, Piazza San Silvestro 12, 56127 Pisa, Italy

Maria Celeste Maschio
Dept. of FIM, University of Modena and Reggio Emilia, Via Campi 213/a, 41125 Modena, Italy

Rosa Di Felice
Department of Physics and Astronomy, University of Southern California, Los Angeles, CA 90089, USA

Stefano Corni
Dept. of Chemical Science, University of Padova, via Marzolo 1, 35131 Padova, Italy

In the last decade we have addressed protein-nanoparticle interactions, focusing on interfaces of gold surfaces and nanoparticles with amyloidogenic peptides and protein models. We have developed classical force fields, performed advanced molecular dynamics simulations and compared computational outcome with data from nuclear magnetic resonance experiments. Protein-gold complexes with differently coated gold nanoparticles were modelled to explore the effects of charge and size on the protein structure. Our work unravels that a complex interplay between surface properties and characteristics of the biological adsorbate determine whether peptide conformation is influenced and whether protein aggregation is accelerated or inhibited by the presence of the substrate. General guidelines to cope with amyloidogenic proteins could be inferred: these can be essentially summarized with the necessity of balancing the hydrophobic and electrostatic interactions that the amyloidogenic proteins establish with the coating moieties.

1 Introduction

Amyloidogenic proteins are implicated in several neurodegenerative diseases and determine the molecular mechanisms that underlie amyloidogenesis. In this overview article, we summarize current knowledge on the behaviour of amyloidogenic peptides and proteins in the presence of nanoparticles (NPs). We draw general conclusions from the presented results, which emerge from combined recent experimental and computational studies done in our group.

Nanoparticles are known for their size-related properties and are intensely investigated for diverse uses [1,3–5]. They are ubiquitous in our environment and can be exploited for numerous applications, due to exquisite structuring that manifests extensive sizes, shapes and related functions [6,7]. There is a fundamental interest in understanding the interaction of amyloidogenic peptides and proteins with nanoparticles, as humans are routinely exposed to nanoparticles [8,9]. The effect of protein-nanoparticle (NP) interactions may control the toxicity of NPs, which is a crucial issue for the applicability in biological systems within emerging research fields, such as nanomedicine and nanodiagnostics [1].

The large surface-to-mass ratio makes nanoparticles attractive for studying surface effects on amyloidogenic peptides and proteins. Surface effects are proposed to play a major role for the assembly of amyloidogenic peptides *in vivo*: in fact, they may explain why these peptides and proteins misfold *in vivo* at concentrations that are insufficient for fibril formation in solution *in vitro*. Surfaces provide an external constraint for the aggregation of amyloidogenic peptides and might thus promote the aggregation process. **The interaction of AuNPs with proteins is also known to induce cooperative effects, such as self-assembling of NPs. This phenomenon is potentially mediated by protein-protein interaction, which may occur at a high protein concentration on the NP surface. In some cases, protein molecules form bridges between NPs [2]. A better understanding of**

the microscopic mechanisms occurring at the bio-nano interface is thus crucial for further advances in nanotechnological applications.

In recent years, numerous research groups have investigated the effects of various nanoparticles on amyloidogenic peptides and proteins [10,11]. Depending on the specific chemical composition of the NPs and their size, as well as on the peptidic sequence and the chemico-physical conditions used, disparate effects were revealed: from a strong acceleration of fibril formation/aggregation to a complete inhibition of fibrillation.

In 2002, Braun realized a pioneering work on protein-NP complexes, carrying out classical atomistic molecular dynamics (MD) simulations of a gold binding peptide on two different crystal surfaces of gold. There have been scattered attempts to study protein-surface interactions, mostly with atomistic and mesoscopic models [10,12]. More recently, the focus has been again shifted to classical MD simulations, which constitute the single-scale method that presently better compromises between accuracy, size of simulated systems and explored time scales [3,10,11,13–16].

To contribute to the evolution of this field, we have selected two amyloidogenic systems: (i) amyloid- β peptides with 7 and 42 residues; (ii) the beta-2microglobulin (β_2m) and its amyloidogenic variants. The misfolding of these peptides and proteins may have dramatic consequences in pathology and degenerative processes. Furthermore, evidences exist that NPs, in particular citrate-coated gold nanoparticles (Cit-AuNPs), could interfere with protein dynamics along the pathway leading to fibrillogenesis. Contrary to expectations, our studies revealed no promotion of β_2m aggregation in the presence of Cit-AuNPs. Instead, Cit-AuNPs were able to inhibit *in vitro* fibrillogenesis of highly fibrillogenic protein models, through a mechanism based on fast exchange interactions that are capable of interfering with the early aggregation steps of the protein, thereby inhibiting fibril nucleation events. Systems with differently coated AuNPs or Au surfaces and different amyloidogenic molecules were described by enhanced MD simulations, to explore the effects of NP charge and size on protein conformation. An overview of the effects of gold substrates on fibril-prone peptide systems is presented in Table 1.

Experimental NMR determinations have been conducted on the β_2m and its amyloidogenic variants. Contrary to previous reports for β_2m at acidic pH [40], the protein solutions with AuNPs were stable for several months in physiological-like conditions and no evidence of increased aggregation or partial unfolding was observed. Most significantly, however, the presence of AuNPs did not enhance the onset of fibrils, as previously observed [40]. On the contrary, citrate-stabilized AuNPs were shown to inhibit fibrillogenesis of D76N β_2m [30] by interfering with the early aggregation steps of the protein. This inference, showing a decrease of aggregation of the proteins in presence of AuNP [30,14], was definitely demonstrated by combined NMR and QCMD (Quartz Crystal Microbalance with Dissipation monitoring) measurements [37]. In addition to citrate coating, other type of stabilizing decorations were tested [36,39] that

provided quite general indications for the specific coating properties that must be designed for stabilizing amyloidogenic proteins in NP colloidal suspensions. Computational modeling yields structural information that is in fair agreement with such experimental evidences.

Characterization of the surface effects of nanomaterials on the aggregation of amyloidogenic peptides and proteins may help assess the potential risks of NPs with respect to neurodegenerative diseases and eventually design smart nanomaterials that do not have negative impact on living organisms, or even have positive impact. In this review, we address recent advances in the field, focusing on work from our group.

2 Methodology

2.1 Development of Force Fields for classical MD simulations

When we started this research lines more than a decade ago, while a plethora of force fields (FFs) exist to simulate the Newtonian dynamics of biological molecules and inorganic materials separately, bio-inorganic interfaces elusive to known FF parameterizations. Thus, we undertook a research line devoted to the development of FF parameters to simulate protein-surface and protein-NP interfaces. The development of the GolP force field [18], which explicitly includes protein-Au(111) interaction parameters, has allowed us to access various levels of computational description of protein-surface interactions, from classical MD to Brownian Dynamics (BD). GolP was originally developed in the OPLS/AA format and later made compatible with CHARMM [21]. It includes image charge effects that account for the surface charge induced in the metal by the local charges in amino acids. Its parameterization is based on density functional theory (DFT) of small molecules representative of amino acid side chains adsorbed on the Au(111) surface. The FF parameters were tuned by fitting molecular mechanics (MM) total energies and geometries to those obtained by DFT. The (111) face of gold was chosen because it is the most stable among the variety of Au crystal surfaces, and therefore widely occurring in nanoparticles [3]. GolP quantitatively reproduced experimental adsorption energies for small molecules on Au and enabled prediction of the binding affinity scale for amino acids on Au coherent with available experiments.

The first extension of GolP to describe NPs was done for Cit-AuNPs: the FF parameters for classical MD simulations of proteins on Cit-AuNPs have been tested and released [3,14]. Force field parameters for differently functionalized nanoparticles are currently being derived, according to the same strategy used to develop GolP but taking explicitly into account the functional groups with different chemical nature and size. The parameterization of thiol-protected AuNP has been performed in line with GolP [13] but also to be compatible with the AMBER force field [19]. Various other bare surfaces have

been parametrized using the GoIP paradigm [20,21], but here we focus on Au(111) and functionalized NPs.

The force field for citrate anions (as well as other surfactants) decorating gold nanoparticles can be developed starting from structural optimization and electronic structure calculations of the unbound citrates at the *ab initio* (e.g., DFT) level of theory; we have used the Gaussian09 computer package. The missing bond and angle parameters can be generated from a Hessian matrix determined at the *ab initio* level of theory. Charges on individual atoms can be derived by fitting the *ab initio* electrostatic potential (ESP) grid points following the Merz-Kollman scheme. From these, a set of RESP (Restrained ElectroStatic Potential) atomic charges are derived. The interactions of the AuNP with the surfactants include dispersive forces, which are described with a Lennard-Jones potential. To model these interactions, the atom-atom 12-6 LJ parameters can be obtained using mixing rules, which were shown to reproduce the experimental interaction energies for a test set of molecules [18]. In our atomistic model, a positive gold core has been covered with a reasonable citrate surface concentration of 2.8×10^{-10} mole/cm², resulting in a surface charge density of -0.3 e/nm², consistent with the experimental zeta potential [3,17].

General strategies for simulating and predicting the acceleration/inhibition of the aggregation of amyloidogenic peptides or proteins in the presence of nanoparticles is concisely reviewed in the next two subsections. Such strategies are based on the combination of explicit solvent, enhanced sampling, implicit solvent simulations and post-processing of trajectories using entropy calculation.

2.2 Computational strategies for peptides on substrates

Computational attempts to define the conformational ensemble of intrinsically disordered peptides (IDPs) in solution have been carried out [22]. Recently, two different computational strategies have been established by our group to investigate peptides interacting with bare or coated Au(111) substrates, both based in the use of advanced sampling techniques and all atom MD simulation in explicit solvent.

The first strategy is based on the combination of temperature replica exchange (T-REMD) and metadynamics (MetaD) techniques. The use of T-REMD aims at facilitating the sampling of the conformational space of the peptide. In particular, with the use of high temperatures, the crossing of the energy barriers can be accelerated. Thus, statistically significant sampling of complex systems can be attained. On the other hand, MetaD can be used to force the system to explore specific coordinates [23,15]. A useful reaction coordinate is for example the “vertical” component of the distance between the peptide and the gold surface, which is effective to describe the adsorption and desorption. Other useful reaction coordinates are the torsional angles that embed the inherent conformations of the peptide adsorbates [23]. MetaD coupled

with T-REMD can be performed with GROMACS [24] in conjunction with the PLUMED plugin [25]. The systems can be modelled with the GoIP force field in explicit solvent, e.g. using the SPC water model. Methods have been used concurrently by other groups [26,27].

A second strategy consists of a series of three MD simulations, the first of which is aimed at sampling the conformational ensemble of the peptide in water (without surface or NP), often found to be crucial to obtain a reliable picture of the relevant phases of the peptide adsorption process [16]. The first step is achieved through an initial T-REMD (over a proper temperature range) simulation covering a number of replicas that depends on the target system. The second step, a free MD simulation at 300 K of multiple different systems extracted from the T-REMD in water, to disclose the early stage of adsorption of peptides on Au(111). The third step is a Hamiltonian-Temperature Replica Exchange (HT-REMD) simulation over a cumulative period of some microseconds, which should be initialized from the final structures of the adsorption trajectories in step two [16]. By scaling the specific gold-protein potential in the modified-Hamiltonian replicas, it is possible to decrease the high energy barriers due to the interactions between the surface and the peptide, whereas with the use of high temperatures it is possible to accelerate the crossing of the energy barriers of the whole system. The HT-REMD protocol is available with the PLUMED plugin [25]. It is a robust method to sample heterogeneous systems where the interactions among the various species can be very different in intensity and where the complexity and size of the peptide do not allow a profitable use of specific conformational sampling techniques.

2.3 Multi-step simulation protocol for proteins on substrates

In the case of larger proteins, an established protocol for the computational description of protein-NP interactions consists of a multi-scale computational pipeline that includes an initial extensive sampling of the adsorption orientations of the adsorbate on the substrate and the corresponding driving forces. This first step is performed in an efficient way by BD and generates reasonable configurations of encounter complexes of one protein with the substrate by following the diffusional progression of the protein towards the substrate. The docked configurations are then clustered to extract a small number of representative structures to be used for atomistic T-REMD refinement. Considering a proper temperature range, it is possible to sample the conformational space and energy profile [3,28]. The protocol is based on different software packages implemented in a consistent and compatible way at the different scales, i.e. the SDA7.2 software [29] for docking using the ProMetCS continuum solvent model (derived from GoIP) for protein-gold association [28] and the GROMACS package [24] for T-REMD simulations using the GoIP FF [18].

The same protocol can be broadened to investigate the early stages of aggregation of proteins on surfaces or nanoparticles, allowing for the possibility of dimeric protein aggregates existing in solution. To this aim, we devised and

assessed the following chain of steps: (1) BD in solution of two proteins to extract a number of viable dimeric configurations; (2) T-REMD of such selected dimers for structural refinement of the dimers; (3) BD of each dimer with the surface or NP in the presence of the solvent; (4) T-REMD to refine a small number of most representative encounter complexes, each constituted of a protein dimer attached to the substrate. The results can then be analyzed against those obtained for monomeric adsorption. This protocol has been applied to the case of the native β_2m and its amyloidogenic variants D76N and $\Delta N6$ [14,30], providing results in agreement with nuclear magnetic resonance (NMR) experiments.

Implicit solvent models have been recently developed [31] within methods to compute the configurational entropy due to internal and external degrees of freedom, based on the nearest neighbour method [32,33]. The combination of explicit solvent, enhanced sampling and implicit solvent simulations with post-processing of trajectories using improved implicit solvent methods and entropy calculations, will eventually provide a thermodynamic picture where all contributions are known.

3 Results

3.1 $A\beta_{16-22}$ and $A\beta_{1-42}$ peptides at the interface between gold and water

The alanine dipeptide (i.e., Ac-Ala-NHMe) is the simplest peptidic chain. Its adsorption on a gold surface was investigated [23] as a case study to evaluate the first methodological strategy reported above for peptides on substrates. By computing the free energy landscape of the adsorption process of the peptide onto a gold surface through MetaD simulations, we found that the substrate modifies the structure and dynamical behaviour of the alanine dipeptide [23]. This evidence stimulated us to progress towards more complex peptides interacting with gold surface or NP.

Amyloidogenic peptides are the subject of intensive studies, due to their involvement in neurodegenerative disorders. For example, Alzheimer's disease [34] is related to the self-assembly of the IDP amyloid- β ($A\beta$). The self-assembly of $A\beta$ into insoluble fibrils is mainly influenced by the physicochemical features of the segment 16-22 ($A\beta_{16-22}$). As the full length peptides $A\beta_{1-40}$ ($A\beta_{40}$) or $A\beta_{1-42}$ ($A\beta_{42}$), $A\beta_{16-22}$ in solution does not attain a stable structure and, under certain conditions (e.g., increasing concentration) can aggregate to form bio-nano structured fibrils. It has been shown that the presence of NPs in the environment can profitably accelerate or inhibit the fibrillation process [35]. Before this experimental evidence, we studied by computer simulations the interaction between $A\beta_{16-22}$ and the Au(111) surface: the results of this pioneering work identified atomistic mechanisms behind the amyloidogenesis driven or mediated by the presence of a substrate [15]. By applying a combination of T-REMD and MetaD, we found that the $A\beta_{16-22}$ conformations were strongly perturbed by the presence of the substrate. We observed

[15] that in solution the peptide assumed fiber-like conformations in agreement with its propensity to fibrillate, but onto the surface fiber-like conformations were not populated. In other words, the interaction of the peptide with the surface suppressed the fiber-like conformations. In particular, we observed a depletion of the fiber-like conformations via a mechanism that was intermediate between induced fitting and conformational selection, which relied on the high affinity of the surface towards the two contiguous Phe₁₈ and Phe₁₉ residues of A β _{16–22} (Fig. 1A). Considering that fiber-like conformations have been correlated with fibrillation propensity, we concluded that the effect of the surface was to inhibit the fibrillation propensity of A β _{16–22}. However, one should not exclude a possible opposite effect due to the increased local concentration on the nanoparticle, which could act as a catalyst for peptide nucleation.

The results obtained for A β _{16–22} on Au(111) [15] opened the way to rationalize, at the atomic level, the effects of metal substrates on the structure and related function of peptides. Currently, we are investigating the A β _{16–22} peptide on functionalized gold substrates, specifically on the Cit-AuNP, represented by a citrate coated Au(111) surface, and on the gold surface decorated with hydroxy-terminated polyethylene glycol (PEG), with PEG attached to the gold via a thiolate functional group. Preliminary analysis indicates that A β _{16–22} adsorbs preferentially onto the PEG functionalized surface, whereas the Cit-AuNP mildly attracts the charged terminals of the peptide, mainly in an elongated conformation (Fig. 1B). As a consequence, Cit-Au(111) surface would enhance fibril-like conformations, eventually triggered by the citrates, while PEG functionalized surfaces would act as inhibitor.

The investigation of the mechanism ruling the interaction of the A β ₄₂ peptide with the Au(111) surface is more challenging, due to the higher complexity of the system [16]. By means of the three-step computational protocol described above (T-REMD, MD, HT-REMD), the adsorption mechanism of A β ₄₂ on a gold surface in aqueous solution, was disclosed. The protocol included as the first step one of the most extensive T-REMD simulations of the A β ₄₂ peptide realized so far. The obtained conformations for the A β ₄₂ peptide adsorbed on the Au(111) surface in the presence of explicit solvent unequivocally prove the ability of the gold surface to induce elongated, fibril-prone states of the peptide [16] at the interface (Fig. 1C). Overall, we provided an exhaustive description of the conformational ensemble of A β in solution, describing how the peptide approaches the gold surface and the early stage of the adsorption and the effect of Au(111)/AuNP on the amyloidogenesis of A β ₄₂ (Fig. 1D). This finding has also reinforced the notion that the behaviour of short peptide segments extracted from A β ₄₂ cannot be safely extrapolated to the full-length chain. In fact, the behaviour of A β _{16–22} described in the previous paragraphs is opposite to that of A β ₄₂, thanks to the preponderant role of the diphenylalanine core of such a short peptide, which is easily captured by the Au surface [15] (Fig. 1A). Instead, the role of the diphenylalanine dimer is not so central in the full-length A β ₄₂ peptide.

3.2 The role of gold substrates on β_2m aggregation

A systematic investigation of the interaction of the amyloidogenic protein β_2m (and its naturally occurring variants $\Delta N6$ and D76N) with Cit-AuNPs [3, 13, 14, 30, 36, 37] was carried out in our group (Fig. 2 A). The interaction between β_2m and Cit-AuNPs was modeled at multiple levels and the results were in excellent agreement with the NMR experiments. The Cit-AuNPs were modeled by either a coated Au(111) surface or a Au_{25} cluster decorated with thiol-attached ligands. **In most reviewed work, AuNPs that expose an Au(111) face significantly larger than the protein diameter (3-4 nm) are approximated as a flat crystalline surface: this treatment is motivated by the fact that the space available on the surface of a single large NP is roughly hundreds of times that occupied by a single peptide/protein. Instead, for the interaction of peptides and proteins with NPs smaller than 3 nm, our models include full atomistic details of the NP core and organic ligands.** Via the combination of experiments and simulations, we could explain in terms of electrostatic interactions the origin of the observed protein signal perturbations mostly localized at the amino-terminal region [3, 13, 14, 30, 37].

β_2m and its amyloidogenic variants represent a prototypical amyloidogenic system. Our motivation to study this class of proteins stems from the crucial relevance of protein misfolding in pathology and degenerative processes. Furthermore, there are experimental hints that AuNPs could have a concerted action with the protein along the pathway leading to fibrillogenesis. β_2m naturally occurs in class I major histocompatibility complexes. Due to renal failure and consequent high concentration from impaired clearance or because of a mutation, a pathologic fibrillar aggregation of β_2m takes place, leading to amyloid deposition [30].

Colloidal gold nanoparticles are unstable in solution and thus are usually stabilised with carboxylic acids, alcohols or polymers. The stabilised nanoparticle surface is then covered with a biomolecule layer, the *corona*, upon contact with a biological medium. This *corona* determines the NP surface properties. When a protein approaches this complex object, the competition between the protein intrinsic propensity for aggregation and the protein-NP attraction governs the behaviour of the amyloidogenic protein in solution [10, 11].

However, a clear picture detailed at the atomic level of the effects of AuNPs and their coatings on protein interactions is still missing. Experimentally, the atomic-level structure resolution of NP-protein systems is tackled by NMR [38]. Atomistic MD simulations are an effective computational complement to NMR measurements [28].

We investigated three different variants of β_2m in the early stages of aggregation [13, 3], at the dimer level. Specifically, we included in our study: (i) wild-type β_2m ; (ii) the naturally occurring amyloidogenic single mutant D76N β_2m [30] (Fig. 2B); and (iii) the amyloidogenic variant $\Delta N6$ β_2m (Fig. 2A). $\Delta N6$ β_2m is a truncated form of wild-type β_2m , devoid of the first six residues; it can trigger the fibrillar conversion of wild-type β_2m *in vitro* in physiological

conditions [14]. Our computational results allowed us to propose a comparative mechanism for how different protein modifications can affect protein dimerization and fibril formation. Noteworthy, the role and the strength of intermolecular salt bridges at the protein-protein interface, at a physiologically relevant pH, has been correlated with the experimentally established degree of amyloidogenicity of each individual species ($D76N > \Delta N6 > \text{Wild-Type}$).

Computational and experimental studies were conducted by us for the three selected β_2m forms on Cit-AuNPs of variable size at physiological-like pH. We found that the protein solutions with AuNPs at physiological-like pH were stable for several months: no evidence of increasing aggregation or partial unfolding was observed [30]. Most significantly, however, in our study the presence of AuNPs did not enhance the onset of fibrils, as instead was previously observed. We found that Cit-AuNPs inhibit fibrillogenesis of D76N β_2m [30] by interfering with the early aggregation steps of the protein (Fig. 2B). This inference, derived from both MD simulations and NMR measurements that show a decrease of protein aggregation in the presence of AuNPs [30,14], was eventually confirmed by combined NMR and Quartz Crystal Microbalance with Dissipation monitoring (QCMD) measurements [37].

In addition to citrate coating, other types of stabilizing decorations are currently tested in our group [14,36,39]. We are focusing now our computational efforts on promising candidate that are likely to have an effect on amyloidogenic proteins in NP colloidal suspensions (Fig. 3); thus, we focus our computational efforts on promising candidates. Preliminary simulations indicate that hydrophilic carboxylic coatings (Fig. 3C) establish important and structure-destabilizing interactions with the protein: this is the opposite effect to that found for surfaces with anionic citrates (Fig. 3B). We also found that the interaction of the β_2m native monomer with a small AuNP (2 nm diameter) terminated with hydrophobic phenyl groups [13] stabilizes the protein structure (Fig. 3A) against unfolding induced by large hydrophobic surfaces (e.g., graphite). These preliminary findings on different functionalisations are in line with recent experimental findings [39].

Overall, our simulations suggest that the balance between hydrophobicity, ligand chain length and NP size, is further modulated by the charge effects. These results stress the complexity of the bio-nano interface and the need for fine tuning the NP properties to master proteinNP interactions.

Discussion and conclusion

The results obtained for the A β 42 peptide on Au(111) enable a generalization to the fate of the full amyloidogenic peptide on AuNPs, at least in cases where the NPs expose rather wide surfaces. We have proposed that NP-induced acceleration of the fibrillation process of A β 42 is closely linked to the ability of the NP facets to bind the amyloidogenic species at the surface/solvent interface. The flat interface geometry favours the formation of critical nuclei, which in turn can facilitate the fibrillation process [12,16,41].

The mechanism beyond the inhibition is less intuitive. A mechanism is based on the assumption that NPs recruit peptides from the solution decreasing the concentration, thus lowering the probability of peptides to clump together [41,12,43]. An alternative mechanism of inhibition, which we hypothesise and for which we have preliminary evidence, relies on the ability of NPs to prevent the propensity of the amyloidogenic species to assume fiber-like conformations [15,41]. In fact, NPs affect the dynamical behaviour of the amyloidogenic species through a conformational-selection/induced-fit mechanism [15,30]. This property hampers the formation of fiber-like conformations and thus inhibits the development of ordered supramolecular structures. Our simulations [15,16] reveal a shallow selectivity of the gold surface for individual amino acids, which implies that many of the 42 amino acids significantly interact with the surface, which is possible only by realizing elongated, linear-like structures. We propose that higher binding selectivity can be achieved by using small NPs, with a diameter of about 5 nm or less, of the same order of magnitude of the interatomic distances of A β 42 in water [16]. Such small NPs will only recruit a fraction of highly reactive amino acids in the peptidic chain, selectively binding a small portion of the peptide species and thus preventing the formation of fiber-prone conformations. Thus, the size of AuNPs and their affinity towards specific segments of A β 42 may hence be used as a control knob for modulating the fibrillation process [15,16]. This operation is likely extendable to other amyloidogenic species, such as β_2m [13]. Remarkably, a recent experimental work [35] revealed that large L-glutathione coated AuNPs enhance the fibrillation process, whereas small AuNPs with the same coating (diameter of about 6 nm) significantly reduce fibrillation. In the same work, the authors observed that coated AuNPs with diameter of the order of 2 nm can completely inhibit the fibrillation process, further corroborating our prediction.

In summary, experimental findings complemented by computational modeling have demonstrated that the protein-NP interaction can be controlled by tuning the size, the spatial orientation and the electrical properties of the NP. The binding propensity of various chemical functionalisations of AuNPs depends not only on the exposed surface area, but also on the surface charge density that is imposed by the functional groups. These fundamental insights into the interaction between proteins and functionalised NPs offer opportunities for developing novel core/shell receptors with highly specific protein-substrate recognition ability, which would possess promising properties for applications in protein stabilization, unfolding, and delivery.

Acknowledgements Oak Ridge National Laboratory is acknowledged for the supercomputing project CNMS2018-338, through the Scientific User Facilities Division, Office of Basic Energy Sciences, U.S. Department of Energy. Facilities of the National Energy Research Scientific Computing Center (NERSC), which is supported by the Office of Science of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231, are also acknowledged.

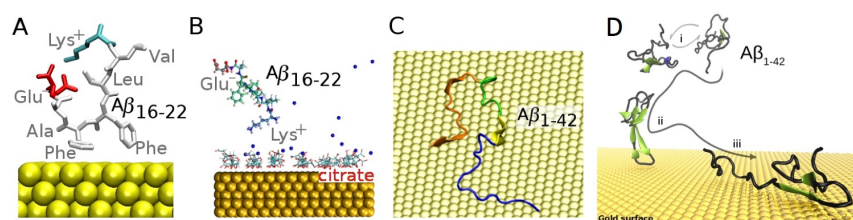


Fig. 1 Summary of the amyloidogenic peptide simulations on gold. A: Atomic representation of a stable conformation of $A\beta_{16-22}$ on bare Au(111), with a “U-shape” peptide conformation. B: Atomic representation of a stable conformation of $A\beta_{16-22}$ on citrate coated Au(111), with a “elongated” peptide conformation. C: Atomic representation of a stable conformation of $A\beta_{42}$ on bare Au(111), with an “elongated/fibril-like” peptide conformation. D: The main phases of the adsorption of $A\beta_{42}$ onto the gold surface in water. (i) the peptide in solution is mainly disordered. (ii) The early stage of the adsorption mainly occurs in a random way; eventually, portion with high affinity towards gold surface, are preferentially bounded. (iii) After binding, $A\beta_{42}$ can form amorphous protein-corona structures or relax towards extended conformations, eventually forming a fibril-template.

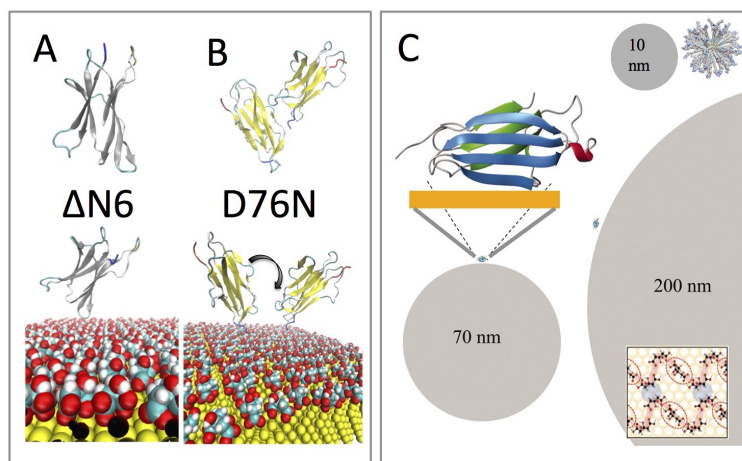


Fig. 2 Summary of the protein-NP simulations. A: Representative conformations of the $\Delta N6$ monomer in solution (top) and adsorbed on a surface representing a Cit-AuNP (bottom): computational outcome is compatible with NMR intensity reduction. B: Representative conformations of the D76N dimer in solution (top) and adsorbed on Cit-AuNP; adsorption leads to complete dissociation of the dimeric adducts present in solution. C: Conceptual scheme of the studied systems.

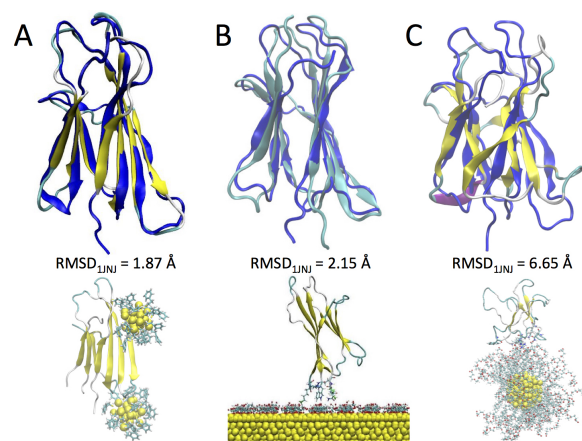


Fig. 3 Deviation of each β_2m refined structure (excluding the N-terminal and C-terminal tails) from the starting NMR structure (PDB:1JNJ). A: Representative conformation of β_2m associated to two hydrophobic phenyl terminated NPs, $(Au_{25}[S(CH_2)_2Ph]_{18})^-$ (bottom), and superposition of the adsorbed structure to the NMR structure (top); B: Representative conformation of β_2m associated to a Cit-AuNP (bottom), and superposition of the adsorbed structure to the NMR structure (top). C: Representative conformation of β_2m in solution (top) associated to carboxyl terminated NPs, $Au_{144}[S(CH_2)_9(OC_2H_4)_4COO]^{60-}$ (bottom), and superposition of the adsorbed structure to the NMR structure (top). Modest internal rearrangements are observed in panels A and B upon adsorption, a more pronounced change emerges in C.

Table 1 Overview of the effects of AuNPs of different size and surface decorations tested in our group on amyloid peptides and proteins. Large AuNP are usually modeled with flat surfaces in simulations (upper two entries). Thiolated NPs are usually modeled with nanoclusters (lower two entries).

Substrate and coating	Substrate charge	Peptide/Protein	Adsorbate charge	Effect on Fibril
AuS Bare	neutral	A β 16-42	0	Inhibition [15]
AuS		A β 1-42	-3	Promotion [16]
AuNP Citrate	negative	$\beta_2m^{(mon,dim)}$	0	Low inhibition [3]
		$\Delta N6 \beta_2m^{(mon,dim)}$	-1	Inhibition [14]
		D76N $\beta_2m^{(mon,dim)}$	+3	Inhibition [14,30]
AuS		A β 16-42	0	Weak Promotion, <i>in fieri</i>
AuS PEG-OH	neutral	A β 16-42	0	“Inhibition”, <i>in fieri</i>
AuS Carboxyl	negative	$\beta_2m^{(mon)}$	0	Weak Promotion, <i>in fieri</i>
AuS Phenyl	negative	$\beta_2m^{(mon)}$	0	Inhibition [13]

References

1. Wang P, Wang X, Wang L, Hou X, Liu W, Chen C. Interaction of gold nanoparticles with proteins and cells. *Science and Technology of Advanced Materials* 2015;16:1-15.
2. Shemetov A A, Nabiev I, Sukhanova A. Molecular Interaction of Proteins and Peptides with Nanoparticles. *ACS Nano*, 2012;6:4585-4602.
3. Brancolini G, Corazza A, Vuano M, Fogolari F, Mimmi MC, Bellotti V, Stoppini M, Corni M, Esposito G. Probing the influence of citrate-capped gold nanoparticles on an amyloidogenic protein. *ACS Nano* 2015;9:2600-13.
4. Cantarutti C, Raimondi S, Brancolini G, Corazza A, Giorgetti S, Ballico M, Zanini S, Palmisano G, Bertoincin P, Marchese L, Mangione PP, Bellotti V, Corni S, Fogolari F, Esposito G. Citrate-stabilized gold nanoparticles hinder fibrillogenesis of a pathological variant of β 2-microglobulin. *Nanoscale* 2017;9:3941-51. ●●
5. Ke PC, Sani MA, Ding F, Kallinen A, Javed I, Separovic F, Davis TP, Mezzenga R. Implications of peptide assemblies in amyloid diseases. *Chemical Society Reviews* 2017;46:6492-531.
6. Albanese A, Tang PS, Chan WCW. The effect of nanoparticle size, shape, and surface chemistry on biological systems. *Annual Review of Biomedical Engineering* 2012;14:1-16.
7. Kim Y, Park JH, Lee H, Nam JM. How do the size, charge and shape of nanoparticles affects amyloid *beta* aggregation on brain lipid bilayer?. *Scientific Report* 2016;6:19548.
8. Fadeel B, Farcas L, Hardy B, Viquez-Campos S, Hristozov D, Marcomini A, Lynch I, Valsami-Jones E, Alenius H, Savolainen K. Advanced tools for the safety assessment of nanomaterials. *Nature Nanotechnology* 2018;13:537-43.
9. Afantitis A, Melagraki G, Tsoumanis A, Valsami-Jones E, Lynch I. A nanoinformatics decision support tool for the virtual screening of gold nanoparticle cellular association using protein corona fingerprints. *Nanotoxicology* 2018;1-18.
10. Charchar P, Christofferson AJ, Todorova N, Yarovsky I. Understanding and designing the gold/bio interface: insights from simulations. *Small* 2016;12:2395-418. ●●
11. Torsten J, Anika G, Clemens K, Lisandra LM, Herre JR, Bernd A. The role of nanoparticles in amyloid peptide and protein aggregation: overview, mechanisms and perspectives. *Nanoscale* 2018; Advance article. ●●
12. Radic S, Davis TP, Ke PC, Ding F. Contrasting effects of nanoparticle-protein attraction on amyloid aggregation. *RSC Advances* 2015;5:105489-98.
13. Brancolini G, Toroz D, Corni S. Can small hydrophobic gold nanoparticles inhibit β 2-microglobulin fibrillation?. *Nanoscale* 2014;6:7903-11. ●
14. Brancolini G, Maschio MC, Cantarutti C, Corazza A, Fogolari F, Corni S, Esposito G. Citrate stabilized gold nanoparticles interfere with amyloid fibril formation: D76N and Δ N6 variants. *Nanoscale* 2018;10:4793-806.
15. Bellucci L, Ardèvol A, Parrinello M, Lutz H, Lu H, Weidner T, Corni S. The interaction with gold suppresses fiber-like conformations of the amyloid β (1622) peptide. *Nanoscale* 2016;8:8737-48. ●●
16. Bellucci L, Bussi G, Di Felice R, Corni S. Fibrillation-prone conformations of the amyloid- β -42 peptide at the gold/water interface. *Nanoscale* 2017;9:227990. ●●
17. Wright LB, Rodgera PM, Walsh TR. Aqueous citrate: a first-principles and force-field molecular dynamics study. *RSC Advances* 2013;3:16399-409.
18. Iori F, Di Felice R, Molinari E, Corni S. GolP: an atomistic force field to describe the interaction of proteins with Au(111) surfaces in water. *Journal of Computational Chemistry* 2009;30:1465-76.
19. Pohjolainen E, Chen X, Malola S, Groenhof G, Häkkinen H. A unified AMBER-compatible molecular mechanics force field for thiolate-protected gold nanoclusters. *Journal of Chemical and Theory Computation* 2016;12:1342-50.
20. Hughes ZE, Walsh TR. Distinct differences in peptide adsorption on palladium and gold: introducing a polarizable model for Pd(111). *Journal Physical Chemistry C* 2018;122:19625-38.
21. Wright LB, Rodger PM, Walsh TR, Corni S. First-principles-based force field for the interaction of proteins with Au(100)(51): an extension of GolP-CHARMM. *Journal of Physical Chemistry C* 2013;117:24292-306.

22. Nasica-Labouze J, Nguyen PH, Sterpone F, Berthoumieu O, Buchete NV, Cote S, De Simone A, Doig AJ, Faller P, Garcia A, Laio A, Mai SL, Melchionna S, Mousseau N, Mu Y, Paravastu A, Pasquali S, Rosenman DJ, Strodel B, Tarus B, Viles JH, Zhang T, Wang C, Derreumaux P. Amyloid β protein and Alzheimer's disease: when computer simulations complement experimental studies. *Chemical Reviews* 2015;115:3518-3563.
23. Bellucci L, Corni S. Interaction with a gold surface reshapes the free energy landscape of alanine dipeptide. *Journal of Physical Chemistry C* 2014;118:11357-64. •
24. Abraham MJ, Murtola T, Schulz R, Pii S, Smith JC, Hess B, Lindahl E. GROMACS: High performance molecular simulations through multi-level parallelism from laptops to supercomputers. *SoftwareX* 2015;1:19-25.
25. Bonomi M, Branduardi D, Bussi G, Camilloni C, Provasi D, Raiteri P, Donadio D, Marinelli F, Pietrucci F, Broglia R, Parrinello M. PLUMED: a portable plugin for free-energy calculations with molecular dynamics. *Computer Physics Communications* 2009;180:1961-72.
26. Wright LB, Palafox-Hernandez JP, Rodger PM, Corni S, Walsh TR. Facet selectivity in gold binding peptides: exploiting interfacial water structure. *Chemical Sciences* 2015;6:5204-14.
27. Schneider J, Ciacchi LC. Specific material recognition by small peptides mediated by the interfacial solvent structure. *Journal of American Chemical Society* 2012;134:2407-13. ••
28. Ozboyaci M, Kokh D, Corni S, Wade R. Modeling and simulation of proteinsurface interactions: achievements and challenges. *Quarterly Reviews of Biophysics* 2016;49:E4.
29. Martinez M, Bruce NJ, Romanowska J, Kokh DB, Ozboyaci M, Yu X, Ozturk MA, Richter S, Wade RC. SDA7: a modular and parallel implementation of the simulation of diffusional association software. *Journal of Computational Chemistry* 2015;36:1631-45.
30. Cantarutti C, Raimondi S, Brancolini G, Corazza A, Giorgetti S, Ballico M, Zanini S, Palmisano G, Bertocin P, Marchese L, Mangione PP, Bellotti V, Corni S, Fogolari F, Esposito G. Citrate-stabilized gold nanoparticles hinder fibrillogenesis of a pathological variant of β 2-microglobulin. *Nanoscale* 2017;9:3941-51. ••
31. Fogolari F, Corazza A, Esposito G. Free energy, enthalpy and entropy from implicit solvent end-point simulations. *Frontiers in Molecular Biosciences* 2018;5:11.
32. Serra F, Romualdi C, Fogolari F. Similarity measures based on the overlap of ranked genes are effective for comparison and classification of microarray data. *Journal of Computational Biology* 2016;23:603-14.
33. Fogolari F, Corazza A, Fortuna S, Soler MA, VanSchouwen B, Brancolini G, Corni S, Melacini G, Esposito G. *PloS one* 2015;10:e0132356.
34. Ke PC, Sani MA, Ding F, Kakinen A, Javed I, Separovic F, Davis TP, Mezzenga R. Implications of peptide assemblies in amyloid diseases. *Chemical Society Reviews* 2017;46:6492-531.
35. Gao G, Zhang M, Gong D, Chen R, Hu X, Sun T. The size-effect of gold nanoparticles and nanoclusters in the inhibition of amyloid- β fibrillation. *Nanoscale* 2017;9:4107-13. •
36. Cantarutti C, Bertocin P, Corazza A, Giorgetti S, Mangione PP, Bellotti V, Fogolari F, Esposito G. Short-chain alkanethiol coating for small-size gold nanoparticles supporting protein stability. *Magnetochemistry* 2017;3:40.
37. Cantarutti C, Raj G, Fogolari F, Giorgetti S, Corazza A, Bellotti V, Naumov P, Esposito G. Interference of citrate-stabilized gold nanoparticles on β 2-microglobulin oligomeric association. *Chemical Communications* 2018;54:5422-25. •
38. Assfalg M, Ragona L, Pagano, D'Onofrio M, Zanzoni S, Tomaselli S, Molinari H. The study of transient protein-nanoparticle interactions by solution NMR spectroscopy. *Biochimica et Biophysica Acta* 2015;1864:102-14.
39. Cantarutti C, Bertocin P, Posocco P, Hunashal Y, Giorgetti S, Bellotti V, Fogolari F, Esposito G. The interaction of β 2-microglobulin and gold nanoparticles: impact of coating, charge and size. *Journal of Materials Chemistry B*, 2018;6:5964-5974.
40. Linse S, Cabaleiro-Lago C, Xue W-F, Lynch I, Lindman S, Thulin E, Radford SE, Dawson KA. Nucleation of protein fibrillation by nanoparticles. *Proceedings of the National Academy of Sciences of the United States of America*, 2007;104:8691-8696.
41. Vácha R, Linse S, Mikael M. Surface effects on aggregation kinetics of amyloidogenic peptides. *Journal of American Chemical Society* 2014;136:11776-82.

42. Kim Y, Park JH, Lee H, Nam JM. How do the size, charge and shape of nanoparticles affect amyloid β aggregation on brain lipid bilayer? *Scientific Reports* 2016;6:19548.
43. Xiong N, Zhao Y, Dong X, Zheng J, Sun Y. Design of a molecular hybrid of dual peptide inhibitors coupled on AuNPs for enhanced inhibition of amyloid- β -Protein aggregation and cytotoxicity. *Small* 2017;13:1-14.

ACCEPTED MANUSCRIPT