

# Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: F. Genuzio, O. T. Montes, K. Freindl, N. Spiridis, J. Korecki and A. Locatelli, *J. Mater. Chem. C*, 2020, DOI: 10.1039/D0TC00311E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Chemistry-dependent magnetic properties at the FeNi oxide-metal interface

F. Genuzio

*Elettra - Sincrotrone Trieste S.C.p.A., Basovizza, Trieste 34149, Italy*

T. O. Mentęs

*Elettra - Sincrotrone Trieste S.C.p.A., Basovizza, Trieste 34149, Italy*

K. Freindl

*Jerzy Haber Institute of Catalysis and Surface Chemistry, Polish Academy of Sciences, ul. Niezapominajek 8, 30-239 Kraków, Poland*

N. Spiridis

*Jerzy Haber Institute of Catalysis and Surface Chemistry, Polish Academy of Sciences, ul. Niezapominajek 8, 30-239 Kraków, Poland*

J. Korecki

*Jerzy Haber Institute of Catalysis and Surface Chemistry, Polish Academy of Sciences, ul. Niezapominajek 8, 30-239 Kraków, Poland**AGH University of Science and Technology, Faculty of Physics and Applied Computer Science, al. Mickiewicza 30, 30-259 Kraków, Poland*

A. Locatelli

*Elettra - Sincrotrone Trieste S.C.p.A., Basovizza, Trieste 34149, Italy*

---

**Abstract**

Fe and Ni compounds and their oxides offer stoichiometry-dependent magnetic properties, owing to an extremely rich variety of crystallographic phases and a complex phase diagram. They foster the fabrication of oxide/metal magnetic junctions with tunable coupling, thus avoiding the usage of costly materials such as Co and rare-earths. Along these lines, here, spectro-microscopy is employed to study the oxidation of FeNi alloy ultrathin films featuring laterally-separated fcc and bcc phases. Under mild oxidation conditions at  $T < 250^\circ\text{C}$ , Fe segregates to the surface forming a thin superficial Fe-oxide layer, which eventually evolves to  $\text{Fe}_3\text{O}_4$  supported on an interfacial FeNi oxide with spinel structure. Notably, the bcc FeNi oxidizes faster than the fcc one, while the fcc/bcc phase boundary is found to be the most reactive surface region. The magnetic coupling and domain morphology of the oxide-metal heterostack, characterized by XMCD-PEEM and CEMS, are shown to depend on the crystallographic structure of the alloy film. In particular, the Fe-oxide layer on top of the fcc regions exhibits micron-sized uniform magnetic domains antiferromagnetically coupled to the metal support. On the contrary, the corresponding oxide on the bcc regions displays fragmented magnetic domains at a length scale of about 100 nm, with ferromagnetic coupling



to the underlying FeNi metal support. Our study identifies novel principles for engineering the magnetic coupling through interface structure and chemistry, with potential applications in sustainable spintronics.

## 1. Introduction

Metal-oxide heterostructures are widely used materials, with prototypical usage in interfacial chemistry and magnetism. Among the plethora of phenomena, magnetic tunnel junctions and magnetoresistivity, [1, 2] control of magnetic anisotropy [3] and subsequent formation of exotic magnetic structures [4] can be given as examples to magnetism at the metal-oxide interface. In stacked systems, the epitaxial relation and the atomic termination between adjacent layers are particularly important for interface-induced magnetism, as reviewed recently by *Hellman et al.* [5] In artificially fabricated hetero-structures, the presence of structural mismatch, epitaxial strain, atomic defects or intermixing at the layer boundaries might significantly perturb the intrinsic interfacial magnetic properties. On the other hand, this sensitivity can be used to modify, control and tune the properties of magnetic layers via the interface structure. [6, 7, 8]

Here, we focus on the formation and magnetic coupling of Fe-oxides grown on Fe-Ni bimetallic alloy with varying stoichiometry, constituting a metal support with tunable surface structure and composition. Regarding magnetic oxides, iron oxide has been in the forefront from the very early history of magnetism, [9] to the recent day. [10] It features several phases with various oxidation states and crystalline structures. [11] The controlled growth and transformations of the thin film counterparts of these phases were studied by the authors among others. [12, 13, 14, 15, 16] Among all the Fe oxide phases, Fe<sub>3</sub>O<sub>4</sub> is the one with the highest interest for magnetic applications, owing to the high Curie temperature and the half-metallic character at RT. [11] Hence, Fe<sub>3</sub>O<sub>4</sub> thin films are attractive candidates for incorporation in spintronic devices operating at RT as high-spin-polarized electrode. [17, 18, 8, 19, 20]

Similarly, Fe-Ni alloys have outstanding magnetic properties, [21, 22] and were exploited for the first demonstration of the spin-valve like behaviour. [23, 24] The Fe-Ni alloy offers several phases with distinct structural and magnetic properties as a function of composition and temperature. [25, 26] The alloy magnetization evolves throughout the entire range of compositions, featuring the two of the most popular alloys in permalloy ( $\approx 80\%$  Ni) and Invar ( $\approx 35\%$  Ni). [27] Furthermore, the presence of a miscibility gap in the range about 10% - 50% Ni introduces the microstructure as another aspect of the bimetallic alloy. [26] In particular, the miscibility gap leads to a phase separation into micron-sized fcc(111) and bcc(110) regions for Fe-Ni ultrathin films grown on W(110). [28, 29]

The oxidation of Fe<sub>1-x</sub>Ni<sub>x</sub> surfaces was reported to result in Fe surface segregation and its selective oxidation in the early literature. [30, 31] The current work is built on these observations and is extended to Fe-Ni surfaces showing lateral heterogeneity. Thus, in the following we address the questions: (i) how does the oxidation rate depend on the structure and composition of Fe-Ni; (ii) what is the chemical state of the



interface; (iii) how are the magnetic properties of the oxide-metal system influenced by the symmetry and chemistry at the interface?

The present paper first presents the growth of  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  films on W(110) and its subsequent separation into fcc(111) and bcc(110) regions upon annealing. Then, it shows the effect of exposing this surface to varying amounts of oxygen, using complementary surface microscopy and spectroscopy methods. Such characterization demonstrates the formation of a layered oxide/metal structure. In the last part, bearing in mind the potential application for spintronic devices, the magnetic properties and the magnetic coupling between the layers of the resulting oxide-metal composite are discussed.

## 2. Experimental

The experiments were carried out using the spectroscopic photoemission and low-energy electron microscopy (SPELEEM) instrument at the Nanospectroscopy beamline at Elettra (Trieste, Italy) [32] and using the conversion electron Mössbauer spectroscopy (CEMS) situated at the Jerzy Haber Institute of Catalysis and Surface Chemistry Polish Academy of Sciences (Krakow, Poland). [12]

The SPELEEM instrument combines x-ray photoemission electron microscopy (XPEEM) with low-energy electron microscopy (LEEM). The former provides laterally-resolved chemical and magnetic information, whereas the latter is a structural probe mostly applied to crystalline surfaces. [33, 34] In the SPELEEM microscope, the lateral resolution is about 30 nm in XPEEM, and it reaches 10 nm in LEEM mode. [35] In addition to real space imaging, the microscope can also perform diffraction measurements by imaging the backfocal plane of the objective lens. In the case of elastic backscattering of incident electrons, this allows a measurement of low-energy electron diffraction with a micron sized probed area ( $\mu$ -LEED).

The Nanospectroscopy beamline boasts two Apple II type undulators, which provide linearly and circularly polarized soft x-rays to the SPELEEM microscope in the energy range from 25 eV up to about 1000 eV. [32, 35] The circular polarization is used in order to image magnetic domains via x-ray magnetic circular dichroism photoemission electron microscopy (XMCD-PEEM). [36]

The CEMS measurements were performed using a constant acceleration spectrometer adopted to the UHV system. A small active-area 100 mCi  $^{57}\text{Co}$  (Rh)  $\gamma$ -source is placed outside the UHV and irradiates the sample through a beryllium window at a  $54^\circ$  angle from the sample normal, with the azimuthal angle corresponding to the  $[1\bar{1}0]$  direction of the W(110) substrate. A large opening channeltron is used as a conversion electron detector. The Mössbauer spectra were analyzed numerically using Voigt lines, which allows consistent implementation of the hyperfine parameter distribution that is an inherent feature of ultra thin films. The isomer shift values are given with respect to metallic  $\alpha$ -Fe. CEMS was used to investigate the composition and magnetic properties of the film volume beyond the topmost layers.

The W(110) substrate was cleaned by annealing in oxygen ( $P_{O_2} = 10^{-6}$  mbar,  $T=1100^\circ\text{C}$ ), followed



65 by flash annealing to 2000 °C in ultrahigh vacuum (UHV) in order to remove the oxygen. The Fe<sub>0.7</sub>Ni<sub>0.3</sub> thin films were grown at room temperature (RT) by co-deposition of Fe and Ni on the W(110) support, with a total film thickness of about 15 ML. In the SPELEEM, the Fe and Ni evaporators were precalibrated by monitoring the completion of their respective pseudomorphic monolayers on W(110) using LEEM and  $\mu$ -LEED. The pressure during all depositions remained in the low 10<sup>-10</sup> mbar range. In the CEMS system  
70 the Ni and Fe evaporation rate was precalibrated with a quartz crystal monitor, and the films were grown using the <sup>57</sup>Fe isotope.

The structure and the stoichiometry of the films were verified with LEED and x-ray photoemission spectroscopy (XPS) at the Fe 3*p* and Ni 3*p* core levels, respectively. The XPS result was compared to the value obtained from the ratio of white line intensities at the respective *L*<sub>3</sub> *L*<sub>2,3</sub>-edge absorption thresholds.  
75 The XAS spectra were measured using secondary electron photo-emission yield (kinetic energy range 1-2 eV) across the Fe and Ni *L*<sub>3</sub> absorption thresholds, with an estimated maximum penetration depth of 5-10 nm.

The room temperature grown Fe<sub>0.7</sub>Ni<sub>0.3</sub> films were observed to retain a uniform bcc crystal structure. The phase separation into  $\mu$ m-sized fcc and bcc regions was induced upon annealing to moderate temperatures  
80 (340 °C to 400 °C). [29]

The oxidation was carried out at 200-250°C using molecular oxygen at a pressure of 1 × 10<sup>-6</sup> mbar in a stepwise manner. XPEEM at Ni 3*p* and Fe 3*p* core levels, x-ray absorption spectroscopy (XAS-PEEM),  $\mu$ -LEED and LEEM-IV data were acquired at RT and in UHV after each oxidation step. In XPEEM, the dependence of the photoelectron inelastic mean free path on the electron kinetic energy was used to obtain  
85 information on the depth profile of each chemical species.

### 3. Results

#### 3.1. Phase separation of Fe<sub>0.7</sub>Ni<sub>0.3</sub> thin film

The phase separation at high temperature in Fe<sub>0.7</sub>Ni<sub>0.3</sub> films on W(110) have been studied recently from the monolayer limit [28] up to several nanometers thickness. [29] With increasing temperature, first Ni  
90 segregation at the film surface is observed at about 200 °C, followed by a lateral separation into micron-sized regions of fcc and bcc phases at above 300 °C. At slightly higher temperatures, film dewetting occurs.

Fig. 1a shows the laterally phase-separated surface with fcc (gray) and bcc (bright) regions, as well as some areas (dark) covered only by a single wetting layer of FeNi due to partial film breakup. The actual Ni compositions in the fcc and bcc phases for the sample in Fig. 1 are found to be in the range  
95  $x_{fcc} = 0.40 \pm 0.02$  and  $x_{bcc} = 0.26 \pm 0.02$ , respectively, from an analysis of their corresponding x-ray absorption spectra (XAS) at the respective *L*-edges. The observed stoichiometry slightly deviates from the previously reported values. [29] This is due to the different thermal treatment which the surface was subject



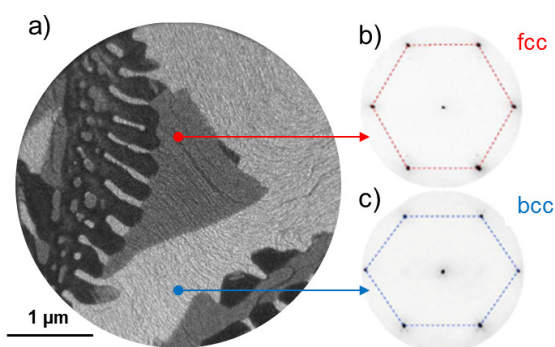


Figure 1: a) LEEM image of the phase separated FeNi film. Electron energy is 21 eV. The  $\mu$ -LEED patterns from b) gray (fcc) and c) bright (bcc) regions are acquired at 65 eV. The finger-like dark regions in the LEEM image correspond to dewetting.

to. In fact, the surface displayed in Fig. 1 was annealed for a shorter period in order to avoid extensive dewetting, and thus it was not fully developed towards the preferred phase compositions. Thus, in different sample preparations, variations in the stoichiometry of the two phases are expected.

### 3.2. Oxidation

After separation in fcc and bcc regions, the  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film was exposed to molecular oxygen in incremental steps at 200-250 °C ( $P_{\text{O}_2} = 1 \times 10^{-6}$  mbar), up to the final exposure of about 3000 L. During oxidation, the change in the surface composition was monitored by probing the Fe and Ni x-ray photoemission core levels,

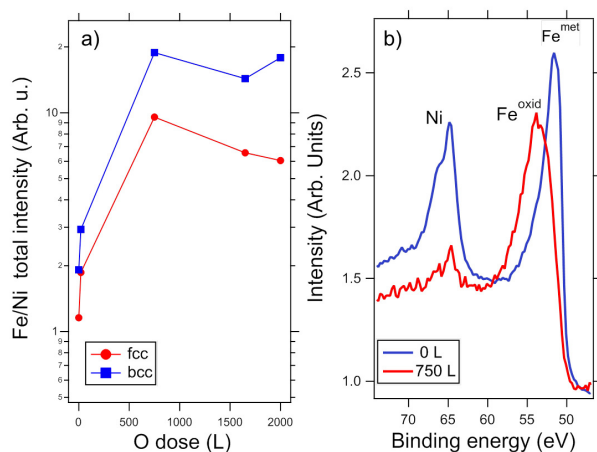


Figure 2: a) Evolution of the Fe 3p and Ni 3p core-level intensity ratio as a function of O<sub>2</sub> exposure. b) Comparison of the XPS spectra at the two core levels acquired at 0 L and 750 L oxygen exposure. Photon energy is 250 eV.



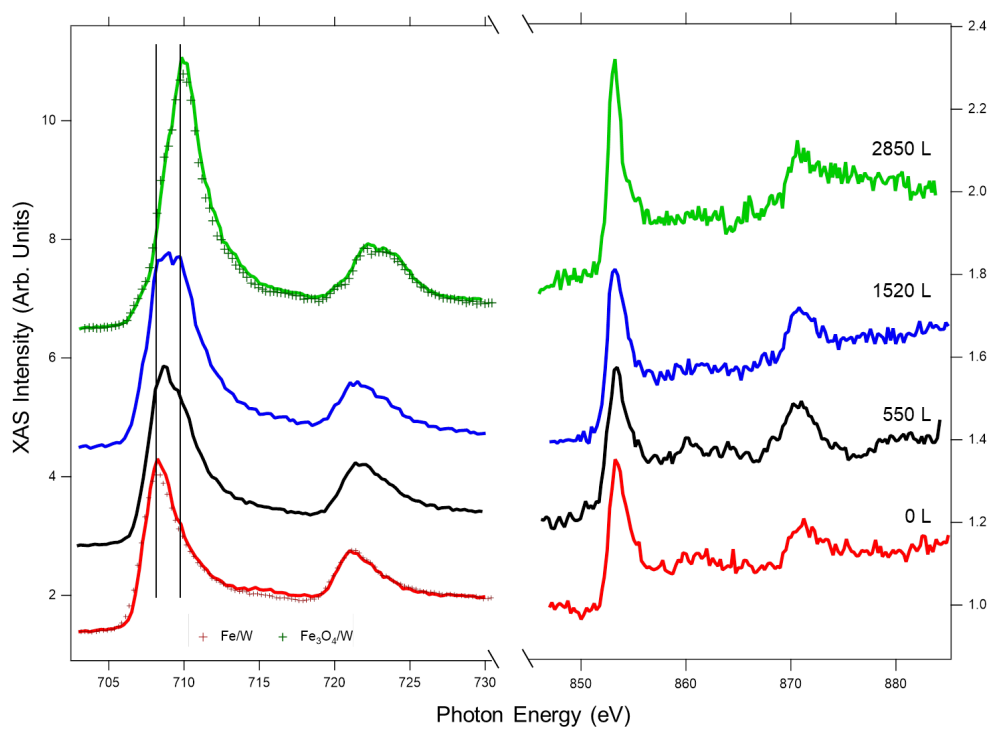


Figure 3: Integrated XAS measurements at the Fe  $L_{2,3}$ - and Ni  $L_{2,3}$  edges for a  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  thin film at increasing  $\text{O}_2$  exposure. The reference Fe  $L$ - edge spectrum of metallic Fe/W samples is superimposed to the first spectrum as full lines. On the right side, the Ni spectra do not show any relevant modifications.





105 as well as x-ray absorption spectroscopy (XAS) at the Fe and Ni *L*- edges.

The alloy film surface undergoes dramatic changes upon oxidation, as reflected by the XPS data at a photon energy of 250 eV. The Fe 3*p* core level shifts to higher binding energy by  $\Delta E_B = 2.25$  eV (see Fig.2b), while the binding energy of the Ni peak remains unchanged, indicating preferential oxidation of the Fe (both fcc and bcc). At the same time, we find that the Fe 3*p* (or  $I_{XPS}^{Fe}$  in the following) and Ni 3*p* (110  $I_{XPS}^{Ni}$ ) intensities change progressively with the oxygen dose. In particular, the intensity ratio  $I_{XPS}^{Fe} / I_{XPS}^{Ni}$  increases both on fcc and bcc regions as the oxidation proceeds (Fig. 2). Considering that the amount of Fe and Ni in the film is conserved, the change in the photoemission intensity ratio can be attributed to a surface enrichment of Fe, along with the limited inelastic mean free path of photoelectrons. [37] This is in line with the previous observations of Fe surface segregation in Fe-Ni alloys in the presence of oxygen. [30]

115 The element-selective oxidation is also revealed in the sequence of XAS measurements in Fig. 3, which are less surface sensitive compared to XPS. The formation of an Fe-oxide layer can be seen in the Fe *L*-edge spectra by the decrease of the metallic peak intensity (at 707.8 eV) and the appearance of a new peak at 709 eV as well as a smaller component at 710 eV. On the other hand, the Ni spectra remains unchanged, with a single peak at 853 eV, ascribable to metallic Ni. The characteristic shape of the Fe *L*<sub>3</sub> spectra [38] 120 indicates that the superficial Fe firstly oxidizes to FeO<sub>x</sub> (see for instance the spectrum at 550 L). As will be shown below, in the subsequent stages of the oxidation, this layer transforms to Fe<sub>3</sub>O<sub>4</sub>.

The composition of the film beyond the surface layer was probed using CEMS by averaging over the entire surface sample. The CEMS spectra at the oxygen doses of 250 L and 1650 L are shown in Fig. 4 along with the pristine alloy film surface. Before oxygen exposure, the CEMS spectrum (Fig.4, top) has 125 a purely metallic character. The numerical fit shows two components with distinctly different hyperfine parameters. The intense, comprising 80 % of the spectral intensity component (light gray in Fig. 4), with an average hyperfine magnetic field  $\langle B_{hf} \rangle = 33.0$  T and isomer shift IS = 0.05 mm/s well corresponds to a bcc FeNi alloy with approximately 75% of Fe.[39] The second component, with a low  $\langle B_{hf} \rangle = 19.0$  T

	IS [mm/s]	$\langle B_{hf} \rangle$ [T]	%
tetrahedral	$0.26 \pm 0.02$	$46.8 \pm 0.1$	$18 \pm 1$
octahedral	$0.64 \pm 0.01$	$44.1 \pm 0.1$	$26 \pm 2$
octa-like	$0.63 \pm 0.05$	$38.7 \pm 0.9$	$13 \pm 3$
metallic	$0.06 \pm 0.03$	$28.5 \pm 0.3$	$29 \pm 2$
rest	$0.3 \pm 0.09$	$8.1 \pm 0.9$	$14 \pm 2$

Table 1: Fit parameters and fit uncertainties for the CEMS spectrum after 1650 L oxygen dose at 250°C: IS – isomer shift relative to metallic Fe,  $\langle B_{hf} \rangle$  – average magnetic hyperfine field.





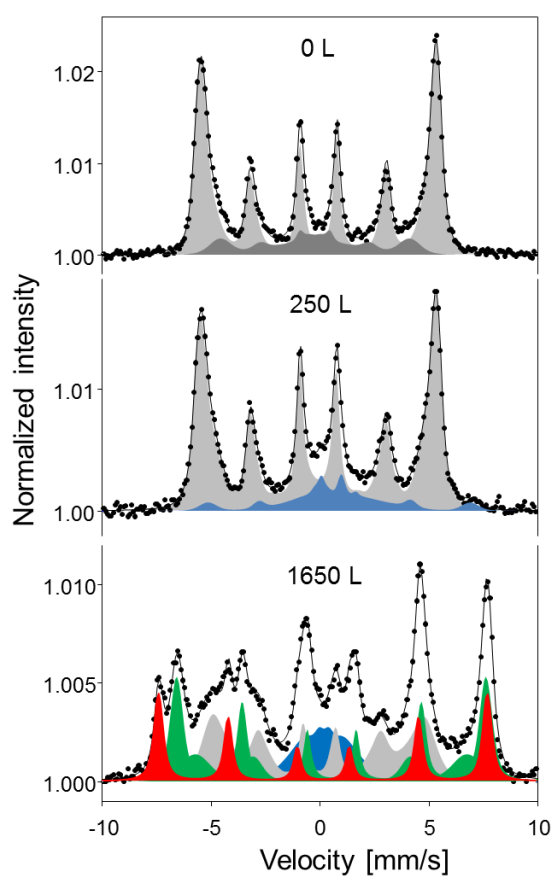


Figure 4: CEMS spectra from the  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film are shown for varying oxygen dose. The measurement averages over both fcc and bcc phases of the phase-separated alloy film. The spectral components are color-coded: light gray – metallic FeNi; red – tetrahedral site in spinel; green – octahedral site in spinel; blue – non-specific oxide components. For the top spectrum of the pristine film the decomposition into bcc-FeNi (light gray) and fcc-FeNi is shown



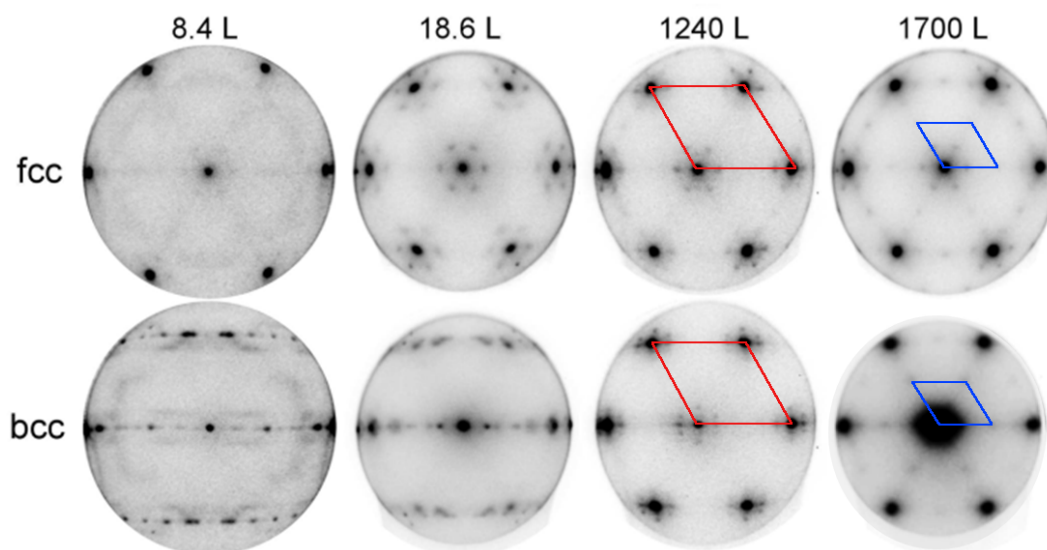


Figure 5:  $\mu$ -LEED patterns as a function of oxygen dose for the fcc (top row) and bcc (bottom row) phases present in the phase-separated alloy surface. Electron energy is 45 eV. The unit cell for the FeO and Fe<sub>3</sub>O<sub>4</sub> phases are indicated in the image (red and blue lines, respectively); substrate [1 $\bar{1}$ 0] direction is along the horizontal axis.

and negative IS = -0.11 mm/s is characteristic for an fcc FeNi alloy with approximately 60% Fe.[39] At 250 L dose, the CEMS spectrum shows a predominant metallic component from the FeNi alloy, as well as an oxide component with a non-characteristic widely-distributed hyperfine pattern. On the basis of a large positive isomer shift, the latter can be interpreted as the fingerprint of Fe<sup>2+</sup>, i.e. as in a magnetically-polarized FeO layer. The oxide contribution accounts for about 15% of the total spectral intensity, suggesting the oxidation of somewhat below 2 ML equivalent of Fe, in agreement with the XPS data.

At the O<sub>2</sub> dose of 1650 L, the CEMS spectrum shows that approximately one third of the FeNi remains in the metallic state. As seen in Table 1, the low hyperfine field value ( $B_{hf} = 28.5$  T) of the metallic component compared to that of the pristine film (average  $B_{hf} = 32.1$  T), indicates Ni enrichment within the metallic part, consistent with the segregation and selective oxidation of Fe. The oxide phase is mainly of Fe<sub>3</sub>O<sub>4</sub> character. Compared to the ideal Fe<sub>3</sub>O<sub>4</sub> composition, this oxide shows a deficit of the ideal octahedral sites. Moreover, the low-field tail of the component reveals the presence of a non-stoichiometric Fe-Ni spinel, where Ni cations are located at the octahedral sites. Such a mixed spinel phase could not be detected by surface sensitive XPS and XAS measurements, and most likely is situated in the subsurface region at the interface between the oxide layer and the metallic alloy.

Finally, a small part of the signal forms a component that cannot easily be attributed to known Fe species. Its significantly lower hyperfine field ( $B_{hf} = 8.1$  T) and its non-zero isomer shift (IS = 0.30 mm/s) differ from the parameters of metallic Fe, as well as those of the well-defined oxide species. The isomer shift points towards 3+ oxidation state, whereas the low hyperfine field may result from a lower coordination (e.g. at the film surface). This component possibly reflects the disorder induced in the film by the mass



transport and oxide formation at relatively low temperature.

### 150 3.3. Reactivity of the bcc and fcc phases

Spatially-resolved measurements were used to characterize the evolution of the bcc and fcc phases in the phase-separated  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film by increasing the oxygen dose in a stepwise manner. The  $\mu$ -LEED patterns from each region at different stages of oxidation, displayed in Fig. 5, show the formation of symmetry-dependent moiré patterns starting at the lowest dose, which develop into  $\text{FeO}(111)$  layers on both regions at 1240 L. The weak  $(2 \times 2)$  pattern at 1700 L, also visible on both phases, indicates the transformation towards an  $\text{Fe}_3\text{O}_4(111)$  surface.

Importantly, the rate of oxidation as a function of dose is significantly different for the bcc and fcc phases, as reflected in the LEEM IV curve. The XAS spectra were measured using the secondary electron photo-emission yield (in the energy range 1-2 eV) across the adsorption thresholds, with an estimated penetration depth of 5-10 nm, as discussed in the supplementary material. The changes at low dose appear to take place faster in the bcc region. Higher reactivity of the bcc phase is also confirmed by the XPEEM image at the O 1s core level, which reveals a higher oxygen concentration at the bcc surface at 8.4 L dose as seen in Fig. 6.

We should note that at an  $\text{O}_2$  dose of about 1250 L, at which the surface is mostly covered with an  $\text{FeO}(111)$  layer, the fcc-bcc phase boundary has a different contrast in laterally resolved images (see the supplementary material). The nature of the border can be identified as  $\text{Fe}_3\text{O}_4$ , based on the O  $K$ -edge and Fe  $L$ -edge XAS data, as well as the observation of magnetic domains in XMCD-PEEM images at the Fe  $L_3$  edge (also shown in the supplementary material). Therefore, we conclude that the boundaries between these two regions are by far the most reactive regions.

170 In order to reach an asymptote in the oxidation deliver a higher  $\text{O}_2$  dose than in vacuum, the phase-separated surface was briefly exposed to air at room temperature, followed by annealing at  $200^\circ\text{C}$  in  $1.0 \times$

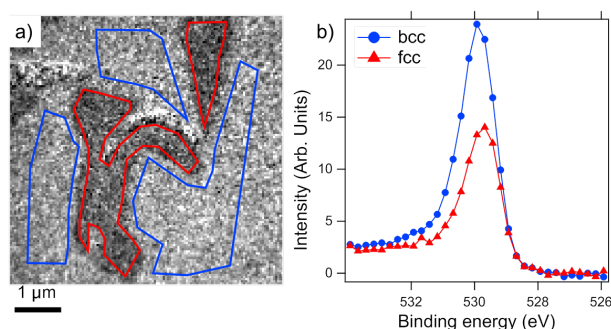


Figure 6: a) XPEEM image at the oxygen 1s core level after exposing the phase-separated alloy surface to 8.4 L  $\text{O}_2$ . The dark (bright) regions, highlighted by the red (blue) contours, correspond to the fcc (bcc) areas. b) The XPS spectra from the bcc and fcc regions, which are marked on the XPEEM image.



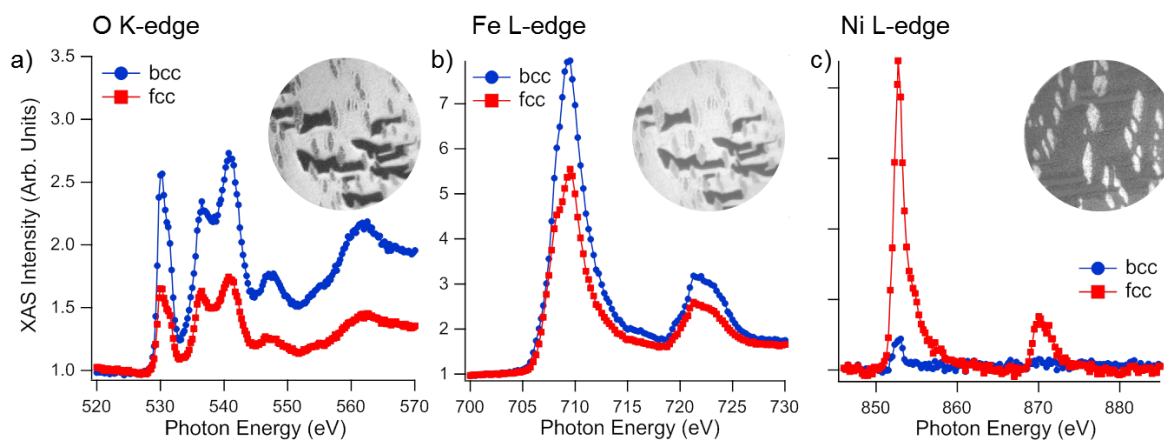


Figure 7: a) O K-edge, b) Fe L-edge, c) Ni L-edge XAS spectra from the fcc and bcc regions of a phase-separated  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film after air exposure followed by annealing at  $200^\circ\text{C}$  in  $1.10^{-6}$  mbar oxygen. The baseline is normalized to unity for all the spectra. The insets show the XPEEM images at the absorption thresholds (for oxygen integrated from 529 to 550 eV; for Fe and Ni at their  $L_3$  edges) normalized pixel-by-pixel to the corresponding pre-edge intensity (senza dire image). The field of view is  $5\ \mu\text{m}$  in all XPEEM images. The darkest regions correspond to dewetted areas, whereas the fcc regions appear as vertically elongated islands. Ni spectra is taken from a different region on the same surface.

$10^{-6}$  mbar oxygen. The resulting surface is chemically mapped by x-ray absorption spectroscopy in Fig. 7. Apart from the large dewetted areas formed during phase separation and recognizable by the dark contrast, the fcc islands are visible as micron-sized elongated regions. The presence of  $\text{Fe}_3\text{O}_4$  and metallic Ni can be seen both for bcc and fcc regions. The main difference between the two regions is the corresponding white line intensities of the respective elements. The Fe L-edge and O K-edge signals are considerably stronger in the bcc region, whereas the Ni L-edge signal is significantly stronger in the fcc region compared to the bcc areas.

We interpret the different intensities to be due to a considerably thicker  $\text{FeO}_x$  overlayer on top of the bcc areas. The Ni XAS signal in the fcc regions are quantitatively very similar to the corresponding signal level before oxidation, therefore, we can conclude that the Fe oxide layer on the fcc region is atomically thin and thus it does not cause any discernible screening of the secondary photoelectrons. The magnetic nature of the resulting oxide/metal complex will be the subject of the following section.

### 3.4. Magnetism

As we have reported in the previous section, the fcc Fe-Ni phase is significantly more difficult to oxidize in comparison to the bcc phase. Nevertheless, the CEMS and x-ray absorption spectroscopy measurements point to the formation of a magnetite layer over the entire surface upon sufficient level of oxidation. After air exposure, the magnetic properties of the same  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film shown in Fig. 7 were investigated using XMCD-PEEM at the Fe and Ni  $L_3$  edges in an element-specific manner.

An XMCD-PEEM image at the Ni  $L_3$  edge is shown in Fig. 8a. Considering that the Ni XAS signal is



highly suppressed in the bcc region (see Fig. 7c), the domains can be reliably determined only within the fcc regions. The fcc islands are mostly in a single domain state, with only small variations of the magnetic contrast within individual islands. The absorption peak of Ni predominantly shows metallic nature, thus, we can attain the magnetic contrast to the Fe-Ni alloy underneath the oxide layer above.

On the other hand, the XMCD images at the Fe L<sub>3</sub> edge show a more complex photon-energy dependent magnetization map. In Fig. 8b, the XMCD-PEEM image at the photon energy corresponding to metallic Fe (708 eV) reveals the presence of small (less than 100 nm) magnetic domains within the bcc region. The laterally-resolved XAS and XMCD spectra at the Fe L<sub>3</sub> edge extracted from these domains are shown in Fig. 8c. The XMCD spectrum is typical of Fe<sub>3</sub>O<sub>4</sub> with the negative peaks corresponding to the Fe<sup>2+</sup> and Fe<sup>3+</sup> ions at octahedral sites and the positive peak due to the Fe<sup>3+</sup> ions at tetrahedral sites. [40, 41, 42, 13] The peaks in the asymmetry spectrum in Fig. 8c are marked by vertical arrows, and the XMCD images at the latter two energies are shown in Fig. 8d,e. Indeed, the small domains within the bcc region appear with weak but inverted contrast at 709.1 eV in comparison to the image at 708.0 eV, while at 709.9 eV the contrast is the same as that at 708.0 eV.

The contribution of the metallic Fe underneath, which is expected to reach a maximum at photon energy of 708 eV, cannot be unequivocally determined within the bcc regions, as the thick oxide layer suppresses the signal from the metallic alloy underneath. Therefore, the oxide-metal metal-oxide interface in the bcc phase was evaluated for a lower oxygen dose, as shown in the supplementary material. For such thinner oxide layer, we observe an indication for ferromagnetic coupling between Fe<sub>3</sub>O<sub>4</sub> and Fe-Ni(bcc).

Instead, in the fcc regions (surrounded by the red contours in Fig. 8 for a clear visualization) the situation is completely different as compared to the bcc areas. A strong contrast is seen at the Fe edge at 708.0 eV (Fig. 8b) coinciding with the XMCD image at the Ni edge at 853.0 eV (Fig. 8a), i.e. the relative grayscale in the two images remains the same. At 709.1 eV the XMCD contrast within the fcc islands is the same but much weaker (Fig. 8d). Surprisingly, at 709.9 eV (shown in Fig. 8e) the XMCD contrast inverts in the fcc regions, that is, brighter regions become darker and vice versa; this can be seen very clearly looking at the two joint islands in the top of the image (highlighted by green circle), but is also observed for all the other fcc regions. This unusual sequence of contrast inversion differs from that of pure Fe<sub>3</sub>O<sub>4</sub> (or of a sufficiently thick oxide layer, in this case), for which we would expect the images at 708.0 eV and 709.9 eV to have the same contrast, opposite in respect to the image acquired at 709.1 eV photon energy. A similar reasoning can be applied to the case of pure metallic Fe (or a sufficiently thin oxide layer), which would exhibit high contrast at 708.0eV, aligned with the Ni edge, and vanishing at higher photon energies. To explain the observed behavior one has to take into account The interpretation is based on a superposition of contributions from the metallic Fe underneath and the oxide layer above. At the photon energy of 708.0 eV XMCD signal from the metallic Fe (aligned with that of metallic Ni) dominates and overtakes the Fe<sub>oct</sub><sup>2+</sup> peak from the relatively thin Fe<sub>3</sub>O<sub>4</sub> overlayer. At 709.9 eV seen in Fig. 8e, there is no contribution from metallic






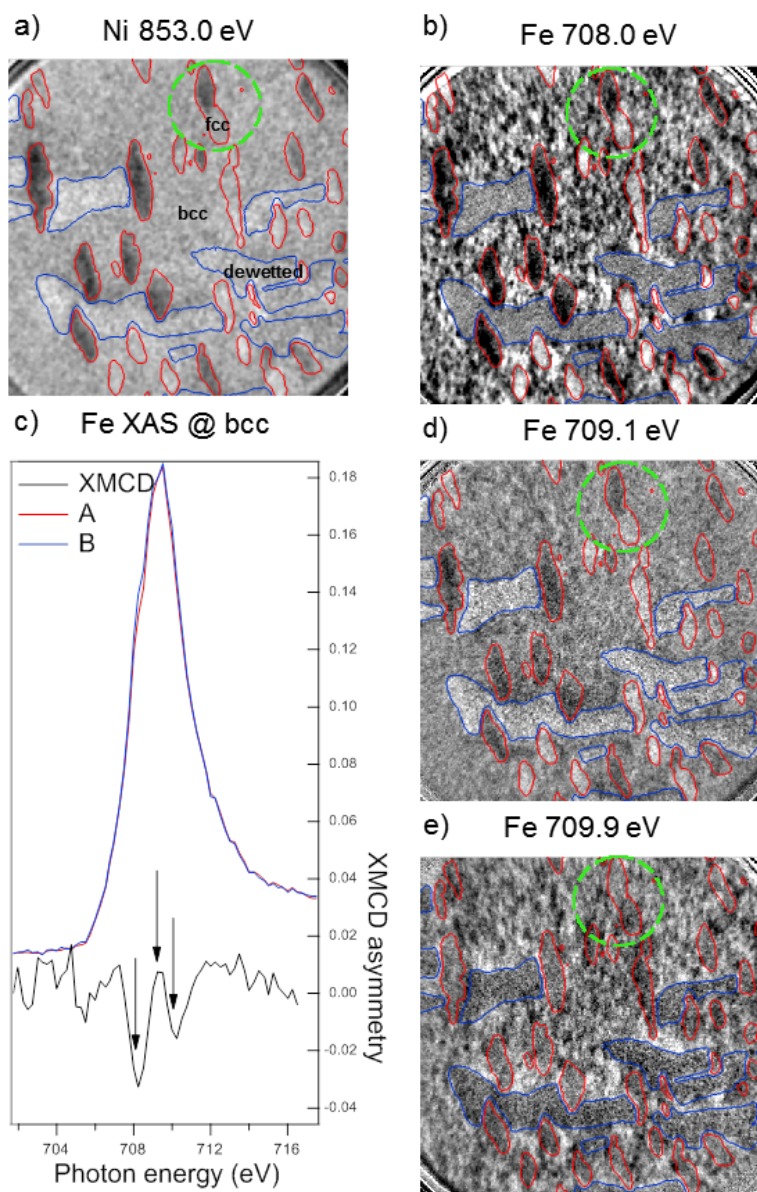


Figure 8: XMCD-PEEM images of the air-exposed  $\text{Fe}_{0.7}\text{Ni}_{0.3}$  film at a) Ni  $L_3$  at 853.0 eV, b) Fe  $L_3$  at 708.0 eV. c) Laterally-resolved Fe  $L_3$  spectra with circular polarization from dark (A) and bright (B) domains in panel (b) are shown along with the asymmetry between the two spectra. Based on the spectrum, XMCD-PEEM images are acquired also at photon energies c) 709.1 eV, d) 709.9 eV. In all images, the red lines delineate the fcc regions, whereas the blue lines indicate the dewetted areas. In the asymmetry spectrum, the vertical arrows indicate the photon energies at which the images are acquired.



Fe, and the XMCD signal originates solely from the  $\text{Fe}_{oct}^{3+}$  in  $\text{Fe}_3\text{O}_4$ . The inverted contrast between Fig. 8b and Fig. 8e is indeed a direct evidence of antiferromagnetic coupling between the metallic alloy underneath and the oxide layer above. At the intermediate photon energy, 709.1 eV in Fig. 8d, the contrast is thus the same as the metallic Fe at 708.0 eV, because both the tail of the metallic XMCD peak and the  $\text{Fe}_{tet}^{3+}$  oxide peak give the same sign of dichroic asymmetry. Moreover, we note that in any other possible magnetic state of the stack, such as: (i) FM alignment, (ii) thick or (iii) ultrathin  $\text{Fe}_3\text{O}_4$  layer, and (iv) non-magnetic oxide, the third image should either have the same contrast as the first (first two cases) or no magnetic contrast at all (last two cases).

Aside the magnetic coupling between the metal and oxide layers, considering that the XMCD measurements were carried out with the substrate  $[\bar{1}\bar{1}0]$  direction aligned with the circularly polarized x-ray beam, we can state that at least part of the magnetization lies along this direction. Additional information about the magnetization direction comes from the CEMS measurements. Given the CEMS measurement geometry, the intensity ratio  $I_2/I_3 = 0.9$  of the second and third line in the spectrum of the pristine film (compare Fig. 4) clearly corresponds to the  $[\bar{1}\bar{1}0]$  magnetization direction. Upon oxidation the  $I_2/I_3$  ratio increases to 1.45 for the metallic component, whereas for the spinel components takes a value of 2, which indicates a tendency of the easy magnetization axis to rotate from  $[\bar{1}\bar{1}0]$  towards  $[001]$ . The discussion of whether this tendency is due to the abundance of domain walls or whether it indicates a spin reorientation transition is beyond the scope of this work, and it will be the subject of an experimental study with full vectorial mapping of the magnetization.

#### 4. Discussion

In the previous sections we have reported the oxidation of the phase-separated  $\text{Fe}_{0.70}\text{Ni}_{0.30}$  film. The main findings can be summarized as: (i) the oxidation proceeds over both fcc and bcc phases with the segregation of Fe to the surface and the formation of an  $\text{FeO}(111)$  layer, which transforms into  $\text{Fe}_3\text{O}_4(111)$  upon further oxidation; (ii) the small contribution from  $\text{Ni}_x\text{Fe}_{3-x}\text{O}_4$  in the CEMS data is attributed to a buffer layer between the metallic alloy underneath and the Fe-oxide on top; (iii) in the phase-separated alloy, the fcc region is found to be much less reactive towards oxidation in comparison to the bcc regions; (iv) the magnetic coupling between the metal alloy and the  $\text{Fe}_3\text{O}_4$  overlayer is found to be antiferromagnetic for the fcc regions; instead the coupling within the bcc regions cannot be unambiguously determined for the heavily-oxidized sample.

The first point, which is the formation of an  $\text{FeO}_x$  layer on top of the Fe-Ni alloy, had been reported long ago, explained by the higher heat of formation of  $\text{Fe}_3\text{O}_4$  in comparison to NiO. [30] The same work ruled out the formation of a mixed Ni-Fe oxide below 70% Ni content. Our data confirms the absence of an extensive Ni-Fe-O spinel phase due to the metallic nature of the observed Ni XAS spectrum. Moreover, in Fig. 8c, we show the typical  $\text{Fe}_3\text{O}_4$  XMCD spectrum, while the literature reports a considerably enhanced





260  $\text{Fe}_{tet}^{3+}$  peak in the  $\text{Ni}_x\text{Fe}_{3-x}\text{O}_4$  XMCD spectrum at the Fe  $L_3$  edge. [43] Thus,  $\text{NiFe}_2\text{O}_4$  contribution to our CEMS data can be attributed to an atomically-thin layer restricted to the metal-oxide interface.

The difference in the level of oxidation between the fcc and bcc regions is equally evident both for the lowest and highest oxygen exposures, as seen from Fig. 6 and Fig. 7, respectively. The lower oxidation rate with increasing Ni content in Fe-Ni alloys was reported in the early literature and it was explained to be due to a Ni-rich passivating buffer layer. [31] Nevertheless, our results are obtained from ultrathin films, where the stoichiometry of buried metal alloy depends sensitively on the amount of Fe segregated to the surface in the Fe-oxide layer. Thus, a thermodynamic consideration comparing the relative energy of different alloy compositions may be relevant in the explanation of the difference in the oxidation rates. In particular, for the fcc  $\text{Fe}_{1-x}\text{Ni}_x$  alloys, the  $L1_0$  structure at  $x = 0.50$  is identified as the global minimum in energy. [44] 265  
270 Based on this, one may argue that the fcc phase in the phase separated alloy may oppose to release the necessary Fe for the oxide formation beyond a stoichiometry of  $\text{Fe}_{0.50}\text{Ni}_{0.50}$ .

In short, the suppressed reactivity of the fcc phase in comparison to the Fe-rich bcc phase may have contributions both from kinetic limitations increasing with Ni content and from energetics favoring a particular alloy stoichiometry. In order to identify which of the two mechanisms is the dominant one, further studies of composition-dependent reactivity in fcc  $\text{Fe}_{1-x}\text{Ni}_x$  ultrathin films near  $x = 0.50$  will be necessary. 275

The magnetization measurements provide direct comparisons between the bcc(110) and fcc(111) films as the support layer for the  $\text{Fe}_3\text{O}_4$  top layer. Before oxidation both phases in the film display large and uniform magnetic domains. Upon forming the Fe-oxide layer on top, the domain size and distribution is distinctly different for the fcc and bcc phases. The fcc phase retains the single domain state in each fcc island, while the bcc phase breaks into magnetic domains of size below 100 nm, as seen in Fig. 8a and Fig. 8b. The reason for the small domains may be due to a more defective interface between the lattices with different symmetries. Alternatively, the domain morphology may be due to the defect density in the oxide overlayer resulting from the relatively low oxidation temperature or in the alloy underlayer after the removal of a considerable amount of Fe in order to form the relatively thick  $\text{Fe}_3\text{O}_4$  layer on top. 280

285 Regarding the magnetic coupling between the metal support and the oxide overlayer, the fcc regions are coupled antiferromagnetically to the  $\text{Fe}_3\text{O}_4$  top layer. This behaviour in the fcc regions is different than the reported ferromagnetic coupling between  $\text{Fe}_3\text{O}_4$  and Ni(111). [20] A similar situation is found for the bcc regions. Contrary to what was observed for  $\text{Fe}_3\text{O}_4/\text{Fe}(110)$ , we have seen an indication of ferromagnetic coupling at the metal-oxide interface within the bcc(110) regions for a thinner oxide layer, as displayed in the supplementary material. 290

These differences necessarily originate from the details of the interface. The effect of the interface has been documented well in the case of  $\text{Fe}_3\text{O}_4/\text{Fe}(110)$ , in which the antiferromagnetic coupling was explained by an Fe layer at the interface featuring only 3+ octahedral sites. [45] On the other hand, in  $\text{NiFe}_2\text{O}_4$  the  $\text{Ni}^{2+}$  ions preferentially replace the  $\text{Fe}^{2+}$  ions at the octahedral sites. [46] Therefore, the presence of Ni



atoms at the oxide-metal interface likely favors a different oxide layer termination, and subsequently may change the spin orientation of the layer coupled to the metal.


We note here that the results summarized above lead to two significant predictions: (i) oxidation of Ni/Fe(110) may help tune the resulting oxide-metal magnetic coupling from antiparallel to parallel depending on the Ni coverage; (ii) based on the opposite coupling observed between bcc and fcc regions, we expect that the magnetic trilayer  $\text{Fe}_{1-x}\text{Ni}_x(\text{fcc})/\text{Fe}_3\text{O}_4/\text{Fe}_{1-y}\text{Ni}_y(\text{bcc})$  is a candidate for the observation of large magnetoresistivity based on the half-metallic character of  $\text{Fe}_3\text{O}_4$ . [10]

## 5. Conclusion

We report on the oxidation of fcc and bcc Fe-Ni phases under identical conditions. In both phases, Fe segregation and its selective oxidation to FeO and  $\text{Fe}_3\text{O}_4$  is observed. The bcc phase, with its higher Fe content, is shown to be significantly more reactive in comparison to the fcc phase. At the interface between the underlying metal and the  $\text{FeO}_x$  overlayer, a Ni containing buffer layer is revealed by Mössbauer measurements. The resulting magnetic domains and the metal-oxide magnetic coupling are shown to be distinctly different compared to the coupling between  $\text{Fe}_3\text{O}_4$  and the elemental constituents of the alloy. Thus, the oxidation of the phase separated Fe-Ni alloy provides information on how the symmetry and interface chemistry modifies the magnetic coupling at an oxide-metal interface, and opens up possibilities to tailor the interface properties with applications in mind.

## References

- [1] J. M. D. Teresa, A. Barthélémy, A. Fert, J. P. Contour, F. Montaigne, P. Seneor, "Role of metal-oxide interface in determining the spin polarization of magnetic tunnel junctions", *Science* 286 (1999) 507.
- [2] S. Ikeda, K. Miura, H. Yamamoto, K. Mizunuma, H. D. Gan, M. Endo, S. Kanai, J. Hayakawa, F. Matsukura, H. Ohno, "A perpendicular-anisotropy CoFe-MgO magnetic tunnel junction.", *Nature Materials* 9 (2010) 721.
- [3] A. Koziol-Rachwał, T. Ślezak, K. Matlak, P. Kuświk, M. Urbaniak, F. Stobiecki, L. D. Yao, S. van Dijken, J. Korecki, "Tunable magnetic properties of monoatomic metal-oxide Fe/MgO multilayers", *Phys. Rev. B* 90 (2014) 045428.
- [4] O. Boulle, J. Vogel, H. Yang, S. Pizzini, D. de Souza Chaves, A. Locatelli, T. O. Menteş, A. Sala, L. D. Buda-Prejbeanu, O. Klein, M. Belmeguenai, Y. Roussigné, A. Stashkevich, S. M. Chérif, L. Aballe, M. Foerster, M. Chshiev, S. Auffret, I. M. Miron, G. Gaudin, "Room-temperature chiral magnetic skyrmions in ultrathin magnetic nanostructures.", *Nature Nanotechnology* 11 (2016) 449.
- [5] F. Hellman, A. Hoffmann, Y. Tserkovnyak, G. S. D. Beach, E. E. Fullerton, C. Leighton, A. H. MacDonald, D. C. Ralph, D. A. Arena, H. A. Dürr, P. Fischer, J. Grollier, J. P. Heremans, T. Jungwirth, A. V. Kimel, B. Koopmans, I. N. Krivorotov, S. J. May, A. K. Petford-Long, J. M. Rondinelli, N. Samarth, I. K. Schuller, A. N. Slavin, M. D. Stiles, O. Tchernyshyov, A. Thiaville, B. L. Zink, "Interface-induced phenomena in magnetism", *Rev. Mod. Phys.* 89 (2017) 025006.
- [6] J. Coey, Ariando, W. Pickett, "Magnetism at the edge: New phenomena at oxide interfaces", *MRS Bulletin* 38 (2013) 1040–1047.
- [7] G. Li, G. R. Blake, T. T. M. Palstra, "Vacancies in functional materials for clean energy storage and harvesting: the perfect imperfection", *Chem. Soc. Rev.* 46 (2017) 1693–1706.
- [8] Z. Huang, W. Liu, J. Yue, Q. Zhou, W. Zhang, Y. Lu, Y. Sui, Y. Zhai, Q. Chen, S. Dong, J. Wang, Y. Xu, B. Wang, "Enhancing the spin orbit coupling in  $\text{Fe}_3\text{O}_4$  epitaxial thin films by interface engineering", *ACS Applied Materials & Interfaces* 8 (2016) 27353–27359.
- [9] F. Ozcep, *Earth Sciences History* 37 (2018) 1.
- [10] J.-H. Park, E. Vescovo, H.-J. Kim, C. Kwon, R. Ramesh, T. Venkatesan, "Direct evidence for a half-metallic ferromagnet", *Nature* 392 (1998) 794.
- [11] G. S. Parkinson, "Iron oxide surfaces", *Surface Science Reports* 71 (2016) 272.
- [12] N. Spiridis, D. Wilgocka-Ślezak, K. Freindl, B. Figarska, T. Giela, E. Młyńczak, B. Strzelczyk, M. Zajac, J. Korecki, "Growth and electronic and magnetic structure of iron oxide films on Pt(111)", *Phys. Rev. B* 85 (2012) 075436.



- [13] M. Monti, B. Santos, A. Mascaraque, O. Rodríguez de la Fuente, M. A. Niño, T. O. Menteş, A. Locatelli, K. F. McCarty, J. F. Marco, J. de la Figuera, "Magnetism in nanometer-thick magnetite", *Phys. Rev. B* 85 (2012) 020404.
- [14] M. Monti, B. Santos, A. Mascaraque, O. Rodríguez de la Fuente, M. A. Niño, T. O. Menteş, A. Locatelli, K. F. McCarty, J. F. Marco, J. de la Figuera, "Oxidation pathways in bicomponent ultrathin iron oxide films", *The Journal of Physical Chemistry C* 116 (2012) 11539–11547.
- [15] F. Genuzio, A. Sala, T. Schmidt, D. Menzel, H.-J. Freund, "Interconversion of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> and Fe<sub>3</sub>O<sub>4</sub> thin films: Mechanisms, morphology, and evidence for unexpected substrate participation", *J. Phys. Chem. C* 118 (2014) 29068.
- [16] F. Genuzio, A. Sala, T. Schmidt, D. Menzel, H.-J. Freund, "Phase transformations in thin iron oxide films: Spectromicroscopic study of velocity and shape of the reaction fronts", *Surface Science* 648 (2016) 177.
- [17] D. Tripathy, A. O. Adeyeye, "Giant magnetoresistance in half metallic Fe<sub>3</sub>O<sub>4</sub> based", *Journal of Applied Physics* 101 (2007) 09J505.
- [18] S. v. Dijken, X. Fain, S. M. Watts, J. M. D. Coey, "Negative magnetoresistance in Fe<sub>3</sub>O<sub>4</sub>AuFe spin valves", *Phys. Rev. B* 70 (2004) 052409.
- [19] K. Omori, T. Kawai, N. Takahashi, T. Yanase, T. Shimada, T. Nagahama, "The magnetic properties of Fe<sub>3</sub>O<sub>4</sub>/nonmagnetic metal/Fe hybrid systems", *Applied Physics Letters* 110 (2017) 212402.
- [20] W. Xiao, W. Song, T. S. Heng, Q. Qin, Y. Yang, M. Zheng, X. Hong, Y. P. Feng, J. Ding, "Novel room-temperature spin-valve-like magnetoresistance in magnetically coupled nano-column Fe<sub>3</sub>O<sub>4</sub>/Ni heterostructure", *Nanoscale* 8 (2016) 15737.
- [21] W. F. McDonough, S. s. Sun, "The composition of the Earth", *Chemical Geology* 120 (1995) 223.
- [22] B. D. Culity, C. D. Graham, "Introduction to Magnetic Materials", Wiley-IEEE Press, 2008.
- [23] B. Dieny, V. S. Speriosu, S. Metin, S. S. P. Parkin, B. A. Gurney, P. Baumgart, D. R. Wilhoit, "Magnetotransport properties of magnetically soft spin valve structures", *Journal of Applied Physics* 69 (1991) 4774–4779.
- [24] B. Dieny, V. S. Speriosu, S. S. P. Parkin, B. A. Gurney, D. R. Wilhoit, D. Mauri, "Giant magnetoresistive in soft ferromagnetic multilayers", *Phys. Rev. B* 43 (1991) 1297–1300.
- [25] K. B. Reuter, D. B. Williams, J. I. Goldstein, "Determination of the Fe/Ni phase diagram below 400 °C", *Metall. Trans. A* 20 (1989) 711.
- [26] C. W. Yang, D. B. Williams, J. I. Goldstein, "A revision of the Fe-Ni phase diagram at low temperatures < 400 °C", *J. Phase Equilibria* 17 (1996) 522.
- [27] B. Glaubitz, S. Buschhorn, F. Brüßing, R. Abrudan, H. Zabel, "Development of magnetic moments in Fe<sub>1-x</sub>Ni<sub>x</sub>-alloys", *J. Phys. Condens. Matter* 23 (2011) 254210.
- [28] T. O. Menteş, A. Sala, A. Locatelli, E. Vescovo, J. M. Ablett, M. A. Niño, "Phase coexistence in two-dimensional Fe<sub>0.70</sub>Ni<sub>0.30</sub> films on W(110)", *e-J. Surf. Sci. Nanotech.* 13 (2015) 256.
- [29] T. O. Menteş, N. Stojić, E. Vescovo, J. M. Ablett, M. A. Niño, A. Locatelli, "Vacancy-mediated fcc/bcc phase separation in Fe<sub>1-x</sub>Ni<sub>x</sub> ultrathin films", *Phys. Rev. B* 94 (2016) 085402.
- [30] K. Wandelt, G. Ertl, "Electron spectroscopic studies of the oxidation of Fe/Ni alloys", *Surf. Sci.* 55 (1976) 403.
- [31] G. R. Wallwork, "The oxidation of alloys", *Rep. Prog. Phys.* 39 (1976) 401.
- [32] A. Locatelli, L. Aballe, T. O. Menteş, M. Kiskinova, E. Bauer, "Photoemission electron microscopy with chemical sensitivity: SPELEEM methods and applications", *Surf. Interface Anal.* 38 (2006) 1554.
- [33] E. Bauer, *Surface Microscopy with Low-Energy Electrons*, Springer-Verlag New York, 2014. doi:10.1007/978-1-4939-0935-3.
- [34] A. Locatelli, E. Bauer, "Recent advances in chemical and magnetic imaging of surfaces and interfaces by XPEEM", *J. Phys.: Condens. Matter* 20 (2008) 093002.
- [35] T. O. Menteş, G. Zamborlini, A. Sala, A. Locatelli, "Cathode lens spectromicroscopy: methodology and applications", *Beilstein J. Nanotechnol.* 5 (2014) 1873.
- [36] C. M. Schneider, G. Schönhense, "Investigating surface magnetism by means of photoexcitation electron emission microscopy", *Prog. Rep. Phys.* 65 (2002) R1785.
- [37] S. Tanuma, C. J. Powell, D. R. Penn, "Calculations of electron inelastic mean free paths. IX. data for 41 elemental solids over the 50 eV to 30 keV range", *Surface and Interface Analysis* 43 (2011) 689–713.
- [38] W. Weiss, W. Ranke, "Surface chemistry and catalysis on well-defined epitaxial iron-oxide layers", *Progress in Surface Science* 70 (2002) 1.
- [39] J. Restrepo, G. A. Pérez Alcázar, A. Bohórquez, "Description in a local model of the magnetic field distributions of Fe<sub>x</sub>Ni<sub>x</sub> disordered alloys", *Journal of Applied Physics* 81 (1997) 4101–4103.
- [40] P. Kuiper, B. Searle, L.-C. Duda, R. Wolf, P. Van Der Zaag, "Fe L<sub>2,3</sub> linear and circular magnetic dichroism of Fe<sub>3</sub>O<sub>4</sub>", *Journal of Electron Spectroscopy and Related Phenomena* 86 (1997) 107–113.
- [41] F. Schedin, P. Morrall, V. Petrov, S. Case, M. Thomas, E. Dudzik, G. van der Laan, G. Thornton, "Magnetic properties of ultrathin epitaxial Fe<sub>3</sub>O<sub>4</sub> films on Pt(111)", *Journal of Magnetism and Magnetic Materials* 211 (2000) 266 – 270.
- [42] H.-J. Kim, J.-H. Park, E. Vescovo, "Oxidation of the Fe(110) surface: An Fe<sub>3</sub>O<sub>4</sub>(111)/Fe(110) bilayer", *Phys. Rev. B* 61 (2000) 15284.
- [43] A. Mandziak, J. de la Figuera, S. Ruiz-Gómez, G. D. Soria, L. Pérez, P. Prieto, A. Quesada, M. Foerster, L. Aballe, "Structure and magnetism of ultrathin nickel-iron oxides grown on Ru(0001) by high-temperature oxygen-assisted molecular beam epitaxy", *Scientific Reports* 8 (2018) 17980.
- [44] S. V. Barabash, R. V. Chepulskii, V. Blum, A. Zunger, "First-principles determination of low-temperature order and ground states of Fe-Ni, Fe-Pd, and Fe-Pt", *Phys. Rev. B* 80 (2009) 220201.
- [45] H.-J. Kim, J.-H. Park, E. Vescovo, "Fe<sub>3</sub>O<sub>4</sub>(111)/Fe(110) magnetic bilayer: Electronic and magnetic properties at the surface and interface", *Phys. Rev. B* 61 (2000) 15288.



View Article Online  
DOI: 10.1039/D0TC00311E

- [46] G. van der Laan, C. M. B. Henderson, R. A. D. Patrick, S. S. Dhesi, P. F. Schofield, E. Dudzik, D. J. Vaughan, "Orbital polarization in NiFe<sub>2</sub>O<sub>4</sub> measured by Ni-2p x-ray magnetic circular dichroism", Phys. Rev. B 59 (1999) 4314.

