



THE UNIVERSITY *of* EDINBURGH

Edinburgh Research Explorer

Nanophase-photocatalysis: loading, storing, and release of H₂O₂ using graphitic carbon nitride

Citation for published version:

Karunakaran, A, Francis, KJ, Bowen, CR, Ball, RJ, Zhao, Y, Wang, L, McKeown, NB, Carta, M, Fletcher, PJ, Castaing, R, Isaacs, MA, Hardwick, LJ, Cabello, G, Sazanovich, IV & Marken, F 2023, 'Nanophase-photocatalysis: loading, storing, and release of H₂O₂ using graphitic carbon nitride', *Chemical Communications*, vol. 59, no. 48, pp. 7423-7426. <https://doi.org/10.1039/d3cc01442h>

Digital Object Identifier (DOI):

[10.1039/d3cc01442h](https://doi.org/10.1039/d3cc01442h)

Link:

[Link to publication record in Edinburgh Research Explorer](#)

Document Version:

Publisher's PDF, also known as Version of record

Published In:

Chemical Communications

General rights

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact openaccess@ed.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.




 Cite this: *Chem. Commun.*, 2023, 59, 7423

 Received 23rd March 2023,
 Accepted 23rd May 2023

DOI: 10.1039/d3cc01442h

rsc.li/chemcomm

Nanophase-photocatalysis: loading, storing, and release of H₂O₂ using graphitic carbon nitride†



 Akalya Karunakaran,^{ab} Katie J. Francis,^a Chris R. Bowen,^b Richard J. Ball,^c Yuanzhu Zhao,^a Lina Wang,^a Neil B. McKeown,^{id d} Mariolino Carta,^{id e} Philip J. Fletcher,^f Remi Castaing,^f Mark A. Isaacs,^{id g} Laurence J. Hardwick,^{id hi} Gema Cabello,^{hij} Igor V. Sazanovich^{id k} and Frank Marken^{id *a}

A blue light mediated photochemical process using solid graphitic carbon nitride (g-C₃N₄) in ambient air/isopropanol vapour is suggested to be linked to “nanophase” water inclusions and is shown to produce approx. 50 μmol H₂O₂ per gram of g-C₃N₄, which can be stored in the solid g-C₃N₄ for later release for applications, for example, in disinfection or anti-bacterial surfaces.

Graphitic carbon nitride (g-C₃N₄, see Fig. 1A, first synthesised by Berzelius and named by Liebig¹) has a layered structure with many defects that can be produced at low cost and is employed in a number of important applications.^{2,3} Here, we explore the potential of g-C₃N₄ for the formation, storage, and release of hydrogen peroxide (H₂O₂). The photocatalytic formation of H₂O₂ has been widely reported⁴ and is useful to disinfect,⁵ bleach,⁶ or clean environments.⁷ In addition to effective production of H₂O₂ based on photo-catalysis⁸ from ambient oxygen and a hole quencher, there are reports of piezo-catalysis,⁹ which is indicative of a broader range of molecular activation

processes for g-C₃N₄ at the microscopic scale. Singlet oxygen formation with g-C₃N₄ has been observed.¹⁰

Previously, when exploring the photochemical reactivity of g-C₃N₄ (as a solid powder or when immobilising g-C₃N₄ particles into an intrinsically microporous host material PIM-1)¹¹ immersed in a liquid phase, we observed H₂O₂ production in the aqueous phase in the presence of hole quenchers such as glucose or Triton X-100. Here, isopropanol vapour is employed in order to provide a quencher during the corresponding solid-state photochemical process. In contrast to previous studies, here the photocatalytic process is performed with the g-C₃N₄ powder exposed to light in ambient air. H₂O₂ is released only later in the absence of light upon contact to water (eqn (1) and (2)).



In a typical experiment,‡ 50 mg of yellow g-C₃N₄ powder, possessing a flaky layered morphology (Fig. 1B), with surface area = 36.4 m² g⁻¹ (based on nitrogen adsorption data),¹¹ was placed into a Petri dish with a transparent cover and illuminated with a blue light source (Thorlabs M385LP1 with typically 80 mW cm⁻² 385 nm light in approx. 2 cm distance).¹¹ A small vial containing liquid isopropanol was placed into the same Petri dish to maintain an atmosphere of isopropanol vapour as a quencher for holes that are generated by photoexcitation. After a 30 minute treatment, the yellow powder was recovered and then stored in a glass vial. Data from X-ray diffraction analysis (Fig. 1C) show essentially the same features before and after photochemical treatment, which is consistent with literature data for layered g-C₃N₄ (for disordered heptazine-based polymer organized in layers with a separation of 0.326 nm).¹² The main (002) peak occurs at 27.5°. Although literature reports indicate that under long term photo-irradiation conditions *endo*-peroxide signals should be seen,¹³ the data reported here for Raman analysis, surface enhanced Raman, and XPS surface analysis (see Fig. S2–S8, ESI†) all confirm that there is no significant structural change in the bulk, or on the surface, of

^a Department of Chemistry, University of Bath, Claverton Down, Bath BA2 7AY, UK. E-mail: f.marken@bath.ac.uk

^b Department of Mechanical Engineering, University of Bath, Claverton Down, Bath BA2 7AY, UK

^c Department of Architecture & Civil Engineering, University of Bath, Claverton Down, Bath BA2 7AY, UK

^d EaStCHEM School of Chemistry, University of Edinburgh, Joseph Black Building, David Brewster Road, Edinburgh, Scotland EH9 3JF, UK

^e Department of Chemistry, Swansea University, College of Science, Grove Building, Singleton Park, Swansea SA2 8PP, UK

^f University of Bath, Materials & Chemical Characterisation Facility, MC2, UK

^g HarwellXPS, Research Complex at Harwell, STFC Rutherford Appleton Laboratory, Harwell Campus, Didcot, OX11 0FA, UK

^h Stephenson Institute for Renewable Energy, Department of Chemistry, University of Liverpool, Liverpool L69 7ZF, UK

ⁱ The Faraday Institution, Harwell Campus, Didcot, OX11 0RA, UK

^j Schlumberger Cambridge Research, High Cross, Madingley Road, Cambridge CB3 0EL, UK

^k Central Laser Facility, Research Complex at Harwell, STFC Rutherford Appleton Laboratory, Harwell Campus, Didcot OX11 0QX, UK

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3cc01442h>



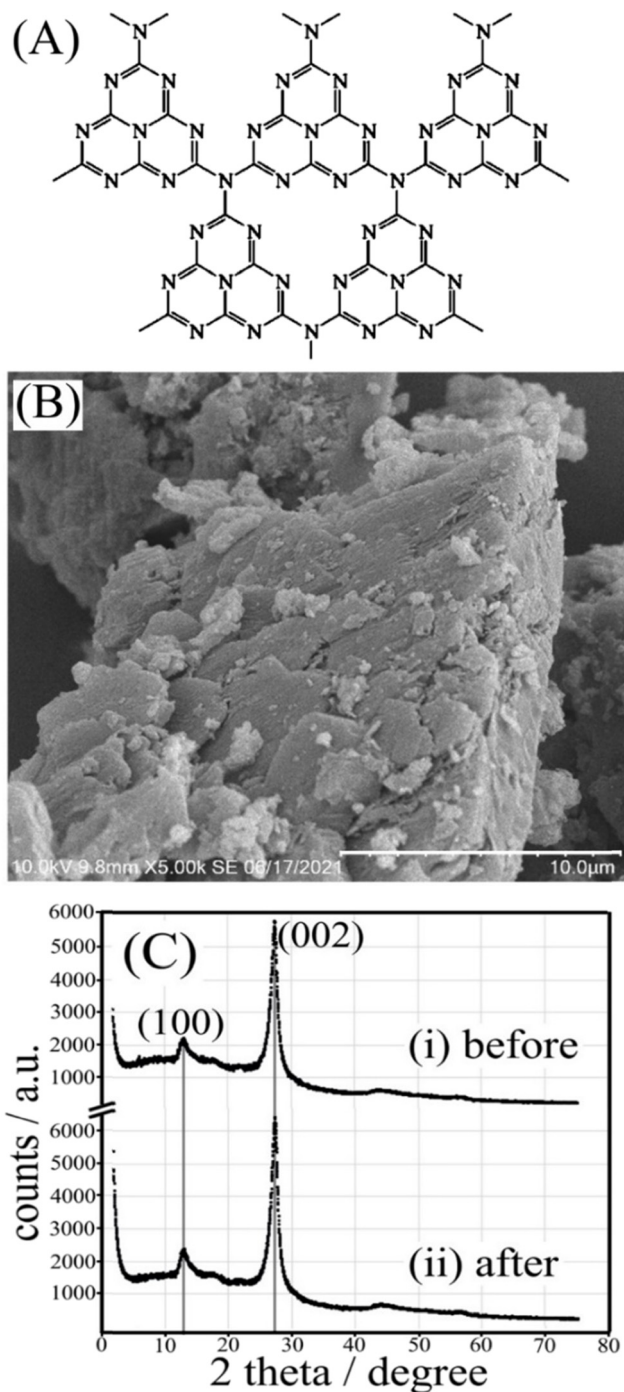


Fig. 1 (A) Molecular structure (idealised) for g-C₃N₄. (B) Scanning electron micrograph for g-C₃N₄ powder. (C) X-ray diffraction data for g-C₃N₄ (i) before and (ii) after blue light treatment in the presence of isopropanol vapour.

the g-C₃N₄ after blue light treatment. Most likely, the endoperoxide content is too low to be detected under these reaction conditions, although a shift from C–N to C–O at% in XPS data (see ESI,† Fig. S2) appears to be linked to the formation of products from the photochemical process on the g-C₃N₄ surface.

Data in Fig. 2A demonstrate the production of H₂O₂ (determined with *para*-nitrophenol and LC/MS detection; ESI†) when

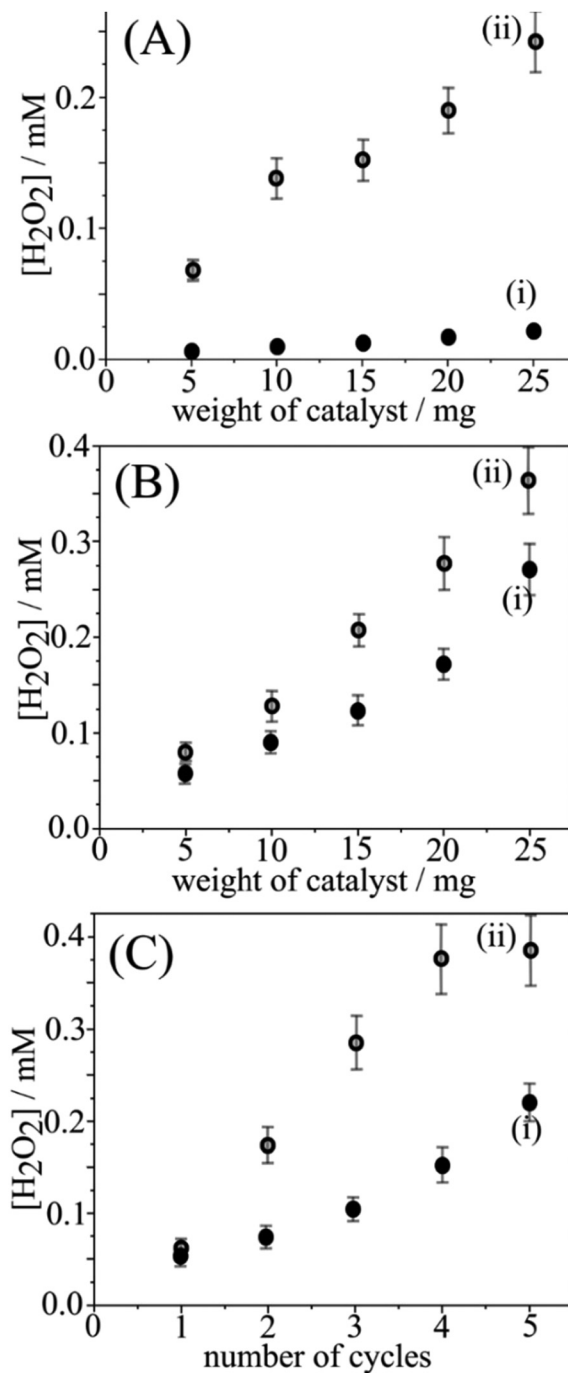






Fig. 2 (A) Production of H₂O₂ with g-C₃N₄ powder suspended in 2 mL water (after 5 minutes) (i) as prepared catalyst and (ii) blue light/isopropanol vapour treated g-C₃N₄ (30 minutes). (B) H₂O₂ release (i) with g-C₃N₄ and (ii) with g-C₃N₄@PIM-1 dispersed in 2 mL water (5 minutes) both after blue light treatment. (C) Repeat measurements with g-C₃N₄@PIM-1 (5 mg) comparing the effects of (i) just intermittent drying in ambient light and (ii) intermittent treatment with blue light in isopropanol vapour. Error bars estimated ±10%.

placing the photoactivated g-C₃N₄ powder into pure water. For the activated g-C₃N₄, typically 100–200 μM H₂O₂ in 2 cm³ water are released, whereas only traces of H₂O₂ are released without prior photoactivation. The release of H₂O₂ occurs immediately



upon immersion and does not continue with time. Adding more $g\text{-C}_3\text{N}_4$ increases the H_2O_2 concentration in an approximately linear fashion. The number of moles of H_2O_2 released suggests approx. one H_2O_2 molecule for every 300 heptazine units in the $g\text{-C}_3\text{N}_4$ powder (or 0.06 wt% H_2O_2) assuming a bulk reaction. Fig. 2B shows data for the release of H_2O_2 (i) for $g\text{-C}_3\text{N}_4$ powder and (ii) for $g\text{-C}_3\text{N}_4$ @PIM-1 composite (employing 17 wt% intrinsically microporous polymer PIM-1 to give a film on filter paper; see ESI†). As in previous studies,^{11,14} PIM-1 is employed as molecularly rigid material to make the photocatalyst easily accessible to the aqueous phase and allows easy recovery for re-use of the catalyst. Fig. 2B shows that both $g\text{-C}_3\text{N}_4$ powder and polymer-embedded $g\text{-C}_3\text{N}_4$ exhibit similar H_2O_2 release.

The data in Fig. 2C demonstrate the re-use of $g\text{-C}_3\text{N}_4$ @PIM-1 with/without additional blue light treatment for up to five cycles. The intermittent blue light treatment clearly enhances the H_2O_2 release so that 0.5 mM H_2O_2 can be produced with only a few reaction cycles. The formation and release of H_2O_2 under blue light conditions can be discussed in terms of the following reaction steps:



Photoexcitation of $g\text{-C}_3\text{N}_4$ leads to an excited state (eqn (3)), which after charge separation produces a hole and an electron. The hole reacts with the isopropanol quencher to give protons and products (eqn (4)). The electrons, which have been reported to generate a strong electron paramagnetic resonance and blue coloration,¹⁵ can combine with ambient oxygen and protons to give trapped H_2O_2 (eqn (5)). The $g\text{-C}_3\text{N}_4(\text{H}_2\text{O}_2)$ material can be stored for several weeks without significant loss of H_2O_2 content (Fig. 3B), and its eventual immersion into water releases H_2O_2 (eqn (6)). Thermogravimetric analysis of $g\text{-C}_3\text{N}_4$ before and after photoreaction (see ESI,† Fig. S9) reveals the presence of water (approx. 2.5 wt%), which is likely to be present as a “nanophase” in between layers and likely to play a crucial role (see eqn (4) during the solid state photochemical formation of H_2O_2). Heating the $g\text{-C}_3\text{N}_4(\text{H}_2\text{O}_2)$ sample to 150 °C removes H_2O and immediately destroys the H_2O_2 . Intriguingly, a vacuum treatment (2h, approx. 10 mTorr) at room temperature also removes the H_2O_2 .

The release of H_2O_2 into aqueous media can be visualised with the 3,3',5,5'-tetramethylbenzidine (TMB) colour reaction.¹⁶ The $g\text{-C}_3\text{N}_4$ treated with blue light and isopropanol was added 2 cm³ of deionized water. After 5 minutes, the solution was filtered with a 0.2 μm filter. The solution is added to the vial containing TMB and 0.1 M CH_3COOH . Fig. 3A shows photographs of the test solutions (i) without and (ii) with 50 μM H_2O_2 intentionally added as reference. Samples (iii) to (viii) correspond to added weights (0, 5, 10, 15, 20, 25 mg) of $g\text{-C}_3\text{N}_4$

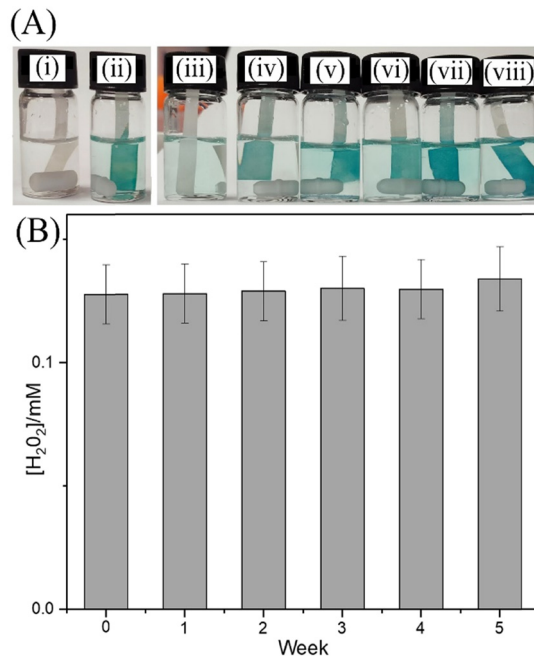


Fig. 3 (A) Test solutions containing 2.5 mL water, 0.5 mL DMSO, 0.1 M CH_3COOH , 0.5 mM TMB, with (i) no addition, with (ii) 50 μM H_2O_2 as a reference, and with (iii) 0 mg, (iv) 5 mg, (v) 10 mg, (vi) 15 mg, (vii) 20 mg, (viii) 25 mg of photoactivated $g\text{-C}_3\text{N}_4$. (B) Plot of release of H_2O_2 (10 mg $g\text{-C}_3\text{N}_4$ in 2 mL water) versus time after blue light/isopropanol treatment (error bars based on one standard deviation and triplicate measurements).

photochemically charged $g\text{-C}_3\text{N}_4$. A Nafion-impregnated filter paper was employed to bind the cationic oxidised form of TMB to amplify the blue colour signal. The colour reaction is consistent with the analysis of H_2O_2 concentration by mass spectrometry and suggests H_2O_2 release in the 50 to 500 μM range.

In conclusion, active sites for photo-generated H_2O_2 binding/storage in the solid $g\text{-C}_3\text{N}_4$ material appear to exist (approx. one bound H_2O_2 per 300 heptazine units), which are probably associated with nanophase water. Once bound, H_2O_2 in $g\text{-C}_3\text{N}_4$ remains stable over prolonged periods of time (Fig. 3B). However, a short vacuum treatment at room temperature or a heat treatment at 150 °C removes both the liquid nanophase H_2O and any trapped H_2O_2 .

Coatings of $g\text{-C}_3\text{N}_4$ could be employed to release H_2O_2 upon contact with water, for example as a disinfectant in hospital environments.²⁰ Further studies of the nature of the H_2O_2 binding interaction, the effects of humidity and the nature of the hole quencher, and further $g\text{-C}_3\text{N}_4$ structural engineering provide future potential to achieve higher levels of H_2O_2 to be bound, stored, and released. Other types of photochemical gas conversions could be performed under illumination in solid state and with aqueous nanophase entrapment.

Akalya Karunakaran: data curation; formal Analysis; investigation; methodology; writing – review & editing. Katie J. Francis: data curation; investigation. Chris R. Bowen and Richard J. Ball: conceptualization; methodology; supervision; writing – review & editing. Yuanzhu Zhao and Lina Wang: data curation; investigation; writing – review & editing. Neil B. McKeown and Mariolino



Carta: conceptualization; supervision; writing – review & editing. Philip J. Fletcher, Remi Castaing, and Mark Isaac: data curation; investigation; writing – review & editing. Laurence J. Hardwick: formal analysis; supervision; writing – review & editing. Gema Cabello and Igor V. Sazanovich: data curation; formal analysis; investigation; methodology; writing – review & editing. Frank Marken: conceptualization; project administration; resources; supervision; writing – original draft.

A. K. thanks the National Overseas Scholarship-India. L. J. H. and G. C. were supported by the UK Faraday Institution (EPSRC EP/S003053/1) through the Degradation Project (grant numbers FIRG001 and FIRG024). STFC is acknowledged for beam time on the ULTRA facility to carry out Kerr-gated experiments. We thank Alexander Cowan (University of Liverpool) for helpful discussion.

Conflicts of interest

There are no conflicts of interest to declare.

Notes and references

‡ Experimental: g-C₃N₄ was prepared as reported previously.¹⁷ PIM-1 was prepared following a literature method.^{18,19} Films of g-C₃N₄@PIM-1 were obtained by drop casting. An amount of 5 mg of graphitic carbon nitride (measured with a Ohaus PX224 analytical balance) was added to the 1 cm³ solution of 1 mg PIM-1 in chloroform and sonicated for 15 minutes. The solution was drop-casted on filter paper with a size of 2 × 2 cm². The sample was air dried to leave a layer of g-C₃N₄@PIM-1 on the filter paper (thickness approx. 0.25 mm). Further experimental details are provided in the ESI.†

- 1 J. V. Liebig, *Ann. Pharm.*, 1834, **10**, 10.
- 2 Y. Wang, X. C. Wang and M. Antonietti, *Angew. Chem., Int. Ed.*, 2012, **51**(1), 68–89.
- 3 K. Z. Qi, S. Y. Liu and A. Zada, *J. Taiwan Inst. Chem. Eng.*, 2020, **109**, 111–123.

- 4 J. Q. Wen, J. Xie, X. B. Chen and X. Li, *Appl. Surf. Sci.*, 2017, **391**, 72–123.
- 5 L. L. Chen, W. P. Shi, T. D. Zhang, R. B. Zhou, X. Q. Jin, Y. Q. Zhou, W. J. Lin, W. H. Guo and D. C. Yin, *2D Mater.*, 2022, **9**(4), 045034.
- 6 Z. Haider, H. I. Cho, G. H. Moon and H. I. Kim, *Catal. Today*, 2019, **335**, 55–64.
- 7 F. Ding, D. Yang, Z. W. Tong, Y. H. Nan, Y. J. Wang, X. Y. Zou and Z. Y. Jiang, *Environ. Sci.: Nano*, 2017, **4**(7), 1455–1469.
- 8 S. W. Cao, J. X. Low, J. G. Yu and M. Jaroniec, *Adv. Mater.*, 2015, **27**(13), 2150–2176.
- 9 C. Hu, F. Chen, Y. G. Wang, N. Tian, T. Y. Ma, Y. H. Zhang and H. W. Huang, *Adv. Mater.*, 2021, **33**(24), 2101751.
- 10 M. Tamtaji, A. Tyagi, C. Y. Young, P. R. Galligan, H. W. Liu, Z. J. Liu, R. Karimi, Y. T. Cai, A. P. Roxas, H. L. Wong and Z. T. Luo, *ACS Appl. Nano Mater.*, 2021, **4**(8), 7563–7586.
- 11 Y. Z. Zhao, L. N. Wang, R. Malpass-Evans, N. B. McKeown, M. Carta, J. P. Lowe, C. L. Lyall, R. Castaing, P. J. Fletcher, G. Kociok-Kohn, J. Wenk, Z. Y. Guo and F. Marken, *ACS Appl. Mater. Interfaces*, 2022, **14**(17), 19938–19948.
- 12 F. Fina, S. K. Callear, G. M. Carins and J. T. S. Irvine, *Chem. Mater.*, 2015, **27**(7), 2612–2618.
- 13 Y. Shiraishi, S. Kanazawa, Y. Sugano, D. Tsukamoto, H. Sakamoto, S. Ichikawa and T. Hirai, *ACS Catal.*, 2014, **4**, 774–780.
- 14 Y. Z. Zhao, J. Dobson, C. Harabaiju, E. Madrid, T. Kanyanee, C. Lyall, S. Reeksting, M. Carta, N. B. McKeown, L. Torrente-Murciano, K. Black and F. Marken, *Bioelectrochemistry*, 2020, **134**, 107499.
- 15 D. Hollmann, M. Karnahl, S. Tschierlei, K. Kailasam, M. Schneider, J. Radnik, K. Grabow, U. Bentrup, H. Junge, M. Beller, S. Lochbrunner, A. Thomas and A. Brückner, *Chem. Mater.*, 2014, **26**(4), 1727–1733.
- 16 L. N. Wang, M. Carta, R. Malpass-Evans, N. B. McKeown, P. J. Fletcher, P. Estrela, A. Roldan and F. Marken, *J. Catal.*, 2011, **416**, 253–266.
- 17 Y. Z. Zhao, N. A. Al Abass, R. Malpass-Evans, M. Carta, N. B. McKeown, E. Madrid, P. J. Fletcher and F. Marken, *Electrochem. Commun.*, 2019, **103**, 1–6.
- 18 P. M. Budd, E. S. Elabas, B. S. Ghanem, S. Makhseed, N. B. McKeown, K. J. Msayib, C. E. Tattershall and D. Wang, *Adv. Mater.*, 2004, **16**, 456–457.
- 19 P. M. Budd, B. S. Ghanem, S. Makhseed, N. B. McKeown, K. J. Msayib and C. E. Tattershall, *Chem. Commun.*, 2004, 230–231.
- 20 Z. Y. Teng, N. L. Yang, H. Y. Lv, S. C. Wang, M. Z. Hu, C. Y. Wang, D. Wang and G. X. Wang, *Chemistry*, 2019, **5**, 664–680.

