

# Electrocatalytic reduction of CO<sub>2</sub> on size-selected nanoclusters of first-row transition metal nanoclusters

Raju, Rajesh Kumar; Rodriguez, Paramaconi; Brothers, Edward N

DOI:  
[10.1039/d3cp00739a](https://doi.org/10.1039/d3cp00739a)

License:  
Creative Commons: Attribution (CC BY)

*Document Version*  
Publisher's PDF, also known as Version of record

*Citation for published version (Harvard):*  
Raju, RK, Rodriguez, P & Brothers, EN 2023, 'Electrocatalytic reduction of CO<sub>2</sub> on size-selected nanoclusters of first-row transition metal nanoclusters: a comprehensive mechanistic investigation', *Physical Chemistry Chemical Physics*, vol. 25, no. 16, pp. 11630-11652. <https://doi.org/10.1039/d3cp00739a>

[Link to publication on Research at Birmingham portal](#)

## General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

## Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.



Cite this: *Phys. Chem. Chem. Phys.*, 2023, 25, 11630

# Electrocatalytic reduction of CO<sub>2</sub> on size-selected nanoclusters of first-row transition metal nanoclusters: a comprehensive mechanistic investigation†

Rajesh Kumar Raju,<sup>id</sup>\*<sup>ab</sup> Paramaconi Rodriguez<sup>id</sup><sup>ac</sup> and Edward N. Brothers<sup>b</sup>

Recycling CO<sub>2</sub> back to fuels offers an ideal solution to control anthropogenic global CO<sub>2</sub> emissions as well as providing a sustainable green solution to alternative energy resources from a cheap and earth-abundant carbon source. Size-selected nanoclusters open a novel area in catalysis as these atomically precise nanoclusters possess unique electronic and catalytic properties different from larger nanoparticles and traditional bulk catalysts. In this work, we have investigated the ability of first-row transition metal nanoclusters (Sc–Cu) of varying sizes (3 to 10 atoms) for CO<sub>2</sub> electroreduction (CO<sub>2</sub>RR). Employing computational hydrogen model (CHE), we have performed detailed analyzes on various CO<sub>2</sub>RR electrocatalytic reaction pathways on all nanocluster surfaces. We have identified a general trend of decreasing adsorption energies while moving across the periodic table from Sc to Cu. Moreover, we have found a general preference for CHO\* mediated pathways over COH\* mediated pathways for methane formation. The CHO\* mediated pathways prefer the reaction route *via* CHO\* → CH<sub>2</sub>O\* → CH<sub>2</sub>OH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \* on most of the nanocluster surfaces. In addition, we have established that methanol formation is greatly disfavored on all nanocluster surfaces, and the release of CO and HCOOH is greatly suppressed on all nanoclusters. We have identified several nanoclusters as potential nanocluster-based electrocatalysts for CO<sub>2</sub>RR for methane formation with relatively lower limiting potential values below 0.50 V. CO<sub>2</sub> electroreduction *versus* hydrogen evolution reaction (HER) competition was also evaluated on various nanoclusters, and we identified a number of nanoclusters (Ti<sub>6</sub>, V<sub>5</sub>, V<sub>6</sub>, Mn<sub>4</sub>, Mn<sub>7</sub>, Mn<sub>10</sub>, Fe<sub>4</sub>, Fe<sub>8</sub>, Fe<sub>10</sub>, Ni<sub>4</sub>, and Cu<sub>5</sub>) that can suppress the formation of HER over CO<sub>2</sub>RR. We have also established a linear scaling relationship between the adsorption free energies of various CO<sub>2</sub>RR adsorbates to the adsorption free energies of CO<sub>2</sub>\*, O\*, and C\* adsorbates. We have found that scaling free energy relationships that exit on heterogeneous catalysts such as the correlation between the adsorption energies of AH<sub>x</sub> with the adsorption energies of atom A (A = C, N, O, S, etc.) often breaks on nanocluster surfaces, especially for adsorbates with more than one binding motifs.

Received 15th February 2023,  
Accepted 5th April 2023

DOI: 10.1039/d3cp00739a

[rsc.li/pccp](http://rsc.li/pccp)

<sup>a</sup> School of Chemistry, University of Birmingham, Edgbaston, Birmingham B15 2TT, UK. E-mail: [rajesh444@gmail.com](mailto:rajesh444@gmail.com)

<sup>b</sup> Science Program, Texas A&M University, Education City, Doha, Qatar

<sup>c</sup> CIC EnergiGune, Parque Tecnológico de Álava, Albert Einstein, 48, 01510 Vitoria-Gasteiz, Álava, Spain

† Electronic supplementary information (ESI) available: Energy corrections (gas-phase, liquid, and solvent corrections); coefficient of determination ( $R^2$ ) values for linear free energy relationship between the adsorption free energies of CO<sub>2</sub>\*, C\*, and O\* with other adsorbates; adsorption free energies ( $\Delta G$ , eV), residual charges ( $e^-$ ), HOMO–LUMO gaps (eV), and spin multiplicities of various adsorbates on first-row transition metal nanoclusters; correlations between residual charges and HOMO–LUMO gaps with adsorption free energies for various adsorbates; free energy changes (eV) for various electrochemical steps in the CO<sub>2</sub>RR process on mid to late TM nanoclusters (Cr–Cu); potential-determining step (PDS) for various CHO\* and COH\* mediated pathways and the free energy changes of the PDSs. See DOI: <https://doi.org/10.1039/d3cp00739a>

## Introduction

One of the defining environmental, energy, and societal challenges of the 21st century is how to efficiently control global warming and the associated climate change by reducing anthropogenic CO<sub>2</sub> emissions. Recycling CO<sub>2</sub> into useful chemicals, in particular to fuels such as carbon monoxide (CO), formic acid (HCOOH), methanol (CH<sub>3</sub>OH), and methane (CH<sub>4</sub>) is an excellent strategy to reduce CO<sub>2</sub> emissions.<sup>1–4</sup> Moreover, it offers a simultaneous sustainable energy solution to the rapid depletion of fossil fuel resources. Even though CO<sub>2</sub> is an inexpensive, abundant, and renewable C1 source for synthesizing many chemicals, the activation and subsequent chemical transformation of CO<sub>2</sub> is a formidable challenge due to its chemical inertness.

Although there have been many heterogeneous catalysts with different supports and promoters reported for the direct



hydrogenation of CO<sub>2</sub> with H<sub>2</sub>, these catalysts exhibit some serious drawbacks such as high operating temperatures and pressures (>200 °C and 50–100 atm pressures), lack of catalyst tuning and formation of undesirable by-products.<sup>5,6</sup> Electrochemical reduction of CO<sub>2</sub> (CO<sub>2</sub>RR) is an alternative way of achieving CO<sub>2</sub> reduction and has the distinct advantage that it operates at room temperature and atmospheric pressure. Moreover, the electrocatalytic activity and selectivity can be easily controlled by varying the electrode potentials.<sup>7–11</sup> Among many metals tested, Cu is the only metal that has been experimentally shown to produce higher-order reduction products such as methane or ethylene, albeit with higher overpotentials for CO<sub>2</sub>RR.<sup>12,13</sup> Although many metals have been proposed for electrocatalytic reduction of CO<sub>2</sub>, industrial-level large-scale conversion is still a formidable challenge. Moreover, hydrogen evolution reaction (HER), a competing side reaction, often prohibits the efficacy of the CO<sub>2</sub>RR catalysts. The development of highly efficient robust catalyst made of cheap and earth-abundant metals are an inevitable necessity to convert the enormous amount of CO<sub>2</sub> that is released into the atmosphere to control global emissions.

Nanocatalysis, more specifically catalysis by nanoparticles (NPs) has gained significant momentum recently due to their high activity and selectivity as well as low metal cost replacing the traditional metal-based bulk catalysts.<sup>14–19</sup> Nanoclusters (NCs), a subclass of nanoparticles with a fewer number of metal atoms (typically < 150 atoms) and subnanometre clusters (size-selected nanoclusters of very few atoms typically < 30), a further subclass of NCs, often exhibit unique electronic and catalytic properties different from their superclass NPs or bulk materials primarily due to size-induced quantum effects.<sup>19,20</sup> These properties depend on the cluster size, cluster composition, shape, increased density of exposed low-coordinated unsaturated sites, and high surface-to-volume ratio. Subnanometre clusters show particular promise in the field of nanocatalysis as the addition or removal of an atom can impart dramatic effects on their catalytic activity and selectivity.

CO<sub>2</sub>RR studies for several metal NPs (Cu, Ni, Au, Ag, Bi, Pd, Sn, *etc.*) were reported previously.<sup>21–41</sup> These studies in general show different CO<sub>2</sub>RR activities and selectivities for NPs of different sizes, which often exhibit enhanced CO<sub>2</sub>RR activities compared to metal surfaces. For instance, CO<sub>2</sub> to CO reduction shows significant improvement on Au<sub>25</sub> nanoclusters compared to larger Au NPs or Au surfaces.<sup>33</sup> Salehi-Khojin *et al.* and Kim *et al.* have shown the enhanced catalytic activity and selectivity for silver NPs.<sup>35,41</sup> Studies on Pd NPs for CO<sub>2</sub>RR show significant enhancement in the faradaic efficiency from 5.8% to 91.2% and an 18.4-fold increase in current density when the size of the Pd NPs reduced from 10.3 nm to 3.7 nm.<sup>39</sup> Different redox behavior for Cu<sub>5</sub> and Cu<sub>20</sub> NPs were reported by Vajda and co-workers.<sup>36</sup> Manthiram *et al.* have demonstrated that Cu NPs supported on glassy carbon exhibit 4 times higher methanation current densities compared to high purity Cu foil electrodes.<sup>42</sup> Similarly, Peter Strasser and co-workers have shown that Cu NPs in the 2–15 nm size range were analyzed for CO<sub>2</sub> electroreduction and found a dramatic increase in the

activity and selectivity for CO with decreasing Cu particle size, particularly below 5 nm.<sup>43</sup> Overpotentials as low as 340 mV were reported for nanostructured Sn catalysts.<sup>44</sup> Bismuth nanoparticles anchored on reduced graphene oxide (Bi/rGO) show very high faradaic efficiency up to 98% for CO<sub>2</sub> reduction to formic acid.<sup>32</sup> The ultimate downsizing of subnanoclusters to one single atom leads to a novel area in nanocatalysis termed “single atom catalysis (SAC).<sup>45,46</sup> Ni and Cu SACs were reported for CO<sub>2</sub>RR with excellent faradaic efficiency and current density.<sup>23,47</sup> Besides electrocatalytic CO<sub>2</sub> reduction, the NP size effects on thermal catalysis (direct hydrogenation of CO<sub>2</sub> with H<sub>2</sub>) were also reported. Most importantly, Stefan Vajda and co-workers reported that Cu<sub>4</sub> is the most active low-pressure catalyst reported to date for the direct CO<sub>2</sub> hydrogenation to CH<sub>3</sub>OH and the removal of one atom from Cu<sub>4</sub> to Cu<sub>3</sub> reduces the activity of CH<sub>3</sub>OH production drastically, by more than 50%.<sup>48,49</sup> They also reported that catalytic activity for methanol formation depends on cluster size and varies in the order Cu<sub>4</sub> > Cu<sub>20</sub> > Cu<sub>3</sub>.

Several theoretical studies have reported for electrocatalytic reduction of CO<sub>2</sub> on nanoclusters. Using the computational hydrogen electrode (CHE) model, Nørskov and co-workers provided the first theoretical insights into copper's unique ability to reduce CO<sub>2</sub> to methane and other hydrocarbons.<sup>50</sup> They proposed a CHO\* intermediate pathway and found the potential-determining step (PDS) is the formation of CHO\* species from CO\* (\* indicates an adsorbed species). Asthagiri *et al.* based on their theoretical work proposed an alternative reaction route that involves the formation of COH\* (hydroxymethylidyne) intermediate.<sup>51,52</sup> DFT studies have been reported for the electroreduction of CO<sub>2</sub> on larger NPs such as Au<sub>38</sub> and Au<sub>55</sub>, Pd<sub>38</sub> and Pd<sub>55</sub>, Au<sub>25</sub>(SCH<sub>3</sub>)<sub>18</sub>, Cu<sub>85</sub>, and Cu<sub>79</sub> as well as on tetra-atomic subnanometre metal clusters (Co<sub>4</sub>, Fe<sub>4</sub>, Cu<sub>4</sub>, Ni<sub>4</sub>, and Pt<sub>4</sub>) for CO<sub>2</sub>RR.<sup>33,37–39,53–56</sup> In a recent work, we have investigated systematically the size effect of Cu subnanometre clusters (Cu<sub>*n*</sub>, *n* = 3–6) and found that nanoclusters with odd numbers of electrons, Cu<sub>3</sub> and Cu<sub>5</sub>, and clusters with even numbers of electrons, Cu<sub>4</sub> and Cu<sub>6</sub>, exhibit similar activity and selectivity.<sup>57</sup> In general, the electrochemical steps which are endergonic on Cu<sub>3</sub> and Cu<sub>5</sub> are exergonic on Cu<sub>4</sub> and Cu<sub>6</sub>, and *vice versa*. These results show that even a single Cu atom can alter the entire reaction pathway at the subnanometre level.

Most of the previous computational work was centered on a few metal clusters such as Cu, Ni, Pd, *etc.* as support information to complement experimental work. In this work, we are systematically evaluating the ability of the atomically precise subnanometre nanoclusters of first-row transition metals (TMs) (Sc–Cu) with 3 to 10 metal atoms for CO<sub>2</sub> electrocatalytic reduction. Our major goal is to identify the potential first-row TM nanoclusters that can be used as CO<sub>2</sub> electroreduction catalysts for the reduction of CO<sub>2</sub> to higher-order reduction products such as methane or methanol with high-efficacy as a sustainable green energy solution to recycling CO<sub>2</sub> back to fuel. Moreover, we aimed at elucidating any general trend in the CO<sub>2</sub>RR activity and selectivity on these metal clusters as well as identifying the most preferred reaction pathways on various



nanoclusters. Moreover, if exists, we tried to establish linear scaling relationships between the free energies of adsorbates on these metal nanoclusters. We have not discussed the synthesizability of the various nanoclusters as it is beyond the scope of our detailed work on the DFT investigation on the first-row TM nanoclusters for CO<sub>2</sub> electroreduction and the elucidation of the general trend on activity and selectivity for CO<sub>2</sub>RR on these nanoclusters.

## Computational methods

Global minimum configurations of the various nanoclusters at the DFT level were determined using birmingham parallel genetic algorithm (BPGA).<sup>58</sup> We used GIGA, a recent advanced version of the BPGA which was coupled to Vienna *ab initio* simulation package (VASP)<sup>59–62</sup> for local DFT relaxations.<sup>63</sup> BPGA uses a pool-based methodology to relax and evaluate the geometries in parallel and has been successfully applied previously to locate the global minimum of pure and alloyed nanoclusters of varied sizes.<sup>64–69</sup>

Gamma-point spin-polarized DFT method was used for local DFT relaxations employing a plane-wave basis set and Perdew–Burke–Erzenhof (PBE)<sup>70</sup> exchange–correlation GGA functional. The ion–electron interaction is treated with projected augmented wave (PAW) pseudopotentials.<sup>71</sup> A plane wave cutoff energy of 400 eV was applied and Methfessel–Paxton<sup>72</sup> smearing with a Sigma value of 0.01 eV was used to improve convergence. The final geometries in the pool including the global minimum were reoptimized with tighter convergence criteria (10<sup>−6</sup> eV in energy and 0.01 eV Å<sup>−1</sup> in force and a higher plane wave cut-off energy of 600 eV) to get more accurate geometries and energy values. We have also included van der Waals correction through Grimme's DFT-D3<sup>73,74</sup> method during re-optimization. We have found that all nanoclusters retained similar geometrical arrangements with minor shifts in some of the atom positions.

Global minimum and other lower energy configurations were used for locating the most stable adsorbate configurations on each of the nanoclusters. Optimization of the cluster-adsorbate complexes was carried out using local DFT relaxations employing VASP. We use the same optimization strategy (PBE functional, DFT-D3 corrections, tighter convergence, and plane wave cut-off energy of 600 eV) for the relaxation of cluster-adsorbate bound complexes for locating the most preferred binding sites on different nanoclusters. The Bader method was used for charge analysis.<sup>75</sup> Free energy of the adsorbates were computed by performing vibrational analysis on adsorbates assuming the nanoclusters were immobilized on some supports. Thermal corrections (zero-point energy corrections, enthalpy and entropy corrections) were computed using harmonic vibrational frequencies of the adsorbates at 298.15 K employing VASPKIT,<sup>76</sup> and these corrections were then added to the DFT electronic energies to get the free energies of the adsorbates. It should be noted that all the reported Gibbs free energy values are standard values, Δ*G*<sup>0</sup> and is calculated at 298.15 K.

Computational hydrogen electrode model (CHE)<sup>50,77</sup> was used to calculate the reaction free energy changes (Δ*G*) for various electrochemical steps. According to the CHE model, the free energy change for an electrochemical step can be calculated as:

$$\Delta G[A^* + (H^+ + e^-) \rightarrow AH^*] = \mu(AH^*) - \mu(A^*) - [\mu(H^+) + \mu(e^-)] \quad (1)$$

In the CHE model, the chemical potential of the (H<sup>+</sup>/e<sup>−</sup>) pair is equal to half the chemical potential of the gas-phase H<sub>2</sub> molecule. The total chemical potential of the proton–electron pair as a function of applied potential *U*, at all temperatures, can be calculated as:

$$\mu(H^+) + \mu(e^-) = 0.5\mu(H_2(g)) - |e|U \quad (2)$$

At the applied potential *U*, the free energy of the proton–electron pair is shifted by −|*e*|*U* which implies that the CO<sub>2</sub>RR step in which proton–electron pairs are transferred becomes less endergonic at negative applied potential bias. At *U* = *U*<sub>L</sub> where *U*<sub>L</sub> is the limiting potential, Δ*G* becomes zero and Δ*G* becomes negative at any *U* < *U*<sub>L</sub>. At standard conditions, Δ*G* = Δ*G*<sup>0</sup> + |*e*|*U* and for a reaction to be spontaneous, Δ*G* should be less than or equal to zero. The limiting potential is the minimum bias to be applied (least-negative potential) which makes all the electrochemical steps in the reaction pathway become downhill (exergonic) in free energy. This potential corresponds to the highest endergonic free energy step in the reaction pathway. The limiting potential is always negative and is measured in volts (*V*) whereas the corresponding free energy of the potential-determining step (PDS) is positive and is measured in eV. For instance, if CO\* → CHO\* is the potential-determining step (PDS) with a free energy change of the PDS of 1.0 eV for the CO<sub>2</sub>RR on a particular material, a negative potential of −1.0 V should be applied to make all the electrochemical steps be exergonic. The CHE model is a thermodynamic model and ignores the kinetic barriers for (H<sup>+</sup>/e<sup>−</sup>) pair transfers to adsorbate species. It assumes that the barriers for proton transfer to adsorbed species are small enough to be surmountable at room temperatures. Previous studies on the proton transfer barriers for the reduction of O<sub>2</sub> to OOH and OH to H<sub>2</sub>O on Pt supports this assumption as these proton transfer barriers lie in the range of 0.15 to 0.25 eV for zero applied potential and decrease with increasing applied voltage.<sup>78,79</sup> The thermodynamic free energy changes for various electrochemical steps predicted by the CHE model can be used as a catalytic descriptor for the favorability of the CO<sub>2</sub> electroreduction on various nanocluster surfaces. Further details regarding DFT energy correction of gas-phase molecules, solvent corrections, and liquid-phase corrections were provided in the ESI.†

## Results and discussions

### Global minimum configurations of first-row TM nanoclusters Sc<sub>*n*</sub>–Cu<sub>*n*</sub> (*n* = 3–10)

Structural characterization and locating the global minima of nanoclusters is one of the primary steps in the modeling of



nanocatalysts as the catalytic activity and selectivity are often dependent on the size and shape of the nanoclusters. Moreover, the multitude of possible geometrical arrangements for a given nanocluster composition makes the potential energy surface (PES) highly complex as a variety of configurations can have very similar energies. Atomically precise smaller-sized nanoclusters require an accurate description of the PES at the DFT level as the quantum size effects tend to dominate as the system decreases. We have performed an extensive search for locating the global minimum configurations for all the first-row TM nanoclusters employing the GIGA version of the birmingham parallel genetic algorithm (BPGA) at the DFT level.

The first step in the GA run is to generate a number of random geometries (10 in this study) followed by relaxing these geometries into local minima to form the initial pool population. Based on the crossover and mutation rate, GA crossover and mutation operations are applied to the members of the pool to generate new structures. For crossover operation, a pair of clusters are selected from the pool using a weighted roulette-wheel selection method<sup>80</sup> and they undergo mating using a variant of the Deaven and Ho phenotypic cut-and-splice method<sup>81</sup> to generate a single offspring. Different mutation operations such as “move”, “rotate”, “twist”, “partial inversion”, “rattle” *etc.* are performed on a randomly selected cluster through roulette-wheel selection. Skin mutation will keep 80% of the cluster atoms remain intact and the remaining 20% atoms will be placed in random positions around the cluster; rattle mutation operation will choose a random atom and move 40% of the cluster atoms nearest to that atom; change core mutation will change the core of the cluster; rotation and twist mutations will rotate and twist a percentage of cluster atoms; partial inversion operation will invert a subclass of cluster atoms with respect to their geometrical center; tunnel operation will move one of the atoms farthest from the center to the other side of the cluster. The overall objective of these operations is to update the pool with diverse geometries to avoid stagnation after a few generations.

For each cluster, we have run the genetic algorithm for a minimum of 400 generations and often more than 1500 generations. Each generation involves the relaxation of the newly generated geometry *via* crossover or mutation operations. Another parallel run was also performed to make sure that both the BPGA runs arrive at the same global minimum configurations for all the clusters. The global minimum configurations for first-row TM nanoclusters ( $\text{Sc}_n\text{-Cu}_n$ ,  $n = 3\text{--}10$ ) were shown in Fig. 1. The geometry, spin-state, and point group of the global minimum of the Sc–Cu clusters are given in Table 1.

For nanoclusters with three metal atoms, an isosceles triangular arrangement is the global minimum configuration for all first-row TM nanoclusters except for Cr, Mn, and Ni.  $\text{Cr}_3$  shows a V-shaped arrangement whilst  $\text{Mn}_3$  and  $\text{Ni}_3$  show an equilateral triangle arrangement. Tetrahedral, distorted tetragonal (butterfly-shape), and parallelogram are the global minimum configurations for clusters with four atoms. The global minimum for first-row metal nanoclusters with five, six, and seven

atoms prefer in general, a trigonal bipyramid (TBP) octahedron ( $\text{O}_h$ ), and pentagonal bipyramid (PBP) arrangement. These arrangements often exhibit reduced symmetries owing to the elongation or contraction of some of the metal–metal bonds. There are exceptions such as tetragonal bipyramid for  $\text{V}_6$ , W-shaped planar arrangement for  $\text{Cu}_5$ , and capped octahedron for  $\text{Co}_7$  and  $\text{Ni}_7$ . Dodecahedron with varied symmetries is the global minimum configuration for all first-row nanoclusters with eight atoms except for  $\text{V}_8$  and  $\text{Fe}_8$  which prefer hexagonal bipyramid and capped pentagonal bipyramid geometries as the global minima. Tricapped tetragonal prism is the global minimum configuration for  $\text{Sc}_9$ ,  $\text{Fe}_9$ ,  $\text{Co}_9$ , and  $\text{Ni}_9$ . Bicapped pentagonal bipyramid with varying degrees of distortion is the preferred geometrical arrangement for global minimum configuration for  $\text{Ti}_9$ ,  $\text{V}_9$ ,  $\text{Cr}_9$ , and  $\text{Mn}_9$  whilst  $\text{Cu}_9$  prefers a tricapped octahedral arrangement.  $\text{Sc}_{10}$ ,  $\text{Cr}_{10}$ , and  $\text{Fe}_{10}$  adopt a tricapped pentagonal bipyramid configuration for the global minimum. Other clusters adopt different configurations such as bi-capped tetragonal antiprism for  $\text{Ti}_{10}$ ,  $\text{Cu}_{10}$ , and  $\text{Mn}_{10}$ , bi-capped square antiprism for  $\text{V}_{10}$ , bi-octahedra for  $\text{Co}_{10}$ , and tetra-capped  $\text{O}_h$  for  $\text{Ni}_{10}$ . The geometrical arrangement for  $\text{Mn}_{10}$  and  $\text{Cu}_{10}$  exhibits a  $D_{2d}$  symmetry in its bicapped tetragonal antiprism arrangement and can be considered as a spiro-pentagonal bipyramid configuration similar to spiro-pentane. We have also noticed alternative shorter (1.7–1.8 Å) and longer bond lengths for Cr clusters in the range of (2.5–2.7 Å). The existence of the shorter bonds between Cr atoms may be attributed to the higher-order quintuple bonds as experimentally characterized in a number of dichromium complexes.<sup>82,83</sup>

We then performed an extensive search for the energetically most preferred binding sites on the reoptimized global minimum configurations. We have considered all the possible unsymmetrical edges and metal atom sites for binding the adsorbates as well as different binding modes and orientations of the adsorbates. In addition to the global minimum configurations, we have also considered other lower energy configurations for locating the adsorbate binding sites as the energy difference between the global minimum and these low-lying configurations is often very small. We have sampled all the nanoclusters configurations obtained in the genetic algorithm search that falls within 0.5 eV of the global minimum energy. This leads to a significantly higher number of initial configurations for adsorbates on nanoclusters for geometry relaxation. We performed such an extensive search on cluster-adsorbate complexes to reaffirm that we found the most stable adsorbate binding site on the nanocluster. Nørskov *et al.* and Asthagiri *et al.* proposed the lowest energy reaction pathways for  $\text{CO}_2$  electroreduction *via*  $\text{CHO}^*$  and  $\text{COH}^*$  adsorbates on metallic Cu surfaces, respectively.<sup>50,51</sup> We have chosen the adsorbate species involved in these pathways for our  $\text{CO}_2$ RR studies on first-row TM nanoclusters.

### Activation of $\text{CO}_2$

$\text{CO}_2$  activation is one of the primary challenges in the  $\text{CO}_2$  recycling process due to the high thermodynamic stability of the  $\text{CO}_2$ . We have evaluated the adsorption free energies



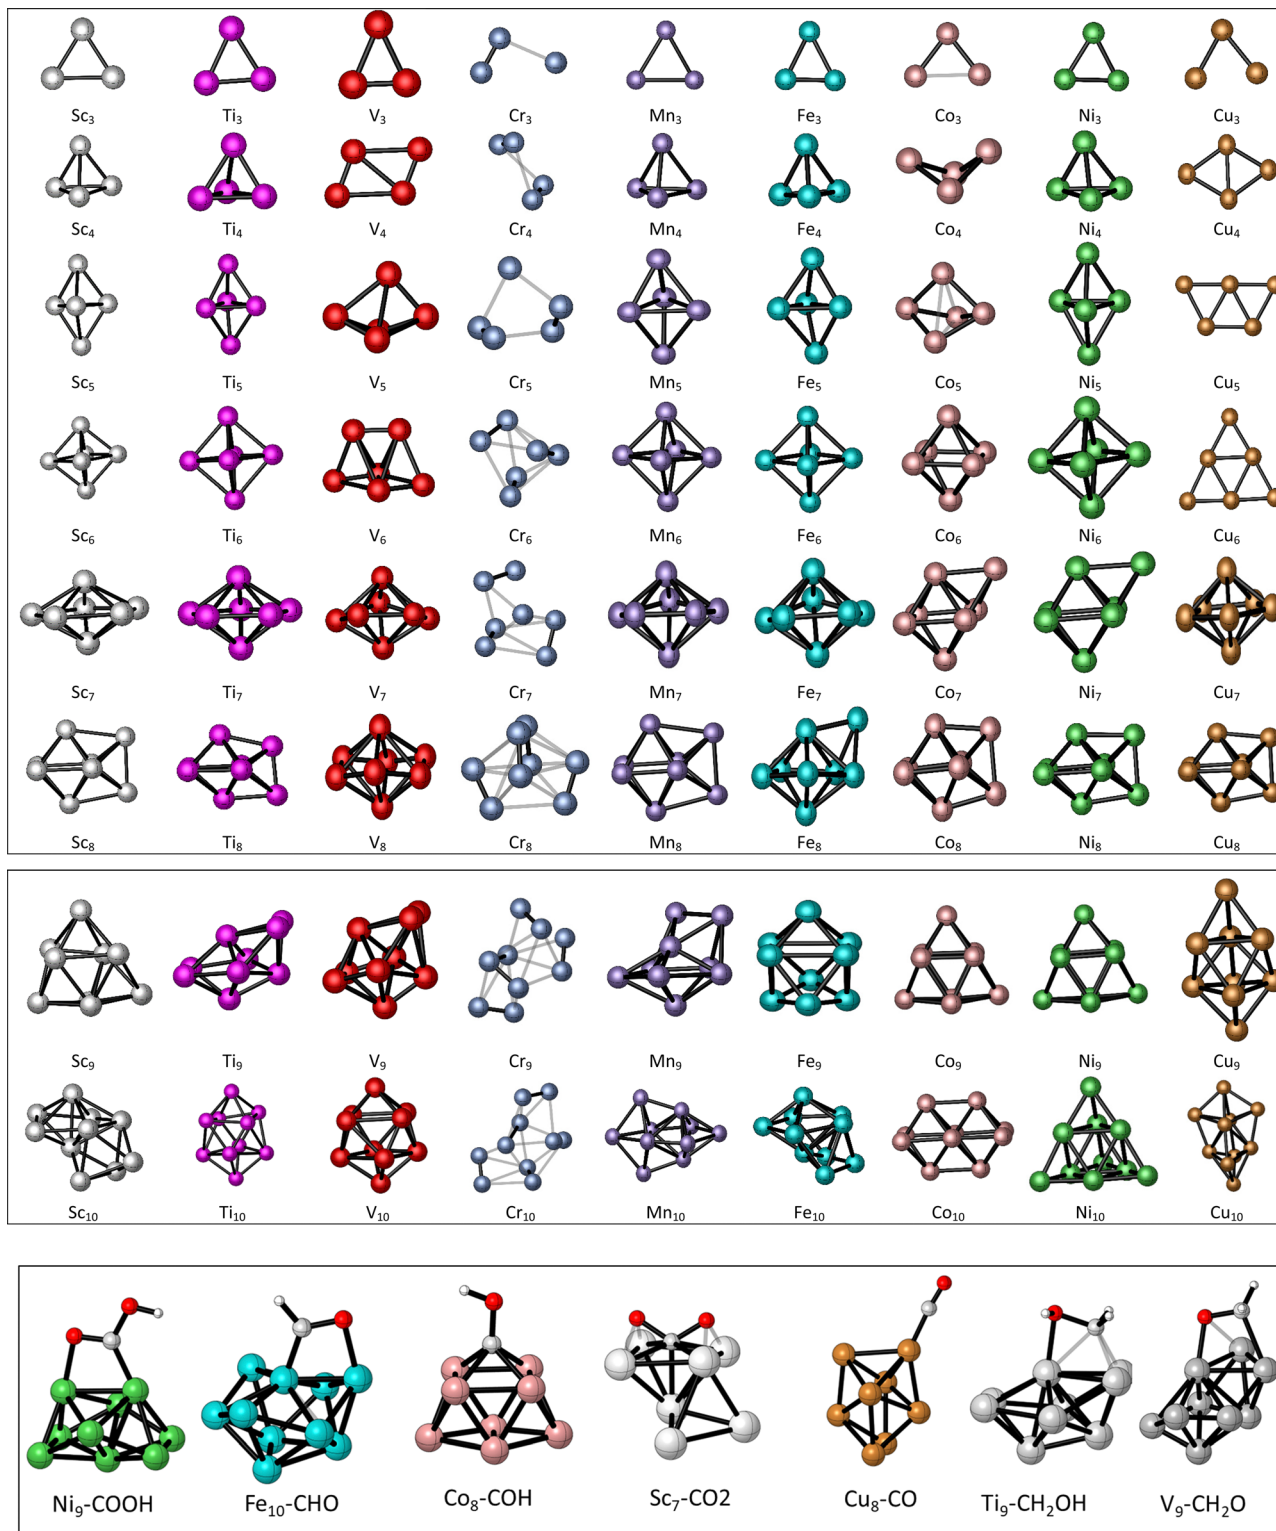


Fig. 1 Top panel: Global minimum geometries for first-row TM nanoclusters ( $\text{Sc}_n\text{-Cu}_n$ ,  $n = 3\text{--}10$ ). Bottom panel: Some representative examples of the cluster-adsorbates.

(or chemisorption energies) of  $\text{CO}_2$  on various first-row TM nanoclusters and are shown in Fig. 2(a). The adsorption free energies are highest on Sc nanoclusters followed by on Ti nanoclusters as evident from Fig. 2(a). Sc and Ti nanoclusters

exhibit the  $\text{CO}_2$  adsorption energies in the range of  $-3.8$  eV to  $-4.5$  eV and  $-2.4$  eV to  $-3.1$  eV, respectively. All other TM nanoclusters show relatively lower adsorption energies compared to Sc and Ti. The adsorption energies for V ( $-1.5$  eV to



**Table 1** Geometry description, point group symmetry and spin state for the global minimum configurations of the first-row TM nanoclusters  $Sc_n$ – $Cu_n$  ( $n = 3$ – $10$ ) determined through birmingham parallel genetic algorithm (BPGA) using PBE functional

Geometry	Symmetry	Spin state
Sc <sub>3</sub>	Isosceles triangle	C <sub>2v</sub> 2
Sc <sub>4</sub>	Tetrahedron	D <sub>2d</sub> 3
Sc <sub>5</sub>	Trigonal bipyramid	D <sub>3h</sub> 6
Sc <sub>6</sub>	Octahedron	D <sub>4h</sub> 5
Sc <sub>7</sub>	Pentagonal bipyramid	C <sub>5h</sub> 6
Sc <sub>8</sub>	Dodecahedron	C <sub>2v</sub> 5
Sc <sub>9</sub>	Tri-capped trigonal prism	C <sub>s</sub> 8
Sc <sub>10</sub>	Tri-capped Pentagonal bipyramid	C <sub>s</sub> 7
Ti <sub>3</sub>	Isosceles triangle	C <sub>2v</sub> 3
Ti <sub>4</sub>	Tetrahedron	D <sub>2d</sub> 5
Ti <sub>5</sub>	Trigonal bipyramid	C <sub>2</sub> 3
Ti <sub>6</sub>	Octahedron	D <sub>4h</sub> 5
Ti <sub>7</sub>	Pentagonal bipyramid	D <sub>5h</sub> 1
Ti <sub>8</sub>	Dodecahedron	C <sub>s</sub> 3
Ti <sub>9</sub>	Bicapped Pentagonal bipyramid	C <sub>2v</sub> 3
Ti <sub>10</sub>	Bicapped quadrilateral antiprism	D <sub>2</sub> 3
V <sub>3</sub>	Isosceles triangle	C <sub>2v</sub> 2
V <sub>4</sub>	Parallelogram	C <sub>2h</sub> 3
V <sub>5</sub>	Buckled tetragonal pyramid	C <sub>s</sub> 2
V <sub>6</sub>	Tetragonal bipyramid	C <sub>2</sub> 3
V <sub>7</sub>	Distorted PBP	C <sub>s</sub> 2
V <sub>8</sub>	Hexagonal bipyramid	D <sub>3d</sub> 1
V <sub>9</sub>	Bicapped buckled pentagonal bipyramid	C <sub>1</sub> 2
V <sub>10</sub>	Bicapped square antiprism	D <sub>4</sub> 1
Cr <sub>3</sub>	V-Shaped	C <sub>s</sub> 7
Cr <sub>4</sub>	Butterfly-shaped	D <sub>2</sub> 3
Cr <sub>5</sub>	Distorted tetragonal bipyramid	C <sub>2</sub> 7
Cr <sub>6</sub>	Bicapped butterfly	C <sub>1</sub> 3
Cr <sub>7</sub>	Distorted pentagonal bipyramid	C <sub>1</sub> 7
Cr <sub>8</sub>	Dodecahedron	C <sub>2</sub> 1
Cr <sub>9</sub>	Bicapped distorted pentagonal bipyramid	C <sub>1</sub> 5
Cr <sub>10</sub>	Tricapped distorted pentagonal bipyramid	C <sub>1</sub> 1
Mn <sub>3</sub>	Equilateral triangle	D <sub>3h</sub> 16
Mn <sub>4</sub>	Tetrahedron	C <sub>3</sub> 11
Mn <sub>5</sub>	Trigonal bipyramid	C <sub>s</sub> 14
Mn <sub>6</sub>	Octahedron	C <sub>3v</sub> 3
Mn <sub>7</sub>	Distorted pentagonal bipyramid	C <sub>s</sub> 6
Mn <sub>8</sub>	Dodecahedron	C <sub>s</sub> 19
Mn <sub>9</sub>	Bicapped pentagonal bipyramid	C <sub>s</sub> 16
Mn <sub>10</sub>	Bicapped tetragonal antiprism	D <sub>2d</sub> 13
Fe <sub>3</sub>	Isosceles triangle	C <sub>s</sub> 11
Fe <sub>4</sub>	Tetrahedron	D <sub>2d</sub> 13
Fe <sub>5</sub>	Trigonal bipyramid	D <sub>3h</sub> 19
Fe <sub>6</sub>	Octahedron	C <sub>s</sub> 21
Fe <sub>7</sub>	Distorted pentagonal bipyramid	C <sub>2</sub> 23
Fe <sub>8</sub>	Capped pentagonal bipyramid	C <sub>s</sub> 25
Fe <sub>9</sub>	Tricapped trigonal prism	C <sub>1</sub> 27
Fe <sub>10</sub>	Tricapped pentagonal bipyramid	C <sub>3v</sub> 29
Co <sub>3</sub>	Isosceles triangle	C <sub>s</sub> 8
Co <sub>4</sub>	Butterfly-shaped	D <sub>2d</sub> 11
Co <sub>5</sub>	Trigonal bipyramid	D <sub>3h</sub> 14
Co <sub>6</sub>	Octahedron	O <sub>h</sub> 15
Co <sub>7</sub>	Capped Octahedron	C <sub>3v</sub> 16
Co <sub>8</sub>	Dodecahedron	C <sub>2</sub> 17
Co <sub>9</sub>	Tricapped Trigonal prism	D <sub>3h</sub> 18
Co <sub>10</sub>	Bi-Octahedron	C <sub>2h</sub> 21
Ni <sub>3</sub>	Equilateral triangle	D <sub>3h</sub> 3
Ni <sub>4</sub>	Tetrahedron	D <sub>2d</sub> 5
Ni <sub>5</sub>	Trigonal bipyramid	D <sub>3h</sub> 5
Ni <sub>6</sub>	Octahedron	D <sub>3d</sub> 9
Ni <sub>7</sub>	Capped octahedron	C <sub>3v</sub> 9
Ni <sub>8</sub>	Dodecahedron	C <sub>2v</sub> 9
Ni <sub>9</sub>	Tri-capped trigonal prism	D <sub>3h</sub> 9
Ni <sub>10</sub>	Tetra-capped Octahedron	T <sub>d</sub> 9
Cu <sub>3</sub>	Isosceles triangle	C <sub>2v</sub> 2
Cu <sub>4</sub>	Parallelogram	D <sub>2h</sub> 1

**Table 1** (continued)

Geometry	Symmetry	Spin state
Cu <sub>5</sub>	W-Shaped	C <sub>2v</sub> 2
Cu <sub>6</sub>	Equilateral triangle	D <sub>3h</sub> 1
Cu <sub>7</sub>	Pentagonal bipyramid	D <sub>5h</sub> 2
Cu <sub>8</sub>	Dodecahedron	D <sub>2d</sub> 1
Cu <sub>9</sub>	Bicapped buckled pentagonal bipyramid	C <sub>s</sub> 2
Cu <sub>10</sub>	Bicapped tetragonal antiprism	D <sub>2d</sub> 1

–2.1 eV), Cr (–1.0 to –1.4 eV), Mn (–0.8 eV to –2.0 eV), Fe (–0.6 eV to –1.15 eV) Co (–0.32 eV to –1.31 eV) Ni (–0.55 eV to –1.28 eV) and Cu (+0.14 eV to –0.44 eV) nanoclusters are smaller than CO<sub>2</sub> adsorption energies on Sc and Ti nanoclusters. Among all the nanoclusters studied Cu nanoclusters exhibit the lowest CO<sub>2</sub> adsorption free energies.

Fig. 2(b) shows the residual charges on CO<sub>2</sub> moiety on the nanoclusters. Bader charge analysis has shown that there is always a net negative charge accumulation of approximately 2e<sup>–</sup> on the two O atoms of the CO<sub>2</sub> moiety on binding on all the nanoclusters. Depending on the charge accumulation or depletion on the C atom of the CO<sub>2</sub>, the overall residual charges on nanoclusters vary. We have found a trend of increasing positive charge on the C atom of CO<sub>2</sub> moving from Sc to Cu. Except on Sc<sub>3</sub> and Sc<sub>4</sub> clusters, all other Sc clusters show a small increase in electron density on the C atom of the CO<sub>2</sub>. All other first-row TM nanoclusters show a depletion of electron density on the C atom and carry a positive charge. From the linear regression plot in Fig. 2(f), we have identified a strong correlation between the residual charges on CO<sub>2</sub> moiety and the adsorption free energies. Fig. 2(c) and (d) show the HOMO–LUMO gaps and spin multiplicities on CO<sub>2</sub>-bound nanoclusters. We could not find a direct correlation between the adsorption energies with HOMO–LUMO gaps or spin multiplicities. Mn, Fe, and Co nanoclusters exhibit significantly higher spin state multiplicities whilst Cu shows only two spin states: singlet or doublets. We have also analyzed the changes in the C–O bond distances of CO<sub>2</sub>\* on various nanoclusters and the average bond distances of the two C–O bond distances were plotted in Fig. 2(e). The significantly larger activation of CO<sub>2</sub> on Sc and Ti nanoclusters was also reflected in the CO<sub>2</sub> bond elongation.

### Electrochemical adsorption of CO<sub>2</sub>

The first step in the electrochemical reduction of CO<sub>2</sub> (CO<sub>2</sub>RR) is the transfer of a proton–electron (H<sup>+</sup> + e<sup>–</sup>) pair to CO<sub>2</sub> to form electrochemical adsorption species COOH\*. However, there is a competition between chemisorption of CO<sub>2</sub> (CO<sub>2</sub>\*) versus electrochemical adsorption of CO<sub>2</sub> (COOH\*). The COOH\* adsorption free energies are shown in Fig. 3(a). As in the case of CO<sub>2</sub>\* adsorption free energies, the free energy values show a regular decrease across the first-row TM nanoclusters from Sc to Cu. In Fig. 3(c), we have plotted the difference between chemisorption free energies of CO<sub>2</sub>\* and adsorption free energies of COOH\*. It can be seen that Sc clusters show a greater preference for chemisorbed CO<sub>2</sub>\* species. In general, we have seen a trend that moving from early TMs (Sc–V) to mid TMs (Cr–Fe) to late



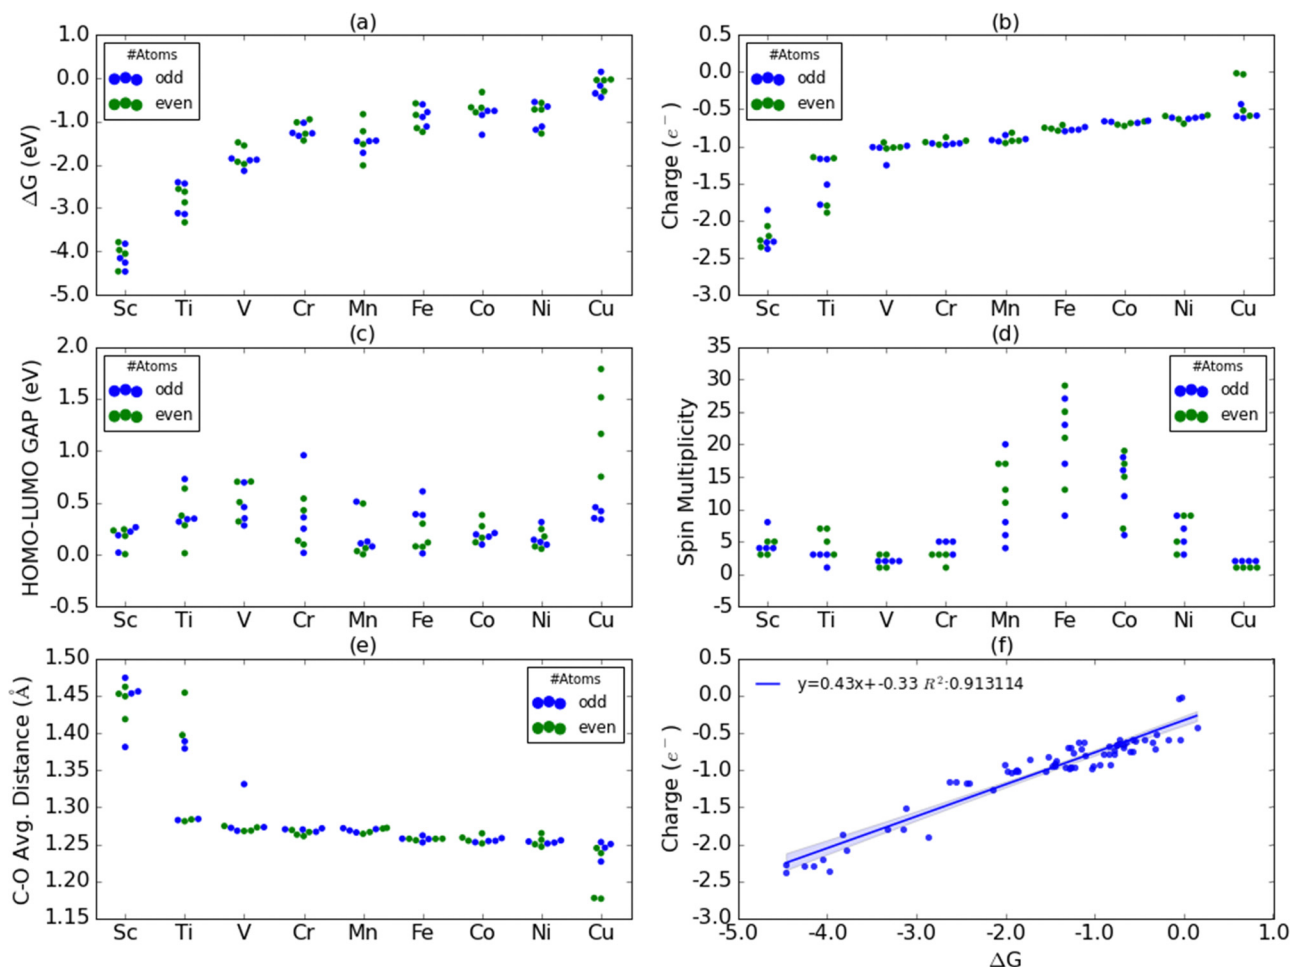


Fig. 2 (a)  $\text{CO}_2^*$  adsorption free energies ( $\Delta G$ , eV) (b) residual charges ( $e^-$ ) on  $\text{CO}_2$  moiety, (c) HOMO–LUMO gaps of  $\text{CO}_2^*$  (d) spin multiplicity of  $\text{CO}_2^*$ , (e) average C–O bond distances in  $\text{CO}_2^*$  adsorbates, and (f) correlation between  $\text{CO}_2^*$  adsorption free energies and residual charges on  $\text{CO}_2^*$  for various Sc, Ti, V, Cr, Mn, Fe, Co, Ni and Cu nanoclusters of 3 to 10 atom sizes. Residual charge indicates the total Bader charge density resides on  $\text{CO}_2$  moiety on binding on cluster moiety. The labels ‘odd’ and ‘even’ indicate whether the total cluster atoms are odd or even number composition.

TMs (Co–Cu), the difference between  $\text{CO}_2^*$  adsorption energies and  $\text{COOH}^*$  electrochemical adsorption energies decreases. Except for Fe, Co, Ni, and Cu, all other metal clusters show a general preference for chemisorbed  $\text{CO}_2^*$  species. Similar to  $\text{CO}_2^*$ , we have seen a decrease in the residual negative charges on  $\text{COOH}^*$  moiety in moving from early to late first-row TM nanoclusters (Fig. 3(b)). We have also identified a similar correlation between adsorption free energies and residual charges on  $\text{COOH}^*$  species (Fig. 3(d)). Bader charge analysis shows that each O atom of the  $\text{COOH}^*$  carries a negative charge of  $\sim 1e^-$  and the H atom carries a positive charge of  $\sim 0.5e^-$ . Moving from Sc to Cu, we have seen a trend of reduction in the electron density on the C atom of the  $\text{COOH}^*$  and the overall positive charge on the C atom depends on the extent to which electron density depletion occurs around the C atom of the  $\text{COOH}^*$  species.

#### Adsorption of CO and other $\text{CO}_2\text{RR}$ intermediates

The adsorption energy of  $\text{CO}^*$  is one of the important factors that determine whether the electrochemical reduction reaction

proceeds beyond the two-electron reduction process. CO is weakly coordinated on most of the metal surface and easily escapes from the surface forming the free CO as the major  $\text{CO}_2\text{RR}$  product prohibiting the formation of the higher-order six or eight electron reduction products such as  $\text{CH}_3\text{OH}$  or  $\text{CH}_4$ . In Fig. 4(a) we have shown the adsorption energies of CO on various nanoclusters. Similar to  $\text{CO}_2^*$ , the adsorption free energies of  $\text{CO}^*$  are significantly larger on Sc and Ti nanoclusters. Moreover, we have seen a significant stretching of C–O bonds on Sc and Ti nanoclusters ( $1.35 \text{ \AA}$  to  $1.52 \text{ \AA}$ ) and a decrease in the C–O stretching effect in moving from early TM nanoclusters to late TM nanoclusters. We have seen that for all cluster-CO adsorbates, there is always an increase of  $\sim 1e^-$  charge density on the O atom of the CO moiety. We have seen increased electron density on the C atom results in the higher overall negative charge on CO moiety on Sc and Ti clusters. In general, we have seen a trend of reduced electronic density on C of the CO moving from early- to mid- to late first-row TM nanoclusters and the overall residual charge resides on CO moiety varies depending on the extent to which depletion of





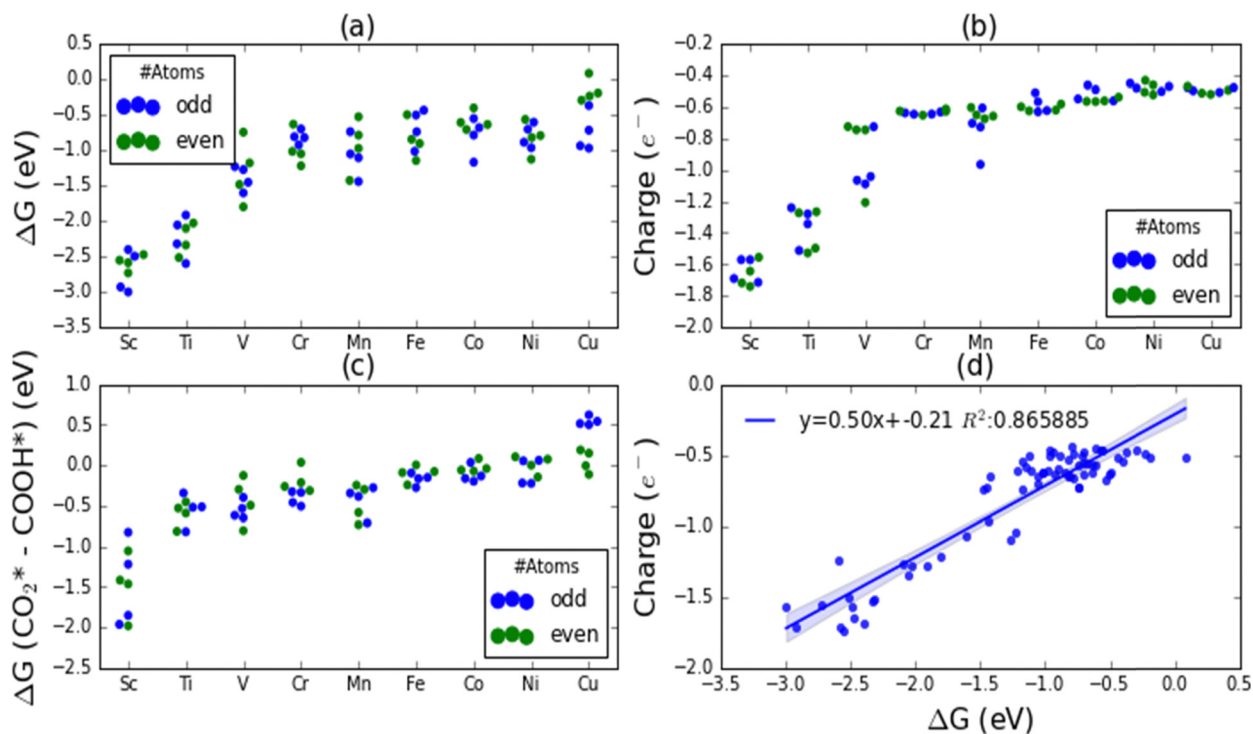


Fig. 3 (a) COOH\* adsorption free energies ( $\Delta G$ , eV), (b) residual charges ( $e^-$ ) on COOH\*, (c) difference in CO<sub>2</sub>\* and COOH\* adsorption free energies (eV), and (d) correlation between COOH\* adsorption free energies and residual charges on COOH\* for various Sc–Cu nanoclusters. Residual charge indicates the total Bader charge density resides on COOH moiety on binding on cluster moiety.

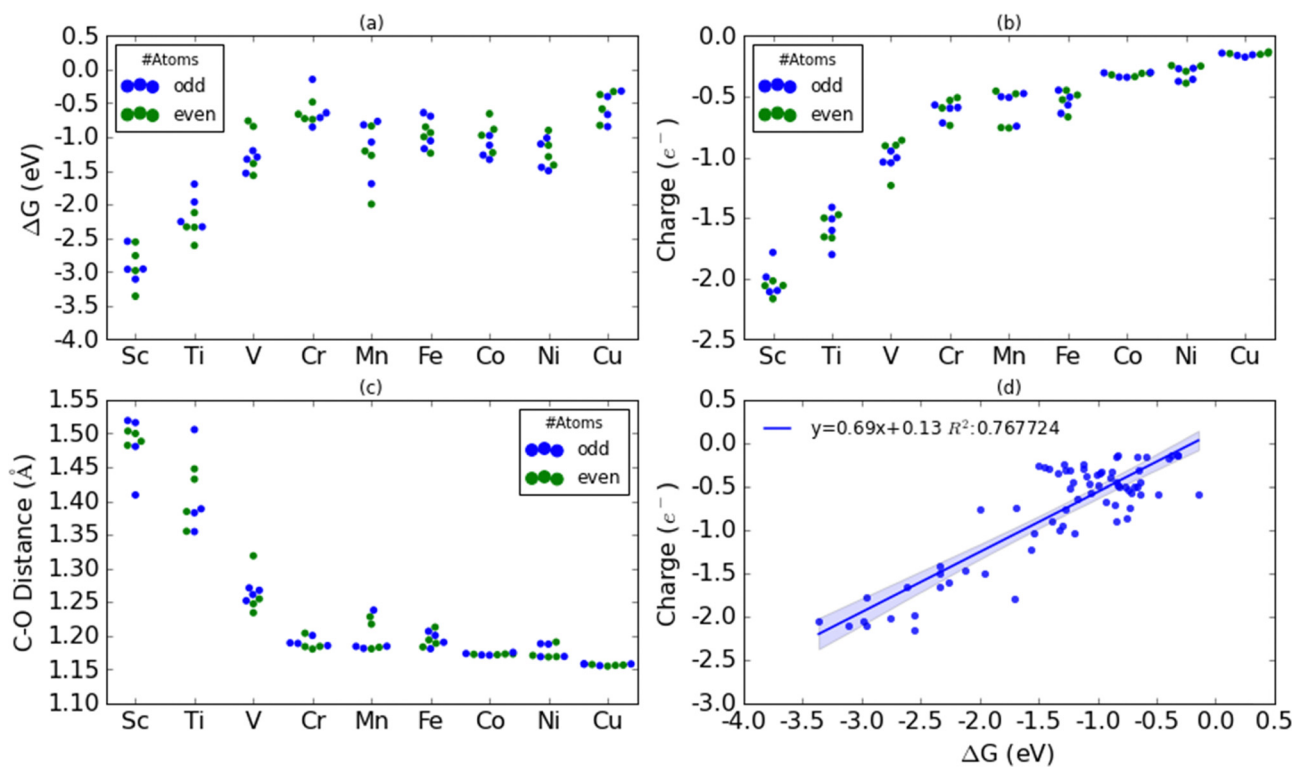


Fig. 4 (a) CO\* adsorption free energies ( $\Delta G$ , eV), (b) residual charge ( $e^-$ ) on CO\*, (c) C–O bond distances ( $\text{\AA}$ ) in CO\*, and (d) correlation between CO\* adsorption free energies and residual charges on CO\* for various Sc–Cu nanoclusters. Residual charge indicates the total Bader charge density resides on CO moiety on binding on cluster moiety.



electron density happens on C atoms. We have also established a correlation between CO\* adsorption energy and residual charges on CO moiety which is shown in Fig. 4(d).





We have shown the adsorption free energies, residual charges, HOMO–LUMO gaps, spin multiplicities, and correlation between adsorption free energies with residual charges and HOMO–LUMO gaps for all adsorbates in Fig. S1–S6 (ESI†). We have identified that in general, all adsorbates show stronger adsorption free energies on early first-row TM nanoclusters and the adsorption free energies show a general trend of reduced binding affinity as we move across the periodic table from early to late first-row TMs (Fig. S1, ESI†). Some exceptions in the general trend are expected which can be attributed to the stability differences that arise from the rearrangement of cluster atoms on binding with the adsorbates and the associated spin state changes. A similar trend of decreasing residual charge density on adsorbate species on Sc to Cu nanoclusters was also identified (Fig. S2, ESI†). However, a similar high correlation between adsorption free energies and residual charges on CO<sub>2</sub>\*, COOH\*, and CO\* species were not observed for other adsorbates except for CHO\* and CH<sub>2</sub>O\* (Fig. S3, ESI†). All other adsorbates show a coefficient of determination (*R*<sup>2</sup>) value below 0.70. The adsorbates exhibit a range of spin multiplicities on all TM nanoclusters except for Cu which shows only singlet and doublet states. We have noted that there exists no correlation between the adsorption free energies with spin multiplicities or HOMO–LUMO gaps of different adsorbates.

### Electrochemical reduction of CO<sub>2</sub>




We now turn to the CO<sub>2</sub>RR reaction pathways to various reduction products such as methanol, methanol, carbon monoxide, and formic acid using the CHE model. Each reduction step involves the transfer of a proton–electron (H<sup>+</sup> + e<sup>−</sup>) pair to the adsorbates. A schematic representation of the mechanism is shown in Scheme 1. In the first proton–electron transfer step, the hydrogenation on CO<sub>2</sub> can either form formate (OCHO\*) species or carboxyl (COOH)\* species. The (H<sup>+</sup> + e<sup>−</sup>) transfer can hydrogenate either the C or the O atom of the adsorbates and leads to different reaction intermediates. The formate (OCHO\*) species is an end product and releases formic acid in the second proton–electron transfer step albeit with a huge endergonic energy requirement. As we are interested in the reduction of CO<sub>2</sub> to higher-order reduction products such as methane and methanol, we will focus on the COOH\* pathway. The carboxyl species (COOH\*) can release formic acid (HCOOH) by hydrogenating the C atom or form a CO\* adsorbate by eliminating a water molecule by hydrogenating the O atom. The CO\* can be released from the nanocluster surface as a free CO molecule if it is weakly coordinated or can lead to the formation of CHO\* or COH\* intermediates depending on the hydrogenation site on CO\* in the third (H<sup>+</sup> + e<sup>−</sup>) transfer step. Most metal surfaces weakly adsorb CO which can be easily desorbed from the surface leading to CO as the major product prohibiting further CO<sub>2</sub>RR reduction steps. Further electrochemical (H<sup>+</sup> + e<sup>−</sup>) transfers to CHO\* and COH\* species and the subsequent intermediates lead to various CO<sub>2</sub>RR reduction pathways (Scheme 1)

depending on the hydrogenation sites. To differentiate between these steps, we have listed them below:




CHO\* mediated pathways to methane




COH\* mediated pathways to methane



CHO\* mediated pathways to methanol




COH\* mediated pathways to methanol:



In Table S5 (ESI†), we have shown the adsorption free energies of various adsorbates, and in Fig. 5, we have shown the thermodynamic free energy changes for CHO\* and COH\* mediated electrochemical steps for CO<sub>2</sub>RR on early TMs (Sc–V) nanoclusters. Similar endergonic/exergonic free energy changes for various electrochemical steps on other first-row TM clusters were shown in the ESI† (Fig. S7 and S8). The endergonicity or exergonicity associated with each electrochemical step will decide the thermodynamically favorable reaction pathways and the extent to which a step is preferred over a competing side reaction step which in turn depends on the relative stabilities of the adsorbates. The formation of COOH\* is highly exergonic on Sc–V clusters while the formation of CO\* from COOH\* is mildly exergonic or mildly endergonic on Sc–V clusters. The COH\* formation in the third (H<sup>+</sup> + e<sup>−</sup>) transfer step is a highly disfavored endergonic process whilst the formation of CHO\*



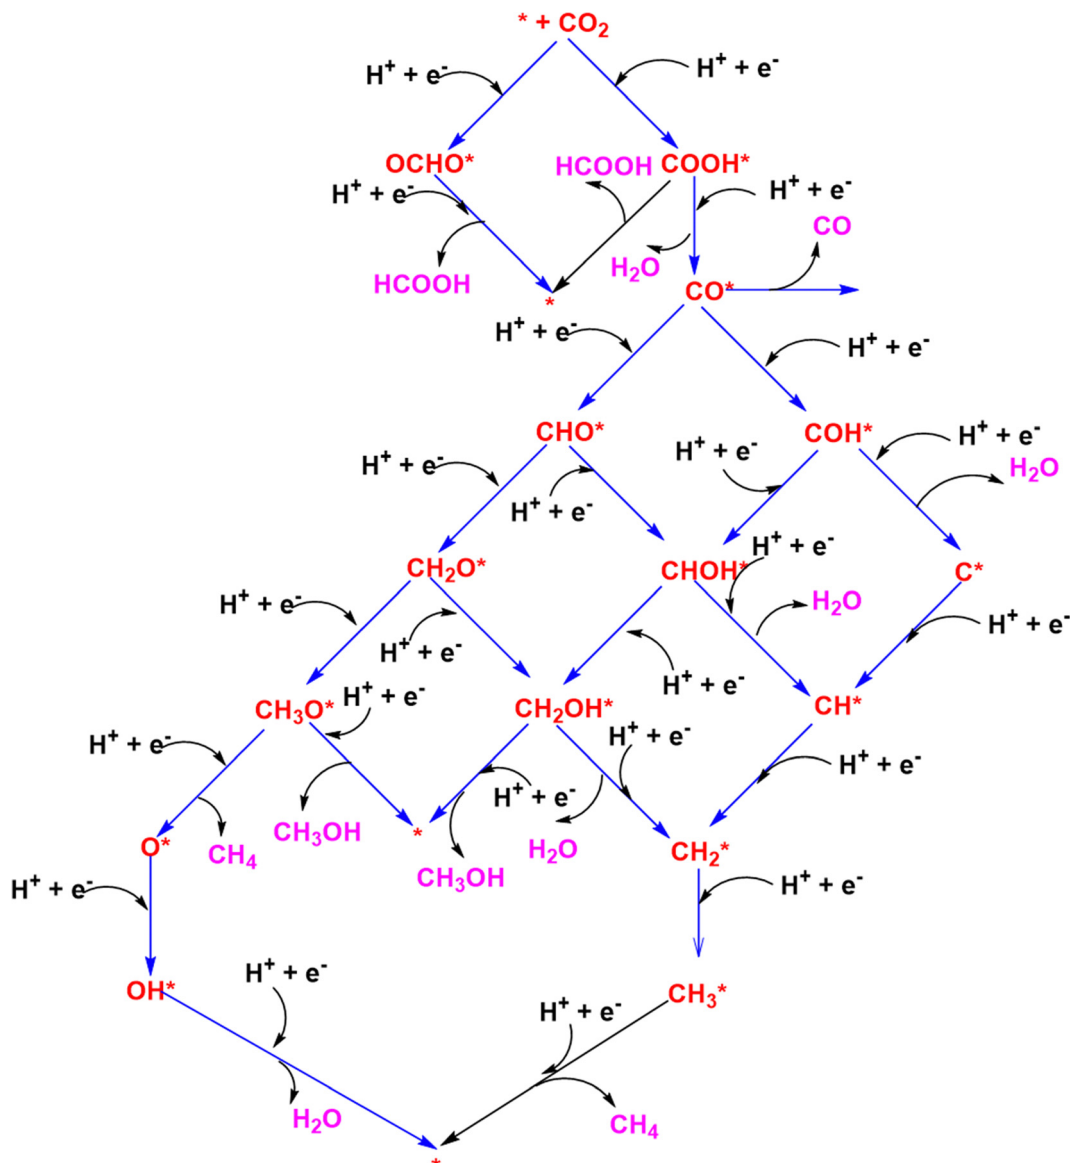

Scheme 1 Various CO<sub>2</sub>RR electrochemical steps via CHO\* and COH\* pathways.

species is a favorable mildly exergonic process. In a similar way, we can identify the thermodynamical preferences for the formation of other adsorbates such as the preference for the formation of CH<sub>2</sub>O\* over CHOH from CHO\* adsorbates. However, a general trend for the formation of different adsorbates cannot be easily elucidated from these endergonic/exergonic free energy change plots.

To facilitate further in-depth insights into CO<sub>2</sub>RR on various first-row TM nanoclusters, we have made detailed analyzes of the various reaction pathways (Path I to Path XI) including both CHO\* and COH\* mediated pathways to methane and methanol formation by examining the thermodynamic free energy changes associated with each electrochemical step. From these thermodynamic free energy changes, we have determined the PDS as well as the free energy changes of the PDS for all these different CHO\* and COH\* reaction pathways on all

nanoclusters which are summarized in Table S6 (ESI†). From all these various CHO\* and COH\* mediated pathways, we have identified for all nanoclusters, the most preferred CO<sub>2</sub>RR reaction route that requires the lowest free energy change of the PDS and are given in Table 2. The preferred CHO\* and COH\* mediated pathways for CO<sub>2</sub>RR on Sc to Cu TM nanoclusters and the free energy change of the PDS are presented in Fig. 6.

From thermodynamic free energy changes associated with CO\* → CHO\* and CO\* → COH\* steps, we have found in general that the formation of COH\* adsorbate from CO\* in the third ( $\text{H}^+ + \text{e}^-$ ) pair transfer step is greatly disfavored on first-row TM clusters compared to the formation of the CHO\* adsorbates. Similarly, we have identified general preferences that CHO\* on the fourth electrochemical step prefers CH<sub>2</sub>O\* adsorbate (CHO\* → CH<sub>2</sub>O\* vs. CHOH); CH<sub>2</sub>O\* on the fifth



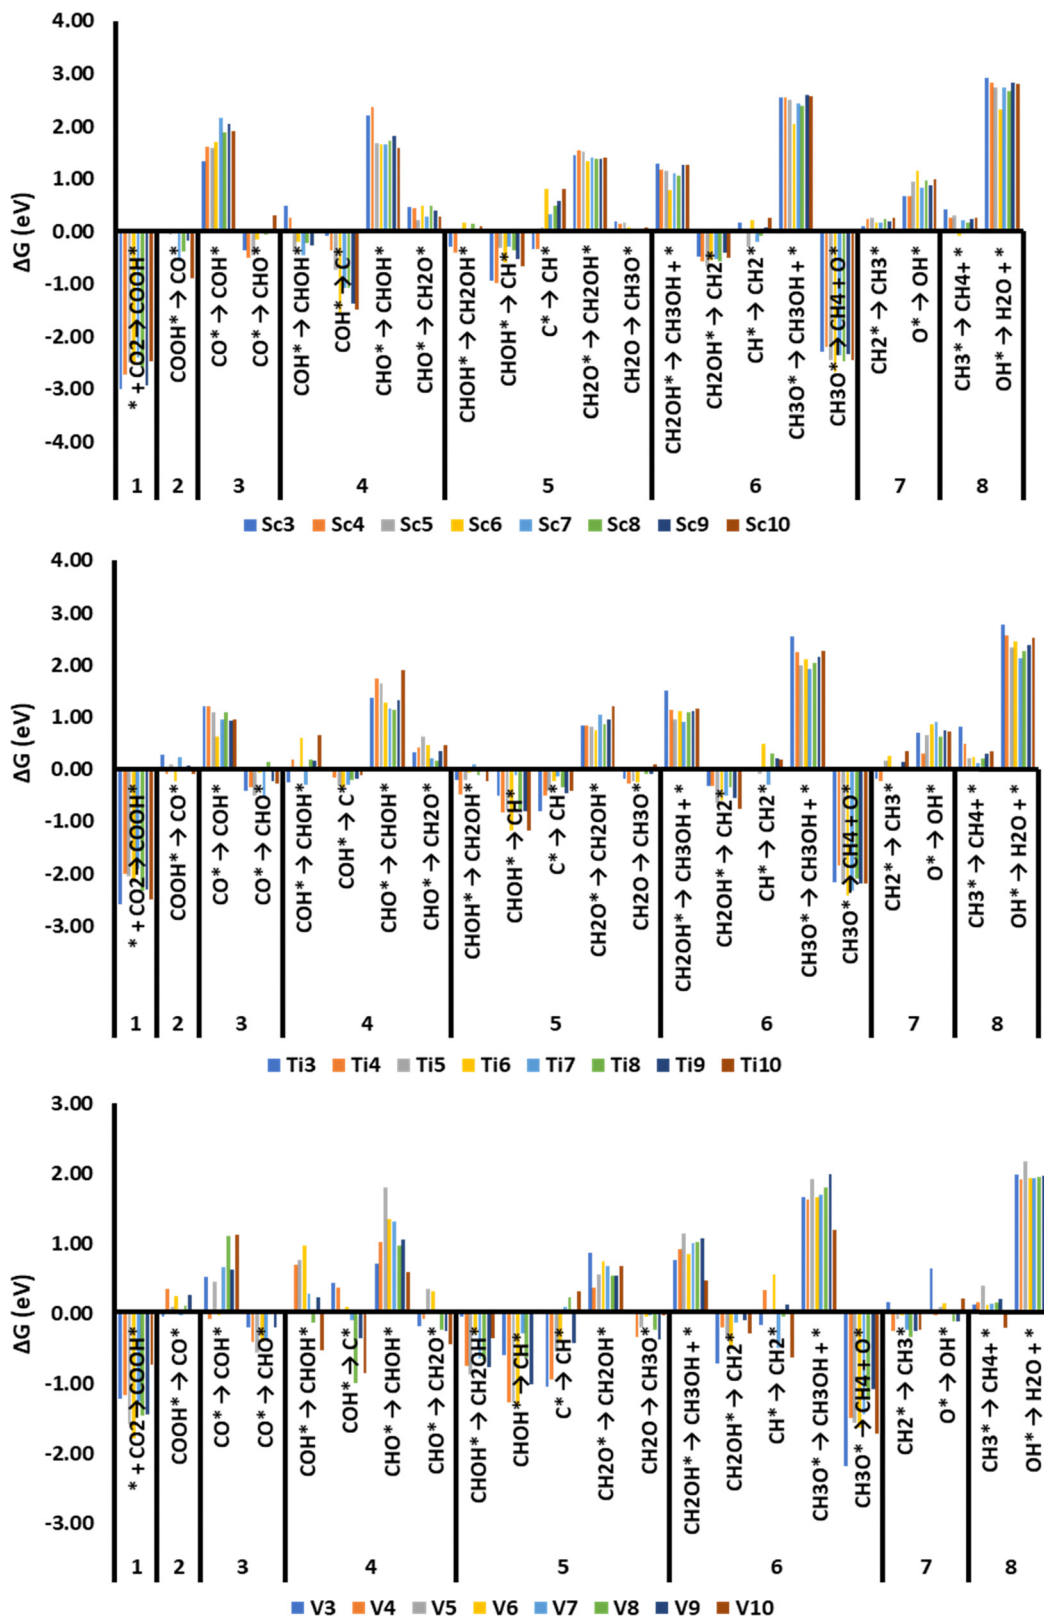


Fig. 5 Free energy changes (eV) for various electrochemical steps in the  $\text{CO}_2\text{RR}$  process on Sc, Ti, and V clusters. Step numbers 1–8 show the total number of ( $\text{H}^+ + \text{e}^-$ ) pairs transferred relative to  $\text{CO}_2$ .



Table 2 Lowest energy CO<sub>2</sub>RR reaction pathways and the potential-determining step (PDS) on each nanocluster

Lowest energy pathways <sup>a</sup>	Clusters	PDS
CHO* Path I	Co <sub>6</sub> Cu <sub>4</sub> , Cu <sub>6</sub> , Cu <sub>8</sub> , Cu <sub>10</sub>	CO* → CHO* CO* → CHO*
CHO* Path II	Sc <sub>4</sub> -Sc <sub>10</sub> ; Ti <sub>3</sub> -Ti <sub>5</sub> , Ti <sub>8</sub> ; V <sub>4</sub> , V <sub>8</sub> , V <sub>9</sub> , Cr <sub>5</sub> , Cr <sub>6</sub> , Cr <sub>9</sub> Cr <sub>3</sub> , Cr <sub>7</sub> , Cr <sub>10</sub> Cr <sub>4</sub> , Cr <sub>8</sub> Mn <sub>5</sub> , Mn <sub>7</sub> , Mn <sub>10</sub> Mn <sub>8</sub> , Fe <sub>3</sub> , Fe <sub>7</sub> -Fe <sub>10</sub> , Co <sub>3</sub> -Co <sub>5</sub> , Co <sub>7</sub> -Co <sub>10</sub> , Ni <sub>3</sub> -Ni <sub>5</sub> , Ni <sub>7</sub> -Ni <sub>9</sub> , Cu <sub>3</sub> , Cu <sub>5</sub> , Cu <sub>7</sub>	CH <sub>2</sub> O* → CH <sub>2</sub> OH* COOH* → CO* CH <sub>2</sub> OH* → CH <sub>2</sub> * CH <sub>3</sub> * → CH <sub>4</sub> + * CO* → CHO*
CHO* Path III	V <sub>10</sub> , Mn <sub>4</sub> , Mn <sub>9</sub>	CHO* → CHOH*
CHO* Path IV	Mn <sub>3</sub> , Mn <sub>6</sub> , Cu <sub>9</sub>	CHO* → CHOH*
COH* Path V	Sc <sub>3</sub> , Ti <sub>6</sub> , Ti <sub>9</sub> , Ti <sub>10</sub> , V <sub>5</sub> , V <sub>7</sub> , Fe <sub>5</sub> , Ni <sub>6</sub> , Ni <sub>10</sub> V <sub>6</sub>	CO* → COH* CH* → CH <sub>2</sub> *
COH* Path VI	Ti <sub>7</sub> , V <sub>3</sub> , Fe <sub>4</sub>	CO* → COH*
COH* Path VII	Fe <sub>6</sub>	CO* → COH*

<sup>a</sup> CHO\* Path I: \* + CO<sub>2</sub> → COOH\* → CO\* → CHO\* → CH<sub>2</sub>O\* → CH<sub>3</sub>O\* → O\* + CH<sub>4</sub> → OH\* → \*; CHO\* Path II: \* + CO<sub>2</sub> → COOH\* → CO\* → CHO\* → CH<sub>2</sub>O\* → CH<sub>2</sub>OH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*; CHO Path III: \* + CO<sub>2</sub> → COOH\* → CO\* → CHO\* → CHOH\* → CH<sub>2</sub>OH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*; CHO Path IV: \* + CO<sub>2</sub> → COOH\* → CO\* → CHO\* → CHOH\* → CH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*; COH\* Path V: \* + CO<sub>2</sub> → COOH\* → CO\* → COH\* → C\* → CH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*; COH\* Path VI: \* + CO<sub>2</sub> → COOH\* → CO\* → COH\* → CHOH\* → CH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*; COH\* Path VII: \* + CO<sub>2</sub> → COOH\* → CO\* → COH\* → CHOH\* → CH<sub>2</sub>OH\* → CH<sub>2</sub>\* → CH<sub>3</sub>\* → CH<sub>4</sub> + \*.

electrochemical step prefers CH<sub>3</sub>O\* adsorbate (CH<sub>2</sub>O\* → CH<sub>3</sub>O\* vs CH<sub>2</sub>OH), and CH<sub>3</sub>O\* on the six electrochemical steps prefers the formation of CH<sub>4</sub> (CH<sub>3</sub>O\* → O\* + CH<sub>4</sub> vs CH<sub>3</sub>OH). This gives the impression that the CO<sub>2</sub>RR prefers to proceed through CHO\* Path I (CHO\* → CH<sub>2</sub>O\* → CH<sub>3</sub>O\* → CH<sub>4</sub> + O\* → OH\* → \*) as in the case of CHO\* Path I reported for CO<sub>2</sub>RR on Cu surface by Nørskov and co-workers.<sup>50</sup> However, we have noticed that the removal of the OH\* species (OH\* → \* + H<sub>2</sub>O) in the eight (H<sup>+</sup> + e<sup>-</sup>) electrochemical step (Fig. 7) is an uphill process that requires significantly larger endergonic free energy changes and is the PDS for the formation of CH<sub>4</sub> *via* CHO\* Path I on all first-row TM nanoclusters except on Co<sub>6</sub> and Cu clusters with even-numbered cluster configurations (Cu<sub>4</sub>, Cu<sub>6</sub>, Cu<sub>8</sub>, and Cu<sub>10</sub>) for which CO\* → CHO\* is the PDS for CHO\* Path I. Due to the larger endergonicity associated with the OH\* removal step, CHO\* Path I is not a preferred reaction route except on these five nanoclusters (Co<sub>6</sub>, Cu<sub>4</sub>, Cu<sub>6</sub>, Cu<sub>8</sub>, and Cu<sub>10</sub>).

Further detailed investigations on various reaction pathways reveal that alternative pathways *via* CHO\* Paths II to IV and COH\* Paths V to VII can lead to CH<sub>4</sub> without passing through the highly endergonic OH\* removal step. We have found that CHO\* Path II is the lowest energy pathway for CO<sub>2</sub>RR on a majority of the clusters (Table 2). Clusters Co<sub>6</sub>, Cu<sub>4</sub>, Cu<sub>6</sub>, Cu<sub>8</sub>, and Cu<sub>10</sub> prefer CHO\* Path I; V<sub>10</sub>, Mn<sub>4</sub>, and Mn<sub>9</sub> prefer CHO\* Path III; Mn<sub>3</sub>, Mn<sub>6</sub>, and Cu<sub>9</sub> prefer CHO\* Path IV; Sc<sub>3</sub>, Ti<sub>6</sub>, Ti<sub>9</sub>, Ti<sub>10</sub>, V<sub>5</sub>, V<sub>6</sub>, V<sub>7</sub>, Fe<sub>5</sub>, Ni<sub>6</sub>, and Ni<sub>10</sub> prefers COH\* Path V; Ti<sub>7</sub>, V<sub>3</sub> and Fe<sub>4</sub> COH\* Path VI; and Fe<sub>6</sub> prefers COH\* Path VII (Table 2). With a few exceptions, we have found in general that the electrochemical step CO\* → CHO\* is the PDS on first-row TM nanoclusters from Fe to Cu for the CHO\* Path II. For early TM nanoclusters Sc, Ti, and V, we have found that the electrochemical step for the formation of CH<sub>2</sub>OH\* adsorbate from the CH<sub>2</sub>O\* (CH<sub>2</sub>O\* → CH<sub>2</sub>OH\*) is the PDS for CHO\* Path II. For the clusters that exhibit CHO\* Path I as the preferred reaction route, CO\* → CHO\* is the PDS as in the case of the reported

work of Nørskov, and co-workers<sup>50</sup> on Cu metal surface. For clusters that prefer CHO\* Paths III and IV, the electrochemical step CHO\* → CHOH\* is the PDS. With a single exception on V<sub>6</sub>, CO\* → COH\* is the PDS on all the clusters that prefer COH\* mediated pathways. The limiting potential for a reaction pathway is determined by the electrochemical step with the largest endergonic free energy change in that pathway which is directly related to the relative stabilities of the adsorbates for the PDS step. It should be noted that some nanoclusters undergo geometrical rearrangement on binding with adsorbates and the energetic cost associated with these structural arrangements is a major factor that decides the thermodynamic stabilities of the adsorbates. Most importantly, we have found that all the preferred lowest energy pathway for all first-row TM nanoclusters leads exclusively to the formation of CH<sub>4</sub> and none of them prefers the exclusive formation of methanol. The methanol *vs.* methane selectivity depends on two electrochemical steps: the preference for the formation of CH<sub>3</sub>OH or CH<sub>2</sub>\* from CH<sub>2</sub>OH\* adsorbate and the preference for the formation of CH<sub>3</sub>OH or CH<sub>4</sub> + O\* from CH<sub>3</sub>O\* adsorbate. We have found a greater preference for CH<sub>2</sub>OH\* → CH<sub>2</sub>\* and CH<sub>3</sub>O\* → CH<sub>4</sub> + O\* paths on all nanoclusters which eventually leads to the formation of CH<sub>4</sub>. Moreover, it is evident from Table S6 (ESI<sup>†</sup>) that although COH\* mediated pathways are preferred on some of the nanocluster surfaces, there is strong competition from the CHO\* mediated pathways as free energy changes of the PDS for CHO\* pathways do not show any significant differences from the free energy changes of the PDS for COH\* mediated pathways on these nanoclusters. A further detailed discussion of the CO<sub>2</sub>RR on all the first-row TMs is given below:

(i) **CO<sub>2</sub>RR on early first-row TM nanoclusters (Sc, Ti, and V).** Sc nanoclusters exhibit a much greater stabilization of adsorbates than other transition metals in the first row. Both Sc and Ti clusters show a preference for the CHO\* mediated Path II of CO<sub>2</sub>RR, with the PDS being the formation of CH<sub>2</sub>OH\*



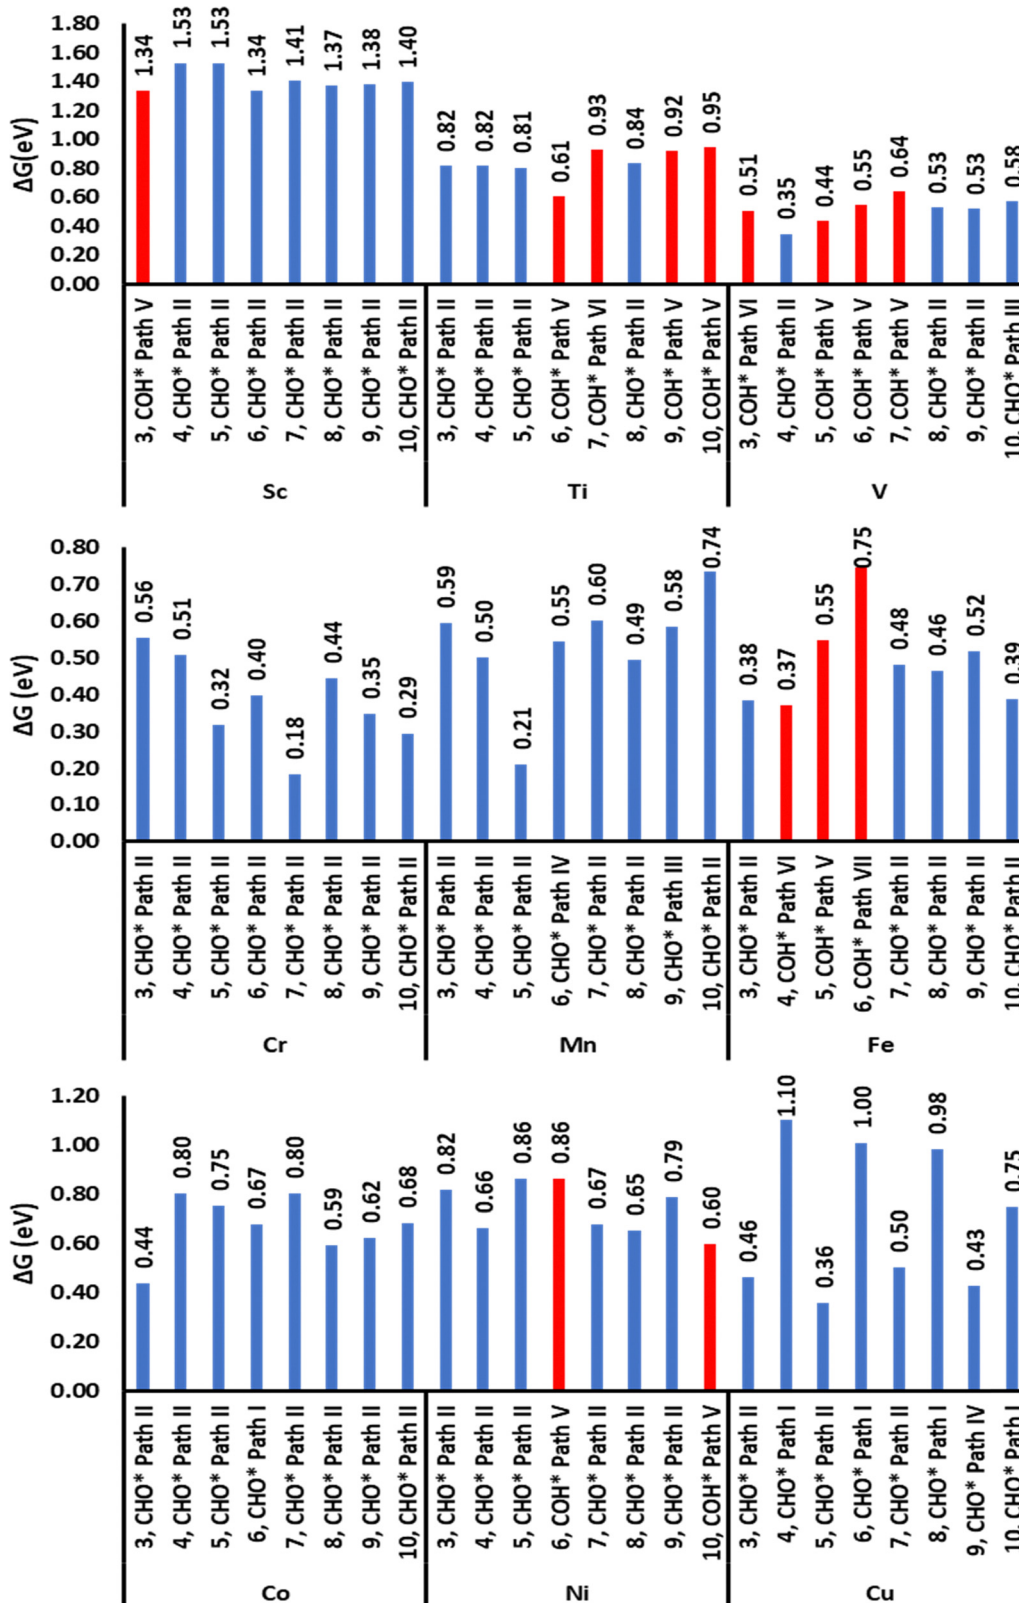


Fig. 6 The lowest energy pathways for CO<sub>2</sub>RR on first-row TM nanoclusters (Sc–Cu). The free energy change of the PDS for CO<sub>2</sub>RR were shown in each bar. The blue and red bars represent the CHO\* and COH\* mediated pathways, respectively. The limiting potential values corresponds to the negative of the free energy change of the PDS in Volts (V). See Table 2 for the PDS for various nanoclusters.



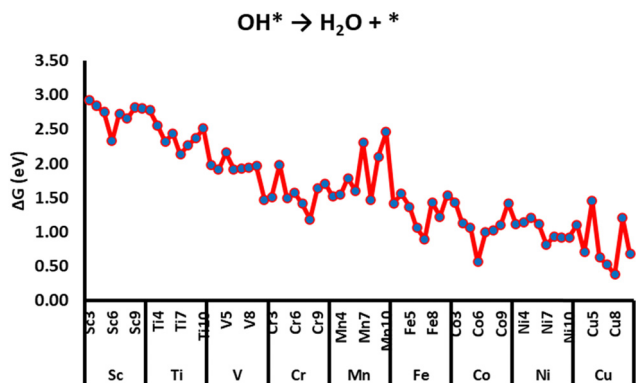


Fig. 7 Free energy change ( $\Delta G$ , eV) for the  $\text{OH}^*$  removal step ( $\text{OH}^* \rightarrow * + \text{H}_2\text{O}$ ) in the  $\text{CHO}^*$  mediated Path I.

from  $\text{CH}_2\text{O}^*$ . The  $\text{COH}^*$  mediated Path V is slightly preferred over Path II on  $\text{Sc}_3$ , with the PDS being the conversion of  $\text{CO}^*$  to  $\text{COH}^*$ . The limiting potentials on Sc clusters falls between  $-1.34$  V to  $-1.53$  V and  $-0.61$  V to  $-0.95$  V on Ti clusters, with  $\text{Ti}_6$  having the lowest potential. The limiting potential values on vanadium clusters significantly reduced to  $-0.35$  V to  $-0.64$  V compared to the limiting potentials on Sc and Ti clusters.  $\text{V}_4$  exhibits the lowest limiting potential on vanadium clusters with a limiting potential of  $-0.35$  V.  $\text{CHO}^*$  mediated pathways were favored on  $\text{V}_4$  and  $\text{V}_8$ – $\text{V}_{10}$  clusters and  $\text{COH}^*$  mediated pathways were favored on  $\text{V}_3$  and  $\text{V}_5$ – $\text{V}_7$  clusters. The PDS of all the different pathways are listed in Table 2.

Although  $\text{CO}_2\text{RR}$  on some of the Ti and V clusters as well on  $\text{Sc}_3$  prefer to proceed through  $\text{COH}^*$  intermediate, the limiting potentials for the  $\text{CHO}^*$  and  $\text{COH}^*$  pathways differ by only 0.10 eV on most of these clusters, and hence, both these pathways are possible for  $\text{CO}_2\text{RR}$ . The relative preference for the various reaction routes depends on the stability of the adsorbate-bound complexes which in turn depends on the geometry rearrangement of the cluster moieties from their global minimum configurations on binding with adsorbate species. For example, the cluster moiety  $\text{V}_8$  in the  $\text{COH}^*$ – $\text{V}_8$  shows significant changes from its global minimum configuration and the energetic cost associated with the reorganization of the cluster moiety on adsorbate binding leads to the lower thermodynamic stability of the  $\text{COH}^*$  adsorbates which in turn results in a highly disfavored endergonic uphill process for the formation of  $\text{COH}^*$  species from  $\text{CO}^*$ .

(ii)  **$\text{CO}_2\text{RR}$  on mid first-row TM nanoclusters (Cr, Mn, and Fe).** The  $\text{CO}_2\text{RR}$  on all Cr clusters prefers to proceed through the  $\text{CHO}^*$  Path II with relatively smaller limiting potentials in the range of  $-0.18$  V to  $-0.56$  V with  $\text{Cr}_7$  having the lowest limiting potential followed by  $\text{Cr}_{10}$  ( $-0.29$  V). Similar to Cr clusters, Mn clusters prefer  $\text{CHO}^*$  mediated reaction pathways for  $\text{CO}_2$  electroreduction with  $\text{Mn}_5$  having the lowest limiting potential value of  $-0.21$  V. The competing  $\text{COH}^*$  mediated pathways were greatly disfavored on Cr and Mn clusters owing to the larger endergonicity associated with the PDS  $\text{CO}^* \rightarrow \text{COH}^*$ . There is no specific preference for a particular  $\text{CHO}^*$  path and the PDS varies depending on the stability of the

different intermediates on different Cr and Mn clusters and are listed in Table 2. Iron clusters exhibit a general preference for  $\text{CHO}^*$  Path II with the electrochemical step  $\text{CO}^* \rightarrow \text{CHO}^*$  as the PDS.  $\text{Fe}_4$ ,  $\text{Fe}_5$ , and  $\text{Fe}_6$  clusters prefer both  $\text{CHO}^*$  and  $\text{COH}^*$  mediated pathways due to similar endergonic free energy changes associated with the PDS  $\text{CO}^* \rightarrow \text{CHO}^*$  and  $\text{CO}^* \rightarrow \text{COH}^*$ . The limiting potentials fall in the range of  $-0.37$  V to  $-0.55$  V on all Fe clusters except on  $\text{Fe}_6$  which shows a limiting potential value of  $-0.75$  V.

(iii)  **$\text{CO}_2\text{RR}$  on late first-row TM nanoclusters (Co, Ni, and Cu).** The  $\text{CHO}^*$  Path II is the preferred  $\text{CO}_2\text{RR}$  on cobalt clusters except on  $\text{Co}_6$  with limiting potential in the range of  $-0.44$  V to  $-0.80$  V with  $\text{CO}^* \rightarrow \text{CHO}^*$  as the PDS step.  $\text{Co}_6$  prefers  $\text{CHO}^*$  Path I due to the lower endergonicity associated with the removal of  $\text{OH}^*$  adsorbate from the cluster surface. The  $\text{CO}_2\text{RR}$  on cobalt clusters greatly disfavored the  $\text{COH}^*$  mediated pathway owing to the larger endergonicity associated with the electrochemical step  $\text{CO}^* \rightarrow \text{COH}^*$  which is in the range of  $\sim 1$  eV. Nickel clusters in general exhibit a greater preference for  $\text{CHO}^*$  Path II with  $\text{CO}^* \rightarrow \text{CHO}^*$  as the PDS. The limiting potential values ranges from  $-0.60$  V to  $-0.86$  V. However, on most of the Ni clusters, the stabilities of the  $\text{CHO}^*$  and  $\text{COH}^*$  adsorbates do not show any significant difference, and hence, both these reaction routes are possible on Ni clusters.

Copper clusters with even-number composition ( $\text{Cu}_4$ ,  $\text{Cu}_6$ ,  $\text{Cu}_8$ , and  $\text{Cu}_{10}$ ) prefer the  $\text{CO}_2\text{RR}$  via  $\text{CHO}^*$  Path I with significantly larger limiting potential ( $-0.75$  V to  $-1.10$  V); the lowest limiting potential is exhibited by  $\text{Cu}_{10}$ . On the other hand, clusters with odd-number compositions  $\text{Cu}_3$ ,  $\text{Cu}_5$ , and  $\text{Cu}_7$  prefer the reaction path  $\text{CHO}^*$  Path II, and  $\text{Cu}_9$  prefers the reaction  $\text{CHO}^*$  Path IV with relatively smaller limiting potentials ( $-0.36$  V to  $-0.50$  V).  $\text{COH}^*$  pathways are greatly disfavored on all Cu clusters due to the larger endergonic free energy change ( $> 1.1$  eV) associated with the PDS  $\text{CO}^* \rightarrow \text{COH}^*$ . The  $\text{CHO}^*$  Path I is not favored on clusters with odd-number compositions due to the larger endergonicity ( $> 1$  eV) associated with the  $\text{OH}^*$  removal step. It should be noted that  $\text{CHO}^*$  Path I is the lower energy route proposed by Nørskov and co-workers for the formation of  $\text{CH}_4$  on the Cu surface with a limiting potential of  $-0.74$  V for the key step  $\text{CO}^* \rightarrow \text{CHO}^*$ .<sup>50</sup> In a previous work, we have reported detailed studies on the alternating nature of endergonicity and exergonicity associated with various electrochemical steps on Cu clusters with odd- and even-number compositions ( $\text{Cu}_3$ – $\text{Cu}_6$ ) as well as the relationship between the free energy changes with the spin state and HOMO–LUMO gap of the Cu adsorbates using  $\omega\text{B97XD}$  density functional and a localized atomic orbital basis set.<sup>57</sup> Although the present work shows some discrepancies in the free energy values which is acceptable due to the usage of different DFT functional and basis set, in general, the overall trend and conclusions remain intact. The  $\text{Cu}_{10}$  shows a limiting potential of  $-0.75$  V, a value that is very close to the limiting potential on the Cu surface by Nørskov and co-workers.<sup>50</sup> This implies that clusters with a greater number of atoms with even number composition resemble more close to the Cu surface.



In short, we have seen stronger binding affinity for all the adsorbates on early TM nanoclusters and a general trend of reduced binding affinity across the first-row TM nanoclusters from Sc to Cu with the highest adsorption free energies on Sc and lowest on Cu. Among the differently sized nanoclusters of the same clusters, the adsorption free energies do not exhibit significant deviation as most of the adsorption free energies fall within a range of 0.3–0.5 eV of the average adsorption energies for that particular metal nanocluster. Still, we have noticed that clusters with smaller numbers of atoms, especially three or four atoms exhibit somewhat larger deviations in adsorption free energies compared to cluster compositions with larger numbers of metal atoms. It should be noted that we should also need to consider the energetic cost associated with the rearrangement of cluster atoms from their global minimum configurations on binding with adsorbates while discussing the endergonicity/exergonicity associated with each electrochemical step. All metal nanoclusters except Cu show a range of spin states for different adsorbates. However, we could not find a direct relationship between the adsorption free energies and hence, endergonicity/exergonicity associated with each electrochemical step with the spin-states of the various adsorbates. On the contrary, adsorbates on Cu nanoclusters exhibit alternating exergonicity and endergonicity based on the spin-state of the adsorbates. Similarly, we could not find a direct link between the endergonicity/exergonicity associated with each electrochemical step and the HOMO–LUMO gap for adsorbates on all nanoclusters except on Cu. On Cu clusters, the proton-electron pair transfers to singlet adsorbates to form doublet adsorbates are considerably higher endergonic step due to the

larger HOMO–LUMO gap on singlet adsorbates and *vice versa*. We have also established that although CO<sub>2</sub>RR can proceed through various CHO\* and COH\* mediated pathways, all these pathways lead to the formation of methane on all first-row TM nanoclusters.

### Competition between CO, HCOOH, and H<sub>2</sub> formations

Based on the free energy change of the PDS values for CO<sub>2</sub>RR, we have identified several nanoclusters that can reduce CO<sub>2</sub> to CH<sub>4</sub> with relatively lower limiting potential values (*i.e.*, the negative potential that should be applied to make all the electrochemical steps exergonic which corresponds to the free energy change of the PDS). Cr<sub>7</sub> exhibits the lowest free energy change of the PDS with a value of 0.18 eV (*i.e.*, the limiting potential value is −0.18 V) followed closely by the Mn<sub>7</sub> cluster with a limiting potential value of −0.21 V. Nanoclusters Cr<sub>10</sub>, Cr<sub>5</sub>, Cr<sub>9</sub>, V<sub>4</sub>, Cu<sub>5</sub>, Fe<sub>4</sub>, Fe<sub>3</sub>, and Fe<sub>10</sub> shows relatively lower limiting potentials in the range of −0.29 V to −0.39 V, and clusters Cr<sub>6</sub>, Cu<sub>9</sub>, Co<sub>3</sub>, V<sub>5</sub>, Cr<sub>8</sub>, Cu<sub>3</sub>, Fe<sub>8</sub>, Fe<sub>7</sub>, Mn<sub>8</sub>, Cu<sub>7</sub>, and Mn<sub>4</sub> exhibits limiting potentials in the range of −0.40 V to −0.50 V. We have found in general that nanoclusters of mid-transition metals *i.e.*, Cr, Mn, and Fe exhibit relatively lower limiting potential values for CO<sub>2</sub>RR to methane.

One of the major hindrances in CO<sub>2</sub> electroreduction to higher-order reduction products such as methane or methanol is the formation of two-electron reduction products such as CO, HCOOH, and H<sub>2</sub>. The COOH\* species can either release free formic acid (HCOOH) by hydrogenating the C atom of the COOH\* species or CO\* by eliminating a water molecule by hydrogenating the O atom of the COOH\* species in the second

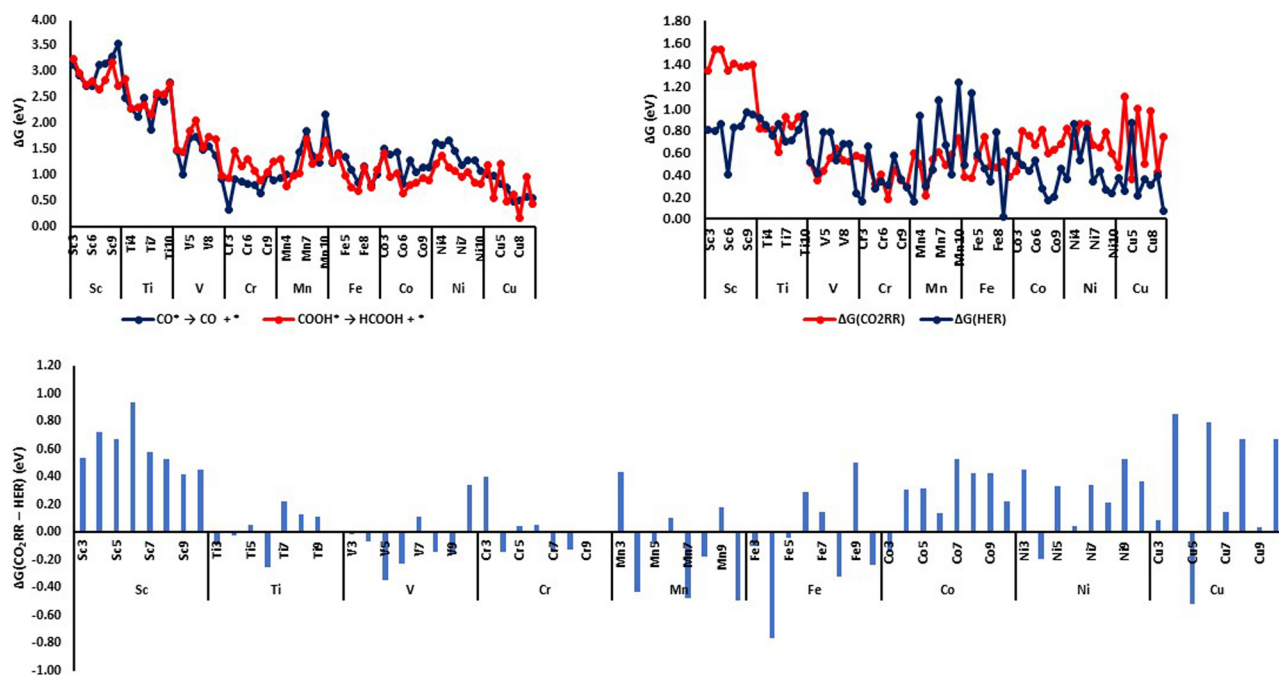


Fig. 8 (a) Free energy changes ( $\Delta G$ , eV) for CO desorption and HCOOH formation in the second ( $\text{H}^+ + \text{e}^-$ ) transfer step; (b) free energy changes ( $\Delta G$ , eV) of the PDS for CO<sub>2</sub>RR and HER and (c) relative free energy changes of PDS for CO<sub>2</sub>RR and HER ( $\Delta G(\text{CO}_2\text{RR}-\text{HER})$ , eV) on various first-row TM nanoclusters.





( $H^+ + e^-$ ) transfer step. One of the major drawbacks of  $CO_2RR$  on metal surfaces is the weak adsorption of CO and its subsequent escape from the surface through an easier desorption process. Due to the availability of the unsaturated coordinate sites, CO is chemisorbed on nanoclusters and hence the desorption requires the breaking of much stronger metal–CO bonds resulting in significantly larger desorption energies as evident from Fig. 8(a). Among all the metal clusters,  $Cr_3$  (0.32 eV) shows the smallest CO desorption energy. Cu clusters

$Cu_7$ – $Cu_{10}$  also show relatively smaller CO desorption energies around 0.5–0.6 eV. Since CO desorption is a thermodynamically disfavored process on all the metal clusters, the  $CO^*$  adsorbates are readily available for further reduction steps and may lead to the formation of higher-order reduction products such as methane.

Except on Cu clusters with even-number atom composition ( $Cu_4$ ,  $Cu_6$ ,  $Cu_8$ , and  $Cu_{10}$ ), the release of formic acid in the second ( $H^+ + e^-$ ) transfer step on all other nanoclusters requires

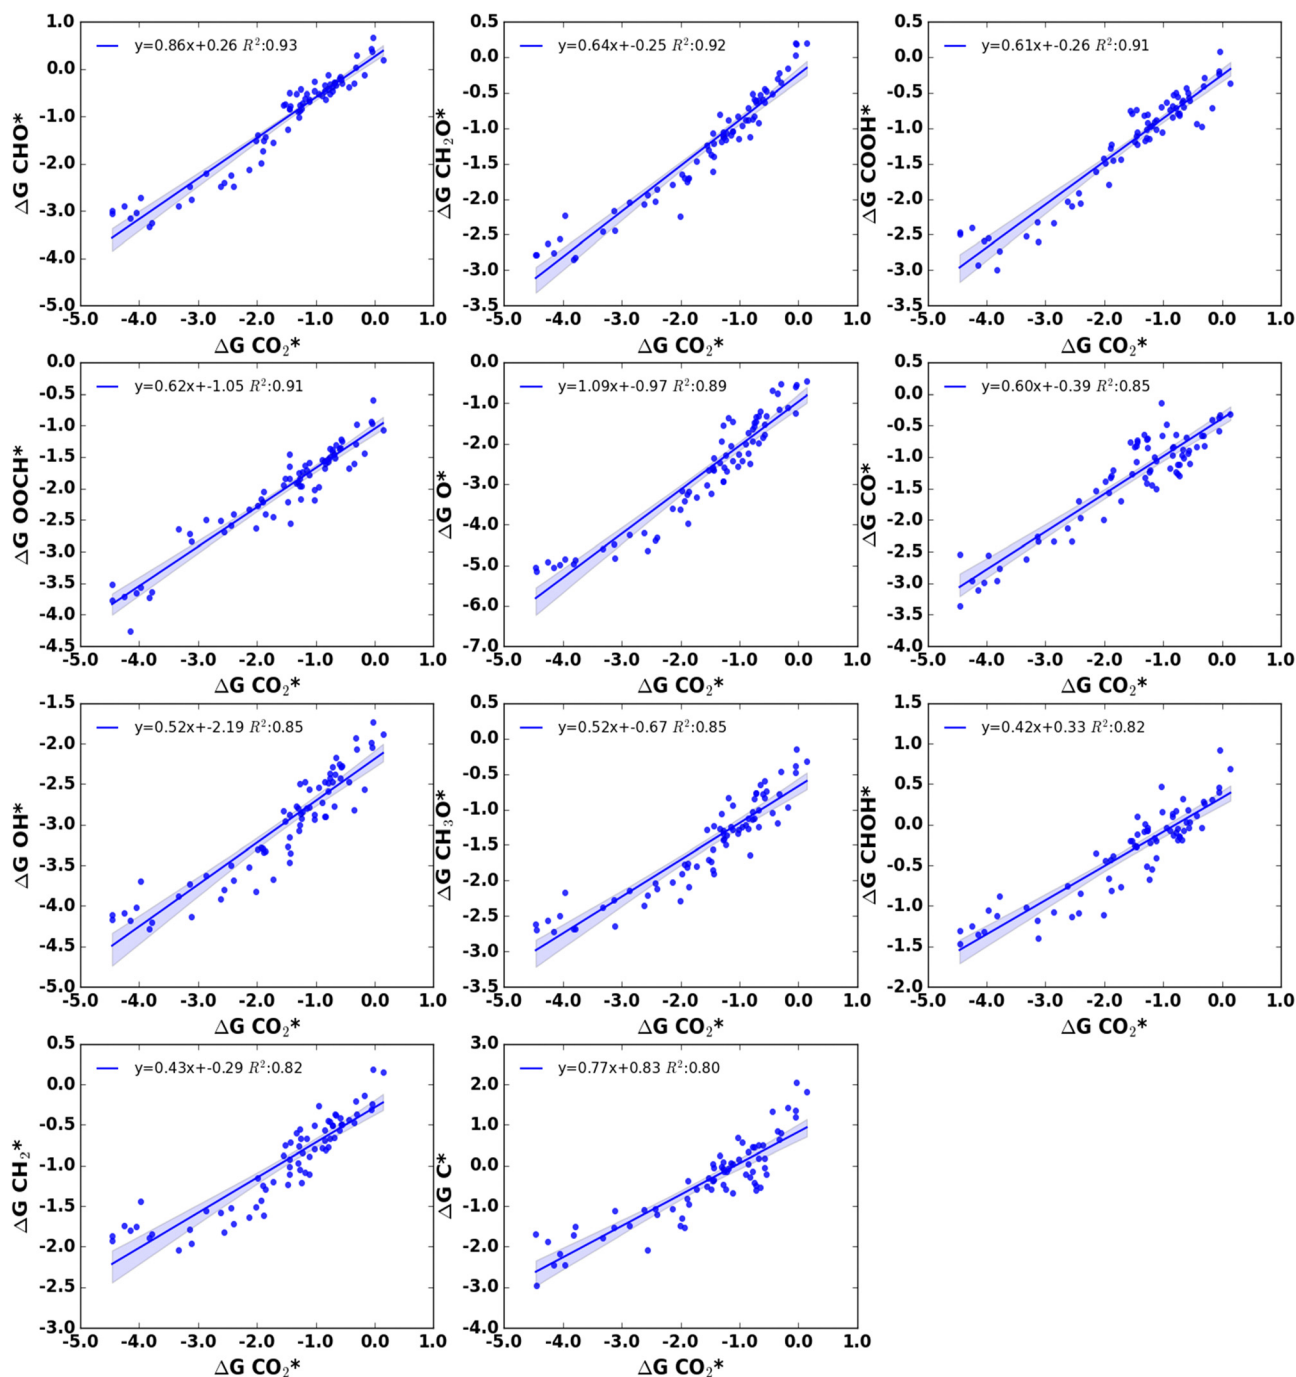


Fig. 9 Liner scaling relationship between adsorption free energies of  $CO_2^*$  and various adsorbates with the coefficient of determination ( $R^2$ ) value  $\geq 0.80$ .



significantly higher endergonic free energy changes ( $>0.8$  eV) (Fig. 8(a)). This implies that COOH\* species cannot be easily desorbed from the nanocluster surface as free formic acid and hence, COOH\* is available on the nanocluster surface for further reduction steps. Of the Cu clusters with even-number atom compositions, Cu<sub>8</sub> shows the lowest endergonic free energy change (0.17 eV) for formic acid release while Cu<sub>4</sub>, Cu<sub>6</sub>, and Cu<sub>10</sub> show a relatively larger endergonic free change in the range of 0.44 eV to 0.55 eV. In short, we can see that the release of formic acid from the nanocluster surfaces is not an easy step except on Cu<sub>8</sub> and the COOH\* species is available for further reduction steps.

The competing hydrogen evolution reaction (HER) is another major challenge that hinders the efficacy of the CO<sub>2</sub> electroreduction catalysts. An efficient catalyst should be able to suppress the competing HER side reaction. The free energy change of the PDS for HER reaction on various nanoclusters were shown in Fig. 8(b) along with the free energy change of the PDS for CO<sub>2</sub>RR. To get a clear idea of the relative preference for CO<sub>2</sub>RR *versus* HER, we have plotted the difference in the free energy changes of the PDS for CO<sub>2</sub>RR and HER in Fig. 8(c). An endergonic (positive) free energy difference means HER happens before CO<sub>2</sub>RR and an exergonic (negative) free energy

difference means CO<sub>2</sub>RR happens before HER. It can be seen that there are only a few nanoclusters that favor CO<sub>2</sub>RR over HER. From the PDS difference plot, it can be seen that HER is greatly favored on Sc clusters as the limiting potential for CO<sub>2</sub>RR is significantly larger compared to HER and at the applied limiting potential for CO<sub>2</sub>RR, the HER triggers first. On most of the nanocluster surfaces, the hydrogen absorption ( $* + (\text{H}^+ + \text{e}^-) \rightarrow \text{H}^*$ ) is weak and the adsorbed hydrogen can be easily released leading to higher HER evolution at much lower limiting potentials. Still, we have identified a number of nanoclusters such as Ti<sub>6</sub>, V<sub>5</sub>, V<sub>6</sub>, Mn<sub>4</sub>, Mn<sub>7</sub>, Mn<sub>10</sub>, Fe<sub>4</sub>, Fe<sub>8</sub>, Fe<sub>10</sub>, Ni<sub>4</sub>, and Cu<sub>5</sub> as possible electrocatalysts which show a preference for CO<sub>2</sub>RR over HER by 0.2 eV or more.

### Linear scaling relationships for CO<sub>2</sub>RR on first-row TM nanoclusters

Linear scaling relationships which relate the binding energies of chemically related adsorbates across different catalytic surfaces have been successfully applied to understand the reactivity trends across a vast material space. We have investigated whether there exists a linear scaling relationship using our data on adsorption free energies on Sc to Cu first-row TM nanoclusters. In Fig. 9, we have shown the linear free energy relation between

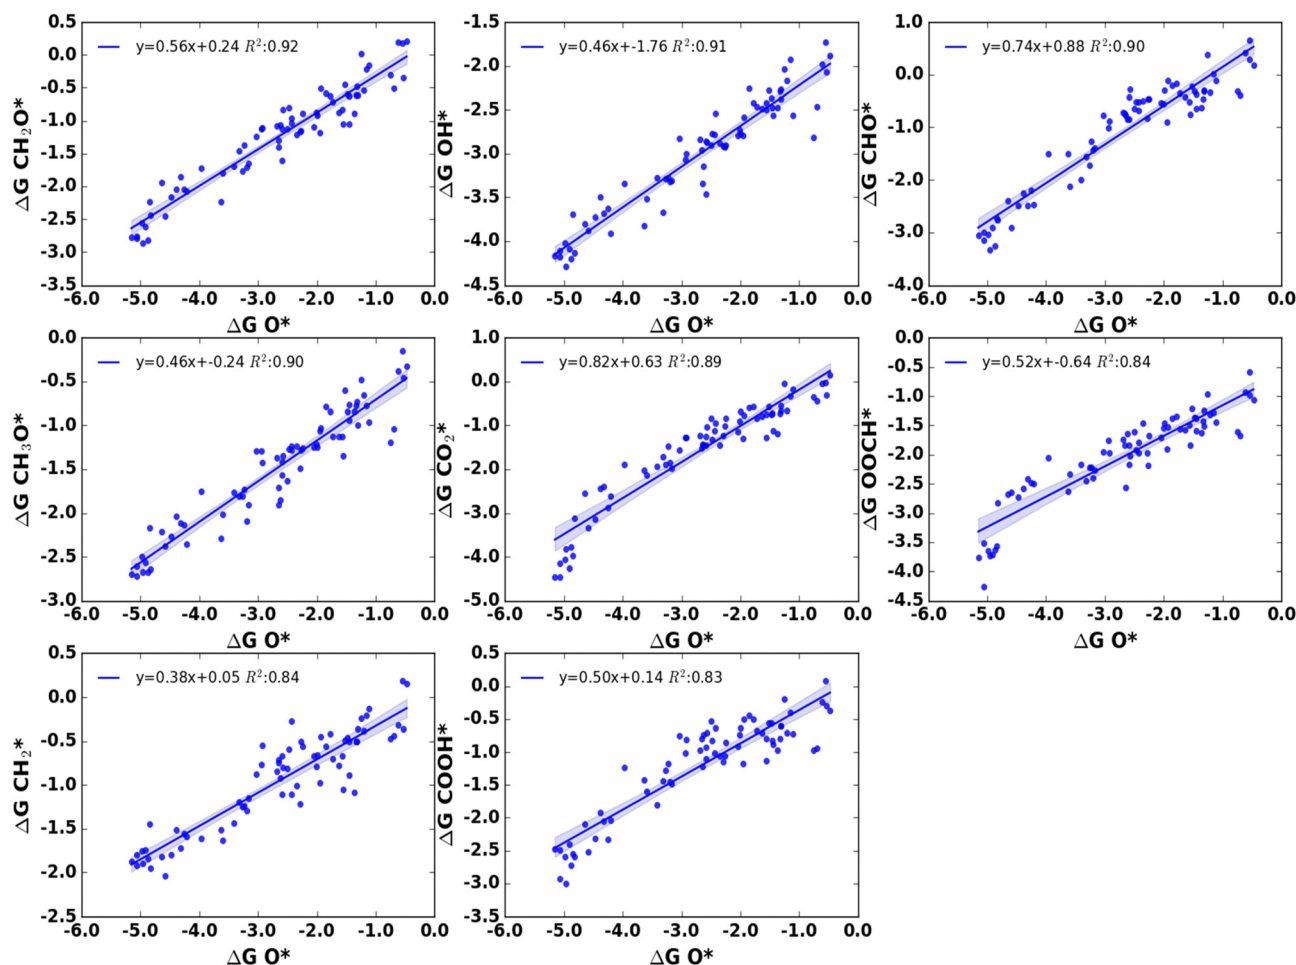


Fig. 10 Linear scaling relationship between adsorption free energies of O\* and various adsorbates with the coefficient of determination ( $R^2$ ) value  $\geq 0.80$ .



$\text{CO}_2^*$  adsorption free energies and adsorption free energies of other adsorbates with coefficient determination ( $R^2$ ) values higher than 0.80. We have found a strong correlation between the adsorption free energies of  $\text{CO}_2^*$  with the adsorption free energies of  $\text{COOH}^*$ ,  $\text{OOCH}^*$ ,  $\text{CHO}^*$ ,  $\text{CH}_2\text{O}^*$ ,  $\text{O}^*$ ,  $\text{CO}^*$ ,  $\text{OH}^*$ , and  $\text{CH}_3\text{O}^*$  with coefficient determination ( $R^2$ ) values larger than 0.85. In all these cluster-adsorbate complexes except on  $\text{O}^*$ ,  $\text{OH}^*$ , and  $\text{CH}_3\text{O}^*$ , both the C and O can take part in the bonding process with the metal cluster moiety. In general, we have noticed that the binding free energies for adsorbates that can bind through both C and O atoms show an excellent correlation with the binding free energies of  $\text{CO}_2^*$ . A single O atom is the sole binding motif for three adsorbates  $\text{O}^*$ ,  $\text{OH}^*$ , and  $\text{CH}_3\text{O}^*$  and a high correlation for the adsorption free energies of these three adsorbates with  $\text{CO}_2^*$  adsorption energies implies that binding through O determines the extent of correlation with  $\text{CO}_2^*$  adsorption energies. Adsorption free energies of other adsorbates  $\text{CHOH}^*$ ,  $\text{CH}_2^*$ , and  $\text{C}^*$  also exhibit relatively higher correlations with the adsorption free energies of  $\text{CO}_2^*$  adsorbate with  $R^2$  values in the range of 0.80–0.82 eV. Moreover, we have found that  $\text{COH}^*$  and  $\text{CH}_2\text{OH}^*$  adsorption free energies do not exhibit a significant correlation with  $\text{CO}_2^*$  adsorption free energies. In these adsorbates along with  $\text{CHOH}^*$ , the O atom is not readily available for binding and

the primary binding motif is the C atom. This implies a higher correlation above 0.85 with  $\text{CO}_2^*$  adsorption free energies are possible only for adsorbates that can bind through the O atom.

Fig. 10 and 11 show the linear scaling relationships between  $\text{O}^*$  and  $\text{C}^*$  adsorbates. We have seen that the adsorption energies of  $\text{O}^*$  correlate very well with the adsorption energies of  $\text{CH}_2\text{O}^*$ ,  $\text{OH}^*$ ,  $\text{CHO}^*$ ,  $\text{CH}_3\text{O}^*$ , and  $\text{CO}_2^*$  with  $R^2$  values in the range of 0.89 to 0.92. In addition, adsorption free energies of  $\text{CH}_2^*$ ,  $\text{OOCH}^*$ , and  $\text{COOH}^*$  also exhibit relatively better correlations ( $R^2 = 0.83$ – $0.84$ ) with  $\text{O}^*$  adsorption free energies. All these adsorbates except  $\text{CH}_2^*$  species can bind on the nanoclusters through the O atom. It should be noted that  $\text{CH}_2\text{O}^*$  and  $\text{CHO}^*$  which are often considered as C-bound adsorbates on metal surfaces for linear scaling relation studies, show a significantly larger correlation with  $\text{O}^*$  adsorption energies on nanoclusters. Surprisingly, we have found the adsorption free energies of  $\text{CH}_2^*$  adsorbate correlates relatively well with the adsorption free energies of  $\text{O}^*$  with an  $R^2$  value of 0.84. All other adsorbates including  $\text{CO}^*$ ,  $\text{COH}^*$ ,  $\text{CHOH}^*$ , and  $\text{CH}_2\text{OH}^*$  do not correlate well with  $\text{O}^*$  in their linear free energy relationship (Table S4, ESI†). It should be noted that a free O is unavailable to participate in bonding with the metal clusters for  $\text{COH}^*$ ,  $\text{CHOH}^*$ , and  $\text{CH}_2\text{OH}^*$ .  $\text{CO}^*$  adsorbates although use its two binding motifs C and O atoms for binding on some of the

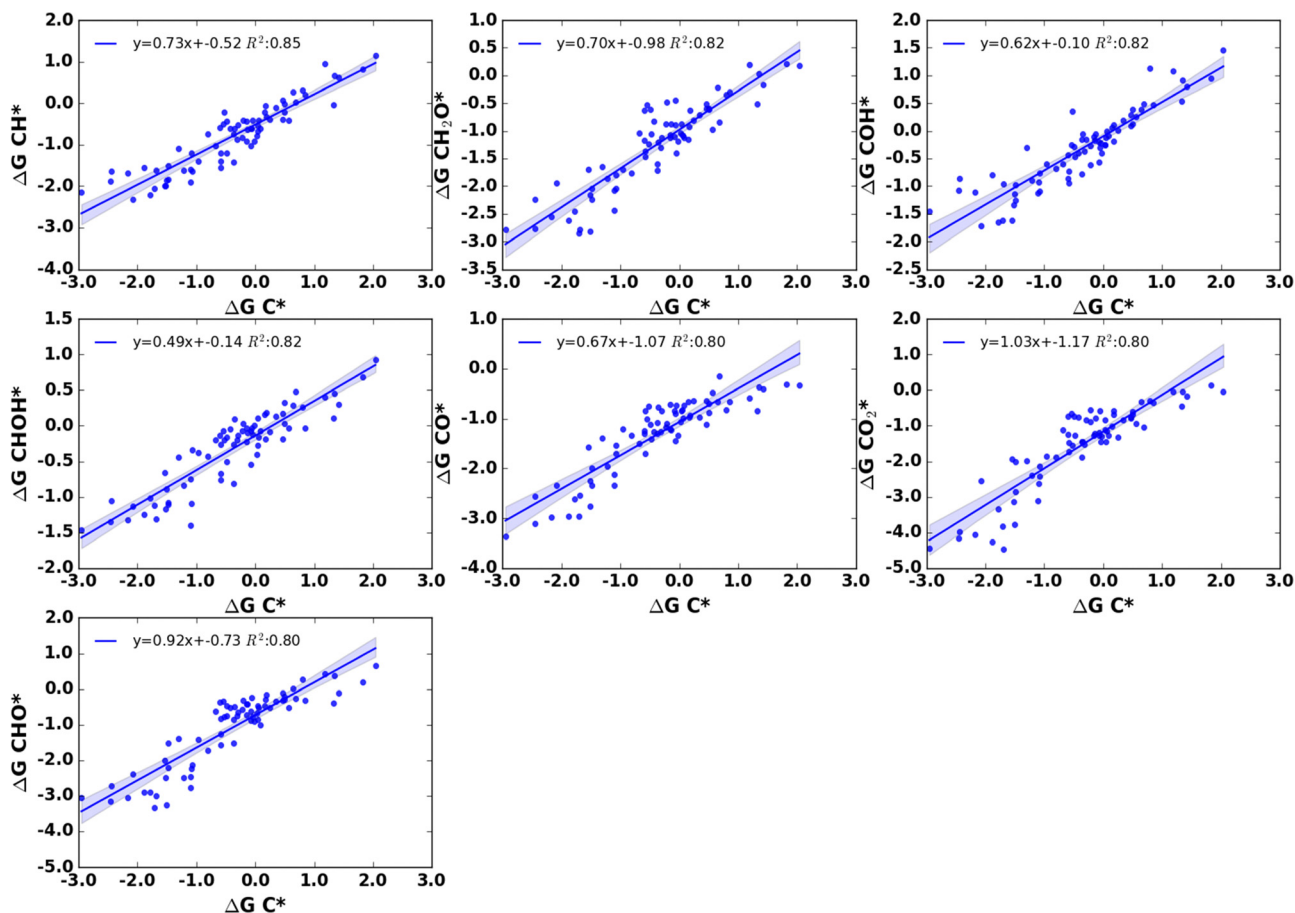


Fig. 11 Linear scaling relationship between adsorption free energies of  $\text{C}^*$  and various adsorbates with the coefficient of determination ( $R^2$ ) value  $\geq 0.80$ .



nanoclusters especially for early first-row TMs, it mostly uses the C atom for bonding on cluster moieties, and a lower correlation in the linear free energy relationship can be attributed to this observation. This argument is further supported by the fact that a higher correlation ( $R^2 = 0.80$ ) exists between the adsorption free energies of  $\text{CO}^*$  and  $\text{C}^*$ .

The adsorption free energies of  $\text{C}^*$  show a better linear scaling relationship with the adsorption free energies of  $\text{CH}^*$  with an  $R^2$  value of 0.85. In addition,  $\text{C}^*$  shows a relatively better correlation with  $\text{CO}^*$ ,  $\text{COH}^*$ ,  $\text{CH}_2\text{O}^*$ ,  $\text{CHOH}^*$ ,  $\text{CO}_2^*$  and  $\text{CHO}^*$  within a range of  $R^2$  value of 0.80–0.82 in their free energy relationship. Of these adsorbates,  $\text{COH}^*$  and  $\text{CHOH}^*$  do not have a free O atom that can take part in binding on nanoclusters and their predominant binding motif is the C atom, and the  $\text{CO}^*$  adsorbate as discussed above binding through the C atom on most of the nanoclusters. Other adsorbates  $\text{CH}_2\text{O}^*$ ,  $\text{CO}_2^*$ , and  $\text{CHO}^*$  are bidentate which can use C and/or O atoms for binding on nanoclusters.

Although there are exceptions, in general, we have found that the adsorption energies of adsorbates that contain O atom which can participate in bonding interactions with cluster moiety show a higher correlation with adsorption free energies of  $\text{CO}_2^*$  or  $\text{O}^*$  compared to that of  $\text{C}^*$  adsorbates.  $\text{C}^*$  adsorption energies exhibit a relatively better correlation with species that use the C atom as the main binding motif such as  $\text{COH}^*$ ,  $\text{CHOH}^*$ , and  $\text{CO}^*$ . We have found that the linear scaling relationship that exists in heterogeneous catalysts such as the correlation between the adsorption energies of  $\text{AH}_x$  with the adsorption energies of atom A ( $A = \text{C}, \text{N}, \text{O}, \text{S}, \text{etc.}$ ) breaks on nanocluster surfaces if the adsorbate has more than one atom that can act as a binding motif on nanoclusters. Some discrepancies in the linear scaling relationship were expected due to the scattering of the adsorption energies around the linear relationships. The scattering of the adsorption energies primarily arises from the differences in the adsorption sites on nanoclusters and the relative stabilities of the different adsorbates.

## Conclusions

We have investigated the  $\text{CO}_2\text{RR}$  activity and selectivity on first-row TM nanoclusters (Sc–Cu) containing 3 to 10 atoms. The global minimum configurations of all the nanoclusters were determined using the GIGA version of the birmingham parallel genetic algorithm (BPGA). We have also determined the best adsorbate binding positions for various  $\text{CO}_2\text{RR}$  adsorbates on nanoclusters. The adsorption free energies for all the adsorbates, in general, show a trend of decreasing while moving across the first-row TMs from Sc to Cu. For some of the adsorbates, we have found a strong correlation between the adsorption free energies and residual charges on the adsorbates. We have found that  $\text{CHO}^*$  mediated pathways are preferred, in general, over  $\text{COH}^*$  mediated pathways for  $\text{CH}_4$  production. Due to the larger endergonicity associated with the  $\text{OH}^*$  removal step for the  $\text{CHO}^*$  Path I:  $\text{*} + \text{CO}_2 \rightarrow \text{COOH}^* \rightarrow \text{CO}^* \rightarrow \text{CHO}^* \rightarrow \text{CH}_2\text{O}^* \rightarrow \text{CH}_3\text{O}^* \rightarrow \text{O}^* + \text{CH}_4 \rightarrow \text{OH}^* \rightarrow \text{*}, \text{CO}_2\text{RR}$

*via* this reaction pathway is greatly disfavored on all nanoclusters except on Cu clusters containing even number of atom compositions. We have identified an alternative lowest reaction route *via*  $\text{CHO}^*$  Path II:  $\text{*} + \text{CO}_2 \rightarrow \text{COOH}^* \rightarrow \text{CO}^* \rightarrow \text{CHO}^* \rightarrow \text{CH}_2\text{O}^* \rightarrow \text{CH}_2\text{OH}^* \rightarrow \text{CH}_2^* \rightarrow \text{CH}_3^* \rightarrow \text{CH}_4 + \text{*}$  which can proceed to  $\text{CH}_4$  without passing through the highly endergonic  $\text{OH}^*$  removal step on most of the clusters. With a limited number of exceptions, for the reaction route *via*  $\text{CHO}^*$  Path II, the potential-determining step is the formation of  $\text{CH}_2\text{OH}^*$  from  $\text{CH}_2\text{O}^*$  ( $\text{CH}_2\text{O}^* \rightarrow \text{CH}_2\text{OH}^*$ ) on most of the Sc to Mn nanoclusters whilst the potential-determining step for the  $\text{CHO}^*$  Path I is the formation of  $\text{CHO}^*$  intermediate from  $\text{CO}^*$  ( $\text{CO}^* \rightarrow \text{CHO}^*$ ) on Fe to Cu nanoclusters. Moreover, Cu clusters with even numbers of cluster atom compositions prefer the reaction route *via*  $\text{CHO}^*$  Path I with  $\text{CO}^* \rightarrow \text{CHO}^*$  as the potential-determining step, similar to the reported work of Nørskov and co-workers on Cu metal surfaces.<sup>50</sup> On many metal nanoclusters, we have found that  $\text{COH}^*$  mediated pathways can compete with  $\text{CHO}^*$  Path II. Unlike  $\text{CHO}^*$  mediated pathways, we have not found a preference for any particular  $\text{COH}^*$  pathway and the potential-determining step varies depending on the relative stabilities of different adsorbates and the free energy changes associated with various electrochemical steps for their formation. Our studies on  $\text{CH}_4$  vs  $\text{CH}_3\text{OH}$  selectivity establish that methanol formation is greatly disfavored on all nanoclusters irrespective of which is the preferred  $\text{CO}_2\text{RR}$  reaction pathway ( $\text{CHO}^*$  or  $\text{COH}^*$  mediated pathway) on all nanoclusters. Most importantly, the formation of side reaction products CO and HCOOH is greatly suppressed on all nanoclusters due to the high endergonicity associated with the release of CO and HCOOH from the nanocluster surface. Moreover, unlike on metal surfaces where CO is weakly bound to the catalyst surface, the availability of the uncoordinated binding sites on nanoclusters allows the chemisorption of CO on the cluster surface. Desorption of CO from the nanocluster surfaces is often a high endergonic step as it requires the breaking of strong metal–CO bonds and hence, these  $\text{CO}^*$  species are readily available for further reduction steps leading to the formation of higher-order reduction product, methane. We have found that several nanoclusters  $\text{Cr}_{10}$ ,  $\text{Cr}_5$ ,  $\text{Cr}_9$ ,  $\text{V}_4$ ,  $\text{Cu}_5$ ,  $\text{Fe}_4$ ,  $\text{Fe}_3$ ,  $\text{Fe}_{10}$ ,  $\text{Cr}_6$ ,  $\text{Cu}_9$ ,  $\text{Co}_3$ ,  $\text{V}_5$ ,  $\text{Cr}_8$ ,  $\text{Cu}_3$ ,  $\text{Fe}_8$ ,  $\text{Fe}_7$ ,  $\text{Mn}_8$ ,  $\text{Cu}_7$ , and  $\text{Mn}_4$  exhibit relatively lower limiting potential values and can be considered as a potential nanocluster-based electrocatalysts for  $\text{CO}_2\text{RR}$  for methane formation. We have also compared the limiting potentials for  $\text{CO}_2\text{RR}$  and HER and found that HER triggers at much lower potentials on most of the nanocluster surface. Still, we have identified a number of nanoclusters ( $\text{Ti}_6$ ,  $\text{V}_5$ ,  $\text{V}_6$ ,  $\text{Mn}_4$ ,  $\text{Mn}_7$ ,  $\text{Mn}_{10}$ ,  $\text{Fe}_4$ ,  $\text{Fe}_8$ ,  $\text{Fe}_{10}$ ,  $\text{Ni}_4$ , and  $\text{Cu}_5$ ) as possible electrocatalysts which show a preference for  $\text{CO}_2\text{RR}$  over HER by 0.2 eV or more.

We have also tried to establish a linear scaling relationship on nanoclusters based on adsorption free energies of  $\text{CO}_2^*$ ,  $\text{C}^*$ , and  $\text{O}^*$ . With few exceptions, we have found in general that the adsorption free energies of adsorbates that can bind through O atom on the nanoclusters show a higher correlation with the



adsorption free energies of CO<sub>2</sub>\* or O\* compared to that of C\* adsorbates. On the other hand, the adsorption energies of C\* adsorbates show a higher level of correlation with the adsorption energies of COH\*, CH<sub>2</sub>OH\*, CHOH\*, and CO\* adsorbates whose O atoms are not readily available for binding on nanocluster surfaces. A breaking of scaling relationships that exists on heterogeneous catalysts such as the correlation between the adsorption energies of AH<sub>x</sub> with the adsorption energies of atom A (A = C, N, O, S, etc.) was observed for adsorbates that can bind on nanocluster through more than one atom such as CH<sub>2</sub>O\*.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

RKR would like to thank the IT Research Computing group at the Texas A&M University at Qatar and the University of Birmingham's BlueBEAR HPC facility (<http://www.bear.bham.ac.uk/bluebear>) for providing computational resources and support. RKR acknowledges the UK's national HPC Facility, ARCHER, via membership of the UK's HEC Materials Chemistry Consortium, which is funded by EPSRC (EP/R029431). RKR acknowledges Prof. Richard Catlow, Cardiff University for his valuable suggestions and comments on the work. ENB acknowledges that this publication was made possible by National Priorities Research Program (NPRP) Grant NPRP11S-0116-180320 from the Qatar National Research Fund (a member of Qatar Foundation) and the use of computational resources at Texas A&M University at Qatar (TAMUQ).

## References

- 1 D. D. Zhu, J. L. Liu and S. Z. Qiao, Recent Advances in Inorganic Heterogeneous Electrocatalysts for Reduction of Carbon Dioxide, *Adv. Mater.*, 2016, **28**(18), 3423–3452, DOI: [10.1002/adma.201504766](https://doi.org/10.1002/adma.201504766).
- 2 J. Eppinger and K. W. Huang, Formic Acid as a Hydrogen Energy Carrier, *ACS Energy Lett.*, 2017, **2**(1), 188–195, DOI: [10.1021/acseenergylett.6b00574](https://doi.org/10.1021/acseenergylett.6b00574).
- 3 G. A. Olah, Beyond Oil and Gas: The Methanol Economy, *Angew. Chem., Int. Ed.*, 2005, **44**, 2636, DOI: [10.1002/anie.200462121](https://doi.org/10.1002/anie.200462121).
- 4 S. Sun, H. Sun, P. T. Williams and C. Wu, Recent Advances in Integrated CO<sub>2</sub> capture and Utilization: A Review, *Sustainable Energy Fuels*, 2021, **5**(18), 4546–4559, DOI: [10.1039/d1se00797a](https://doi.org/10.1039/d1se00797a).
- 5 S. Saeidi, N. A. S. Amin and M. R. Rahimpour, Hydrogenation of CO<sub>2</sub> to Value-Added Products—A Review and Potential Future Developments, *J. CO<sub>2</sub> Util.*, 2014, **5**, 66–81, DOI: [10.1016/j.jcou.2013.12.005](https://doi.org/10.1016/j.jcou.2013.12.005).
- 6 S. G. Jadhav, P. D. Vaidya, B. M. Bhanage and J. B. Joshi, Catalytic Carbon Dioxide Hydrogenation to Methanol: A Review of Recent Studies, *Chem. Eng. Res. Des.*, 2014, **92**, 2557–2567, DOI: [10.1016/j.cherd.2014.03.005](https://doi.org/10.1016/j.cherd.2014.03.005).
- 7 I. Sullivan, A. Goryachev, I. A. Digdaya, X. Li, H. A. Atwater, D. A. Vermaas and C. Xiang, Coupling Electrochemical CO<sub>2</sub> Conversion with CO<sub>2</sub> Capture, *Nat. Catal.*, 2021, **4**(11), 952–958, DOI: [10.1038/s41929-021-00699-7](https://doi.org/10.1038/s41929-021-00699-7).
- 8 L. Rotundo, R. Gobetto and C. Nervi, Electrochemical CO<sub>2</sub> Reduction with Earth-Abundant Metal Catalysts, *Curr. Opin. Green Sustain. Chem.*, 2021, **31**, DOI: [10.1016/j.cogsc.2021.100509](https://doi.org/10.1016/j.cogsc.2021.100509).
- 9 Y. Xue, Y. Guo, H. Cui and Z. Zhou, Catalyst Design for Electrochemical Reduction of CO<sub>2</sub> to Multicarbon Products, *Small Methods*, 2021, **5**(10), 2100736, DOI: [10.1002/smt.202100736](https://doi.org/10.1002/smt.202100736).
- 10 F. Liang, K. Zhang, L. Zhang, Y. Zhang, Y. Lei and X. Sun, Recent Development of Electrocatalytic CO<sub>2</sub> Reduction Application to Energy Conversion, *Small*, 2021, **17**(44), 2100323, DOI: [10.1002/smll.202100323](https://doi.org/10.1002/smll.202100323).
- 11 D. T. Whipple and P. J. A. Kenis, Prospects of CO<sub>2</sub> Utilization via Direct Heterogeneous Electrochemical Reduction, *J. Phys. Chem. Lett.*, 2010, **1**(24), 3451–3458, DOI: [10.1021/jz1012627](https://doi.org/10.1021/jz1012627).
- 12 M. Gattrell, N. Gupta and A. Co, A Review of the Aqueous Electrochemical Reduction of CO<sub>2</sub> to Hydrocarbons at Copper, *J. Electroanal. Chem.*, 2006, 1–19, DOI: [10.1016/j.jelechem.2006.05.013](https://doi.org/10.1016/j.jelechem.2006.05.013).
- 13 Y. Hori, A. Murata and R. Takahashi, Formation of Hydrocarbons in the Electrochemical Reduction of Carbon Dioxide at a Copper Electrode in Aqueous Solution, *J. Chem. Soc., Faraday Trans. 1*, 1989, **85**(8), 2309–2326.
- 14 D. Astruc, Introduction: Nanoparticles in Catalysis, *Chem. Rev.*, 2020, **120**(2), 461–463, DOI: [10.1021/acs.chemrev.8b00696](https://doi.org/10.1021/acs.chemrev.8b00696).
- 15 E. C. Tyo and S. Vajda, Catalysis by Clusters with Precise Numbers of Atoms, *Nat. Nanotechnol.*, 2015, **10**(7), 577–588, DOI: [10.1038/NNANO.2015.140](https://doi.org/10.1038/NNANO.2015.140).
- 16 I. Chakraborty and T. Pradeep, Atomically Precise Clusters of Noble Metals: Emerging Link between Atoms and Nanoparticles, *Chem. Rev.*, 2017, **117**(12), 8208–8271, DOI: [10.1021/acs.chemrev.6b00769](https://doi.org/10.1021/acs.chemrev.6b00769).
- 17 F. Li, D. R. MacFarlane and J. Zhang, Recent Advances in the Nanoengineering of Electrocatalysts for CO<sub>2</sub> Reduction, *Nanoscale*, 2018, **10**(14), 6235–6260, DOI: [10.1039/c7nr09620h](https://doi.org/10.1039/c7nr09620h).
- 18 Y. Dai, Y. Wang, B. Liu and Y. Yang, Metallic Nanocatalysis: An Accelerating Seamless Integration with Nanotechnology, *Small*, 2015, **11**(3), 268–289, DOI: [10.1002/smll.201400847](https://doi.org/10.1002/smll.201400847).
- 19 L. Liu and A. Corma, Metal Catalysts for Heterogeneous Catalysis: From Single Atoms to Nanoclusters and Nanoparticles, *Chem. Rev.*, 2018, **118**(10), 4981–5079, DOI: [10.1021/acs.chemrev.7b00776](https://doi.org/10.1021/acs.chemrev.7b00776).
- 20 A. Munir, K. S. Joya, T. Ul haq, N. U. A. Babar, S. Z. Hussain, A. Qurashi, N. Ullah and I. Hussain, Metal Nanoclusters: New Paradigm in Catalysis for Water Splitting, Solar and Chemical Energy Conversion, *ChemSusChem*, 2019, **12**(8), 1517–1548, DOI: [10.1002/cssc.201802069](https://doi.org/10.1002/cssc.201802069).
- 21 M. Jia, C. Choi, T.-S. Wu, C. Ma, P. Kang, H. Tao, Q. Fan, S. Hong, S. Liu, Y.-L. Soo, J. Qiu and Z. Sun, Carbon-Supported



- Ni Nanoparticles for Efficient CO<sub>2</sub> Electroreduction, *Chem. Sci.*, 2018, **9**(47), 8775–8780, DOI: [10.1039/c8sc03732a](https://doi.org/10.1039/c8sc03732a).
- 22 J. Wei, H.-L. Ya, S.-N. Qin, H. Zhang, Z.-Q. Tian and J.-F. Li, Efficient CO<sub>2</sub> Electroreduction on Pd-Based Core–Shell Nanostructure with Tensile Strain, *J. Electroanal. Chem.*, 2021, **896**, DOI: [10.1016/j.jelechem.2021.115205](https://doi.org/10.1016/j.jelechem.2021.115205).
- 23 G. Hwa Jeong, Y. Chuan Tan, J. Tae Song, G.-Y. Lee, H. Jin Lee, J. Lim, H. Young Jeong, S. Won, J. Oh and S. Ouk Kim, Synthetic Multiscale Design of Nanostructured Ni Single Atom Catalyst for Superior CO<sub>2</sub> Electroreduction, *Chem. Eng. J.*, 2021, **426**, 131063, DOI: [10.1016/j.cej.2021.131063](https://doi.org/10.1016/j.cej.2021.131063).
- 24 L.-B. Zhang, T. Tang, J. Fu, S. Niu, C. He, J.-S. Hu and L.-J. Wan, Molecular Linking Stabilizes Bi Nanoparticles for Efficient Electrochemical Carbon Dioxide Reduction, *J. Phys. Chem. C*, 2021, **125**(23), 12699–12706, DOI: [10.1021/acs.jpcc.1c03790](https://doi.org/10.1021/acs.jpcc.1c03790).
- 25 Y.-B. Chang, C. Zhang, X.-L. Lu, W. Zhang and T.-B. Lu, Graphdiyne Enables Ultrafine Cu Nanoparticles to Selectively Reduce CO<sub>2</sub> to C<sup>2+</sup> Products, *Nano Res.*, 2022, **15**(1), 195–201, DOI: [10.1007/s12274-021-3456-2](https://doi.org/10.1007/s12274-021-3456-2).
- 26 Z. Zhu, Z. Li, X. Wei, J. Wang, S. Xiao, R. Li, R. Wu and J. S. Chen, Achieving Efficient Electroreduction of CO<sub>2</sub> to CO in a Wide Potential Window by Encapsulating Ni Nanoparticles in N-Doped Carbon Nanotubes, *Carbon N. Y.*, 2021, **185**, 9–16, DOI: [10.1016/j.carbon.2021.08.072](https://doi.org/10.1016/j.carbon.2021.08.072).
- 27 Y. Li, C. Chen, R. Cao, Z. Pan, H. He and K. Zhou, Dual-Atom Ag<sub>2</sub>/Graphene Catalyst for Efficient Electroreduction of CO<sub>2</sub> to CO, *Appl. Catal., B*, 2020, **268**, DOI: [10.1016/j.apcatb.2020.118747](https://doi.org/10.1016/j.apcatb.2020.118747).
- 28 X. Ma, J. Tian, M. Wang, M. Shen and L. Zhang, Polymeric Carbon Nitride Supported Bi Nanoparticles as Highly Efficient CO<sub>2</sub> Reduction Electrocatalyst in a Wide Potential Range, *J. Colloid Interface Sci.*, 2022, **608**, 1676–1684, DOI: [10.1016/j.jcis.2021.10.049](https://doi.org/10.1016/j.jcis.2021.10.049).
- 29 Q. He, J. H. Lee, D. Liu, Y. Liu, Z. Lin, Z. Xie, S. Hwang, S. Kattel, L. Song and J. G. Chen, Accelerating CO<sub>2</sub> Electroreduction to CO Over Pd Single-Atom Catalyst, *Adv. Funct. Mater.*, 2020, **30**(17), 2000407, DOI: [10.1002/adfm.202000407](https://doi.org/10.1002/adfm.202000407).
- 30 B. Ávila-Bolívar, V. Montiel and J. Solla-Gullón, On the Activity and Stability of Sb<sub>2</sub>O<sub>3</sub>/Sb Nanoparticles for the Electroreduction of CO<sub>2</sub> toward Formate, *J. Electroanal. Chem.*, 2021, **895**, DOI: [10.1016/j.jelechem.2021.115440](https://doi.org/10.1016/j.jelechem.2021.115440).
- 31 W. Zheng, C. Guo, J. Yang, F. He, B. Yang, Z. Li, L. Lei, J. Xiao, G. Wu and Y. Hou, Highly Active Metallic Nickel Sites Confined in N-Doped Carbon Nanotubes toward Significantly Enhanced Activity of CO<sub>2</sub> Electroreduction, *Carbon N. Y.*, 2019, **150**, 52–59, DOI: [10.1016/j.carbon.2019.04.112](https://doi.org/10.1016/j.carbon.2019.04.112).
- 32 Y.-X. Duan, K.-H. Liu, Q. Zhang, J.-M. Yan and Q. Jiang, Efficient CO<sub>2</sub> Reduction to HCOOH with High Selectivity and Energy Efficiency over Bi/RGO Catalyst, *Small Methods*, 2020, **4**(5), 1900846, DOI: [10.1002/smt.201900846](https://doi.org/10.1002/smt.201900846).
- 33 D. R. Kauffman, D. Alfonso, C. Matranga, P. Ohodnicki, X. Deng, R. C. Siva, C. Zeng and R. Jin, Probing Active Site Chemistry with Differently Charged Au<sub>25</sub><sup>q</sup> Nanoclusters ( $q = -1, 0, +1$ ), *Chem. Sci.*, 2014, **5**(8), 3151, DOI: [10.1039/c4sc00997e](https://doi.org/10.1039/c4sc00997e).
- 34 C. Zhao, X. Dai, T. Yao, W. Chen, X. Wang, J. Wang, J. Yang, S. Wei, Y. Wu and Y. Li, Ionic Exchange of Metal–Organic Frameworks to Access Single Nickel Sites for Efficient Electroreduction of CO<sub>2</sub>, *J. Am. Chem. Soc.*, 2017, **139**(24), 8078–8081, DOI: [10.1021/jacs.7b02736](https://doi.org/10.1021/jacs.7b02736).
- 35 C. Kim, H. S. Jeon, T. Eom, M. S. Jee, H. Kim, C. M. Friend, B. K. Min and Y. J. Hwang, Achieving Selective and Efficient Electrocatalytic Activity for CO<sub>2</sub> Reduction Using Immobilized Silver Nanoparticles, *J. Am. Chem. Soc.*, 2015, **137**(43), 13844–13850, DOI: [10.1021/jacs.5b06568](https://doi.org/10.1021/jacs.5b06568).
- 36 R. Passalacqua, S. Parathoner, G. Centi, A. Halder, E. C. Tyo, B. Yang, S. Seifert and S. Vajda, Electrochemical Behaviour of Naked Sub-Nanometre Sized Copper Clusters and Effect of CO<sub>2</sub>, *Catal. Sci. Technol.*, 2016, **6**(18), 6977–6985, DOI: [10.1039/c6cy00942e](https://doi.org/10.1039/c6cy00942e).
- 37 H. Mistry, R. Reske, Z. Zeng, Z.-J. Zhao, J. Greeley, P. Strasser and B. R. Cuenya, Exceptional Size-Dependent Activity Enhancement in the Electroreduction of CO<sub>2</sub> over Au Nanoparticles, *J. Am. Chem. Soc.*, 2014, **136**(47), 16473–16476, DOI: [10.1021/ja508879j](https://doi.org/10.1021/ja508879j).
- 38 D. R. Kauffman, D. Alfonso, C. Matranga, H. Qian and R. Jin, Experimental and Computational Investigation of Au<sub>25</sub> Clusters and CO<sub>2</sub>: A Unique Interaction and Enhanced Electrocatalytic Activity, *J. Am. Chem. Soc.*, 2012, **134**(24), 10237–10243, DOI: [10.1021/ja303259q](https://doi.org/10.1021/ja303259q).
- 39 D. Gao, H. Zhou, J. Wang, S. Miao, F. Yang, G. Wang, J. Wang and X. Bao, Size-Dependent Electrocatalytic Reduction of CO<sub>2</sub> over Pd Nanoparticles, *J. Am. Chem. Soc.*, 2015, **137**(13), 4288–4291, DOI: [10.1021/jacs.5b00046](https://doi.org/10.1021/jacs.5b00046).
- 40 Z. Zhang, M. Chi, G. M. Veith, P. Zhang, D. A. Lutterman, J. Rosenthal, S. H. Overbury, S. Dai and H. Zhu, Rational Design of Bi Nanoparticles for Efficient Electrochemical CO<sub>2</sub> Reduction: The Elucidation of Size and Surface Condition Effects, *ACS Catal.*, 2016, **6**(9), 6255–6264, DOI: [10.1021/acscatal.6b01297](https://doi.org/10.1021/acscatal.6b01297).
- 41 A. Salehi-Khojin, H. R. M. Jhong, B. A. Rosen, W. Zhu, S. Ma, P. J. A. Kenis and R. I. Masel, Nanoparticle Silver Catalysts That Show Enhanced Activity for Carbon Dioxide Electrolysis, *J. Phys. Chem. C*, 2013, **117**(4), 1627–1632, DOI: [10.1021/jp310509z](https://doi.org/10.1021/jp310509z).
- 42 K. Manthiram, B. J. Beberwyck and A. P. Alivisatos, Enhanced Electrochemical Methanation of Carbon Dioxide with a Dispersible Nanoscale Copper Catalyst, *J. Am. Chem. Soc.*, 2014, **136**(38), 13319–13325, DOI: [10.1021/ja5065284](https://doi.org/10.1021/ja5065284).
- 43 R. Reske, H. Mistry, F. Behafarid, B. Roldan Cuenya and P. Strasser, Particle Size Effects in the Catalytic Electroreduction of CO<sub>2</sub> on Cu Nanoparticles, *J. Am. Chem. Soc.*, 2014, **136**(19), 6978–6986, DOI: [10.1021/ja500328k](https://doi.org/10.1021/ja500328k).
- 44 S. Zhang, P. Kang and T. J. Meyer, Nanostructured Tin Catalysts for Selective Electrochemical Reduction of Carbon Dioxide to Formate, *J. Am. Chem. Soc.*, 2014, **136**(5), 1734–1737, DOI: [10.1021/ja4113885](https://doi.org/10.1021/ja4113885).
- 45 X. F. Yang, A. Wang, B. Qiao, J. Li, J. Liu and T. Zhang, Single-Atom Catalysts: A New Frontier in Heterogeneous Catalysis, *Acc. Chem. Res.*, 2013, **46**(8), 1740–1748, DOI: [10.1021/ar300361m](https://doi.org/10.1021/ar300361m).



- 46 H. Zhang, G. Liu, L. Shi and J. Ye, Single-Atom Catalysts: Emerging Multifunctional Materials in Heterogeneous Catalysis, *Adv. Energy Mater.*, 2018, **8**(1), 1701343, DOI: [10.1002/aenm.201701343](https://doi.org/10.1002/aenm.201701343).
- 47 Y. Wang, Z. Chen, P. Han, Y. Du, Z. Gu, X. Xu and G. Zheng, Single-Atomic Cu with Multiple Oxygen Vacancies on Ceria for Electrocatalytic CO<sub>2</sub> Reduction to CH<sub>4</sub>, *ACS Catal.*, 2018, **8**(8), 7113–7119, DOI: [10.1021/acscatal.8b01014](https://doi.org/10.1021/acscatal.8b01014).
- 48 C. Liu, B. Yang, E. Tyo, S. Seifert, J. DeBartolo, B. von Issendorff, P. Zapol, S. Vajda and L. A. Curtiss, Carbon Dioxide Conversion to Methanol over Size-Selected Cu<sub>4</sub> Clusters at Low Pressures, *J. Am. Chem. Soc.*, 2015, **137**(27), 8676–8679, DOI: [10.1021/jacs.5b03668](https://doi.org/10.1021/jacs.5b03668).
- 49 B. Yang, C. Liu, A. Halder, E. C. Tyo, A. B. F. Martinson, S. Seifert, P. Zapol, L. A. Curtiss and S. Vajda, Copper Cluster Size Effect in Methanol Synthesis from CO<sub>2</sub>, *J. Phys. Chem. C*, 2017, **121**(19), 10406–10412, DOI: [10.1021/acs.jpcc.7b01835](https://doi.org/10.1021/acs.jpcc.7b01835).
- 50 A. A. Peterson, F. Abild-Pedersen, F. Studt, J. Rossmeisl and J. K. Nørskov, How Copper Catalyzes the Electroreduction of Carbon Dioxide into Hydrocarbon Fuels, *Energy Environ. Sci.*, 2010, **3**(9), 1311–1315, DOI: [10.1039/c0ee00071j](https://doi.org/10.1039/c0ee00071j).
- 51 X. Nie, M. R. Esopi, M. J. Janik and A. Asthagiri, Selectivity of CO<sub>2</sub> Reduction on Copper Electrodes: The Role of the Kinetics of Elementary Steps, *Angew. Chem., Int. Ed.*, 2013, **52**(9), 2459–2462, DOI: [10.1002/anie.201208320](https://doi.org/10.1002/anie.201208320).
- 52 X. Nie, W. Luo, M. J. Janik and A. Asthagiri, Reaction Mechanisms of CO<sub>2</sub> Electrochemical Reduction on Cu(111) Determined with Density Functional Theory, *J. Catal.*, 2014, **312**, 108–122, DOI: [10.1016/j.jcat.2014.01.013](https://doi.org/10.1016/j.jcat.2014.01.013).
- 53 K. S. Rawat, A. Mahata and B. Pathak, Thermochemical and Electrochemical CO<sub>2</sub> Reduction on Octahedral Cu Nanocluster: Role of Solvent towards Product Selectivity, *J. Catal.*, 2017, **349**, 118–127, DOI: [10.1016/j.jcat.2017.03.011](https://doi.org/10.1016/j.jcat.2017.03.011).
- 54 H. Dong, Y. Li and D. Jiang, First-Principles Insight into Electrocatalytic Reduction of CO<sub>2</sub> to CH<sub>4</sub> on a Copper Nanoparticle, *J. Phys. Chem. C*, 2018, **122**(21), 11392–11398, DOI: [10.1021/acs.jpcc.8b01928](https://doi.org/10.1021/acs.jpcc.8b01928).
- 55 C. Liu, H. He, P. Zapol and L. A. Curtiss, Computational Studies of Electrochemical CO<sub>2</sub> Reduction on Subnanometer Transition Metal Clusters, *Phys. Chem. Chem. Phys.*, 2014, **16**(48), 26584–26599, DOI: [10.1039/c4cp02690j](https://doi.org/10.1039/c4cp02690j).
- 56 R. Shanmugam, A. Thamaraiichelvan, T. K. Ganesan and B. Viswanathan, Computational Evaluation of Sub-Nanometer Cluster Activity of Singly Exposed Copper Atom with Various Coordinative Environment in Catalytic CO<sub>2</sub> transformation, *Appl. Surf. Sci.*, 2017, **396**, 444–454, DOI: [10.1016/j.apsusc.2016.10.174](https://doi.org/10.1016/j.apsusc.2016.10.174).
- 57 R. K. Raju, P. Rodriguez and R. L. Johnston, Can a Single Valence Electron Alter the Electrocatalytic Activity and Selectivity for CO<sub>2</sub> Reduction on the Subnanometer Scale?, *J. Phys. Chem. C*, 2019, **123**(23), 14591–14609, DOI: [10.1021/acs.jpcc.9b04745](https://doi.org/10.1021/acs.jpcc.9b04745).
- 58 J. B. A. Davis, A. Shayeghi, S. L. Horswell and R. L. Johnston, The Birmingham Parallel Genetic Algorithm and Its Application to the Direct DFT Global Optimisation of Ir<sub>N</sub> (*N* = 10–20) Clusters, *Nanoscale*, 2015, **7**(33), 14032–14038, DOI: [10.1039/c5nr03774c](https://doi.org/10.1039/c5nr03774c).
- 59 G. Kresse and J. Furthmüller, Efficiency of Ab Initio Total Energy Calculations for Metals and Semiconductors Using a Plane-Wave Basis Set, *Comput. Mater. Sci.*, 1996, **6**(1), 15–50, DOI: [10.1016/0927-0256\(96\)00008-0](https://doi.org/10.1016/0927-0256(96)00008-0).
- 60 G. Kresse and J. Hafner, Ab Initio Molecular-Dynamics Simulation of the Liquid–Metalamorphous–Semiconductor Transition in Germanium, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **49**(20), 14251–14269, DOI: [10.1103/PhysRevB.49.14251](https://doi.org/10.1103/PhysRevB.49.14251).
- 61 G. Kresse and J. Furthmüller, Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**(16), 11169–11186, DOI: [10.1103/PhysRevB.54.11169](https://doi.org/10.1103/PhysRevB.54.11169).
- 62 G. Kresse and J. Hafner, Ab Initio Molecular Dynamics for Liquid Metals, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **47**(1), 558–561, DOI: [10.1103/PhysRevB.47.558](https://doi.org/10.1103/PhysRevB.47.558).
- 63 M. Jäger, R. Schäfer and R. L. Johnston, GIGA: A Versatile Genetic Algorithm for Free and Supported Clusters and Nanoparticles in the Presence of Ligands, *Nanoscale*, 2019, **11**(18), 9042–9052, DOI: [10.1039/c9nr02031d](https://doi.org/10.1039/c9nr02031d).
- 64 A. Granja-Delrío, H. A. Abdulhussein and R. L. Johnston, DFT-Based Global Optimization of Sub-Nanometer Ni-Pd Clusters, *J. Phys. Chem. C*, 2019, **123**(43), 26583–26596, DOI: [10.1021/acs.jpcc.9b05970](https://doi.org/10.1021/acs.jpcc.9b05970).
- 65 F. Buendía, J. A. Vargas, R. L. Johnston and M. R. Beltrán, Study of the Stability of Small AuRh Clusters Found by a Genetic Algorithm Methodology, *Comput. Theor. Chem.*, 2017, **1119**, 51–58, DOI: [10.1016/j.comptc.2017.09.008](https://doi.org/10.1016/j.comptc.2017.09.008).
- 66 H. A. Hussein and R. L. Johnston, *The DFT-Genetic Algorithm Approach for Global Optimization of Subnanometer Bimetallic Clusters*, Elsevier Ltd., 1st edn, 2018, Vol. 12., DOI: [10.1016/B978-0-08-102232-0.00004-X](https://doi.org/10.1016/B978-0-08-102232-0.00004-X).
- 67 P. Ferrari, H. A. Hussein, C. J. Heard, J. Vanbuel, R. L. Johnston, P. Lievens and E. Janssens, Effect of Palladium Doping on the Stability and Fragmentation Patterns of Cationic Gold Clusters, *Phys. Rev. A*, 2018, **97**(5), 1–10, DOI: [10.1103/PhysRevA.97.052508](https://doi.org/10.1103/PhysRevA.97.052508).
- 68 M. Jäger, R. Schäfer and R. L. Johnston, First Principles Global Optimization of Metal Clusters and Nanoalloys, *Adv. Phys. X*, 2018, **3**(1), 1077–1108, DOI: [10.1080/23746149.2018.1516514](https://doi.org/10.1080/23746149.2018.1516514).
- 69 H. A. Hussein, I. Demiroglu and R. L. Johnston, Application of a Parallel Genetic Algorithm to the Global Optimization of Medium-Sized Au–Pd Sub-Nanometre Clusters, *Eur. Phys. J. B*, 2018, **91**(2), 34, DOI: [10.1140/epjb/e2017-80314-2](https://doi.org/10.1140/epjb/e2017-80314-2).
- 70 J. P. Perdew, K. Burke and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Phys. Rev. Lett.*, 1996, **77**(18), 3865–3868, DOI: [10.1103/PhysRevLett.77.3865](https://doi.org/10.1103/PhysRevLett.77.3865).
- 71 G. Kresse and D. Joubert, From Ultrasoft Pseudopotentials to the Projector Augmented-Wave Method, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**(3), 1758–1775, DOI: [10.1103/PhysRevB.59.1758](https://doi.org/10.1103/PhysRevB.59.1758).
- 72 M. Methfessel and A. T. Paxton, High-Precision Sampling for Brillouin-Zone Integration in Metals, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1989, **40**(6), 3616–3621, DOI: [10.1103/PhysRevB.40.3616](https://doi.org/10.1103/PhysRevB.40.3616).
- 73 S. Grimme, S. Ehrlich and L. Goerigk, Effect of the Damping Function in Dispersion Corrected Density Functional



- Theory, *J. Comput. Chem.*, 2011, **32**(7), 1456–1465, DOI: [10.1002/JCC.21759](https://doi.org/10.1002/JCC.21759).
- 74 S. Grimme, J. Antony, S. Ehrlich and H. Krieg, A Consistent and Accurate Ab Initio Parametrization of Density Functional Dispersion Correction (DFT-D) for the 94 Elements H-Pu, *J. Chem. Phys.*, 2010, **132**(15), 154104, DOI: [10.1063/1.3382344](https://doi.org/10.1063/1.3382344).
- 75 W. Tang, E. Sanville and G. Henkelman, A Grid-Based Bader Analysis Algorithm without Lattice Bias, *J. Phys.: Condens. Matter*, 2009, **21**(8), 84204, DOI: [10.1088/0953-8984/21/8/084204](https://doi.org/10.1088/0953-8984/21/8/084204).
- 76 V. Wang, N. Xu, J. C. Liu, G. Tang and W. T. Geng, VASPKIT: A User-Friendly Interface Facilitating High-Throughput Computing and Analysis Using VASP Code, *Comput. Phys. Commun.*, 2021, **267**, 108033, DOI: [10.1016/j.cpc.2021.108033](https://doi.org/10.1016/j.cpc.2021.108033).
- 77 J. K. Nørskov, J. Rossmeisl, A. Logadottir, L. Lindqvist, J. R. Kitchin, T. Bligaard and H. Jónsson, Origin of the Overpotential for Oxygen Reduction at a Fuel-Cell Cathode, *J. Phys. Chem. B*, 2004, **108**(46), 17886, DOI: [10.1021/jp047349j](https://doi.org/10.1021/jp047349j).
- 78 M. J. Janik, C. D. Taylor and M. Neurock, First-Principles Analysis of the Initial Electroreduction Steps of Oxygen over Pt(111), *J. Electrochem. Soc.*, 2009, **156**(1), B126–B135, DOI: [10.1149/1.3008005](https://doi.org/10.1149/1.3008005).
- 79 V. Tripković, E. Skúlason, S. Siahrostami, J. K. Nørskov and J. Rossmeisl, The Oxygen Reduction Reaction Mechanism on Pt(111) from Density Functional Theory Calculations, *Electrochim. Acta*, 2010, **55**, 7975–7981, DOI: [10.1016/j.electacta.2010.02.056](https://doi.org/10.1016/j.electacta.2010.02.056).
- 80 R. L. Johnston, Evolving Better Nanoparticles: Genetic Algorithms for Optimising Cluster Geometries, *J. Chem. Soc., Dalton Trans.*, 2003, **3**(22), 4193–4207, DOI: [10.1039/b305686d](https://doi.org/10.1039/b305686d).
- 81 D. M. Deaven and K. M. Ho, Molecular Geometry Optimization with a Genetic Algorithm, *Phys. Rev. Lett.*, 1995, **75**(2), 288–291, DOI: [10.1103/PhysRevLett.75.288](https://doi.org/10.1103/PhysRevLett.75.288).
- 82 R. H. Duncan Lyngdoh, H. F. Schaefer, R. B. King and M. M. Metal-Metal, Bond Distances and Bond Orders in Binuclear Metal Complexes of the First Row Transition Metals Titanium through Zinc, *Chem. Rev.*, 2018, **118**(24), 11626–11706, DOI: [10.1021/acs.chemrev.8b00297](https://doi.org/10.1021/acs.chemrev.8b00297).
- 83 L.-C. Wu, C.-W. Hsu, Y.-C. Chuang, G.-H. Lee, Y.-C. Tsai and Y. Wang, Bond Characterization on a Cr–Cr Quintuple Bond: A Combined Experimental and Theoretical Study, *J. Phys. Chem. A*, 2011, **115**(45), 12602–12615, DOI: [10.1021/jp203080j](https://doi.org/10.1021/jp203080j).

