

Colorless nonlinear optical D-p-A polymers with sulfones as electron acceptors

Citation for published version (APA):

Nijhuis, S., Rikken, G. L. J. A., Havinga, E. E., Hoeve, ten, W., Wynberg, H., & Meijer, E. W. (1990). Colorless nonlinear optical D-p-A polymers with sulfones as electron acceptors. *Journal of the Chemical Society, Chemical Communications*, (16), 1093-1094.

Document status and date:

Published: 01/01/1990

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Colourless Nonlinear Optical D- π -A Polymers with Sulphones as Electron Acceptors

S. Nijhuis,^a G. L. J. A. Rikken,^{*a} E. E. Havinga,^a W. ten Hoeve,^b H. Wynberg,^b and E. W. Meijer^{a†}

^a Philips Research Laboratories, P.O. Box 80000, 5600 JA Eindhoven, The Netherlands

^b Syncom b.v., Department of Chemistry, State University, Groningen, The Netherlands

Novel colourless side-chain methacrylate copolymers exhibiting relatively narrow charge-transfer bands at 335 nm and second-order optical nonlinearities up to $d_{33} = 4.3 \text{ pm V}^{-1}$ (at 1064 nm) have been synthesized and characterized.

Recently, poled polymers with high second-order nonlinearities (χ^2) have raised much interest as promising candidates for electro-optic switching and second-harmonic generation (SHG).^{1,2} The theory of molecular contributions (β) to nonlinear optical properties shows that high values of β occur for molecules with low-lying transitions involving a large oscillator strength and a large difference in dipole moment of ground and excited states.^{3,4} This explains the preference for strongly absorbing charge-transfer (C-T) molecules in nonlinear optical (NLO) polymers. Various studies have appeared on polymers in which the coloured C-T molecules are dissolved,⁵ covalently attached,⁶ or incorporated in network matrices.⁷

A drawback for SHG application stems from the fact that CT bands are generally rather broad.⁸ The residual absorption of the second harmonic in the tail of such a broad band, which often leads to photodegradation, limits the attainable increase of χ^2 by resonant enhancement in SHG polymers.


For this reason, well known molecules in nonlinear optics such as DANS (*N,N*-dimethylamino-*p*-nitrostilbene, $\lambda_{\text{max}} = 438 \text{ nm}$) cannot be used to double the frequency of light of a solid-state laser (from about 800 to 400 nm). A polymer bearing NLO-active groups with narrower C-T absorption bands would, therefore, be very valuable. The width of the C-T bands in the usual molecules with electron accepting and donating groups of mainly resonant character is partly due to the condition of the Franck-Condon excited state far from equilibrium geometry. For inductive donors and acceptors the geometries of ground and excited state are much more alike. Hence, such substituents could lead to narrower C-T absorption bands.

We now report on novel colourless NLO polymers with C-T groups in their side chains having sulphone groups as strong inductive⁹ electron acceptors. The sulphone group as an acceptor in NLO polymers has been independently disclosed by Ulman *et al.*¹⁰ in that the synthetic use of sulphones was stressed.

The synthesis of the polymers used in this study is given in Scheme 1. Homopolymers (**3a,b**) as well as copolymers of methyl methacrylate (MMA) and a methacrylate substituted with a 4-alkoxy-4'-alkylsulphone stilbene unit (**2a,b**) are synthesized by thermal radical polymerization, using benzoyl peroxide or azoisobutyronitrile (AIBN) as initiator. Semi-dilute solutions are required to avoid crosslinking.¹¹ The key step in the converging synthesis of the substituted monomer consists of the Wittig reaction, in which the donor side and the acceptor side are linked together, enabling both the length of the spacer between the main chain and acceptor, and the alkyl group linked to the sulphone to be varied independently.‡

Homopolymers (**3a,b**) are semi-crystalline, which is not acceptable for NLO applications because of light scattering.

Amorphous materials are obtained by copolymerization with MMA at contents of (**2a,b**) below 50 wt% (**2a**) or 25 wt% (**2b**), respectively. The molar mass (M_w) of all polymers, as determined by GPC [tetrahydrofuran eluent, poly methyl methacrylate (PMMA) standards], was in the range of $1.5 \times$

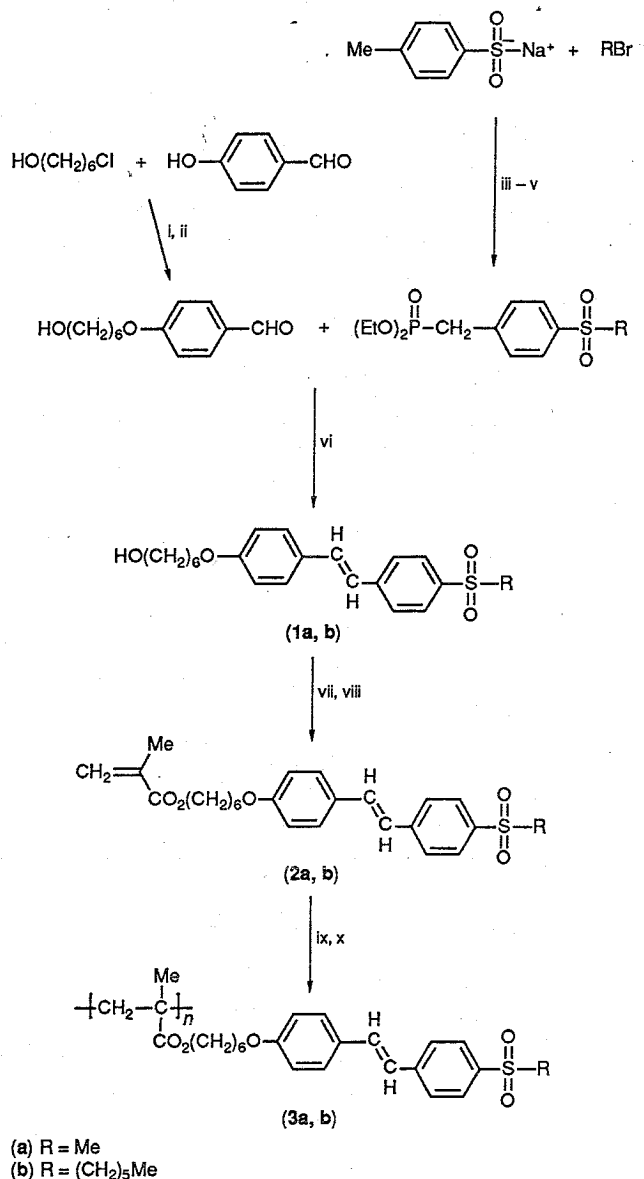

Scheme 1. Reagents and conditions: i, NaI-EtOH; ii, KOH-H₂O; iii, NaI-MeOH; iv, NBS-CCl₄; v, P(OEt)₃; vi, NaH; vii, CH₂=C(Me)-C(O)Cl; viii, C₆H₅NMe₂-CH₂Cl₂; ix, AIBN-toluene; x, benzoylperoxide.

[†] Present address: DSM Research, P.O. Box 18, 6160 MD Geleen, The Netherlands.

‡ Yields (**1a, 1b**) 48%; (**2a**) 90%; (**2b**) 32%.

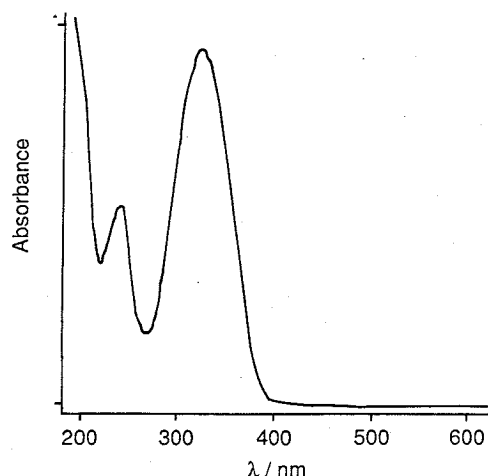


Figure 1. UV-VIS absorption spectrum of (3b), showing the narrow absorption C-T band in the near UV and transparency in the visible region.

10^4 – 3×10^4 g mol⁻¹. Spectroscopic data of monomers (2a,b) and of (co)polymers agree with the structures assigned. §

The UV-VIS absorption spectra of (co)polymers with (2a,b) (Figure 1) show rather narrow bands, with a negligible absorption around 400 nm ($\epsilon < 10^{-4} \epsilon_{\text{max}}$). Electric field induced second harmonic generation (EFISH) measurements at 1064 nm on (1a) yield a value of $\beta = 10 \times 10^{-30}$ esu, assuming parallelism of dipole and transition moments. The actual value will be larger, as it can be easily seen that the dipole moment of the ground state, mainly located on the $-\text{SO}_2-$ unit, makes an appreciable angle (ca. 45°) with the molecular axis, along which the transition moment will be directed. Measurement of SHG at 1064 nm on corona-poled

§ *Experimental data:* (2a): IR (KBr) 1150, 1300, 1580, 1620, 1720, 2800 cm⁻¹. (2b): ¹H NMR (80 MHz, CDCl₃) δ 0.8–1.8 (br, m), 1.9 (s), 3.1 (t), 4.1 (m), 5.5 (s, t), 6.1 (s), 6.8–8.0 (br, m); ¹³C NMR (80 MHz, CDCl₃) δ 14, 18, 23, 24, 26, 28, 29, 30, 32, 57, 65, 68, 115, 125, 126, 127, 129, 130, 133, 137, 138, 143, 160, 167; UV-VIS (chloroform) 335 nm (ϵ 24 100 dm³ mol⁻¹ cm⁻¹); DSC m.p. 100°C. (3a): IR (KBr) 1150, 1300, 1600, 1680, 2800 cm⁻¹. (3b): ¹H NMR (80 MHz, CDCl₃) δ 0.6–2.2 (br, b), 3.1 (t), 4.0 (br, m), 6.6–8.0 (br, m); UV-VIS (chloroform) 335 nm (ϵ 24 100 dm³ mol⁻¹ cm⁻¹); DSC T_g 124°C.

layers of copolymers give d_{33} values of 1.2, 1.4, and 4.3 pm V⁻¹ for compositions containing 25 wt% (2b), 25 and 50 wt% (2a), respectively. Detailed optical and NLO data will be published presently.

We may conclude that these novel polymers, owing to their relatively narrow absorption bands, offer great possibilities for use as frequency doubling devices by means of SHG. In view of the cut-off wavelength around 400 nm, they can in principle be used to double the frequency of a solid-state laser ($\lambda = 820$ nm \rightarrow $\lambda = 410$ nm). Their efficiency can probably be increased significantly by substitutions that turn the ground-state dipole moment in the direction of the molecular axis. Experiments with that aim are in progress.

Received, 17th April 1990; Com. 0101700K

References

- 1 'Nonlinear Optical Properties of Organic and Polymeric Materials,' ed. D. J. Williams, ACS Symp. Series 233, American Chemical Society, Washington DC, 1983.
- 2 'Nonlinear Optical Properties of Organic Molecules and Crystals,' eds. D. S. Chemla and J. Zyss, Academic Press, New York, 1987.
- 3 B. F. Levine and C. G. Bethea, *J. Chem. Phys.*, 1975, **63**, 2666; B. F. Levine, *Chem. Phys. Lett.*, 1976, **37**, 516.
- 4 J. L. Oudar and D. S. Chemla, *J. Chem. Phys.*, 1977, **66**, 2664.
- 5 E. E. Havinga and P. van Pelt, *Ber. Bunsenges. Phys. Chem.*, 1979, **83**, 816; G. R. Meredith, J. G. van Dusen, and D. J. Williams, *Macromolecules*, 1982, **15**, 1385; K. D. Singer, J. E. Sohn, and S. J. Lamala, *Appl. Phys. Lett.*, 1986, **49**, 248.
- 6 C. Ye, T. J. Marks, J. Yang and G. K. Wong, *Macromolecules*, 1987, **20**, 2322; K. D. Singer, M. G. Kuzyk, W. R. Holland, J. E. Sohn, S. J. Lamala, R. B. Comizzoli, H. E. Katz, and M. L. Schilling, *Appl. Phys. Lett.*, 1988, **53**, 1800.
- 7 B. Reck, M. Eich, D. Jungbauer, R. J. Twieg, C. G. Wilson, D. Y. Yoon, and G. C. Bjorklund in 'Nonlinear Optical Properties of Organic Materials,' ed. G. Khanarian, Proc. of SPIE 1989, p. 1147.
- 8 N. J. Turro, 'Modern Molecular Photochemistry,' Benjamin, Menlo Park, 1978.
- 9 J. Shorster in 'The Chemistry of Sulphones and Sulphoxides,' ed. S. Patai, Z. Rappoport, and C. J. M. Stirling, John Wiley, New York, 1988, p. 483.
- 10 A. Ulman, D. J. Williams, T. L. Penner, D. R. Robello, J. S. Schildkraut, M. Scozzofava, and C. S. Willard, US Patent 4,792,208/1988.
- 11 See e.g. D. R. Robello, *J. Polym. Sci., Polym. Chem. Ed.*, 1990, **28**, 1.

Role of Valency of Copper in the Direct Decomposition of Nitrogen Monoxide over Well Characterized La_{2-x}A'_xCu_{1-y}B'_yO₄

Hiroyuki Yasuda, Noritaka Mizuno, and Makoto Misono*

Department of Synthetic Chemistry, Faculty of Engineering, The University of Tokyo, Hongo, Bunkyo-ku, Tokyo 113, Japan

Catalytic activity is closely related to the valency of copper in the direct decomposition of NO over well characterized La_{2-x}A'_xCu_{1-y}B'_yO₄ catalysts (K₂NiF₄ structure; A' = Sr, B' = Al, Zr, x = 0–1.0, y = 0, 0.2); the formal valency of copper was controlled in the range 1.60–2.30.

Mixed oxides which have the perovskite and related structures have attracted attention as useful catalysts for practical applications and for fundamental studies.¹ It has been reported that Cu-containing compounds such as Cu-ion-exchanged ZSM-5 and Cu-containing oxide showed high catalytic activities for the decomposition of NO.^{2,3} However, little is known of the factors controlling the activities.

We have studied the direct decomposition of NO over La_{2-x}A'_xCu_{1-y}B'_yO₄, in which the valency of copper was controlled by substitution without changing the K₂NiF₄ structure.

The La_{2-x}A'_xCu_{1-y}B'_yO₄ catalysts were prepared by calcining the precipitate from the appropriate mixture of aqueous solutions of the metal acetates at 1123–1273 K for 5–20 h, as