

## Counter-ion influences on the electrical conduction properties of 1,2-dithiolene coordination compounds

**Citation for published version (APA):**

Groeneveld, L. R., Kramer, G. J., Marinelli, von, T. B. L. W., Brom, H. B., Haasnoot, J. G., & Reedijk, J. A. (1987). Counter-ion influences on the electrical conduction properties of 1,2-dithiolene coordination compounds. In P. Delhaes, & M. Drillon (Eds.), *Organic and inorganic low-dimensional crystalline materials : NATO Advanced Research Workshop on Organic and Inorganic Low-Dimensional Crystalline Materials (1987 : Minorca, Spain)* (pp. 349-352). (NATO ASI Series, Series B: Physics; Vol. 168). Plenum Press.

**Document status and date:**

Published: 01/01/1987

**Document Version:**

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

**Please check the document version of this publication:**

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

**Take down policy**

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

COUNTER-ION INFLUENCES ON THE ELECTRICAL CONDUCTION PROPERTIES OF  
1,2-DITHIOLENE COORDINATION COMPOUNDS

L.R. Groeneveld\*, G.J. Kramer\*\*, T.B.L.W. von Marinelli\*,  
H.B. Brom\*\*, J.G. Haasnoot\* and J. Reedijk\*

\* Department of Chemistry, Gorlaeus Laboratories, Leiden  
University, P.O. Box 9502, 2300 RA Leiden, The Netherlands

\*\* Department of Physics, Kamerlingh Onnes Laboratory, Leiden  
University, P.O. Box 9506, 2300 RA Leiden, The Netherlands

INTRODUCTION

The intention of the present study is to investigate the coordination chemistry and the magnetic and conducting properties of polynuclear coordination compounds containing 1,2-dithioleenes. DMIT-based ( $H_2DMIT = 4,5$ -dimercapto-1,3-dithiol-2-thione) complexes have become of particular interest since the discovery of superconductivity in  $(TTF)[Ni(DMIT)_2]_2^{1}$ . With DMIT and related ligands square planar compounds are obtained for  $M = Ni, Cu, Pd$  and  $Pt$ , see Figure 1.


An important and general feature of the above-described compounds is the variety of apparent oxidation states for the metal ions, as well as the fact that these can easily be converted into each other.

RESULTS, DISCUSSION AND CONCLUSIONS

The compound  $(Et_4N)_1[Ni(DMIT)_2]$ , prepared by oxidation by iodine of  $(Et_4N)_2[Ni(DMIT)_2]^{2,3}$ , crystallizes in the space group  $P2_1/n$ , its structure has been solved by X-ray diffraction methods. See Figure 1. for crystallographic parameters and distances. It is a zig-zag chain with the shortest intermolecular distances  $3.8 \text{ \AA}$ .

Oxidation of  $(Et_4N)_2 Pd(DMIT)_2$  with air afforded crystals of  $(Et_4N)_{0.5} [Pd(DMIT)_2]$ , of which the crystal structure was solved as well. Its structural parameters are tabulated in Figure 1. This compound is a two-dimensional  $S\dots S$  network with nearest  $S\dots S$  contacts in the range of  $3.26$  to  $3.72 \text{ \AA}$ .

Both compounds are semiconductors with a linear behaviour of  $\ln \sigma$  vs.  $1/\sqrt{T}$ , see Figure 2. From the single crystal conductivity measurements of several compounds with DMIT can be concluded that the conductivity is strongly dependent on the cation, as well as on the metal atom and its oxidation state (Figure 3).

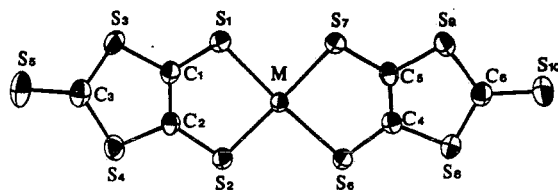

	$[(C_2H_5)_4N]_1Ni(DMIT)_2$	$[(C_2H_5)_4N]_{0.5}Pd(DMIT)_2$
Space group	P 2 <sub>1</sub> /n	P $\bar{1}$
a, Å	7.333(1)	18.873(6)
b, Å	25.734(3)	8.515(3)
c, Å	12.798(4)	6.295(2)
$\alpha$ , (°)	90.0	117.77(9)
$\beta$ , (°)	104.95(2)	96.66(3)
$\gamma$ , (°)	90.0	90.78(3)
Z	4	2
R/R <sub>w</sub>	4.49/5.36	2.89/2.97
M-S1, Å	2.151(4)	2.294(1)
M-S2	2.158(4)	2.308(1)
M-S6	2.159(4)	2.292(1)
M-S7	2.163(4)	2.302(1)
C1-C2	1.34(1)	1.375(5)
C4-C5	1.36(1)	1.401(6)
S1-M-S2, (°)	93.3(1)	90.41(5)
S1-M-S7	87.1(1)	87.84(5)
S2-M-S6	86.0(1)	91.44(5)
S6-M-S7	93.8(2)	90.07(5)

Fig. 1. Molecular structure and structural parameters of  $(Et_4N)_1 Ni(DMIT)_2$  and  $(Et_4N)_{0.5} Pd(DMIT)_2$ .

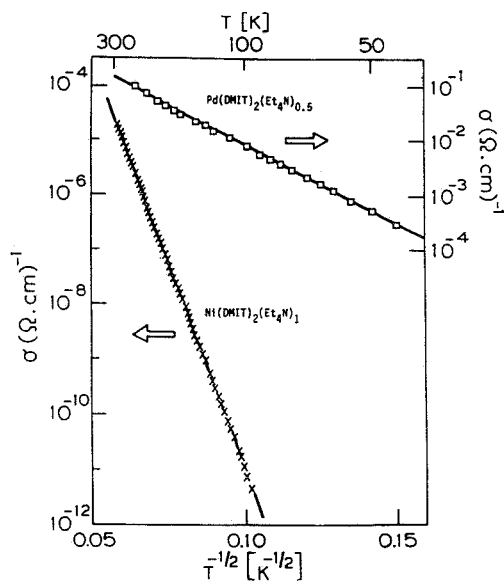


Fig. 2. Conductivity of  $(Et_4N)_1[Ni(DMIT)_2]$  and  $(Et_4N)_{0.5}[Pd(DMIT)_2]$  vs.  $1/\sqrt{T}$ .

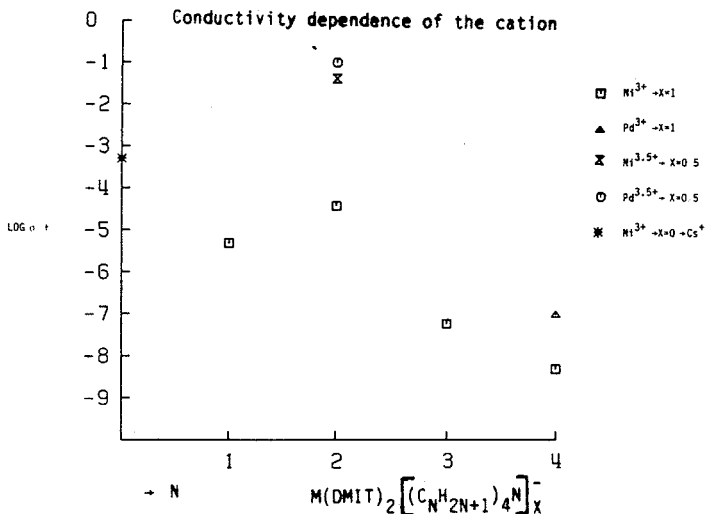


Fig. 3. Conductivity dependence on the cation of  $(cat)_x[M(DMIT)_2]$ . For  $Ni^{3.5+}$  see ref. 4.

The magnetic measurements of the Ni and Pd compounds indicate 1-D behaviour and possibly a small trace of impurities.  $^1H$ -NMR reveals that at low temperature molecular motion of the tetraethylammonium group is still present (Figure 4). This is of particular importance, since the anomalous conductivity behaviour is in general an indication of disorder. In the present compounds disorder may be caused by cationic motion. Because linewidth studies reveal that two cation conformations occur, static disorder might be expected at the lowest temperature.

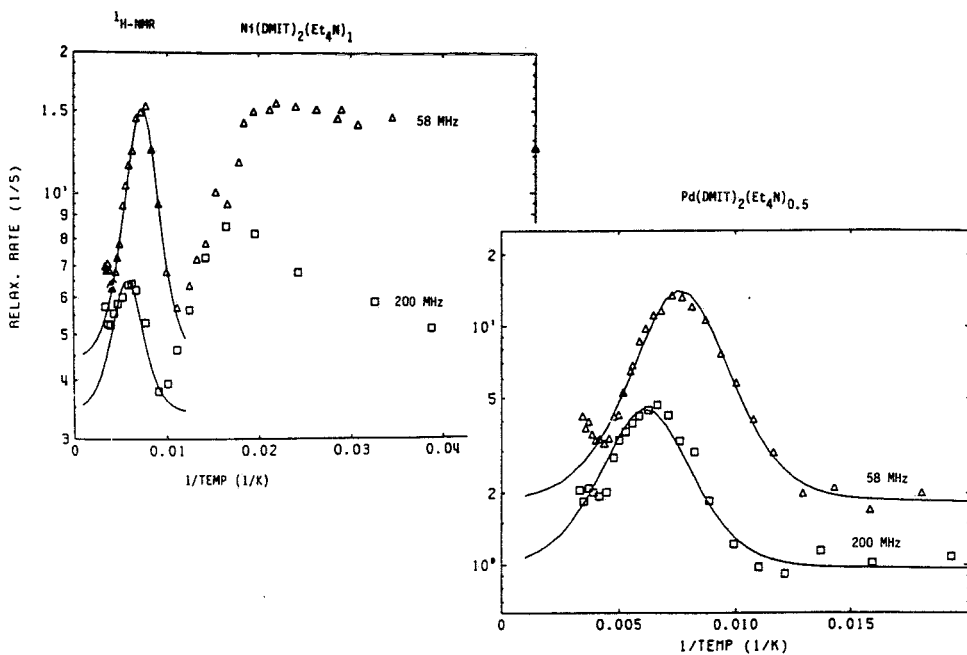


Fig. 4. Proton NMR relaxation rates vs.  $1/T$  of  $(Et_4N)_1[Ni(DMIT)_2]$  and  $(Et_4N)_{0.5}Pd(DMIT)_2$

#### ACKNOWLEDGEMENT

The authors acknowledge the support of the Leiden Materials Science Centre (Werkgroep Fundamenteel Materialenonderzoek).

#### REFERENCES

1. M. Bousseau, L. Valade, J-P. Legros, P. Cassoux, H. Garbauskas and L.V. Interrante, *J. Am. Chem. Soc.* 108: 1908 (1986)
2. L.R. Groeneveld, B. Schuller, G.J. Kramer, J.G. Haasnoot and J. Reedijk, *Recl. Trav. Chim. Pays Bas* 105: 507 (1986)
3. G.J. Kramer, L.R. Groeneveld, J.L. Joppe, H.B. Brom, L.J. de Jongh and J. Reedijk, *Synthetic Metals* 19: 745 (1987)
4. R. Kato, T. Mori, A. Kobayashi, Y. Sasaki and H. Kobayashi, *Chem. Letters*, 1 (1984)