

A novel route towards interface integrity in stretchable electronics

Citation for published version (APA):

Neggers, J., Hoefnagels, J. P. M., & Geers, M. G. D. (2010). *A novel route towards interface integrity in stretchable electronics*. Poster session presented at Mate Poster Award 2010 : 15th Annual Poster Contest.

Document status and date:

Published: 01/01/2010

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy


If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

A novel route towards interface integrity in stretchable electronics

J. Neggers, J.P.M. Hoefnagels and M.G.D. Geers

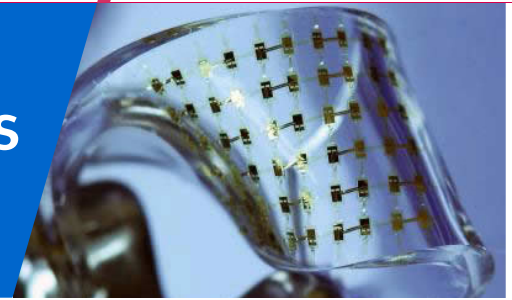

Introduction

Stretchable electronics is a new field aiming to enable a range of bio-compatible futuristic devices (Fig. 1,2). **Interface delamination** is a precursor to the failure of stretchable electronics made of elastically mismatched metal interconnects and rubber matrix materials.

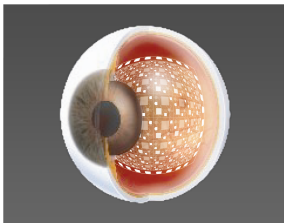


Figure 1: Intraocular retinal sensor array

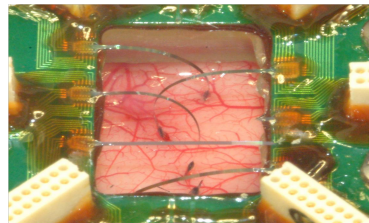


Figure 2: Neural activity monitoring array

Goals

1. Obtain insights in the **macroscopic** delamination mechanics of copper-rubber interfaces.
2. Develop a method to test and characterize these interfaces at **microscopic** scales.

Macroscopic interface testing

Real-time *in-situ* ESEM imaging of the progressing delamination front shows that (Fig. 3) interfaces that have the highest work of separation (G_c) do not have the cleanest surface. Showing that, delamination is a delicate balance between **the forming, elongation and rupture of fibrils** and **interface debonding**.

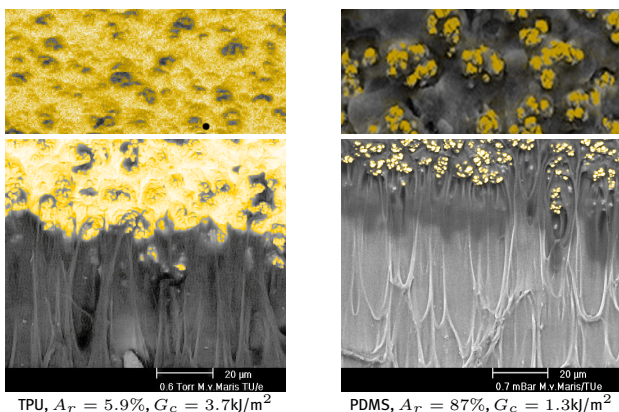


Figure 3: (top) ESEM images of the rubber area fraction A_r on the copper after peeling, rubber is shown in black and copper in yellow. (bottom) Fibrillation of the progressing delamination front.

Microscopic interface testing

The bulge test is used as a loading platform for the stretchable electronics, originally designed to characterize thin films, it is enhanced with global DIC to capture **local stress-strain** information needed to measure inhomogeneous films.

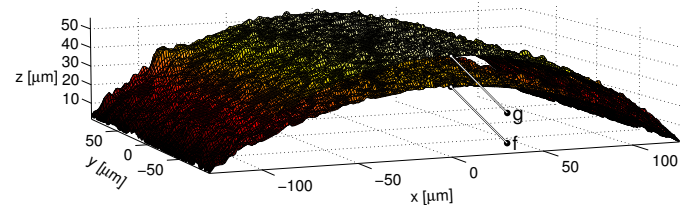


Figure 4: Two measured bulge test profiles f and g at 5% and 10% strain respectively. A pattern is applied on the surface using 80-500 nm Ag particles. In global DIC, the image g is mapped onto f by fitting its deformation $u(x)$ by minimizing $\eta^2 = \int (f(x) - g\{x + u(x)\})^2 dx$.

The quasi 3D data obtained from Confocal (or Atomic Force) Microscopy required a new DIC method because the pattern (Fig. 4), used to correlate with, also moves in the out of plane direction. The **global DIC** method is developed in cooperation with F. Hild.

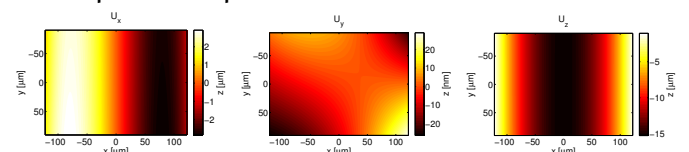


Figure 5: The displacement fields in x , y and z obtained from the global DIC method, using basis functions of the type $\varphi_n = x^a y^b$.

Conclusions

- Fibrillation of the rubber is observed, where $50\mu\text{m}$ long fibrils are formed.
- A delicate balance arises between the rupture of the fibrils and delamination of the interface.
- The rubber fraction on the delaminated Cu surface decreases with increasing rubber toughness and/or decreasing interface adhesion.
- A 2D^+ global DIC method is developed, useful for confocal, interferometry, and atomic force microscopy data.
- Which is very robust, even with 5% strain steps, yielding continuous full field displacement fields (Fig. 5), with sub pixel displacement resolution.