

Characterization of oriented semi-crystalline polymer samples (2)

Citation for published version (APA):

Housmans, J. W., Peters, G. W. M., & Meijer, H. E. H. (2004). *Characterization of oriented semi-crystalline polymer samples (2)*. Poster session presented at Mate Poster Award 2004 : 9th Annual Poster Contest.

Document status and date:

Published: 01/01/2004

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Characterization of Oriented Semi-Crystalline Polymer Samples (2).

J.W. Housmans, G.W.M. Peters, H.E.H. Meijer

Eindhoven University of Technology, Department of Mechanical Engineering

Introduction

Numerical models to predict properties of polymer products have to be validated with detailed experimental results on the level of modeling (in our case structural data). A powerful method to obtain morphological data is X-ray diffraction, but this is not a standard laboratory set-up and measuring time at special X-ray facilities like the ESRF in Grenoble is expensive. Easy-to-use techniques available in most polymer laboratories are optical light microscopy and Fourier Transform Infra Red (FT-IR) [1]. In this study these techniques are compared with X-ray diffraction.

Experimental set-up

Samples from isotactic polypropylene (iPP) with dimensions 2x12x135 [mm], Fig. 1, are made on a modified capillary rheometer.

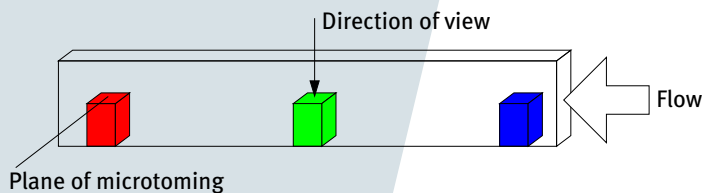


Figure 1 iPP sample. Measuring techniques are used at 3 different positions, blue = GATE, green = MID and red = END.

Methods

The following methods are used to characterize the final micro-structure:

- Optical light microscopy (LM): visualizing different layers [1].
- Fourier Transform Infra Red (FT-IR): determining crystallinity and orientation [1].
- Wide Angle X-ray Diffraction (WAXD): determining crystallinity, orientation and phases [2,3].

Crystallinity: ratio between the area under the crystalline peaks and the total area (crystalline and amorphous phase).

$$\square X_c = \frac{A_{cr}}{A_{total}}$$

Crystalline phase Hermans' orientation factor:

- Apply Wilchinsky's method [2] to the 2D diffraction patterns.

Crystal phase(s):

- Each phase has distinctive peaks, corresponding to crystal planes.

Results

Fig. 2 shows the cross section at the mid position of the sample (left), the 2D WAXD patterns of the oriented, outer layer and the core (mid) and the normalized, integrated intensity versus 2θ (right).

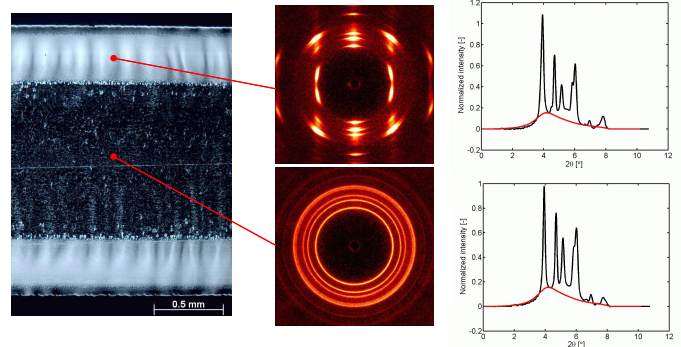


Figure 2 Micrographs at the mid position (left), 2D WAXD patterns (mid) and normalized, integrated intensity curves (right).

In Fig. 2 (right) the peaks clearly indicate α -phase, the most common crystal form in iPP. In the oriented layer also the β -phase is observed (shoulder left of the second peak) which normally appears under a strong imposed flow [3].

Fig. 3 shows the crystallinity, measured with both WAXD and FT-IR (left) and Hermans' orientation factor (right) over the thickness of the sample. The difference in crystallinity is due to the fact that the 2nd order reflection of the (110) crystal plane is taken into account (extra contribution) and that the samples have experienced secondary crystallization in time.

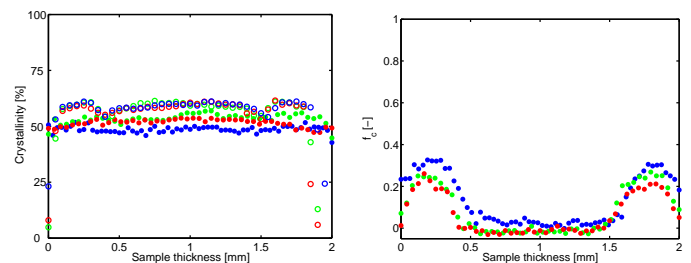


Figure 3 Crystallinity (left) and f_c , only FT-IR, (right) over the thickness of the sample (open symbol: WAXD, closed symbol: FT-IR).

Conclusions

- FT-IR gives results comparable to WAXD, with the benefit that orientation can be determined more easily.

Future work

- Study the influence of shear rate and temperature by varying the processing conditions.
- Validate the numerical model with this experimental data.

References:

- [1] HOUSMANS, J.W. ET AL.: *MaTe postercontest 2003*
- [2] SCHRAUWEN, B.A.G.: *PhD thesis (2003)*
- [3] BURGH, F.P.T.J.. VAN DER: *PhD thesis (2002)*