

New horizons in computer analysis of damage and fracture in quasi-brittle materials

Citation for published version (APA):

Borst, de, R., Carmeliet, J., & Sluys, L. J. (1994). New horizons in computer analysis of damage and fracture in quasi-brittle materials. In Z. P. Bazant, & Z. Bittnar (Eds.), *Fracture and damage in quasibrittle structures : experiment, modelling and computer analysis : proceedings of the US-Europe workshop on fracture and damage in quasibrittle structures, held in Prague, Czech Republic, 21-23 September 1994* (pp. 359-372). E&FN SPON.

Document status and date:

Published: 01/01/1994

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

32 NEW HORIZONS IN COMPUTER ANALYSIS OF DAMAGE AND FRACTURE IN QUASI-BRITTLE MATERIALS

(Invited Lecture)

R. de BORST

Faculty of Civil Engineering, Delft University of Technology, and
Faculty of Mechanical Engineering, Eindhoven University of
Technology, The Netherlands

J. CARMELIET

Department of Civil Engineering, Catholic University of Leuven,
Belgium

J. PAMIN and L.J. SLUYS

Faculty of Civil Engineering, Delft University of Technology, Delft,
The Netherlands

Abstract

Continuum approaches are reviewed which can properly model localised deformations that act as a precursor to final fracture in quasi-brittle materials. Next, one such higher-order damaging continuum model is combined with a stochastic approach to describe the heterogeneity in quasi-brittle materials.

Keywords: Higher-order continua, softening, localisation, finite element analysis, random fields.

1 Introduction

Failure in quasi-brittle and frictional materials involves localisation of deformation, i.e., we observe that at incipient failure small zones of highly strained material develop abruptly while the remainder of the body experiences virtually no additional straining. Examples are cracks in concrete, shear bands in soils and rock faults. Experiments show that these localisation phenomena are accompanied by a sharp decrease of the load-carrying capacity. This phenomenon is commonly named strain softening and leads to ill-posed boundary value problems in standard continuum theories, since in quasi-static problems ellipticity of the governing set of differential equations is lost and in dynamic problems hyperbolicity is lost. In numerical simulations this leads to an extreme mesh sensitivity in terms of fineness and direction of the grid lines. To remedy this improper behaviour the standard continuum model must be enriched by adding higher-order terms, either spatially or in the time domain. These techniques are commonly referred to as regularisation methods.

In this contribution we shall scrutinise the possibilities of using enriched continuum theories (non-local and gradient theories) to remedy this deficiency of the

standard continuum. For dynamic problems the possibility of adding viscosity to the constitutive model will also be investigated. Finite element analyses are presented to illustrate some of the approaches.

Another important property of these materials is the inherent heterogeneity at a relatively large scale. This heterogeneity may imply that the exact failure mode can be highly dependent upon the precise flaw distribution. To model this inhomogeneity stochastic material properties must be assumed in numerical simulations. However, the use of a stochastic approach does not resolve the above mentioned issue of the change of character of the governing differential equations during progressive damage. A simulation technique that describes the true failure process properly within the framework of continuum mechanics must incorporate both a regularisation of the standard continuum during progressive damage and a stochastic strength distribution. This statement will be substantiated in this contribution. To do so we will present finite element analyses of direct tension tests with a local damage model and with a nonlocal damage model. In both cases deterministic as well as stochastic calculations using a Monte Carlo technique will be presented for two different levels of discretisation. The randomness in the damage process will be introduced by considering the initial damage as a univariate homogeneous random field, describing the continuous spatial distribution and the autocorrelation. The relation between the relative variation of the correlation distance and the internal length scale of the nonlocal continuum will also be discussed.

2 Cracking, damage and localisation of deformation

A major problem when using a standard, rate-independent continuum for modelling degradation processes such as smeared cracking is that beyond a certain level of damage accumulation the governing set of partial differential equations changes type. In the static case the elliptic character of the set of partial differential equations is lost, while, on the other hand, in the dynamic case we observe a change of a hyperbolic set into an elliptic set. In both cases the rate boundary value problem becomes ill-posed and numerical solutions suffer from spurious mesh sensitivity.

The inadequacy of the standard, rate-independent continuum to model failure zones correctly is due to the fact that *force-displacement relations* measured in testing devices are simply mapped onto *stress-strain curves* by dividing the force and the elongation by the original load-carrying area and the original length of the specimen, respectively. This is done without taking into account the changes in the micro-structure that occur when the material is so heavily damaged as in fracture processes. Therefore, the mathematical description ceases to be a meaningful representation of the physical reality.

To solve this problem one must either introduce additional terms in the continuum description which reflect the changes in the micro-structure that occur during fracture, or one must take into account the viscosity of the material. In both cases the effect is that the governing equations do not change type during the damage evolution process and that physically meaningful solutions are obtained

for the entire loading range (regularisation procedures). It is emphasised that although concrete can be regarded as a disordered material, the introduction of stochastic distributions of defects does not replace the need for the introduction of regularisation procedures. For a proper description of failure in concrete both enhancements are necessary: enrichment of the continuum by higher-order terms, either in space or in time, and the introduction of the occurrence of material flaws as a stochastic quantity.

2.1 The standard continuum for localised failure computations

The essential deficiency of the standard continuum model can be demonstrated simply by the example of a simple bar loaded in uniaxial tension [1]. Let the bar be divided into m elements. Now suppose that one element has a tensile strength that is marginally below that of the other $m - 1$ elements. Upon reaching the tensile strength of this element failure will occur. In the other, neighbouring elements the tensile strength is not exceeded and they will unload elastically. The result in terms of the displacement of the end of the bar is fully dominated by the discretisation, and convergence to a 'true' post-peak failure curve does not seem to occur. In fact, it does occur, as the failure mechanism in a standard continuum is a line crack with zero thickness. The finite element solution of our continuum rate boundary value problem simply tries to capture this line crack, which results in localisation in one element, irrespective of the width of this element. The result on the load-average strain curve is obvious: for an infinite number of elements ($m \rightarrow \infty$) the post-peak curve doubles back on the original loading curve. Numerous numerical examples for all sorts of materials exist which further illustrate the above argument. From a physical point of view the above behaviour is unacceptable and when we adhere to continuum descriptions one must enrich the continuum by adding higher-order terms, either in space or in time, which can accommodate narrow zones of highly localised deformations.

2.2 The fracture-energy 'trick'

As an intermediate solution between using the standard continuum model and adding higher-order terms a number of authors [2-4] have proposed to regard the area under the softening curve as a material parameter, namely the fracture energy G_f :

$$G_f = \int \sigma du = \int \sigma \varepsilon(s) ds \quad (1)$$

Assuming a constant softening modulus h and adopting a constant strain distribution over the band, we now obtain that

$$\frac{\dot{u}/L}{\dot{\sigma}} = \frac{1}{E} + \frac{2G_f}{Lf_t^2}, \quad (2)$$

which shows that the solution in the post-peak regime is now only dependent upon the Young's modulus E , the fracture energy G_f , the tensile strength f_t ,

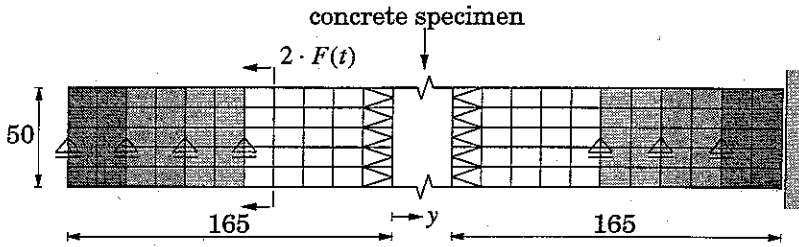
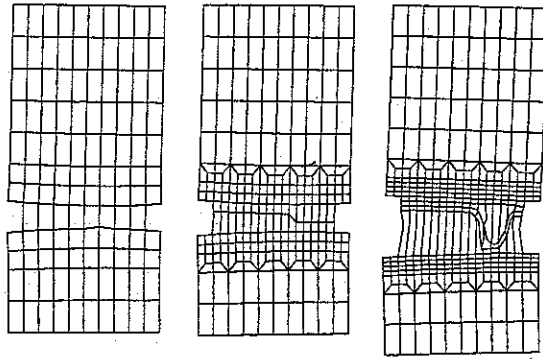


Figure 1: Numerical model of Split-Hopkinson bar

Figure 2: Displacements of concrete specimen ($t = 0.50 \cdot 10^{-3}$ s)

and the length of the bar L . When we prescribe the fracture energy G_f as an additional material parameter the global load-displacement response can become insensitive to the discretisation. However, locally nothing has altered and localisation still takes place in one row of elements. This is logical, since the loss of ellipticity occurs at a local level, even though the energy that is dissipated remains constant by adapting the softening modulus to the element size. For numerical simulations this implies for instance that severe convergence problems are usually encountered if the mesh is refined or if in addition to matrix failure interface debonding between matrix and fibres is modelled by inserting interface elements in the numerical model. Also, the frequently reported observation still holds that the localisation zones are biased by the discretisation and tend to propagate along the mesh lines. This can be nicely demonstrated with the example of impact loading a concrete specimen in a Split-Hopkinson device, Fig. 1 [5]. The results for the deformed specimen at failure are shown in Fig. 2 for three different discretisations in the region between the notches. We observe a clear spurious localisation pattern with the localisation concentrated in a single band of elements which generally follows the mesh lines and occasionally jumps from one row to the next and back without any physical motivation.

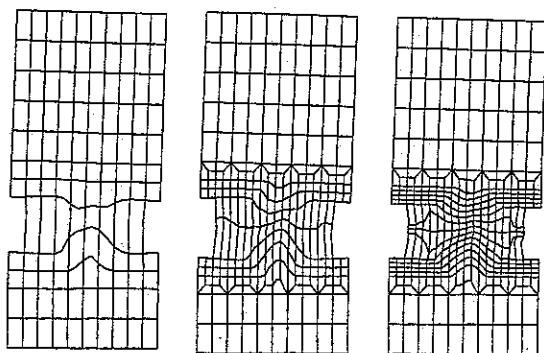


Figure 3: Displacements for rate-dependent analysis at $t = 0.45 \cdot 10^{-3}$ s.

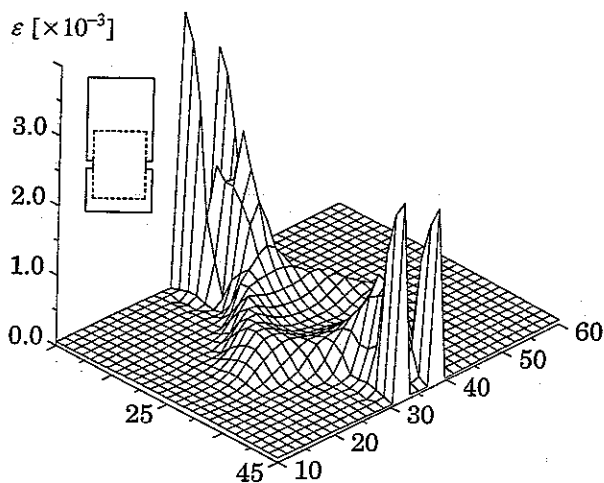


Figure 4: Axial strain profile in the notched area at $t = 0.45 \cdot 10^{-3}$ s.

2.3 Rate-dependent continuum models

From a physical point of view the introduction of rate dependence is perhaps the most natural way to regularise ill-posed initial value problems which arise because of the introduction of damage or frictional effects. Here we adopt a simple, linear rate-dependent smeared crack model as developed by Sluys [5]. In it the major principal stress degrades according to

$$\sigma = f_t + h\varepsilon^i + m \frac{\partial \varepsilon^i}{\partial t}, \quad (3)$$

with ε^i the inelastic strain, h the softening modulus and m a rate-sensitivity parameter.

Using the rate-dependent smeared crack model as defined in Eq. 3 the experiment of a concrete specimen under impact loading in a Split-Hopkinson bar (cf. Figs 1 and 2) has been reanalysed. The incremental displacement patterns are

shown in Fig. 3. The most striking difference with the displacement pattern of Fig. 2 is that localisation now does not proceed along the element lines and is no longer confined to the rows of elements between the notches. This is even more obvious when the strains in the vertical direction are plotted (ϵ_{yy}) as has been done in Fig. 4. We observe a clear branching of the cracks.

2.4 Non-standard continuum models

The deficiency of the standard continuum model with regard to properly describing strain localisation can also be overcome by introducing higher-order terms in the continuum description, which are thought to reflect the microstructural changes that take place at a level below the continuum level. Examples of such changes are void formation in metals and crack bridging phenomena in the context of concretes [6]. Essentially, one then departs from the concept of a 'simple' solid which has been the starting point for virtually all modern developments in continuum mechanics. A number of suggestions have been put forward for non-standard continuum descriptions that are capable of properly incorporating failure zones. These include the non-local models [7,8], the use of the Cosserat continuum [9-11] and the gradient models [11-16].

Non-local models can either be introduced in a plasticity-based formalism or in a damage-based format. The latter approach has gained most popularity. In fact, it has been shown in [17] that non-local plasticity models are extremely difficult to implement properly. Non-local damage theory follows standard elasticity-based damage mechanics in that it introduces an internal variable, the damage parameter ω , which accounts for degradation of the elastic stiffness matrix D :

$$\sigma = (1 - \omega)D^e \epsilon \quad (4)$$

In this isotropic elasticity-based damage theory the damage variable ω grows from zero to one (complete loss of integrity). Damage growth is possible if the damage loading function

$$f(\tilde{\epsilon}, \kappa) = \tilde{\epsilon} - \kappa \quad (5)$$

vanishes. In particular, the damage loading function f and the rate of damage growth $\dot{\omega}$ have to satisfy the discrete Kuhn-Tucker conditions

$$f \leq 0, \quad \dot{\omega} \geq 0, \quad f\dot{\omega} = 0. \quad (6)$$

In (5) $\tilde{\epsilon}$ is the equivalent strain, which can be a function of the strain invariants, the principal strains as in Mazars [18,19]:

$$\tilde{\epsilon} = \sqrt{\sum_{i=1}^3 \langle \epsilon_i \rangle^2} \quad (7)$$

with ϵ_i the principal strains, and $\langle \epsilon_i \rangle = \epsilon_i$ if $\epsilon_i > 0$ and $\langle \epsilon_i \rangle = 0$ otherwise, or the local energy release due to damage. The parameter κ starts at a damage

threshold level κ_0 and is updated by the requirement that during damage growth $f = 0$. Damage growth occurs according to an evolution law $F(\bar{\epsilon})$ such that

$$\omega = F(\bar{\epsilon}) \tag{8}$$

The salient departure from the local damage theory occurs when the local damage parameter ω in the above identities is replaced by an averaged or non-local value $\bar{\omega}$, such that

$$\bar{\omega}(\mathbf{x}) = \frac{1}{V_g} \int_V \omega(\mathbf{x} + \boldsymbol{\tau})g(\boldsymbol{\tau})dV, \quad V_g = \int_V g(\boldsymbol{\tau})dV \tag{9}$$

with $\boldsymbol{\tau}$ the separation vector between the points \mathbf{x} and $\mathbf{x} + \boldsymbol{\tau}$, and g an attenuating weighting function, e.g., the error function

$$g(\boldsymbol{\tau}) = \exp(-|\boldsymbol{\tau}|^2/2l^2) \tag{10}$$

in which the non-local parameter l has the role of an internal length scale.

Non-local damage theory suffers from the drawback that the issue of additional boundary conditions for this higher-order continuum is still not completely settled, thus rendering the theory incomplete. Also, they seem less amenable to an efficient implementation, thus making large-scale computations less feasible. It is for these reasons that gradient models, in which the higher-order gradients of internal parameters are considered instead of averaging one or more internal parameters, are here considered as a serious alternative for non-local approaches.

Below we shall restrict ourselves to a brief discussion and an example of a gradient-enhanced Rankine flow plasticity theory [20-22]. The essential feature of gradient plasticity theory is that the yield function f not only depends upon the stress $\boldsymbol{\sigma}$ and an equivalent inelastic strain measure γ^i , but that there is also a dependence upon gradients of γ^i , e.g., the Laplacian:

$$f = f(\boldsymbol{\sigma}, \gamma^i, \nabla^2 \gamma^i) \tag{11}$$

If we denote by σ_1 the major principal stress and by $\bar{\sigma}$ the instantaneous tensile strength, then

$$f = \sigma_1 - \bar{\sigma}(\gamma^i, \nabla^2 \gamma^i) \tag{12}$$

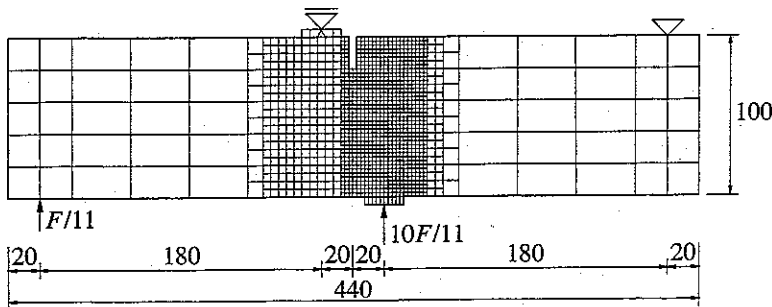


Figure 5: Loading configuration and discretisation of SEN beam

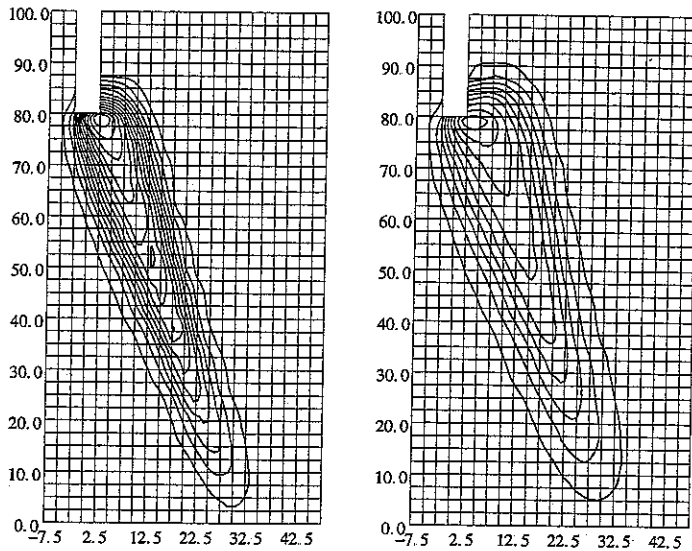


Figure 6: Contour plots of equivalent fracture strain at the final load level for $l=2$ mm (left) and $l=3$ mm (right)

When it is further assumed that the dependence upon the gradient term is linear—the simplest possible case—then Eq. (12) reduces to

$$f = \sigma_1 - \bar{\sigma}(\gamma^i) - \bar{c}\nabla^2\gamma^i \quad (13)$$

In the example calculations that will be presented below \bar{c} has been taken proportional to the rate of softening: $\bar{c} = l^2\partial\bar{\sigma}/\partial\gamma^i$. The material parameter l has the dimension of length and represents the gradient influence. For $l = 0$ the standard Rankine flow theory is recovered.

The gradient-dependent Rankine plasticity model has been applied to mixed-mode crack propagation in a Single-Edge Notched plain concrete beam (Iosipescu geometry). The experimental results are from Schlangen [23]. The loading configuration including some aspects of the numerical discretisation is shown in Fig. 5. The loading plates have been included in the discretisation and have also been modelled with reduced integrated eight-noded quadrilaterals, but with a higher stiffness. Details of the employed mixed finite element formulation are given in [21,22].

The material data for the concrete, determined as the average experimental values are: Young's modulus $E = 35$ GPa, Poisson's ratio $\nu = 0.2$, the tensile strength $f_t = 3.0$ MPa and fracture energy $G_f = 0.1$ N/mm. For this value of the fracture energy two different length scales l have been considered, namely $l = 3$ mm and subsequently $l = 2$ mm. The differences with respect to the width of the fracture process zone are shown in the contour plots of the equivalent fracture strain of Fig. 6. Provided that the fracture energy is kept constant a variation of the internal length parameter l does, however, not affect the load-CMSD diagrams shown in Fig. 7, neither does the discretisation influence the

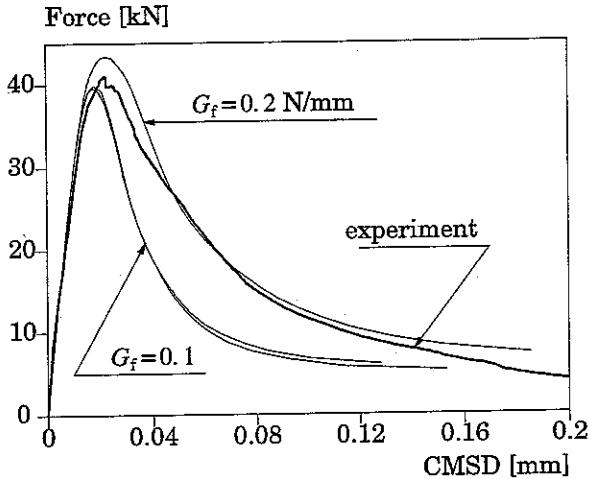


Figure 7: Computed and experimentally obtained load-CMSD diagrams

results for this level of mesh refinement. Since the computed load-CMSD diagram is too brittle compared with the experiment another analysis with a higher value of the fracture energy (0.2 N/mm) has also been conducted, Fig. 7.

3 Stochastic methods and damage evolution

A fundamental question regarding application of random fields to localisation phenomena is whether a statistical description of the standard continuum resolves the ill-posedness that arises after the onset of localisation. This question becomes imperative especially if we consider that the description of a heterogeneous continuum by correlated random variables introduces a length parameter in the form of the correlation length θ analogous to the introduction of an internal length scale l in non-standard continua. The correlation length θ is a measure for the rate of fluctuations of the random field and may significantly influence the damage process and global response of the structure. The example of a tensile specimen with random initial damage is well suited to study this fundamental issue. We assume that the initial damage threshold is randomly distributed over the solid and can be represented by a non-Gaussian correlated random field. For the non-Gaussian field a three-parameter Weibull distribution function is assumed:

$$f(K_0) = \lambda \mu (K_0 - K_0^{min})^{\mu-1} \exp[-\lambda (K_0 - K_0^{min})^\mu] \quad (14)$$

with λ, μ the Weibull-parameters and K_0^{min} the lower bound of the initial damage threshold. The material parameters are taken from Carmeliet [24] and have been assigned the following values: $\lambda = 6.56 \cdot 10^5$, $\mu = 1.6$, $K_0^{min} = 0.66 \cdot 10^{-4}$. An inverse fitting procedure, comparing the numerical responses to the experimental distribution of tensile strength and energy dissipation, was used for the proper identification of the material parameters [24]. The field is assumed to

be homogeneous and isotropic, which implies that the autocorrelation coefficient function can be expressed in terms of the separation vector τ between the points \mathbf{x} and $\mathbf{x} + \tau$. The autocorrelation coefficient function is assumed to be of the same form as the weight function of the nonlocal damage model:

$$\rho(\tau) = \exp(-|\tau|^2/2d^2) \quad (15)$$

with d a parameter. In case of a squared exponential function as in Eq. (15), d is related to the correlation length θ by $d = \theta/\sqrt{2}$. The correlation length θ is defined here as the length over which the autocorrelation coefficient function drops to a small value, say e^{-1} .

For finite element analysis involving random field properties, it is necessary to discretise the continuous random field into random vector representations. This discretisation involves the division of the structure into several stochastic elements and the representation of the stochastic field within the elements by random variables. In this paper, we will use the midpoint method [25]. To accurately describe the random field, the size of the stochastic element is taken less than one half of the correlation length θ . A sample tensile specimen with initial damage is generated following a cutting procedure. Firstly a sample of $200 \times 200 \text{ mm}^2$ with random initial damage is digitally generated according to the method of Yamazaki and Shinozuka [26]. Out of this sample a tensile specimen with dimensions of $100 \times 25 \text{ mm}^2$ is cut at a random position. This cutting procedure obviates the problem of defining statistical boundary conditions or considering boundary layer effects. In the reference simulations the correlation parameter has been assigned the value $d = 5 \text{ mm}$ or, equivalently, a correlation length $\theta = 7 \text{ mm}$. For the finite element discretisation two different meshes have been used: 8×32 and 16×64 elements. During the discretisation process, the size of the stochastic element is not changed. This means that a stochastic element is

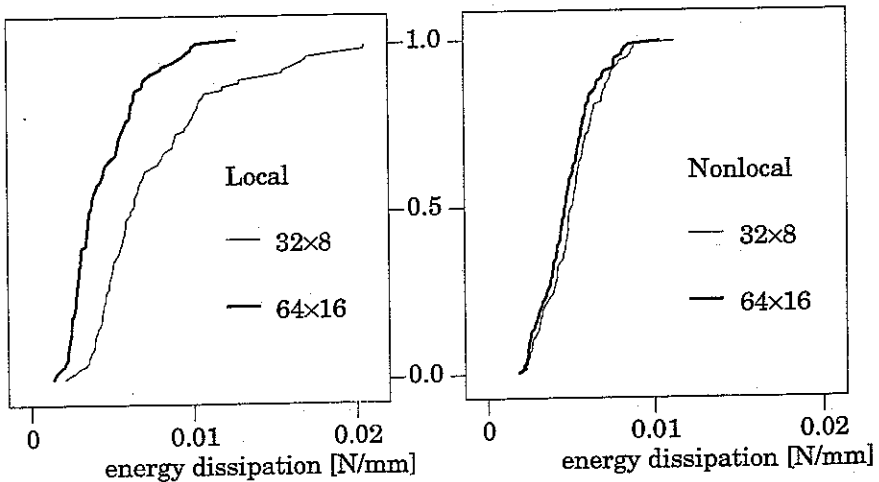


Figure 8: Cumulative distribution of the energy dissipation during failure. Left: local damage model. Right: non-local damage model.

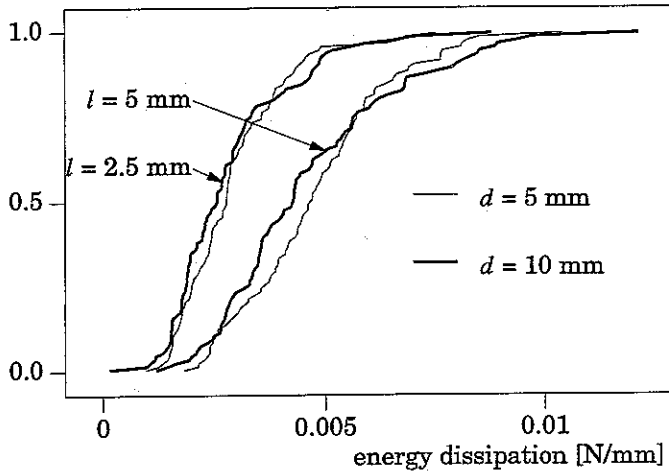


Figure 9: Cumulative distribution of the energy dissipation during failure for the non-local continuum. Influence of the original length scale l vs the correlation parameter d .

either a block of one or of four finite elements with identical random properties. Furthermore, we assume a constant linear softening diagram with a softening modulus $h = -0.1E$ and an elastic modulus $E = 20000 \text{ MPa}$.

The differences between the local and nonlocal stochastic models become most clear when comparing the total energy dissipation during damage for the two different finite element discretisations. Fig. 8 shows the cumulative distributions calculated from the responses of 100 samples using the Monte Carlo technique. The results for the local damage model, obtained for a less steep softening branch, $h = -0.01E$, are clearly mesh dependent: a decreasing energy dissipation is observed upon mesh refinement. On the contrary, the results for the nonlocal stochastic model show a perfect agreement for both discretisations. These observations correspond fully with the findings for deterministic models.

So far, we have shown that a stochastic continuum description of damage localisation must include a regularisation technique to prevent loss of well-posedness of the rate boundary value problem. A major problem now lies in combining the two different length parameters introduced in a physically realistic manner: the internal length scale l of the nonlocal continuum and the correlation length θ of the random field. Both length parameters result from the transition of a micro-level to a macro continuum level. While the internal length l depends merely on the typical size of defects (or aggregates), the correlation length θ depends on the size as well on the frequency, i.e. the distance between successive defects. This important issue will be illustrated by means of an example. Fig. 9 compares the cumulative distribution of the energy dissipation for various values of the internal length scale of the nonlocal model ($l = 5 \text{ mm}$ and $l = 2.5 \text{ mm}$) and of the correlation parameter ($d = 5 \text{ mm}$ and $d = 10 \text{ mm}$). Otherwise the standard material data have been used. The figure suggests that variations of l have a

larger influence on the cumulative distribution of the energy dissipation than the correlation length θ .

4 Some reflections on future work

In this contribution current developments have been reviewed for modelling localisation and fracture via continuum methods. Various promising approaches exist, but there is no such a thing like a panacea which cures the shortcomings of standard, rate-independent continua upon the introduction of strain softening and/or non-symmetry in the constitutive rate equations.

In the authors' opinion the most pressing issues that require further attention for failure computations are:

- The proper determination of the additional model parameters that emerge in the higher-order and rate-dependent continuum models when compared to the classical approach. Especially in higher-order continua this problem is not solved easily, since the additional parameters are not directly derivable from elementary tests such as uniaxial or triaxial tension or compression tests. Even if one would be able to carry out a test on a perfect specimen, so that homogeneous deformations would occur throughout the entire loading programme, these parameters could not be measured because for homogeneous deformations there is no effect of the higher-order continuum models. Therefore, one must proceed in a semi-inverse manner, whereby the experimental results of different types of tests are fitted in the post-peak regime.
- The steep strain gradients that occur in higher-order and rate-dependent continua during failure require that very fine meshes are used to capture the failure mode properly. If such analyses are to be carried out on nowadays' or even tomorrow's computers, then the use of adaptive mesh refinement techniques or spectral overlay methods is a *conditio sine qua non*. A problem is the development of proper criteria for mesh refinement in inelastic, non-standard continua. Although necessary this will probably not prove an easy task.
- The combination of stochastic methods with higher-order continuum models for frictional and damaging materials.

Acknowledgements

Financial support of the Commission of the European Communities through the Brite-EuRam programme (project BE-3275) and the Human Capital and Mobility Programmes (A.L.E.R.T. Geomaterials), the Netherlands Academy of Arts and Sciences and the Dutch Technology Foundation (project DCT72.1405) is gratefully acknowledged.

References

- [1] de Borst, R. (1986) *Non-linear analysis of frictional materials*, Dissertation, Delft University of Technology, Delft.
- [2] Bažant, Z.P. and Oh, B. (1983) Crack band theory for fracture of concrete, in *Materials and Structures*, Vol. 16, 155-177.
- [3] Pietruszczak, S. and Mróz, Z. (1981) Finite element analysis of deformation of strain softening materials, in *International Journal for Numerical Methods in Engineering*, Vol. 17, 327-334.
- [4] Willam, K. (1984) Experimental and computational aspects of concrete fracture, in *Proceedings International Conference on Computer Aided Analysis and Design of Concrete Structures*, (eds. F. Damjanič et al.), Pineridge Press, Swansea, pp. 33-70.
- [5] Sluys, L.J. (1992) *Wave propagation, localisation and dispersion in softening solids*, Dissertation, Delft University of Technology, Delft, 1992.
- [6] van Mier, J.G.M. (1991) Mode-I fracture of concrete: discontinuous crack growth and crack interface grain bridging, *Cement and Concrete Research*, Vol. 21, 1-15.
- [7] Pijaudier-Cabot, G. and Bažant, Z.P. (1987) Nonlocal damage theory, *ASCE Journal of Engineering Mechanics*, Vol. 113, 1512-1533.
- [8] Bažant, Z.P. and F.B. Lin (1988) Non-local yield limit degradation, in *International Journal for Numerical Methods in Engineering*, Vol. 26, 1805-1823.
- [9] Mühlhaus, H.-B. and Vardoulakis, I. (1987) The thickness of shear bands in granular materials, *Geotechnique*, Vol. 37, 271-283.
- [10] de Borst, R. (1991) Simulation of strain localisation: A reappraisal of the Cosserat continuum, *Engineering Computations*, Vol. 8, 317-332.
- [11] de Borst, R. (1993) A generalisation of J_2 -flow theory for polar continua, in *Computer Methods in Applied Mechanics and Engineering*, Vol. 103, 347-362.
- [12] Aifantis, E.C. (1984) On the microstructural origin of certain inelastic models, *Journal of Engineering Materials and Technology*, Vol. 106, 326-334.
- [13] Schreyer, H.L. and Chen, Z. (1986) One-dimensional softening with localization, *ASME Journal of Applied Mechanics*, Vol. 53, 791-799.
- [14] Lasry, D. and Belytschko, T. (1988) Localization limiters in transient problems, *International Journal of Solids and Structures*, Vol. 24, 581-597.
- [15] Mühlhaus, H.-B. and Aifantis, E.C. (1991) A variational principle for gradient plasticity, *International Journal of Solids and Structures*, Vol. 28, 845-858.
- [16] de Borst, R. and Mühlhaus, H.-B. (1992) Gradient-dependent plasticity: Formulation and algorithmic aspects, *International Journal for Numerical Methods in Engineering*, Vol. 35, 521-539.
- [17] de Borst, R., Sluys, L.J., Pamin, J. and Mühlhaus, H.-B. (1993) Fundamental issues in finite element analyses of localisation of deformation, *Engineering Computations*, Vol. 10, 99-121.
- [18] Mazars, J. (1984) *Application de la mécanique de l'endommagement au comportement non linéaire et à la rupture du béton de structure*, These d'Etat, Université Paris VI, Paris.

- [19] Mazars, J. and Pijaudier-Cabot, G. (1989) Continuum damage theory—application to concrete, *ASCE Journal of Engineering Mechanics*, Vol. 115, 345-365.
- [20] Pamin, J. (1993) *Mesh sensitivity in gradient dependent softening plasticity: II. Application of Rankine and Drucker-Prager yield criteria*, Report 25-2-93-2-14, Delft University of Technology, Delft.
- [21] Pamin, J. (1993) *Mesh sensitivity in gradient dependent softening plasticity: III. Finite element formulations*, Report 25-2-93-2-15, Delft University of Technology, Delft.
- [22] Pamin, J. and de Borst, R. (1994) Gradient plasticity and finite elements in the simulation of concrete fracture, in *Computational Modelling of Concrete Structures*, (eds. H. Mang, N. Bičanič and R. de Borst), Pineridge Press, Swansea, pp. 393-402.
- [23] Schlangen, E. (1993) *Experimental and numerical analysis of fracture processes in concrete*, Dissertation, Delft University of Technology, Delft.
- [24] Carmeliet, J. (1992) *Durability of fiber-reinforced renderings for outside insulation: a probabilistic approach based on the nonlocal continuum damage mechanics (in Dutch)*, Dissertation, Catholic University of Leuven, Leuven.
- [25] Der Kiureghian, A. and Ke, J.-B. (1988) The stochastic finite element method in structural reliability, *Probabilistic Engineering Mechanics*, Vol. 3, 83-91.
- [26] Yamazaki, F. and Shinozuka, M. (1988) Digital generation of non-Gaussian stochastic fields, *ASCE Journal of Engineering Mechanics*, Vol. 114, 1183-1197.