

## Strong human tissue-engineered blood vessels : cultured in weeks instead of months

***Citation for published version (APA):***

Stekelenburg, M., Rutten, M. C. M., Baaijens, F. P. T., & Snoeckx, L. H. E. H. (2006). *Strong human tissue-engineered blood vessels : cultured in weeks instead of months*. Poster session presented at Mate Poster Award 2006 : 11th Annual Poster Contest.

***Document status and date:***

Published: 01/01/2006

***Document Version:***

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

***Please check the document version of this publication:***

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

***General rights***

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

***Take down policy***

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

# Strong Human Tissue-Engineered Blood Vessels: Cultured in Weeks instead of Months

M. Stekelenburg<sup>a</sup>, M.C.M. Rutten<sup>a</sup>, F.P.T. Baaijens<sup>a</sup>, L.H.E.H. Snoeckx<sup>b</sup>

<sup>a</sup>Department of Materials Technology, Department of Biomedical Engineering, Eindhoven University of Technology

<sup>b</sup>Department of Physiology, Maastricht University

## Introduction

Vascular tissue engineering represents a promising approach for the development of living small diameter blood vessels that can be used for replacement therapy, including coronary artery bypass grafting (CABG). So far, the culture of strong human tissue-engineered (TE) blood vessels required long culture times, up to several months, whether or not combined with telomerase gene therapy. In the present study we describe the culture of strong, living, human TE blood vessels in 28 days.

## Materials & Methods

Blood vessel constructs (n=8) were fabricated from P4HB coated PGA (Fig. 1). Myofibroblasts were harvested from the saphenous vein of CABG patients and the tubular constructs were seeded using fibrin as a cell carrier.

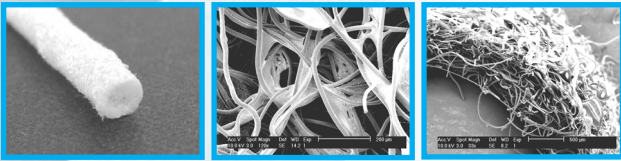


Figure 1: Blood vessel construct of P4HB coated PGA

The TE blood vessels were cultured in a bioreactor for 4 weeks. To improve the tissue formation, tubular constructs were constrained in axial direction and dynamically strained in circumferential direction (Fig. 2). The properties of the engineered blood vessels were compared to those of native CABG grafts, i.e., the left internal mammary artery (LIMA, n=3) and the saphenous vein (SV, n=5).

## Results

Living TE blood vessels after 4 weeks of in-vitro culture (Fig. 3) showed dense tissue formation. Uniaxial tensile tests showed that the vessels were significantly stronger and stiffer in axial than in circumferential direction (Fig. 4).



Figure 2: bioreactor set-up

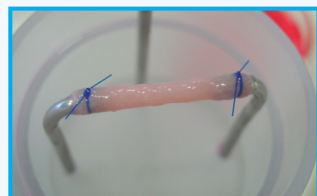


Figure 3: Living TE blood vessel in bioreactor after 4 weeks of in-vitro culture

The burst pressure of the TE vessels was  $906 \pm 123$  mmHg (n=4). The experiments showed that the strain at 100 mmHg was approximately 10%. The compliance of the vessels was in the order of 0.03%/mmHg.

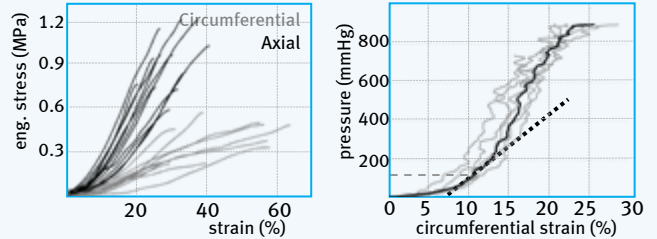


Figure 4: Uniaxial tensile tests (left) and burst pressure measurement (right) of TE vessels

Histological examination revealed significant amounts of collagen in the TE blood vessel, although less, and not as organized as in the native vessels. (Fig. 5)

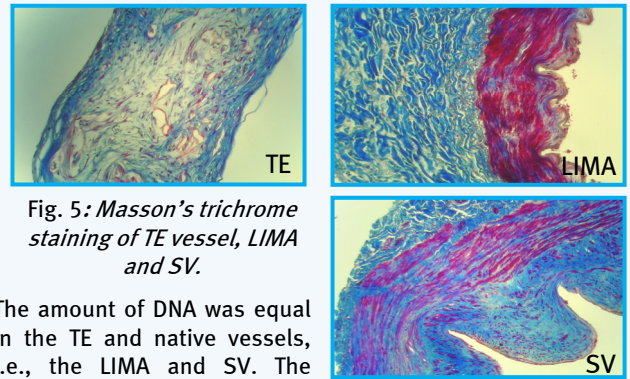


Fig. 5: Masson's trichrome staining of TE vessel, LIMA and SV.

The amount of DNA was equal in the TE and native vessels, i.e., the LIMA and SV. The amount of glycosaminoglycans was higher in the TE constructs than in the native vessels, whereas the amount of hydroxyproline, as a measure for collagen, was 50% of native (Fig. 6).

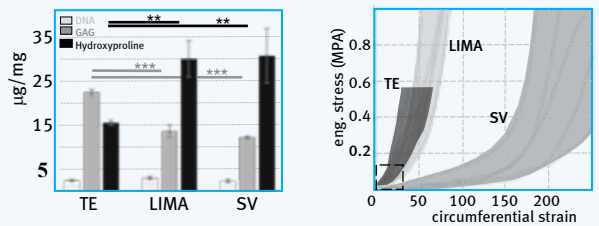


Figure 6: DNA, GAG and hydroxyproline content of TE and native vessels (left). Circ. tensile tests at low stress values (right).

Tensile tests showed that the mechanical behavior of the TE blood vessels resembled that of native arteries in the physiologically relevant range (Fig. 6, dashed box).

## Conclusions

In this study we present the strongest human TE blood vessels in a 28d-culture period, in which the scaffold no longer contributed to the mechanical properties. Mechanical behavior of the TE vessels resembled that of native arteries in the physiologically relevant range.