

Particle growth of nano-silica below the isoelectric point

Citation for published version (APA):

Lazaro, A., & Brouwers, H. J. H. (2015). *Particle growth of nano-silica below the isoelectric point*. P1.282-. Poster session presented at conference; Fourth International Conference on Multifunctional, Hybrid and Nanomaterials (Hybrid Materials 2015); 2015-03-09; 2015-03-13.

Document status and date:

Published: 01/01/2015

Document Version:

Accepted manuscript including changes made at the peer-review stage

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Particle growth of nano-silica below the isoelectric point

Dr. Alberto Lazaro
a.lazaro.garcia@tue.nl
Prof. Dr. Ir. H.J.H. Brouwers


Eindhoven University of Technology, The Netherlands

Current production of nano-silica


Nano-silica is one of the compounds that is boosting the field of nano-materials with an annual rise of 5.6 % reaching 2.8 million metric tons in 2016 and with a total value of \$6.4 billion [1]. The current production methods involve steps with high temperatures. To reach these temperatures huge amounts of fuel are consumed making these processes: a) **non-sustainable** because of the scarcity of fuels; b) not environmentally friendly because of the huge amount of CO₂ emissions released; and c) expensive because of the fuel price.

Production of olivine nano-silica

Initial research has demonstrated that nano-silica can be produced by dissolving olivine in acid at **low temperatures**. The acid is neutralized by olivine mineral, according to:

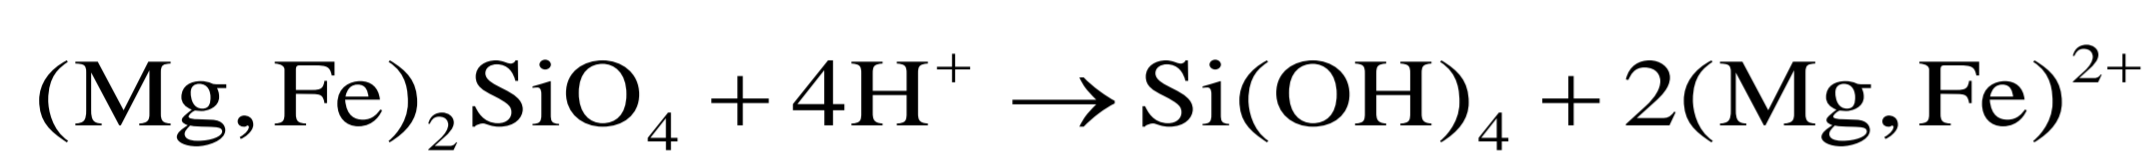

The neutralization yields a slurry consisting of magnesium/iron salts, silica and unreacted silicates (more details in [2, 3, 4]).

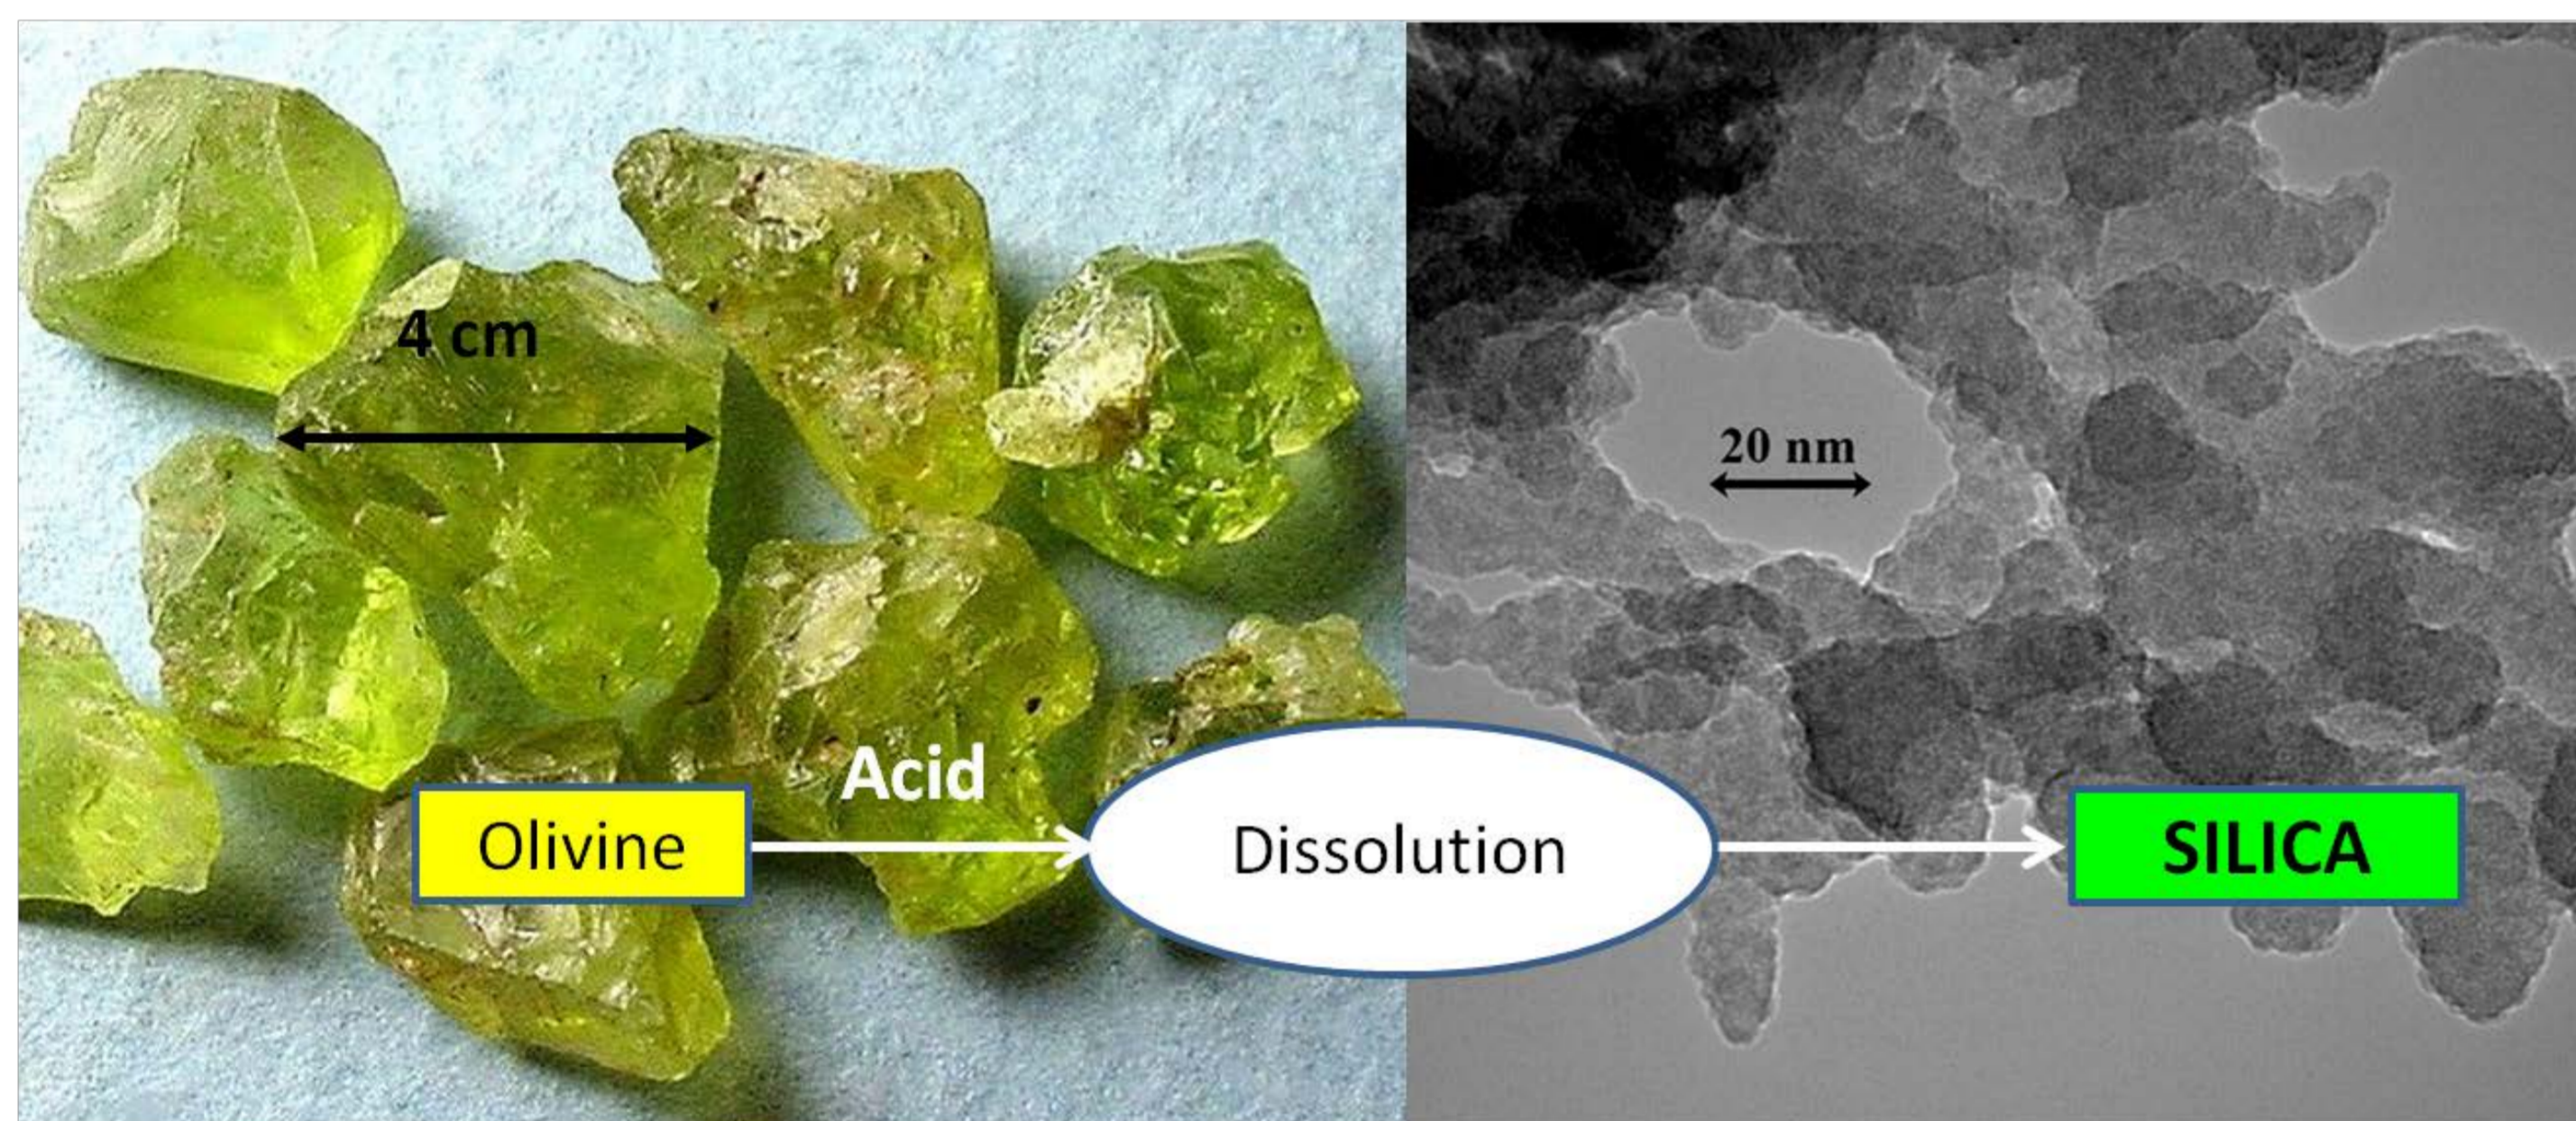

Featured article and cover of the Chemical Engineering Journal [2]: *The properties of amorphous nano-silica synthesized by the dissolution of olivine.*

Experimental Methods

The **particle growth** of silica during the olivine dissolution (**negative pH**) was investigated using olivine. These experiments were carried out at 20 °C in a vigorously stirred reactor of two liters with sulfuric acid. The experimental variables were the concentration of sulfuric acid and surface area of olivine (see Table 1). The silica particle size (or cluster size) was measured with a Malvern ZS after passing the samples through a filter of 1 μm in order to avoid the presence of olivine particles.

Table 1. Conditions of the nano-silica polymerization experiments.

Experiment	m _{ol} (g/L)	[Si] _{eq} (mmol/L)	d ₅₀ (μm)	SSA _G (m ² /g)	SA _T (m ²)	[H ⁺] (mol/L)	T (°C)
NS-PO-2	50	307	116	0.09	9.0	4.0	20
NS-PO-3	50	307	116	0.09	9.0	2.0	20
NS-PO-4	100	613	116	0.09	18.0	3.9	20
NS-PO-5	70	429	116	0.09	12.6	3.9	20
NS-PO-6	70	429	116	0.09	12.6	4.1	20

[Si]_{eq} refers to the equivalent concentration of silica from the olivine amount, SSA_G geometric specific surface area, and SA_T total geometric surface area of the olivine in the reactor.

Results

Figure 1 the concentration of silica produced during the dissolution of olivine in the polymerization experiments. Figure 2 presents the average particle size of silica over time.

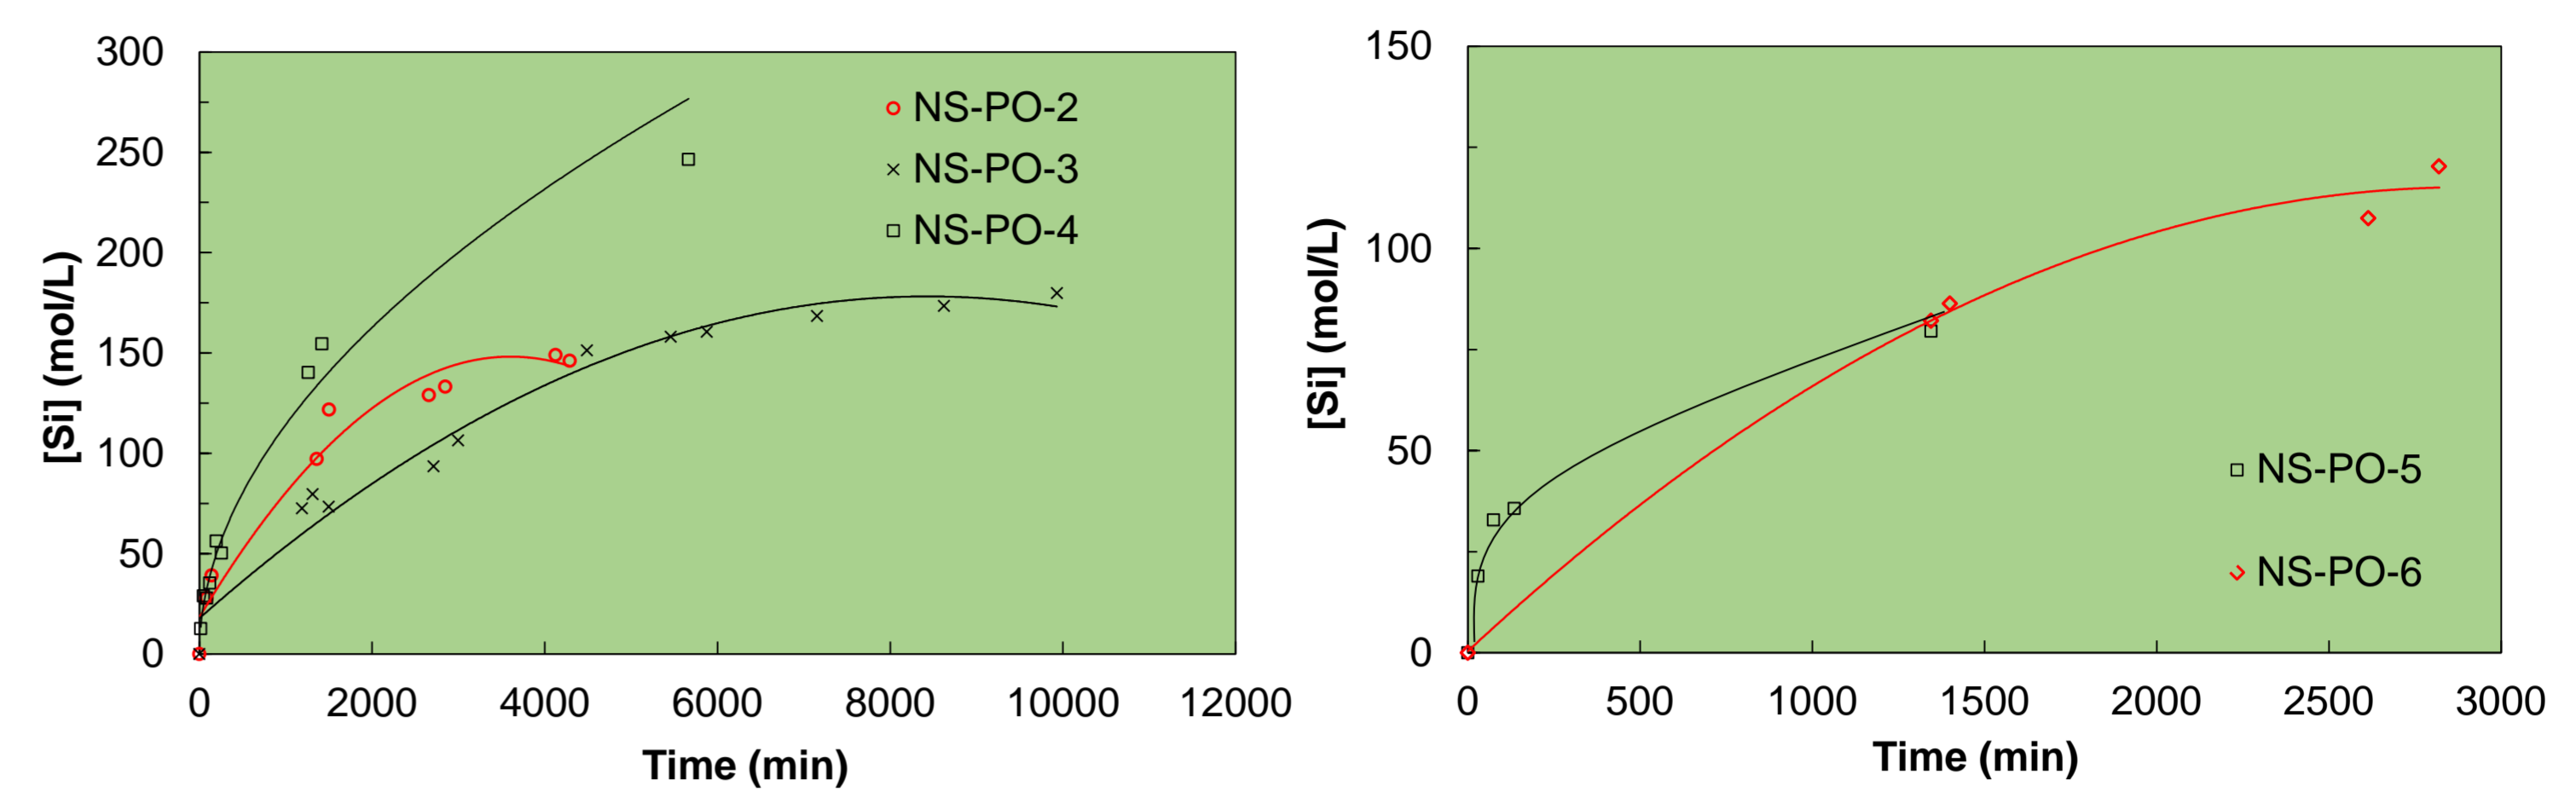


Figure 1. Silica produced over time for the particle growth experiments.

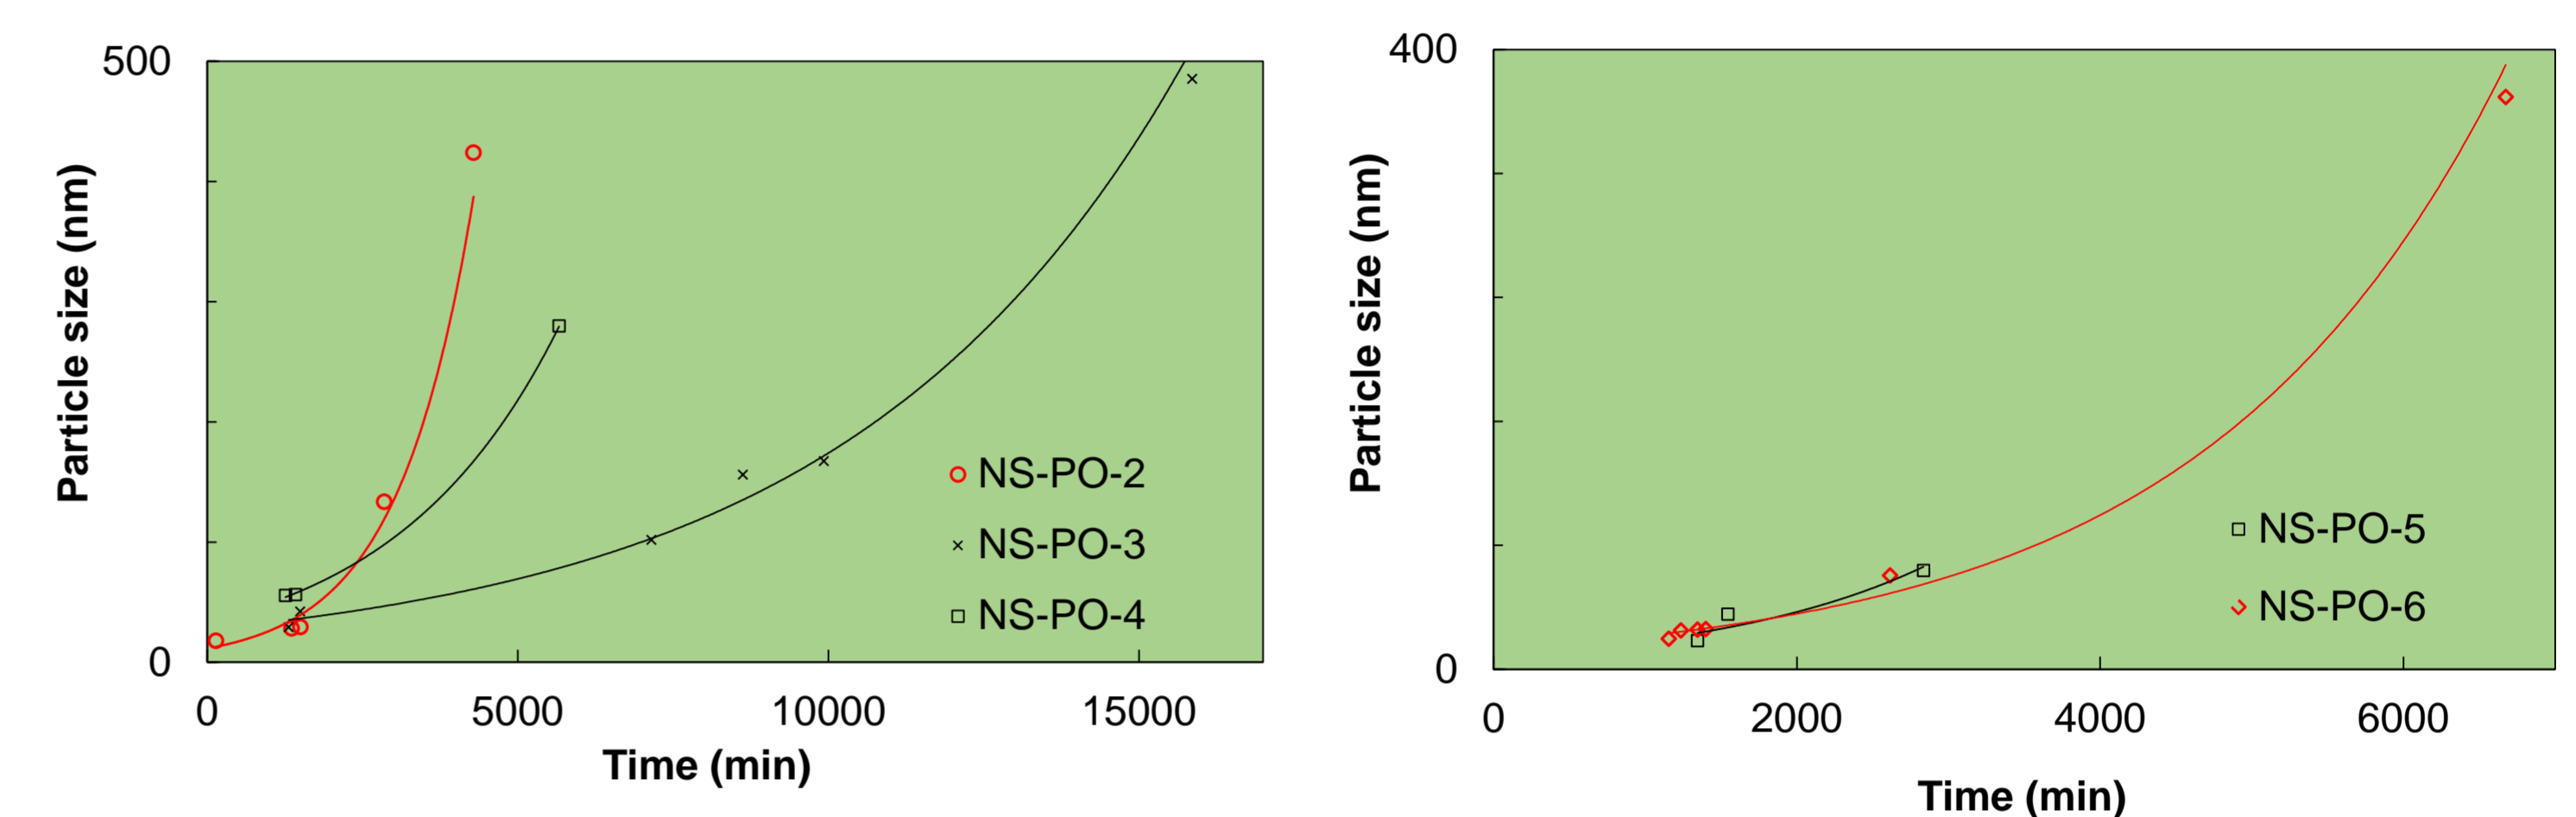


Figure 2. Growth of silica particles during the dissolution of olivine.

The cluster size of silica increased exponentially with time. The growth rate of silica accelerated with the increase of the hydrogen ion concentration and amount of nano-silica released.

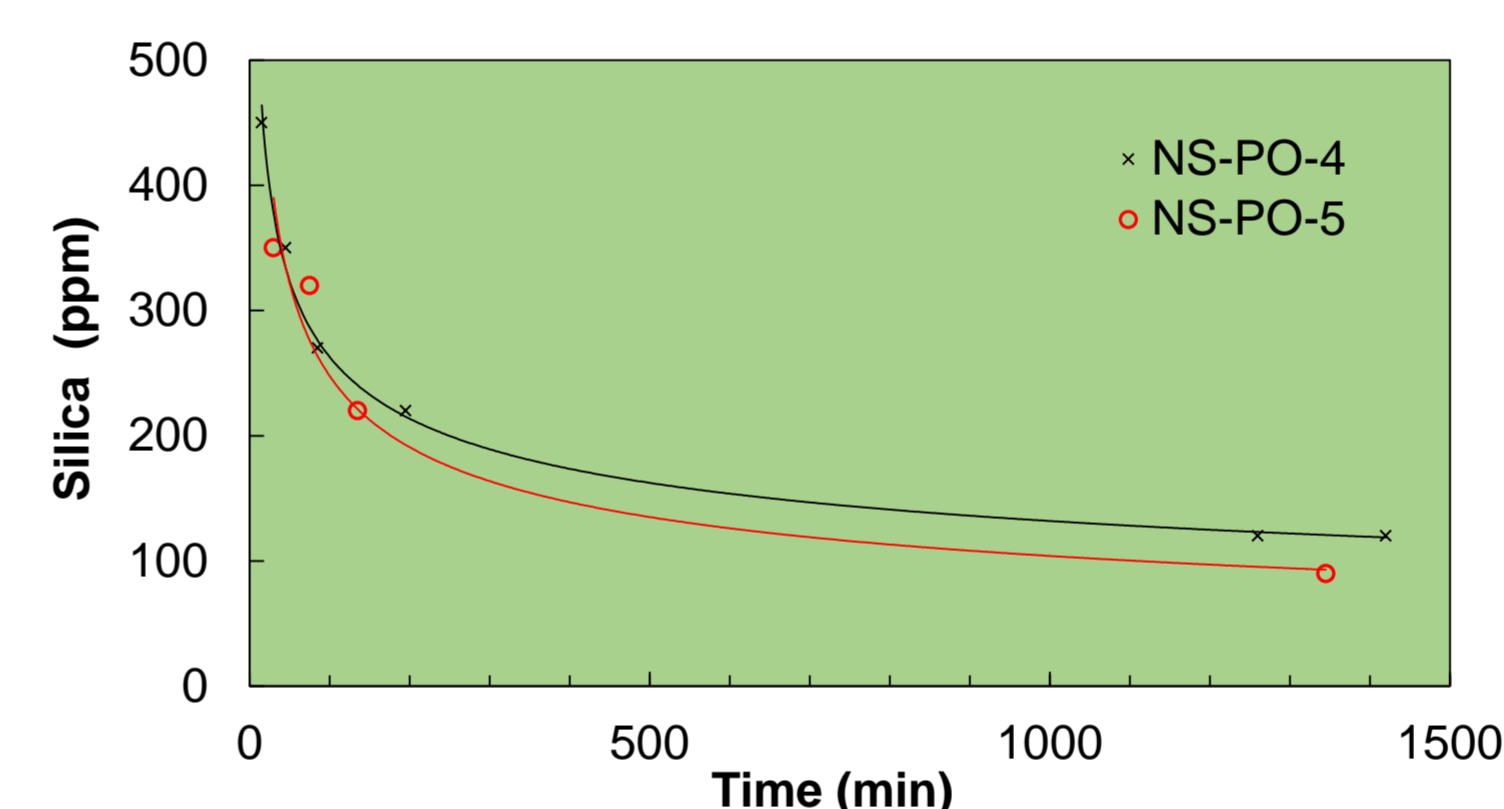


Figure 3. Concentration of soluble silica in the solution at early reaction times.

The evolution of the silica solubility reaches a maximum at the early stages of the experiment. Subsequently, the concentration of soluble silica slowly decreases over time due to the nucleation and formation of colloids, reaching a constant value around 100 ppm.

Conclusions

The cluster size of olivine silica grows up to 420 nm after 4300 minutes of reaction at 20 °C in 2M H₂SO₄ solution. The particle growth should be much faster under the production conditions of olivine nano-silica (90 °C and 3M H₂SO₄), which cause olivine to dissolve within 4-6 hours.

Olivine nano-silica does not gel. This behavior of olivine silica can be due to three reasons:

- 1) silica polymerizes fast at 90 °C in 3M H₂SO₄ solution, forming particles above 100 nm in a short time;
- 2) the concentration of small silica colloids is low;
- 3) the reactor is vigorously stirred.

References

- [1] Freedonia. World Specialty Silicas Market., (2010).
- [2] A. Lazaro, H. J. H. Brouwers, G. Quercia Bianchi, J. W. Geus. Chem. Eng. J. (2012).
- [3] A. Lazaro, M.C. Van de Griend, H. J. H. Brouwers, J. W. Geus. Micropor. Mesop. Mat. (2013).
- [4] A. Lazaro, et al. Applied Geochemistry (2015).