

2022

## Charge Transfer Mediated Triplet Excited State Formation in Donor-Acceptor-Donor BODIPY: Application for Recording of Holographic Structures in Photopolymerizable Glass

Tatsiana Mikulchyk

*Technological University Dublin*, tatsiana.mikulchyk@tudublin.ie

Safakath Karuthedath

*King Abdullah University of Science and Technology*

Catherine S.P. De Castro

*King Abdullah University of Science and Technology*

*See next page for additional authors*

Follow this and additional works at: <https://arrow.tudublin.ie/cieoart>



Part of the [Atomic, Molecular and Optical Physics Commons](#), and the [Materials Chemistry Commons](#)

### Recommended Citation

Mikulchyk, Tatsiana; Karuthedath, Safakath; De Castro, Catherine S.P.; Buglak, Andrey A.; Sheehan, Aimee; Wieder, Aaron; Laquai, Frédéric; Naydenova, Izabela; and Filatov, Mikhail, "Charge Transfer Mediated Triplet Excited State Formation in Donor-Acceptor-Donor BODIPY: Application for Recording of Holographic Structures in Photopolymerizable Glass" (2022). *Articles*. 104.

<https://arrow.tudublin.ie/cieoart/104>

This Article is brought to you for free and open access by the Centre for Industrial and Engineering Optics at ARROW@TU Dublin. It has been accepted for inclusion in Articles by an authorized administrator of ARROW@TU Dublin. For more information, please contact [arrow.admin@tudublin.ie](mailto:arrow.admin@tudublin.ie), [aisling.coyne@tudublin.ie](mailto:aisling.coyne@tudublin.ie), [gerard.connolly@tudublin.ie](mailto:gerard.connolly@tudublin.ie), [vera.kilshaw@tudublin.ie](mailto:vera.kilshaw@tudublin.ie).



This work is licensed under a [Creative Commons Attribution-NonCommercial 4.0 International License](#)  
Funder: Technological University Dublin; Kazan Federal University

---

## Authors

Tatsiana Mikulchyk, Safakath Karuthedath, Catherine S.P. De Castro, Andrey A. Buglak, Aimee Sheehan, Aaron Wieder, Frédéric Laquai, Izabela Naydenova, and Mikhail Filatov

# Charge Transfer Mediated Triplet Excited State Formation in Donor-Acceptor-Donor BODIPY: Application for Recording of Holographic Structures in Photopolymerizable Glass

Tatsiana Mikulchyk,<sup>a</sup> Safakath Karuthedath,<sup>b</sup> Catherine S. P. De Castro,<sup>b</sup> Andrey A. Buglak,<sup>c,d</sup> Aimee Sheehan,<sup>e</sup> Aaron Wieder,<sup>e</sup> Frédéric Laquai,<sup>b</sup> Izabela Naydenova<sup>a</sup> and Mikhail A. Filatov<sup>e\*</sup>

Donor-acceptor-donor BODIPY triads bearing anthracene or pyrene as electron donating subunits were prepared through a stepwise synthesis. Photoinduced electron transfer and formation of long-lived triplet excited states *via* spin-orbit charge transfer intersystem crossing (SOCT-ISC) was studied by steady-state and ultrafast pump-probe spectroscopy and further supported by DFT computations. New BODIPYs were found to form triplet states and sensitize singlet oxygen in both polar and non-polar solvents which is unusual for photosensitizers operating *via* SOCT-ISC. BODIPY-anthracene triad (**ABA**) was used as a photosensitizer component in a photopolymerizable glass that was prepared by a four-step sol-gel process. **ABA** in combination with N-phenylglycin (NPG) showed the ability to initiate a free-radical polymerization of methacrylate monomers under 532 nm irradiation thus allowing for holographic recording of diffractive structures. High diffraction efficiency (up to 87%) obtained for **ABA**-NPG containing glass as compared to a reference diiodo-BODIPY (**I<sub>2</sub>BDP**) demonstrates for the first time that heavy-atom-free SOCT-ISC photosensitizers can efficiently operate in the solid state.

## Introduction

The development of photonic technologies for health, energy and communication creates a need for novel functional dyes with optimized excited state properties to meet new and demanding criteria. Triplet photosensitizers (PSs) are organic dyes showing rapid intersystem crossing (ISC) and forming long-lived excited states.<sup>1</sup> Such dyes have found multiple uses in photocatalysis,<sup>2</sup> photodynamic therapy (PDT),<sup>3</sup> photovoltaics<sup>4</sup> and triplet-triplet annihilation up-conversion (TTA-UC),<sup>5</sup> where long-lived triplet excited states are required for efficient harvesting of light energy. A common approach for the enhancement of ISC in organic chromophores relies on the introduction of heavy atoms into the structure, such as halogens or transition metals, which promote ISC *via* spin-orbital interactions.<sup>6</sup> However, the incorporation of heavy

atoms results in high cost of synthesis, increased toxicity and shortening of the triplet state lifetimes.<sup>7</sup> Therefore, replacing of costly transition metal complexes with heavy-atom-free organic PSs has drawn considerable attention and alternative approaches for promoting ISC in organic chromophores have been actively studied.<sup>8</sup>

The formation of triplet excited states in electron donor-acceptor molecules *via* the process of spin-orbit charge transfer intersystem crossing (SOCT-ISC) has attracted particular attention. In these systems, photoinduced electron transfer between the donor and acceptor subunits leads to formation of a charge-transfer state (<sup>1</sup>CT), which further undergoes charge recombination into the lowest triplet excited state (T<sub>1</sub>). SOCT-ISC has been observed in donor-acceptor dyads based on BODIPYs<sup>9</sup> and other difluoroboron complexes,<sup>10</sup> metal dipyrrens,<sup>11</sup> biphenyls,<sup>12</sup> naphthalimides,<sup>13</sup> perylenimides,<sup>14</sup> Nile Red derivatives<sup>15</sup> and *spiro* rhodamines.<sup>16</sup> Many reported molecular systems undergoing SOCT-ISC exhibit triplet quantum yields that are comparable or even higher than those of transition metal complexes and halogenated dyes. Other important advantages include synthetic accessibility, low toxicity, high singlet oxygen quantum yields (Φ<sub>Δ</sub>), long triplet excited state lifetimes and intense visible light absorption. Due to these advantages, heavy-atom-free donor-acceptor PSs gained increasing attention in applications where contamination with transition metals may not be suitable, e.g., biomedical and electronic applications. In particular, such dyes have been proven to be successful as catalysts for photocontrolled polymerization through an oxidative quenching mechanism.<sup>17</sup>

<sup>a</sup> Centre for Industrial and Engineering Optics, School of Physics and Clinical and Optometric Sciences, College of Science and Health, Technological University Dublin, City Campus, Grangegorman, Dublin 7, Ireland

<sup>b</sup> King Abdullah University of Science and Technology (KAUST), KAUST Solar Center (KSC), Physical Sciences and Engineering Division (PSE), Material Science and Engineering Program (MSE), Thuwal 23955-6900, Kingdom of Saudi Arabia

<sup>c</sup> Faculty of Physics, Saint-Petersburg State University, University Emb. 7-9, 199034 St. Petersburg, Russia

<sup>d</sup> Institute of Physics, Department of Quantum Electronics and Radiospectroscopy, Kazan Federal University, Kremlevskaya 18, Kazan, 420008, Russia

<sup>e</sup> School of Chemical and Pharmaceutical Sciences, Technological University Dublin, City Campus, Grangegorman, Dublin 7, Ireland

\*Electronic Supplementary Information (ESI) available: synthetic procedures and analytical data for new compounds; optical spectra; computation details; sol-gel preparation and holographic recording procedure.

E-mail: mikhail.filatov@tudublin.ie

Volume holographic optical elements are critically important for information storage,<sup>18,19</sup> augmented reality displays,<sup>20,21</sup> solar energy harvesting,<sup>22,23</sup> and LED light management technologies.<sup>24</sup> Photopolymerization is one of the most convenient processes for creating holographic microstructures in the volume of photosensitive materials as it can be spatially and temporally controlled.<sup>25,26,27</sup>

Microstructures created using this method represent holographic optical elements with high efficiency (up to 100 %) and tunable selectivity (angular bandwidth varying in the range from a fraction of a degree to tens of degrees and spectral bandwidth varying from a few to hundreds of nanometres).<sup>28,29</sup> A widely used type of photoinitiating system for holographic recording relies on the combination of a photosensitizer and a co-initiator component, which forms free radicals under light irradiation. Photosensitizers, such as methylene blue<sup>30</sup> and xanthene dyes,<sup>31</sup> are regularly employed in photoinitiating systems. However, their performance is not always satisfactory in terms of diffraction efficiency of the resulting holographic structures, presumably due to insufficient photostability and short excited state lifetimes.<sup>32</sup> Taking into account the SOCT-ISC photosensitizers' excellent optical characteristics and tunable properties, their use for holographic recording could allow to enhance photosensitivity of the photopolymerizable material and improve the resulting diffraction efficiency. To the best of our knowledge, such dyes have not yet been tested in this process.

Among potential limitations for using SOCT-ISC dyes in photopolymerization is the inherent dependence of triplet state formation *via* this mechanism on parameters of the environment, in particular its polarity<sup>33</sup> and viscosity.<sup>34</sup> Although, solvent-independent PSs operating *via* SOCT-ISC are highly desirable, so far, only a few examples of such systems have been reported. Zhao and co-workers described carbazole–anthracene–BODIPY triads in which the carbazole unit was used as the secondary electron donor besides the anthryl moiety.<sup>35</sup> These systems exhibited  $\Phi_{\Delta}$  values almost independent of the solvent polarity in contrast to donor–acceptor BODIPY dyads featuring SOCT-ISC. Recently, Durka and co-workers reported spiro 9-borafluorene complexes undergoing SOCT-ISC while not exhibiting solvent polarity dependence of  $\Phi_{\Delta}$  values.<sup>36</sup>


Although predicting the efficiency of SOCT for a given structure in different media is still challenging, recently, we performed the first quantitative structure-property relationship (QSPR) study of these systems and developed a method for predicting singlet oxygen generation quantum yields for heavy-atom-free BODIPYs in different solvents based on a combination of quantum mechanical molecular descriptors and topological descriptors.<sup>37</sup> QSPR analysis shows that structures containing a higher number of electron donor/acceptor subunits, e.g., donor-acceptor-donor (D-A-D) and acceptor-donor-acceptor

triads, in general exhibit less pronounced solvent dependence of triplet state formation compared to D-A dyads. Such triads have been actively studied as materials for photovoltaics<sup>38</sup> and it has been demonstrated that intramolecular charge transfer (ICT) in these systems is faster than in D-A dyads.<sup>39</sup> Such triads also show weaker dependence of charge transfer on solvent polarity and exhibit efficient ICT even in non-polar solvents. Inspired by these observations, herein we investigated the possibility to attenuate the solvent polarity-dependence of triplet formation through SOCT-ISC in BODIPY by introducing two electron donating groups. For this study, we designed new triads by functionalizing the BODIPY core with anthracene or pyrene groups in positions 2 and 6 to facilitate the electron transfer. These newly synthesized triads were characterized using different spectroscopic techniques, demonstrating efficient charge transfer and triplet states formation. The BODIPY-anthracene triad (**ABA**) which showed higher triplet state yield was further studied as a photosensitizer in a two-component photoinitiating system. Here, the second component, *N*-phenylglycine, acts as a co-initiator reacting with excited states of **ABA** and forming free radicals. This system was applied by us for polymerization of methacrylate monomers in the volume of a photopolymerizable glass material under 532 nm laser patterning. The obtained high diffraction efficiency (up to 87 %) of the resulting grating proved the excellent capability of **ABA** to initiate photopolymerization. Moreover, **ABA** showed comparable performance with respect to a reference diiodo-BODIPY photosensitizer (**I<sub>2</sub>BDP**) under the same conditions.

## Results and Discussion

### Synthesis of BODIPY triads


The synthesis of target BODIPY triads is shown in Scheme 1. The synthesis started from 9-anthracenecarboxaldehyde and 2-pyrenylcarboxaldehyde which were reacted with 1-nitropropane to give the corresponding nitroalkenes **1a-b** (step 1). These compounds were subjected to Barton-Zard reaction with ethyl isocyanacetate (step 2), delivering pyrrolocarboxylates **2a-b**. The obtained products were cleanly transformed into pyrroles **3a-b** *via* the reduction with LiAlH<sub>4</sub> (step 3). Pyrroles were reacted with benzaldehyde and the resulting intermediate dipyrromethanes were oxidized without isolation, followed by treatment with BF<sub>3</sub>·Et<sub>2</sub>O in the presence of *N,N*-diisopropylethylamine (step 4) to give compounds **ABA** and **PBP**. BODIPY products were isolated by silica gel column chromatography in good yields. Isolated products were fully characterized through <sup>1</sup>H and <sup>13</sup>C NMR spectroscopy and high-resolution mass spectrometry (HRMS, Figures S7-S10).

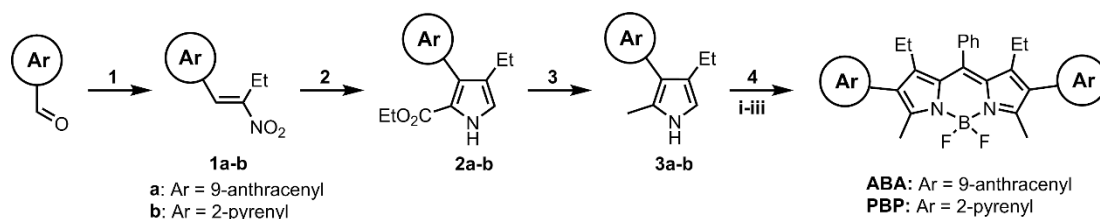

**Scheme 1.** Synthesis of target compounds. Reagents and conditions: (1) 1-nitropropane (neat),  $(\text{NH}_4)_2\text{CO}_3$ , reflux, 4–8 h, 59% yield for **1a** and 63% yield for **1b**; (2)  $\text{CNCH}_2\text{CO}_2\text{Et}$ , DBU, THF, room temperature (r.t.), 18 h, 78% yield for **2a** and 66% yield for **2b**; (3)  $\text{LiAlH}_4$ , THF, reflux, 4 h, 99% yield for **3a** and 93% yield for **3b**; (4) (i)  $\text{PhCHO}$ , TFA, DCM, r.t., 18 h; (ii) DDQ, r.t., 1 h; (iii)  $\text{BF}_3\cdot\text{Et}_2\text{O}$ , DIPEA, DCM, r.t., 2 h, 36% yield for **ABA**, 23% yield for **PBP**.



### Steady-state optical properties of the triads

The absorption and fluorescence emission properties of the prepared BODIPYs are presented in Figure 1 and summarized in Table 1. For both triads the absorption spectra show transitions associated with the two subunits, indicating weak coupling of the chromophores in the ground state. The experimental and DFT-simulated spectra (Fig. S14–S15, ESI) are similar, with the main band corresponding to  $S_0 \rightarrow S_1$  transition in BODIPY. As shown in Fig. S16 (ESI), triads have well-separated HOMO/LUMO distributions, indicating feasibility of the electron transfer from anthracene/pyrene subunits to the BODIPY in the excited state. Upon changing the solvent polarity, the shape and maxima of the absorption undergo little change. At the same time, the emission properties are greatly affected by solvent polarity. The emission spectrum of **ABA** in toluene (Fig. 1) shows a fluorescence band centred at 575 nm, characterized by a Stokes shift of 46 nm and an emission quantum yield ( $\Phi_{\text{em}}$ ) of 0.513. Unlike previously reported BODIPY-anthracene and pyrene dyads,<sup>40</sup> **ABA** and **PBP** do not display emission bands corresponding to the transition from the CT state which may be due to the negligible quantum yield of such emission. Increase in solvent polarity leads to a red shift of the emission and drop in quantum yields for both triads. In polar acetonitrile (ACN) the emission of **ABA** shows a Stokes shift of 125 nm and quantum yield of 0.025. Likewise, the excited state lifetime in ACN is much shorter (1.13 ns) than that in toluene (3.65 ns). This observation was reproduced in other solvents, showing a clear correlation between polarity, red shift of the emission, and its quantum yield. Such emission quenching in polar media is the signature of intramolecular electron transfer.<sup>41</sup> Similar behaviour was observed for triad **PBP**, except for its slightly stronger emission in polar solvents compared to **ABA**. This indicates that although ICT takes place in dyad **PBP**, it is less efficient compared to the triad based on anthracene. This is consistent with higher oxidation potential of pyrene which makes it less efficient at quenching BODIPY fluorescence than anthracene.<sup>42</sup>

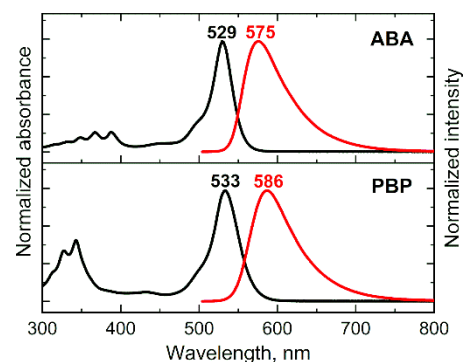

**Figure 1.** Absorption and emission spectra of **ABA** and **PBP** in toluene ( $\lambda_{\text{exc}} = 490$  nm).

**Table 1.** Optical properties of **ABA** and **PBP** in different solvents.

Compound	Solvent	$\lambda_{\text{abs}}^a$ (nm)	$\lambda_{\text{em}}^b$ (nm)	$\Phi_{\text{em}}^c$	$\Phi_{\Delta}^d$
 <b>ABA</b>	HEX	528	561	0.617	0.22
	TOL	529	575	0.513	0.289
	THF	528	580	0.291	0.307
	DCM	529	587	0.207	n.d. <sup>e</sup>
	EtOH	527	591	0.094	0.299
	CAN	525	640	0.025	0.14
 <b>PBP</b>	HEX	531	573	0.676	0.18
	TOL	533	586	0.634	0.203
	THF	530	586	0.445	0.185
	DCM	531	589	0.352	n.d. <sup>e</sup>
	EtOH	530	589	0.191	0.19
	ACN	527	602	0.078	0.09

<sup>a</sup> Absorption maxima corresponding to the BODIPY chromophore. <sup>b</sup> The emission spectra were collected with excitation at the vibrational shoulder of the BODIPY absorption (490 nm). <sup>c</sup> Measured using Rhodamine 6G ( $\Phi_{\text{em}} = 0.95$  in ethanol) as a reference. <sup>d</sup> Measured using 2,6-diiodo-8-phenyl-1,3,5,7-tetramethylBODIPY ( $\Phi_{\Delta} = 0.85$  in toluene) as a reference. <sup>e</sup> DCM was not used due to possible photolysis of the sensor in this solvent, leading to overestimation of  $\Phi_{\Delta}$  values.<sup>43</sup> HEX – hexane, TOL – toluene, THF – tetrahydrofuran, DCM – dichloromethane, EtOH – ethanol, ACN – acetonitrile.

To rationalize the effect of anthracenyl and pyrenyl substituents on the geometry and electronic structure of the triads, density functional theory (DFT) calculations were performed (see Supporting Information for computational details). Calculated


ground state geometries of **ABA** and **PBP** are presented in Figure 2. **ABA** possesses  $C_s$  symmetry since the dihedral angle between the anthracene subunit and the BODIPY core (d(C4-C1-C25-C28),  $\psi_1$ ) equals  $108^\circ$ , whereas for the second anthracene residue the dihedral angle (d(C10-C11-C31-C34),  $\psi_2$ ) is equal to  $-73^\circ$ . The **PBP** triad is strictly symmetrical ( $C_s$  point group) since both dihedral angles between the mean BODIPY plane and pyrene subunits are  $65.5^\circ$ . Similar molecular geometries were obtained in toluene and ACN: the root mean square deviation (RMSD) of Cartesian coordinates (toluene vs acetonitrile) equals  $0.01 \text{ \AA}$ . The optimized geometry of **ABA** in  $S_1$  state shows rotation along C-C bond between anthracene subunits and BODIPY core:  $\psi_1$  and  $\psi_2$  were calculated to be  $118^\circ$  and  $-63^\circ$  (Fig. S17, ESI), respectively. Similarly, the  $S_1$  state geometry of **PBP** shows rotation with  $\psi_1$  and  $\psi_2$  between pyrene and the BODIPY planes of  $54.5^\circ$  (Fig. S19, ESI). Hence, the dihedral angles of  $S_1$  state differ by  $10^\circ$  and  $13.3^\circ$  for **ABA** and **PBP**, respectively, as compared to the ground state geometries.

The observed Stokes shifts for **ABA** and **PBP** are much larger compared to BODIPYs bearing aryl groups in the *meso* position (typically,  $<15 \text{ nm}$ ).<sup>44</sup> Large Stokes shifts observed for both triads can be rationalized by the scheme presented in Figure 3. In **ABA**, geometry relaxation following photoexcitation leads to a significant change of the frontier molecular orbital energies. Thus, the LUMO is stabilized by  $0.1 \text{ eV}$  at the  $S_1$  state geometry as compared to the  $S_0$  structure. At the same time, the HOMO is destabilized by  $0.15 \text{ eV}$  for the  $S_1$  state geometry as compared to the  $S_0$  state. As a result, the HOMO-LUMO energy gap is greatly decreased with  $S_1$  geometry relaxation. In **PBP**, geometry relaxation following photoexcitation leads to LUMO stabilization by  $0.11 \text{ eV}$ . The HOMO is destabilized by  $0.14 \text{ eV}$  for the  $S_1$  state geometry as compared to the  $S_0$  state (Fig. S21, ESI). These results corroborate with previous reports on geometry relaxation-induced large Stokes shifts (up to  $100 \text{ nm}$ ) in 2,6-bisthieryl BODIPY derivatives.<sup>45</sup>


To probe the efficiency of triplet state formation in compounds **ABA** and **PBP**, singlet oxygen sensitization was evaluated using the chemical trapping method with 1,9-dimethylantracene (DMA). Irradiation of air-saturated solutions of the triads with  $514 \text{ nm}$  laser ( $20 \text{ mW cm}^{-2}$ ) did not lead to any changes in the absorption spectra (Fig. S12, ESI), proving sufficient photostability of these compounds and the absence of singlet oxygen addition which was previously observed by us for BODIPYs bearing anthracene moiety in the *meso* position.<sup>46</sup> Irradiation of DMA solutions containing each BODIPY triad, resulted in formation of a corresponding endoperoxide and linear decrease of DMA absorption (Fig. S22a, ESI), allowing to obtain  $\Phi_\Delta$  value from comparison with reference photosensitizer, 2,6-diiodo-8-phenyl-1,3,5,7-tetramethylBODIPY (**I<sub>2</sub>BDP**, Fig. S22b, ESI). As shown in Table 1, the resulting  $\Phi_\Delta$  values only slightly vary depending on the solvent. The most efficient  $^1\text{O}_2$  sensitization was observed for **ABA** in toluene, tetrahydrofuran and ethanol ( $\Phi_\Delta = 0.289\text{--}0.307$ ). This correlates with rapid charge transfer and triplet state generation observed in the TA experiments (*vide infra*). Dyad **PBP** showed  $\Phi_\Delta$  values of  $0.185\text{--}0.2$  in these solvents. In acetonitrile, **ABA** and **PBP** showed reduced  $\Phi_\Delta$  values of  $0.14$

and  $0.09$ , respectively. Such effect was observed for other BODIPYs exhibiting SOCT-ISC in acetonitrile and was attributed to a strong stabilization of the CT state in highly polar media and a reduced  $^1\text{CT-S}_0$  energy gap, which promotes ground state recombination.<sup>47</sup>

Reference BODIPY-anthracene and pyrene dyads bearing donor subunits in the *meso*-position of the BODIPY scaffold showed much more pronounced dependence of  $\Phi_\Delta$  values on solvent polarity (Table S1, ESI). For 8-anthryl-1,3,5,7-tetramethylBODIPY,  $\Phi_\Delta$  values reduced by a factor of 10 upon changing the solvent from polar ethanol to non-polar toluene. Lower  $\Phi_\Delta$  values for **ABA** and **PBP** compared to reference dyads can be rationalized taking into account different molecular geometries of these systems. *Meso*-substituted dyads are rigidly constrained in the orthogonal geometry due to the steric effect of methyl groups in positions 3 and 5.<sup>40</sup> This provides high yields of triplet state formation *via* SOCT-ISC as orthogonal mutual arrangement compensates the change of spin magnetic momentum by a large change in the orbital magnetic momentum during the recombination.<sup>48</sup> For anthracene/pyrene groups introduced in positions 2 or 6 the rotational barrier is lower allowing a deviation from orthogonality as is evidenced by computed  $S_0$ ,  $S_1$  and  $T_1$  excited state geometries of **ABA** and **PBP** (Fig. S17-S20, ESI) and thus leading to reduced triplet state yields.

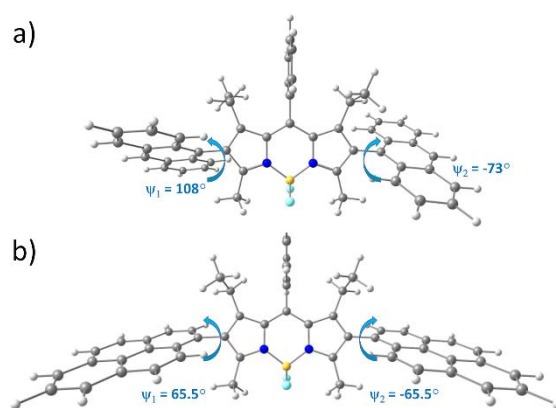

**Figure 2.** Optimized ground state geometries of a) **ABA** and b) **PBP**.

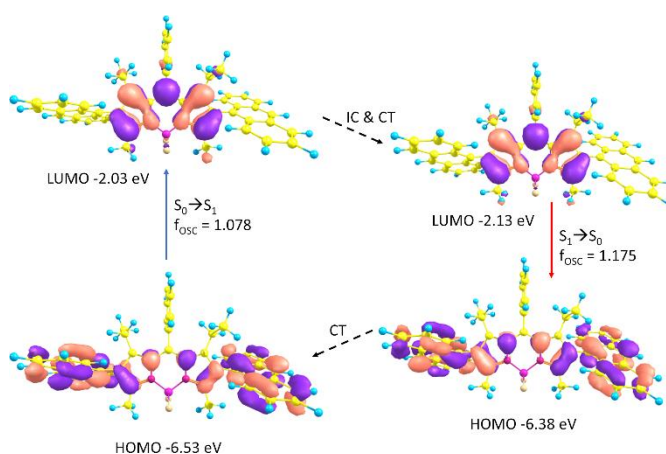

**Figure 3.** Rationalization of the large Stokes shift of **ABA** in ACN: the geometry relaxation upon photoexcitation and molecular orbitals involved in the




vertical absorption and emission. The vertical excitations were calculated based on the optimized ground state geometry ( $S_0$ ), the emission was calculated based on the optimized geometry of the excited state ( $S_1$ ).

### Femto- and nanosecond pump-probe transient absorption spectroscopy of the triads

To reveal the photoexcited state dynamics in the new triads, transient absorption (TA) spectroscopy was employed. Figure 4 shows the picosecond-nanosecond (ps-ns) and nanosecond-microsecond (ns- $\mu$ s) TA spectra and kinetics (inset) of selected spectral regions of **ABA** (a,c) and **PBP** (b,d) dissolved in toluene after photoexcitation at 505 nm (ps-ns TA) and 532 nm (ns- $\mu$ s TA), respectively. The negative  $\Delta T/T$  signals represent photoinduced absorption (PA), while positive  $\Delta T/T$  signals represent photo-bleaching (PB). In Figure 4a, the band centered at 520 nm (PB of BODIPY) showed no temporal evolution. On the other hand, the PA regions centered at  $\sim 420$  nm and  $\sim 800$  nm showed a spectral evolution with time, indicating the formation of charge-transfer (CT) states. The reason for the absence of a temporal evolution of the PB band is that both photoexcited singlet and CT states exhibit the same photobleaching, and the population of CT states compensates the decay of singlet states. The kinetics of the band at 550-570 nm exhibited a clear decay until 10 ps, and thereafter no further changes were observed until 500 ps (inset Fig. 4a). In contrast, the kinetics of the 770-870 nm band exhibited a clear rise due to the generation of CT states. An exponential fit to the kinetics

yielded an inverse rate constant of 3.4 ps (singlet exciton decay) and 4.5 ps (CT state generation) for the bands at 550-570 nm and 770-870 nm, respectively. The ps-ns TA spectra of **ABA** in acetonitrile showed different spectral shape and evolution (Fig. S23, ESI) compared those of **ABA** in toluene. Unlike in the case of toluene, the PB band of **ABA** in acetonitrile showed a clear decay after 50 ps. This is supported by the fast decay of the CT states (band centered at 630 nm). Table S2 summarizes the inverse generation rates of CT states in both toluene and acetonitrile solution.

Figure 4b shows the ps-ns TA spectra and associated kinetics of **PBP** in toluene. As in the case of **ABA** in toluene, the PB of **PBP** in toluene showed no spectral evolution, while the 550-570 nm band showed a fast decay, indicating the formation of CT states. An exponential fit to the kinetics shown in the inset of Figure 4b yielded an inverse rate constant of 2.7 ps for the band at 550-570 nm. This indicates that the CT state formation is slightly faster in **PBP** in toluene compared to **ABA** in toluene. The spectral shape and evolution are different for **PBP** in acetonitrile compared to **PBP** in toluene solution (Fig. S23, ESI). The inverse rate constants are provided in Table S2. In acetonitrile, both **ABA** and **PBP** showed early (after 50 ps), and faster decay of the CT states compared to their toluene counterparts. To further explore the CT state decay and generation and decay of triplet states, we performed also nanosecond-microsecond (ns- $\mu$ s) TA spectroscopy.

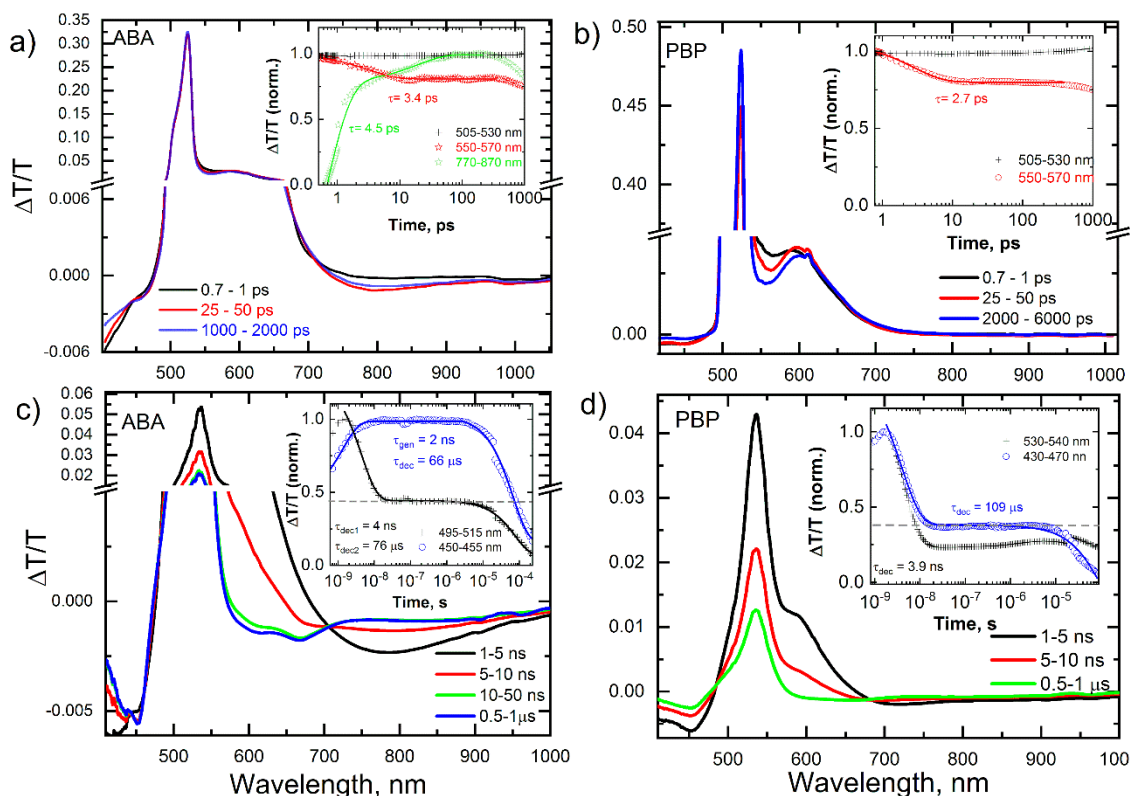


**Figure 4.** ps-ns TA spectra with kinetics (inset) of selected spectral region of **ABA** and **PBP** in toluene (a, b) after excitation with 505 nm laser pulses under inert atmosphere. ns- $\mu$ s TA spectra with kinetics (inset) of selected spectral region of **ABA** and **PBP** in toluene (c,d) after excitation with 532 nm laser pulses under inert atmosphere.

Figures 4c and 4d shows the nanosecond-microsecond (ns- $\mu$ s) TA spectra and kinetics (inset) of **ABA** and **PBP**, respectively, in toluene. Unlike the ps-ns TA spectra, the ns- $\mu$ s TA spectra show the emergence of a very long-lived (several microseconds) excited state. Both **ABA** and **PBP** showed a clear difference in the spectral and kinetics evolution of the excited state. In **ABA**, the CT state peaked around 800 nm and decayed within  $\sim$ 10 ns, causing the emergence of two new long-lived bands at 600 nm and 670 nm. Based on the previous reports,<sup>40,46</sup> we assigned these bands to the BODIPY triplet state and confirmed this assignment by TA measurements in the presence of air (Fig. S24, ESI). The  $\Delta T/T$  values (amplitude of the signal) of the TA spectra measured in inert atmosphere ( $N_2$ ) and in air are significantly different, indicating that the triplets were quenched by oxygen present in air. An exponential fit to the kinetics shown in the inset of Figure 4c yielded an inverse rate constant of 2 ns for triplet generation and 66  $\mu$ s for the triplet decay. We obtained an estimated triplet yield of 44%, assuming both triplet and CT states exhibit the same absorption cross-section (see the horizontal dashed line in the inset) as was reported in a previous work.<sup>49</sup> Furthermore, the triplet yield was independently estimated by using MCR-ALS (multivariate curve resolution – alternate least square) and by using the relative actinometry method<sup>50</sup> with Rose Bengal in methanol as a reference and  $\lambda_{\text{pump}} = 532$  nm, all yielding comparable values for **PBP** in toluene, shown in Table S2 (ESI). Figure 4d shows the ns- $\mu$ s TA spectra and kinetics (inset) of **PBP** in toluene. Unlike in **ABA**, we did not observe a distinct spectral signature of triplets (since the CT state and triplet state photoinduced spectra overlap), yet the kinetics showed the presence of long-lived states, which we assigned to triplets. An exponential fit to the kinetics shown in the inset of Figure 4d yielded a lifetime of 3.9 ns for the CT states (leading to triplet generation) and 109  $\mu$ s for the triplet decay, and we obtained an estimated triplet yield of 36%. A similar analysis was done for **ABA** and **PBP** in acetonitrile and we obtained an estimated triplet yield of 23% for **ABA** and 13% for **PBP** in acetonitrile (Fig. S27, ESI), respectively. Details are summarized in Table S2 (ESI).


### Photopolymerizable glass preparation and holographic recording

Due to its higher triplet state yield, **ABA** was chosen as a photosensitizer component for free-radical polymerization in a holographic recording material based on a photopolymerizable glass (PG), a hybrid organic-inorganic sol-gel material. Previously reported PG<sup>51</sup> was sensitized by incorporation of Irgacure 784 as a photoinitiator with maximum absorption in the range of 400–480 nm. This makes the material less sensitive at 532 nm, the second harmonic of single frequency Nd:YAG lasers typically used for holographic recording. For full utilisation of the potential of these readily available light sources a sensitizer with optimum absorption near 532 nm wavelength is needed. In this work, the PG composition was modified by introducing a two-component photoinitiating system containing **ABA** and N-phenylglycine (NPG). This compound was chosen as a co-initiator as its efficiency for the free-radical polymerization has been demonstrated in a photosensitive resin for 3D printing<sup>52</sup> and in holographic recording materials.<sup>53,54</sup> Although the photochemistry underlying the initiating radical generation has not been studied in detail, NPG was shown to interact with triplet states of xanthene dyes forming free radicals (NPG $\bullet$ ) which initiate polymerization of methacrylate and acrylamide monomers.<sup>54,55</sup> PG was synthesized by employing a four-step sol-gel process using two hybrid precursors: 3-trimethoxysilylpropyl methacrylate and a zirconium complex obtained by chelation of zirconium (IV) propoxide with methacrylic acid (see Supporting Information for synthetic details). After obtaining a homogeneous sol, **ABA** (0.025 % mol with respect to the total amount of monomers) and NPG (1.4 % mol) were added and the resulting composition was cross-linked by (3-aminopropyl)triethoxysilane to yield a fast-drying and water-resistant hybrid photopolymerizable glass (PG-**ABA**). In order to evaluate the performance of **ABA**, a reference PG containing 2,6-diiodo-BODIPY (PG-**I<sub>2</sub>BDP**) and NPG was prepared using the method described above. **I<sub>2</sub>BDP** is a common triplet photosensitizer with triplet state yield near unity and excellent photostability, which account for its broad use in photocatalysis.<sup>56</sup> Notably, it was shown to enable photopolymerization of acrylate monomers with high rates under low light intensities.<sup>57</sup>

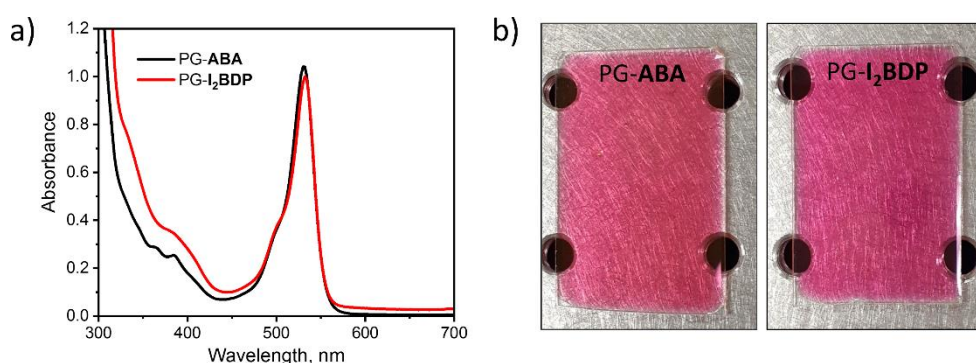

**Figure 5.** a) UV-Vis absorption spectra of PG-**ABA** and PG-**I<sub>2</sub>BDP** sol dissolved in isopropanol. b) Photographs of PG-**ABA** and PG-**I<sub>2</sub>BDP** layers with 260  $\mu$ m thickness.



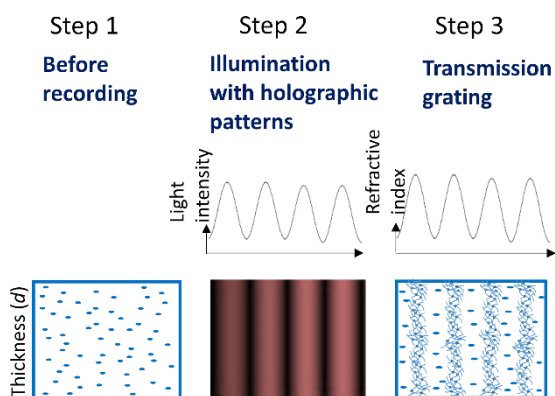


**Figure 6.** Grating formation in PG under holographic exposure. Step 1 shows the uniform distribution of monomers in PG layer before recording. Step 2 illustrates the sinusoidal profile of the light intensity produced by two coherent laser beams during recording. Step 3 displays spatially-varying refractive index within the PG layer due to density changes induced by polymerization of photoreactive components.

Spectra of both PG-**ABA** and PG-**I<sub>2</sub>BDP** sols showed a wide absorption band with the maximum absorbance in the range of 500–550 nm (Fig. 5a) which confirmed the suitability of these

materials for holographic recording with 532 nm laser. For the recording, dry layers with 220–260  $\mu\text{m}$  thickness were obtained by a drop-casting method followed by temperature curing as described in the Supporting Information. Dry layers of PG-**ABA** and PG-**I<sub>2</sub>BDP** showed low light scattering as seen from a clear image of the pattern on the optical table observed through the layer in Figure 5b. This allowed reducing losses due to scattering of light during holographic recording and achieving high diffraction efficiency of the grating.

Holographic recording of volume phase transmission gratings was carried out using the set-up presented in Figure S28 (ESI). As was proposed in a previous work,<sup>51</sup> during holographic patterning of PG layers, photopolymerization is triggered in illuminated areas. Under these conditions, **ABA** is expected to undergo intermolecular charge transfer and form triplet excited states of BODIPY *via* SOCT-ISC, which further react with NPG to produce free radicals. Thus formed radicals react with methacrylate groups initiating polymerization and leading to the formation of rigidly structured nanoparticle-based domains in illuminated areas. As result of holographic recording, a periodic distribution of areas with different density is achieved, leading to the periodic distribution of the refractive index and thus the holographic grating formation (Fig. 6).

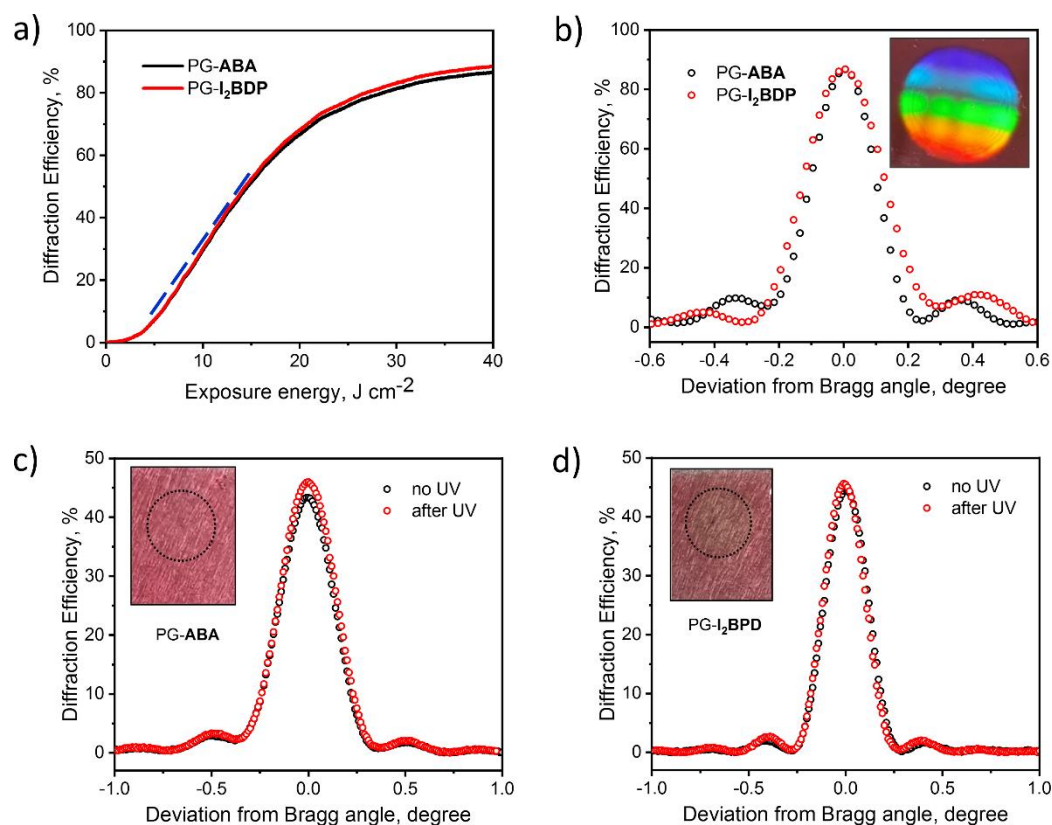

**Figure 7.** a) Holographic recording of volume phase transmission gratings in PG-**ABA** and PG-**I<sub>2</sub>BDP** layers. Real-time diffraction efficiency growth curves showing the formation of transmission gratings with the spatial frequency of about 800 lines  $\text{mm}^{-1}$ . The blue dashed line prepresents the curve's slope. b) Angular selectivity curves of the transmission gratings recorded. Inset: image of the light pattern created by a typical transmission grating recorded in PG-**ABA** and PG-**I<sub>2</sub>BDP**, under illumination with a white light source. c)-d) Experimental data on UV-curing. Angular selectivity curves of the transmission gratings recorded in PG-**ABA** and PG-**I<sub>2</sub>BDP** show unchanged diffraction efficiency before and after UV-curing using exposure energy of 22  $\text{J cm}^{-2}$ . Inset: the photograph of the layer after UV-curing indicates no layer cracking and confirms its stability to UV-exposure at current experimental conditions.

To characterize the process of grating formation, diffraction efficiency growth curves were monitored in real time using a 633 nm laser during holographic recording (see Fig. S28 (ESI) for details on the experimental set up). Obtained diffraction efficiency growth curves showed the successful formation of highly efficient gratings in PG-**ABA** and PG-**I<sub>2</sub>BDP** (Fig. 7a). The resulting photosensitivity was estimated from the linear part of the growth curves using the method described in the Supporting Information. As seen from Figure 7a, the linear part of the curves for PG-**ABA** and PG-**I<sub>2</sub>BDP** has identical slopes, which denotes equal exposure sensitivity of the two compositions, found to be  $6.1 \times 10^{-5} \text{ mJ}^{-1} \text{ cm}^2$  (Fig. S29, ESI). A shelf-life study confirmed that the recorded structures are stable and unchanged diffraction efficiency is observed over a period of 6 months (Fig. S30, ESI).

Diffraction efficiency up to 87 % was achieved using an exposure energy of  $35 \text{ J cm}^{-2}$  (Fig. 7b). It should be noted that this value is significantly higher than for holographic photopolymers in which the diffusion of mobile species such as monomers, dyes and short polymer chains plays a dominant role in the grating formation.<sup>58</sup> However, the total exposure energy required for PG-**ABA** and PG-**I<sub>2</sub>BDP** is in the same range as for previously reported photopolymer-filled glass in which the diffusion of mobile components through the nano-sized pores of the glass is hindered.<sup>59</sup> Thus, relatively high value of the total exposure energy possibly indicates a slow diffusion of any mobile components in PG.

Refractive index modulation is another crucial parameter of holographic recording materials characterising their performance. In this work, the recorded transmission gratings are considered as volume gratings since the Klein-Cook *Q*-parameter calculated using Equation S4 is 317 for 260  $\mu\text{m}$  thick layers. Thus, the coupled-wave theory<sup>60</sup> can be applied. The refractive index modulation estimated by Equation S5 was found to be dependent on the layer thickness for both materials, PG-**ABA** and PG-**I<sub>2</sub>BDP**. The values varied from  $0.9 \times 10^{-3}$  to  $1.1 \times 10^{-3}$  for layers with the thickness ranging from 260 to 220  $\mu\text{m}$ , respectively (Fig. S31, ESI). This value is close to one previously reported for gratings with similar thickness and spatial frequency recorded in a photopolymerizable glass sensitized with Irgacure 784.<sup>51</sup> Thus, successful holographic recording of transmission gratings confirms comparable efficiency of both **ABA**-NPG and **I<sub>2</sub>BDP**-NPG photoinitiating systems for polymerisation of methacrylates in PG.

Among the various aspects of the holographic recording material, stability under UV-exposure is one of the key parameters required for the sustained performance of holographic optical elements and their successful implementations. In order to investigate the effect of UV-exposure on the grating stability, diffraction efficiency before and after UV-curing was monitored for PG-**ABA** and PG-**I<sub>2</sub>BDP** samples (Fig. 7c-d). For this experiment, transmission gratings with the diffraction efficiency of about 45 % were recorded by using the total exposure energy of  $22 \text{ J cm}^{-2}$ . After recording, corresponding samples were exposed to UV-A light by means of Dymax UV-curing System (ECE Series) using the same total

exposure energy as used for recording ( $22 \text{ J cm}^{-2}$ ). As seen from Figures 7c-d, a slightly increased diffraction efficiency was observed for PG-**ABA** and PG-**I<sub>2</sub>BDP**. Moreover, no layer deterioration (cracking or breaking) was observed after UV-curing.

## Conclusions

In summary, we prepared two novel donor-acceptor-donor systems comprised of BODIPY as an electron acceptor and anthracenes (**ABA**) or pyrenes (**PBP**) as donor subunits. These triads undergo efficient intramolecular charge transfer and form corresponding CT states in both polar and non-polar solvents. Femtosecond transient absorption spectra indicate that charge separation takes place on the timescale of a few picoseconds for both triads. Furthermore, recombination of CT states leads to formation of long-living BODIPY triplet excited states *via* SOCT-ISC mechanism without heavy atoms. Nanosecond transient absorption spectra show the formation of triplet states with 44% and 36% for **ABA** and **PBP**, respectively, in toluene. Notably, unlike previously investigated donor-acceptor systems, new triads showed only moderate solvent dependence of triplet state formation as is evidenced by singlet oxygen quantum yield values in different solvents.

The two-component photoinitiating system containing **ABA** as a photosensitizer and NPG as a co-initiator was proposed for free-radical polymerization under 532 nm excitation. Feasibility of **ABA**-NPG photoinitiating system for the free-radical polymerization of methacrylates was demonstrated by holographic recording in a photopolymerizable hybrid sol-gel. Volume phase transmission gratings with the diffraction efficiency up to 87 % were obtained in PG-**ABA** layers with 220-260  $\mu\text{m}$  thickness confirming the efficiency of the **ABA**-NPG photoinitiating system. UV-resistance and sustained performance of holographic optical elements recorded on PG-**ABA** were proved by stable diffraction efficiency of transmission gratings under UV-curing. These results confirm stability of the diffraction grating under UV-exposure and provide further perspectives for utilisation of PG sensitized with heavy-atom-free BODIPYs as a holographic recording material with improved UV-resistance.

## Conflict of Interests

There are no conflicts to declare.

## Acknowledgements

M.A.F. and A.S. acknowledges TU Dublin Research Scholarship programme for the financial support of this work and Dr. Alla Lemeune (ENS de Lyon) for HRMS measurements. This publication is based on work supported by the KAUST Office of Sponsored Research (OSR) under award no. OSR-CRG2018-3746 and OSR-CRG2019-4025. C.S.P.D.C would like to acknowledge Luis Gutiérrez-Arzaluz for help getting started with the modified microscope used for TRPL measurements.

## References

- 1 J. Zhao, W. Wu, J. Sun and S. Guo, *Chem. Soc. Rev.*, 2013, **42**, 5323.
- 2 X. Zhao, Y. Hou, L. Liu and J. Zhao, *Energy Fuels*, 2021, **35**, 18942.
- 3 A. Kamkaew, S.H. Lim, H.B. Lee, L.V. Kiew, L.Y. Chung and K. Burgess, *Chem. Soc. Rev.*, 2013, **42**, 77.
- 4 J. Lee, P. Jadhav, P.D. Reusswig, S.R. Yost, N.J. Tompson, D.N. Congreve, E. Hontz, T. Van Voorhis and M.A. Baldo, *Acc. Chem. Res.*, 2013, **46**, 1300.
- 5 J. Zhou, Q. Liu, W. Feng, Y. Sun and F. Li, *Chem. Rev.*, 2015, **115**, 395.
- 6 (a) H.L. Wang, C.H. Du, Y. Pu, R. Adur, P.C. Hammel and F.Y. Yang, *Phys. Rev. Lett.*, 2014, **112**, 197201; (b) C. Du, H. Wang, F. Y. Yang and P. C. Hammel, *Phys. Rev. B*, 2014, **90**, 140407.
- 7 X. Zhang, Z. Wang, Y. Hou, Y. Yan, J. Zhao and B. Dick, *J. Mater. Chem. C*, 2021, **9**, 11944.
- 8 V.-N. Nguyen, Y. Yan, J. Zhao and J. Yoon, *Acc. Chem. Res.*, 2021, **54**, 207.
- 9 (a) M.A. Filatov, *Org. Biomol. Chem.*, 2020, **18**, 10; (b) E. Bassan, A. Gualandi, P. Giorgio Cozzi and P. Ceroni, *Chem. Sci.*, 2021, **12**, 6607.
- 10 (a) J.H. Golden, L. Estergreen, T. Porter, A.C. Tadle, D.M.R. Sylvinson, J.W. Facendola, C.P. Kubiak, S.E. Bradforth and M.E. Thompson, *ACS Appl. Energy Mater.*, 2018, **1**, 1083; (b) W. Huang, X. Zhang, B. Chen, H. Miao, C.O. Trindle, Y. Wang, Y. Luo and G. Zhang, *Chem. Commun.*, 2019, **55**, 67; (c) J.-X. Wang, L.-Y. Niu, P.-Z. Chen, Y.-Z. Chen, Q.-Z. Yang and R. Boulatov, *Chem. Commun.*, 2019, **55**, 7017.
- 11 (a) C. Trinh, K.O. Kirlikovali, S. Das, M.E. Ener, H.B. Gray, P.I. Djurovich, S. Bradforth and M.E. Thompson, *J. Phys. Chem. C*, 2014, **118**, 21834; (b) S. Das, W.G. Thornbury, A.N. Bartynski, M.E. Thompson and S.E. Bradforth, *J. Phys. Chem. Lett.*, 2018, **9**, 3264.
- 12 Y. Tsuga, M. Katou, S. Kuwabara, T. Kanamori, S. Ogura, S. Okazaki, H. Ohtani and H. Yuasa, *Chem. – Asian J.*, 2019, **14**, 2067.
- 13 G. Tang, A.A. Sukhanov, J. Zhao, W. Yang, Z. Wang, Q. Liu, V.K. Voronkova, M. Di Donato, D. Escudero and D. Jacquemin, *J. Phys. Chem. C*, 2019, **123**, 30171.
- 14 (a) N. Rehmat, A. Toffoletti, Z. Mahmood, X. Zhang, J. Zhao and A. Barbon, *J. Mater. Chem. C*, 2020, **8**, 4701; (b) Y. Zhao, A.A. Sukhanov, R. Duan, A. Elmali, Y. Hou, J. Zhao, G.G. Gurzadyan, A. Karatay, V.K. Voronkova and C. Li, *J. Phys. Chem. C*, 2019, **123**, 18270; (c) Y. Zhao, R. Duan, J. Zhao and C. Li, *Chemical Communications*, 2018, **54**, 12329.
- 15 F. Faroldi, B. Bardi, I. Tosi, S. Doria, J. Isopi, L. Baldini, M. Di Donato, M. Marcaccio, F. Sansone and Francesca Terenzi, *J. Mater. Chem. C*, 2021, **9**, 10899.
- 16 D. Liu, A.M. El-Zohry, M. Taddei, C. Matt, L. Bussotti, Z. Wang, J. Zhao, O.F. Mohammed, M. Di Donato and S. Weber, *Angew. Chem. Int. Ed.*, 2020, **59**, 11591.
- 17 (a) B.G. McCarthy, R.M. Pearson, C.-H. Lim, S.M. Sartor, N.H. Damrauer and G.M. Miyake, *J. Am. Chem. Soc.*, 2018, **140**, 5088; (b) C.H. Lim, M.D. Ryan, B.G. McCarthy, J.C. Theriot, S.M. Sartor, N.H. Damrauer, C.B. Musgrave and G.M. Miyake, *J. Am. Chem. Soc.*, 2017, **139**, 348; (c) X. Pan, C. Fang, M. Fantin, N. Malhotra, W.Y. So, L.A. Peteanu, A.A. Isse, A. Gennaro, P. Liu and K. Matyjaszewski, *J. Am. Chem. Soc.*, 2016, **138**, 2411.
- 18 F.-K. Bruder, R. Hagen, T. Rölle, M.-S. Weiser and T. Fäcke, *Angew. Chem. Int. Ed.*, 2011, **50**, 4552.
- 19 J. Guo, M. R. Gleeson and J. T. Sheridan, *Phys. Res. Int.*, 2012, **16**, ID 803439.
- 20 C. M. Bigler, P.-A. Blanche and K. Sarma, *Appl. Opt.*, 2018, **57**, 2007.
- 21 J. Xiao, J. Liu, X. Duan, X. Shi and Z. Zhang, *Opt. Express*, 2020, **28**, 31316.
- 22 D. Chemisana, J. Atencia, J. Marín-Sáez and M.-V. Collados, *Opt. Express*, 2016, **24**, A720.
- 23 H. Akbari, I. Naydenova, H. Ahmed, S. McCormack and S. Martin, *Sol. Energy*, 2017, **155**, 103.
- 24 K. Murphy, V. Toal, S. Martin and I. Naydenova, *Opt. Express*, 2018, **26**, 8916.
- 25 Y. Tomita, T. Aoi, S. Hasegawa, F. Xia, Y. Wang and J. Oshima, *Opt. Express*, 2020, **28**, 28366.
- 26 M. Sevilla, J. Marín-Sáez, D. Chemisana, M.-V. Collados and J. Atencia, *Photonics*, 2021, **8**, 465.
- 27 A. V. Velasco, M. L. Calvo and P. Cheben, *J. Appl. Phys.*, 2013, **113**, 033101.
- 28 N. Zhang, J. Liu, J. Han, X. Li, F. Yang, X. Wang, B. Hu and Y. Wang, *Appl. Opt.*, 2015, **54**, 3645.
- 29 J. Han, J. Liu, X. Yao and Y. Wang, *Opt. Express*, 2015, **23**, 3534.
- 30 R. Mallavia, A. Fimia, C. García and R. J. Sastre, *Mod. Opt.*, 2001, **48**, 941.
- 31 Q. Gong, S. Wang, M. Huang and F. Gan, *Mat. Lett.*, 2005, **59**, 2969.
- 32 Y. Qi, H. Li, J. Guo, M. R. Gleeson and J. Sheridan, *Opt. Commun.*, 2014, **320**, 114.
- 33 N. Kiseleva, M.A. Filatov, J.C. Fischer, M. Kaiser, M. Jakoby, D. Busko, I.A. Howard, B.S. Richards and A. Turshatov, *Phys. Chem. Chem. Phys.*, 2022, **24**, 3568.
- 34 A. Harriman, L.J. Mallon, G. Ulrich and R. Ziessel, *ChemPhysChem*, 2007, **8**, 1207.
- 35 Z. Mahmood, M. Taddei, N. Rehmat, L. Bussotti, S. Doria, Q. Guan, S. Ji, J. Zhao, M. Di Donato, Y. Huo and Y.H. Xing, *J. Phys. Chem. C*, 2020, **124**, 5944.
- 36 P.H. Marek-Urban, M. Urban, M. Wiklińska, K. Paplińska, K. Woźniak, A. Blacha-Grzechnik and K. Durka, *J. Org. Chem.*, 2021, **86**, 12714.
- 37 A.A. Buglak, A. Charisiadis, A. Sheehan, C.J. Kingsbury, M.O. Senge and M.A. Filatov, *Chem. Eur. J.*, 2021, **27**, 9934.
- 38 Y. Wu and W. Zhu, *Chem. Soc. Rev.*, 2013, **42**, 2039.
- 39 (a) E. Vauthey, *ChemPhysChem*, 2012, **13**, 2001; (b) B. Dereka, A. Rosspeintner, Z. Li, R. Liska and E. Vauthey, *J. Am. Chem. Soc.*, 2016, **138**, 4643; (c) M. Soderberg, B. Dereka, A. Marrocchi, B. Carloti and E. Vauthey, *J. Phys. Chem. Lett.*, 2019, **10**, 2944; (d) X. Niu, Z. Kuang, M. Planells, Y. Guo, N. Robertson and A. Xia, *Phys. Chem. Chem. Phys.*, 2020, **22**, 15743.
- 40 (a) M.A. Filatov, S. Karuthedath, P.M. Polestshuk, S. Callaghan, K. Flanagan, M. Telitchko, T. Wiesner, F. Laquai and M.O. Senge, *Phys. Chem. Chem. Phys.*, 2018, **20**, 8016; (b) M.A. Filatov, S. Karuthedath, P.M. Polestshuk, S. Callaghan, K. Flanagan, T. Wiesner, F. Laquai and M.O. Senge, *ChemPhotoChem*, 2018, **2**, 606; (c) N. Kiseleva, D. Busko, B. S. Richards, M. A. Filatov and A. Turshatov, *J. Phys. Chem. Lett.*, 2020, **11**, 6560.
- 41 (a) J. Li, Y. Qian, L. Xie, Y. Yi, W. Li and W. Huang, *J. Phys. Chem. C*, 2015, **119**, 2133; (b) Y. Qian, M. Cai, X. Zhou, Z. Gao, X. Wang, Y. Zhao, X. Yan, W. Wei, L. Xie and W. Huang, *J. Phys. Chem. C*, 2012, **116**, 12187.
- 42 E. S. Pysh and N. C. Yang, *J. Am. Chem. Soc.*, 1963, **85**, 2124.
- 43 X.-F. Zhang and X. Li, *J. Lumin.*, 2011, **131**, 2263.
- 44 A. Loudet and K. Burgess, *Chem. Rev.*, 2007, **107**, 4891.
- 45 Y. Chen, J. Zhao, H. Guo and L. Xie, *J. Org. Chem.*, 2012, **77**, 2192.
- 46 M.A. Filatov, S. Karuthedath, P.M. Polestshuk, H. Savoie, K.J. Flanagan, C. Sy, E. Sitte, M. Telitchko, F. Laquai, R.W. Boyle and M.O. Senge, *J. Am. Chem. Soc.*, 2017, **139**, 6282.
- 47 J.T. Buck, A.M. Boudreau, A. DeCarminé, R.W. Wilson, J. Hampsey and T. Mani, *Chem*, 2019, **5**, 138.

- 
- 48 (a) Z.E.X. Dance, S.M. Mickley, T.M. Wilson, A.B. Ricks, A.M. Scott, M.A. Ratner and M.R. Wasielewski, *J. Phys. Chem. A*, 2008, **112**, 4194; (b) Z. E. X. Dance, Q. Mi, D.W. McCamant, M.J. Ahrens, M.A. Ratner and M.R. Wasielewski, *J. Phys. Chem. B*, 2006, **110**, 25163; (c) D. J. Gibbons, A. Farawar, P. Mazzella, S. Leroy-Lhez and R. M. Williams, *Photochem. Photobiol. Sci.*, 2020, **19**, 136.
- 49 N. Kiseleva, M. A. Filatov, M. Oldenburg, D. Busko, M. Jakoby, I. A. Howard, B. S. Richards, M. O. Senge, S. M. Borisov and A. Turshatov, *Chemical Communications*, 2018, **54**, 1607.
- 50 J. S. de Melo, J. Pina, F. B. Dias and A. L. Maçanita, in *Applied Photochemistry*, ed. R. C. Evans, P. Douglas and H. D. Burrows, Springer, 2013, ch. 15, p. 533.
- 51 T. Mikulchyk, M. Oubaha, A. Kaworek, B. Duffy, M. Lunzer, A. Ovsianikov, S. E-Gul, I. Naydenova and D. Cody, *Adv. Opt. Mater.*, 2022, **10**, 2102089.
- 52 A. Al Mousawi, P. Garra, M. Schmitt, J. Toufaily, T. Hamieh, B. Graff, J. P. Fouassier, F. Dumur and J. Lalevée, *Macromolecules*, 2018, **51**, 4633.
- 53 T. Mikulchyk, S. Martin and I. Naydenova, *Appl. Opt.*, 2017, **56**, 6348.
- 54 Q. Gong, S. Wang, M. Huang and F. Gan, *Mater. Lett.*, 2005, **59**, 2969.
- 55 G. Qiaoxia, H. Mingju and G. Fuxi, *Dyes Pigment.*, 2006, **69**, 204.
- 56 S. Lacombe and T. Pigot, *Catal. Sci. Technol.*, 2016, **6**, 1571.
- 57 A. Stafford, D. Ahn, E. K. Raulerson, K.-Y. Chung, K. Sun, D. M. Cadena, E. M. Forrister, S. R. Yost, S. T. Roberts and Z. A. Page, *J. Am. Chem. Soc.*, 2020, **142**, 14733.
- 58 T. Babeva, I. Naydenova, S. Martin and V. Toal, *Opt. Express*, 2008, **16**, 8487.
- 59 M. G. Schnoes, L. Dhar, M. L. Schilling, S. S. Patel and P. Wiltzius, *Opt. Lett.*, 1999, **24**, 658.
- 60 H. Kogelnik, *Bell Syst. Tech. J.*, 1969, **48**, 2909.