

Title	Main group catalysis for H ₂ purification based on liquid organic hydrogen carriers
Author(s)	Hashimoto, Taiki; Asada, Takahiro; Ogoshi, Sensuke et al.
Citation	Science Advances. 2022, 8(43), p. eade0189
Version Type	VoR
URL	https://hdl.handle.net/11094/92547
rights	© 2022 The Authors, some rights reserved.
Note	

Osaka University Knowledge Archive : OUKA

<https://ir.library.osaka-u.ac.jp/>

Osaka University

CHEMISTRY

Main group catalysis for H₂ purification based on liquid organic hydrogen carriers

Taiki Hashimoto, Takahiro Asada, Sensuke Ogoshi*, Yoichi Hoshimoto*

Molecular hydrogen (H₂) is one of the most important energy carriers. In the midterm future, a huge amount of H₂ will be produced from a variety of hydrocarbon sources through conversion and removal of contaminants such as CO and CO₂. However, bypassing these purification processes is desirable, given their energy consumption and environmental impact, which ultimately increases the cost of H₂. Here, we demonstrate a strategy to separate H₂ from a gaseous mixture of H₂/CO/CO₂/CH₄ that can include an excess of CO and CO₂ relative to H₂ and simultaneously store it in N-heterocyclic compounds that act as liquid organic hydrogen carriers (LOHCs), which can be applied to produce H₂ by subsequent dehydrogenation. Our results demonstrate that LOHCs can potentially be used for H₂ purification from CO- and CO₂-rich crude H₂ in addition to their well-established use in H₂ storage.

INTRODUCTION

Molecular hydrogen (H₂) is an essential reductant that has been widely used in, e.g., petroleum refineries, the industrial production of ammonia and methanol, and the chemical industry. Moreover, H₂ is one of the most promising energy carriers of the future, given its high stability and thus transportability, its high gravimetric energy density, and the low environmental impact of its combustion product compared to those of hydrocarbon-based energy sources (1–4). These features make H₂ an attractive candidate for the construction of a greener and sustainable economy, which is commonly referred to as the “hydrogen economy” (3). Thus, it can be expected that a huge amount of H₂, on a magnitude of more than 10¹² standard cubic feet per year, will be produced from a wide range of hydrocarbon and renewable resources (1, 2). In this context, H₂ production combined with CO₂ capture and storage from hydrocarbon resources such as petroleum, coal, natural gas, and biomass represents a pragmatic choice for the midterm future due to the limited supply of renewable energy (2), while the electrolysis of water using electricity obtained from renewable resources seems to be an alternative option in the long-term future (5). The predominant contemporary route to H₂ production includes the intensive purification of crude H₂, which is a gaseous mixture of H₂, CO, CO₂, and other components that is produced by gasification, reforming, and/or water-gas shift (WGS) (process I in Fig. 1A). Purification processes such as pressure swing adsorption (PSA), membrane separation, and cryogenic separation critically determine the purity of the H₂, which is sometimes required to exceed 99.99% for fuel cells, and influence the total energy consumption of the H₂ production process, making it cost inefficient. Notable advances have been made to improve the efficiency, H₂ recovery rate, and reproducibility of H₂ purification processes (4). Nevertheless, an approach that could fundamentally solve all these challenging issues remains to be found (1). Thus, although H₂ can currently be stored after or during the process I in Fig. 1A (6), we envisaged a solution where H₂ could be stored in its carrier directly from crude H₂, which often includes more CO than H₂, without the requirement for any of the aforementioned

shift and purification processes (process II in Fig. 1A) (7). Moreover, the recovery of H₂ after our proposed path ultimately leads to the production of highly pure H₂.

To this end, we focused on the use of liquid organic hydrogen carriers (LOHCs), which have been widely used for H₂ storage and transportation (8–12). H₂ storage systems with LOHCs are based on a reaction sequence in which a H₂ lean state (H₀-LOHC) is hydrogenated to produce a H₂-rich state (H_x-LOHC), followed by a subsequent dehydrogenation of H_x-LOHC after storage/transport that regenerates H₂ and H₀-LOHC (Fig. 1B). The use of LOHCs has been extensively researched, as the technical, environmental, and economic advantages of H₂ storage using LOHCs are widely accepted (8). Furthermore, the pool of potential candidates for H₀-LOHCs has recently been expanded from the well-studied aromatic hydrocarbons to include heteroaromatics (11–13), cyclic dipeptides (14), amides (15, 16), cyclic ureas (17), and oligoesters (10), some of which provide hydrogenated products (H_x-LOHC) with H₂ storage capacity [H₂ weight % (wt %)] values that exceed the practical guidelines proposed by the European Union (5.0 wt %) and the U.S. government (5.5 wt %) (8). However, hitherto reported H₂ storage systems using LOHCs have predominantly been based on the use of transition metal catalysts. This presents a critical issue for H₂ separation in the presence of CO and CO₂, both of which can severely inhibit transition metal-catalyzed hydrogenation reactions (6, 9). We have successfully showed a strategy for H₂ separation from multicomponent gas mixtures such as H₂/CO/CO₂ via the main group-catalyzed hydrogenation of organic molecules in 2017 (7). Note here that Breakman-Danheux *et al.* (18) in 1996 and Jorschick *et al.* (19) in 2019 have independently reported transition metal-based heterogeneous compounds that have been applied to the hydrogenation of hydrocarbon-based LOHCs using contaminated H₂ including CO, CO₂, and/or gaseous hydrocarbons, which led to a marked suppression of the catalytic activity by CO despite the great excess of H₂ present.

Against this background, we have focused on main group catalysis (20, 21) including the use of frustrated Lewis pairs (FLPs) that are composed of Lewis bases (LBs) and triaryl boranes as the Lewis acids (LAs) (22–24). Triaryl boranes of the type B^{III} such as B(C₆F₅)₃ (B^I) have been reported to catalyze the hydrogenation of N-heteroaromatic compounds such as 2-methylquinoline (Qin) under diluted conditions (25–27). FLPs are well known to mediate the heterolytic cleavage of

Copyright © 2022 The Authors, some rights reserved; exclusive licensee American Association for the Advancement of Science. No claim to original U.S. Government Works. Distributed under a Creative Commons Attribution License 4.0 (CC BY).

Department of Applied Chemistry, Faculty of Engineering, Osaka University, Suita, Osaka 565-0871, Japan.

*Corresponding author. Email: ogoshi@chem.eng.osaka-u.ac.jp (S.O.); hoshimoto@chem.eng.osaka-u.ac.jp (Y.H.)

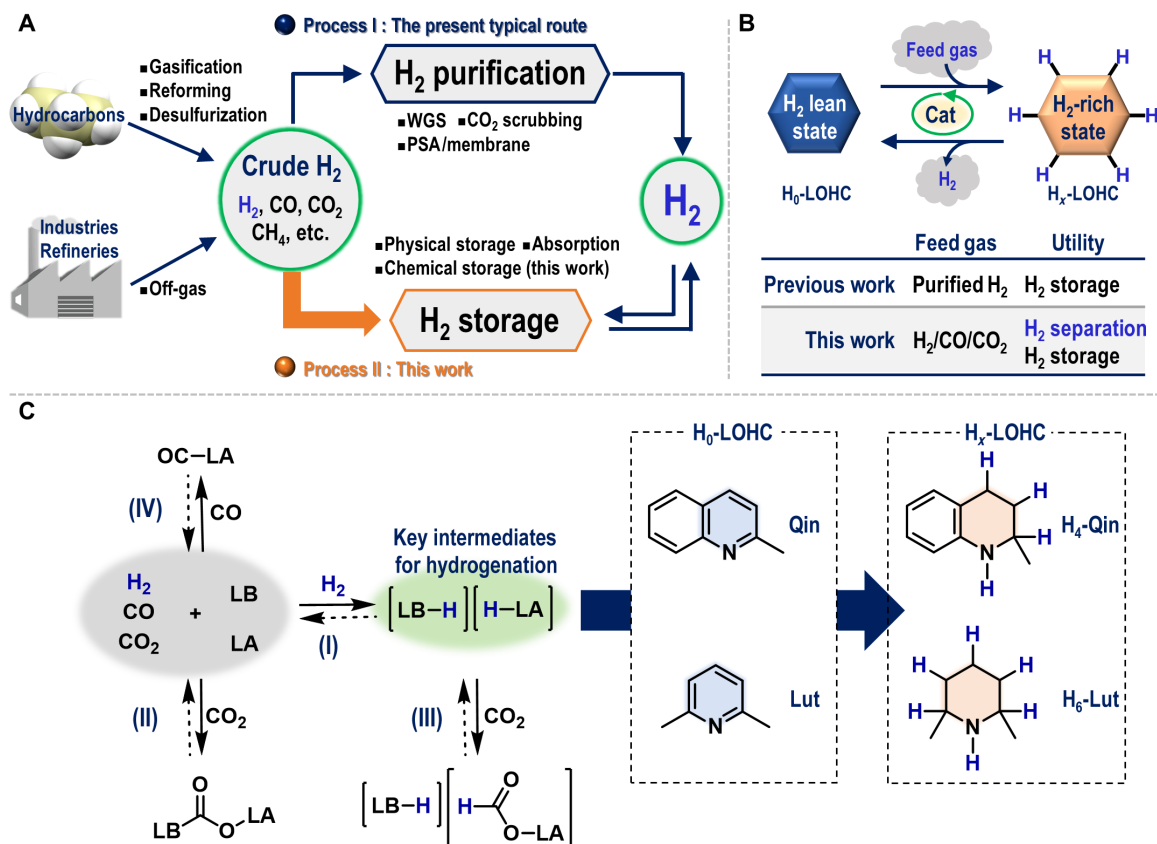


Fig. 1. Research background and concept of this study. (A) Simplified schemes of representative contemporary routes of H₂ purification followed by H₂ storage (process I) and a conceptually novel route involving the simultaneous separation and storage of H₂ from crude H₂ (process II); WGS, water-gas shift; PSA, pressure swing adsorption. (B) Schematic illustration of the general concept behind well-established methods and this work. (C) Potential reactions among H₂, CO, CO₂, LA (Lewis acid/acidic part), and/or LB (Lewis base/basic part). Dashed arrows represent backward reactions that do not always occur under the same conditions as the corresponding forward reaction.

the H–H bond to generate [LB–H][H–LA] species (Fig. 1C, I) (23). The subsequent proton/hydride transfer from [LB–H][H–LA] to N-heteroaromatic compounds facilitates the storage of H₂ (26). CO₂ fixation by FLPs has also been widely studied and found to proceed in either a reversible or irreversible manner (e.g., Fig. 1C, II) (28, 29). The hydrogenation of CO₂ has been reported in the presence of FLPs that are composed of B¹ and nitrogen-based LBs (Fig. 1C, III) (29–32). CO can reversibly bind to the boron center (Fig. 1C, IV), which would kinetically affect the H₂ cleavage step (29, 33). Moreover, these gases contain a certain amount of H₂O, which often triggers the decomposition of triaryl boranes to yield, e.g., [LB–H][HO–LA], although sophisticated strategies to minimize the influence of H₂O have been reported (34, 35). The reactions shown in Fig. 1C (II to VI) can seriously affect the progress of the targeted catalytic hydrogenation in the presence of CO, CO₂, and H₂O when the undesired paths are irreversible (or nearly irreversible). Therefore, a suitable triaryl borane that exhibits sufficient reactivity toward H₂ in cooperation with LBs, yet simultaneously avoids the aforementioned irreversible deactivation paths, would be highly desirable. Note that Voicu *et al.* (36) successfully applied an FLP comprising B¹ and P^tBu₃ to the microfluidic separation of ethylene and ethane.

Here, we demonstrate the direct storage of H₂ in N-heterocyclic compounds such as H₄-Qin and 2,6-dimethylpiperidine (H₆-Lut)

under various mixed gas conditions including H₂, CO, CO₂, and CH₄ via a shelf-stable Bⁿ-catalyzed hydrogenation of Qin and 2,6-lutidine (Lut), respectively. Furthermore, the same Bⁿ also catalyzes the dehydrogenation from H₄-Qin to produce H₂ with concomitant generation of Qin. The molar compositions of H₂/CO/CO₂ used in this work (1/1/1, 1/5/1, and 1/1/5) were based on the molar composition of the typical crude H₂ produced by hydrocarbon resources (H₂/CO/CO₂ = 1/1/0.2 to 1/2/0.5) and the typical PSA off-gas (H₂/CO/CO₂ = 1/0.1/2), albeit these compositions vary depending on the feedstock (4). In addition, these gases include up to 0.9 mmol of H₂O (table S2), which should be considered under the applied conditions.

RESULTS

The interconversion between Qin and H₄-Qin was used as a model LOHC system to separate H₂ under these mixed gas conditions (Fig. 2). As expected, well-established transition metal complexes based on Rh (TM¹), Ru (TM²), or Ir (TM³) (37) did not catalyze the hydrogenation of Qin (1.5 M in toluene) using a gaseous mixture of H₂/CO/CO₂ (4 atm each; runs 1 to 3), whereas H₄-Qin was efficiently yielded when H₂ (99.95% purity, 4 atm) was used in the cases of TM² and TM³ (38). A higher yield of H₄-Qin (12%) was observed when 1 mole percent (mol %) B¹ was subjected to these mixed gas

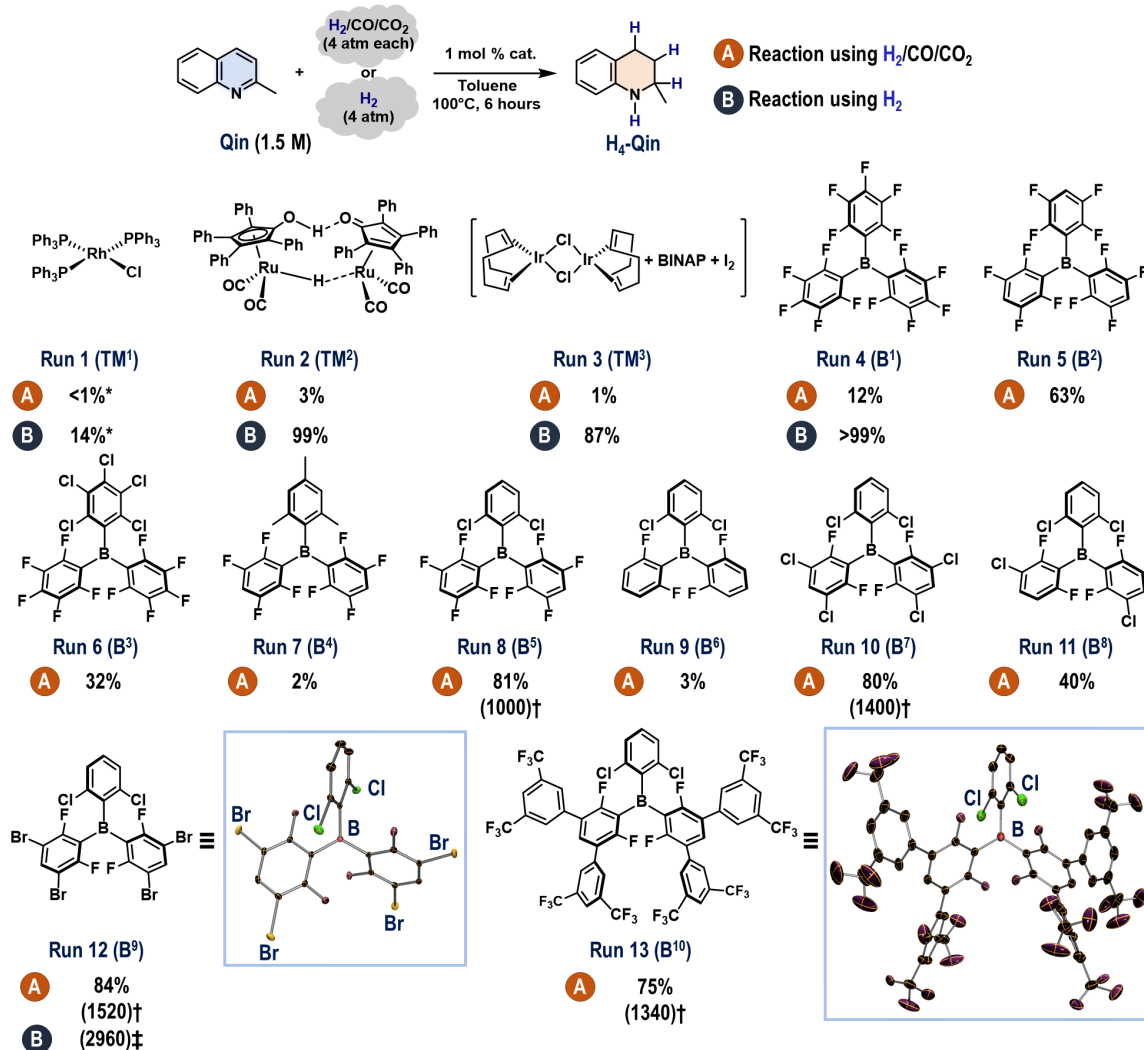


Fig. 2. Optimization of the reaction conditions. General conditions for the catalytic hydrogenation of **Qin**: A mixture of **Qin** (2.5 mmol, 1.5 M in toluene) and **Bⁿ** (1 mol %) was treated with H₂/CO/CO₂ (4 atm each; conditions A) or H₂ (4 atm; conditions B) at 100°C. Yields of **H₄-Qin** were determined by GC analysis. The molecular structures of **B⁹** and **B¹⁰** were determined by single-crystal x-ray diffraction analysis and are shown with thermal ellipsoids at 30% probability (H atoms are omitted for clarity). BINAP, 2,2'-bis(diphenylphosphino)-1,1'-binaphthyl. *denotes 10 mol % catalyst. †denotes catalyst turnover number (TON) after a period of 48 hours under solvent-free conditions using 0.1 mol % **Bⁿ** and H₂/CO/CO₂ (30 atm each). ‡denotes catalyst TON after a period of 48 hours under solvent-free conditions using 0.05 mol % **B⁹** and H₂ (85 atm).

conditions (run 4A), although the deleterious influence of the contaminants (CO, CO₂, and/or H₂O) was again observed compared to the result obtained using pure H₂ (run 4B). Encouraged by this result, we explored the triaryl boranes **B²** to **B⁶**, which have been developed by Stephan *et al.* (39), Ashley *et al.* (40), and Soós *et al.* (26, 41, 42) (runs 5 to 9). The decreasing Lewis acidity exhibited by the boron centers when the C₆F₅ group in **B¹** were replaced with three para-H-C₆F₄ groups (**B²**) or with two para-H-C₆F₄ groups and a 2,6-Cl₂-C₆H₃ group (**B⁵**) was found to be critical, and **H₄-Qin** was afforded in 63 and 81% yield when **B²** and **B⁵** were used, respectively (runs 5 and 8). We thus carried out additional structural modifications via the substitution of the meta-F with respect to the boron atom in **B⁵** with Cl atoms (**B⁷**), H and Cl atoms (**B⁸**), Br atoms (**B⁹**), and (CF₃)₂C₆H₃ groups (**B¹⁰**) (runs 10 to 13). **B⁹** showed the best result, affording **H₄-Qin** in 84% yield even in the presence of CO and CO₂ (run 12). Moreover, a significant enhancement in

the hydrogenation of **Qin** was observed when the reactions were conducted using **B⁵**, **B⁷**, **B⁹**, and **B¹⁰** in the absence of solvent (fig. S17); **B⁹** exhibited a catalyst turnover number (TON) of 1520 at 100°C in the presence of H₂/CO/CO₂ (30 atm each), which is far higher than the TONs obtained using **B⁵** (1000), **B⁷** (1400), or **B¹⁰** (1340) (runs 8, 10, 12, and 13; see also fig. S18). Note that the TON eventually reached to 2960 when the **B⁹**-catalyzed hydrogenation of **Qin** was carried out under the solvent-free conditions including H₂ (85 atm). The differences observed among **B⁵**, **B⁷**, **B⁹**, and **B¹⁰** can be rationalized in terms of the electronic and steric properties of the meta-substituents, i.e., their electron-withdrawing ability, which influences the electron-accepting ability of the boron center, and their steric size, which should cause intramolecular steric repulsion among the introduced aryl groups (table S4 and fig. S44) (43). In this context, the larger size of the Br atoms in **B⁹** compared to the F (**B⁵**) and Cl (**B⁷**) atoms can be expected to play a key role in maintaining high

activity under the applied mixed gas conditions by destabilizing the four coordinated boron species that would be formed during the reactions involving CO, CO₂, and/or H₂O.

Both **B**⁷ and **B**⁹ exhibited high stability toward air and moisture. **B**⁹ can be stored under ambient conditions (22°C, ca. 30% humidity) for at least 1 year without any apparent decomposition, while very minor levels (ca. 1%) of decomposition were observed for **B**⁷ after 1 year of storage (figs. S14 and S15).

The **B**⁹-catalyzed hydrogenation of **Qin** (1 mol % catalyst, without solvent) also proceeded to furnish **H**₄-**Qin** in >99 and 94% yield using CO-rich (H₂/CO/CO₂ = 4/20/4 atm; a model of syngas) and CO₂-rich (H₂/CO/CO₂ = 4/4/20 atm; a model of industrial off-gas) mixtures, respectively, although a longer reaction time was required in both cases (Fig. 3A). These results imply that CO and CO₂ kinetically affect the catalytic activity of **B**⁹ toward hydrogenation, with obvious suppression when an excess of the contaminant CO₂ with respect to H₂ is present. The coexistence of CH₄ did not hamper the progress of the reaction.

We also explored the optimal conditions for the catalytic dehydrogenation of **H**₄-**Qin** to afford **Qin** (Fig. 3B) (44, 45). Without solvent, 2 mol % **B**⁵, **B**⁷, and **B**⁹ successfully catalyzed the production of **Qin** in 84 to 88% yields at 200°C for 6 hours, whereas **B**¹ and **B**¹⁰ exhibited inferior results (18 and 68%, respectively) under

otherwise identical reaction conditions. The recovery of H₂ [193% yield; CO and CO₂ were not detected by gas chromatography (GC) analysis; fig. S20] was confirmed during the **B**⁹-catalyzed dehydrogenation of **H**₄-**Qin** (2 hours) to **Qin** in 90% yield. Under the applied reaction conditions, the hydrogenation of **Qin** and the dehydrogenation of **H**₄-**Qin** could be catalyzed simultaneously by **B**⁹. Further optimization of the reaction equipment so that the recovered H₂ can be efficiently removed could thus be expected to increase the dehydrogenation efficiency.

To develop a strategy for the purification of the contaminated H₂, we designed a reaction system based on a **B**⁹-catalyzed hydrogenation/dehydrogenation sequence starting from H₂/CO/CO₂ [1/1/1 molar ratio; H₂ purity = (molar amount of H₂)/(sum of the molar amounts of H₂, CO, and CO₂) × 100 = 33.3%] as a feed gas (Fig. 3C). In the presence of 2 mol % **B**⁹, H₂ was directly stored in **H**₄-**Qin** (0.95 mmol, 95%) from H₂/CO/CO₂ (5.4 equivalents each) via the hydrogenation of **Qin** (1.0 mmol). After a simple evacuation, dehydrogenation of the obtained **H**₄-**Qin** was carried out to generate H₂ (1.74 mmol, 174%) with a concomitant regeneration of **Qin** (0.91 mmol, 91%). Thus, a significant increase in the H₂ purity from 33.3 to 99.9% was demonstrated by the efficient removal of CO (not detected by GC analysis) and CO₂ (detected in ca. 0.1%; fig. S21) via a single cycle of the **B**⁹-catalyzed hydrogenation/dehydrogenation sequence. The

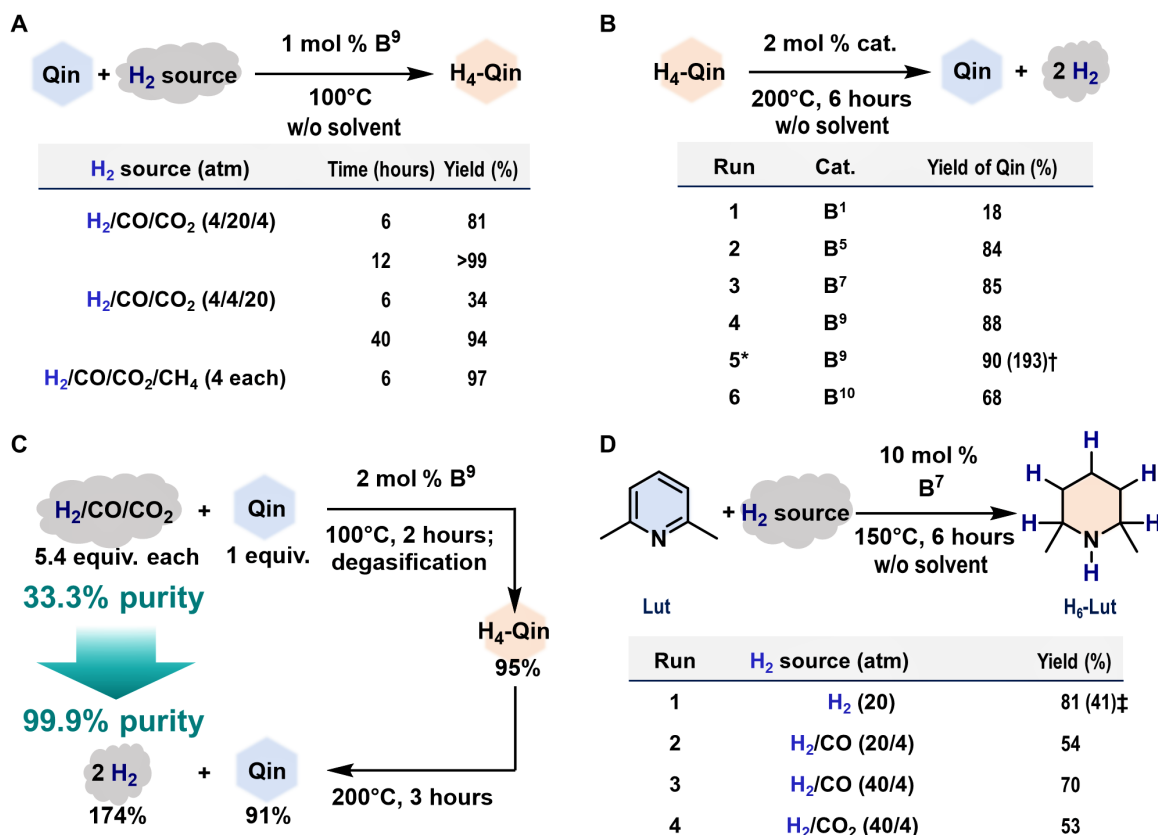


Fig. 3. Direct H₂ purification/storage from contaminated H₂ gas based on the present catalytic process. (A) Exploration of the gas composition of the H₂ source. Yields of **H**₄-**Qin** were determined using GC analysis. (B) Catalytic dehydrogenation of **H**₄-**Qin** (3.8 mmol) to **Qin** in the absence of solvent. Yields of **Qin** were determined by GC analysis. *denotes 2 hours. †denotes yield of recovered H₂ based on the collected volume (V = 164 ml, 7.32 mmol). (C) H₂ purification based on the **B**⁹-catalyzed hydrogenation of **Qin** (1.0 mmol) under mixed gas conditions and subsequent catalytic dehydrogenation. Yield of recovered H₂ based on the collected volume (V = 39.0 ml, 1.74 mmol); H₂ purity (%) = (molar amount of H₂)/(sum of the molar amounts of H₂, CO, and CO₂) × 100. (D) **B**⁷-catalyzed hydrogenation of **Lut** using a variety of H₂ sources that were dried over 4-Å MS before use. ‡indicates that **B**⁹ was used.

complete removal of CO in a single cycle would be especially noteworthy, as the removal of CO remains challenging in the well-developed multistep, multibed PSA and membrane technologies (4).

We further explored the catalytic activity of **B**⁷ and **B**⁹ toward the hydrogenation of **Lut** to afford **H**₆-**Lut** under the mixed gas conditions (Fig. 3D). This further investigation revealed that the H₂ storage capacity could be increased from 2.7 (**H**₄-**Qin**) to 5.3 wt % (**H**₆-**Lut**). Note that **Lut** has been a challenging substrate in previously reported organoborane-catalyzed hydrogenations using H₂ even under diluted conditions (46, 47). In the presence of **B**⁷ (10 mol %) and the absence of solvent, **H**₆-**Lut** was formed in 81% yield using H₂ [20 atm; dried over 4-Å molecular sieves (MSs) before use], while a decrease in yield was observed for **B**⁹ (run 1). Without the dehydration of H₂, the hydrogenation of **Lut** also proceeded to afford **H**₆-**Lut** in 72% under identical conditions (fig. S22). Moreover, **B**⁷ exhibited promising results for the simultaneous separation and storage of H₂ in **H**₆-**Lut** from CO- and CO₂-contaminated H₂ gas (runs 2 to 4), albeit an excess of H₂ with respect to the contaminants was present.

To gain insight into the reaction mechanism for the present hydrogenation of N-heteroaromatic compounds in the presence of CO, CO₂, and H₂O, preliminary mechanistic studies were conducted using **Qin** (Fig. 4). First, we monitored the progress of the conversion of **Qin** to **H**₄-**Qin** using **B**¹, **B**⁷, or **B**⁹ under each condition using solely H₂ or H₂/CO/CO₂ (Fig. 4A). The production of **H**₄-**Qin** exhibited a zeroth-order dependence on the concentration of **Qin** with rate constants (*k*_{obs}) as follows: 3.08(29) × 10⁻⁴ mol m⁻³ s⁻¹ (H₂) and 3.56(60) × 10⁻⁶ m⁻³ s⁻¹ (H₂/CO/CO₂) (**B**¹); 1.71(6) × 10⁻⁴ m⁻³ s⁻¹ (H₂) and 1.66(5) × 10⁻⁴ m⁻³ s⁻¹ (H₂/CO/CO₂) (**B**⁷); and 2.21(13) × 10⁻⁴ m⁻³ s⁻¹ (H₂) and 1.93(10) × 10⁻⁴ m⁻³ s⁻¹ (H₂/CO/CO₂) (**B**⁹). Moreover, these results suggest that **H**₄-**Qin** itself does not affect the rate of hydrogenation, as neither an increase nor decrease in the rate was observed increasing conversion to **H**₄-**Qin**. Thus, the influence of CO and/or CO₂ is almost negligible for the **B**⁷- and **B**⁹-catalyzed hydrogenation processes, at least under conditions that do not involve excess amounts of CO/CO₂ with respect to H₂ (vide supra). In stark contrast, the **B**¹-catalyzed process was significantly inhibited in the presence of CO and/or CO₂. Control experiments using H₂/CO (10 atm each) and H₂/CO₂ (10 atm each) clarified that both CO and CO₂ affect the catalytic activity of **B**¹ and that contamination with CO₂ is especially deleterious (Fig. 4B). We also confirmed the kinetic orders in catalyst **B**⁷ [1.2(1)] and **B**⁹ [1.4(1)] under the H₂/CO/CO₂ atmosphere, demonstrating that these triaryl boranes do catalyze the formation of **H**₄-**Qin** (Fig. 4C).

Next, the influence of CO₂, CO, and H₂O was investigated using **B**¹ and **B**⁹. The hydrogenation of **Qin** was carried out in the presence of each borane (50 mol %) using H₂/CO₂ (2.5 atm each) at 100°C in toluene-*d*₈ and analyzed using multinuclear nuclear magnetic resonance (NMR) spectroscopy. In the case of **B**¹, the resultant mixture included C₆F₅H (20%), an equilibrium mixture of [**H**₄-**Qin**-COOB¹] and [**H**₄-**Qin**-H][**H**₃-**Qin**-COOB¹] (12%) (28, 29), and several unidentified compounds (Fig. 4D and fig. S38). Precipitation of the nitrogen-boron adduct [**H**₄-**Qin**-**B**¹] was also confirmed. We separately confirmed that C₆F₅H was not formed in the absence of CO₂ (fig. S41). These results clarify that CO₂ triggers the irreversible decomposition of **B**¹ to yield C₆F₅H via protodeboronation from both [**H**₄-**Qin**-COOB¹] and [**H**₄-**Qin**-H][**H**₃-**Qin**-COOB¹] under heating conditions. In stark contrast, when **B**⁹ was used, the generation of **H**₄-**Qin** and recovery of **B**⁹ in >99%

yields were observed under otherwise identical conditions. These results are consistent with the fact that the **B**⁹-catalyzed hydrogenation of **Qin** is not irreversibly inhibited by CO₂.

Density functional theory calculations were carried out at the ωB97X-D/6-311+G(d,p)//ωB97X-D/6-31G(d,p)//gas phase level of theory to shed light on the observed kinetic suppression of the hydrogenation of **Qin** by CO (48). The relative Gibbs energies (kilocalorie mole⁻¹) for **OC**-**B**^{*n*} (Lewis pairs comprising CO and **B**^{*n*} and **TS**-**B**^{*n*} (saddle point species) with respect to [CO + **B**^{*n*}] (*n* = 1 and 9) are shown in Fig. 4E. The coordination of CO to the boron atoms in both **B**¹ and **B**⁹ is an endothermic process (29, 33), and coordination to the latter is far less favorable from a kinetic and thermodynamic perspective. The standard Gibbs free energies for the formation of **OC**-**B**^{*n*} are +3.2 (*n* = 1) and +8.1 (*n* = 9) kcal mol⁻¹, and the activation energies to overcome **TS**-**B**^{*n*} are +10.2 (*n* = 1) and +14.3 (*n* = 9) kcal mol⁻¹. These results rationalize the experimental results, i.e., the observations that contamination with excess CO kinetically affects both the **B**¹- and **B**⁹-catalyzed hydrogenation of **Qin** under the applied conditions, with this suppression being significant in the former case. The differences in the stability of **OC**-**B**^{*n*} should be related to the degree of geometric deviation from the ideal tetrahedral geometry around their boron centers, which can be evaluated on the basis of the value of τ₈(B) [τ₈ = {360 - (α + β)/141 × β/α}], where α and β are the largest and second largest C-B-C angles obtained from the gas phase-optimized structures of **OC**-**B**^{*n*}] (49). More efficient orbital overlap between the lone pair on the carbon atom in CO and the p orbital on the boron atom in **B**^{*n*} should result in higher stabilization of **OC**-**B**^{*n*} adducts, adopting a more ideal tetrahedral geometry [τ₈(B) = 0.9 to 1.0] and a linear arrangement of the B-C-O atoms (∠B-C-O ≈ 180°). In the present study, the lower τ₈(B) of 0.88 for **OC**-**B**⁹ indicates that its boron atom adopts a more distorted tetrahedral geometry compared to that of **OC**-**B**¹ [τ₈(B) = 0.92], and the B-C-O atoms in **OC**-**B**⁹ are confirmed to exhibit a bent alignment (169.9° versus 179.6° in **OC**-**B**¹). These results thus demonstrate the effective destabilization of **OC**-**B**⁹ due to the increased steric repulsion between CO and the 2,6-Cl₂-C₆H₃ group introduced on **B**⁹, which eventually results in the reduced impact of CO on the **B**⁹ hydrogenation of **Qin**.

We further evaluated the influence of H₂O on the hydrogenation (Fig. 4F). GC analysis confirmed that no conversion of **Qin** occurred in the presence of H₂ (4 atm) at 100°C when 10 mol % [**Qin**-H][**HO**-**B**¹] was used. Although **H**₄-**Qin** was furnished in 13% yield when 10 mol % [**Qin**-H][**HO**-**B**⁹] was used, the low yield again confirmed the deleterious influence of H₂O. On the basis of these results and the stability of **B**⁹ toward moisture at ambient conditions (vide supra), [**Qin**-H][**HO**-**B**⁹] was not generated under the applied conditions shown in Figs. 2 and 3, although H₂O might be present as a contaminant.

DISCUSSION

The present results demonstrate a proof of concept for a H₂ purification technology based on LOHCs that goes beyond their well-established use in H₂ storage. This technology can be expected to change the industrial value of crude H₂ containing substantial amounts of CO, CO₂, and CH₄, which can be produced from a variety of carbon resources such as biomass and industrial off-gases. The operational simplicity of the present method should allow the construction of combined processes involving PSA and/or membranes. Moreover,

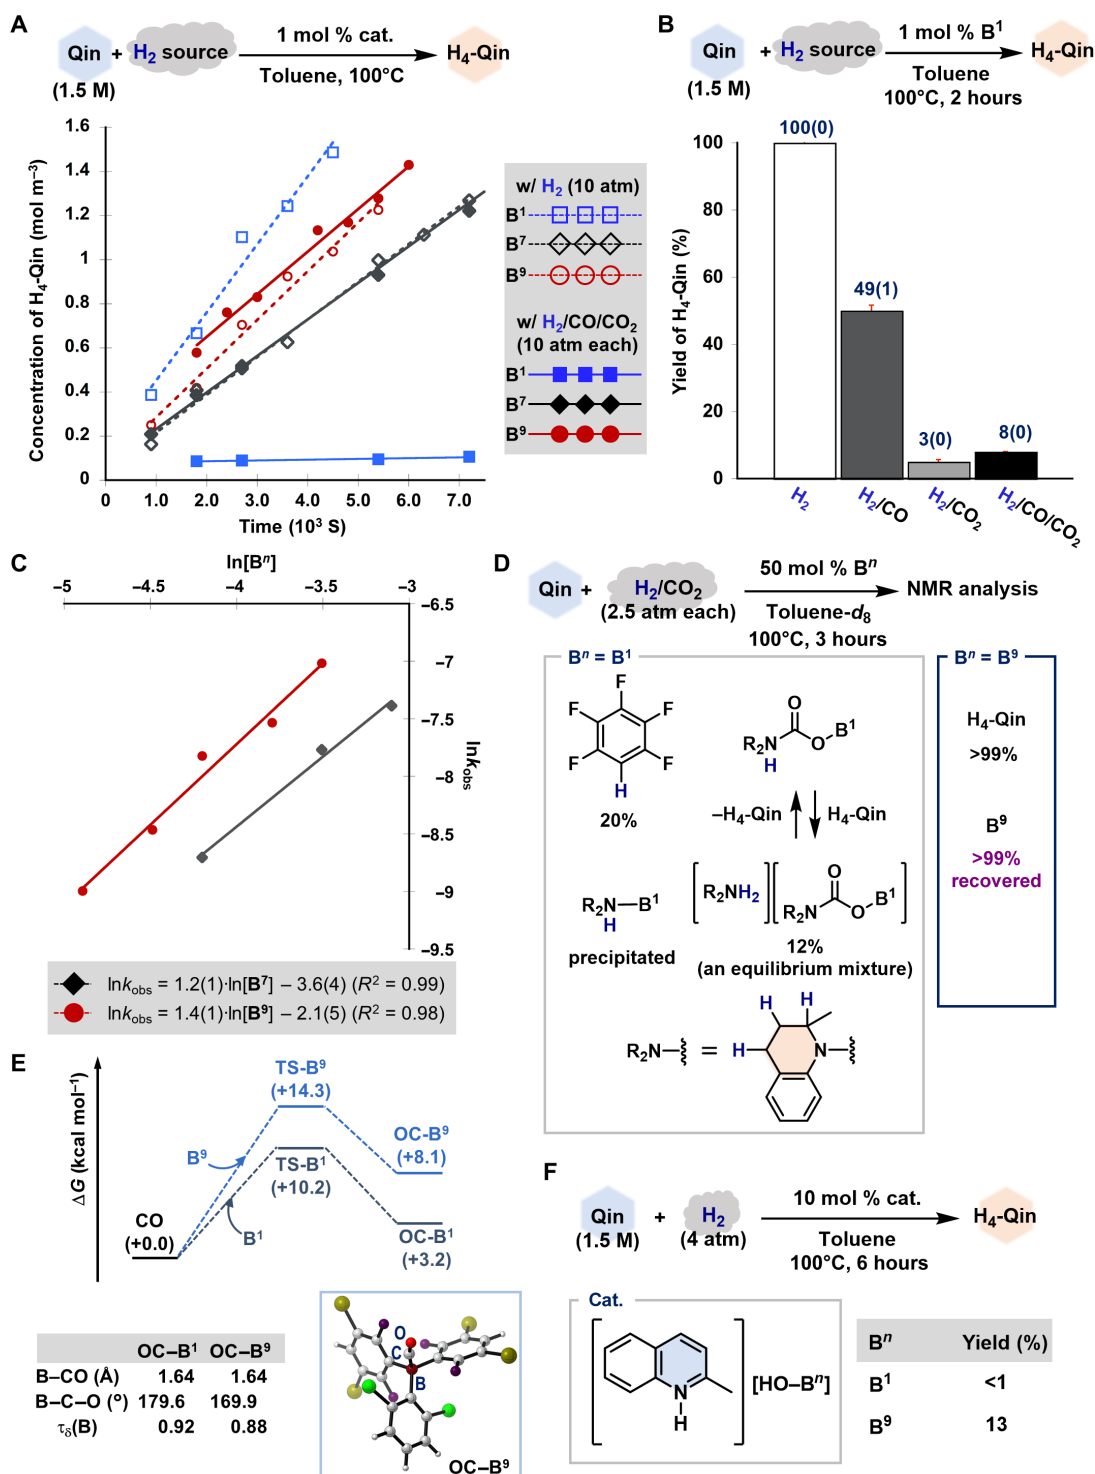


Fig. 4. Mechanistic experiments. (A) Kinetic profiles of the concentration of H₄-Qin (mole meter⁻³) with respect to reaction time (10³ s) obtained from the hydrogenation of Qin (1.5 M in toluene) in the presence of Bⁿ (n = 1, 7, and 9) and different H₂ sources (pure H₂ or H₂/CO/CO₂; 10 atm each). (B) Influence of the gas composition on the B¹-catalyzed hydrogenation of Qin. Each experiment was pressurized with H₂ (10 atm) and/or CO_x (10 atm; x = 1 and/or 2). Average yields of independent three runs are shown with SEs. (C) Profile of ln k_{obs} with respect to ln[Bⁿ] (n = 7 and 9). (D) Detailed analysis of the Bⁿ-catalyzed hydrogenation of Qin (n = 1 and 9) in the presence of H₂/CO₂ (2.5 atm each). Product yields were calculated using ¹⁹F NMR analysis with C₆H₅CF₃ as the internal standard. In the case of B¹, several unidentified resonances were observed (for details, see fig. S38). (E) Calculated free energy profiles for the formation of OC-Bⁿ (n = 1 and 9) [kilojoule mole⁻¹; ωB97X-D/6-311+G(d,p)//ωB97X-D/6-31G(d,p) level]. The gas phase-optimized structure of OC-B⁹ and selected structural parameters for OC-Bⁿ (n = 1 and 9) are also shown. (F) Hydrogenation of Qin using [Qin-H][HO-Bⁿ] (n = 1 and 9). Yields of H₄-Qin were determined via GC analysis.

this work demonstrates a new aspect of main group catalysis beyond its application as a simple alternative to well-established transition metal-catalyzed processes, i.e., the main group-catalyzed hydrogenation of unsaturated molecules under mixed gas conditions.

MATERIALS AND METHODS

General considerations

Unless otherwise noted, all manipulations were conducted under a nitrogen atmosphere using standard Schlenk line or glove box techniques. MSs (4 Å) were activated by heating with a heat gun in vacuo (ca. 0.2 mmHg) for 5 min. ^1H , ^{11}B , ^{13}C , ^{19}F , and ^{31}P NMR spectra were recorded on Bruker Avance III 400 or JEOL JNM-400 spectrometers at 25°C. The chemical shifts in the ^1H NMR spectra were recorded relative to Me_4Si or residual protonated solvent [$\text{C}_6\text{D}_5\text{H}$ (δ 7.16), CHCl_3 (δ 7.26), $\text{C}_7\text{D}_7\text{H}$ (δ 2.08), and CDHCl_2 (δ 5.32)]. The chemical shifts in the ^{11}B NMR spectra were recorded relative to BF_3 . The chemical shifts in the ^{13}C NMR spectra were recorded relative to Me_4Si or deuterated solvent [C_6D_6 (δ 128.06), CDCl_3 (δ 77.16), and CD_2Cl_2 (δ 53.84)]. The chemical shifts in the ^{19}F NMR spectra were recorded relative to α,α,α -trifluorotoluene [δ -65.64]. The chemical shifts in the ^{31}P NMR spectra were recorded relative to 85% H_3PO_4 as an external standard. Assignment of the resonances in ^1H and ^{13}C NMR spectra was based on ^1H - ^1H correlation spectroscopy, heteronuclear multiple-quantum coherence, and/or heteronuclear multiple-bond correlation experiments. High-resolution mass spectrometry was performed at the Instrumental Analysis Center, Faculty of Engineering, Osaka University. A single-crystal x-ray diffraction analysis was carried out using the Rigaku XtaLAB Synergy equipped with the HyPix-6000HE detector. Analytical GC was carried out on a Shimadzu GC-2025 gas chromatograph, equipped with a flame ionization detector, or a Shimadzu GC-2010 gas chromatograph, equipped with a barrier discharge ionization detector.

Materials

All commercially available reagents including superdehydrated solvents (*n*-hexane, toluene, tetrahydrofuran, and diethyl ether) were used as received. Benzene- d_6 and toluene- d_8 were distilled from sodium benzophenone ketyl before use. CDCl_3 and CD_2Cl_2 were stored inside the glove box over MSs (4 Å) after several freeze-pump-thaw cycles. **Qin**, **H₄-Qin**, and **Lut** were used after distillation over CaH_2 . Triaryl boranes (**B²** to **B⁶**), (26, 39–42) potassium (2,6-dichlorophenyl)trifluoroborate, (**A1**) 1,5-dichloro-2,4-difluoro-3-iodobenzene (**50**), 1-chloro-2,4-difluoro-3-iodobenzene (**50**), and 1,5-dibromo-2,4-difluoro-3-iodobenzene (**50**) were prepared by following the reported procedures. Gaseous chemicals including H_2 , CO , CO_2 , CH_4 , H_2/CO (a 1/1 molar ratio), H_2/CO_2 (a 1/1 molar ratio), and $\text{H}_2/\text{CO}/\text{CO}_2$ (a 1/1/1 molar ratio) were purchased and used as received otherwise noted.

Synthesis of **B⁹**

A solution of 1,5-dibromo-2,4-difluoro-3-iodobenzene (3.45 g, 8.67 mmol, 0.29 M in Et_2O) was slowly treated with $i\text{PrMgCl}$ (8.7 ml, 8.7 mmol, 1.0 M in Et_2O). After stirring at room temperature for 1 hour, the resultant solution was transferred into a suspension of potassium (2,6-dichlorophenyl)trifluoroborate (1.05 g, 4.16 mmol, 0.42 M in Et_2O) at 0°C. The reaction mixture was then allowed to warm to room temperature, where it was stirred for another 14 hours. After the removal of all volatiles in vacuo, the residue was extracted

with α,α,α -trifluorotoluene (50 ml for three times; warmed to 70°C before use). The combined organic layers were concentrated in vacuo and washed with hexane (cooled to -20°C before use) to afford **B⁹** as a white solid (2.56 g, 3.66 mmol, 88%).

H₂ purification from $\text{H}_2/\text{CO}/\text{CO}_2$ via a **B⁹-catalyzed hydrogenation/dehydrogenation sequence**

A 30-ml autoclave was charged with **Qin** (145 mg, 1.01 mmol), **B⁹** (13.9 mg, 0.199 mmol), and tetradecane (59.5 mg; internal standard). Once sealed, the autoclave was pressurized with $\text{H}_2/\text{CO}/\text{CO}_2$ (4 atm each; 5.4 mmol each) and heated to 100°C for 2 hours. After cooling to room temperature, all volatiles were removed in vacuo, and GC analysis showed the production of **H₄-Qin** in 95%. Then, the reaction mixture was transferred into a 10-ml two-neck flask. During this manipulation, the residue inside the autoclave reactor was extracted with toluene to minimize the loss of reagents. The toluene was then removed in vacuo; however, this extraction step is not essential for the following dehydrogenation. The reaction mixture was then stirred at 200°C for 3 hours. The volume of collected gas was measured using a graduated cylinder to calculate the yield of H_2 (39 ml, 1.7 mmol). The conversion of **H₄-Qin** (94%), the yield of **Qin** (91%), and the purity of the collected H_2 gas were determined using GC analysis.

SUPPLEMENTARY MATERIALS

Supplementary material for this article is available at <https://science.org/doi/10.1126/sciadv.ade0189>

REFERENCES AND NOTES

1. K. Liu, C. Song, V. Subramani, Eds., *Hydrogen and Syngas Production and Purification Technologies* (Wiley, 2010).
2. F. Dawood, M. Anda, G. M. Shafiqullah, Hydrogen production for energy: An overview. *Int. J. Hydrogen Energy* **45**, 3847–3869 (2020).
3. M. Voldsund, K. Jordal, R. Anantharaman, Hydrogen production with CO_2 capture. *Int. J. Hydrogen Energy* **41**, 4969–4992 (2016).
4. J. D. Holladay, J. Hu, D. L. King, Y. Wang, An overview of hydrogen production technologies. *Catal. Today* **139**, 244–260 (2009).
5. H. Nishiyama, T. Yamada, M. Nakabayashi, Y. Maehara, M. Yamaguchi, Y. Kuromiya, Y. Nagatsuma, H. Tokudome, S. Akiyama, T. Watanabe, R. Narushima, S. Okunaka, N. Shibata, T. Takata, T. Hisatomi, K. Domen, Photocatalytic solar hydrogen production from water on a 100- m^2 scale. *Nature* **598**, 304–307 (2021).
6. Y. Okada, M. Saito, S. Wakayama, M. Shimura, Method for producing hydrogen aimed at storage and transportation, Patent US8758722 (2014); <https://patents.google.com/patent/JP5737853B2/en>.
7. Y. Hoshimoto, S. Ogoshi, T. Tanaka, N. Kawamoto, Method for hydrogenating unsaturated compound, Patent JP2017206474A (2017); <https://patents.google.com/patent/JP2017206474A/en>.
8. E. Gianotti, M. Taillades-Jacquín, J. Rozière, D. J. Jones, High-purity hydrogen generation via dehydrogenation of organic carriers: A review on the catalytic process. *ACS Catal.* **8**, 4660–4680 (2018).
9. H. Jorschick, P. Preuster, A. Bösmann, P. Wasserscheid, Hydrogenation of aromatic and heteroaromatic compounds—A key process for future logistics of green hydrogen using liquid organic hydrogen carrier systems. *Sustain. Energy Fuels* **5**, 1311–1346 (2021).
10. Y.-Q. Zou, N. von Wolff, A. Anaby, Y. Xie, D. Milstein, Ethylene glycol as an efficient and reversible liquid-organic hydrogen carrier. *Nat. Catal.* **2**, 415–422 (2019).
11. T. Shimbayashi, K.-i. Fujita, Metal-catalyzed hydrogenation and dehydrogenation reactions for efficient hydrogen storage. *Tetrahedron* **76**, 130946 (2020).
12. T. He, Q. Pei, P. Chen, Liquid organic hydrogen carriers. *J. Energy Chem.* **24**, 587–594 (2015).
13. K.-i. Fujita, T. Wada, T. Shiraiishi, Reversible interconversion between 2,5-dimethylpyrazine and 2,5-dimethylpiperazine by iridium-catalyzed hydrogenation/dehydrogenation for efficient hydrogen storage. *Angew. Chem. Int. Ed.* **56**, 10886–10889 (2017).
14. P. Hu, E. Fogler, Y. Diskin-Posner, M. A. Iron, D. Milstein, A novel liquid organic hydrogen carrier system based on catalytic peptide formation and hydrogenation. *Nat. Commun.* **6**, 6859 (2015).

15. P. Hu, Y. Ben-David, D. Milstein, Rechargeable hydrogen storage system based on the dehydrogenative coupling of ethylenediamine with ethanol. *Angew. Chem. Int. Ed.* **55**, 1061–1064 (2016).
16. J. Kothandaraman, S. Kar, R. Sen, A. Goeppert, G. A. Olah, G. K. Surya Prakash, Efficient reversible hydrogen carrier system based on amine reforming of methanol. *J. Am. Chem. Soc.* **139**, 2549–2552 (2017).
17. Y. Xie, P. Hu, Y. Ben-David, D. Milstein, A reversible liquid organic hydrogen carrier system based on methanol-ethylenediamine and ethylene urea. *Angew. Chem. Int. Ed.* **58**, 5105–5109 (2019).
18. C. Breakman-Danheux, A. Fontana, P. Laurent, P. Lovlie, Catalytic hydrogenation of polycyclic aromatic hydrocarbons with coke oven gas. *Fuel* **75**, 579–584 (1996).
19. H. Jorschick, M. Vogl, P. Preuster, A. Bösmann, P. Wasserscheid, Hydrogenation of liquid organic hydrogen carrier systems using multicomponent gas mixtures. *Int. J. Hydrogen Energy* **44**, 31172–31182 (2019).
20. K. Revunova, G. I. Nikonov, Main group catalysed reduction of unsaturated bonds. *Dalton Trans.* **44**, 840–866 (2015).
21. M. Oestreich, J. Hermeke, J. Mohr, A unified survey of Si–H and H–H bond activation catalysed by electron-deficient boranes. *Chem. Soc. Rev.* **44**, 2202–2220 (2015).
22. G. C. Welch, R. R. S. Juan, J. D. Masuda, D. W. Stephan, Reversible, metal-free hydrogen activation. *Science* **314**, 1124–1126 (2006).
23. A. R. Jupp, D. W. Stephan, New directions for frustrated Lewis pair chemistry. *Trends Chem.* **1**, 35–48 (2019).
24. D. W. Stephan, Diverse uses of the reaction of frustrated Lewis pair (FLP) with hydrogen. *J. Am. Chem. Soc.* **143**, 20002–20014 (2021).
25. S. J. Geier, P. A. Chase, D. W. Stephan, Metal-free reductions of N-heterocycles via Lewis acid catalyzed hydrogenation. *Chem. Commun.* **46**, 4884–4886 (2010).
26. G. Erős, K. Nagy, H. Mehdi, I. Pápai, P. Nagy, P. Király, G. Tárkányi, T. Soós, Catalytic hydrogenation with frustrated Lewis pairs: Selectivity achieved by size-exclusion design of Lewis acids. *Chem. A Eur. J.* **18**, 574–585 (2012).
27. D. J. Scott, M. J. Fuchter, A. E. Ashley, Metal-free hydrogenation catalyzed by an air-stable borane: Use of solvent as a frustrated Lewis base. *Angew. Chem. Int. Ed.* **53**, 10218–10222 (2014).
28. C. M. Mömning, E. Otten, G. Kehr, R. Fröhlich, S. Grimme, D. W. Stephan, G. Erker, Reversible metal-free carbon dioxide binding by frustrated Lewis pairs. *Angew. Chem. Int. Ed.* **48**, 6643–6646 (2009).
29. D. W. Stephan, G. Erker, Frustrated Lewis pair chemistry of carbon, nitrogen and sulfur oxides. *Chem. Sci.* **5**, 2625–2641 (2014).
30. T. Voss, T. Mahdi, E. Otten, R. Fröhlich, G. Kehr, D. W. Stephan, G. Erker, Frustrated Lewis pair behavior of intermolecular amine/ $B(C_6F_5)_3$ pairs. *Organometallics* **31**, 2367–2378 (2012).
31. A. E. Ashley, A. L. Thompson, D. O'Hare, Non-metal-mediated homogeneous hydrogenation of CO_2 to CH_3OH . *Angew. Chem. Int. Ed.* **48**, 9839–9843 (2009).
32. S. D. Tran, T. A. Tronic, W. Kaminsky, D. M. Heinekey, J. M. Mayer, Metal-free carbon dioxide reduction and acidic C–H activations using a frustrated Lewis pair. *Inorg. Chim. Acta* **369**, 126–132 (2011).
33. M. Finze, E. Bernhardt, A. Terheiden, M. Berkei, H. Willner, D. Christen, H. Oberhammer, F. Aubke, $Tris(trifluoromethyl)borane$ carbonyl, $(CF_3)_3BCO$ -synthesis, physical, chemical and spectroscopic properties, gas phase, and solid state structure. *J. Am. Chem. Soc.* **124**, 15385–15398 (2002).
34. V. Fasano, M. J. Ingleson, Recent advances in water-tolerance in frustrated Lewis pair chemistry. *Synthesis* **50**, 1783–1795 (2018).
35. Y. Hoshimoto, S. Ogoshi, Triarylborane-catalyzed reductive N-alkylation of amines: A perspective. *ACS Catal.* **9**, 5439–5444 (2019).
36. D. Voicu, D. W. Stephan, E. Kumacheva, Microfluidic separation of ethylene and ethane using frustrated Lewis pairs. *ChemSusChem* **8**, 4202–4208 (2015).
37. W.-B. Wang, S.-M. Lu, P.-Y. Yang, X.-W. Han, Y.-G. Zhou, Highly enantioselective iridium-catalyzed hydrogenation of heteroaromatic compounds, quinolines. *J. Am. Chem. Soc.* **125**, 10536–10537 (2003).
38. We also confirmed that the hydrogenation of **Qin** under otherwise identical mixed gas conditions did not proceed effectively and that **H₄-Qin** was obtained only in ~1% when Ru-MACHO and Pd/C were used as catalysts. For experimental details, see the Supplementary Materials.
39. M. Ullrich, A. J. Lough, D. W. Stephan, Reversible, metal-free, heterolytic activation of H_2 at room temperature. *J. Am. Chem. Soc.* **131**, 52–53 (2009).
40. A. E. Ashley, T. J. Herrington, G. G. Wildgoose, H. Zaher, A. L. Thompson, N. H. Rees, T. Krämer, D. O'Hare, Separating electrophilicity and Lewis acidity: The synthesis, characterization, and electrochemistry of the electron deficient $tris(aryl)boranes$ $B(C_6F_5)_{3-n}(C_6Cl_5)_n$ ($n = 1–3$). *J. Am. Chem. Soc.* **133**, 14727–14740 (2011).
41. Á. Gyömöre, M. Bakos, T. Földes, I. Pápai, A. Domján, T. Soós, Moisture-tolerant frustrated Lewis pair catalyst for hydrogenation of aldehydes and ketones. *ACS Catal.* **5**, 5366–5372 (2015).
42. É. Dorkó, B. Kótai, T. Földes, Á. Gyömöre, I. Pápai, T. Soós, Correlating electronic and catalytic properties of frustrated Lewis pairs for imine hydrogenation. *J. Organomet. Chem.* **847**, 258–262 (2017).
43. P. A. Chase, L. D. Henderson, W. E. Piers, M. Parvez, W. Clegg, M. R. J. Elsegood, Bifunctional perfluoroaryl boranes: Synthesis and coordination chemistry with neutral Lewis base donors. *Organometallics* **25**, 349–357 (2006).
44. M. Kojima, M. Kanai, $Tris(pentafluorophenyl)borane$ -catalyzed acceptorless dehydrogenation of N-heterocycles. *Angew. Chem. Int. Ed.* **55**, 12224–12227 (2016).
45. A. F. G. Maier, S. Tussing, T. Schneider, U. Flörke, Z.-W. Qu, S. Grimme, J. Paradies, Frustrated Lewis pair catalyzed dehydrogenative oxidation of indolines and other heterocycles. *Angew. Chem. Int. Ed.* **55**, 12219–12223 (2016).
46. Y. Liu, H. Du, Metal-free borane-catalyzed highly stereoselective hydrogenation of pyridines. *J. Am. Chem. Soc.* **135**, 12968–12971 (2013).
47. P. Eisenberger, B. P. Bestvater, E. C. Keske, C. M. Crudden, Hydrogenations at room temperature and atmospheric pressure with mesoionic carbene-stabilized boronium catalysts. *Angew. Chem. Int. Ed.* **54**, 2467–2471 (2015).
48. The effect of using quinoline as the reaction medium was also simulated using the polarizable continuum model (PCM), which provided virtually identical results. For details, see the Supplementary Materials.
49. M. H. Reineke, M. D. Sampson, A. L. Rheingold, C. P. Kubiak, Synthesis and structural studies of nickel(0) tetracarbene complexes with the introduction of a new four-coordinate geometric index, τ_4 . *Inorg. Chem.* **54**, 3211–3217 (2015).
50. J. T. Manka, P. Kaszynski, Synthesis and thiolation of 1,3-difluoro-2,4,6-trihaloanilines and benzenes. *J. Fluor. Chem.* **124**, 39–43 (2003).
51. P. Sánchez, M. Hernández-Juárez, N. Rendón, J. López-Serrano, L. L. Santos, E. Álvarez, M. Paneque, A. Suárez, Hydrogenation/dehydrogenation of N-heterocycles catalyzed by ruthenium complexes based on multimodal proton-responsive CNN(H) pincer ligands. *Dalton Trans.* **49**, 9583–9587 (2020).
52. M. A. Beckett, G. C. Strickland, J. R. Holland, K. S. Varma, A convenient n.m.r. method for the measurement of Lewis acidity at boron centres: Correlation of reaction rates of Lewis acid initiated epoxide polymerizations with Lewis acidity. *Polymer* **37**, 4629–4631 (1996).
53. Gaussian 16, Revision C.01, M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, G. A. Petersson, H. Nakatsuji, X. Li, M. Caricato, A. V. Marenich, J. Bloino, B. G. Janesko, R. Gomperts, B. Mennucci, H. P. Hratchian, J. V. Ortiz, A. F. Izmaylov, J. L. Sonnenberg, D. Williams-Young, F. Ding, F. Lipparini, F. Egidi, J. Goings, B. Peng, A. Petrone, T. Henderson, D. Ranasinghe, V. G. Zakrzewski, J. Gao, N. Rega, G. Zheng, W. Liang, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, K. Throssell, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. J. Bearpark, J. J. Heyd, E. N. Brothers, K. N. Kudin, V. N. Staroverov, T. A. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. P. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, J. M. Millam, M. Klene, C. Adamo, R. Cammi, J. W. Ochterski, R. L. Martin, K. Morokuma, O. Farkas, J. B. Foresman, D. J. Fox, Gaussian, Inc., Wallingford CT, 2019.
54. J. D. Chai, M. H. Gordon, Long-range corrected hybrid density functionals with damped atom–atom dispersion corrections. *Phys. Chem. Chem. Phys.* **10**, 6615–6620 (2008).
55. J. Tomasi, B. Mennucci, R. Cammi, Quantum mechanical continuum solvation models. *Chem. Rev.* **105**, 2999–3094 (2005).
56. B. Cordero, V. Gómez, A. E. Platero-Prats, M. Revés, J. Echeverría, E. Cremades, F. Barragán, S. Alvarez, Covalent radii revisited. *Dalton Trans.*, 2832–2838 (2008).

Acknowledgments: Y.H. thanks NIPPON SHOKUBAI CO. for valuable suggestions. Parts of the computational calculations were performed using resources of the Research Center for Computational Science, Okazaki, Japan (project: 21-IMS-C105). **Funding:** This project was supported by the Environment Research and Technology Development Fund (JPMEERF20211R01) of the Environmental Restoration and Conservation Agency provided by the Ministry of the Environment of Japan and the Adaptable and Seamless Technology Transfer Program through Target-driven R&D (A-STEP) from the Japan Science and Technology Agency (JST). Y.H. acknowledges financial support from the Yazaki Memorial Foundation for Science and Technology, the Izumi Science and Technology Foundation, the Arai Science and Technology Promotion Foundation, and ENEOS Tonen General Research/Development Encouragement & Scholarship Foundation. T.A. expresses thanks for a Grant-in-Aid for JSPS Fellows. **Author contributions:** Y.H. developed the original concept for this study and conceived the outline of the project. Y.H. directed the project with support of S.O. The experiments and theoretical calculations were carried out by Y.H., T.H., and T.A. The manuscript was written by Y.H. with feedback from the other authors. **Competing interests:** The authors declare that they have no competing interests. **Data and materials availability:** All data needed to evaluate the conclusions in the paper are present in the paper and/or the Supplementary Materials. Metrical data for the following solid-state structures are available from Cambridge Crystallographic Data Centre: CCDC2162155 (**B⁷**), 2162156 (**B⁹**), 2162157 (**B¹⁰**), 2162153 (**[Qin–H][HO–B¹]**), 2162154 (**[Qin–H][HO–B⁹]**), and 2164165 (**H₄-Qin–B¹**).

Submitted 19 July 2022

Accepted 8 September 2022

Published 26 October 2022

10.1126/sciadv.ade0189

Main group catalysis for H₂ purification based on liquid organic hydrogen carriers

Taiki Hashimoto, Takahiro Asada, Sensuke Ogoshi, and Yoichi Hoshimoto

Sci. Adv., **8** (43), eade0189.
DOI: 10.1126/sciadv.ade0189

View the article online

<https://www.science.org/doi/10.1126/sciadv.ade0189>

Permissions

<https://www.science.org/help/reprints-and-permissions>

Use of this article is subject to the [Terms of service](#)