



<b>Title</b>	Selective H-D exchange catalysed by aqueous phase and immobilised Pd nanoparticles
<b>Authors(s)</b>	Sullivan, James A., Flanagan, Keith A., Hain, Holger
<b>Publication date</b>	2008-12-30
<b>Publication information</b>	Sullivan, James A., Keith A. Flanagan, and Holger Hain. "Selective H-D Exchange Catalysed by Aqueous Phase and Immobilised Pd Nanoparticles" 139, no. 3 (December 30, 2008).
<b>Publisher</b>	Elsevier
<b>Item record/more information</b>	<a href="http://hdl.handle.net/10197/4001">http://hdl.handle.net/10197/4001</a>
<b>Publisher's statement</b>	This is the author's version of a work that was accepted for publication in Catalysis Today. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Catalysis Today, 139 (3) 2008-12, pp.154-160. DOI: 10.1016/j.cattod.2008.03.031
<b>Publisher's version (DOI)</b>	10.1016/j.cattod.2008.03.031

Downloaded 2023-10-06T13:54:56Z

The UCD community has made this article openly available. Please share how this access benefits you. Your story matters! (@ucd\_oa)



© Some rights reserved. For more information

# Selective H-D Exchange Catalysed by Aqueous-Phase and Immobilised Pd Nanoparticles

James A Sullivan<sup>1</sup>, Keith A Flanagan<sup>1</sup> and Holger Hain<sup>1,2</sup>,

<sup>1</sup>UCD School of Chemistry and Chemical Biology, Belfield, Dublin 4, Ireland.

<sup>2</sup>Institut fuer Anorganische Chemie, Universitaet Wuerzburg, Wuerzburg Germany.

e-mail: james.sullivan@ucd.ie

## Abstract

Pd nanoparticles (with a mean diameter of  $3.4 \pm 0.5$  nm) prepared through  $\text{BH}_4^-$  reduction of  $\text{Na}_2\text{PdCl}_4$  can catalyse selective H-D exchange (through reaction with  $\text{D}_2\text{O}$ ) at the carbon  $\alpha$  to the N atom of a pyridine ring. Oxidised Pd(II) complex species also present in the nanoparticle dispersion play no part in the exchange.

We have studied the effect of several different variables on the rate of the selective H-D exchange activity for a model pyridine, *i.e.* 4-Dimethylaminopyridine (DMAP). These variables include temperature, nanoparticle aging, nanoparticle re-reduction with  $\text{H}_2$  and nanoparticle immobilisation onto multi-walled carbon nanotubes (MWCNT). We have also extended the study to related pyridine containing molecules.

**Keywords:** Selective H-D exchange, Pd nanoparticles, Carbon nanotubes.

## Introduction

The ability to selectively label molecules with deuterium is extremely important in pharmacological, chemical and environmental research especially in the investigation of reaction mechanisms [1] and kinetics [2] of carbon hydrogen bond activation processes. Deuterated molecules can also be used in stable isotopic tracer studies for use in GC or LC MS internal standardisation as well as in more specialist applications such as the development of non-linear optical materials [3]. Such labelling also provides a route to obtain analogous tritium labelled molecules for radiotracer studies [4]. Furthermore, using acid catalysed, base catalysed or metal catalysed processes [5], D and T labels can be introduced into organic substrates post-synthetically in contrast to the introduction of most  $^{13}\text{C}$  labels and other isotopically labelled atoms. The post-synthetic formation of D-labelled materials has been the subject of recent reviews [2, 6].

Specifically the selective labelling of pyridine and other N-hetero-aromatic units is of particular importance since these components find application in many important pharmaceutical (*e.g.* anti-tuberculosis agents such as isonicotinic hydrazide) [7], agrochemical (*e.g.* feed additives such as nicotinic acid) [8] and industrially relevant chemicals (*e.g.* polymer precursors such as 2-vinyl pyridine) [9] and thus, methods for selectively labelling these materials are important because of the proposed use of such deuterated materials in absorption, metabolism, environmental and toxico-kinetic radiotracer studies [10].

Pd/C catalysts have previously been used [11] to catalyse H-D exchange at activated sites within benzylic compounds using  $\text{D}_2$  as a deuterium source while Pd/C and Pt/C

have been used synergistically [12, 13] to catalyse such reactions on activated and sterically-hindered sites using D<sub>2</sub>O.

There are also many publications dealing with the use of a variety of Pd-based catalysts to perform these reactions on various organic molecules (including N-containing heterocyclic molecules) but several seem to use conditions of relatively high temperature and pressure [14-16]. Activated Pd/C catalysts have also been frequently used in combination with D<sub>2</sub>O as the D<sub>2</sub>-source for labelling of benzylic as well as un-activated compounds [15, 17-20, 25].

Recently, we have described the preparation and characterisation of a relatively monodisperse aqueous phase DMAP stabilised Pd nanoparticle dispersion [21]. During the course of the characterisation of this dispersion it became apparent that (a) there existed within the dispersion an oxidised ionic Pd(II) species (which proved to be an active Suzuki coupling catalyst [22, 23]) that formed from reaction of the nanoparticles with air and (b) the nanoparticles within the dispersion were active in promoting selective H-D exchange of the protons  $\alpha$  to the endocyclic N atom of the DMAP molecule through reaction with D<sub>2</sub>O.

This selective H-D exchange of DMAP was previously confirmed using <sup>1</sup>H NMR, FTIR and high resolution mass spectrometry [21]. Figure 1(i) shows a <sup>1</sup>H NMR spectrum of a fresh dispersion and a dispersion which was held in D<sub>2</sub>O. Figure 1(ii) shows a DRIFTS spectrum of the 4-DMAP used in the initial nanoparticle dispersion preparation and the 4-DMAP isolated from such dispersions. The former spectra

**Deleted:** In this manuscript we describe the use of Pd nanoparticles as a catalyst that promotes selective H-D exchange at the less activated  $\alpha$  position of 4-substituted pyridines. We look at some factors which influence the rate and selectivity of this exchange reaction (temperature, age of the nanoparticle dispersion and the presence of H<sub>2(g)</sub>). Furthermore, via judicious ligand exchange techniques, we develop a recyclable Pd-MWCNT composite material by immobilising the nanoparticles onto MWCNTs. We demonstrate that this composite material also catalyses the selective H-D exchange reaction for the 4-DMAP molecule and more importantly allows us to extend this catalytic activity to other pyridine-based substrates.¶

shows the disappearance of resonances at  $\delta \sim 8.0$  which are due to  $\alpha$  protons in both the stabilizing DMAP molecules and also in oxidised Pd(II)DMAP complexes which formed in the dispersion over time while the latter highlight the lower energy aromatic C-D vibrations (at  $\sim 2240 \text{ cm}^{-1}$  compared to aromatic C-H stretches at  $\sim 3000 \text{ cm}^{-1}$ ). Analysis of the  $^1\text{H}$  NMR spectra suggests these  $\alpha$  protons are selectively exchanged with Deuterium from the  $\text{D}_2\text{O}$  over the period of two days with no such exchange seen on the aromatic  $\beta$  or methyl protons of the DMAP molecule. The mass spectrum of the post-exchanged DMAP molecules confirmed the replacement of two H atoms by two D atoms in all the isolated DMAP molecules.

In this manuscript we describe the use of Pd nanoparticles as a catalyst that promotes selective H-D exchange at the less activated  $\alpha$  position of 4-substituted pyridines. We look at some factors which influence the rate and selectivity of this exchange reaction (temperature, age of the nanoparticle dispersion and the presence of  $\text{H}_{2(\text{g})}$ ). Furthermore, via judicious ligand exchange techniques, we develop a recyclable Pd-MWCNT composite material by immobilising the nanoparticles onto MWCNTs. We demonstrate that this composite material also catalyses the selective H-D exchange reaction for the 4-DMAP molecule and more importantly allows us to extend this catalytic activity to other pyridine-based substrates.

**Comment [KF1]:** I know we cut the last bit of the introduction because it was a repetition of what we say here. I feel this fits better here now than above.

## Experimental

All chemicals were used as supplied by the Sigma-Aldrich Chemical Company Ltd or, unless otherwise stated. Sodium tetrachloropalladate(II) was purchased from Reagecon. All chemicals were used as received without further purification. Multi-Walled-Carbon-Nanotubes (MWCNTs), prepared by a carbon arc discharge method, were supplied by the MER Corporation. Polycarbonate membrane filters ( $0.2 \mu\text{m}$

pore diameter) were purchased from Whatman-UK. The water used in all experiments was distilled deionized Millipore-MilliQ water ( $18 \text{ M}\Omega \text{ cm}^{-1}$ ).

### *Catalyst Preparation*

(a) Nanoparticle dispersions were prepared as previously reported [21].  $\text{Na}_2\text{PdCl}_4$  (0.127 mmol) was dissolved in distilled-deionised water (3 mL) and stirred vigorously. 4-Dimethylaminopyridine (DMAP) (0.682 mmol) was sonicated into 9 mL of distilled-deionised water and added to the stirring solution. The resulting mixture was stirred for 20 minutes. This solution was reduced by the addition of  $\text{NaBH}_4$  (1% w/v, 1.100 mL) in 0.100 mL aliquots. A colour change from pale yellow to black was observed immediately. The resulting DMAP stabilised palladium nanoparticles were stirred vigorously for a further 30 minutes. TEM analysis has shown that the particles, which are stable in solution for more than 6 months,[22] have a mean diameter of  $3.4 \pm 0.5 \text{ nm}$ .

To facilitate  $^1\text{H}$  NMR characterisation of the nanoparticle dispersions and to analyse the selective H-D exchange activity of the prepared particles, the nanoparticles were also produced in  $\text{D}_2\text{O}$ . The preparation procedure was the same as described above except reduced to one third the amounts described above.

### (b) Thiol-Modified Multi-Walled Carbon Nanotubes

To facilitate the immobilisation of the Pd nanoparticles we employ a previous observation that the DMAP stabilising ligand can be easily removed from the Pd

nanoparticles and replaced with a thiol ligand [21]. We have used this chemistry to immobilise the nanoparticles onto the thiol-modified MWCNTs.

Deleted: 24

Multi-Walled-Carbon-Nanotubes (MWCNTs), prepared by a carbon arc discharge method, were supplied by the MER Corporation and thiolated using a slightly modified procedure to that described by Sainsbury et al. [24] as follows: As-received MWCNTs (0.003 g) were suspended in nitric acid (3 mL, 70% w/w) by sonication (15 minutes). The resulting black suspension was refluxed for 24 hours at 130 °C and allowed to cool to room temperature. The suspension was then filtered through a polycarbonate membrane filter (Whatman-UK, 0.2 µm pore diameter) and washed with deionised-distilled water (1 L). The MWCNTs retained on the membrane filter were suspended in deionised-distilled water (10 mL) by sonicating the filter membrane (10 minutes).  $\text{KMnO}_4$  (0.009 g,  $5.696 \times 10^{-5}$  mol) was added and the resulting dark-purple suspension cooled in an ice bath to 0 °C under magnetic stirring for 1 h.  $\text{HClO}_4$  (3 mL, 70% w/w) was added to the solution, which was stirred at room temperature for 1 hour. Citric acid monohydrate (0.186 g,  $8.851 \times 10^{-4}$  mol) was added and the suspension was stirred until it became grey in colour. The resulting suspension of MWCNTs was filtered through a polycarbonate membrane filter (Whatman-UK, 0.2 µm pore diameter) and washed with deionised-distilled water (1 L).

The retained MWCNTs were suspended in deionised-distilled water (10 mL) through sonication of the filter membrane. DMAP (0.003 g,  $2.456 \times 10^{-5}$  mol,) and 1-(3-Dimethylaminopropyl)-3-Ethyl-Carbodiimide Hydrochloride (EDAC) (0.191 g, 9.963

$\times 10^{-3}$  mol) were added and stirred for 10 minutes. 2-mercaptoethylamine hydrochloride (0.050 g,  $4.401 \times 10^{-4}$  mol) was added and the resulting suspension stirred for 24 hours at room temperature. The suspension of MWCNTs was filtered through a polycarbonate membrane filter (Whatman-UK, 0.2  $\mu\text{m}$  pore diameter) and washed with deionised-distilled water (1 L). The retained MWCNTs were again suspended in deionised-distilled water (10 mL) by sonication and were ready for use.

(c) MWCNT/Pd-DMAP NP composites, *i.e.* Multi-Walled-Carbon-Nanotube/DMAP Stabilised Pd Nanoparticle composites were prepared by the addition of a known amount of DMAP stabilised palladium nanoparticle dispersion to thiol-modified multi-walled-carbon-nanotubes.

In a typical composite preparation, 3 separate 1 mL aliquots of the prepared thiolated MWCNTs were sonicated for 5 minutes and the DMAP stabilised palladium nanoparticle dispersion (65  $\mu\text{L}$  of an 887 ppm Pd dispersion) was added to each with brief mixing. Over the next 10 hours the three resulting composite solutions precipitated twice and were subsequently redispersed by sonication for 10 seconds. The three separate composite solutions were then combined and left for 12 hours to fully precipitate. The resulting clear supernatant was carefully removed and distilled-deionised water (3 mL) was added followed by sonication for 10 seconds.

This subsequent MWCNT/Pd-DMAP NP composite solution was filtered through a polycarbonate membrane filter (Whatman-UK, 0.2  $\mu\text{m}$  pore diameter) and the retained composite was washed with a further 100 mL of distilled-deionised water and



1 mL of D<sub>2</sub>O. The retained composite was removed from the membrane by sonication into ~2 mL of D<sub>2</sub>O and was ready for use. An aliquot of the resulting MWCNT/Pd-DMAP NP composite (10 μL) was deposited on a carbon-coated copper grid and was characterised by TEM. The average Pd nanoparticle size, as measured by TEM, is 3.6±0.6 nm. Figure 2 gives a schematic of the composite preparation procedure, a typical TEM and a histogram showing Pd nanoparticle size distribution.

#### *Selective H-D Exchange Activity tests*

The selective H-D exchange of the DMAP and other pyridine based molecules was followed using <sup>1</sup>H NMR spectrometry by monitoring the various proton resonances against those of an appropriate internal standard (1,2-ethylene glycol). All <sup>1</sup>H nuclear magnetic resonance spectra (<sup>1</sup>H NMR) were recorded on a Varian 300 MHz FT-NMR spectrometer using Mestrec software to evaluate relevant sample and internal standard peak integrations.

#### (a) Selective H-D exchange of DMAP using the nanoparticle dispersion

In a typical experiment 0.040 ml of internal standard (0.078 ml 1,2-ethylene glycol in 2.00 ml D<sub>2</sub>O) was added to 0.8 ml of a nanoparticle preparation (prepared as above) in D<sub>2</sub>O. <sup>1</sup>H NMR spectra were run relatively frequently for the first three hours following preparation of the dispersion and subsequently run at less frequent intervals (*e.g.* samples were left overnight *etc.*)

Parameters such as temperature (RT, 50°C and 80°C), age of the nanoparticle dispersion (fresh and 1 month old) and effect of H<sub>2</sub>/Ar (3% H<sub>2</sub>) treatment (flow rate ~200 ml/min for 30 min) were varied during these experiments. Typically, in a dispersion catalysed reaction the mol % of Pd (relative to DMAP substrate) was ~16%.

For experiments where fresh DMAP (16.4 μmols) in D<sub>2</sub>O (50 μmols) was added to the preformed nanoparticle dispersion (800 μL) the mol% of Pd (relative to the added DMAP substrate) was ~ 41 %.

It should be noted that after certain periods of time the nanoparticles precipitated from solution. This time proved to be shorter at higher temperatures. However they could be re-dispersed with short sonication and no long-term deterioration of the nanoparticles was observed following such a precipitation.

(b) Selective H-D exchange of DMAP and related pyridine-based molecules using MWCNT/Pd-DMAP NP composite.

MWCNT/Pd-DMAP NP composite prepared as above was removed from the membrane by sonication for 30 seconds into 2 mL of the *reaction solution* (see below). The membrane was removed and washed with less than 1 ml of the *reaction solution* if necessary to ensure all composite was removed. The subsequent reaction mixture was heated to 50°C for 5 hrs while H<sub>2</sub>/Ar (3% H<sub>2</sub>) was bubbled through the solution (~200 ml/min). The reaction mixture was cooled and sonicated periodically

during this period. After 5 hours the reaction was cooled and again sonicated to remove the composite from the walls of the reaction vessel. The reaction mixture was filtered through a polycarbonate membrane (Whatman-UK, 0.2  $\mu\text{m}$  pore diameter). Another 1 mL of  $\text{D}_2\text{O}$  was added to the reaction vessel, sonicated and also filtered. The filtrate was analysed by  $^1\text{H}$  NMR spectroscopy characterisation and compared to the  $^1\text{H}$  NMR spectrum of the starting *reaction solution* to study the selectivity and yield of deuterated target molecule (Mestrec software used). The composite retained on the membrane was sonicated into the next reaction solution and was ready for re-use.

Note the *reaction solution* involved a mixture of the target for selective H-D exchange (DMAP or other related pyridine-based molecule) (82  $\mu\text{mol}$ s) dissolved in 10 mL  $\text{D}_2\text{O}$  with sonication and 125  $\mu\text{L}$  of EG standard solution was added (78  $\mu\text{l}$  ethylene glycol in 2 ml  $\text{D}_2\text{O}$ ). A  $^1\text{H}$  NMR of this solution (800 $\mu\text{l}$ ) was run prior to any selective H-D exchange reaction.

Typically, in a recyclable composite catalysed reaction (given that 80% of Pd in a dispersion can be immobilised<sup>13</sup>) the mol % of Pd (relative to the moles of substrate) was  $\sim 8$  mol %.

#### *Catalyst Characterisation Techniques*

All Transmission Electron Microscopy (TEM) images were recorded using a JEOL JEL-2000 EX electron microscope with a lattice resolution of 0.14 nm and a point-to-point resolution of 0.3 nm operating at 80 kV. Samples were prepared by evaporating

a drop of the appropriate dispersion onto the surface of a carbon-coated 400 square mesh copper TEM grid.

## Results and Discussion

When considering the effects of different parameters on the rate of the selective H-D exchange activity for pyridine-containing molecules, it should firstly be stated that there is no H-D exchange noted at any stage in the absence of Pd in solution. Furthermore, experiments at extended times in the presence of Pd(DMAP)<sub>4</sub>(OH)<sub>2</sub> complexes which can be isolated from the nanoparticle dispersion [21] also show no measurable (by <sup>1</sup>H NMR) deuterium exchange activity. This complex has previously been shown to contribute substantially to the catalytic activities of the Pd nanoparticle dispersions in the promotion of model Suzuki reactions [22, 23]. Finally, the functionalised and non-functionalised MWCNTs do not promote H-D exchange in the absence of Pd nanoparticles. Therefore it is clear that it is the Pd nanoparticles that catalyse this reaction under the basic conditions of the nanoparticle dispersion (pH > 9).

### *Effect of Temperature.*

Figure 3 shows the effect of temperature on the selective H-D exchange activity of three freshly prepared nanoparticle dispersions as monitored by the disappearance of the resonances attributed to the  $\alpha$  protons of DMAP. It is clear that at elevated temperatures there is a more rapid exchange of the  $\alpha$  protons. However, it should be noted that there is also a less desired side reaction seen at elevated temperatures where the  $\beta$  protons are also exchanged to a certain extent *e.g.* ~16% of the  $\beta$  protons were exchanged following 5 h of reaction at 80 °C. On the other hand no exchange of the  $\beta$

protons was noted from any nanoparticle dispersion which had been maintained at room temperature even following extended periods of time (> 4 months).

This suggests that the mode of co-ordination of the DMAP molecules becomes less selective at higher temperatures with perhaps the DMAP adsorbing side-on or face-on to the nanoparticles rather than through the endocyclic N atom.

*Effect of extra DMAP addition.*

In order to determine whether the exchange of the  $\alpha$  protons was a result of reactions taking place during the formation of the nanoparticle dispersion or whether it was due to some catalytic function of the nanoparticle dispersion an experiment was carried out where extra DMAP (at ~40% of the initial level) was added to a dispersion held at 50 °C approximately 25 hours following its initial preparation, *i.e.* when more than 98% of the DMAP initially present had already undergone H-D exchange. The final profile (black circles) in Figure 3 shows the exchange of the  $\alpha$  protons from this sample as a function of time. Two features should be noted here. Firstly the added DMAP does undergo H-D exchange – proving that the formation of the nanoparticles is not a crucial step in the exchange process, and secondly, the rate of decrease of the signal attributed to the  $\alpha$  protons is far lower than it was initially for fresh nanoparticles. An induction period of ~ 5h is noted before exchange begins and over 30% of the  $\alpha$  protons remained un-exchanged after ~ 50 h of further reaction at 50 °C. Note: In the case of the fresh nanoparticles approximately twice this concentration of DMAP underwent ~ 90% exchange at 50 °C in roughly three hours.

The fact that extra DMAP added to the nanoparticle dispersion also undergoes H-D exchange is important when considering the possible modularity of this catalyst and extension of its activity to other related molecules (discussed later).

#### *Effect of dispersion age.*

The final result above also suggests that the promotion of the H-D exchange reaction becomes less effective as the nanoparticles age. We envisage two possible explanations for this behaviour, *i.e.* the Pd surface becomes passivated due to the build-up of 2<sup>nd</sup> and subsequent layers of stabilising DMAP or the Pd surface becomes deactivated due to the formation of a passivating oxygen over-layer. To further assess this feature the activity of two differently aged nanoparticle dispersions in promoting the exchange of the  $\alpha$  protons of freshly added DMAP was determined.

In Figure 4 the H-D exchange profile of a fresh dispersion (at 50 °C) is compared to that of a dispersion which had been aged for one month (with additional DMAP added to ~40% of the concentration present in the initial preparation). It is clear that (as expected from the results shown in Figure 3) the H-D exchange rate is far faster over the fresh dispersion than over the aged dispersion. Over 70% of the  $\alpha$  protons of the DMAP added to the aged nanoparticle dispersion still remain un-exchanged after 170 hours in D<sub>2</sub>O.

#### *Effect of treatment with H<sub>2</sub>.*

Several workers [12-13, 25-26] who have previously studied exchange reactions over group VIII metals have used “catalytic amounts” of H<sub>2</sub> within their reaction protocols. We assume (although it is not explicitly stated) that at least one function of H<sub>2</sub> is to

keep the Pd in a reduced state although Esaki et al.[15, 26] also postulate a direct role for H<sub>2</sub> in the reaction mechanism for the H-D exchange of the carbon skeleton of aliphatic alcohols. These authors also speculate that H<sub>2</sub> may keep Pd in a zero valent state.

The third profile in Figure 4 shows the H-D exchange activity of an aged dispersion (at 50 °C) that had been pre-treated in bubbling H<sub>2</sub>/Ar (3% H<sub>2</sub>) for 30 minutes at this temperature prior to the addition of the extra DMAP.

It is obvious that the rate of H-D exchange over this aged and H<sub>2</sub>-treated dispersion (while not being as rapid as that of the fresh catalyst) is significantly higher than that of the aged nanoparticle dispersion which has not been so treated. If it is assumed that the H<sub>2</sub> facilitates the reduction and removal of any Pd-O surface species (and it has been shown that H<sub>2</sub> can reduce particles of Pd-O below room temperature) [27-29] then we can suggest that a reason for decreased H-D exchange rate over older nanoparticle dispersions relates to the formation of an oxygen containing species which either blocks access to the surface or modifies the interaction of the pyridine-containing molecules with the surface in a manner that slows the reaction.

Further experiments (results not shown) using nanoparticle dispersions which were aged for longer than that shown in Figure 4 (4 month versus 1 month aged) showed similar activity profiles in the absence and presence of H<sub>2</sub>. This shows that further aging does not severely further affect the activity of these nanoparticles.

**Comment [KF2]:** Did we do deuteration experiments with nanoparticle dispersions aged for 4 months?

As an aside, these particular nanoparticles are oxidation sensitive and do rapidly oxidise under atmospheric conditions to yield a Pd(II)DMAP complex [21, 22]. However, the rate of this atmospheric oxidation slows over time (such that the nanoparticles are stable for periods in excess of 6 months) and we assume that this is also due to the build up of a passivating overlayer on the Pd surface.

To our knowledge there are no reports of the formation of any such oxygen overlayers on Pd nanoparticles following room temperature exposure to O<sub>2</sub>. However, recent work using model supported Pd nanoparticle systems, has shown that Pd nanoparticles chemisorb O<sub>2</sub> at temperatures below 400 K [30-32] and that the extent of this oxidation varies inversely as a function of the nanoparticle size. Thus it is not improbable that the nanoparticles described here are - to some extent - poisoned by O<sub>2</sub> following their preparation.

*Immobilisation of the nanoparticles and recycling of the supported Pd catalyst.*

In order for this catalytic system to be of practical use in the production of selectively deuterated molecules for use in further kinetic, radiotracer or calibration functions it is obviously necessary to be able to remove the product molecules from the reaction mixture. Isolating the deuterated DMAP molecules from the nanoparticle dispersion following the exchange reaction, by necessity, involves precipitating the nanoparticles since the DMAP plays a vital role in stabilising the nanoparticles against aggregation and irreversible precipitation.

This is not ideal in terms of a modular catalytic process where a recyclable catalyst



would be desired. Immobilising the nanoparticles onto a solid support offers a solution to this issue. Previously we have immobilized these nanoparticles onto thiolated multi walled carbon nanotubes MWCNT [22, 23] (see experimental section) and have used these composite materials as catalysts in model Suzuki coupling reactions [23].

Another benefit of such immobilisation would be that selective H-D exchange reactions could be performed on pyridine-containing molecules that do not themselves stabilise the Pd nanoparticles. This is in contrast with the nanoparticle dispersion catalysed system discussed above where only molecules that can adsorb onto the nanoparticle surface, form an electrical double layer and thus prevent irreversible aggregation may undergo selective H-D exchange in this manner. Other advantages in this process is that any work-up procedure would be considerably simplified in the presence of a heterogeneous catalyst and the possibility of Pd atom incorporation into the product molecules is much decreased.

**Deleted:** possibilities

Figure 5 shows the H-D exchange levels observed using the Pd-MWCNT composite as a catalyst following a 5 hour reaction at 50 °C. The levels of Pd present in the reaction mixtures were approximately 1.3  $\mu\text{mol}$ , *i.e.* ~8 mol % of the reaction mixture.

The first set of data indicates that no H-D exchange whatsoever is observed under these reaction conditions using the Pd-MWCNT composite material directly following its preparation.

The second data set shows that there is a dramatic increase in reactivity when the reactions are carried out in the presence of bubbling H<sub>2</sub>/Ar. The activity is dramatically increased but there is a decrease in selectivity, with a certain amount (~13%) of the  $\beta$  protons also becoming exchanged.

We can attribute the increased reactivity to the presence of H<sub>2</sub> which removes Pd-O species from the surface of the catalyst thereby freeing adsorption sites for the added DMAP to adsorb and undergo the exchange reaction.

The formation of a certain amount of  $\beta$  exchanged DMAP molecules is also not a surprise given the elevated temperature of this reaction. Under these conditions the nanoparticle dispersion itself (see above) also catalyses a certain amount of non-selective aromatic H-D exchange. Thus it is clear that carrying out the exchanges at lower temperatures leads to slower but more selective reactions.

The final set of data shows that the composite material can behave as a recyclable catalyst following filtration and washing. In a repeat H-D exchange experiment using the same sample of catalytic composite with freshly added DMAP, it is observed that the activity and selectivity of the composite is not significantly altered ( $\alpha$  exchange falls from 87% to 83% and the level of  $\beta$  exchange falls from 13% to 12%). Therefore it can be concluded that the composite is an active and recyclable catalyst for this particular exchange reaction.

*Extending the H-D exchange reaction to related substrates.*

**Comment [KF3]:** I would remove this, if we are lucky enough that the reviewer lets us get away with it. I would then say nothing in the manuscript.

Anyone reading this manuscript would say to themselves why didn't they just do repeat deuteration recycling.

**Deleted:** We have further tested the recyclability of these composite catalysts in Suzuki coupling reactions which operated under far more demanding conditions, *i.e.* under reflux (100 °C) in the presence of Na<sub>2</sub>CO<sub>3</sub>, 4-halobenzoic acid and phenylboronic acid for reaction times of 6 h [23]. Only minimal deactivation of the catalysts was observed under these conditions. Given these results and the fact that catalyst ageing beyond 1 month (see above) does not severely further affect catalyst activity or selectivity gives us confidence that these composites do not become deactivated under the H-D exchange reaction conditions used here. ¶

While the prepared composite can be used and reused to promote the selective exchange reaction of the  $\alpha$  protons in DMAP, it would be exceptionally useful if the selectivity and reactivity of the material could be extended to other related substrates. In our first attempts to extend the activity and selectivity of the composite to related substrates of interest the two analogues 4-aminopyridine and 4-hydroxypyridine were chosen for further study. It should be noted that previously Werstiuk and Ju [33] have exchanged the aromatic protons on 2-hydroxy pyridine and 2-mercapto pyridine using  $D_2O$  as a deuterium source. These authors noted a certain amount of selectivity in the reaction with hydrogens at C3, C5 and C6 preferentially exchanging in both molecules. However, these reactions were carried out at temperatures of 200 and 260 °C in the absence of any catalyst. We would hope that the process described here would provide H-D exchange selectivity under far more benign conditions.

Figure 6 shows the level of H-D exchange observed for the  $\alpha$  and  $\beta$  protons of these molecules using the Pd-MWCNT composite following the same reaction regime as was used in the reactions shown in Figure 5 (*i.e.* a 5 hour reaction at 50 °C). The reactivity and selectivity of the exchange reaction using DMAP as the substrate and composite as the catalyst is also shown to aid comparison.

The first alternative substrate analysed for selective H-D exchange was 4-aminopyridine. The H-D exchange characteristics (level of  $\alpha$  and  $\beta$  exchange) following such a 5 hour reaction in  $D_2O$  with the composite material in the presence of bubbling  $H_2/Ar$  are similar to those of the DMAP molecule, *i.e.* 76 %  $\alpha$  exchange and 17%  $\beta$  exchange (compared to 87% and 13% respectively for DMAP). This

shows that the 4-aminopyridine has similar adsorption and reaction properties to its di-methylated analogue.

When the substrate is further altered (to 4-hydroxy pyridine) the H-D exchange reactivity is much decreased and the  $\alpha$  /  $\beta$  selectivity is inverted, *i.e.* the overall level of aromatic H-D exchange is lower than in the previous cases and the selectivity is altered in that the  $\beta$  protons of the aromatic ring (34% exchanged after 5 hours) are more rapidly exchanged than the  $\alpha$  protons (6% exchanged after 5 hours). This suggests that the 4-hydroxypyridine co-ordinates in a different manner to the surface of the Pd nanoparticles than the aminopyridine-type molecules and that this co-ordination is of extreme importance in the reaction process.

These reactions were also repeated with recycled composite materials and the activity / selectivity profiles were not significantly different to those shown in Figure 6 (results not shown).

**Comment [KF4]:** They will ask why didn't you show them???

## Conclusions

An aqueous phase dispersion of Pd nanoparticles with a mean diameter of  $3.4 \pm 0.5$  nm can catalyse the selective H-D exchange reaction at carbons  $\alpha$  to the endocyclic N atom of the aromatic ring of pyridine-containing compounds through reaction with  $D_2O$ .

Increasing the temperature increases the rate of this exchange but decreases the selectivity of the reaction with minor amounts of H-D exchange also occurring at the  $\beta$  position of the aromatic ring.

The reaction is slower using aged nanoparticles and this decrease in activity is ascribed to the growth of an oxygen overlayer with time following the initial preparation of the dispersion. This effect can be ameliorated by pretreatment of the particles in  $H_2$  prior to reaction or by the continuous bubbling of  $H_{2(g)}$  into the reaction mixture.

The system can be heterogenised by immobilisation of the Pd nanoparticles onto functionalised (thiolated) multi walled carbon nanotubes thereby generating a Pd-MWCNT composite. This composite material is active in promoting the H-D exchange reaction at the  $\alpha$  position of DMAP and 4-aminopyridine.

However, attempts to extend this activity and selectivity to other related molecules have shown that the presence of other functional groups within the substrate of interest can have detrimental consequences for both the activity and the selectivity of the reaction. We ascribe this effect to varied modes of coordination of the substrates to the Pd nanoparticle surface resulting in different selectivities.

**Deleted:** different and

**Comment [KF5]:** I think this was related to our initial proposed mechanism, which we have now removed.

**Deleted:** types of stabilised anion intermediates and thus different

### **Acknowledgements.**

We gratefully acknowledge funding from EPA Ireland and invaluable discussions with Prof M. Brust. We also acknowledge travel funding to allow JAS attend the

Helsinki workshop from the COST network through COST action D36 and funding for HH through the EU Socrates-Erasmus exchange programme.

## References

- 1 D. M. Marcus, K. A. McLachlan, M. A. Wildman, J. O. Ehresmann, P.W. Kletnieks, J. F. Haw, *Angew. Chem.* 2006, 118, 3205 – 3208.
- 2 T. Junk and W.J. Catallo, *Chem. Soc. Rev.* 26, (1997), 26, 401.
- 3 M. Okazaki, N. Uchino, N. Nozaki and K. Kubo, *Bull. Chem. Soc. Jpn.* 68, (1995), 1024.
- 4 M. Saljoughian and P.G. Williams, *Current Pharmaceutical Design*, 6, (2000), 1029.
- 5 N. Elander, J.R. Jones, S.-Y Lu, and S. Stone-Elander, *Chem. Soc. Rev.* 29, (2000), 239.
- 6 J. Atzrodt, V. Derdau, T. Fey, T. and J. Zimmermann, *Angew. Chem. Int. Ed.* 46, (2007), 7744.
- 7 A.E. Perelman, B.I. Vishnevskii, G.I. Vavilin, T.B. Ilina, T.M. Yakovleva, V.A. Kropachev and L.B. Trukhmanova L.B., *Pharma. Chem. J.* 11, (1977), 1573.
- 8 Y. Higashio and T. Shoji, *Appl.Catal. A:Gen.*, 260, (2004), 251.
- 9 A.R. Sherman in *Encyclopedia of Reagents for Organic Synthesis* (2004), J.Wiley and Sons, New York.

Comment [KF6]: Full stop

Deleted: ;

Comment [KF7]: Full stop

- 10 E. Alexakis, J.R. Jones, and W.J.S. Lockley, *Tet. Lett.* 47, (2006), 5025.
- 11 J. Azran, M. Shimoni and O. Buchman, *J. Catal.* 1994, 148, 648.
- 12 N. Ito, T. Watahiki, T. Maesawa, T. Maegawa, and H. Sajiki, *Adv. Synth. Catal.*, 348, (2006), 1025.
- 13 H. Sajiki, N. Ito, H. Esaki, T. Maesawa, T. Maegawa, K. Hirota *Tetrahedron Lett.* 2005, 46, 6995.
- 14 T. Maegawa, A. Akashi, H. Esaki, F. Aoki, H. Sajiki and K. Hirota, *Synlett.*, 5, (2005), 845.
- 15 H. Esaki, F. Aoki, T. Maegawa., K. Hirota and H. Sajiki. *Heterocycles*, 66,(2005) 361.
- 16 H. Esaki, F. Aoki, M. Umemura, M. Kato, T. Maegawa, Y. Monguchi and H. Sajiki, *Chem. Eur. Journal.* 13, (2007), 4052.
- 17 V. Derdau and J. Atzrodt, *SynLett.* 12, (2006), 1918.
- 18 H. Sajiki, F. Aoki, H. Esaki, T. Maegawa, and K. Hirota, *Org. Lett.* 2004, 6(9), 1485.
- 19 H. Esaki, N. Ito, S. Sakai, T. Maegawa, Y. Monguchi H. Sajiki, *Tetrahedron* 2006, 62, 10954.
- 20 V. Derdau, J. Atzrodt, W. Holla, *J. Label Compd. Radiopharm.* 2007, 50, 295-299.
- 21 K.A. Flanagan, J.A. Sullivan and H. Mueller-Bunz, *Langmuir.* 23, (2007), 12508.

- 22 K.A. Flanagan, PhD Thesis, UCD, 2007.
- 23 J.A. Sullivan, K.A. Flanagan and H. Hain, submitted to Catalysis Today.
- 24 T. Sainsbury and D. Fitzmaurice, D. Chem. Mater. 2004, 16, 2174.
- 25 H. Sajiki, K. Hattori, F. Aoki, K. Yasunaga and K. Hirota, Synlett , 7, (2002), 1149.
- 26 H. Esaki, R. Ohtaki, T. Maegawa, Y. Monguchi, H. Sajiki, J. Org. Chem. 72, (2007) , 2143.
- 27 K. Muto, M. Katada and M. Niwa. Appl.Catal. A: Gen., 134, (1996), 203.
- 28 Z. Karpinski, Adv. Catal., 37, (1990), 45.
- 29 C.B. Wang, H.K. Lin and C.M. Ho, J.Mol.Catal A Chem., 180, (2002), 285.
- 30 T. Schalow, B. Brandt, D.E. Starr, M. Laurin, S.K. Shaikhutdinov, S. Schauermaun, J. Libuda, H.J. Freund, H.J., Angew. Chem, Int. Ed. 45, (2006), 3693.
- 31 T. Schalow, B. Brandt, M. Laurin, S. Guimond, D.E. Starr, S.K. Shaikhutdinov, S. Schauermaun, J. Libuda and H.J. Freund, Top. Catal. 42 (2007) 387.
- 32 T. Schalow, B. Brandt, D.E. Starr, M. Laurin, S.K. Shaikhutdinov, S. Schauermaun, J. Libuda and H.J. Freund, Phys. Chem. Chem. Phys. 9 (2007) 1347.
- 33 N.H. Werstiuk., and C. Ju, Can.J.Chem., 67, (1989), 5.

**Comment [KF8]:** Remove bracket

**Deleted:** ]

**Comment [KF9]:** Full stop

**Comment [KF10]:** Full stop



**Figure Legends:**

**Figure 1:** (i) A comparison between the  $^1\text{H}$  NMR spectra of the DMAP stabilised palladium nanoparticle dispersion in  $\text{D}_2\text{O}$  obtained (a) one hour and (b) two days after preparation. (ii) a comparison of the DRIFTS spectrum of DMAP used in the initial dispersion preparation and DMAP subsequently isolated from the dispersion in  $\text{D}_2\text{O}$ .

**Figure 2:** (a) Schematic of preparation procedure used to produce Pd/MWCNT composite material (b) TEM of resultant composite material (c) histogram showing particle size distribution.

**Figure 3:** Plot of  $\alpha$   $^1\text{H}$  resonance intensity as a function of time in DMAP stabilised Pd nanoparticle dispersions. (■) dispersion at room temperature, (▲) dispersion held at 50 °C, (○) Dispersion held at 80 °C, (●) dispersion held at 50 °C with extra DMAP added following 25 h of H-D exchange- see text for details.

**Figure 4:** Plot of  $\alpha$   $^1\text{H}$  resonance intensity as a function of time in DMAP stabilized Pd nanoparticle dispersions held at 50 °C. (□) fresh dispersion, (■) 1 month old dispersion, (●) 1 month old dispersion following a treatment in  $\text{H}_2/\text{Ar}$ .


**Figure 5:** Histogram showing normalised activity, selectivity and re-cyclability of the Pd-MWCNT composite material in promoting the selective H-D exchange reaction of DMAP molecules in the presence and absence of  $\text{H}_{2(\text{g})}$ . The experiment involved a 5 hour reaction at 50 °C.  $\alpha$  proton selectivity (black columns),  $\beta$  proton selectivity (grey columns).

**Figure 6:** Histogram showing normalised activity and selectivity of Pd-MWCNT composite catalyst in promoting the H-D exchange reaction of DMAP, 4-aminopyridine and 4-hydroxypyridine molecules in the presence of  $\text{H}_{2(\text{g})}$ . The experiment involved a 5 hour reaction at 50 °C.  $\alpha$  proton selectivity (black columns),  $\beta$  proton selectivity (grey columns).

## Figures

### Figure 1

(i)

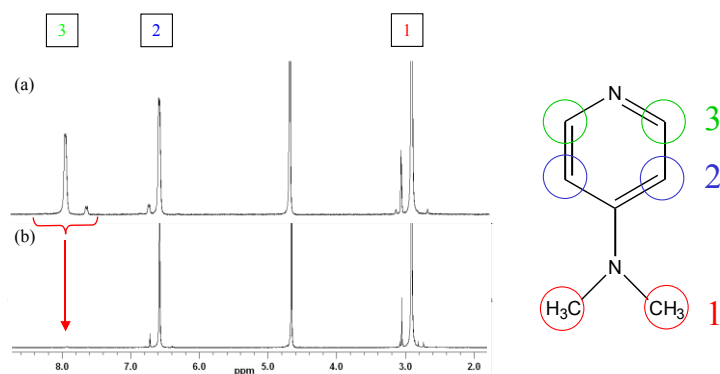

(ii)


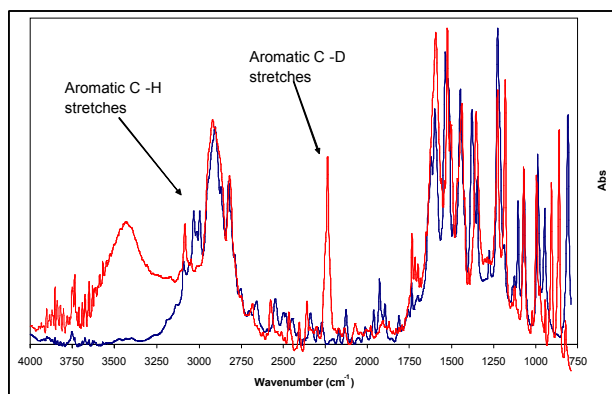


Figure 1: (i) A comparison between the <sup>1</sup>H NMR spectra of the DMAP stabilised palladium nanoparticle dispersion in D<sub>2</sub>O obtained (a) one hour and (b) two days after preparation. (ii) a comparison of the DRIFTs spectrum of DMAP used in the initial dispersion preparation and DMAP subsequently isolated from the dispersion in D<sub>2</sub>O.

Figure 2

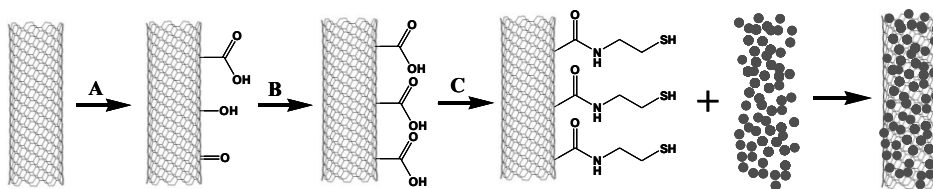

**Reagents and conditions:**

A. HNO<sub>3</sub>, 130 °C, 24 hours.

B. KMnO<sub>4</sub> / HClO<sub>4</sub>

C. EDAC, DMAP, 2-Mercaptoethylamine.HCl, RT, 24 hours.

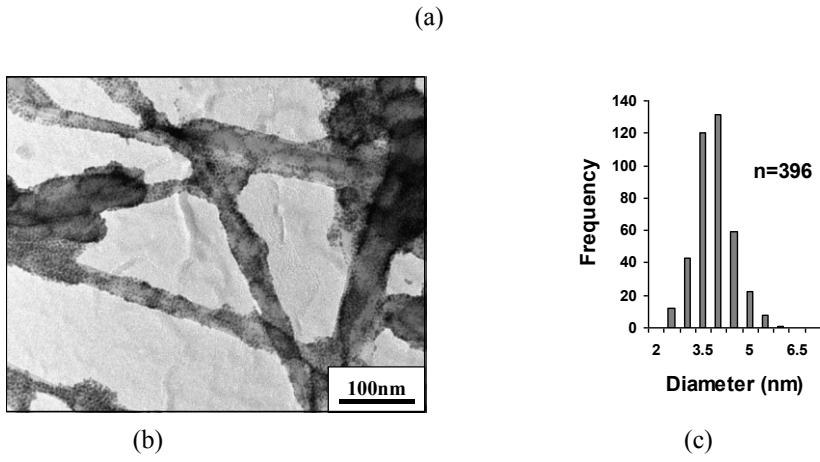


Figure 2: (a) Schematic of preparation procedure used to produce Pd/MWCNT composite material (b) TEM of resultant composite material (c) histogram showing particle size distribution.

### Figure 3

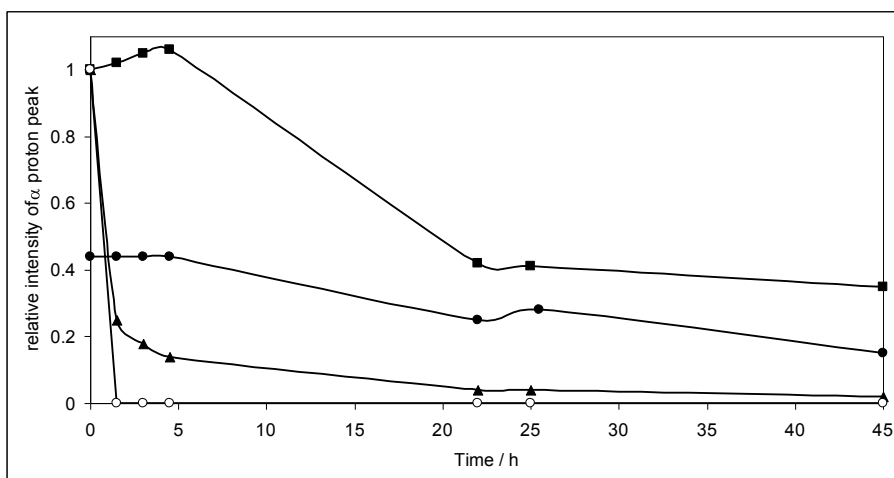


Figure 3: Plot of  $\alpha$   $^1\text{H}$  resonance intensity as a function of time in DMAP stabilised Pd nanoparticle dispersions. (■) dispersion at room temperature, (▲) dispersion held at 50 °C, (○) Dispersion held at 80 °C, (●) dispersion held at 50 °C with extra DMAP added following 25 h of H-D exchange- see text for details.

Figure 4:

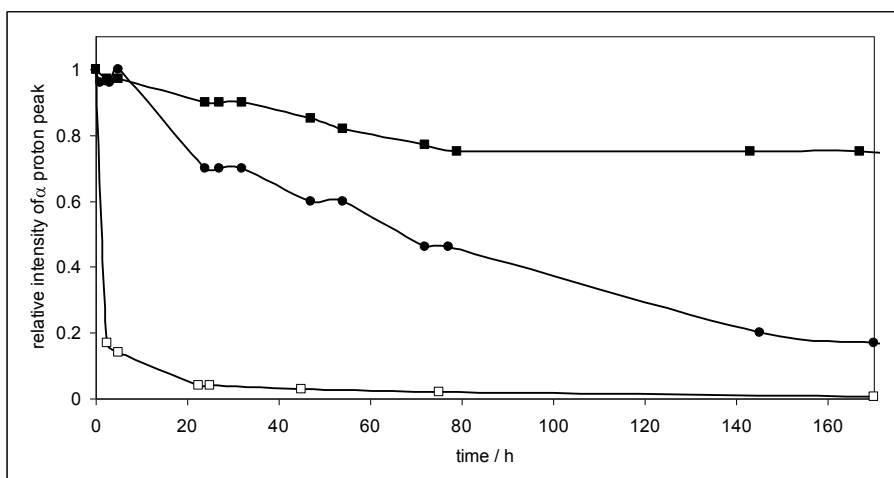


Figure 4: Plot of  $\alpha$   $^1\text{H}$  resonance intensity as a function of time in DMAP stabilized Pd nanoparticle dispersions held at 50 °C. (□) fresh dispersion, (■) 1 month old dispersion, (●) 1 month old dispersion following a treatment in  $\text{H}_2/\text{Ar}$ .

Figure 5:

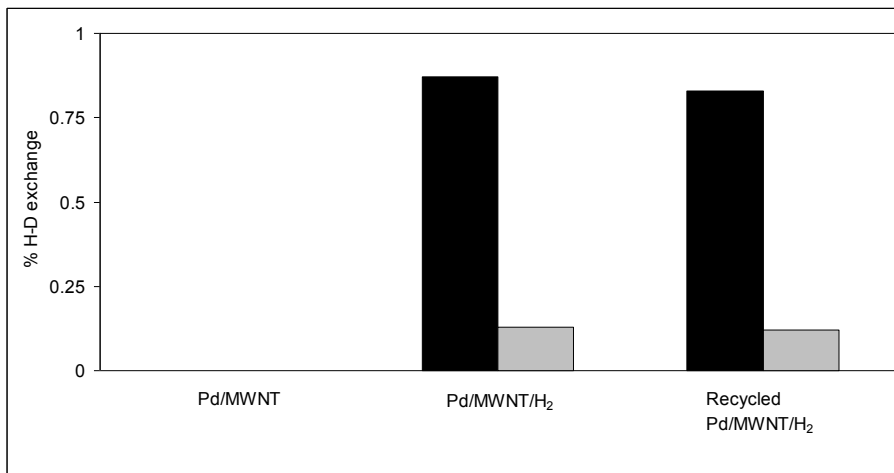


Figure 5: Histogram showing normalised activity, selectivity and re-cyclability of the Pd-MWCNT composite material in promoting the selective H-D exchange reaction of DMAP molecules in the presence and absence of H<sub>2(g)</sub>. The experiment involved a 5 hour reaction at 50 °C.  $\alpha$  proton selectivity (black columns),  $\beta$  proton selectivity (grey columns).

**Figure 6:**

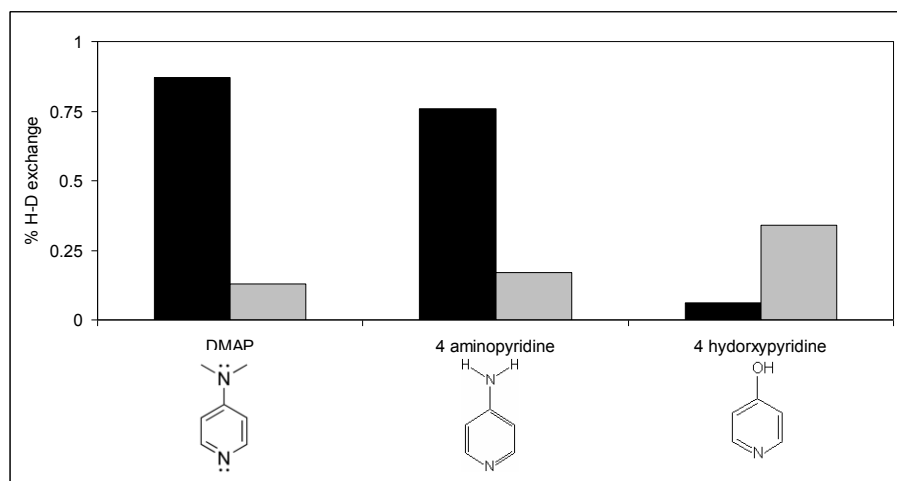


Figure 6: Histogram showing normalised activity and selectivity of Pd-MWCNT composite catalyst in promoting the H-D exchange reaction of DMAP, 4-aminopyridine and 4-hydroxypyridine molecules in the presence of  $H_{2(g)}$ . The experiment involved a 5 hour reaction at 50 °C.  $\alpha$  proton selectivity (black columns),  $\beta$  proton selectivity (grey columns).