



This is a repository copy of *Bioactive protein and peptide release from a mucoadhesive electrospun membrane*.

White Rose Research Online URL for this paper:

<https://eprints.whiterose.ac.uk/205664/>

Version: Published Version

Article:

Edmans, J.G. orcid.org/0000-0002-4539-9145, Murdoch, C. orcid.org/0000-0001-9724-122X, Hatton, P.V. orcid.org/0000-0001-5234-1104 et al. (4 more authors) (2023) Bioactive protein and peptide release from a mucoadhesive electrospun membrane. *Biomedical Materials & Devices*. ISSN 2731-4812

<https://doi.org/10.1007/s44174-023-00098-5>

Reuse

This article is distributed under the terms of the Creative Commons Attribution (CC BY) licence. This licence allows you to distribute, remix, tweak, and build upon the work, even commercially, as long as you credit the authors for the original work. More information and the full terms of the licence here:

<https://creativecommons.org/licenses/>

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>



Bioactive Protein and Peptide Release from a Mucoadhesive Electrospun Membrane

Jake G. Edmans^{1,2} · Craig Murdoch¹ · Paul V. Hatton¹ · Lars Siim Madsen³ · Martin E. Santocildes-Romero³ · Sebastian G. Spain² · Helen E. Colley¹

Received: 5 April 2023 / Accepted: 3 June 2023
© The Author(s) 2023

Abstract

Protein-based biologics constitute a rapidly expanding category of therapeutic agents with high target specificity. Their clinical use has dramatically increased in recent years, but administration is largely via injection. Drug delivery across the oral mucosa is a promising alternative to injections, in order to avoid the gastrointestinal tract and first-pass metabolism. Current drug delivery formulations include liquid sprays, mucoadhesive tablets and films, which lack dose control in the presence of salivary flow. To address this, electrospun membranes that adhere tightly to the oral mucosa and release drugs locally have been developed. Here, we investigated the suitability of these mucoadhesive membranes for peptide or protein release. Bradykinin (0.1%) or insulin (1, 3, and 5%) were incorporated by electrospinning from ethanol/water mixtures. Immersion of membranes in buffer resulted in the rapid release of bradykinin, with a maximal release of $70 \pm 12\%$ reached after 1 h. In contrast, insulin was liberated more slowly, with 88 ± 11 , 69.0 ± 5.4 , and $63.9 \pm 9.0\%$ cumulative release of the total encapsulated dose after 8 h for membranes containing 1, 3, and 5% w/w insulin, respectively. Membrane-eluted bradykinin retained pharmacological activity by inducing rapid intracellular calcium release upon binding to its cell surface receptor on oral fibroblasts, when examined by flow cytometry. To quantify further, time-lapse confocal microscopy revealed that membrane-eluted bradykinin caused a 1.58 ± 0.16 fold-change in intracellular calcium fluorescence after 10 s compared to bradykinin solution (2.13 ± 0.21), relative to placebo. In conclusion, these data show that electrospun membranes may be highly effective vehicles for site-specific administration of biotherapeutic proteins or peptides directly to the oral mucosa for either local or systemic drug delivery applications.

Keywords Electrospinning · Drug delivery · Peptides · Oral mucosa · Mucoadhesion · Bradykinin · Insulin

Introduction

Peptide and protein biologics are a rapidly growing class of pharmaceuticals with high clinical success rates, high specificity, high potency and low toxicity [1]. However, these types of therapeutics suffer from low oral bioavailability due to limited gastrointestinal absorption, enzymatic degradation and first-pass hepatic metabolism, and are therefore almost

exclusively administered parenterally by injection. This has significant associated drawbacks including patient discomfort, non-compliance due to trypanophobia and, in many cases, the need for administration by healthcare professionals. For these reasons, there is much interest in drug delivery via mucosal surfaces [2, 3]. Transmucosal drug delivery via the oral cavity enables easy self-administration and is painless, thus increasing compliance rates. Furthermore, the ability to deliver biologics topically to the oral mucosa may enable new treatments for oral diseases whilst mitigating off-target side effects. Although there is much interest in this mode of delivery, progress is limited by the lack of suitable dosage forms that allow site-specific delivery to mucosal surfaces.

The only formulation that has successfully reached the market for transmucosal peptide delivery to date is the Oral-Lyn™ insulin aerosol spray for the management of

✉ Craig Murdoch
c.murdoch@sheffield.ac.uk

¹ School of Clinical Dentistry, University of Sheffield, 19 Claremont Crescent, Sheffield S10 2TA, UK

² Department of Chemistry, University of Sheffield, Brook Hill, Sheffield S3 7HF, UK

³ AFYX Therapeutics, Ole Maaløes Vej 3, 2200, Copenhagen, Denmark

type 1 diabetes [4]. Unlike competing alternatives, this formulation is absorbed through the buccal oral mucosa rather than the respiratory tract and uses a mixture of surfactants to enhance epithelial permeation as well as to allow aerosol formation [5]. The relatively high doses of insulin required and its poor epithelial permeability make it a challenging candidate drug for transmucosal delivery. Indeed, significant disadvantages of buccal insulin sprays include modest bioavailability of approximately 10% and the large volume of spray required to achieve a therapeutic dose [4]. In vivo investigations into transmucosal biologic delivery suggest that several hydrophilic lower molecular weight therapeutic peptides including glucagon-like-peptide 1 [6], salmon calcitonin [7], and desmopressin [8] delivered to the buccal or sublingual mucosa can permeate sufficiently to achieve therapeutically relevant systemic doses without the need for permeation enhancing excipients. Low molecular weight peptides with fewer rotatable bonds tend to permeate the oral epithelium more easily, facilitating uptake. Absorption of these molecules is often hypothesised to occur by passive diffusion through the epithelial paracellular spaces [9]. There is great potential to develop new dosage forms for the delivery of permeable proteins or peptides into or across the oral mucosa depending on epithelial or systemic targeting. However, previous studies have examined dosage forms with limited suitability for further translation, typically consisting of solutions or dissolving tablets/films that are readily removed from the mucosal surface by saliva, resulting in limited drug/tissue contact times [10, 11].

Electrospinning has recently attracted interest for the fabrication of oromucosal dosage forms with improved flexibility and high surface areas to facilitate drug release and mucoadhesive interactions [12, 13]. Furthermore, dual-layer electrospun membranes with hydrophobic backing layers are highly effective at promoting the retention of drugs on the oral mucosa in the presence of saliva flow [14, 15]. Previous studies investigating electrospinning for protein or peptide encapsulation have primarily focussed on emulsion and coaxial electrospinning, due to the perception that organic electrospinning solvents such as ethanol would cause protein denaturation during uniaxial electrospinning [16]. Alternatively, protein-loaded fibres have been prepared from aqueous solutions to avoid potential solvent-induced denaturation using polymers such as chitosan, silk or alginate [17–19]. We have previously developed a dual-layer mucoadhesive electrospun drug delivery patch consisting of a mucoadhesive inner membrane layer fabricated using Poly(vinylpyrrolidone) (PVP) and Eudragit® RS100, and a protective polycaprolactone-based outer membrane layer to facilitate site-specific delivery to the buccal mucosa [20]. These membranes were highly effective in phase II clinical trials in the delivery of clobetasol-17-propionate for

treatment of erosive oral lichen planus [21], and have potential for several applications in oral medicine [13, 15, 22].

At present, only a few peptides with therapeutic potential have been incorporated into polymer fibres using solvent-based uniaxial blend electrospinning. Moreover, their pharmacological activity following elution from the polymer fibres has not been investigated [16, 23, 24]. In this study, bradykinin (a nine amino acid, 1060 Da peptide) or insulin (a 5.8 kDa protein) were incorporated into a novel mucoadhesive electrospun fibre membrane and their release kinetics examined to further investigate the versatility of the technology for mucosal delivery. Moreover, the biological activity of bradykinin following elution was assessed to determine if released molecules retain their biological activity.

Materials and Methods

Materials

Poly(vinylpyrrolidone) (PVP; MW 2000 kDa) and Eudragit® RS100 (RS100; MW 38 kDa) were kindly donated by BASF, Cheadle Hulme, UK and Evonik Industries AG, Essen, Germany, respectively. Bradykinin ELISA kit was purchased from Abcam, Cambridge, UK. Fluo-4 Direct™ calcium assay kit was purchased from ThermoFisher Scientific, Loughborough, UK. Recombinant bradykinin, insulin, and cell culture reagents were purchased from Sigma-Aldrich, Poole, UK.

Electrospinning System

Electrospun membranes were fabricated using a system composed of a PHD2000 syringe pump (Harvard Apparatus, Cambridge, UK) and an Alpha IV Brandenburg power source (Brandenburg, UK). Plastic syringes (1 mL volume; Henke Sass Wolf, Tuttlingen, Germany) were used to drive the solutions into a 20-gauge blunt metallic needle (Fisnar Europe, Glasgow, UK). Electrospinning was performed at room temperature with a potential difference of 19 kV, a flow rate of 2 mL/h, and a flight path of 14 cm.

Fabrication of Electrospun Membranes Containing Bradykinin or Insulin

Electrospinning solutions for bradykinin contained 0.1025 g/mL PVP and 0.1225 g/mL Eudragit® RS100 (by total solvent volume before mixing). PVP and RS100 were added to ethanol and mixed at room temperature using a magnetic stirrer until dissolved. Bradykinin was dissolved in ice cold phosphate-buffered saline (PBS), added to the polymer solution shortly before electrospinning and stirred until uniformly distributed, contributing 3% v/v to the final solvent composition. Placebo

solutions and membranes were prepared using 3% v/v distilled water instead of bradykinin in PBS. For insulin, all electrospinning solutions contained 0.0825 ± 0.00125 g/mL PVP and 0.1025 ± 0.00125 g/mL Eudragit® RS100 (by total solvent volume before mixing). The required amounts of PVP and RS100 were added to ethanol and mixed at room temperature using a magnetic stirrer until dissolved. The required concentration of insulin was prepared in 2% acetic acid in PBS in a glass vial and vortexed for approximately 60 s with gentle heating until a clear solution was produced. Insulin solutions were combined with the polymer solutions at 20% v/v and mixed until homogenous shortly before electrospinning. Placebo solutions and membranes without recombinant peptides/proteins were prepared under identical conditions.

Surface pH

Membrane samples (10 ± 0.5 mg) were placed in wells of a 24-well plate, submerged in 1 mL deionised water, and shaken briefly until wetted. After 10 minutes, the pH was measured using a pH meter (Hanna Instruments, Rhode Island, USA).

Scanning Electron Microscopy

Electrospun membranes were imaged using a TESCAN Vega3 scanning electron microscope (SEM; Tescan, Cambridge, UK). Samples were sputter coated with gold and imaged using an emission voltage of 10 kV. All images were processed and fibre diameters measured using ImageJ software tools [25], using randomly generated coordinates and a superimposed grid to select fibres. Three images were analysed for each membrane composition with at least 10 measurements per image.

Release Profile of Bradykinin from Electrospun Membranes

Samples of electrospun membranes (20 mg) containing bradykinin were immersed in 4 mL PBS and 10 μ L samples taken at time intervals up to 4 h following vortexing for 5 s. Bradykinin concentrations were quantified using a competitive ELISA kit according to the manufacturer's instructions (abcam, Cambridge, UK). To calculate percentage cumulative release, the active concentration was normalised against the theoretical maximum concentration based on the dry mass fraction of bradykinin in the electrospinning solution.

Release Profile of Insulin from Electrospun Membranes

Membrane samples (3–6 mg) containing insulin were cut using a circular punch and placed in wells of a 12-well

plate. Pre-warmed PBS (2 mL) was added to the wells and the samples incubated at 37 °C with shaking. 50 μ L aliquots were taken every 0.5 h for 8 h and the volume replaced with fresh media. Protein concentration was measured using a Pierce™ bicinchoninic acid (BCA) assay kit as directed (ThermoFisher Scientific). Percentage cumulative release was calculated by normalising against the theoretical maximum concentration, based on the dry mass fraction of insulin in the electrospinning solution.

Cell Isolation and Culture

Normal oral fibroblasts (NOF) were isolated from the connective tissue of biopsies obtained from the oral mucosa of patients during routine dental procedures with written informed consent (Ethical Approval No. 09/H1308/66) and conducted in accordance with the principles embodied in the Declaration of Helsinki. NOF were cultured in Dulbecco's Modified Eagle's Medium supplemented with foetal bovine serum (FBS; 10% v/v), 2 mM L-glutamine, 100 IU/mL penicillin and 100 μ g/mL streptomycin [26].

Intracellular Calcium Mobilisation Using Flow Cytometry

NOF were removed from cell culture flasks and resuspended in buffered Fluo-4 cell-permeant acetoxymethyl ester (ThermoFisher Scientific) at a suspension of 10^6 cells/mL and incubated for 45 minutes at 37 °C followed by 30 minutes at room temperature. Bradykinin-loaded or placebo membranes (10 mg) were eluted in 2 mL PBS for 24 h and stored at -20 °C prior to the experiment. A stock solution of bradykinin in PBS matching the theoretical concentration of the membrane eluent (5 μ g/mL) was prepared as a positive control and stored in identical conditions. Samples and standards were diluted by a factor of 10 in PBS before assaying by flow cytometry. To determine intracellular calcium responses, fluorescence was measured at 488 nm excitation and 530 nm emission using a FACSCalibur flow cytometer (BD Biosciences, Wokingham, UK). For each sample, baseline fluorescence was measured for 40 s before sample addition (10 μ L in 1 mL) after which fluorescence was measured for approximately 160 s. Change in relative fluorescent units (Δ RFU) was calculated by subtracting the median relative fluorescent unit value of the baseline from the maximum median fluorescence (over a 1 s interval) following sample addition. The experiment was performed in triplicate using three independently prepared sets of membranes and different batches of cells.

Intracellular Calcium Mobilisation Using Confocal Microscopy

NOF (2.5×10^4 in 25 μL) were seeded in a half-area glass-bottom 96-well plate and incubated overnight to give a confluent monolayer. Bradykinin samples and controls were prepared as previously described and diluted by a factor of 1000 prior to assaying. Before imaging, 25 μL buffered Fluo-4 cell-permeant acetoxymethyl ester was added and the cells incubated for 45 minutes at 37 $^\circ\text{C}$, followed by 30 minutes at room temperature. Imaging was performed using a Nikon A1 laser scanning confocal microscope with 457–514 nm argon laser. Cells were imaged at room temperature with approximately 1200 cells per image to obtain a baseline. Samples (50 μL) were added, and images immediately acquired every 10 s for 60 s using identical capture settings. The fold-change in fluorescence was calculated from the mean intensity of each the micrograph relative to the baseline. All images were processed using ImageJ software tools using automatic brightness/contrast adjustment on each series of images. The experiment was performed three times using three independently prepared sets of membranes and different batches of cells.

Data Analysis

All data and statistical analyses were performed using GraphPad Prism 9.4.1 software (GraphPad Software, La Jolla, USA). Student's *t*-test was used for pairwise comparisons whilst one-way ANOVA with Tukey's post hoc test was used to compare differences between groups and results considered statistically significant if $p < 0.05$.

Results

Incorporation of Bradykinin or Insulin into Electrospun Membranes

Electrospun membranes containing 0.1% w/w bradykinin by dry mass were prepared by electrospinning from a solution of 97% v/v ethanol. SEM images revealed a randomly aligned fibre morphology, with few defects, and an average diameter of $2.23 \pm 0.81 \mu\text{m}$ that was similar to control membranes (Fig. 1).

Due to the relatively low aqueous solubility of insulin, a solvent composition of 80% v/v ethanol was used to allow the mixing of a larger volume of aqueous protein solution. The aqueous component of the electrospinning solution was acidified with acetic acid to dissolve the insulin and membranes were fabricated to contain 0, 1, 3, and 5% w/w insulin by dry mass. SEM analysis revealed a defect-free fibrous morphology in the absence or presence of insulin (Fig. 2a). Membranes without insulin had a mean fibre diameter of $1.29 \pm 0.36 \mu\text{m}$. Inclusion of insulin at 3% w/w or 5% w/w resulted in significantly increased diameters of $2.16 \pm 0.78 \mu\text{m}$ and $1.55 \pm 0.39 \mu\text{m}$, respectively ($p < 0.001$; Fig. 2b).

To investigate the effect of the use of acetic acid on surface pH, membranes were immersed in a small volume of distilled water before measuring pH with a digital probe. All samples prepared using this method had a surface pH of approximately 6 (Fig. 2c), whereas previously fibre formulation without the use of acetic acid had a pH of 8.2 [15].

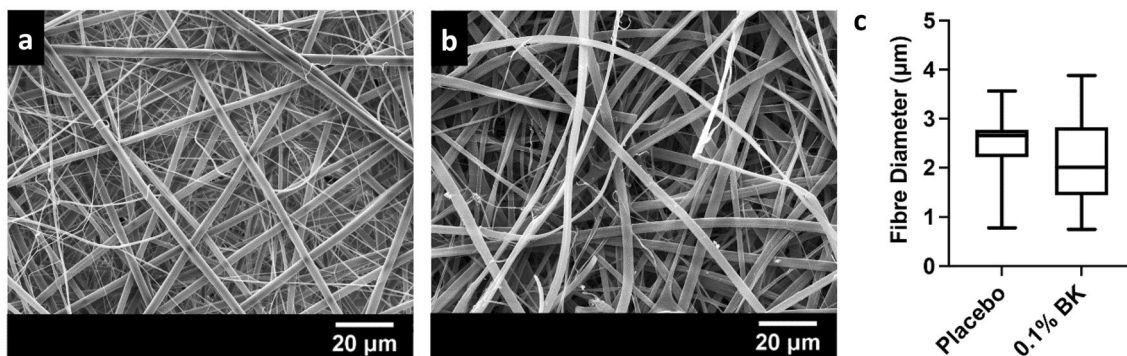


Fig. 1 Characterisation of bradykinin-loaded mucoadhesive electrospun membranes. Bradykinin was incorporated into polymer fibres by mixing with ethanolic polymer solutions immediately before electrospinning and the resulting fibres imaged by SEM. SEM micrographs of **a** control electrospun fibres **b** electrospun fibres containing 0.1%

w/w bradykinin (BK), scale bar = 20 μm . **c** Fibre diameter distribution presented as box and whisker plots displaying median, interquartile range and range ($n = 30$). Statistical analysis was performed by Student's *t*-test

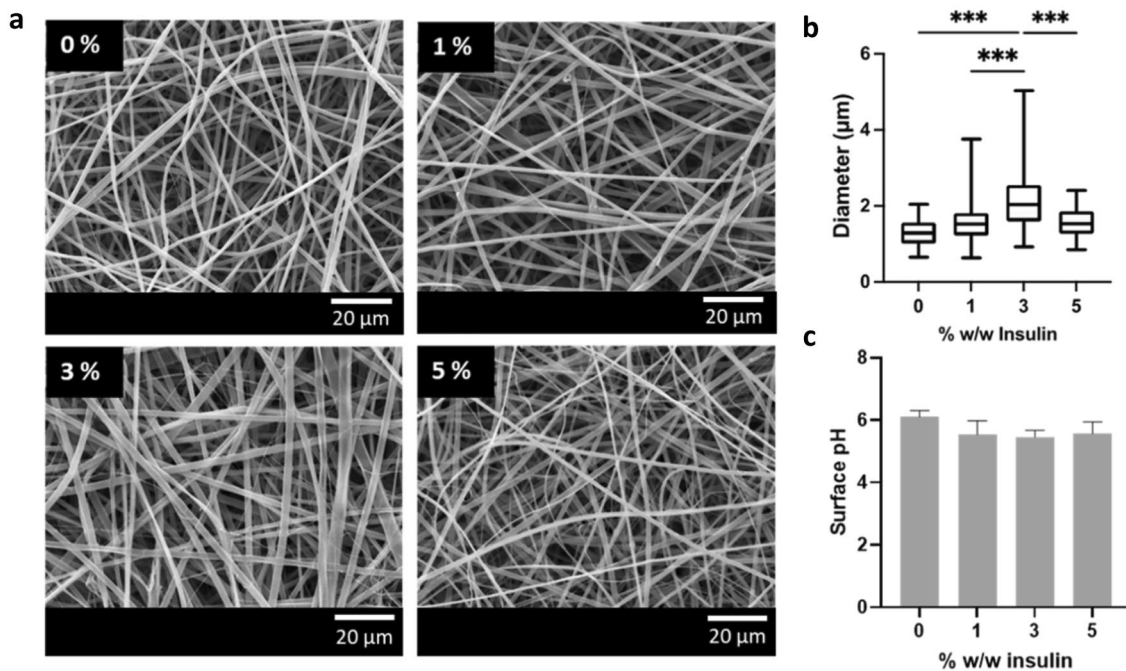


Fig. 2 Preparation of mucoadhesive electrospun fibres containing 0, 1, 3, 5% w/w insulin. Insulin was dissolved in 2% v/v acetic acid in PBS and mixed 1:4 v/v with an ethanolic polymer solution shortly before electrospinning. **a** SEM micrographs of electrospun fibres containing 0, 1, 3, and 5% w/w insulin. **b** Fibre diameter distributions

presented as median, interquartile range, and range. Data were analysed using one-way ANOVA with Tukey post hoc test. $***p < 0.001$ ($n = 30$). **c** Surface pH of electrospun fibres presented as mean \pm SD ($n = 3$) and analysed using one-way ANOVA with Tukey’s post hoc test

Release of Bradykinin and Insulin from Electrospun Membranes

The release profile of bradykinin and insulin from membranes was measured by eluting in PBS and measuring bradykinin concentration by ELISA and insulin by BCA protein assay. Bradykinin release was rapid, with $55 \pm 17\%$

of the theoretical total dose released within 30 minutes. Maximum bradykinin release of $70 \pm 12\%$ was observed after 1 h (Fig. 3a). Release of insulin was slower than that of bradykinin, with maximal but incomplete release after 8 h (Fig. 3b). When evaluating liberation of insulin per mg membrane, release was dependent on insulin content, with the 5 and 3% w/w patch releasing significantly more

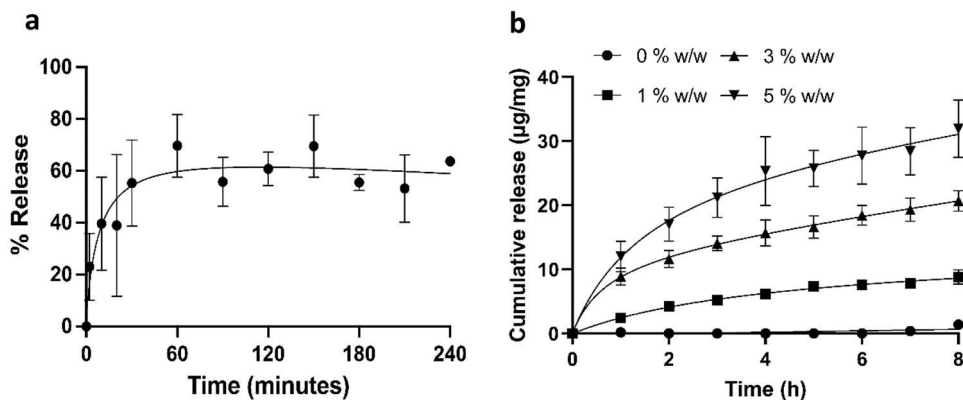


Fig. 3 Release of bradykinin and insulin from mucoadhesive membranes following immersion in PBS. Electrospun membrane samples were eluted in PBS at 37 °C. Bradykinin concentrations in the eluted PBS were measured by ELISA whilst insulin release was measured by BCA assay. **a** Percentage release of bradykinin over 240 minutes

b cumulative insulin release per mg of membrane over 8 h. Data are presented as mean \pm SD ($n = 3$). Statistical analysis for insulin was performed at the 8 h timepoint by one-way ANOVA with Tukey’s post hoc test

insulin than the 1% w/w ($p < 0.001$ and $p < 0.01$, respectively) and placebo membrane ($p < 0.001$) (Fig. 3b). The percent cumulative insulin release after 8 h corresponded to 88 ± 11 , 69.0 ± 5.4 , and $63.9 \pm 9.0\%$ of the total encapsulated dose for membranes containing 1, 3, and 5% w/w insulin, respectively.

Membrane-eluted Bradykinin Stimulates Intracellular Calcium Release in Normal Oral Fibroblasts

The release of insulin from other polymer-based drug carriers for diabetic therapy has previously been reported in several studies [4, 17, 27–29]. Therefore, we decided to focus further experiments on bradykinin as a novel exemplar test molecule for membrane release. Bradykinin is a hydrophilic nine amino acid (1060 Da) peptide that exerts its effects on cells such as fibroblasts, smooth muscle, and endothelial cells that form blood vessels, causing vasodilation and increasing vascular permeability following engagement of G-protein coupled bradykinin receptors. To test whether the biological activity of bradykinin was preserved following release from membranes, its effect on intracellular calcium mobilisation following binding to its cell surface G-protein coupled receptor expressed by NOF was measured using flow cytometry. Bradykinin-containing membranes were eluted in PBS for 24 h and the supernatant added to cell suspensions at 5 ng/mL (assuming 100% loading efficiency and complete release from the membranes) to approximate physiological concentrations. The addition of placebo membrane eluent to NOF had negligible effect on fluorescence as a readout for intracellular calcium release, causing a 0.51 ± 0.46 maximum change in relative fluorescence units (RFU) compared to baseline (Fig. 4a and d). Recombinant bradykinin solution caused a maximum 8.4 ± 1.3 Δ RFU (Fig. 4b and d) whilst electrospun membrane-eluted bradykinin caused a 13.2 ± 1.5 maximum Δ RFU (Fig. 4c and d).

The effect on intracellular calcium mobilisation was also observed in NOF monolayers by confocal microscopy. Bradykinin samples were added at 2.5 ng/mL (assuming 100% loading efficiency and complete release), after which fluorescence micrographs were periodically captured for up to 60 s (Fig. 5). An eluted placebo membrane was used as a negative control and as expected, produced negligible change in fluorescence. Bradykinin in solution and as elute from the membrane cause a rapid (within 2 s) increase in intracellular calcium (Fig. 5a). Bradykinin in solution caused a 2.13 ± 0.21 fold-change in fluorescence intensity peaking at 10 s ($p < 0.001$) relative to placebo, after which fluorescence intensity decreased linearly over time (Fig. 5b and c). Membrane-eluted bradykinin produced similar behaviour, peaking at approximately 2 s, causing a 1.58 ± 0.16 fold-change after 10 s ($p < 0.001$) relative to placebo (Fig. 5b and c).

Discussion

Electrospun mucoadhesive membranes have been developed to address the lack of formulations that enable site-specific drug delivery to the oral mucosa [12]. These membranes have been successfully developed for the delivery of several small molecule drugs [13, 15, 22, 30–32], lysozyme [33], a robust antimicrobial enzyme, and antibody fragments [34], suggesting suitability for oromucosal protein delivery. In order to determine the potential of electrospun membranes for transmucosal peptide delivery it is necessary to demonstrate that a peptide can be incorporated and released at a suitable rate whilst maintaining pharmacological activity. Bradykinin is a small but highly potent vasoactive peptide. It was used in this study as an exemplar test molecule to provide proof-of-concept data that other such small peptides could be incorporated into electrospun membranes, released and retain their biological activity.

Drug delivery from a membrane or patch applied to the oral mucosa is time-limited due to the requirement of patients to refrain from eating and drinking upon membrane application. A previous study observed a clinically measured membrane residence time of approximately 100 min for similar membranes applied to the human buccal mucosa [15]. Therefore, efficient peptide release over a 2 h period would be ideal for delivery within this timeframe. Indeed, maximal bradykinin release corresponding to around 70% of the total dose was detected after just 1 h. This rapid release is consistent with a release mechanism controlled by the swelling of highly hydrophilic electrospun fibres [35]. The release profile is similar to those previously reported for hydrophilic proteins encapsulated within swelling electrospun fibres where it was found that lysozyme was rapidly eluted from an identical polymer system, with approximately 90% of the dose released within 1 h [33]. In addition, Stie et al., showed that mucoadhesive fibres consisting of blended poly(ethylene oxide) and chitosan rapidly released the highly soluble peptide desmopressin through a similar mechanism [14]. Here, desmopressin release was even faster than observed in our system, reaching 80% release within 20 minutes. This can be attributed to narrower fibre diameter of approximately 200 nm, leading to a higher surface area and faster fibre swelling.

Insulin was selected as a second model peptide to investigate the versatility of the patches for the delivery of larger, less soluble peptides, with the potential membrane application for sustained insulin delivery for diabetics. Insulin has low aqueous solubility at neutral pH. However, it is moderately soluble at pH 3, and if required, the pH of the solution can be adjusted back to pH 7 without

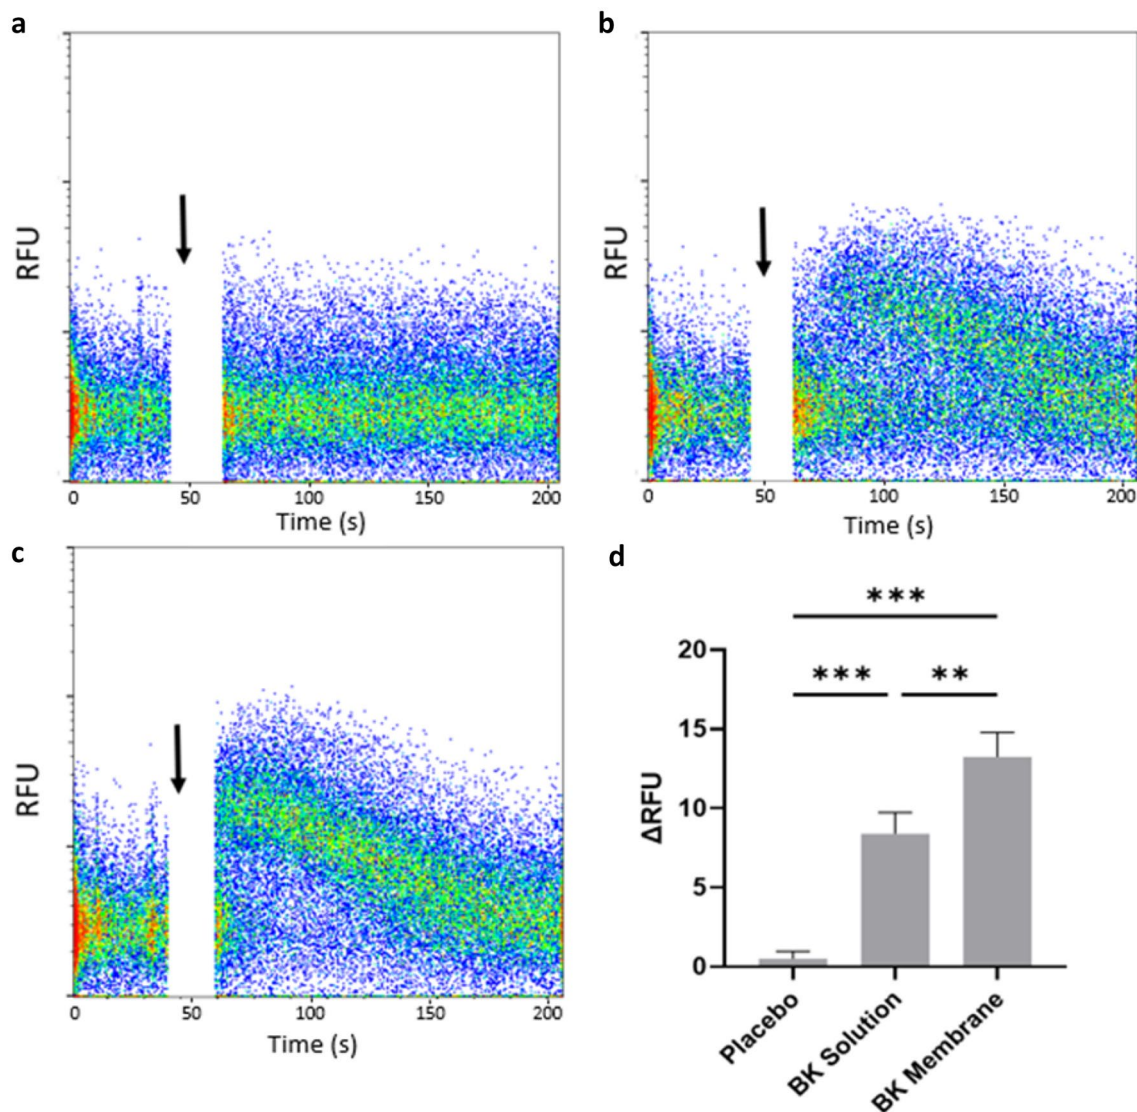



Fig. 4 Bradykinin functionality was preserved following release from electrospun mucoadhesive membranes. Intracellular calcium mobilisation in primary fibroblasts upon stimulation was determined over time using flow cytometry. Each dot represents a fluorescence measurement for an individual cell. Baseline fluorescence was acquired for 40 s before addition of samples (black arrow). **a** Placebo mem-

brane eluent **b** recombinant bradykinin (BK) solution **c** BK electrospun membrane eluent **d** change in relative fluorescence units (RFU) were calculated by subtracting baseline median fluorescence from the maximal median fluorescence following sample addition. Data is presented as mean \pm SD ($n=3$) and analysed using one-way ANOVA with Tukey's post hoc test. ** $p < 0.01$, *** $p < 0.001$

causing protein precipitation [36]. The solubility is further increased by increasing the ionic strength of the solution, for example by using acidified PBS instead of acid in deionised water. Relatively high therapeutic doses in the order of hundreds of micrograms several times daily are required for managing diabetes [37]. Therefore, to achieve suitably high loading in the mucoadhesive layer of the patch, the aqueous portion of the electrospinning solvent was increased to 2% v/v. Acidified PBS was used to solubilise insulin before mixing with the ethanolic polymer solution. This method allowed the fabrication of defect-free fibres containing 0, 1, 3, 5% w/w insulin.

The diameter of fibres containing 1% w/w insulin had a narrower diameter than that those containing bradykinin. This is likely a result of the increased conductivity of the electrospinning solution, due to the higher water and salt content, which produces more rapid fibre elongation in an electric field. The fibres were also narrower than those previously observed for fibres containing 1% w/w lysozyme, also prepared with 80% v/v ethanol [33]. This is likely because PBS was used exclusively instead of deionised water, resulting in a more conductive solution, which is associated with narrower fibre widths [38]. Fibres containing 3% w/w insulin were significantly wider than

Fig. 5 Membrane-eluted bradykinin increases intracellular calcium mobilisation in oral fibroblast monolayers. **a** Representative series of confocal micrographs showing the change in calcium mobilisation over time in primary fibroblast monolayers following treatment with PBS, placebo membrane eluent, bradykinin (BK) solution (2.5 ng/ml), or BK membrane eluent, scale bar = 500 μ m. **b** Fold-change in fluorescence relative units (RFU) over time following addition of solutions. **c** Fold-change in RFU after 10 s for each solution. Data is presented as mean \pm SD ($n=3$). Statistical analysis was performed using one-way ANOVA with Tukey's post hoc test. ** $p < 0.01$, *** $p < 0.001$

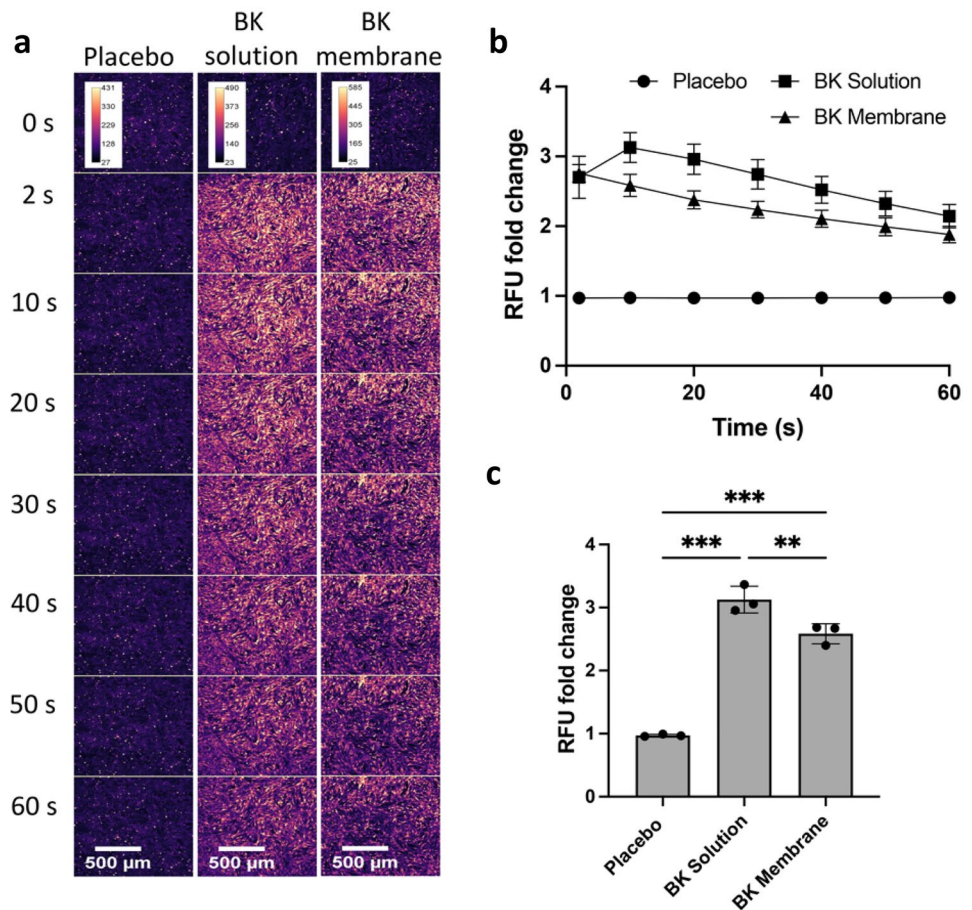

those with 1 or 5% w/w. Insulin concentration affects both solution conductivity and viscosity that may affect fibre diameter. The diameter of electrospun fibres can be modulated using high molecular weight polymers to increase viscosity or salts to increase conductivity [38]. Therefore, it is possible to counteract this size effect if desired. The use of acetic acid to solubilise insulin caused a decrease in surface pH to approximately 6, which is only slightly below the natural range for human saliva and so likely to be tolerable.

Insulin was released more slowly from the fibres in comparison to the rapid release observed for highly water-soluble proteins [14, 33, 34]. A similar electrospun material comprised of a blend of a water soluble polymer (poly(vinyl alcohol)) and a gel-forming polyionic polymer (sodium alginate) containing insulin was investigated by Sharma et al. These fibres also displayed slow insulin release, with complete liberation reached only after 10 h [17]. The authors hypothesised that the slow release was mediated by the biodegradation of sodium alginate. Considering the similar release profile observed for our system, it is possible that the slow release is caused by the intrinsically slow dissolution of insulin at physiological pH. A more rapid release profile may be desirable for oral mucosal insulin delivery, as eating

and drinking could dislodge the membrane and overnight application may present a choking hazard.

There is potential to increase the release rate using off-the-shelf excipients, such as basic amino acids or ethylenediaminetetraacetic acid, which are known to increase the solubility of insulin [39]. Insulin release has been investigated from several polymer-based drug delivery systems. Moreover, it is a less promising candidate for transmucosal delivery using electrospun fibres, as the low density of fibrous materials means that only relatively small masses of drug can feasibly be delivered, whereas doses of several milligrams of insulin would likely be required for sufficient absorption to achieve the desired therapeutic effect [37]. For these reasons, further investigation into the pharmacological activity of insulin upon release was not performed as part of this study.

Bradykinin causes a rapid but transient increase in intracellular calcium levels in target cells upon binding to its cell surface receptor [40], primarily through release from intracellular stores [41]. This effect that can be measured using commercially available fluorescent calcium probes. Here, we show that membrane-eluted bradykinin induced intercellular calcium mobilisation in oral fibroblasts both using flow cytometry and confocal microscopy. These results clearly

indicate bradykinin released from the membrane maintained pharmacological activity. We are aware of only one other study verifying the activity of a therapeutically relevant peptide following release from an electrospun mucoadhesive membrane. Sharma et al., applied fibrous membranes containing insulin to rat sublingual mucosa and upon application, these caused a gradual decrease in blood glucose concentration, indicating successful delivery of biologically active insulin [17]. In conclusion, our mucoadhesive membrane system is suitable for the release of biologically active small hydrophilic peptides over appropriate time-scales required for therapy. It constitutes an attractive new technology for the targeted delivery of permeating peptides to the buccal or sublingual oral mucosa. Potential applications include the topical release of peptides to treat oromucosal diseases locally, or alternatively transmucosal systemic delivery using an optimised dosing regimen.

Acknowledgements This work was funded by the U.K. EPSRC (EP/L016281/1) as a CASE Ph.D. studentship within the Centre for Doctoral Training in Polymers & Soft Matter with sponsorship from AFYX Therapeutics as the industrial partner. The authors would like to acknowledge The Wolfson Light Microscopy Facility (University of Sheffield, supported by a Wellcome Trust grant WT093134AIA) for help with imaging.

Funding The research presented was funded, in part, by AFYX Therapeutics APS. MES and LSM are employed by AFYX Therapeutics. PVH is on the AFYX Therapeutics APS scientific advisory board, where AFYX have translated mucoadhesive electrospun patch technology for clinical use and have intellectual property (international patent application WO 2017/085262 A, WO 2021/072113 A1).

Data Availability The datasets generated during and/or analysed during the current study are available from the corresponding author on reasonable request.

Declarations

Competing interest JGE, HEC, SGS and CM declare that they have no other known competing financial interests.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

References

1. F. Albericio, H.G. Kruger, Therapeutic peptides. *Fut. Med. Chem.* **4**(12), 1527–1531 (2012)
2. R. Kumar, T. Islam, M. Nurunnabi, Mucoadhesive carriers for oral drug delivery. *J. Control Release.* **351**, 504–559 (2022)
3. M. Surendranath, M.R. Rekha, R. Parameswaran, Recent advances in functionally modified polymers for mucoadhesive drug delivery. *J. Mater. Chem. B.* **10**(31), 5913–5924 (2022)
4. L. Heinemann, Y. Jacques, Oral insulin and buccal insulin: a critical reappraisal. *J. Diabetes Sci. Technol.* **3**(3), 568–584 (2009)
5. G. Bernstein, Delivery of insulin to the buccal mucosa utilizing the RapidMist system. *Expert Opin. Drug. Deliv.* **5**(9), 1047–1055 (2008)
6. M.K. Gutniak, H. Larsson, S.J. Heiber, O.T. Juneskans, J.J. Holst, B. Ahren, Potential therapeutic levels of glucagon-like peptide I achieved in humans by a buccal tablet. *Diabetes Care* **19**(8), 843–848 (1996)
7. Z. Cui, R.J. Mumper, Buccal transmucosal delivery of calcitonin in rabbits using thin-film composites. *Pharm. Res.* **19**(12), 1901–1906 (2002)
8. C. Pricop, D.D. Branisteanu, M. Orsolya, D. Puia, A. Matei, I.A. Checherita, Sublingual desmopressin is efficient and safe in the therapy of lithiasic renal colic. *Int. Urol. Nephrol.* **48**(2), 183–189 (2016)
9. T. Caon, L. Jin, C.M. Simoes, R.S. Norton, J.A. Nicolazzo, Enhancing the buccal mucosal delivery of peptide and protein therapeutics. *Pharm. Res.* **32**(1), 1–21 (2015)
10. Y. Sudhakar, K. Kuotsu, A.K. Bandyopadhyay, Buccal bioadhesive drug delivery—a promising option for orally less efficient drugs. *J. Control Release.* **114**(1), 15–40 (2006)
11. V. Hearnden, V. Sankar, K. Hull, D.V. Juras, M. Greenberg, A.R. Kerr, P.B. Lockhart, L.L. Patton, S. Porter, M.H. Thornhill, New developments and opportunities in oral mucosal drug delivery for local and systemic disease. *Adv. Drug. Deliv. Rev.* **64**(1), 16–28 (2012)
12. J.G. Edmans, K.H. Clitherow, C. Murdoch, P.V. Hatton, S.G. Spain, H.E. Colley, Mucoadhesive electrospun fibre-based technologies for oral medicine. *Pharmaceutics.* **12**(6), 504 (2020)
13. K.H. Clitherow, T.M. Binaljadm, J. Hansen, S.G. Spain, P.V. Hatton, C. Murdoch, Medium-chain fatty acids released from polymeric electrospun patches inhibit *Candida albicans* growth and reduce the biofilm viability. *ACS Biomater. Sci. Eng.* **6**(7), 4087–4095 (2020)
14. M.B. Stie, J.R. Gatke, I.S. Chronakis, J. Jacobsen, H.M. Nielsen, Mucoadhesive electrospun nanofiber-based hybrid system with controlled and unidirectional release of desmopressin. *Int J Mol Sci.* **23**(3), 1458 (2022)
15. H.E. Colley, Z. Said, M.E. Santocildes-Romero, S.R. Baker, K. D'Apice, J. Hansen, L.S. Madsen, M.H. Thornhill, P.V. Hatton, C. Murdoch, Pre-clinical evaluation of novel mucoadhesive bilayer patches for local delivery of clobetasol-17-propionate to the oral mucosa. *Biomaterials.* **178**, 134–146 (2018)
16. A. Moreira, D. Lawson, L. Onyekuru, K. Dziemidowicz, U. Angkawinitwong, P.F. Costa, N. Radacsi, G.R. Williams, Protein encapsulation by electrospinning and electrospraying. *J Control Release.* **329**, 1172–1197 (2021)
17. A. Sharma, A. Gupta, G. Rath, A. Goyal, R.B. Mathur, S.R. Dhakate, Electrospun composite nanofiber-based transmucosal patch for anti-diabetic drug delivery. *J. Mater. Chem. B.* **1**(27), 3410–3418 (2013)
18. M.B. Stie, J.R. Gatke, F. Wan, I.S. Chronakis, J. Jacobsen, H.M. Nielsen, Swelling of mucoadhesive electrospun chitosan/polyethylene oxide nanofibers facilitates adhesion to the sublingual mucosa. *Carbohydr. Polym.* **242**, 116428 (2020)

19. M. Farokhi, F. Mottaghalab, M.A. Shokrgozar, J. Ai, J. Hadjati, M. Azami, Bio-hybrid silk fibroin/calcium phosphate/PLGA nanocomposite scaffold to control the delivery of vascular endothelial growth factor. *Mater. Sci. Eng. C Mater. Biol. Appl.* **35**, 401–410 (2014)
20. M.E. Santocildes-Romero, L. Hadley, K.H. Clitherow, J. Hansen, C. Murdoch, H.E. Colley, M.H. Thornhill, P.V. Hatton, Fabrication of electrospun mucoadhesive membranes for therapeutic applications in oral medicine. *ACS Appl. Mater. Interfaces.* **9**(13), 11557–11567 (2017)
21. M.T. Brennan, L.S. Madsen, D.P. Saunders, J.J. Napenas, C. McCreary, R. Ni Riordain, A.M.L. Pedersen, S. Fedele, R.J. Cook, R. Abdelsayed, M.T. Llopiz, V. Sankar, K. Ryan, D.A. Culton, Y. Akhlef, F. Castillo, I. Fernandez, S. Jurge, A.R. Kerr, C. McDuffie, T. McGaw, A. Mighell, T.P. Sollecito, T. Schlieve, M. Carrozzo, A. Papas, T. Bengtsson, I. Al-Hashimi, L. Burke, N.W. Burkhart, S. Culshaw, B. Desai, J. Hansen, P. Jensen, T. Menne, P.B. Patel, M. Thornhill, N. Treister, T. Ruzicka, Efficacy and safety of a novel mucoadhesive clobetasol patch for treatment of erosive oral lichen planus: a phase 2 randomized clinical trial. *J. Oral Pathol. Med.* **51**(1), 86–97 (2022)
22. K.H. Clitherow, C. Murdoch, S.G. Spain, A.M. Handler, H.E. Colley, M.B. Stie, H. Morck Nielsen, C. Janfelt, P.V. Hatton, J. Jacobsen, Mucoadhesive electrospun patch delivery of lidocaine to the oral mucosa and investigation of spatial distribution in a tissue using MALDI-mass spectrometry imaging. *Mol. Pharm.* **16**(9), 3948–3956 (2019)
23. C. Li, Y.S. Wei, P. Wen, K. Feng, M.H. Zong, H. Wu, Preparation and characterization of an electrospun colon-specific delivery system for salmon calcitonin. *RSC Adv.* **8**(18), 9762–9769 (2018)
24. W. Ji, F. Yang, J.J. van den Beucken, Z. Bian, M. Fan, Z. Chen, J.A. Jansen, Fibrous scaffolds loaded with protein prepared by blend or coaxial electrospinning. *Acta Biomater.* **6**(11), 4199–4207 (2010)
25. J. Schindelin, I. Arganda-Carreras, E. Frise, V. Kaynig, M. Longair, T. Pietzsch, S. Preibisch, C. Rueden, S. Saalfeld, B. Schmid, J.Y. Tinevez, D.J. White, V. Hartenstein, K. Eliceiri, P. Tomancak, A. Cardona, Fiji: an open-source platform for biological-image analysis. *Nat. Methods.* **9**(7), 676–682 (2012)
26. H.E. Colley, V. Hearnden, A.V. Jones, P.H. Weinreb, S.M. Violette, S. Macneil, M.H. Thornhill, C. Murdoch, Development of tissue-engineered models of oral dysplasia and early invasive oral squamous cell carcinoma. *Br J Cancer.* **105**(10), 1582–1592 (2011)
27. M.G. Lancina 3rd., R.K. Shankar, H. Yang, Chitosan nanofibers for transbuccal insulin delivery. *J. Biomed. Mater. Res. A.* **105**(5), 1252–1259 (2017)
28. L. Xu, N. Sheybani, S. Ren, G.L. Bowlin, W.A. Yeudall, H. Yang, Semi-interpenetrating network (sIPN) co-electrospun gelatin/insulin fiber formulation for transbuccal insulin delivery. *Pharm. Res.* **32**(1), 275–285 (2015)
29. C.H. Lee, K.C. Hung, M.J. Hsieh, S.H. Chang, J.H. Juang, I.C. Hsieh, M.S. Wen, S.J. Liu, Core-shell insulin-loaded nanofibrous scaffolds for repairing diabetic wounds. *Nanomedicine.* **24**, 102123 (2020)
30. X. Liu, Q. Li, Y. Wang, M. Crawford, P.K. Bhupal, X. Gao, H. Xie, D. Liang, Y.L. Cheng, X. Liu, R.Y.L. Tsai, Designing a mucoadhesive chemopatch to ablate oral dysplasia for cancer prevention. *Small* **18**(25), e2201561 (2022)
31. J. Teno, M. Pardo-Figuerez, K.J. Figueroa-Lopez, C. Prieto, J.M. Lagaron, Development of multilayer ciprofloxacin hydrochloride electrospun patches for buccal drug delivery. *J. Funct. Biomater.* **13**(4), 170 (2022)
32. M. Pardo-Figuerez, J. Teno, A. Lafraya, C. Prieto, J.M. Lagaron, Development of an electrospun patch platform technology for the delivery of carvedilol in the oral mucosa. *Nanomaterials.* **12**(3), 438 (2022)
33. J.G. Edmans, C. Murdoch, M.E. Santocildes-Romero, P.V. Hatton, H.E. Colley, S.G. Spain, Incorporation of lysozyme into a mucoadhesive electrospun patch for rapid protein delivery to the oral mucosa. *Mater. Sci. Eng. C Mater. Biol. Appl.* **112**, 110917 (2020)
34. J.G. Edmans, B. Ollington, H.E. Colley, M.E. Santocildes-Romero, L. Siim Madsen, P.V. Hatton, S.G. Spain, C. Murdoch, Electrospun patch delivery of anti-TNFalpha F(ab) for the treatment of inflammatory oral mucosal disease. *J Control Release.* **350**, 146–157 (2022)
35. J. Wu, Z. Zhang, J. Gu, W. Zhou, X. Liang, G. Zhou, C.C. Han, S. Xu, Y. Liu, Mechanism of a long-term controlled drug release system based on simple blended electrospun fibers. *J Control Release.* **320**, 337–346 (2020)
36. M. Somogyi, E.A. Doisy, P.A. Shaffer, On the preparation of insulin. *J. Biol. Chem.* **60**, 31–58 (1924)
37. A. Janez, C. Guja, A. Mitrakou, N. Lalic, T. Tankova, L. Czupryniak, A.G. Tabak, M. Prazny, E. Martinka, L. Smircic-Duvnjak, Insulin therapy in adults with type 1 diabetes mellitus: a narrative review. *Diabetes Ther.* **11**(2), 387–409 (2020)
38. N. Bhardwaj, S.C. Kundu, Electrospinning: a fascinating fiber fabrication technique. *Biotechnol. Adv.* **28**(3), 325–347 (2010)
39. R. Quinn, J.D. Andrade, Minimizing the aggregation of neutral insulin solutions. *J. Pharm. Sci.* **72**(12), 1472–1473 (1983)
40. K.W. Buchan, W. Martin, Bradykinin induces elevations of cytosolic calcium through mobilisation of intracellular and extracellular pools in bovine aortic endothelial cells. *Br. J. Pharmacol.* **102**(1), 35–40 (1991)
41. B.F. Reber, R. Neuhaus, H. Reuter, Activation of different pathways for calcium elevation by bradykinin and ATP in rat pheochromocytoma (PC 12) cells. *Pflugers Arch.* **420**(2), 213–218 (1992)