

Proceedings of the

# 4th Historic Mortars Conference HMC2016

10<sup>th</sup>-12<sup>th</sup> October 2016, Santorini, Greece

### **Editors**

Ioanna Papayianni Maria Stefanidou Vasiliki Pachta



Proceedings of the  $4^{\rm th}$  Historic Mortars Conference - HMC 2016 10-12 October 2016, Santorini, Greece

Editors Ioanna Papayianni Maria Stefanidou Vasiliki Pachta

Published by Laboratory of Building Materials Department of Civil Engineering Aristotle University of Thessaloniki

Thessaloniki, Greece, 2016

ISBN: 978-960-99922-3-7

### **Organizing Committee**

Papayianni Ioanna Professor, Aristotle University of Thessaloniki
Stefanidou Maria Associate Professor, Aristotle University of Thessaloniki
Palyvou Clairy Emeritus Professor, Aristotle University of Thessaloniki
Pachta Vasiliki Dr Architect, Conservator, Aristotle University of Thessaloniki

### **Scientific Committee**

Binda Luigia Politecnico di Milano, Italy

Biçer-Şimşir Beril The Getty Conservation Institute, USA

Bokan Bosiljkov Violeta University of Ljubljana, Slovenia

Groot Caspar Delft University of Technology, Netherlands

Hughes John University of the West of Scotland, Scotland

Jornet Alberto University of Applied Sciences and Arts of Switzerland, Switzerland

Lindqvist Jan Erik Cement & Concrete Research Institute, Sweden

Maurenbrecher Paul National Research Council of Canada, Canada

Middendorf Bernhard Technische Universität Dortmund, Germany

Pachta Vasiliki Aristotle University of Thessaloniki, Greece

Papayianni Ioanna Aristotle University of Thessaloniki, Greece

Piqué Francesca University of Applied Sciences and Arts of Switzerland, Switzerland

Stefanidou Maria Aristotle University of Thessaloniki, Greece

Tedeschi Christina Politecnico di Milano, Italy

Toniolo Lucia Politecnico di Milano, Italy

Toumbakari Eleni Hellenic Ministry of Culture, Greece

Valek Jan Academy of Sciences, Czech Republic

Van Hees Rob Delft University of Technology, TNO, Netherlands

Veiga Maria-Rosario National Laboratory for Civil Engineering, Portugal

Velosa Ana University of Aveiro, Portugal

### **PREFACE**

The Historic Mortar Conferences (HMC's) resulted from the need of dissemination of the latest information and advances in materials and techniques for the conservation of Heritage Structures. The HMC's have been established and supported by the core members of RILEM Technical Committees on Historic Mortars, Repair Mortars and Grouts during the last twenty years.

HMC2016 has taken place in Santorini, Greece, where one of the famous prehistory civilization, the Cycladitic one, was developed and destroyed by the eruption of the volcano in Thera, before 3300 years, covering with lava and rock fragments the island. This lava, an igneous and amorphous material, the Thera Earth has been used for centuries, from antiquity up to cement years, as natural pozzolan for producing lime-pozzolan hydraulic type mortars. Many monumental structures and great infrastructure projects, such as the Suez Canal (1866) have been erected with Thera Earth.

That is why the Laboratory of Building Materials of the Aristotle University of Thessaloniki, to which was given the task to organize the HMC2016, decided the venue to be in Santorini on Thera Island, a unique place of the world for its geomorphology and natural beauty.

The participants of HMC 2016 have exceeded 150, coming from more than 35 countries all over the world.

Special thanks are going to the Members of the Organizing Committee and the Scientific staff of the Laboratory of Building Materials AUTH for their dedicated work for the organization, as well as to the Members of the Scientific Committee for their great effort on reviewing the papers. All sponsors are gratefully acknowledged for their financial assistance and active support. Last but not least, I would like to thank all participants, chair persons and discussion contributors for the success of HMC2016.

Ioanna Papayianni Professor AUTH HMC2016 Chair

### **Table of Contents**

Session I / Historical & Constructional aspects of Thera - Theran earth
Analysis and evaluation of mortars in Santorini's construction technology from the Venetian period up to 19 <sup>th</sup> century
Session II / Analysis and characterisation of historic mortars
Historic Mortars: current issues and future work
Characterization of archaeological mortars from Messapian and Roman sites in Lecce
(Italy)
<b>Defects of surface mortar layers</b>
Characterization of Mortars from the Fort of <i>Nossa Senhora da Graça</i> , Elvas (Portugal) to support the conservation of the monument
Two-hundred year old lime putty from barrels found in the ground explaining the character of fat historic lime mortar
<b>"Embrechados" cladding– materials and techniques</b>
Session III / Analysis and characterisation of historic mortars
Analytical Challenges in the Study of New Kingdom Plasters from Tombs in the Valley of the Queens, Luxor, Egypt
Chemical and Mineralogical Characterisation of the Hellenistic Mortars and Plasters from Palaeopolis in Andros, Greece

Characterisation of Incised Plaster Works of Historic Monuments in Delhi, India85 S. Divya Rani, Sangeeta Bais, Manu Santhanam
Revealing the ancient secret of lime mortar exposed to marine environment used in and around Padaleeswarar temple, Tamil Nadu, India93 S. Thirumalini, S.K. Sekar, R. Ravi
"Ganch" as historical building material in the Mausoleum Ishrat Khana, Samarkand, Uzbekistan104 Steffen Laue and Shukrullo Kamilov
Durability of Ancient Mud Mortar in Egypt111 Mohamed Abd El-Hady, Mahmoud Abd El-Hafez and Mahmoud Al-Gohary
Session IV / Analysis and characterisation of historic mortars
Characteristics of Roman Period " <i>Cocciopesto</i> " Mortars Used in Western Anatolia 121 Elif Uğurlu Sağın and Hasan Böke
Characterization of Roman mortars of Nysa in the ancient Caria, Turkey129 Duygu Ergenç, Rafael Fort and Serdar Hakan Öztaner
Roman Mortars from the Amphitheatre of <i>Viminacium</i>
Vitruvian recipes in Roman Aquileia (Italy): the floor bedding mortars of Bestie Ferite and Tito Macro domus
Lime slaking in baskets
Session V / Analysis & characterisation of historic mortars
Historical Mortars in Wallonia (Belgium): A New Archaeological Approach. The Case of the Mediaeval Fortress of Pont-de-Bonne (Belgium, Province of Liège)
Research on 17th c. stucco decorations by the Silva family workshop in the Basilica Santa Maria dei Miracoli in Morbio Inferiore (Tessin)

Coping with copings - Croatian experience in conservation and presentation of curated ruins273
Tajana Pleše, Irma Huić
Conservation and Restoration of the Public Fountains of Olinda: São Pedro, Quatro Cantos and Rosário – Colonial System of Water Supply281 Vania Avelar de Albuquerque
Session VIII / Repair mortars for historic masonry
Replication of historic mortars using six different quicklimes290  Jan Válek <sup>1</sup> , Eveline van Halem, Alberto Viani and Olga Skružná
Long term influence of ACR on lime-based mortars properties300 Petra Štukovnik, Marjan Marinšek, Violeta Bokan Bosiljkov
Experimental Study on the Mechanical Properties of Lime-Based Mortars Produced for Consolidation307 Serhan Ulukaya, Didem Oktay and Nabi Yüzer
Influence of the aggregates' nature and particle size distribution on the mechanical properties of lime-based mortars
Relationship between particle size and reactivity in natural pozzolans and the compressive strength of lime-pozzolan conservation mortars324 Eirini Ampatzioglou, Belinda Colston, Ioannis Karatasios and Vassilis Kilikoglou
Session IX / Repair mortars for historic masonry
Red Ceramic versus White Ceramic Residues as Aggregate for Rehabilitation  Mortars
Isabel Torres and Gina Matias
Comparative evaluation of the luminous performance of lime and gypsum pastes343 María del Mar Barbero-Barrera1, António J. Santos and Rosário Veiga
A lime based mortar for thermal insulation of medieval church vaults
Statistical evaluation of strength of lime-based repair mortars358 Aikaterini Manolopoulou and Ioanna Papayianni

## Session X / Repair mortars for historic masonry

Wood ash as an Additive: a Study of its Influence on the Physical Properties of Lime Mortars
Lucie Fusade and Heather Viles
The use of a lignosulfonate superplasticizer in repair air lime-metakaolin mortars375 M. Pérez-Nicolás, A. Duran, R. Sirera, I. Navarro-Blasco, J.M. Fernández, J.I. Alvarez
Behaviour of air lime-metakaolin mortars modified with polynaphthalene sulfonate as superplasticizer383
A. Duran, R. Sirera, M. Pérez-Nicolás, I. Navarro-Blasco, J.M. Fernández, J.I. Alvarez
Preliminary study on the use of ammonium phosphate for the conservation of marble- imitating gypsum-stuccoes391
Enrico Sassoni, Gabriela Graziani, George W. Scherer and Elisa Franzoni
Pompeian stucco plaster without aggregates: a case study of reconstruction399 Christian Kaiser, Katrin Wilhelm, Ronja Emmerich
Session XI / Repair mortars for historic masonry
Restorative Lime Mortars with Inclusion of Spent Cooking Oils
Experimental Study on bond Strength developed between traditional bricks and lime-based mortars413
Dimitrios Papadimitriou and Ioanna Papayianni
Mechanical and durability properties of lightweight mortars for the backing of ancient mosaics
Fiber- reinforced lime mortars422 M. Stefanidou, M. Papachristoforou, F. Kesikidou
Comparative study for water protection of traditional packed flooring mortars431 Katia Matziaris, Maria Stefanidou, George Karagiannis
Session XII / Repair mortars for historic masonry
Hot- or Wet Slaked Lime Mortar? - Restoration of the Façades of Läckö Castle444

Comparative study between industrial mortars for intervention in historical works 456
Carneiro, A.M.P.; Pederneiras, C.M.; Monte Júnior, I.V.; Paiva, D.F.L de; Mendonça,
L.K.M. de.; Fagundes, A.M. de L. and Fernandes, I.C.
Influence of different paint finishes on the water transport characteristics of
rendering mortars for old masonry walls464
Ana Paula Ferreira Pinto, Diogo Bernardo, Augusto Gomes, Bruna Silva
Conservation mortars for archaeological sites: implementation in situ473 Ioanna Doganis and Amerimni Galanos
Plastering the Prehistory: Marl as a unique material to cover, maintain and decorate the Neolithic walls of Çatalhöyük
Duygu Çamurcuoğlu, Ruth Siddall
Session XIII / Assessment of mortars and masonry
Comparison of the crushing value of irregular shaped samples of historic mortars to standard codified compressive strength
Experimental archaeology: Reconstruction of Roman techniques based on antique
plasters and the descriptions of Vitruvius500 Ralf Kilian, Katrin Wilhelm and LauraThiemann
Building material and production analysis of the industrial lime kiln (19 <sup>th</sup> C.)
excavated in the valley of La Panouse, Marseilles
A new fractal model for predicting water transport properties of historic mortars on
the basis of MIP results518
Giorgio Pia, Ludovica Casnedi, Enrico Sassoni, Ulrico Sanna, Elisa Franzoni
Construction Technology in Temples of Central India-Study of Bhojpur Temple,
Madhya Pradesh526 Shweta Vardia
Silweta valuia
The conservation and restoration of architectural surfaces as a learning process534 Claudia Carvalho, Patricia Cordeiro, Thiago Turino, Gabriel Avellar

Session XIV / Grouts for repair of historic masonry and architectural surfaces
Preliminary Study on the Sulfate Resistance of Lime-Based Hydraulic Injection  Grouts for the Conservation of Architectural Surfaces
Requirements and methods for the choice and consolidation of plasters and renders in situ556
Zuzana Slížková, Rosario Veiga, Rob van Hees
Non-structural injection grouts with reduced water content: Changes induced by the partial substitution of water with alcohol
Adaptation of test methods used to evaluate the properties of non-structural grouts572 Andreja Padovnik <sup>1</sup> and Violeta Bokan-Bosiljkov
Holistic methodology for the mix design of hydraulic grouts in strengthening historic masonry structures
Influence of resins on the properties of lime-pozzolan grouts for surface
Vasiliki Pachta and Ioanna Papayianni
Session XVII / Grouts for repair of historic masonry and architectural surfaces
Repeatability and reproducibility in measuring injection grouts properties: three grouts, two operators
Rheology of natural hydraulic limes for masonry repair
Consolidation of lime renders. Study of some consolidation treatments applied in multilayer renders
Injection grouts based on lithium silicate binder: a simulated cavity test622  Andrew Thorn
Reattachment of a wall painting in a 16th century post-Byzantine church630 (oanna Papayianni, Thanasis Karvounaris and Vasiliki Pachta

related properties63
Chiara Pasian, Michele Secco, Francesca Piqué, Stephen Rickerby, Gilberto Artioli and Sharon Cather
Session XV / Advances in repair materials and technologies concerning historic
structures and archaeological sites
Radiocarbon dating of lime mortars: a historic overview
Analysis and characterisation of historic mortars for absolute dating
New strategies for radiocarbon dating of mortars: Multi-step purification of the lime binder
Hybrid methodologies for mortar analysis, a digital view from the Carolina  Lowcountry
Application of acoustic microscopy technique for the evaluation of the renders applied to masonry
Georgios Karagiannis, Maria Stefanidou, Georgios Apostolidis and Katia Matziaris
Obtaining of self-cleaning repair air lime mortars with photocatalysts
Session XVI / Advances in repair materials & technologies concerning historic structures & archaeological sites
Properties of lime-based pastes with nanosilica
Pozzolanic mortars with nano-TiO <sub>2</sub> for restoration applications: physico-chemical and mechanical assessment
K. Kapetanaki, C. Kapridaki, N. Maravelaki
Optimization of hydraulic lime mortars with nano-SiO <sub>2</sub>

Design of repair air lime mortars combining nanosilica and different superplasticizers
J.M. Fernández, M. Pérez-Nicolás, A. Duran, R. Sirera, I. Navarro-Blasco, J.I. Alvarez
<b>POSS-based epoxy soft nanomaterial for repairing historic clay/stone729</b> Yanli Ma and Ling He
Influence of combined nano-particles in traditional binding systems
Poster session
Assessing susceptibility of new mortars for restoration to pink colonization
Sand regions in Austria – an interdisciplinary approach to characterise sandy aggregates for conservation purposes
Lime binder aggregate interface for indigenous Scottish sands: a preliminary investigation
Alan M Forster, Clare Torney, Lee Masson, Phil Banfill & Benny Suryanto
Characterisation of historic mortars, case of Roman, Byzantine and Ottoman periods in Algeria
M.Hamiane, N. Mahinded, S. Dressi, A. Boukenouf, W.Zekar, M.Saidi
<b>Pozzolanic reactions of hydraulic lime mortar components</b>
Influence of diethyl carbonate as an additive in the carbonation process of lime mortars
Duygu Ergenç, Rafael Fort and David Sanz Arauz
The influence of metakaolin on the properties of natural hydraulic lime based grouts for historic masonry repair
Vavričuk A., Bokan Bosiljkov V., Kramar S.
Influence of porosity on adhesion between air lime mortars and antique tiles771 Sandro Botas Rosário Veiga and Ana Velosa

out of gypsum mortars and stone772 Thomas Köberle	,
The using of the lime mortars in the conservation of the frescoes from the wooden	,
churches in Romania	1
The Work of Renaissance Stuccoers on Telč Chateau (UNESCO, Czech Republic) –  Material characterisation	ļ
Lime-Cement Mortars Study: Variation Granulometric and Origin of Sand	,
Drilling Resistance Measurement in masonry buildings: a statistical approach to characterize non-homogeneous materials	,

# **Session IV**

Analysis and characterisation of historic mortars

# Roman Mortars from the Amphitheatre of *Viminacium*

Emilija Nikolić<sup>1</sup>, Ana Radivojević<sup>2</sup>, Ivana Delić-Nikolić<sup>3</sup> and Dragana Rogić<sup>4</sup>

**Abstract:** Although the first archaeological excavations of *Viminacium*, the capital of the Roman province *Moesia Superior*, today's Serbia, began in 1882, only a small amount of laboratory research on applied building materials has been conducted so far. The grandeur and uniqueness of the building of the Roman amphitheatre now being excavated, and the need for its conservation, required the start of the research on the lime mortars used in this building. Some of the results of this particular research are presented in this paper.

### Introduction

*Viminacium* is an archaeological site located in the villages near the confluence of the rivers Mlava and Danube. It is situated by the small town of Kostolac, in eastern Serbia, and lies on the territory of one of the biggest coal mines in the region. This Roman city and legionary camp was founded in the 1st century AD, survived through flourishing and destructive times, and finally fell as a result of the invasions of the 7th century [1].

Excavations of the Viminacium amphitheatre, the only Roman amphitheatre being excavated in present-day Serbia, started in 2007. The foundation of the amphitheatre is dated to the first quarter of the 2nd century and it was in use until the last years of the 3rd, or the beginning of the 4th century [2].

Laboratory research on the building materials of *Viminacium* started in 2002. For the purpose of three PhD dissertations, bricks, pottery and wall paintings were researched, [3, 4 and 5] while in 2015, travertine found in monuments was analysed [6]. The first analysis of mortars was done in 2007, in the C.S.G. Palladio laboratories in Vicenza, Italy. In 2011, the Institute of Archaeology, Belgrade and the Institute for Testing Materials IMS, Serbia, started researching the mortars from the amphitheatre, in order to begin the process of conservation.

<sup>&</sup>lt;sup>1</sup> Institute of Archaeology, Belgrade, Serbia, e.nikolic@ai.ac.rs

<sup>&</sup>lt;sup>2</sup> Faculty of Architecture, University of Belgrade, Serbia

<sup>&</sup>lt;sup>3</sup> Institute for Testing Materials IMS, Serbia

<sup>&</sup>lt;sup>4</sup> Institute of Archaeology, Belgrade, Serbia

### Materials used in Viminacium lime mortars


The origin of the limestone used in *Viminacium* has not yet been determined. The 19<sup>th</sup> century Austro-Hungarian travel writer, Felix Kanitz, wrote about the tertiary limestone quarries in the Belgrade area, near the Danube, as the source of the *Viminacium* building stone [7]. According to the geological map [8], the mentioned area is connected with the deposits of Tortonian and Sarmatian limestone, but is also rich in sands and clays. Many of the limestone types are in transition between marl and pure limestone. It is well known that in the central zone of Belgrade, limestone [9] was exploited by the Romans [10]. However, it can not be excluded that the limestone from eastern Serbia area was transported by the river Mlava to *Viminacium*, although no archaeological evidence for this exploitation has been found. Recent research on the stone has shown that the *Viminacium* builders also used imported stones, such as Proconnesian marble [11] and travertine from the quarries near *Aquincum* [6].

Sediments of the *Viminacium* area consist of loess, sands, alevrites, pebbles, clays and coal [12]. In addition to lime mortars, builders often used mud mortars, and mixtures comprising different combinations of lime and earth [13]. The natural richness in clay materials resulted in large brick production in this Roman town [14], so brick and pottery were often used as mortar additives. The results of laboratory research showed that *Viminacium* bricks and pottery were mostly fired at temperatures lower than 900°C, suggesting pozzolanic features. The overall sum of SiO<sub>2</sub>O<sub>3</sub>, Al<sub>2</sub>O<sub>3</sub> and Fe<sub>2</sub>O<sub>3</sub> is bigger than 70%, and the loss on ignition is lower than 10% for almost all the analysed samples [15, 16].

In one part of the wider Belgrade area near the Danube, zeolitic tuffs were found, [17] but there is no evidence of their exploitation through history. Material that can be called "natural brick", which has the common Serbian name "crvenka", and is internationally known as clinker and porcellanite [18, 19], was often used as a building element in the wall and road structures of *Viminacium* [20, 2]. It is visible as a reddish layer in the nearby hill over the former underground coal mine, and represents metamorphosed sedimentary rock, formed during the combustion of the coal layers underneath [18]. Although very rarely, it is found in some ancient Roman structures in Europe [21]. Several studies have determined the pozzolanic features of this type of material [22, 23], but only the research of local deposits can lead us further to the analyses of its possible use in *Viminacium* mortars.

### Laboratory research

Ten mortar samples from the amphitheatre of *Viminacium* were chosen for the laboratory research in 2011 and 2014. The results of the conducted analyses on four samples of structural and protective mortars (Fig. 1) are shown here.

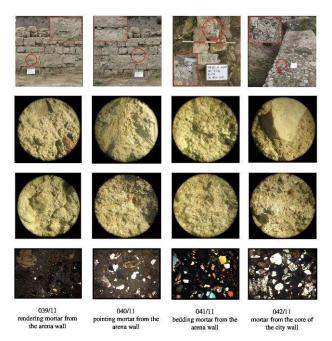

**Fig. 1** Position of the sampling mortars and the results of the optical microscopy: views under the laboratory magnifier and micro views (using crossed Nicols, the field is 6mm wide)

The arena wall of the amphitheatre is preserved up to 4m and was built almost completely from limestone blocks bonded with lime mortar, with traces of collapse and repair in the debris. The wall was rendered on both sides, and the side facing the arena was painted. Unfortunately, the city wall surrounding the amphitheatre is preserved only in the foundations, which were built of schists and different stone and brick fragments, bonded with lime mortar. The research of the mortars included the analyses of the volume mass, water absorption, compression strength, porosity, pore distribution, chemical and mineralogical - petrographic composition with the determination of materials (Tables 1-3).

In the rendering mortar sample 039/11 from the arena wall, noticeable is an increased loss on ignition at 450°C, which indicates an increased quantity of bound moisture and organic substances, in this case the remains of straw that directly influenced the high porosity and the water absorption of the sample. The content of Al<sub>2</sub>O<sub>3</sub> comes from the feldspar and mica grains as well as from the fragments of bricks. One part of the CaO content comes from one of the feldspars (anorthite). This sample is characterised by a low volume mass, a high value of water absorption and porosity, and a middle value of compressive strength.

Table 1 Mineralogical and petrographic composition and the determination of materials

	AGGREGAT	Е											
	_	com	positi	on (%	Vol)								
sample	granulation (mm)	quartz	feldspar	pyroxene	mica	calcite	chert	granitoid	quartzite	schist	brick	limestone	B/A (Vol.)
039/	0-1(98%)	94	5	-	1	-	-	-	-	-	-	-	80/
11	1-10(2%)	-	-	-	-	-	-	-	50	-	50	-	20
040/	0-1(95%)	94	3	-	2	-	-	-	-	-	1	-	75/
11	1-4(5%)	-	-	-	-	-	-	50		-	50	-	25
0.41/	0-2(93%)	90	5	2		-	-	-	3		-	-	65/
041/ 11	2-5(5%)	-	-	-	-	-	-	-	100		-	-	35
••	5-10(2%)	-	-	-	-	-	-	-	100		-	-	33
	0-4(87%)	84	5	-	1		10				-	-	70/
042/ 11	4-10(3%)	40	-	30	-	-	-	-	30	-	-	-	70/
11	15-60(10%)	-	-	-	-	-	-	-	-	-	-	100	30

While observing the pointing mortar sample 040/11 from the arena wall, remains of chopped straw were also found, which caused the high values of porosity and water absorption. A decreased loss on ignition at  $950^{\circ}C$  determined a lower content of the carbonate binding component. The content of  $SiO_2$  is noticeably higher than in the previous sample. The highest proportion of this oxide comes from quartz minerals, but the other parts are connected to other minerals. Although  $Al_2O_3$  comes from the present feldspar and mica grains, as well as from brick fragments, its high content together with the high content of  $SiO_2$  indicates that, during the preparation of the mortar, some other mineral aluminosilicate additive was used in a small quantity. The volume mass is higher than that of the previous sample, water absorption is lower, compression strength is still medium and porosity is high.

Table 2 Results of the chemical analyses

chemical composition (% vol) loss on ignition									gnition
method	SRPS B.D8.205, B.D8.210								
sample	SiO <sub>2</sub>	$Al_2O_3$	Fe <sub>2</sub> O <sub>3</sub>	CaO	MgO	Na <sub>2</sub> O	$K_2O$	$950^{0}$ C	450°C
039/11	16.50	2.79	1.18	43.05	0.95	0.33	0.46	33.72	5.80
040/11	40.25	4.67	1.18	29.17	0.59	0.21	0.45	22.70	3.01
041/11	66.84	5.12	1.42	13.21	1.19	0.13	0.46	10.73	3.23
042/11	53.38	5.15	2.25	20.92	1.08	0.36	0.48	15.82	2.02

**Table 3** Physical and mechanical characteristics of the samples

method	EN 1015-10	EN 1015-18	EN 1015-11	mercury porosimetry			
sample	volume mass (g/cm³)	water absorption ( vol.%)	compres sive strength (MPa)	overall pore volume (cm³/g)	porosity (vol.%)	middle pore diameter (nm)	specific pore area (m²/g)
039/11	1.10	42.4	2.4	0.34	45.8	1342	7.9
040/11	1.27	35.5	2.0	0.36	47.1	1950	6.1
041/11	1.65	22.3	2.7	0.20	33.4	74	14.1
042/11	1.86	11.7	5.3	0.13	24.7	5402	4.3

The bedding mortar sample 041/11 from the arena wall has a very low loss on ignition at  $950^{0}$ C, as well as the content of CaO, which indicates a decreased content of the carbonate binding component compared to the previous two samples. The content of  $SiO_2$  is higher compared to the quantity of the quartz minerals. One part of  $SiO_2$  comes from other minerals, i.e. feldspar, mica, schist and pyroxene. However, the high content of  $SiO_2$  and  $Al_2O_3$  again point to a mineral additive of aluminosilicate composition, even in a higher percentage than in the previous sample. According to the available data, the percentage of this additive could even be 30%. The compression strength was higher in this sample, and the volume mass is noticeably higher than in the previous two samples (even 50% higher than in the first sample). Water absorption is noticeably lower (twice as low as in the first sample) and porosity and the overall volume of pores are decreased.

A notable characteristic of the city wall core mortar sample 042/11 is the presence of large grains in the aggregate. Limestone fragments (sized from 1.5cmx2cm to 4.5cmx6cm) are present in a percentage of 10%. The content of SiO<sub>2</sub> is much higher than the quartz mineral content, also determined by mineralogical and petrographic analyses. The content of Al<sub>2</sub>O<sub>3</sub> is higher than in other samples (a little higher than in the third one). High contents of SiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> again indicate that a mineral aluminosilicate additive was used, probably in a percentage of 25%. With this data, the physical and mechanical characteristics of the sample are correlated. Compression strength is high for lime mortars, which can also be the result of the presence of large limestone fragments. The first descriptions of Viminacium mortar were given in 1907 by Miloje Vasić, the first qualified archaeologist to excavate Viminacium, who wrote that a very hard mortar from a grave was made of lime, crushed, but not baked, limestone and grains of quartz in the form of pebbles [14]. The value of the volume mass is noticeably higher in this sample than in all the previous three. This characteristic is also high for lime mortars, along with the lowest value of water absorption. Correlating to this are the lowest overall pore volumes and the lowest volume percentage of porosity.

### **Discussion**

From the presented laboratory results it can be concluded that all the mortars sampled were made as mixtures of a carbonate binder and fine natural aggregate which, according to the shape of the grains, was assumed to be of a river origin. The voids are present in 3% for the 039/11-041/11 samples, and 2% for sample 042/1. Samples 039/11 and 040/11 show a significant level of mutually similar characteristics, such as granulation, mineralogical and petrographic composition, the presence of straw and brick, as well as physical-mechanical characteristics (Table 3 and Fig. 2). A similar case is seen with the samples 041/11 and 042/11, where the aggregate content is higher, the grains are bigger and the SiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> content is higher. (Table 2 and Fig. 2) The results of the porosity tests showed that, in the examined interval of pore size (7.5nm – 15000.0nm), sample 040/11 had the highest value of overall porosity, while the lowest is in sample 042/11(Fig. 2).

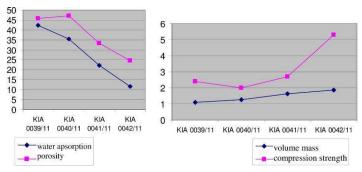


Fig. 2 Diagrams showing the correlated research values, mutually compared

The mutual comparison of the loss on ignition values at the temperatures of 950° and 450° obtained by this research, and the principles applied in the analogous research [24, 25, 26 and 27] can indicate the possible hydraulicity of Viminacium mortars. In the region of the present-day Serbia, the use of brick was the usual way for obtaining the better characteristics of Roman mortars. The Viminacium builders used brick as an additive in wall finishing and floor mortar layers [28], a practice expected in structures directly exposed to water and in humid or warm environments [29], but their structural mortars rarely contained brick [28]. The results of the laboratory research of the samples without brick in the mixture can lead us to the assumption that the builders could have added some natural aluminosilicate materials. Unfortunately, based on current understanding, they had no natural material with pozzolanic features for making mortars stronger. Strength and an increased percentage of silicon and aluminium oxides in these mortars could also have been achieved by the introduction of impurities into the mixtures whilst using hot lime technology or by using lime already containing certain impurities that the builders may not always have recognised. This can be further explored by means of research of the available limestone and the role of different additives and lime inclusions visible in many samples analysed during 2007, 2011 and 2014.

### Conclusion

Provincial Roman architecture always depended on local resources. One of the problems in determining the natural resources of *Viminacium* is the coal exploitation, whose development is constantly changing the landscape.

The laboratory research of the lime mortars from the *Viminacium* amphitheatre showed that they were prepared in a variety of ways, depending on their role in the particular structure. This is most noticeable in the case of the city wall of *Viminacium*, which was built with the mortar of the highest compressive strength.

Future laboratory research of the natural materials that may have been used in the production of lime mortar, as well as research of a larger number of mortar samples from different monuments and periods of the seven century lifespan of *Viminacium*, with special attention given to their possible hydraulicity, will probably provide some answers to the questions this paper has raised.

### Acknowledgments

The article is a result of the project: IRS - Viminacium, Roman city and military legion camp - research of the material and non-material culture of inhabitants by using the modern technologies of remote detection, geophysics, GIS, digitalization and 3D visualization (no 47018), funded by the Ministry of Education, Science and Technological Development of the Republic of Serbia. Authors of the paper thank Ivan Bogdanović, a researcher from The Institute of Archaeology, Belgrade, for sampling the mortars and guiding the laboratory team through the archaeological site.

### References

- Mirković M (1968) Rimski gradovi na Dunavu u Gornjoj Meziji. Arheološko društvo Jugoslavije, Beograd
- Nikolić S, Bogdanović I (2012) Istraživanja viminacijumskog amfiteatra u toku 2011. godine". In: Bikić V, Golubović S, Antonović D (eds) Arheologija u Srbiji: Projekti Arheološkog instituta u 2011.godini. Arheološki institut, Beograd
- Radivojević A (2003) Bricks of late antique buildings in the Roman provinces of the central Balkans.
   Unpublished PhD thesis defended at Faculty of Architecture, University of Belgrade
- Raičković A (2012) Ceramic vessels in graves of the Mala Kopašnica Sase type. Unpublished PhD thesis defended at Faculty of Philosophy, University of Belgrade
- Rogić D (2014) Technology of ancient wall paintings on the territory of Serbia. Unpublished PhD thesis defended at Faculty of Philosophy, University of Belgrade
- Đurić B, Kale S, Rižnar I (2015) The Budakalaász travertine production. In: Proceedings of ASMOSIA XI International conference (in press)
- Каниц Ф (1989) Србија: Земља и становништво од римског доба до краја XIX века, прва књига. Српска књижевна задруга, Београд
- Ivković A (1975) Tumač za list Pančevo. Osnovna geološka karta Pančevo 1:100 000. Savezni geološki zavod, Beograd

- Jović V (2004) Geochemical characteristics of miocene limestones of Tašmajdan and Kalemegdan (Belgrade, Serbia). Geochimica et Cosmochimica Acta 68/11. Supplement 318
- Tomović M (1992) Roman sculpture in Upper Moesia. Posebna izdanja 24. Archaeological Institute, Belgrade
- 11. Томовић М (1991) Проконески саркофаг са гирландама из Viminaciuma. Viminacium 6: 69-82
- 12. Rakić M, (1980) Tumač za list Bela Crkva. Osnovna geološka karta Bela Crkva . Savezni geološki zavod, Beograd
- Stanojlović M (1992) Neka opažanja o upotrebljenim malterima za zidanje i malterisanje grobova u Viminacijumu. Glasnik Društva konzervatora Srbije 16: 56-59
- 14. Васић М (1907) Неколике гробне конструкције из Виминацијума. Старинар н.р. II: 66-98
- Radivojević A, Kurtović-Folić N (2006) Evolution of bricks and brick masonry in the early history of its use in the region of today's Serbia. J.Mater.Civ.Eng.18, Special issue: Innovative materials and technologies for construction and restoration: 692-699
- Marese G, Tucci P, Raičković Savić A (2015) Roman pottery from Viminacium (Serbia, 2<sup>nd</sup>-3<sup>rd</sup> centuries AD): compositional characteristics, production and technological aspects. Archaeology and Science 10/2014: 9-43
- Radosavljevic Mihajlović A, Došen A, Stojanović J et al (2013), Occurences and properties of zeolithic tuffs in Serbia. In (eds) Proceedings of the 5<sup>th</sup> Serbian-Croatian-Slovenian symposium on zeolites
- Murphy EC (2013) Clinker ("scoria") as road surfacing material in western North Dakota. Geonews 40/1: 2-4
- 19. Rădan SC, Rădan S, (2011) Coal palaeofires in the western Dacic Basin (Romania): geophysical, mineralogical and geochemical signatures recovered from porcelanites and clinkers; a case history. In: Gonçalves A, Vieira, A (eds) Fire Effects on Soil Properties, Proceedings of the 3rd international meeting on fire effects on soil properties. NIGP-Univ. Minho and CEGOT, Guimarães
- Golubović S, Korać M (2010) The recent discovery of a temple complex at Viminacium.. Bollettino di archeologia on line I, volume special, poster session 3: 33-36
- Allen JRL, Fulford MG (2004) Early Roman mosaic materials in Southern Britain, with particular reference to Silchester (Calleva Atrebatum): A regional geological perspective. Britannia 35:9-38
- Gutt W, Gaze ME (1975) Trinidad porcellanite as a pozzolan. Materials and Structures Vol.8, No.6: 439-450
- Ríos CA, Williams CD (2008) Synthesis of zeolitic materials from natural clinker: A new alternative for recycling coal combustion by-products. Fuel 87: 2482-2492
- 24. Bakolas A, Biscontin G, Moropoulou A et al (1998) Characterization of structural Byzantine mortars by thermogravimetric analysis. Thermochimica Acta 321:151-160.
- Moropoulou A, Bakolas A, Bisbikou K (2000) Investigation of the technology of historic mortars.
   Journal of Cultural Heritage 1: 45-58
- Marques SF, Ferreira VM, Labrincha JA et al (2006) Study of old rehabilitation mortars by common analytical techniques. In: Fort R, Alvarez de Buergo M, Gomez-Heras M et al (eds) Proceedings of the International Conference on HWC 2006, CRC Press, Boca Raton
- Elsen J, Van Balen K, Mertens G (2012) Hydraulicity in historic lime mortars: a review. In: Valek J, Hughes JJ, Groot CJWP (eds) Historic Mortars: Characterisation, Assesment and Repair. Springer International Publishing, Switzerland
- 28. Nikolić E, Rogić D, Milovanović B (2015) The role of brick in hydraulicity of Viminacium mortars: Decorative mortars from the thermae. Archaeology and Science 10/2014: 71-91
- Stefanidou M, Pachta V, Konopisi, S, Papayianni I (2014) Analysis and characterization of hydraulic mortars from ancient cisterns and baths in Greece. Materials and Structures 47: 571-580

4<sup>th</sup> Historic Mortars Conf HMC 2016



Laboratory of Building Materials Department of Civil Engineering Aristotle University of Thessaloniki



















