

6-14-2022

Synthesis of Phenyl Carbamoylated Guanidine Functionalized Chitosan

Eduardo Hernandez Requejo
Florida International University, ehern347@fiu.edu

Follow this and additional works at: <https://digitalcommons.fiu.edu/etd>

 Part of the [Medicinal-Pharmaceutical Chemistry Commons](#), [Organic Chemistry Commons](#), and the [Polymer Chemistry Commons](#)

Recommended Citation

Hernandez Requejo, Eduardo, "Synthesis of Phenyl Carbamoylated Guanidine Functionalized Chitosan" (2022). *FIU Electronic Theses and Dissertations*. 5124.
<https://digitalcommons.fiu.edu/etd/5124>

This work is brought to you for free and open access by the University Graduate School at FIU Digital Commons. It has been accepted for inclusion in FIU Electronic Theses and Dissertations by an authorized administrator of FIU Digital Commons. For more information, please contact dcc@fiu.edu.

FLORIDA INTERNATIONAL UNIVERSITY

Miami, Florida

SYNTHESIS OF PHENYL CARBAMOYLATED
GUANIDINE FUNCTIONALIZED CHITOSAN

A thesis submitted in partial fulfillment of the

requirements for the degree of

MASTER OF SCIENCE

in

CHEMISTRY

by

Eduardo Hernandez Requejo

2022

To: Dean Michael R. Heithaus
College of Arts, Sciences and Education

This thesis, written by Eduardo Hernandez Requejo, and entitled Synthesis of Phenyl Carbamoylated Guanidine Functionalized Chitosan, having been approved in respect to style and intellectual content, is referred to you for judgment.

We have read this thesis and recommend that it be approved.

Watson Lees

Stanislaw Wnuk

Joong Ho Moon, Major Professor

Date of Defense: June 14, 2022

The thesis of Eduardo Hernandez Requejo is approved.

Dean Michael R. Heithaus
College of Arts, Sciences and Education

Andrés G. Gil
Vice President for Research and Economic Development
and Dean of the University Graduate School

Florida International University, 2022

DEDICATION

I dedicate this dissertation to Maria Teresa, my beloved wife, for her love, support, and encouragement throughout my M.S. journey.

ACKNOWLEDGMENTS

My sincere gratitude to my mentor Dr. Joong Ho Moon, for his guidance and support. I would also like to extend my sincere thanks to my committee members, Dr. Watson Lees and Dr. Stanislaw Wnuk, for their help during this work.

ABSTRACT OF THE THESIS

SYNTHESIS OF PHENYL CARBAMOYLATED GUANIDINE FUNCTIONALIZED
CHITOSAN

by

Eduardo Hernandez Requejo

Florida International University, 2022

Miami, Florida

Professor Joong Ho Moon, Major Professor

The lack of solubility of the chitosan in organic solvents hinders its potential for chemical modifications. For this reason, it was hypothesized that the insertion of the phenyl carbamoylated guanidine moiety could lead to increased solubility in DMSO and new potential modifications and uses.

This research involved the synthesis of S-methyl phenyl carbamoylated guanidine (SMPCG) starting from the commercially available S-methyl isothiurea. This was followed by the reaction of the SMPCG with chitosan to yield phenyl carbamoylated guanidine functionalized chitosan (PCGCs) with a degree of substitution of 14%.

The chitosan derivative is fully soluble in DMSO and partially in DMF. This modified polymer will be used in future experiments in protein delivery, antimicrobial activity, and siRNA transfection. Future research is also planned to obtain PCGCs with different degrees of substitution.

TABLE OF CONTENTS

CHAPTER	PAGE
I. INTRODUCTION AND LITERATURE REVIEW	1
1.1 Chitin and Chitosan	1
1.2 Chitosan Derivatives	3
1.3 Chitosan uses.....	4
1.3.1 Biomaterial and tissue engineering	4
1.3.2 Food packaging	5
1.3.3 Antioxidant and antimicrobial	5
1.3.4 Adsorption of metals and dyes.....	6
1.3.5 Gene delivery	6
1.4 The carbamoylated guanidine moiety.....	8
1.5 Research Purpose	10
II. EXPERIMENTAL METHODS	11
2.1 Materials and Instrumentation	11
2.1.1 Materials.	11
2.1.2 Nuclear magnetic resonance (NMR).....	11
2.2 Solubilization of chitosan in acetic acid 1% v/v solution	12
2.3 Synthesis of mono-BOC protected S-methyl isothiurea	13
2.4 Synthesis of mono-BOC protected S-methyl phenyl carbamoylated guanidine	13
2.5 Synthesis of deprotected S-methyl phenyl carbamoylated guanidine	14
2.6 Synthesis of phenyl carbamoylated guanidine functionalized chitosan.....	15
2.7 BOC deprotection of phenyl carbamoylated guanidine functionalized chitosan	16
III. RESULTS AND DISCUSSION	17
3.1 Synthesis strategies	17
3.2 Solving the chitosan solubility problem.....	17
3.3 Synthesis of the S-methyl phenyl carbamoylated guanidine.....	20
3.4 Reaction of the chitosan with the mono BOC S-methyl phenyl carbamoylated guanidine	23
3.5 NMR analysis of the product and determination of the degree of substitution	26

3.6 BOC deprotection of the phenyl carbamoylated guanidine functionalized chitosan.....	27
IV. CONCLUSION	29
REFERENCES	30
APPENDIX	40

LIST OF TABLES

TABLE	PAGE
1. Examples of Chitosan Modifications.....	3

LIST OF FIGURES

FIGURE	PAGE
1. Chitosan.....	1
2. Chitosan solubility in aqueous acidic solutions.....	2
3. Formation of polyplexes.....	7
4. Examples of cationic polymers.....	7
5. The carbamoylated guanidine and guanidinium groups.....	9
6. Guanidine bidentate interaction with phosphate.....	9
7. Scheme for the synthesis of the PCGCs.....	17
8. Chitosan mesylate salt formation.....	18
9. BOC protection of the S-methyl isothioureia.....	20
10. ¹ H NMR (400 MHz, CDCl ₃) spectrum of mono-BOC protected S-methylisothioureia.....	21
11. Synthesis of the BOC protected S-methyl phenyl carbamoylated guanidine.....	22
12. ¹ H NMR (400 MHz, CDCl ₃) spectrum of BOC protected S-methyl phenyl carbamoylated guanidine.....	22
13. Reaction of the chitosan with the mono BOC S-methyl phenyl carbamoylated guanidine.....	23

14. ^1H NMR (400 MHz, DMSO- d_6) spectrum of phenyl carbamoylated guanidine chitosan.....	23
15. Proposed reaction mechanism for the chitosan modification.....	24
16. ^1H NMR spectra comparison of unmodified chitosan (400 MHz, D $_2$ O/ Acetic acid- d_4 1%) and phenyl carbamoylated guanidine chitosan (400 MHz, DMSO- d_6).....	26
17. Illustration of the ^1H NMR determination of the degree of substitution of the PCGCs.....	27
18. Deprotection of the PCGCs.....	28

LIST OF ABBREVIATIONS AND SYMBOLS

AcOH	Acetic Acid
BOC	tert-Butoxy Carbonyl
BOC ₂ O	Di(tert-butyl) dicarbonate
CAGR	Compound Annual Growth Rate
CDCl ₃	Deuterated Chloroform
CP	Conjugated Polymer
CPPs	Cell-Penetrating Peptides
D ₂ O	Deuterium Oxide
DCM	Dichloromethane
DMF	Dimethyl Formamide
DMSO	Dimethyl Sulfoxide
DMSO-d ₆	Dimethyl Sulfoxide deuterated
DNA	Deoxyribonucleic Acid
EA	Ethyl Acetate
FIU	Florida International University
HCl	Hydrochloric acid
KOH	Potassium hydroxide
MW	Molecular Weight
mRNA	messenger RNA
MSA	Methanesulfonic Acid
NMR	Nuclear Magnetic Resonance

PCGCs	Phenyl carbamoylated guanidine chitosan
PEG	Polyethylene Glycol
PEI	Polyethylene Imine
PhNCO	Phenyl Isocyanate
RBF	Round Bottom Flask
RNA	Ribonuclease Acid
RNAi	RNA Interference
ROMP	Ring-Opening Metathesis Polymerization
siRNA	small interfering RNA
SMPCG	S-methyl Phenyl Carbamoylated Guanidine
TFA	Trifluoro Acetic Acid
THF	Tetrahydrofuran

I. INTRODUCTION AND LITERATURE REVIEW

1.1 Chitin and Chitosan

Chitin is a linear polymer of β -1,4-linked N-acetyl-D-glucosamine¹. It is the second most abundant polysaccharide in nature and is found in insects and crustaceans' exoskeleton and the fungal and yeast cell wall². Chitin has a cellulose-like structure, where the hydroxyl group in the C2 position has been replaced by an acetamido group³. Depending on the orientation of polysaccharide chains, chitin displays three polymorphs, denoted as α , β , and γ ⁴. A notable characteristic of chitin is its poor biodegradability and a high degree of insolubility in organic and inorganic solvents⁵.

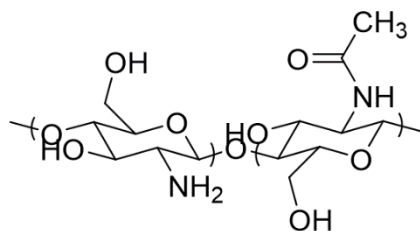


Figure 1. Chitosan.

Discovered by Rouget in 1859 after heating chitin in an alkaline medium⁶, chitosan is the most common chitin derivative⁷. Formed by randomly distributed β -(1-4)-linked D-glucosamine and N-acetyl D-glucosamine units⁸, chitosan is obtained through the deacetylation of the chitin macromolecule by subjecting it to hot alkali (e.g., NaOH concentrated solutions) treatment⁹ (Figure 1). Chitosan has a ridged crystalline structure built through inter- and intra-molecular hydrogen bonds¹⁰. Owing to the deacetylation process, a unique structural feature of chitosan is the primary amine at the C-2 position of the glucosamine, which confers important functional properties to chitosan¹¹. Because of

its linear structure and polysaccharide nature, this biopolymer is biocompatible, non-inflammatory, non-toxic, and biodegradable¹². The pKa of the primary amine of chitosan is ~6.5, depending on the degree of N-deacetylation¹³. Therefore, the amino groups can be protonated at pH below 5, promoting chitosan solubility in aqueous acidic solutions¹⁴ (Figure 2).

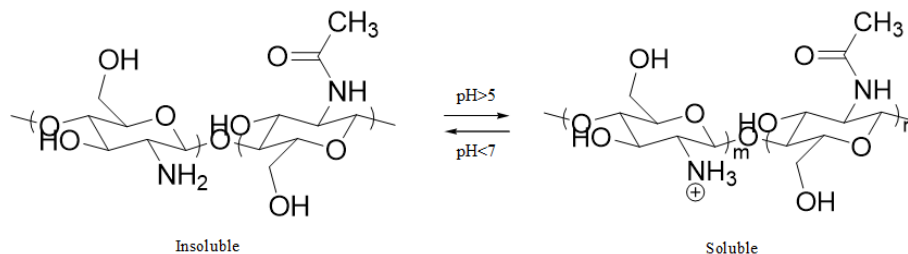


Figure 2. Chitosan solubility in aqueous acidic solutions.

There can be variations in molecular weight, degree of acetylation, and order sequence of the acetylated moieties¹¹ between different chitosan varieties or chains. Due to this, there is a certain degree of variability in the properties of different chitosan varieties¹⁵.

The final extent of deacetylation is one of the most critical factors affecting the properties of chitosan, as it determines the number of available amino groups in the chitosan chain¹⁶. Crystallinity, hydrophilicity, degradation, and cell response are all properties affected by deacetylation¹⁷. Chitosan is characterized by a low acetylation degree, usually below 50%, and molecular weight between 50 and 2000 kDa¹⁸.

However, chitosan also has serious disadvantages, starting with the fact that it is not soluble in water and organic solvents and can only be dissolved by slightly acidic aqueous solutions¹⁹. This limits notably the range of reaction conditions available for performing chemical transformations involving chitosan²⁰. The high dependence of the cationic nature of this polymer on the pH values introduces a degree of unpredictability to its behavior,

especially for protein and nucleic acids carrier uses in biological applications²¹. Under physiological conditions, the pH values will lead to a lowered charge density on the amino groups, with the subsequent reversal of its solubility and cationic properties²². Additionally, once the chitosan is transported inside the cells and the endocytosis process has been initiated, the acidic conditions inside the endosome cause the chitosan to become protonated again, which leads to increased electrostatic interaction with the payload and subsequently hinders their release into the cytoplasm²³.

1.2 Chitosan Derivatives

Chitosan contains nucleophilic functional groups: a C-2 NH₂ group, a C-3 secondary OH group, and a C-6 primary OH group. Chitosan has been chemically modified at the amino group or at the hydroxyl groups to produce derivatives containing cationic or other hydrophilic and hydrophobic moieties²⁴. Because of chitosan's attractive properties, several modifications have been proposed to modify its structure²⁵ (Table 1).

Table 1. Examples of Chitosan Modifications

Modifications to enhance chitosan solubility	Modifications to enhance antimicrobial properties	Modifications to enhance protein/ nucleic acid delivery
Mesylate salt formation ²⁶	Hydroxypropyl chitosan ²⁷	PEI grafting
N-phthalimide insertion ²⁸	Biguanidinylation ²⁹	Guanidinylation ³⁰
Carboxymethylation ³¹	Cyclic substituted chitosan ³²	Hyaluronic acid/ Chitosan multilayer coating
Camphor sulfonic salt formation ²⁶	N-(2-quarternary ammoniumyl) acyl chitosan derivatives ³³	PEGylation ³⁴
Etherification ³⁵	Sulfonamide-chitosan derivative ³⁶	Attachment of diethylamino ethyl groups ³⁷

In some cases, these modifications originated from the need to overcome the poor solubility of chitosan³⁸. In other cases, the motivation is to enhance a desirable characteristic already present in the chitosan³⁹ to maximize its functionality as antimicrobial⁴⁰ or nucleic acid delivery agent⁴¹. These modifications typically target the amino or hydroxyl groups to produce derivatives containing cationic or other hydrophilic and hydrophobic moieties⁴².

1.3 Chitosan uses

The attractive properties of chitosan and its derivatives have applications in many areas. These include biomaterial and tissue engineering, food and nutrition applications, antioxidant and antimicrobial, and drug and gene delivery. As an example of the growing interest in this biomaterial, in 2019, the global chitosan market size was valued at USD 6.8 billion, with an expected expansion at a revenue-based Compound Annual Growth Rate (CAGR) of 24.7% between 2020 and 2027⁴³.

1.3.1 Biomaterial and tissue engineering

The applications of chitosan as a biomaterial for tissue engineering have been widely investigated⁴⁴. Chitosan can be processed into different structures, such as films⁴⁵, nanoparticles⁴⁶, hydrogels⁴⁷, or fibers⁴⁸, which translates into a high degree of versatility for multiple applications⁴⁹.

Developing scaffolds based on synthetic or natural polymers in different forms has been a standard method for providing cells with an environment similar to the biological extracellular matrix (ECM)⁴⁶. Used as a scaffold, chitosan can act as physical support for cells⁵⁰, allowing them an optimal environment for growing and tissue structuring⁵¹. The choice of chitosan as a tissue support material is due to the multiple ways its properties can be controlled and engineered⁵².

1.3.2 Food packaging

The development of biodegradable polymers for eco-friendly food packaging is one way to minimize the problem of the accumulation of plastics in the environment⁵³. Thus, there is a continuous interest in exploring new biomaterials that can serve this purpose.

Chitosan poses good mechanical properties and capacity of selective permeability to O₂ and CO₂⁵⁴. In addition, chitosan also has intrinsic antioxidant and antimicrobial activities against fungi, molds, yeasts, and bacteria⁵⁵, which can potentially extend the shelf life by inhibiting the presence and growth of microorganisms and bacteria when in direct contact with fresh or processed foods⁵⁶.

Properties like tensile strength and elongation percentage at break and barrier properties are significant in the food packaging industry⁵³. Chitosan offers the potential for multiple chemical modifications and polymer blending, allowing for fine-tuning of these and other properties for particular applications⁵⁷. All these factors make chitosan a desirable material for food packaging.

1.3.3 Antioxidant and antimicrobial

Chitosan has unique antimicrobial and antiviral properties, widely described^{24,43,58-60}. Several possibilities have been described as the mode of action for chitosan, from binding to bacterial DNA, which leads to inhibition of mRNA, to interaction with surface molecules⁶¹.

The most accepted hypothesis for the origin of this antimicrobial activity is related to the positively charged amino groups in the chitosan chain, which can interact with the

negatively charged surface components of many microorganisms⁶². This would lead to extensive alterations in the surface, resulting in cell death⁴³.

The antimicrobial activity of CS differs depending on its molecular weight (MW) and the type of attacking microorganism³²:

- High MW chitosan has a marked antibacterial effect against gram-positive and negative bacteria⁶¹.
- Low MW chitosan exerts a more substantial effect against hyphal growth via a dual effect on spores and fungal cells⁶³.
- Oligomeric CS has a more potent antimicrobial effect on fungi⁶⁴.

1.3.4 Adsorption of metals and dyes

The presence of synthetic dyes and metals in water sources can produce severe health and ecological issues. Therefore, there is a high degree of interest in developing new ways of removing these contaminants from aqueous streams⁶⁵. Chitosan has received attention as a viable adsorbent due to its biodegradability, biocompatibility, and low cost⁶⁶. The presence of several active sites in the form of -OH and -NH₂ in the chitosan chain confers this polymer with the ability to interact and adsorb metals⁶⁷⁻⁶⁹ and dyes^{66,70}

1.3.5 Gene delivery

Early efforts to transfect cells using non-viral vectors led to the observation that positively-charged molecules, typically rich in protonating amine groups, could form electrostatic complexes with negatively charged nucleic acids⁷¹ (Figure 3). The resulting nano complexes had transfection capabilities⁷². This transfection capability is currently

described by a mechanism of gene delivery by cationic systems, which includes four steps⁷³:

1. Non-specific interaction between cationic particles and cell surface
2. Endocytosis into endocytic vesicles (endosomes)
3. Compaction and release of the genetic material/particle from endosomes
4. Translocation of the released material to the nucleus by membrane receptors and its transgenic expression.



Figure 3. Formation of polyplexes

The use of these cationic materials as gene vectors started with naturally occurring compounds like protamine⁷⁴ and spermine⁷⁵. The available carriers progressively developed into various cationic compounds specifically aimed at gene delivery, like cationic lipids and polymers.

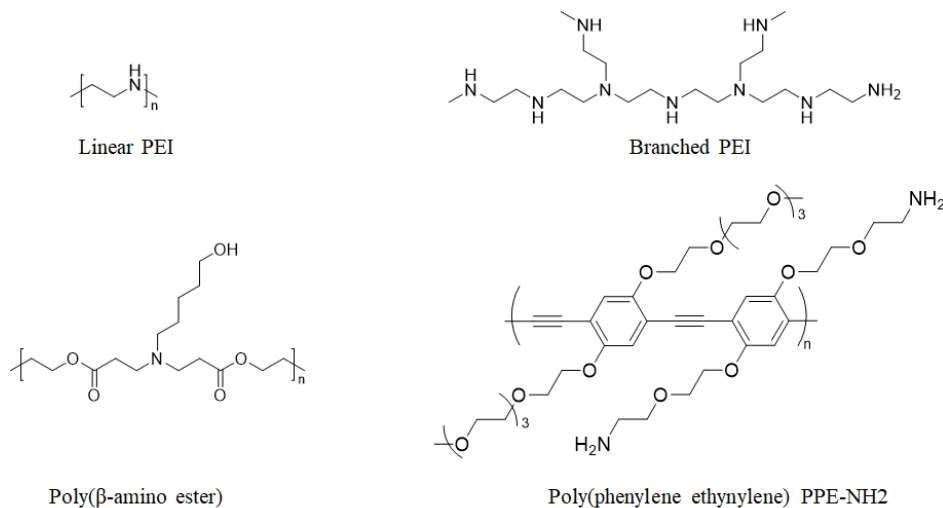


Figure 4. Examples of cationic polymers

Cationic polymers (Figure 4) are an attractive choice for non-viral nucleic acid vectors due to their repeating unit architecture, which grants a large concentration of positive charges per molecule, allowing for increased complexation efficiency while forming polyplexes with the genetic material⁷⁶. These polyplexes have shown the ability to protect the nucleic acids from degradation and allow their successful delivery into the cell cytoplasm⁷⁷. Of these synthetic compounds, the conjugated polymers⁷⁸ and the carbamoylated guanidine modified ROMP polymers⁷⁹ synthesized by Dr. Moon's research group at FIU are successful examples. Another example is the PEI, which has become the golden standard of non-viral vectors due to its high transfection capability but suffers the downside of being very toxic and non-biodegradable.

Chitosan has also been utilized as a cationic polymeric vector⁸⁰. At acidic pH values, the primary amines in the chitosan backbone become positively charged, enabling chitosan to bind to negatively charged DNA/siRNA via electrostatic interactions, leading to the spontaneous formation of nano-sized complexes (polyplexes)⁸¹. Given the substantial number of positive amines present in the chitosan due to its polymeric nature, there will be a high complexation efficiency, which allows for a high gene payload⁸². Furthermore, chitosan is slightly charged at neutral or basic pH but still able to bind to the nucleic acids through secondary (non-electrostatic) interactions, such as hydrogen bonding and hydrophobic interactions⁸³.

1.4 The carbamoylated guanidine moiety

In 2019, Dr. Moon's research group at FIU synthesized a carbamoylated guanidine functionalized CP as a non-viral vector⁷⁹. As a result of this work, it was shown that adding carbamoylated guanidine moieties (Figure 5) to polymers confers a decisive advantage in

terms of transfection capabilities, gene payload, and biocompatibility over PEG and PEI derivatives, especially when transfecting rigid nucleic acids as siRNA. This work aimed explicitly at the transfection of human airway epithelium cells, representing a more significant challenge due to a dense layer of negatively charged mucus⁷⁹.

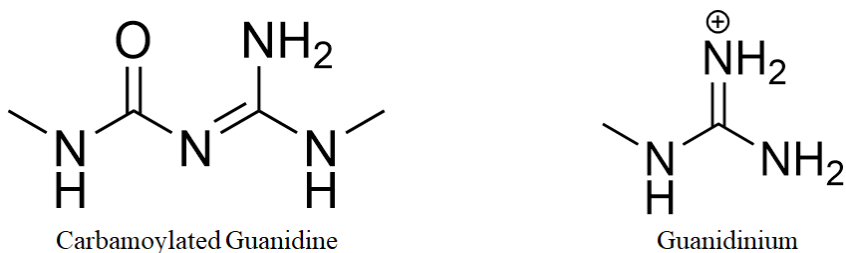


Figure 5. The carbamoylated guanidine and guanidinium groups

The carbamoylated guanidine moiety has a positive delocalized shielded charge on the guanidine substructure, which can establish bidentate interactions with negatively charged compounds, as shown in Figure 6. The presence of the urea substructure extends hydrogen bonding, which translates into stronger interactions with anions (an attractive characteristic for gene vector applications). It also offers the possibility of modification at the positive charge, which can improve biophysical properties.

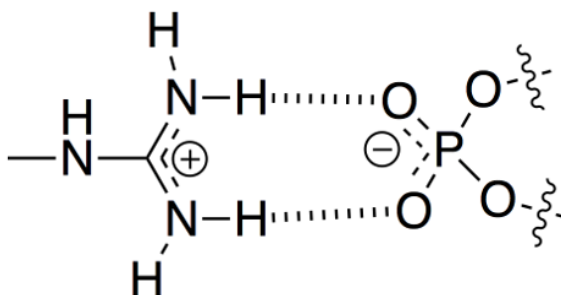


Figure 6. Guanidine bidentate interaction with phosphate

1.5 Research Purpose

Considering the above, this research intends to study the feasibility of obtaining a phenyl carbamoylated guanidine chitosan derivative. It is hypothesized that this modified chitosan will be soluble in DMSO, which will expand its applicability, especially in biological applications, and increase the range of further chemical modifications. This research plan involves synthesizing this target molecule starting from the unmodified chitosan.

II. EXPERIMENTAL METHODS

2.1 Materials and Instrumentation

2.1.1 Materials.

Chitosan (CS), purified powder (MW ~ 15000, 85% deacetylated), was purchased from Polysciences, Inc. Potassium hydroxide (KOH), Triethylamine (TEA), hexane, ethyl acetate (EA), dimethylformamide (DMF), dimethyl sulfoxide (DMSO), acetone and tetrahydrofuran (THF) were acquired from Fischer Scientific. Mercuric chloride (HgCl_2), dichloromethane (DCM), methanesulfonic acid (MSA), and phenyl isocyanate (PhNCO) were purchased from Millipore Sigma. S-methylisothiurea hemisulfate was purchased from Tokyo Chemical Industry (TCI). Sodium hydrogen bicarbonate (NaHCO_3) was purchased from Alfa Aesar. Di(tert-butyl) dicarbonate (BOC_2O) was purchased from Chem Impex International Inc. Deuterated dimethyl sulfoxide (DMSO- d_6), deuterated acetic acid, deuterium oxide (D_2O), and deuterated chloroform (CDCl_3) were acquired from Cambridge Isotope Laboratories.

The DMF and the DMSO were dried over micro sieves acquired from Fischer Chemicals in the laboratory before use.

2.1.2 Nuclear magnetic resonance (NMR).

^1H NMR spectroscopy studies were performed using a Bruker 400 MHz NMR spectrometer for data collection and Topspin software for data analysis. All ^1H NMR studies were conducted at 25° C in CDCl_3 , DMSO- d_6 , or D_2O / Acetic acid- d_4 1% v/v. CDCl_3 was used for the mono-BOC S-methyl isothiurea and the BOC S-methyl phenyl carbamoylated guanidine, while the DMSO- d_6 was utilized for the phenyl carbamoylated

guanidine functionalized chitosan. D₂O / Acetic acid-d₄ 1% v/v was used as a solvent for acquiring the spectra of the unmodified chitosan.

All samples prepared for ¹H NMR analysis contained 10 mg of product and 700 μL of solvent. The solution was then placed into a Branson 2510 ultrasonic bath for 20 min to ensure that the samples were completely dissolved in the solvent and then analyzed. Chemical shifts are expressed in parts per million (δ) using a residual solvent proton as the internal standard.

2.2 Solubilization of chitosan in acetic acid 1% v/v solution

First, 2 ml of acetic acid (AcOH) glacial were pipetted into a 100 mL volumetric flask, followed by the addition of water until the graduation mark. The solution was then transferred to a 250 mL round bottom flask (RBF) and cooled down to 4⁰C in a laboratory fridge for one h. 2 g of chitosan were weighted and slowly added to the cold solution with gently stirring. The mixture was cooled to 4⁰C in the laboratory fridge for 1 h. The cold mixture was then vigorously stirred, and the chitosan solubilized utterly, causing the solution to become denser, with a final concentration of 20 mg/ mL of chitosan. The final solution was stored in the fridge at 4⁰C.

The solution was pipetted into the reaction vial for subsequent uses until the desired amount of chitosan was achieved (e.g., for 100 mg of chitosan, 5 mL of the solution were added to the vial). This allowed faster reaction setup times by eliminating the need to solubilize the chitosan every time a reaction was undertaken.

2.3 Synthesis of mono-BOC protected S-methyl isothiourea

The procedure was based on the protocol described previously by Liang *et al.*⁸⁴. A mixture of 60 mL of H₂O and 60 mL of THF was prepared in a 200 mL graduated beaker and then added to a 250 mL RBF. After this, 12 g of S-methylisothiourea hemisulfate and 7.23 g of NaHCO₃ were dissolved in the mixture, followed by the addition of 14 g of di(tert-butyl) dicarbonate while slowly stirring. A rubber septum was used to cover the RBF mouth, with a needle inserted to avoid pressure buildup. The reaction was stirred at room temperature for 24 hours.

After 24 hours, the reaction was stopped. The mixture was concentrated under reduced pressure using a Buchi R-114 rotary evaporator. The residue was then partitioned in 50 mL of Ethyl Acetate three times. The three organic fractions were collected, mixed, washed with brine twice, dried over magnesium sulfate (MgSO₄), and filtered. The solvent was evaporated under reduced pressure using the rotary evaporator, leaving a white residue. The solid was then collected and dissolved in 25 mL of hexane, stirring while heating with a heat gun. The solution was cooled down and kept at 0 °C overnight. The solvent was decanted and filtered, and the remaining solid was vacuum dried overnight to afford 9.28 g of product as white crystals.

¹H-NMR (CDCl₃, 400 MHz) δ 1.51 (9H, s), δ 2.46 (3H, s), δ 7.62 (2H, s).

2.4 Synthesis of mono-BOC protected S-methyl phenyl carbamoylated guanidine

A reaction path similar to the one described by Hsu *et al.*⁸⁵ for the preparation of amidinoureas was followed for preparing the S-methyl phenyl carbamoylated guanidine (SMPCG). A 40 mL glass vial was flame dried and then purged with N₂, followed by the addition of 9.28 of dried recrystallized mono-BOC protected S-methyl isothiourea. 6 mL

of anhydrous DCM was then added dropwise while slowly stirring to dissolve the mono-BOC protected S-methyl isothiourea. Lastly, 8.72 g (8 mL) of phenyl isocyanate were added dropwise while stirring, and the reaction was then kept at 60 °C for 48 h.

After 48 h, the reaction was stopped. The solvent was evaporated under reduced pressure using a Buchi R-114 rotary evaporator, leaving the crude mix as a white residue. The solid was collected and vacuum dried overnight to afford 11.66 g of crude. The crude mixture was purified using a Yamazen Parallel Frac FR-260 flash chromatography device. The fractions of the crude mix were first dissolved in DCM and introduced in a Yamazen silica gel injection column (M size, 20x75 mm) and then separated using a mixture of hexane/ethyl acetate 80:20 ratio on a Yamazen normal phase silica gel column (L size, 3.0x16.5 cm, particle size 30 μ m). The fractions of interest were collected based on the peaks and time of elution. The solvent was evaporated under reduced pressure using the rotary evaporator, leaving a white residue. This solid was collected and dried overnight to afford 6.1 g of pure product.

$^1\text{H-NMR}$ (CDCl_3 , 400 MHz) δ 1.50 (9H, s), δ 2.39 (3H, s), δ 7.10 (1H, t, $^3J_{\text{H-H}} = 7.4$ Hz), δ 7.33 (2H, t, $^3J_{\text{H-H}} = 7.9$ Hz), δ 7.50 (2H, d, $^3J_{\text{H-H}} = 7.6$ Hz), δ 12.19 (1H, s).

2.5 Synthesis of deprotected S-methyl phenyl carbamoylated guanidine

The removal of the BOC group was carried out using a modification of the procedure described by Greene⁸⁶. Initially, 2 g of mono-BOC protected SMPCG were dissolved in 6 ml of DCM, followed by the addition of 3.68 g (2.5 mL) of trifluoroacetic acid (TFA) dropwise while stirring. The solution was then kept at 35⁰C for 14 h. The solution was then concentrated under vacuum, followed by the addition of ethyl ether in excess. The mix was stirred for 20 min. Once the precipitation was observed, the vial was centrifugated at 4000

rpm for 6 min. The solvent was removed by decantation, and the white residue was vacuum dried overnight to afford the product as a white solid.

$^1\text{H-NMR}$ (CDCl_3 , 400 MHz) δ 2.56 (3H, s), δ 7.04 (1H, t, $^3\text{J}_{\text{H-H}} = 7.4$ Hz), δ 7.30 (2H, t, $^3\text{J}_{\text{H-H}} = 7.9$ Hz), δ 7.55 (2H, d, $^3\text{J}_{\text{H-H}} = 7.6$ Hz), δ 9.82 (1H, s).

2.6 Synthesis of phenyl carbamoylated guanidine functionalized chitosan

Starting from the procedure described by Ch. Yuan and R. Williams⁸⁷ for the synthesis of amidinoureas, the following method was used to prepare the phenyl carbamoylated guanidine functionalized chitosan (PCGCs). Initially, 1.92 g of SMPCG and 0.84 g of HgCl_2 (activator) were added to a 40 mL glass vial containing 2 mL of dry DMF and sonicated for 10 min to achieve complete solubilization. After this, 0.10 g of unmodified chitosan was added to the solution, followed by 10 min of sonication. Lastly, 0.31 g (0.44 mL) of TEA were added dropwise. The reaction was kept at 80°C for 72 h while stirring. After 72 h, the vial was removed from the hotplate, and the reaction mixture was filtered twice. The resulting homogeneous solution was added to a glass vial containing 4 mL of acetone and then centrifuged at 2500 rpm for 3 min. At the end of the centrifugation cycle, the solvent was removed by decantation, and 2 mL of dry DMSO was added to the solid residue. The mix was sonicated for 20 min to ensure complete dissolution and then filtered. The resulting homogeneous brown solution was added to a glass vial containing 2.5 mL of acetone. This vial was then centrifuged at 2500 rpm for 3 min. At the end of the centrifugation, the solvent was removed by decantation, and 1 mL of dry DMSO was added to the solid residue. The mix was sonicated for 10 min to ensure complete dissolution and then filtered. The resulting homogeneous solution was added to a glass vial containing 2 mL of acetone. After a third and final centrifugation cycle at 2500 rpm for 3 min, the solvent

was removed by decantation. The solid residue was vacuum dried overnight to afford 60 mg of PCGCs.

PCGCs:

$^1\text{H-NMR}$ (DMSO- d_6 , 400 MHz) δ 1.98 (1H, s), δ 3.10 (4H, d, $^3J_{\text{H-H}} = 6.4$ Hz), δ 3.44 (2H, m), δ 4.35 (1H, s), δ 6.96 (1H, t, $^3J_{\text{H-H}} = 7.3$ Hz), δ 7.27 (2H, t, $^3J_{\text{H-H}} = 7.9$ Hz), δ 7.44 (2H, d, $^3J_{\text{H-H}} = 7.6$ Hz), δ 8.88 (1H, s).

2.7 BOC deprotection of phenyl carbamoylated guanidine functionalized chitosan

For the deprotection of the phenyl carbamoylated guanidine functionalized chitosan (PCGCs), 0.02 g of BOC protected PCGCs were dispersed in 1 ml of DMF, followed by the addition of 0.027 g (1.5 mL) of HCl 0.5 M dropwise while stirring. The reaction was kept at 40 $^{\circ}$ C for 24 h while stirring.

After 24 h, the vial was removed from the plate, and the reaction mixture was filtered twice. The mixture was added to a glass vial containing 3 mL of acetone and then centrifuged at 2500 rpm for 3 min. At the end of the centrifugation cycle, the solvent was removed by decantation, and 1 mL of dry DMSO was added to the solid residue. The mixture was sonicated for 10 min, filtered, and added to a glass vial containing 2.5 mL of acetone. This vial was then centrifuged at 2500 rpm for 3 min. At the end of the centrifugation, the solvent was removed by decantation, and 1 mL of dry DMSO was added to the solid residue. The mixture was sonicated for 10 min, filtered, and added to a glass vial containing 2 mL of acetone. After a third and final centrifugation cycle at 2500 rpm for 3 min, the solvent was removed by decantation. The solid residue was vacuum dried overnight to afford 13 mg of dry solid.

NMR analysis did not confirm the success of this reaction.

III. RESULTS AND DISCUSSION

3.1 Synthesis strategies

The strategy for synthesizing the carbamoylated guanidine chitosan derivative involved exploiting the nucleophilicity of the amine groups to attack the SMPCG (figure 7), using HgCl_2 as an activator and TEA as the base to form the desired product. This reaction would be aided by the excellent leaving group character of the S-methyl. It was hypothesized that conversion via a single reaction would lead to a higher yield when compared to the alternative path of successive reactions to modify the amine moiety using guanidinylation first, followed by BOC protection and reaction with a primary aromatic amine, like aniline.

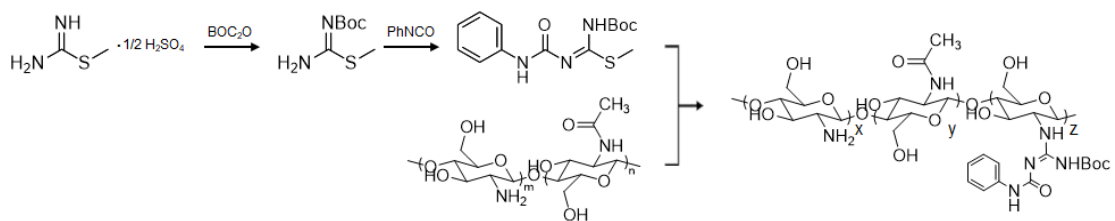


Figure 7. Scheme for the synthesis of the PCGCs.

3.2 Solving the chitosan solubility problem

It was foreseen that the lack of solubility of the chitosan in organic solvents would be an obstacle to this synthesis. Therefore, this issue had to be solved first to ensure a good conversion percentage of the chitosan amines into the desired carbamoylated guanidine.

To remediate this problem, two routes were tried first:

- 1- Dissolve the chitosan in an acetic acid 1% v/v in water solution, and then diluting the chitosan solution in DMSO or DMF.
- 2- Synthesis of a chitosan mesylate salt soluble in DMSO.

A chitosan solution in acetic acid was prepared and then diluted in DMSO or DMF for the first route. Before the reaction, the pH was stabilized to 8-9 by adding KOH to ensure that the chitosan amines were deprotonated. Nevertheless, none of the reactions tried using this method gave the desired product, and thus, it was decided to abandon this path. It was hypothesized that the loss of solubility of the chitosan under basic conditions might have contributed to the failure of these reactions.

The formation of DMSO soluble chitosan salts had been previously described by Sashiwa *et al.*²⁶. The mesylate salt is obtained by reacting the chitosan with MSA using water as a solvent (figure 8).

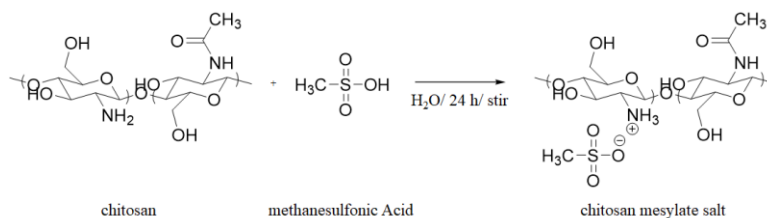


Figure 8. Chitosan mesylate salt formation

Interestingly, freeze-drying is essential in achieving solubility in DMSO²⁶. Therefore, it was decided to utilize this method to dry the chitosan salt before attempting dissolution in DMSO. Accordingly, the mesylate route provided a DMSO soluble chitosan salt upon

sonication treatment for 20 min. Nevertheless, using the chitosan mesylate salt did not lead to the expected product.

One cause for the failure of these reactions is that the formation of the mesylate salt relies on the ionic interactions of the protonated amines in the chitosan chain with the mesylate anions. During the reaction of the chitosan with the SMPCG under basic conditions, these ionic interactions can undergo two paths, both of which negatively impact the possibility of reaction success:

1- A portion of the amine groups remain protonated during the reaction, thus ensuring the continuation of these ionic interactions and the solubility in DMSO but inhibiting the nucleophilic character needed to react with the carbodiimide intermediate (see section 3.4 for details in the proposed reaction mechanism).

2- The addition of the base leads to deprotonation of the vast majority of the amine groups of the chitosan, in which case the nucleophilicity is enhanced at the expense of a loss of solubility in DMSO, which leads to a decrease in the overall interactions between the chitosan and the SMPCG.

Considering the above, it was decided to attempt the reaction by simply dispersing the chitosan in DMF, in conjunction with the 1:10 ratio of SMPCG and activator. The use of sonication allowed for the generation of homogeneously dispersed mixtures. The base was added last to avoid premature aggregation of the reagents in the vial before the reaction started. Using this method, the target molecule was finally achieved.

3.3 Synthesis of the S-methyl phenyl carbamoylated guanidine

The synthesis of the SMPCG was designed considering the methods described previously⁸⁸⁻⁹⁰. The use of the methylisothiurea as the starting point was chosen based on reagent price and availability, as well as the fact that the S-methyl is an excellent leaving group, which contributes to the successful completion of the first step of the proposed reaction mechanism (see section 3.4 below for details) for obtaining the target compound.

For the production of the S-methyl phenyl carbamoylated guanidine in the desired configuration, the phenyl isocyanate can only be allowed to react with the primary amine of the S-methylisothiurea. Subsequently, to avoid the possibility of side reactions, the secondary amine of the starting reagent needs to be protected.

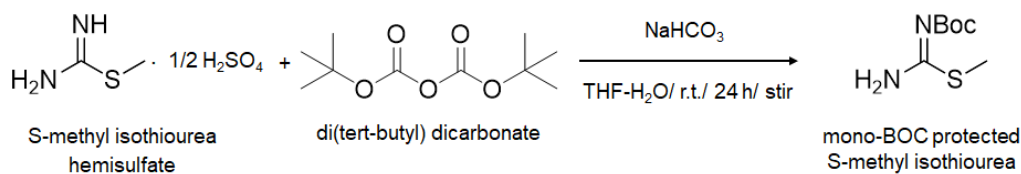


Figure 9. BOC protection of the S-methyl isothiurea.

The BOC group is traditionally used in the protection of amines⁸⁶. In this case, the BOC group also has the added benefit of being an electron-withdrawing moiety, which helps to ensure electron deficit at the carbodiimide carbon (see section 3.4 below for details). Therefore, it was decided to employ BOC protection of the secondary amine.

Mild conditions were used for this reaction to ensure the prevalence of the mono BOC-protected product. As described by Hsu *et al.*⁸⁵, the use of NaHCO_3 , a weak base, in

conjunction with diluted concentrations of BOC₂O in THF-H₂O excess (Figure 9), leads to the production of the mono-BOC protected product with a 99% yield. Purification was possible via partition in EA/ H₂O, followed by recrystallization in hexane.

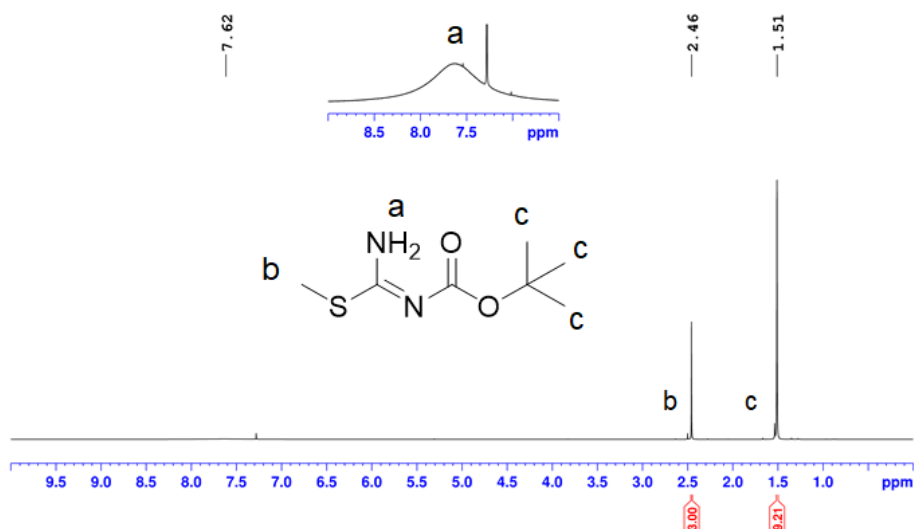


Figure 10. ¹H NMR (400 MHz, CDCl₃) spectrum of mono-BOC protected S-methylisothiourea.

Once the mono BOC-protected product was purified, the second step involved the synthesis of the SMPCG via the reaction with the PhNCO (Figure 11). The use of DCM ensured an easy solvent removal by heating under vacuum. The crude mixture was purified by chromatography, using a mix of hexane and EA in an 80:20 ratio.

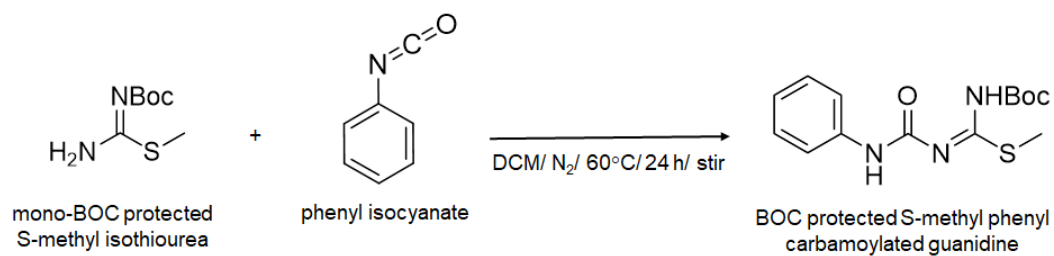


Figure 11. Synthesis of the BOC protected S-methyl phenyl carbamoylated guanidine.

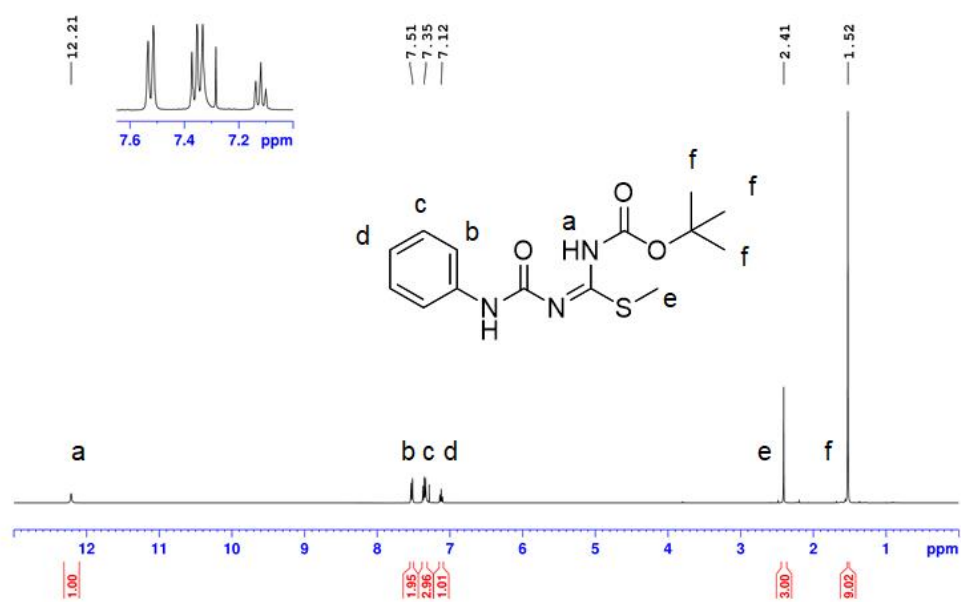


Figure 12. ¹H NMR (400 MHz, CDCl₃) spectrum of BOC protected S-methyl phenyl carbamoylated guanidine.

3.4 Reaction of the chitosan with the mono BOC S-methyl phenyl carbamoylated guanidine

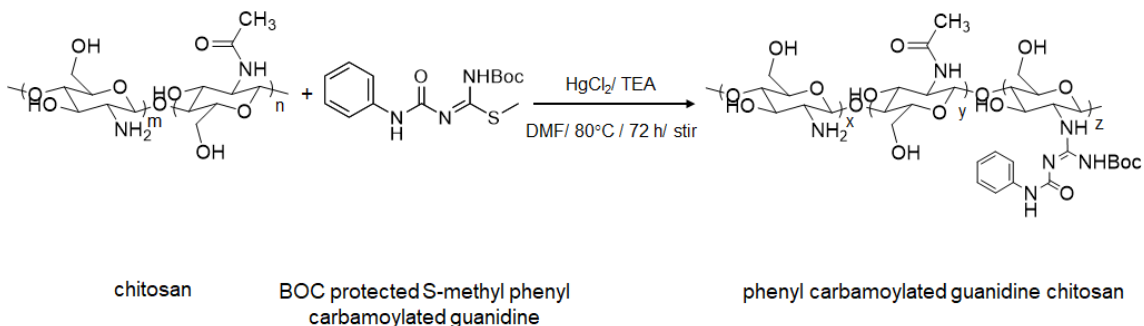


Figure 13. Reaction of the chitosan with the mono BOC S-methyl phenyl carbamoylated guanidine.

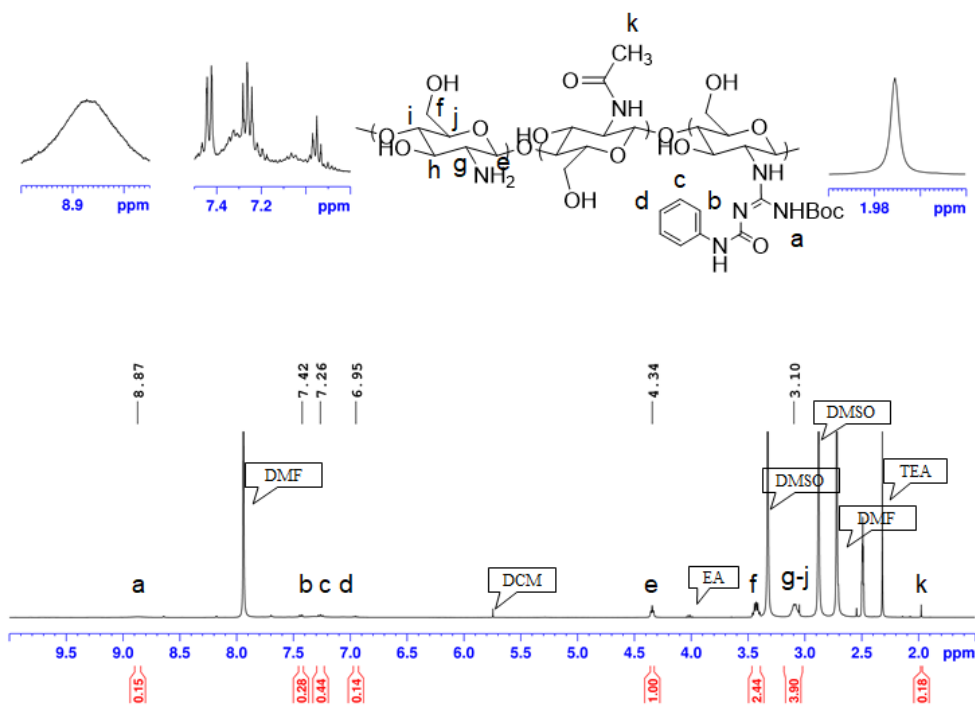


Figure 14. ^1H NMR (400 MHz, DMSO- d_6) spectrum of phenyl carbamoylated guanidine chitosan.

As noted by Kim *et al.*⁹⁰, this reaction (Figure 13) undergoes the following route (Figure 15):

1- Elimination of the S-methyl promoted by HgCl₂ and subsequent complexation of the anionic sulfur with the mercury.

2- Formation of a carbodiimide intermediate with an electron-deficient center.

3- Attack of the primary amine group of the chitosan on the electron-deficient center at the carbodiimide carbon.

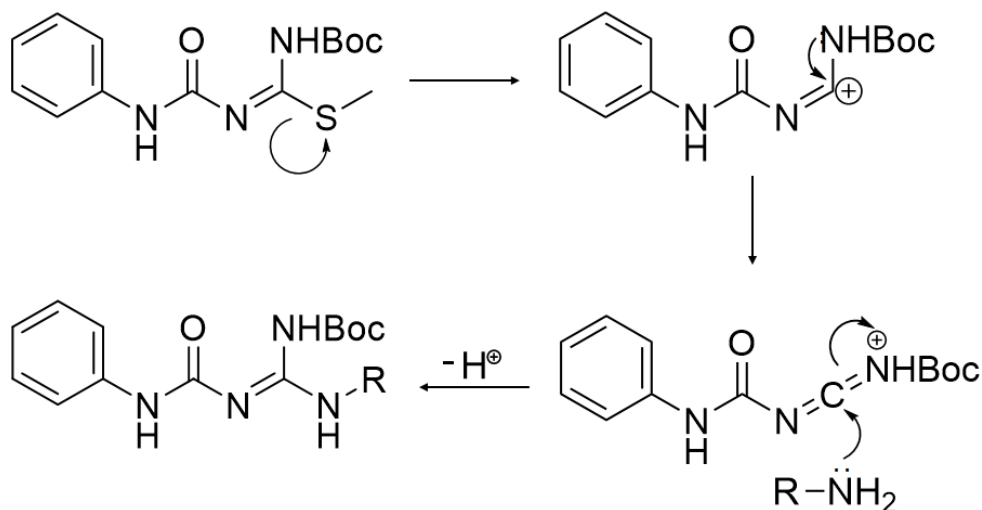


Figure 15. Proposed reaction mechanism for the chitosan modification.

This mechanism is supported by spectroscopic evidence for the formation of the carbodiimide intermediate⁹⁰ the high affinity of the Hg²⁺ to form complexes with anionic sulfur compounds⁹¹.

It has been described that the presence of the BOC group facilitates the occurrence of the third step of this reaction⁸⁸. Owing to its electron-withdrawing nature, the BOC group

increases the electron deficiency at the carbodiimide carbon center, which aids in the nucleophilic addition of the primary amine moiety.

Subsequently, the BOC group serves two roles in this reaction:

1- Ensure that only the primary amine on the S-methylisothiurea reacts with the phenyl isocyanate to yield the SMPCG.

2- Facilitate the attack of the primary amine of the chitosan with the carbodiimide intermediate to produce the target molecule.

Additionally, using a base guarantee that the amine groups in the chitosan remain deprotonated during the reaction, enhancing its nucleophilicity and facilitating the attack on the carbodiimide intermediate.

During this research, several reactions were set up with and without using HgCl_2 . None of the reactions in which the initiator was omitted were successful, which confirms the critical role of this reagent in the first step of the reaction, both as an activator and in avoiding the regeneration of the SMPCG via the reaction of the S-methyl anion with the carbodiimide.

In a separate set of reactions, the BOC group was removed in the SMPCG, and the deprotected compound was used in a set of reactions, none of which yielded the desired product. This reaffirms the theory that the presence of an electron-withdrawing group facilitates the attack on the carbodiimide intermediate by increasing the electron deficiency of its carbon center.

Regarding the solubility of the modified chitosan, it is soluble in DMSO as originally hypothesized and partially soluble in DMF. This product is insoluble in water, acetone, ethanol, and CDCl_3 .

3.5 NMR analysis of the product and determination of the degree of substitution

As shown in Figure 16 and Tables 2 and 3), the NMR results of the PCGCs were compared against the spectra of unmodified chitosan (see Appendix for full ^1H NMR spectrum and peaks interpretation of the unmodified chitosan).

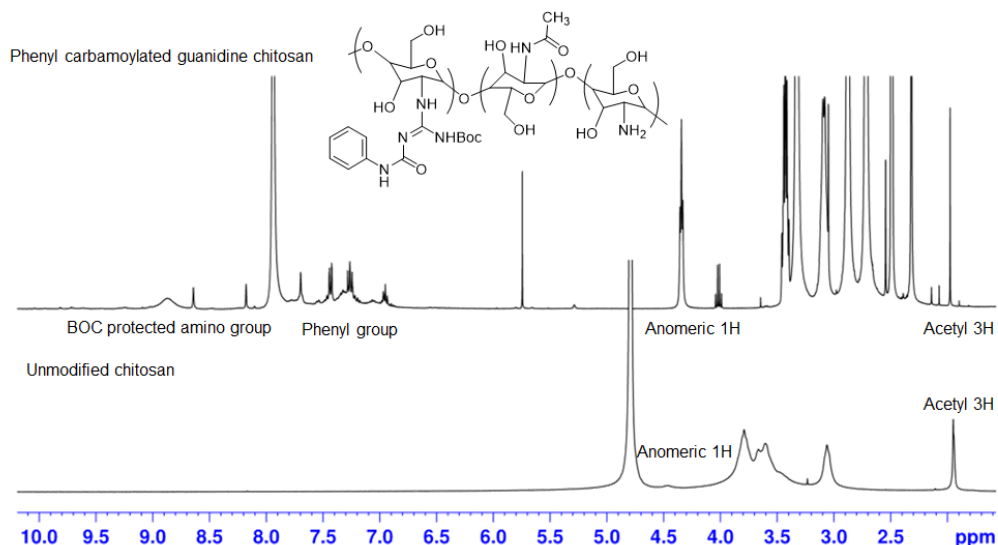


Figure 16. ^1H NMR spectra comparison of unmodified chitosan (400 MHz, D_2O / Acetic acid- d_4 1%) and phenyl carbamoylated guanidine chitosan (400 MHz, DMSO-d_6).

The degree of substitution indicates how many primary amine groups of the unmodified chitosan reacted with the BOC SMPCG to form the PCGCs. As such, it is an essential indicator of the extension of the reaction.

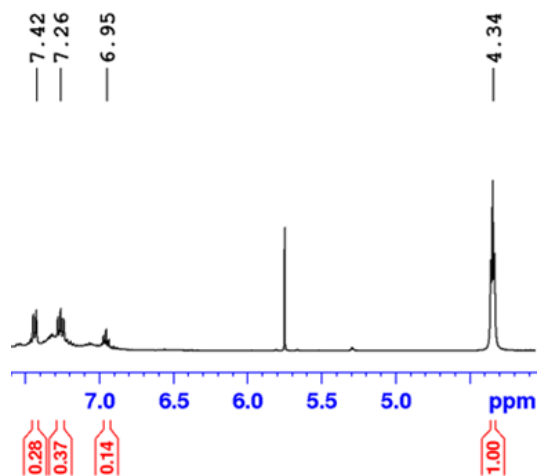


Figure 17. Illustration of the ^1H NMR determination of the degree of substitution of the PCGCs.

For the PCGCs, the percentage of substitution was established by establishing the integration ratio of the anomeric hydrogen in the chitosan chain and the single phenyl hydrogen in the phenyl carbamoylated guanidine substituent (Figure 17). The single anomeric hydrogen is present in all the chitosan units, so it is a good indicator of the size of the polymer chain. Likewise, the phenylic hydrogen is present in all the phenyl carbamoylated moieties, so it is a reliable pointer for the presence of said substituent.

The peak area was 1.00 for the anomeric hydrogen and 0.14 for the phenylic hydrogen. The integration ratio demonstrates a substitution of 14%, which means that 14% of the amines initially present in the unmodified chitosan chain have reacted with the BOC SMPCG.

3.6 BOC deprotection of the phenyl carbamoylated guanidine functionalized chitosan

For the deprotection of the PCGCs, the usual route employing TFA and DCM, as described by Greene⁸⁶, was denied due to the lack of solubility of the product in DCM. The use of

DMSO as solvent was not considered due to the possibility of side reactions, so an alternative path was used, with HCl replacing the TFA as the acid of choice, and employing DMF as solvent to ensure at least partial solubility of the BOC PCGCs (Figure 18).

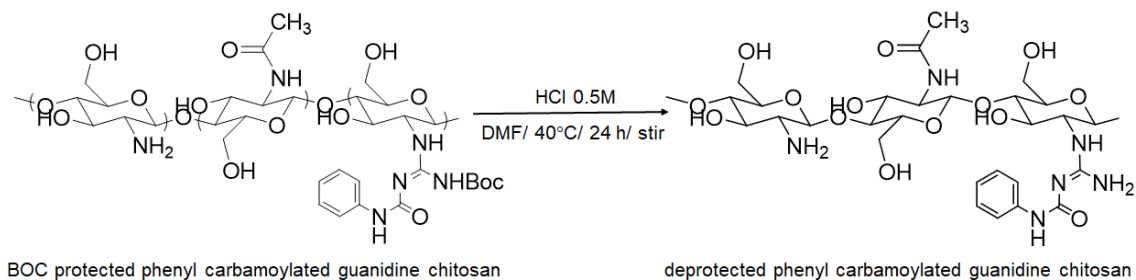


Figure 18. Deprotection of the PCGCs.

This reaction was tried a number of times, without success. Even though the reaction included heating the mixture to 40⁰C, the NMR did not confirm the obtention of the deprotected PCGCs in any of the iterations.

It is hypothesized that a factor contributed to the lack of success of this reaction was the molarity of the HCl. The concentration of the acid mentioned in literature⁸⁶ is 3M, but the acid available at the moment of the reaction had a concentration of 0.5M. To remediate this, an excess of acid was used in combination with heat, but ultimately it did not lead to the desired results.

IV. CONCLUSION

During this research, reaction conditions for synthesizing PCGCs have been established. These conditions include circumventing the lack of solubility of chitosan in organic solvents by using sonication to achieve a high degree of dispersion in the reagents mixture.

It has also been found that the reaction does not occur in the absence of HgCl_2 or BOC protection of the SMPCG. These findings are consistent with the proposed mechanism for the production of PCGCs, which include the HgCl_2 as an activator and an agent avoiding the regeneration of the SMPCG via the reaction of the S-methyl anion with the carbodiimide. The mechanism also includes the BOC group in the role of increasing the electron deficiency at the carbodiimide carbon center, which facilitates the attack of the primary amines of the chitosan.

The PCGCs product was characterized by NMR spectroscopy, and its spectrum was compared with the unmodified chitosan and the SMPCG starting product spectra. The degree of substitution was established to be 14 % using analysis of the NMR spectra.

In virtue of its solubility in DMSO and the presence of the phenyl carbamoylated guanidine moiety, the chitosan derivative obtained during this research will be used in future experiments in protein delivery, and antimicrobial activity, and siRNA transfection. Future research is also planned to establish the conditions to obtain PCGCs with different degrees of substitution to evaluate the optimal value for transfection, protein delivery, and antimicrobial activity.

REFERENCES

- (1) Abdan, K. B.; Yong, S. C.; Chiang, E. C. W.; Talib, R. A.; Hui, T. C.; Hao, L. C. Barrier Properties, Antimicrobial and Antifungal Activities of Chitin and Chitosan-Based IPNs, Gels, Blends, Composites, and Nanocomposites. In *Handbook of Chitin and Chitosan: Volume 2: Composites and Nanocomposites from Chitin and Chitosan, Manufacturing and Characterisations*; Elsevier, 2020; pp 175–227. <https://doi.org/10.1016/B978-0-12-817968-0.00006-8>.
- (2) Kamilya, D.; Khan, Md. I. R. Chitin and Chitosan as Promising Immunostimulant for Aquaculture. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 761–771. <https://doi.org/10.1016/b978-0-12-817966-6.00024-8>.
- (3) Hoseini, M. H. M.; Sadeghi, S.; Azizi, M.; Pouriran, R. Immunomodulatory Activities of Chitin and Chitosan Microparticles. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 609–639. <https://doi.org/10.1016/b978-0-12-817966-6.00019-4>.
- (4) Akpan, E. I.; Gbenedor, O. P.; Adeosun, S. O.; Cletus, O. Chitin and Chitosan Composites for Bone Tissue Regeneration. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 499–553. <https://doi.org/10.1016/b978-0-12-817966-6.00016-9>.
- (5) Kurita, K.; Yoshino, H.; Yokota, K.; Ando, M.; Inoue, S.; Ishii, S.; Nishimura, S. I. Preparation of Tosylchitins as Precursors for Facile Chemical Modifications of Chitin. *Macromolecules* **1992**, *25* (14), 3786–3790. <https://doi.org/10.1021/ma00040a026>.
- (6) Raafat, D.; Sahl, H. G. Chitosan and Its Antimicrobial Potential - A Critical Literature Survey. *Microbial Biotechnology*. March 2009, pp 186–201. <https://doi.org/10.1111/j.1751-7915.2008.00080.x>.
- (7) Farinha, I.; Freitas, F. Chemically Modified Chitin, Chitosan, and Chitinous Polymers as Biomaterials. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 43–69. <https://doi.org/10.1016/b978-0-12-817966-6.00002-9>.
- (8) Hossain, M. R.; Mallik, A. K.; Rahman, M. M. Fundamentals of Chitosan for Biomedical Applications. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 199–230. <https://doi.org/10.1016/b978-0-12-817966-6.00007-8>.
- (9) Younes, I.; Ghorbel-Bellaaj, O.; Nasri, R.; Chaabouni, M.; Rinaudo, M.; Nasri, M. Chitin and Chitosan Preparation from Shrimp Shells Using Optimized Enzymatic Deproteinization. *Process Biochemistry* **2012**, *47* (12), 2032–2039. <https://doi.org/10.1016/j.procbio.2012.07.017>.

- (10) Taylor, M.; Moreira, R. *PREPARATION AND CHARACTERIZATION OF CHITOSAN-ALGINATE NANOPARTICLES FOR TRANS-CINNAMALDEHYDE ENTRAPMENT*; 2014.
- (11) Yi, H.; Wu, L. Q.; Bentley, W. E.; Ghodssi, R.; Rubloff, G. W.; Culver, J. N.; Payne, G. F. Biofabrication with Chitosan. *Biomacromolecules*. November 2005, pp 2881–2894. <https://doi.org/10.1021/bm050410l>.
- (12) Richardson, S. C. W.; Kolbe, H. V. J.; Duncan, R. Potential of Low Molecular Mass Chitosan as a DNA Delivery System: Biocompatibility, Body Distribution and Ability to Complex and Protect DNA. *International Journal of Pharmaceutics* **1999**, *178* (2), 231–243. [https://doi.org/10.1016/S0378-5173\(98\)00378-0](https://doi.org/10.1016/S0378-5173(98)00378-0).
- (13) Mohammed, M. A.; Syeda, J. T. M.; Wasan, K. M.; Wasan, E. K. An Overview of Chitosan Nanoparticles and Its Application in Non-Parenteral Drug Delivery. *Pharmaceutics* **2017**, *9* (4). <https://doi.org/10.3390/PHARMACEUTICS9040053>.
- (14) Ding, S.; Wang, Y.; Li, J.; Chen, S. Progress and Prospects in Chitosan Derivatives: Modification Strategies and Medical Applications. *Journal of Materials Science and Technology* **2020**, No. xxxx. <https://doi.org/10.1016/j.jmst.2020.12.008>.
- (15) Salama, A.; Hesemann, P. Synthesis of N-Guanidinium-Chitosan/Silica Hybrid Composites: Efficient Adsorbents for Anionic Pollutants. *Journal of Polymers and the Environment* **2018**, *26* (5), 1986–1997. <https://doi.org/10.1007/s10924-017-1093-3>.
- (16) Osvaldová, P.; Másson, M.; Eva Benediktsdóttir, B. *Fluorescence Labelling of Chitosan and Its Cationic Derivatives for Biological Studies*; 2017.
- (17) Yuan, Y.; Chesnutt, B. M.; Haggard, W. O.; Bumgardner, J. D. Deacetylation of Chitosan: Material Characterization and in Vitro Evaluation via Albumin Adsorption and Pre-Osteoblastic Cell Cultures. *Materials* **2011**, *4* (8), 1399–1416. <https://doi.org/10.3390/ma4081399>.
- (18) Rinaudo, M. Chitin and Chitosan: Properties and Applications. *Progress in Polymer Science (Oxford)*. July 2006, pp 603–632. <https://doi.org/10.1016/j.progpolymsci.2006.06.001>.
- (19) Kumari, S.; Kumar Annamareddy, S. H.; Abanti, S.; Kumar Rath, P. Physicochemical Properties and Characterization of Chitosan Synthesized from Fish Scales, Crab and Shrimp Shells. *International Journal of Biological Macromolecules* **2017**, *104*, 1697–1705. <https://doi.org/10.1016/j.ijbiomac.2017.04.119>.

- (20) Sahariah, P.; Óskarsson, B. M.; Hjálmarsson, M.; Másson, M. Synthesis of Guanidinylated Chitosan with the Aid of Multiple Protecting Groups and Investigation of Antibacterial Activity. *Carbohydrate Polymers* **2015**, *127*, 407–417. <https://doi.org/10.1016/j.carbpol.2015.03.061>.
- (21) Wang, X.; Yao, J.; Zhou, J. P.; Lu, Y.; Wang, W. Synthesis and Evaluation of Chitosan-Graft-Polyethylenimine as a Gene Vector. *Pharmazie* **2010**, *65* (8), 572–579. <https://doi.org/10.1691/ph.2010.9422>.
- (22) Edson, J. A.; Ingato, D.; Wu, S.; Lee, B.; Kwon, Y. J. Aqueous-Soluble, Acid-Transforming Chitosan for Efficient and Stimuli-Responsive Gene Silencing. *Biomacromolecules* **2018**, *19* (5), 1508–1516. <https://doi.org/10.1021/acs.biomac.8b00170>.
- (23) Becerra, J.; Sudre, G.; Royaud, I.; Montserret, R.; Verrier, B.; Rochas, C.; Delair, T.; David, L. Tuning the Hydrophilic/Hydrophobic Balance to Control the Structure of Chitosan Films and Their Protein Release Behavior. *AAPS PharmSciTech* **2017**, *18* (4), 1070–1083. <https://doi.org/10.1208/s12249-016-0678-9>.
- (24) Sahariah, P.; Már, M.; Másson, M. Antimicrobial Chitosan and Chitosan Derivatives: A Review of the Structure–Activity Relationship. **2017**. <https://doi.org/10.1021/acs.biomac.7b01058>.
- (25) Sahariah, P.; Óskarsson, B. M.; Hjálmarsson, M.; Másson, M. Synthesis of Guanidinylated Chitosan with the Aid of Multiple Protecting Groups and Investigation of Antibacterial Activity. *Carbohydrate Polymers* **2015**, *127*, 407–417. <https://doi.org/10.1016/j.carbpol.2015.03.061>.
- (26) Sashiwa, H.; Shigemasa, Y.; Roy, R. Dissolution of Chitosan in Dimethyl Sulfoxide by Salt Formation. *Chemistry Letters* **2000**, No. 6, 596–597. <https://doi.org/10.1246/cl.2000.596>.
- (27) Xie, W.; Xu, P.; Wang, W.; Liu, Q. Preparation and Antibacterial Activity of a Water-Soluble Chitosan Derivative. *Carbohydrate Polymers* **2002**, *50* (1), 35–40. [https://doi.org/10.1016/S0144-8617\(01\)00370-8](https://doi.org/10.1016/S0144-8617(01)00370-8).
- (28) Kurita, K.; Ikeda, H.; Shimojoh, M.; Yang, J. N-Phthaloylated Chitosan as an Essential Precursor for Controlled Chemical Modifications of Chitosan: Synthesis and Evaluation. *Polymer Journal* **2007**, *39* (9), 945–952. <https://doi.org/10.1295/polymj.PJ2007032>.
- (29) Zhao, X.; Qiao, Z.-Z.; He, J.-X.; Author, C. *Preparation of Chitosan Biguanidine Hydrochloride and Application in Antimicrobial Finish of Wool Fabric*; Vol. 5.
- (30) Zhai, X.; Sun, P.; Luo, Y.; Ma, C.; Xu, J.; Liu, W. Guanidinylation: A Simple Way to Fabricate Cell Penetrating Peptide Analogue-Modified Chitosan

- Vector for Enhanced Gene Delivery. *Journal of Applied Polymer Science* **2011**, *121* (6), 3569–3578. <https://doi.org/10.1002/app.34156>.
- (31) Biswas, S.; Ahmed, T.; Islam, Md. M.; Islam, Md. S.; Rahman, M. M. Bio-medical Applications Carboxymethyl Chitosans. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 433–470. <https://doi.org/10.1016/b978-0-12-817966-6.00014-5>.
- (32) Zhang, Z.; Zhong, Z.; Zhao, Z. Preparation, Characterization and Antimicrobial Activities of Cyclic Substituted Chitosan Derivatives. *International Journal of Biological Macromolecules* **2021**, *193*, 474–480. <https://doi.org/10.1016/J.IJBIOMAC.2021.10.101>.
- (33) Vidar Rúnarsson, Ö.; Holappa, J.; Malainer, C.; Steinsson, H.; Hjálmarisdóttir, M.; Nevalainen, T.; Másson, M. Antibacterial Activity of N-Quaternary Chitosan Derivatives: Synthesis, Characterization and Structure Activity Relationship (SAR) Investigations. *European Polymer Journal* **2010**, *46* (6), 1251–1267. <https://doi.org/10.1016/J.EURPOLYMJ.2010.03.001>.
- (34) Guțoaia, A.; Schuster, L.; Margutti, S.; Laufer, S.; Schlosshauer, B.; Krastev, R.; Stoll, D.; Hartmann, H. Fine-Tuned PEGylation of Chitosan to Maintain Optimal siRNA-Nanoplex Bioactivity. *Carbohydrate Polymers* **2016**, *143*, 25–34. <https://doi.org/10.1016/j.carbpol.2016.01.010>.
- (35) Cao, J.; You, J.; Zhang, L.; Zhou, J. Homogeneous Synthesis and Characterization of Chitosan Ethers Prepared in Aqueous Alkali/Urea Solutions. *Carbohydrate Polymers* **2018**, *185*, 138–144. <https://doi.org/10.1016/J.CARBPOL.2018.01.010>.
- (36) Dragostin, O. M.; Samal, S. K.; Dash, M.; Lupascu, F.; Pânzariu, A.; Tuchiș, C.; Ghetu, N.; Danciu, M.; Dubruel, P.; Pieptu, D.; Vasile, C.; Tatia, R.; Profire, L. New Antimicrobial Chitosan Derivatives for Wound Dressing Applications. *Carbohydrate Polymers* **2016**, *141*, 28–40. <https://doi.org/10.1016/J.CARBPOL.2015.12.078>.
- (37) de Paula Pansani Oliveira, F.; Picola, I. P. D.; Shi, Q.; Barbosa, H. F. G.; de Oliveira Tiera, V. A.; Fernandes, J. C.; Tiera, M. J. Synthesis and Evaluation of Diethylethylamine-Chitosan for Gene Delivery: Composition Effects on the in Vitro Transfection Efficiency. *Nanotechnology* **2013**, *24* (5). <https://doi.org/10.1088/0957-4484/24/5/055101>.
- (38) Rúnarsson, Ö. V.; Malainer, C.; Holappa, J.; Sigurdsson, S. T.; Másson, M. Tert-Butyldimethylsilyl O-Protected Chitosan and Chitooligosaccharides: Useful Precursors for N-Modifications in Common Organic Solvents. *Carbohydrate Research* **2008**, *343* (15), 2576–2582. <https://doi.org/10.1016/j.carres.2008.08.014>.

- (39) Maleki, G.; Milani, J. M. Functional Properties of Chitin and Chitosan-Based Polymer Materials. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 177–198. <https://doi.org/10.1016/b978-0-12-817966-6.00006-6>.
- (40) Vishnu Priya, N.; Vinitha, U. G.; Meenakshi Sundaram, M. Preparation of Chitosan-Based Antimicrobial Active Food Packaging Film Incorporated with *Plectranthus Amboinicus* Essential Oil. *Biocatalysis and Agricultural Biotechnology* **2021**, *34* (January). <https://doi.org/10.1016/j.bcab.2021.102021>.
- (41) Serrano-Sevilla, I.; Artiga, Á.; Mitchell, S. G.; de Matteis, L.; de la Fuente, J. M. Natural Polysaccharides for siRNA Delivery: Nanocarriers Based on Chitosan, Hyaluronic Acid, and Their Derivatives. *Molecules* **2019**, *24* (14). <https://doi.org/10.3390/molecules24142570>.
- (42) Sahariah, P.; Másson, M. Antimicrobial Chitosan and Chitosan Derivatives: A Review of the Structure-Activity Relationship. *Biomacromolecules* **2017**, *18* (11), 3846–3868. <https://doi.org/10.1021/acs.biomac.7b01058>.
- (43) Aranaz, I.; Alcántara, A. R.; Civera, M. C.; Arias, C.; Elorza, B.; Caballero, A. H.; Acosta, N. Chitosan: An Overview of Its Properties and Applications. *Polymers (Basel)* **2021**, *13* (19). <https://doi.org/10.3390/POLYM13193256>.
- (44) Miguel, S. P.; Moreira, A. F.; Correia, I. J. Chitosan Based-Asymmetric Membranes for Wound Healing: A Review. *International Journal of Biological Macromolecules* **2019**, *127*, 460–475. <https://doi.org/10.1016/J.IJBIOMAC.2019.01.072>.
- (45) Song, W.; Gaware, V. S.; Rúnarsson, Ö. V.; Másson, M.; Mano, J. F. Functionalized Superhydrophobic Biomimetic Chitosan-Based Films. *Carbohydrate Polymers* **2010**, *81* (1), 140–144. <https://doi.org/10.1016/j.carbpol.2010.01.041>.
- (46) Azizian, S.; Hadjizadeh, A.; Niknejad, H. Chitosan-Gelatin Porous Scaffold Incorporated with Chitosan Nanoparticles for Growth Factor Delivery in Tissue Engineering. *Carbohydrate Polymers* **2018**, *202*, 315–322. <https://doi.org/10.1016/J.CARBPOL.2018.07.023>.
- (47) Shariatnia, Z.; Jalali, A. M. Chitosan-Based Hydrogels: Preparation, Properties and Applications. *International Journal of Biological Macromolecules* **2018**, *115*, 194–220. <https://doi.org/10.1016/J.IJBIOMAC.2018.04.034>.
- (48) Tao, F.; Cheng, Y.; Tao, H.; Jin, L.; Wan, Z.; Dai, F.; Xiang, W.; Deng, H. Carboxymethyl Chitosan/Sodium Alginate-Based Micron-Fibers Fabricated by Emulsion Electrospinning for Periosteal Tissue Engineering. *Materials & Design* **2020**, *194*, 108849. <https://doi.org/10.1016/J.MATDES.2020.108849>.

- (49) Hernández-Rangel, A.; Prado-Prone, G.; Hidalgo-Moyle, J. J.; Silva-Bermudez, P.; Shirai, K. Electrospun Chitosan Materials and Their Potential Use as Scaffolds for Bone and Cartilage Tissue Engineering. In *Handbook of Chitin and Chitosan*; Elsevier, 2020; pp 231–280. <https://doi.org/10.1016/b978-0-12-817966-6.00008-x>.
- (50) Victor, R. de S.; Santos, A. M. da C.; de Sousa, B. V.; Neves, G. de A.; Santana, L. N. de L.; Menezes, R. R. A Review on Chitosan's Uses as Biomaterial: Tissue Engineering, Drug Delivery Systems and Cancer Treatment. *Materials* **2020**, *13* (21), 1–71. <https://doi.org/10.3390/ma13214995>.
- (51) Kim, I. Y.; Seo, S. J.; Moon, H. S.; Yoo, M. K.; Park, I. Y.; Kim, B. C.; Cho, C. S. Chitosan and Its Derivatives for Tissue Engineering Applications. *Biotechnology Advances* **2008**, *26* (1), 1–21. <https://doi.org/10.1016/J.BIOTECHADV.2007.07.009>.
- (52) Krajewska, B. Membrane-Based Processes Performed with Use of Chitin/Chitosan Materials. *Separation and Purification Technology* **2005**, *41* (3), 305–312. <https://doi.org/10.1016/J.SEPPUR.2004.03.019>.
- (53) Cazón, P.; Manuel Vázquez, . Mechanical and Barrier Properties of Chitosan Combined with Other Components as Food Packaging Film. *Environmental Chemistry Letters* **2020**, *18*, 257–267. <https://doi.org/10.1007/s10311-019-00936-3>.
- (54) Irastorza, A.; Zarandona, I.; Andonegi, M.; Guerrero, P.; de la Caba, K. The Versatility of Collagen and Chitosan: From Food to Biomedical Applications. *Food Hydrocolloids* **2021**, *116*, 106633. <https://doi.org/10.1016/J.FOODHYD.2021.106633>.
- (55) Aider, M. Chitosan Application for Active Bio-Based Films Production and Potential in the Food Industry: Review. *LWT - Food Science and Technology* **2010**, *43* (6), 837–842. <https://doi.org/10.1016/J.LWT.2010.01.021>.
- (56) Manigandan, V.; Karthik, R.; Ramachandran, S.; Rajagopal, S. Chitosan Applications in Food Industry. *Biopolymers for Food Design* **2018**, 469–491. <https://doi.org/10.1016/B978-0-12-811449-0.00015-3>.
- (57) Mujtaba, M.; Morsi, R. E.; Kerch, G.; Elsabee, M. Z.; Kaya, M.; Labidi, J.; Khawar, K. M. Current Advancements in Chitosan-Based Film Production for Food Technology; A Review. *International Journal of Biological Macromolecules* **2019**, *121*, 889–904. <https://doi.org/10.1016/J.IJBIOMAC.2018.10.109>.
- (58) Du, W. L.; Xu, Y. L.; Xu, Z. R.; Fan, C. L. Preparation, Characterization and Antibacterial Properties against E. Coli K88 of Chitosan Nanoparticle Loaded Copper Ions. *Nanotechnology* **2008**, *19* (8). <https://doi.org/10.1088/0957-4484/19/8/085707>.

- (59) Ma, Z.; Garrido-Maestu, A.; Jeong, K. C. Application, Mode of Action, and in Vivo Activity of Chitosan and Its Micro- and Nanoparticles as Antimicrobial Agents: A Review. *Carbohydrate Polymers* **2017**, *176*, 257–265. <https://doi.org/10.1016/J.CARBPOL.2017.08.082>.
- (60) Badawy, M. E. I.; Rabea, E. I.; Eid, A. R.; Badr, M. M.; Marei, G. I. K. Structure and Antimicrobial Comparison between N-(Benzyl) Chitosan Derivatives and N-(Benzyl) Chitosan Tripolyphosphate Nanoparticles against Bacteria, Fungi, and Yeast. *International Journal of Biological Macromolecules* **2021**, *186*, 724–734. <https://doi.org/10.1016/J.IJBIOMAC.2021.07.086>.
- (61) Ma, Z.; Garrido-Maestu, A.; Jeong, K. C. Application, Mode of Action, and in Vivo Activity of Chitosan and Its Micro- and Nanoparticles as Antimicrobial Agents: A Review. *Carbohydrate Polymers* **2017**, *176*, 257–265. <https://doi.org/10.1016/J.CARBPOL.2017.08.082>.
- (62) Jeon, S. J.; Oh, M.; Yeo, W. S.; Galvão, K. N.; Jeong, K. C. Underlying Mechanism of Antimicrobial Activity of Chitosan Microparticles and Implications for the Treatment of Infectious Diseases. *PLoS ONE* **2014**, *9* (3). <https://doi.org/10.1371/JOURNAL.PONE.0092723>.
- (63) vanden Braber, N. L.; di Giorgio, L.; Aminahuel, C. A.; Díaz Vergara, L. I.; Martin Costa, A. O.; Montenegro, M. A.; Mauri, A. N. Antifungal Whey Protein Films Activated with Low Quantities of Water Soluble Chitosan. *Food Hydrocolloids* **2021**, *110*, 106156. <https://doi.org/10.1016/J.FOODHYD.2020.106156>.
- (64) Ma, Z.; Garrido-Maestu, A.; Jeong, K. C. Application, Mode of Action, and in Vivo Activity of Chitosan and Its Micro- and Nanoparticles as Antimicrobial Agents: A Review. *Carbohydrate Polymers* **2017**, *176*, 257–265. <https://doi.org/10.1016/J.CARBPOL.2017.08.082>.
- (65) Salama, A.; Hesemann, P. New N-Guanidinium Chitosan/Silica Ionic Microhybrids as Efficient Adsorbent for Dye Removal from Waste Water. *International Journal of Biological Macromolecules* **2018**, *111*, 762–768. <https://doi.org/10.1016/j.ijbiomac.2018.01.049>.
- (66) Wan Ngah, W. S.; Teong, L. C.; Hanafiah, M. A. K. M. Adsorption of Dyes and Heavy Metal Ions by Chitosan Composites: A Review. *Carbohydrate Polymers* **2011**, *83* (4), 1446–1456. <https://doi.org/10.1016/J.CARBPOL.2010.11.004>.
- (67) Zhang, Y.; Zhao, M.; Cheng, Q.; Wang, C.; Li, H.; Han, X.; Fan, Z.; Su, G.; Pan, D.; Li, Z. Research Progress of Adsorption and Removal of Heavy Metals by Chitosan and Its Derivatives: A Review. *Chemosphere* **2021**, *279*, 130927. <https://doi.org/10.1016/J.CHEMOSPHERE.2021.130927>.

- (68) Li, C.; Duan, L.; Cheng, X. Facile Method to Synthesize Fluorescent Chitosan Hydrogels for Selective Detection and Adsorption of Hg²⁺/Hg⁺. *Carbohydrate Polymers* **2022**, *288*, 119417. <https://doi.org/10.1016/J.CARBPOL.2022.119417>.
- (69) Zhuang, S.; Zhu, K.; Xu, L.; Hu, J.; Wang, J. Adsorption of Co²⁺ and Sr²⁺ in Aqueous Solution by a Novel Fibrous Chitosan Biosorbent. *Science of The Total Environment* **2022**, *825*, 153998. <https://doi.org/10.1016/J.SCITOTENV.2022.153998>.
- (70) de Freitas, F. P.; Carvalho, A. M. M. L.; Carneiro, A. de C. O.; de Magalhães, M. A.; Xisto, M. F.; Canal, W. D. Adsorption of Neutral Red Dye by Chitosan and Activated Carbon Composite Films. *Heliyon* **2021**, *7* (7), e07629. <https://doi.org/10.1016/J.HELİYON.2021.E07629>.
- (71) Kauffman, K. J.; Webber, M. J.; Anderson, D. G. Materials for Non-Viral Intracellular Delivery of Messenger RNA Therapeutics. *Journal of Controlled Release* **2016**, *240*, 227–234. <https://doi.org/10.1016/j.jconrel.2015.12.032>.
- (72) Junghans, M.; Kreuter, J.; Zimmer, A. Antisense Delivery Using Protamine–Oligonucleotide Particles. *Nucleic Acids Research* **2000**, *28* (10), e45–e45. <https://doi.org/10.1093/nar/28.10.e45>.
- (73) Yin, H.; Kanasty, R. L.; Eltoukhy, A. A.; Vegas, A. J.; Dorkin, J. R.; Anderson, D. G. Non-Viral Vectors for Gene-Based Therapy. *Nature Reviews Genetics* **2014**, *15* (8), 541–555. <https://doi.org/10.1038/nrg3763>.
- (74) Li, S.; Huang, L. In Vivo Gene Transfer via Intravenous Administration of Cationic Lipid-Protamine-DNA (LPD) Complexes. *Gene Therapy* **1997**, *4* (9), 891–900. <https://doi.org/10.1038/sj.gt.3300482>.
- (75) Metwally, A. A.; Pourzand, C.; Blagbrough, I. S. Efficient Gene Silencing by Self-Assembled Complexes of SiRNA and Symmetrical Fatty Acid Amides of Spermine. *Pharmaceutics* **2011**, *3* (2), 125–140. <https://doi.org/10.3390/pharmaceutics3020125>.
- (76) Aliabadi, H. M.; Landry, B.; Bahadur, R. K.; Neamark, A.; Suwantong, O.; Uludağ, H. Impact of Lipid Substitution on Assembly and Delivery of SiRNA by Cationic Polymers. *Macromolecular Bioscience* **2011**, *11* (5), 662–672. <https://doi.org/10.1002/mabi.201000402>.
- (77) Singha, K.; Namgung, R.; Kim, W. J. Polymers in Small-Interfering RNA Delivery. *Nucleic Acid Therapeutics* **2011**, *21* (3), 133–147. <https://doi.org/10.1089/nat.2011.0293>.

- (78) Moon, J. H.; Mendez, E.; Kim, Y.; Kaur, A. Conjugated Polymer Nanoparticles for Small Interfering RNA Delivery. *Chemical Communications* **2011**, 47 (29), 8370–8372. <https://doi.org/10.1039/c1cc10991j>.
- (79) Ahmed, M. S.; Dutta, R. K.; Manandhar, P.; Li, X.; Torabi, H.; Barrios, A.; Wang, P.; Chinnapaiyan, S.; Unwalla, H. J.; Moon, J. H. A Guanylurea-Functionalized Conjugated Polymer Enables RNA Interference in: Ex Vivo Human Airway Epithelium. *Chemical Communications* **2019**, 55 (54), 7804–7807. <https://doi.org/10.1039/c9cc02856k>.
- (80) Hu, Y.; Du, Y.; Yang, J.; Kennedy, J. F.; Wang, X.; Wang, L. Synthesis, Characterization and Antibacterial Activity of Guanidinylated Chitosan. *Carbohydrate Polymers* **2007**, 67 (1), 66–72. <https://doi.org/10.1016/j.carbpol.2006.04.015>.
- (81) Guțoaia, A.; Schuster, L.; Margutti, S.; Laufer, S.; Schlosshauer, B.; Krastev, R.; Stoll, D.; Hartmann, H. Fine-Tuned PEGylation of Chitosan to Maintain Optimal siRNA-Nanoplex Bioactivity. *Carbohydrate Polymers* **2016**, 143, 25–34. <https://doi.org/10.1016/j.carbpol.2016.01.010>.
- (82) Ragelle, H.; Vandermeulen, G.; Préat, V. Chitosan-Based siRNA Delivery Systems. *Journal of Controlled Release* **2013**, 172 (1), 207–218. <https://doi.org/10.1016/j.jconrel.2013.08.005>.
- (83) Ding, G. Bin; Meng, X.; Yang, P.; Li, B.; Stauber, R. H.; Li, Z. Integration of Polylactide into Polyethylenimine Facilitates the Safe and Effective Intracellular siRNA Delivery. *Polymers (Basel)* **2020**, 12 (2). <https://doi.org/10.3390/polym12020445>.
- (84) Liang, P.; Shen, S.; Xu, Q.; Wang, S.; Jin, S.; Lu, H.; Dong, Y.; Zhang, J. Design, Synthesis Biological Activity, and Docking of Novel Fluopyram Derivatives Containing Guanidine Group. *Bioorganic and Medicinal Chemistry* **2021**, 29 (November 2020), 115846. <https://doi.org/10.1016/j.bmc.2020.115846>.
- (85) Hsu, P. H.; Chiu, D. C.; Wu, K. L.; Lee, P. S.; Jan, J. T.; Cheng, Y. S. E.; Tsai, K. C.; Cheng, T. J.; Fang, J. M. Acylguanidine Derivatives of Zanamivir and Oseltamivir: Potential Orally Available Prodrugs against Influenza Viruses. *European Journal of Medicinal Chemistry* **2018**, 154, 314–323. <https://doi.org/10.1016/j.ejmech.2018.05.030>.
- (86) Protection for the Amino Group. In *Greene's Protective Groups in Organic Synthesis*; John Wiley & Sons, Ltd, 2006; pp 696–926. <https://doi.org/https://doi.org/10.1002/9780470053485.ch7>.
- (87) Yuan, C.; Williams, R. M. *An Efficient Method for the Preparation of Amidinoureas*; 1996; Vol. 37.

- (88) Levauet, C.; Lerpiniere, J.; Ko, S. Y. *The HgCl₂-Promoted Guanylation Reaction: The Scope and Limitations*; 1997; Vol. 53.
- (89) Cunha, S.; Âsa, M.; Costa, B.; Napolitano, H. B.; Lariucci, C.; Vencato, I. *Study of N-Benzoyl-Activation in the HgCl₂-Promoted Guanylation Reaction of Thioureas. Synthesis and Structural Analysis of N-Benzoyl-Guanidines*.
- (90) Kim, K. S.; Qian, L. *Improved Method for the Preparation of Guanidines*; 1993; Vol. 34.
- (91) Wang, C.; He, C.; Luo, Y. H.; Su, S.; Wang, J. Y.; Hong, D. L.; He, X. T.; Chen, C.; Sun, B. W. Efficient Mercury Chloride Capture by Ultrathin 2D Metal-Organic Framework Nanosheets. *Chemical Engineering Journal* **2020**, 379, 122337. <https://doi.org/10.1016/J.CEJ.2019.122337>.

APPENDIX

^1H NMR (400 MHz, D_2O / Acetic acid- d_4 1%) spectrum of unmodified chitosan.

