



## Synthesis variables effect on TiO<sub>2</sub>/polyester fabrics photoactivity and stability

### Efecto de las variables de síntesis de telas de TiO<sub>2</sub>/poliéster sobre su fotoactividad y estabilidad

### Efeito da síntese variables de tecidos TiO<sub>2</sub>/poliéster sobre seu fotoatividade e estabilidade

Edwing Velasco; Camilo A. Castro; Sonia A. Giraldo\*

Centro de Investigaciones en Catálisis (CICAT), Escuela de Ingeniería Química, Universidad Industrial de Santander (UIS), Cra. 27, Calle 9, Bucaramanga, Colombia

\*sgiraldo@uis.edu.co

Fecha Recepción: 26 de mayo de 2015

Fecha Aceptación: 26 de agosto de 2016

#### Abstract

TiO<sub>2</sub>-SiO<sub>2</sub> coatings on fabric samples were obtained by immersion of 9cm<sup>2</sup> of commercial polyester in a TiO<sub>2</sub>-SiO<sub>2</sub> suspension. This suspension was prepared by adding TiO<sub>2</sub> P25 to a silica matrix obtained from the hydrolysis of tetraethyl orthosilicate (TEOS). The aim of this work was to study the relationship between the immersion time of the fabric on the photocatalytic activity and stability of the coating against several cycles of use and washing. Obtained samples were characterized by scanning electron microscopy (SEM), energy dispersive spectroscopy (EDS) and infrared spectroscopy (FTIR-ATR). Evaluation of modified fabrics was performed by self-disinfection tests under 250W/m<sup>2</sup> of simulated sunlight using *E. coli* as model bacteria. In general, all modified fabrics (except that obtained at 2h immersion time) inactivated bacteria in less than 120min and its regrowth was prevented for at least 24h after the disinfection tests. It was determined that low immersion time (3-4h) lead to active and stable fabrics to 3 cycles of use and washing, whereas higher immersion times (12h) lead to more active but unstable fabrics.

**Keywords:** coated fabric, TiO<sub>2</sub>-SiO<sub>2</sub>, photocatalysis, *E. coli* inactivation.

#### Resumen

Muestras de tela recubiertas con TiO<sub>2</sub>-SiO<sub>2</sub> fueron obtenidas por inmersión de un poliéster comercial de 9cm<sup>2</sup> en una suspensión de TiO<sub>2</sub>-SiO<sub>2</sub>. Esta suspensión se preparó adicionando TiO<sub>2</sub> P25 a una matriz de sílice sintetizada mediante la hidrólisis de ortosilicato de tetraetilo (TEOS). El objetivo de este trabajo fue estudiar la relación entre el tiempo de inmersión de la tela, y la actividad fotocatalítica y estabilidad del recubrimiento a varios ciclos de uso y lavado. Las muestras obtenidas fueron caracterizadas por microscopía electrónica de barrido (SEM), espectroscopía de energía dispersiva (EDS) y espectroscopía infrarroja (FTIR-ATR). La evaluación de los textiles se llevó a cabo mediante pruebas de autodesinfección bajo 250W/m<sup>2</sup> de luz solar simulada usando *E. coli* como microorganismo modelo. En general, todas las telas modificadas (excepto las obtenidas con 2h de inmersión) inactivaron la bacteria en menos de 120min, previniendo su recrecimiento bacteriano al menos por 24h después de las pruebas de desinfección. Se determinó que los tiempos de inmersión bajos (3-4h) dejan telas activas y estables a 3 ciclos de uso y lavado, mientras que tiempos de inmersión más altos (12h) dejan telas más activas pero inestables.

**Palabras clave:** tela recubierta, TiO<sub>2</sub>-SiO<sub>2</sub>, fotocatalisis, inactivación de *E.coli*.

## Resumo

Amostras de tecido revestidas com  $\text{TiO}_2\text{-SiO}_2$  foram obtidas por imersão de um poliéster comercial de  $9\text{cm}^2$  em uma suspensão de  $\text{TiO}_2\text{-SiO}_2$ . Esta suspensão foi preparada por adição de  $\text{TiO}_2$  P25 a uma matriz de sílica sintetizado por hidrólise de ortossilicato de tetraetilo (TEOS). O objetivo deste trabalho foi estudar a relação entre o tempo de imersão do tecido, e a atividade fotocatalítica e a estabilidade do revestimento a vários ciclos de utilização e de lavagem. As amostras obtidas foram caracterizadas por microscopia eletrônica de varredura (MEV), espectroscopia por dispersão de energia (EDS) e espectroscopia no infravermelho (FTIR-ATR). A avaliação dos tecidos foi realizada por meio de testes de autodesinfecção sob a luz solar simulada a utilização de *E. coli* como um modelo microrganismo. Em geral, todos os tecidos modificados (exceto aqueles obtidos com 2h de imersão) inativar bactérias dentro de 120min de irradiação, impedindo o seu novo crescimento bacteriano de pelo menos 24h após o teste de desinfecção. Encontrado que com tempos de imersão de baixo (3-4h) são obtidos tecidos ativos e estáveis a 3 ciclos de utilização e de lavagem, enquanto que os tempos de imersão mais elevado (12h) são obtidos tecidos mais ativos mais instáveis.

**Palabras-chave:** tecido revestido,  $\text{TiO}_2\text{-SiO}_2$ , fotocatalise, inativação de *E. coli*.

## Introduction

A self-disinfecting fabric has the ability to inactivate pathogenic microorganisms such as *E. coli* because on its surface a photocatalyst such as  $\text{TiO}_2$  is fixed and ready to be activated in the presence of UV light, thus leading to the production of oxidative species that attack the cell wall, and cause lysis and death of the microorganism [1-6].

The development of these fabrics, as a strategy to combat the spread of nosocomial infections [7-11], is still in the primary state due to difficulties to immobilize  $\text{TiO}_2$  on the fabric surface, so as to keep it active and stable for several cycles of use and washing [12-14]. Different alternatives have been explored in order to overcome this issue. The use of bonding agents such as silica is one of the most attractive ideas due of its usability and low cost [15-19]. In this case, the linker has two functions: trap  $\text{TiO}_2$  particles and strongly adhere them to the fabric, allowing UV light activation of the semiconductor.

In 2008, Li *et al.* [20] studied the interaction between silica and certain fabrics such as cotton, linen, nylon and polyester, and determined that the adhesion of the coatings of  $\text{SiO}_2$  in synthetic fabrics is mainly the result of thermodynamic affinities, dipole-dipole interactions and hydrogen bonds, while the adhesion over fabrics based on cellulose is produced by covalent bonds formed between the precursor groups of the silica and hydroxyl groups of the fabric. In 2010, Mejia *et al.* [21] reported that different fabric samples coated by the immersion of polyester in a suspension of  $\text{TiO}_2\text{-SiO}_2$  were sufficiently active to degrade gaseous methanol. They also found a relationship

between the immersion time of the fabric and its photocatalytic activity.

Despite of the progress made by these authors regarding immobilization of  $\text{TiO}_2$ , it is still necessary to study the behavior of fabrics coated with  $\text{TiO}_2\text{-SiO}_2$  on self-disinfection processes and their stability during several cycles of use and washing. For this reason, the focus of this paper is to obtain self-disinfecting fabrics by immersion of polyester samples in  $\text{TiO}_2\text{-SiO}_2$  suspensions and determine the influence of immersion time on the activity and stability during three cycles of use and washing.

## Experimental

### Preparation of $\text{SiO}_2\text{-TiO}_2$ suspension

According to the procedure described by Mejia *et al.* [21], the  $\text{TiO}_2\text{-SiO}_2$  suspension was prepared in two steps: first, a sol-gel of  $\text{SiO}_2$  was prepared by ageing during 24h of isopropyl alcohol (isop-OH, Merck), hydrochloric acid (HCl, Merck), tetraethyl orthosilicate (TEOS, Merck) and distilled water. Second,  $\text{TiO}_2$  P-25 (Evonik-Degussa) with surface area of  $50\text{m}^2/\text{g}$  and gap energy of 3.2eV [5,12] was added to sol-gel of  $\text{SiO}_2$  under conditions of constant stirring (100rpm). The following molar ratios were used: isop-OH/TEOS=4.86, HCl/TEOS=0.04,  $\text{TiO}_2/\text{Si}$ =0.014 and distilled water/TEOS=1.97.

### Modification of PE samples with $\text{TiO}_2\text{-SiO}_2$

It was used one type of commercial polyester fabric (PE, polyester:cotton 65:35). Fabric samples of  $9\text{cm}^2$  were coated with  $\text{TiO}_2\text{-SiO}_2$  by a single immersion in the  $\text{TiO}_2\text{-SiO}_2$  suspension during a variable time between 2 to 12h, to adhere

different amounts of TiO<sub>2</sub>-SiO<sub>2</sub> in the fabric. During immersion, the suspension is kept stirred at 100rpm to keep homogeneity and prevent precipitation of TiO<sub>2</sub>. Afterwards, the sample was removed from the suspension and dried in stove at 30±2°C for 15min. Finally, the TiO<sub>2</sub>-SiO<sub>2</sub> coated sample was soaked in distilled water and dried in oven at 100°C. The weakly adhered coating particles were detached from the fabric by washing with water under sonication (model LC-ULTRASONICS ELMA 30H) for 15min at 60Hz. The fixed TiO<sub>2</sub>-SiO<sub>2</sub> in the fabric was determined by difference in weight of the fabric before and after the coating process.

#### Characterization of fabric samples

Samples were analyzed by scanning electron microscopy (SEM) by using a FEI Quanta FEG TM model 650 provided with a BS-SE-detector and an energy dispersive spectrometer (EDS), under high vacuum (6x10<sup>-4</sup>Pa) and vacuum (10-130Pa) conditions, resolution of 6 to 100000x, voltage of 200V to 30kV and peak current continuously adjustable ≤200nA. Infrared spectroscopy (ATR-FTIR) was done using an Attenuated Total Reflectance cell (ATR) equipped with a ZnSe crystal to avoid damage of the polyester. The equipment used to perform spectroscopy was a Bruker Tensor 27 FTIR model supplemented with Bruker ATR Platinum.

#### Evaluation of photocatalytic activity of TiO<sub>2</sub>-SiO<sub>2</sub> coated samples

**Bacterial suspension.** The bacterial strain used as model microorganism was *E. Coli* ATCC 11229 (*E. coli*) provided by Microbiologics® Inc. This microorganism was preserved in cryobanks at -70°C. Two bacterial colonies from cryobank were inoculated into 5mL of nutrient medium Luria Bertani (LB) and incubated for 8h at 35°C with constant aerobic agitation of 100rpm. Then, the incubated culture broth was added to 25mL of fresh LB and remained in growth for 15h at the same temperature and stirring conditions until reaching the stationary growth phase. Subsequently, 1mL of the resulting culture was centrifuged at 3000rpm for 15min, as a result a biomass pellet was obtained to be twice washed with sterile saline solution (0.85g NaCl diluted in 100mL of distilled water). Finally, the washed biomass pellet was suspended in 1mL of sterile water, reaching a concentration of approximately 10<sup>7</sup> colony forming units (CFU)/mL.

**Fabrics Self-disinfection tests.** Duplicate modified PE samples, were contaminated with 100mL of bacterial suspension with a concentration of 10<sup>7</sup>CFU/mL (C<sub>0</sub>). Then, samples were irradiated at 250W/m<sup>2</sup> in a solar simulation chamber (SUNTEST CPS+, with temperature control, radiation between 300-800nm with 7% of photons emitted in the UV-A to B ranges and no photons emitted in UV-C range). Samples were withdrawn from the chamber at different times up to 120min to track their photodisinfection efficiency. Quantification of microorganisms in each sample (C) was conducted by the technique of serial dilutions, sowing on plate count agar (Merck) and plate count by microdroplet [22].

Additionally, the following control tests were performed: first, disinfection test without irradiation, second, disinfection test with the polyester fabric unmodified, third, disinfection test with the polyester fabric coated with SiO<sub>2</sub>.

**Stability of modified PE samples.** The self-disinfection test of each sample was performed 3 times in a row (reuses) in order to determine the stability of the coating. Before each reuse, the coated fabric was washed with distilled water to remove residual organic material from the preceding disinfection.

Moreover, the percentage of detachment TiO<sub>2</sub>-SiO<sub>2</sub> from modified PE samples (% Detachment) during the first use was determined. The following formula was used: %*Detachment* = ((W<sub>b</sub>-W<sub>a</sub>) / W<sub>b</sub>)\*100, where W<sub>b</sub> and W<sub>a</sub> mean weight before and after first use, respectively.


**Effective disinfection time (EDT<sub>24</sub>).** After each self-disinfection test it was determined the EDT<sub>24</sub> for all the modified PE samples. In this case, the samples that were subjected to disinfection tests are stored in dark for 24h. After this time regrowth microorganisms on the sample is quantified. EDT<sub>24</sub> determination was used as an indication of any microorganism regrowth after 24h of no light irradiation after the photocatalytic treatment [5,6].

## Results and Discussion

Figure 1 shows SEM micrographs of: a) unmodified PE sample and b) to d) modified PE sample with 4h immersion time in different approaches. By comparing the a) and b) micrographs it is observed

that the modification of PE sample produces a thick and cracked coating of  $\text{TiO}_2\text{-SiO}_2$ . The c) and d) micrographs shows that  $\text{TiO}_2\text{-SiO}_2$  coating is also amorphous and porous. It was determined in the

SEM-EDS analysis that this coating is composed by a  $\text{TiO}_2/\text{Si}$  mass ratio of 2.26 which is similar to that used in the synthesis of the coating. Figure 2 presents FTIR-ATR spectra of modified

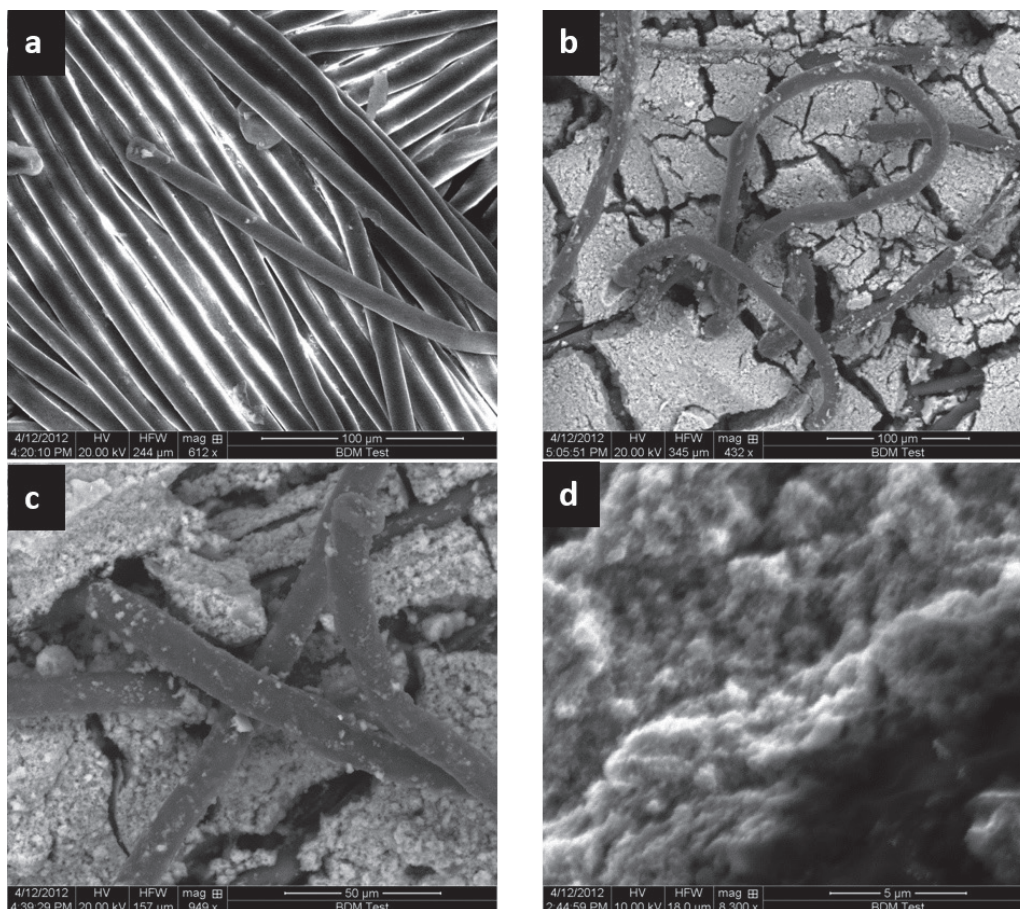


**Figure 1.** SEM images of the unmodified PE sample (a) and modified PE with 4h immersion at different magnifications (b)-(d).

PE samples with  $\text{TiO}_2\text{-SiO}_2$  to different immersion times. All spectra have the same peaks with different intensities. In general the bands shown in IR spectra are attributed to both fabric functional groups and coating species.

First, the bands at  $1713\text{cm}^{-1}$ , and  $1300\text{-}1600\text{cm}^{-1}$  are associated to vibrations of saturated esters due to carbonyl groups ( $-\text{C}=\text{O}$ ), and  $-\text{C}-\text{H}$  bonds associated to the benzene ring [2], respectively. Second, there are bands at  $810$  and  $1095\text{cm}^{-1}$  ascribed to symmetric vibration of  $\text{Si}-\text{O}-\text{Si}$  and to asymmetric stretching of  $\text{Si}-\text{O}-\text{Si}$ , respectively [23-25]. The band at  $1254\text{cm}^{-1}$  is associated with disorder modes of  $\text{SiO}_2$  amorphous layers [25]. The band at  $720\text{cm}^{-1}$  is attributed to  $\text{TiO}_2$  [4,24]. Additional bands are observed in the ranges  $3000\text{-}$

$3800$ ,  $1610\text{-}1650$ ,  $850\text{-}990\text{cm}^{-1}$ . The band located in the first range corresponds to fundamental stretching vibration of the hydroxyl groups.



These hydroxyl groups derived from adsorbed water ( $3400\text{-}3500\text{cm}^{-1}$ ), silanols linked to molecular water through hydrogen bonds ( $3540\text{cm}^{-1}$ ), and Si and OH pairs mutually linked by hydrogen bonds and internal silanol ( $3660\text{cm}^{-1}$ ) [26]. The second range is assigned to the deformation of molecular water. There is a contribution near to  $1650\text{cm}^{-1}$  which may be due to residual ethanol. The third range is associated with silanol bonds vibration ( $\text{Si}-\text{OH}$ ) [25,26]. The Peak in the  $2800\text{-}2980\text{cm}^{-1}$  region is associated to  $\text{C}-\text{H}$  stretching vibrations of  $\text{CH}_3$  and  $\text{CH}_2$  attributed to the PE sample structure or contamination [17].

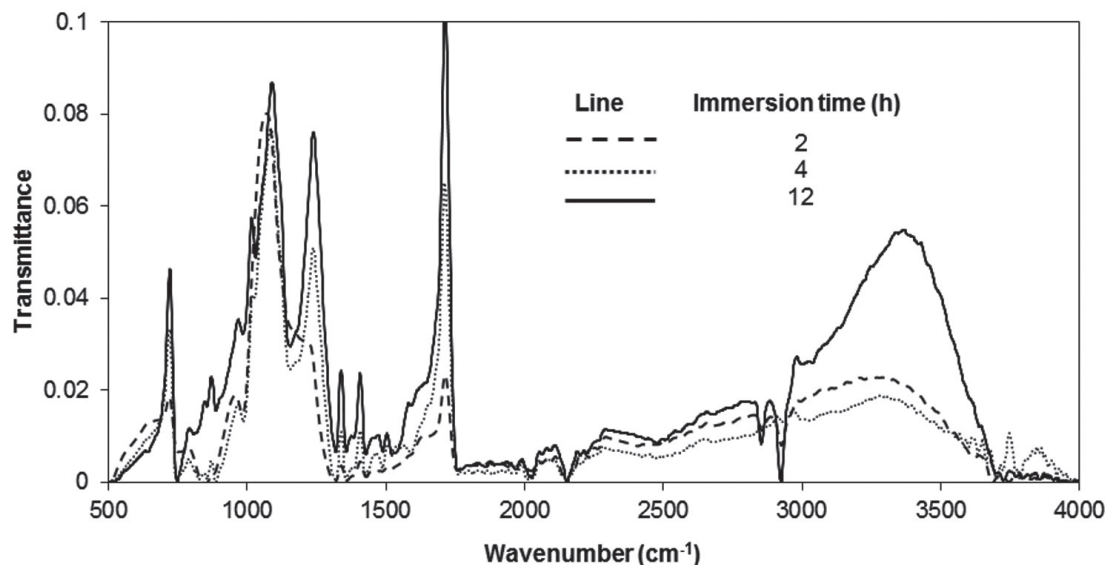

**Figure 2.**ATR-FTIR spectra for modified PE samples with immersion time of 2, 4 and 12h.

The presence of *Si-O-Si* and *Si-OH* in the samples analyzed by FTIR-ATR confirms that during the preparation of the sol-gel of  $\text{SiO}_2$ , hydrolysis and polycondensation reactions occurred as shown in Equations 1 to 3 [24,25].

According to Mejia *et al.* [21], these reactions lead to the formation of a three-dimensional network of  $\equiv \text{Si-O-Si} \equiv$ . The principal function of this network is to trap the  $\text{TiO}_2$  and keep it stationary on the fabric such as it is observed in SEM analysis.



On the other hand, Figure 2 shows that the intensity of both  $\text{TiO}_2$  and *Si-O-Si* symmetric vibration peaks increases with immersion time but the intensity of *Si-O-Si* asymmetric stretching peak is similar for all analyzed samples. These results indicate that the increase of immersion time causes an increment in the disorder modes of the  $\text{SiO}_2$  network that it is associated to increase in the  $\text{TiO}_2$  peak.


#### Photocatalytic activity and coating loss of modified PE samples: effect of immersion time

Figure 3 shows the amount of adhered  $\text{TiO}_2\text{-SiO}_2$  to each PE sample as a function of the immersion time. An increase in the amount of adhered coating on fabric is observed when increasing immersion time. There was a raise in adhesion between 4 and 5.5h in relation to others immersion times. In contrast, the adhesion of the coating tends to stabilize for immersion time nearby to 12h. This


stabilization indicates that adhesion limit of  $\text{TiO}_2\text{-SiO}_2$  in PE samples is nearby to  $25\text{mgcm}^{-2}$ .

Figure 4 shows the relationship between immersion time and photocatalytic activity of modified PE samples. It is observed that after 3h of immersion time the modified PE samples can inactivate *E. coli* ( $10^7\text{CFU/mL}$ ) and achieve effective disinfection in times less than 120min under  $250\text{W/m}^2$  of simulated sunlight irradiation.

Furthermore, the photocatalytic activity increases with the amount of adhered coating and this one increases with time of immersion as previously observed, although this tendency is not notable between samples with 4 and 5.5h immersion time which have a similar photocatalytic activity. In all cases the  $\text{EDT}_{24}$  was equal to the inactivation time shown in Figure 4 indicating that the inactivation of *E. coli* was complete.

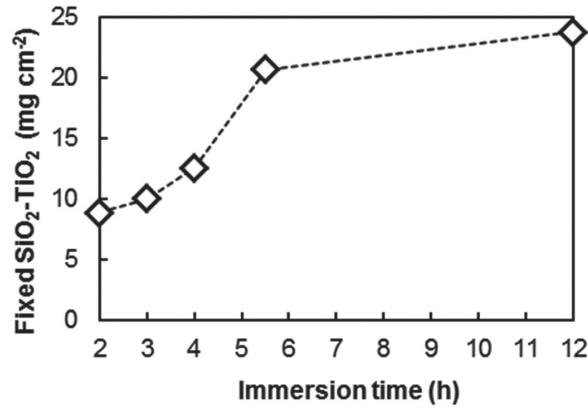

**Figure 3.** Adhered TiO<sub>2</sub>-SiO<sub>2</sub> to modified PE samples with different immersion times.

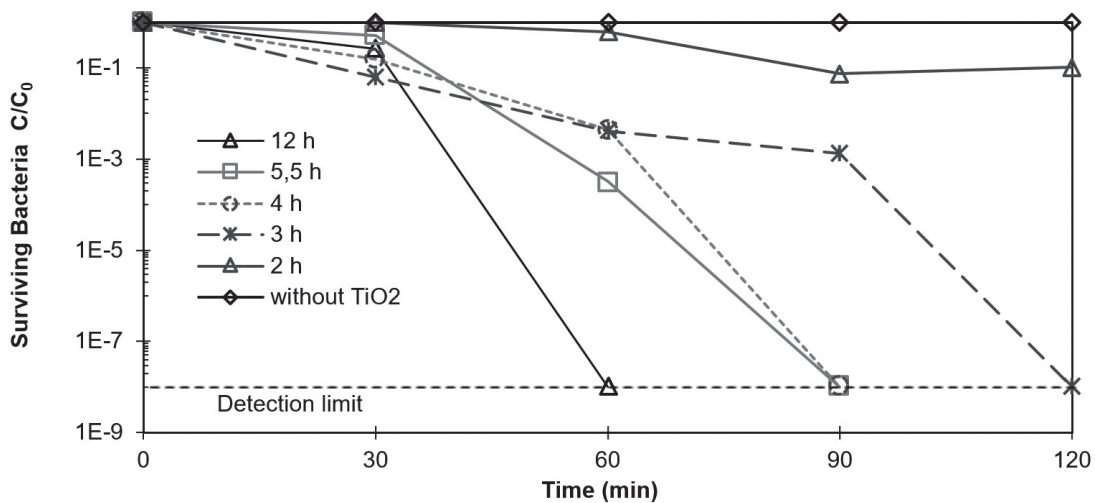

**Figure 4.** *E. coli* inactivation by effect of photocatalytic activity of the modified PE samples at different immersion times.

Inactivation of *E. coli* and effective disinfection of samples was due to TiO<sub>2</sub> presence in the samples, which was observed by SEM-EDS. Since the nature of TiO<sub>2</sub> P25 was not modified as shown in IR analysis, it is expected that when irradiated with UV light below  $\lambda < 385\text{nm}$  (UV-A to B range) in the presence of water or air this semiconductor generates oxidizing radical species (OH<sup>\*</sup>, O<sub>2</sub><sup>\*</sup>) able to degrade the cell wall of microorganisms [5,12,27]. These processes of radicals formation occurs only in the surface of coating because the TiO<sub>2</sub> particles located inside the SiO<sub>2</sub> matrix of TiO<sub>2</sub>-SiO<sub>2</sub> coating do not have access to the incident light. In this case the TiO<sub>2</sub> particles are not photoactivated [28]. Therefore, due to different morphologies, as observed in Figure 1, it is expected that semiconductor coverage do not allow the photocatalytic activation of the entire

coating on the fabrics.

An unexpected behavior is observed in modified PE samples with 5.5 and 12h immersion time since it was found a low difference in TiO<sub>2</sub>-SiO<sub>2</sub> adhesion (Figure 3) but a significant difference in photocatalytic activity compared to other samples. This behavior evidences that the photocatalytic activity of modified PE samples may depend on the TiO<sub>2</sub>/SiO<sub>2</sub> ratio in the coating surface. Mejia *et al.* [21] showed that samples with immersion times up to 11h increase in %TiO<sub>2</sub> loading compared with lower immersion times. Here, a different result was observed for samples with 4 and 5.5h immersion time that show a higher difference in TiO<sub>2</sub>-SiO<sub>2</sub> adhesion (Figure 3) but a negligible difference in photocatalytic activity as compared to higher immersion times. These samples have different amounts of TiO<sub>2</sub>-SiO<sub>2</sub> as shown in Figure 3, but

have a similar amount of  $\text{TiO}_2$  in the coating surface. This indicates that increasing the immersion time cause a variation in the adhesion of the  $\text{TiO}_2$ - $\text{SiO}_2$  and a variation in the  $\text{TiO}_2/\text{SiO}_2$  ratio of the coating surface, as well as it was observed by Selishchev *et al.* [29].

Another determining factor on the sample photoactivity is the adsorbed water on the coating because, as it explain above, the water is necessary for the production of oxidants species (Equation 2) that cause bacterial inactivation. FTIR-ATR analysis showed that the adsorbed water increases with the immersion time. Therefore, the increase of the photoactivity with immersion time can also be associated to the increment in the adsorbed water amount.


Table 1 shows the percentage of detached coating from the modified PE samples during the first use. The samples with 2, 3 and 4h had negligible losses but samples with 5.5 and 12h immersion times have considerable losses. This indicates that increasing the immersion time causes a decrease in the adhesion strength of the aggregates located on the coating surface, possibly because it reaches the adhesion limit of  $\text{TiO}_2$ - $\text{SiO}_2$  in PE samples, as previously discussed. Such a decrease in the resistance of the coating may be associated with the increased vibrations related with disordered modes of amorphous  $\text{SiO}_2$  observed by FTIR-ATR analysis.

**Table 1.**  $\text{TiO}_2$ - $\text{SiO}_2$  detachment during the first use of the modified PE samples with different immersion time.

Immersion time (h)	% Detachment
2	0.2
3	0.3
4	0.3
5.5	5
12	10

**Photocatalytic stability of modified PE sample**

Figure 5 shows the results of first, second and third use of the modified PE samples with 4h immersion time. Control test indicate that both the unmodified PE sample under irradiation and the modified PE sample in obscurity have no photoactivity, therefore, the photocatalytic activity of the modified PE samples with 4h immersion time in the three uses was caused by  $\text{TiO}_2$  presence. An important difference is observed between the result of first and second use which could be associated to a low detachment of  $\text{TiO}_2$  as shown in Table 1. A different result is observed between second and third use where it is not shown variation on photoactivity indicating that the  $\text{TiO}_2$ - $\text{SiO}_2$  coating did not suffer significant changes during the evaluation and washing procedures. The similarity in the results presented in Figure 5 indicates that the fabrics are stable at least until the third use.

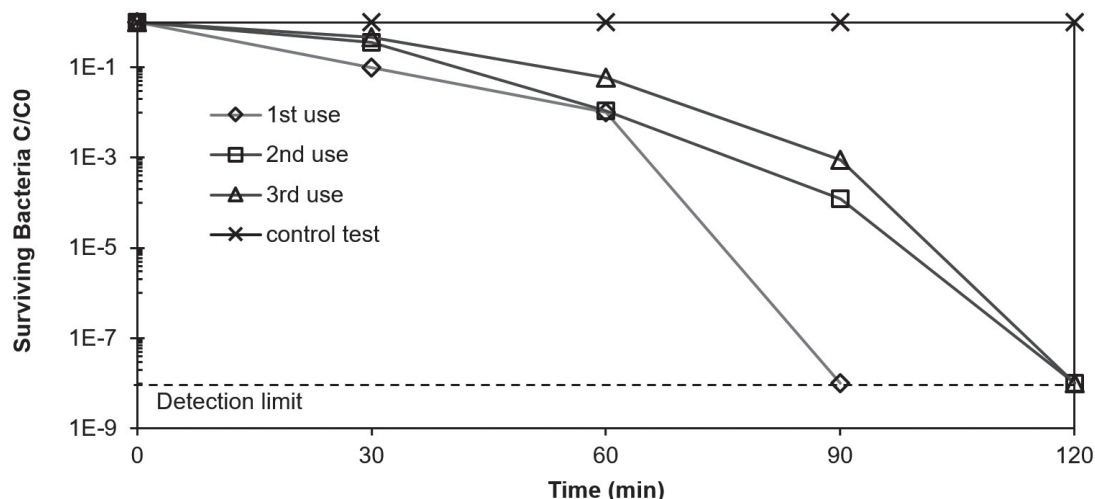

**Figure 5.** Photocatalytic activity of the modified PE sample with 4h immersion time in first, second and third use.

This stability is related with  $-Si-O-Si-$  groups from  $SiO_2$  present in the coating as observed in IR analyses, these groups have the function of trapping the  $TiO_2$  and keep it immobile over the fabric surface. Several authors have mentioned that the modified fabric without  $SiO_2$  shows  $TiO_2$  detachment and indeed a total loss of photoactivity caused by reuse of modified sample [19]. Accordingly, the detached coating from modified PE sample between the first and second use could be  $TiO_2$  deposited in the coating surface that wasn't trapped by  $SiO_2$  matrix

### Conclusion

The use of a  $SiO_2$  matrix obtained by the hydrolysis of TEOS, as a binder between the commercial polyester and  $TiO_2$  allows the modified fabric to remain active and stable during self-disinfection tests.  $TiO_2$ - $SiO_2$ /PE samples inactivate an *E. coli* inoculum ( $10^7$ CFU/mL) in times of 120min under constant irradiation of  $250W/m^2$ . The immersion time of the fabric in the  $TiO_2$ - $SiO_2$  suspension is directly related to the self-disinfecting activity of the  $TiO_2$ - $SiO_2$ /PE. High immersion times (12h) lead to highly active but unstable samples, whereas smaller immersion times (2-4h) lead to less active but stable fabrics during three cycles of use and washing.

### Acknowledgements

This work was possible due to financial support of the VIE-UIS in the frame of the project: "Desarrollo de textiles con propiedades fotobactericidas y de autolimpieza a base de  $TiO_2$  algodón y/o poliéster", VIE-UIS, code 1317.

Authors especially thank L.H. Claro Ortiz and S.A. Gamboa Cáceres for their collaboration during experimental runs.

### References

- [1] Bozzi A, Yuranova T, Guasaquillo I, Laub D, Kiwi J. Self-cleaning of Cotton Textiles Modified with  $TiO_2$  at Low Temperatures under Daylight Irradiation. *J. Photochem. Photobiol. C.* 2005;174:156–64.
- [2] Yuranova T, Laub D, Kiwi J. Synthesis, activity and characterization of textiles showing self-cleaning activity under daylight irradiation *Catal. Today.* 2007;122:109–17.
- [3] Wu D, Long M, Zhou J, Cai W, Zhu X, Chen C, *et al.* Synthesis and characterization of self-cleaning cotton fabrics modified by  $TiO_2$  through a facile approach. *Surf. Coat. Technol.* 2009;203:3728–33.
- [4] Mejía MI, Marín JM, Restrepo G, Pulgarín C, Kiwi J. Photocatalytic evaluation of  $TiO_2$ /nylon systems prepared at different impregnation times. *Catal. Today.* 2011;161:15-22.
- [5] Rincón AG, Pulgarín C. Absence of *E. coli* regrowth after  $Fe^{3+}$  and  $TiO_2$  solar photoassisted disinfection of water in CPC solar photoreactor. *Catal. Today.* 2007;124:204–14.
- [6] Moncayo-Lasso A, Torres-Palma RA, Kiwi J, Benítez N, Pulgarín C. Bacterial inactivation and organic oxidation via immobilized photo-Fenton reagent on structured silica surfaces. *Appl. Catal. B.* 2008;84:577–83.
- [7] Acosta S, Aragón JC, Benoit SR, Betancourt MI, Clara LI, Costa SF, *et al.* Evaluación de la infección hospitalaria en siete países latinoamericanos *Rev. Panam. Infectol.* 2008;10(4):112-22.
- [8] Struelens MJ, Denis O, Rodriguez-Villalobos H. Microbiology of nosocomial infections: progress and challenges. *Microbes Infect.* 2004;6:1043-8.
- [9] Sligl W, Taylor G, Brindley PG. Five years of nosocomial Gram-negative bacteremia in a general intensive care unit: epidemiology, antimicrobial susceptibility patterns, and outcomes. *Int. J. Infect. Diseases.* 2006;10(4):320-5.
- [10] Cáceres Manrique FM, Díaz Martínez LA. Incidencia de infección nosocomial, ESE Hospital Universitario Ramón González Valencia, 1995-2000. *MEDUNAB.* 2002;5(13):5-13.
- [11] Del Río J, Buriticá O. Evaluación de un sistema de vigilancia epidemiológica y riesgos de infección intrahospitalaria en pacientes quirúrgicos. *Colombia Médica.* 2000;31(2):71-6.
- [12] Montazer M, Pakdel E. Functionality of nano titanium dioxide on textiles with future aspects: Focus on wool. *J. Photochem. Photobiol. C.* 2011;12(4):293–303.
- [13] Dastjerdi R, Montazer M. A review on the application of inorganic nano-structured materials in the modification of textiles: Focus on anti-microbial properties. *Colloids Surf. B.* 2010;79(1):5-18.



- [14] Shan AY, Ghazi TIM, Rashid SA. Immobilisation of titanium dioxide onto supporting materials in heterogeneous photocatalysis: A review. *Appl. Catal. A*. 2010;389:1-8.
- [15] Liu B, Wang Z, He J. SiO<sub>2</sub>/TiO<sub>2</sub> multilayer films grown on cotton fibers surface at low temperature by a novel two-step process. *Mater. Lett.* 2012;67:8–10.
- [16] Bellardita M, Addamo M, Di Paola A, Marci G, Palmisano L, Cassar L, *et al.* Photocatalytic activity of TiO<sub>2</sub>/SiO<sub>2</sub> systems. *J. Hazard. Mater.* 2010;174:707–13.
- [17] Fakin D, Veronovski N, Ojstrsek A, Bozic M. Synthesis of TiO<sub>2</sub>-SiO<sub>2</sub> colloid and its performance in reactive dyeing of cotton fabrics. *Carbohydr. Polym.* 2012;88:992–1001.
- [18] Nakano R, Chand R, Obuchi E, Katoh K, Nakano K. Performance of TiO<sub>2</sub> photocatalyst supported on silica beads for purification of wastewater after absorption of reflow exhaust gas. *Chem. Eng. J.* 2011;176–177:260–4.
- [19] Lim LL, Lynch RJ, In SI. Comparison of simple and economical photocatalyst immobilization procedures. *Appl. Catal. A*. 2009;365:214–21.
- [20] Li F, Xing Y, Ding X. Silica xerogel coating on the surface of natural and synthetic fabrics. *Surf. Coat. Technol.* 2008;202(19):4721–7.
- [21] Mejía MI, Marín JM, Restrepo G, Rios LA, Pulgarín C, Kiwi J. Preparation, testing and performance of a TiO<sub>2</sub>/polyester photocatalyst for the degradation of gaseous methanol. *Appl. Catal. B*. 2010;94(1-2):166–72.
- [22] Weenk GH. Microbiological assessment of culture media: comparison and statistical evaluation of methods. *Int. J. Food Microbiol.* 1992;17(2):159-81.
- [23] Pakdel E, Daoud WA. Self-cleaning cotton functionalized with TiO<sub>2</sub>/SiO<sub>2</sub>: Focus on the role of silica. *J. Colloid Interface Sci.* 2013;401:1–7.
- [24] Permpoon S, Houmard M, Riassetto D, Rapenne L, Berthomé G, Baroux B, *et al.* Natural and persistent superhydrophilicity of SiO<sub>2</sub>/TiO<sub>2</sub> and TiO<sub>2</sub>/SiO<sub>2</sub> bi-layer films. *Thin Solid Films.* 2008;516(6):957–66.
- [25] Martínez JR, Ruiz F. Mapeo estructural de sílica xerogel utilizando espectroscopia infrarroja. *Revista Mexicana de Física.* 2002;48(2):142-9.
- [26] Jaroenworoluck A, Pijarn N, Kosachan N, Stevens R. Nanocomposite TiO<sub>2</sub>-SiO<sub>2</sub> gel for UV absorption. *Chem. Eng. J.* 2012;181–182:45–55.
- [27] Rincón AG, Pulgarín C. Effect of pH, inorganic ions, organic matter and H<sub>2</sub>O<sub>2</sub> on *E. coli* K12 photocatalytic inactivation by TiO<sub>2</sub>: Implications in solar water disinfection. *Appl. Catal. B.* 2004;51(4):283–302.
- [28] Pulgarín C, Kiwi J, Nadtochenko V. Mechanism of photocatalytic bacterial inactivation on TiO<sub>2</sub> films involving cell-wall damage and lysis. *Appl. Catal. B.* 2012;128:179–83.
- [29] Selishchev DS, Karaseva IP, Uvaev VV, Kozlov DV, Parmon VN. Effect of preparation method of functionalized textile materials on their photocatalytic activity and stability under UV irradiation. *Chem. Eng. J.* 2013; 224:114–20.